MILITARY SPECIFICATION

TILE, PLASTIC, FIRE-RETARDANT

This specification is approved for use by the Naval Sea Systems Command and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 This specification covers fire-retardant plastic tile for covering interior ship decks (including submarine), or any other purpose as may be required.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

FEDERAL
PPP-B-636 - Boxes, Shipping, Fiberboard.

MILITARY
MIL-C-45662 - Calibration System Requirements.

STANDARDS

FEDERAL
FED-STD-501 - Floor Coverings, Resilient, Nontextile: Sampling and Testing.

MILITARY
MIL-STD-129 - Marking for Shipment and Storage.
MIL-STD-1623 - Fire Performance Requirements and Approved Specifications for Interior Finish Materials and Furnishings (Naval Shipboard Use).

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

UNIFORM CLASSIFICATION COMMITTEE, AGENT
Uniform Freight Classification Rules

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Sample for first article inspection. Prior to beginning production, a sample shall be tested as specified in 4.4 (see 6.2).

3.2 Material. The tile shall consist of a thoroughly-blended composition of thermoplastic binder; filler, such as asbestos; and pigment. The thermoplastic binder shall consist of a polyvinyl chloride resin, or a copolymer resin (made by copolymerizing vinyl chloride with monomeric materials such as vinyl acetate, vinylidene chloride, di-ethyl-maleate), or a rubber base material compounded with plasticizers and stabilizers. Physical properties of the tile shall be in accordance with table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

Table I - Physical requirements.

Property	Requirement	Requirement paragraph	Test paragraph	Associated test method FED-STD-501
Surface tack	No tack	3.3	4.6.2	
Size, inches	9 by 9 or 12 by 12	3.4	4.6.13	2231
Thickness, inches	3/32 or 1/8	3.5	4.6.4	2111 or 2131 [1/]
Indentation at 77°F	See table II	3.6	4.6.5	3211 [1/]
1 minute, inch, min		3.6.1		
10 minutes, inch, min		3.6.2		
Indentation at 115°F inch, max	0.032	3.7	4.6.6	6311
Impact	No breaking	3.8	4.6.7	3311 [1/]
Flexibility				
before aging, inch, min	1.0	3.9	4.6.8	3111 [1/]
after aging, inch, min	1.0	3.10	4.6.9	3111 [2/]
Dimensional stability, inches per linear foot	0.024	3.11	4.6.10	6211
Volatile material, percent, max	0.5	3.12	4.6.11	9211
Chemical resistance, scratch width, inch, max	0.1	3.13	4.6.12	9311
Squareness, inch, max	0.010	3.14	4.6.3	
Fire performance				
average char, inches, max		3.15	4.6.14	
combustion plus ignition, minutes, max		3.15	4.6.14	
Water, absorption, percent, max	2.5	3.16	4.6.15	
Resistance to wear, inch, max	0.045	3.17	4.6.16	
Color and pattern	As specified, (see 6.1.1)	3.18		
Workmanship		3.19		

[1/] Condition samples as described in method 1041 of FED-STD-501.

[2/] Samples shall be heated or conditioned as described in method 6211 of FED-STD-501.

3.3 Surface tack. The tile shall not exhibit any objectionable surface tack when subjected to the test specified in 4.6.2.

3.4 Size. Unless otherwise specified (see 6.1.1), the tile shall be either 9 by 9 or 12 by 12 inches with a tolerance of plus or minus 0.016 inch. The difference between the length and width shall be no greater than 0.020 inch for any size of tile. Measurements shall be made as specified in 4.6.13.

3.5 Thickness. The tiles shall have a thickness of 3/32-inch (0.0938 inch) or 1/8-inch (0.125 as specified (see 6.1.1), with a tolerance of plus or minus 0.005 inch when measured in accordance with 4.6.4.

3.6 Indentation at 77°F.

3.6.1 One minute. When tested as specified in 4.6.5, the tiles shall have an indentation at the end of 1 minute of not less than 0.006 inch and not more than 0.015 inch.

3.6.2 Ten minutes. When tested as specified in 4.6.5, the indentation at the end of 10 minutes shall be as required in table II (or interpolated therefrom), corresponding to the indentation recorded at the end of one minute.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

Table II - Indentation at 77°F.

Indentation at one minute	Maximum indentation at 10 minutes
Inch	Inch
0.006	0.0100
0.007	0.0112
0.008	0.0124
0.009	0.0137
0.010	0.0149
0.011	0.0162
0.012	0.0174
0.013	0.0186
0.014	0.0197
0.015	0.0209

3.7 Indentation at 115°F. When tested as specified in 4.6.6, tiles shall show an indentation of not more than 0.032 inch at the end of 30 seconds.

3.8 Impact. When tested as specified in 4.6.7, the tile shall not break or crack beyond the limits prescribed.

3.9 Flexibility (before aging). When tested as specified in 4.6.8, the tile shall deflect not less than 1.0 inch both with and across the grain without breaking.

3.10 Flexibility (after aging). When tested as specified in 4.6.9, the tile shall deflect not less than 1.0 inch both with and across the grain without breaking.

3.11 Dimensional stability. When tested as specified in 4.6.10, the tile shall not change in linear dimensions more than plus or minus 0.024 inch per linear foot.

3.12 Volatile material. The loss of volatile material shall not exceed 0.5 percent when tested as described in 4.6.11.

3.13 Chemical resistance. The tile, when exposed to ethyl alcohol, tallow, lubricating oil, cottonseed oil, kerosene, and a solution of sodium hydroxide, and tested as described in 4.6.12, shall have a scratch width not greater than 0.100 inch, and shall have no appreciable change in hue.

3.14 Squareness. The out-of-squareness of the tile shall be not greater than 0.010 inch when subjected to the test specified in 4.6.3.

3.15 Fire performance. The fire performance of the tiles shall conform with the maximum test requirements set forth in MIL-STD-1623 (see 4.6.14).

3.16 Water absorption. The tile shall not absorb more than 2.5 percent water when tested as specified in 4.6.15.

3.17 Resistance to wear. The tile shall show wear not greater than 0.045 inch after 1500 revolutions of the wear test apparatus when tested as specified in 4.6.16.

3.18 Color and pattern. The color and pattern shall be as designated by the procuring activity (see 6.1.1). Color and pattern shall extend through the thickness of the tile (through-pattern). Embossed or surface pattern tile is not acceptable.

3.19 Workmanship. The tile shall be free from defects which affect its appearance or serviceability and shall have straight edges and square corners. The surface of the tiles shall be smooth and free from blemishes, spots, indentations, cracks, blisters, and protrusions.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

(a) First article inspection (see 4.4).
(b) Quality conformance inspection (see 4.5).

4.3 Test equipment and inspection facilities. Test and measuring equipment and inspection facilities of sufficient accuracy, quality and quantity to permit performance of the required inspection shall be established and maintained by the supplier. The establishment and maintenance of a calibration system to control the accuracy of the measuring and test equipment shall be in accordance with MIL-C-45662 (see 6.3).

4.4 First article inspection. First article inspection shall consist of the examination and tests specified in table I.

4.4.1 Test reports. The supplier shall prepare a first article test report in accordance with the data ordering document included in the contract or order (see 6.1.2). A copy of the first article test report shall be forwarded to the Commander, Naval Ship Engineering Center (Materials Development and Applications Office), Center Building, Prince Georges' Center, Hyattsville, Maryland 20782.

4.4.2 Sampling and acceptance. Sampling procedures shall conform to the methods and guides set forth in section 5 of FED-STD-501 for those items listed in table I.

4.5 Quality conformance.

4.5.1 Sampling and acceptance. Unless otherwise specified herein, sampling procedures shall conform to the methods and guides set forth in section 5 of FED-STD-501 for those items listed in table III.

Table III - Quality conformance tests.

Test	Requirement paragraph	Test paragraph
Surface tack	3.3	4.6.2
Size	3.4	4.6.13
Thickness	3.5	4.6.4
Squareness	3.14	4.6.3
Workmanship	3.19	

4.6 Methods of test. The methods of test shall be as follows:

4.6.1 Conditioning of specimens for physical tests. Unless otherwise specified herein, the samples shall be conditioned as specified in method 1041 of FED-STD-501.

4.6.2 Surface tack. The surface of the tile shall be pressed tightly with the palm of the hand (see 3.3).

4.6.3 Squareness. Specimens conditioned as described in 4.6.1, and measured as described in method 2421 of FED-STD-501, shall conform to the requirements of 3.14.

4.6.4 Thickness. Condition the tiles as described in 4.6.1. Measure the thickness of five tiles from each lot at four different points as described in method 2111 or 2131 of FED-STD-501. The average of the 20 readings taken on the five tiles shall be recorded as the thickness. The thickness shall be as specified in 3.5.

4.6.5 Indentation at 77°F. The specimens shall be conditioned as specified in 4.6.1. When a water bath is used for conditioning and testing the specimen, the glass plate and the hemispherical end and base of the indentation tester shall also be immersed in water and conditioned for at least the same period of time as the specimen. The specimen shall be tested as described in method 3211 of FED-STD-501.

4.6.5.1 If the median indentation at either time period of either specimen fails to meet the requirements of this specification (see 3.6), or if any single reading taken at the 1 minute time period is greater than 0.002 inch from the median of the three readings at that time period, the sample shall be considered to have failed to meet the requirements of the specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

4.6.6 Indentation at 115°F. The specimens shall be conditioned as described in 4.6.1, and tested as described in method 6311 of FED-STD-501.

4.6.6.1 If the median indentation of either specimen fails to meet the requirements of this specification (see 3.7), or if any single reading is greater than 0.004 inch from the median of the three readings, the sample shall be considered to have failed to meet the requirements of this specification.

4.6.7 Impact. The specimens shall be conditioned as described in 4.6.1, and tested as described in method 3311 of FED-STD-501. The 0.143 pound weight shall be dropped four successives times from a height of 10 inches. If either specimen breaks, or if any cracks are found in either specimen which are of sufficient length to extend beyond the limit of the 3-inch circle of white pigment paste, the sample shall be considered to have failed to meet the requirements of this specification.

4.6.8 Flexibility (before aging). The specimens shall be conditioned as described in 4.6.1, and tested as described in method 3111 of FED-STD-501. Two specimens, one with the long dimension parallel to the grain of the tile and one with the long dimension perpendicular to the grain of the tile shall be tested, using a 1-inch mandrel (see 3.9).

4.6.9 Flexibility (after aging). The specimens, after heating, in accordance with method 6211 of FED-STD-501 shall be tested as described in 4.6.8. The two specimens for test shall be taken from the same tiles used in 4.6.8.

4.6.10 Dimensional stability. The specimens shall be conditioned and tested in accordance with method 6211 of FED-STD-501. The two sets of equally spaced reference points shall be marked along each of the linear dimensions. The average of the changes along the two sets of two marks in each direction of the specimen shall be recorded.

4.6.10.1 If the average change in dimension of either specimen in either direction exceeds the limit given in 3.11, the sample shall be considered to have failed to meet the requirements of this specification.

4.6.11 Volatile material. Use the same specimens as required for 4.6.8. The specimens shall be conditioned and tested in accordance with method 9211 of FED-STD-501. The average of the results obtained from the two specimens shall be the volatile material in the sample. The volatile material shall be recorded to the nearest 0.1 percent and shall not exceed the requirement set forth in 3.12.

4.6.12 Chemical resistance. The specimens shall be tested in accordance with method 9311 of FED-STD-501. (Six specimens required from one tile for test). One specimen shall be immersed in each media listed below:

Sodium hydroxide - 5 percent solution
Ethyl alcohol - C. P. grade 95 percent
Kerosene
Lubricating oil - S.A.E. 10
Tallow
Cottonseed oil

The median of the three readings from the specimen shall be considered as the exposed scratch width of the tile as specified in 3.13.

4.6.12.1 When the exposed sample and the unexposed sample are placed on a plane surface beside each other and viewed in a north light, there shall be no appreciable change in hue. Darkening or lightening of a color is not to be construed as such a change.

4.6.13 Size. Measure five tiles from each lot as described in method 2231 of FED-STD-501. The average of the two measurements in each direction shall be recorded as the dimension of the tile in that direction.

4.6.14 Fire performance test. The test shall be conducted in accordance with the test method specified in MIL-STD-1623.

4.6.15 Water absorption. Three tiles shall be weighed and immersed in fresh tap water at a temperature of 70° to 75°F for 24 hours. At the end of this period, the tiles shall be removed and the surfaces and edges dried between blotting or filter paper and weighed before 2 minutes have elapsed. The increase in mass in percent shall be calculated. The average of the results obtained on the three tiles shall be the water absorption of the sample.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

4.6.16 Resistance to wear. Select three tiles, and cut specimens 3 inches long by 2 inches wide from each tile so that an area of approximately 6 square inches is presented the abrasive in the wear test machine (see figures 1 and 2). The abrasive grit shall be No. 80 aluminum oxide. Before wear-testing, the thickness shall be measured at 12 equally distributed points on the sample by means of a dial thickness gage and a template. The sample shall then be subjected to 1,500 revolutions of the wear-testing machine, and the thickness obtained at the same points previously measured. The differences in thickness shall be averaged to determine the thickness of material worn away by the abrasive.

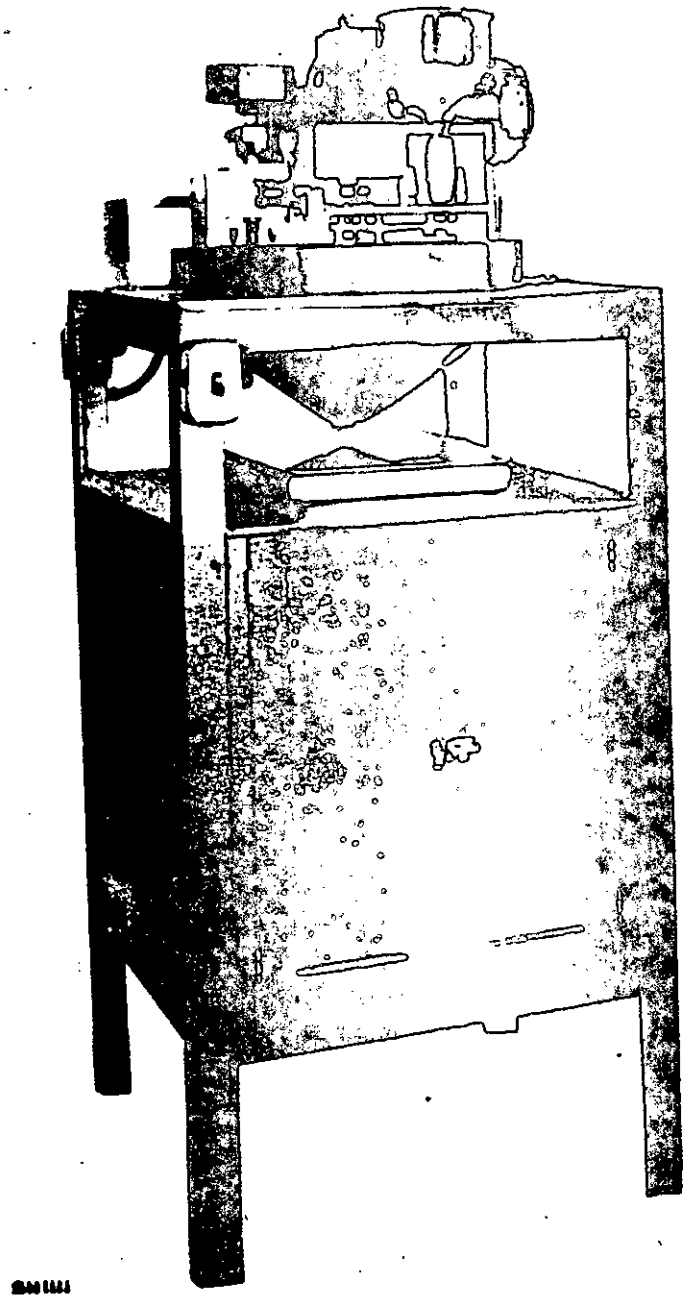


Figure 1 - Wear test machine.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

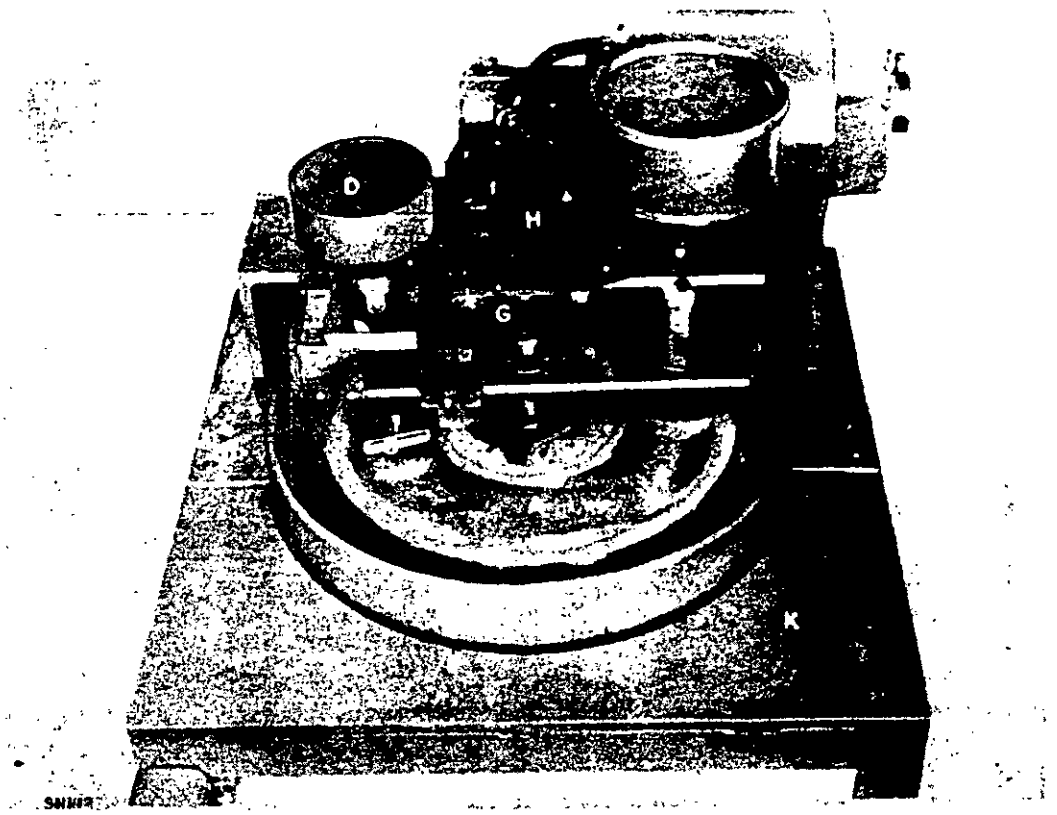


Figure 2 - Detail view of wear-test machine.

4.6.16.1 Wear-test machine. The wear-test machine, as shown on figures 1 and 2, shall have the following essential mechanical characteristics:

(a) Mild steel, abrasion disk, 14-1/8 inches in diameter and 1/2-inch thick, revolved clockwise at a constant speed of 23.5 revolutions per minute (r/min).
(b) Specimen holder, 2 by 4 inches, attached to a 5/8 inch diameter shaft by means of a universal coupling. The distance between centers of the disk and the specimen holder shaft is 5.1 inches. A specimen of tile is secured in the specimen holder by means of clamps at each end of the holder. The holder revolves clockwise at a constant speed of 32.5 r/min.
(c) Hardened tool-steel cam attached to the specimen holder shaft by means of set-screws. In each 1/2 revolution of the shaft, the specimen is lifted a distance of 1/16 inch and then dropped back on disk under a 10-pound mass. Change in the lift due to wear of the specimen is compensated by adjustment of the cam at regular intervals, so that the lift is maintained at a practically constant distance.
(d) Weight, 10 pounds, the maximum found suitable for use with this test machine.
(e) Distributor for abrasive grit. The grit flows by gravity from the hopper through a 13/16-inch inside diameter tube and into the center of the distribution chamber. An impeller in the chamber provides an evenly distributed feed of the grit through eight 3/64-inch diameter holes centered on a 1-5/8 inch diameter pitch circle. A uniform distribution of grit falls to disk in the path of the test specimen. The distributor is revolved at a constant speed of 9 r/min.
(f) Hopper for feeding abrasive grit.
(g) Bevel drive gear.
(h) Predetermining revolution counter and switch.
(i) One-third horsepower (hp) compound wound direct current (d.c.) motor.
(j) Hopper for collecting used abrasive grit.
(k) Steel frame.

Details of the distributor for the abrasive grit, the cam and specimen holder are shown on figures 3 and 4, respectively.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.


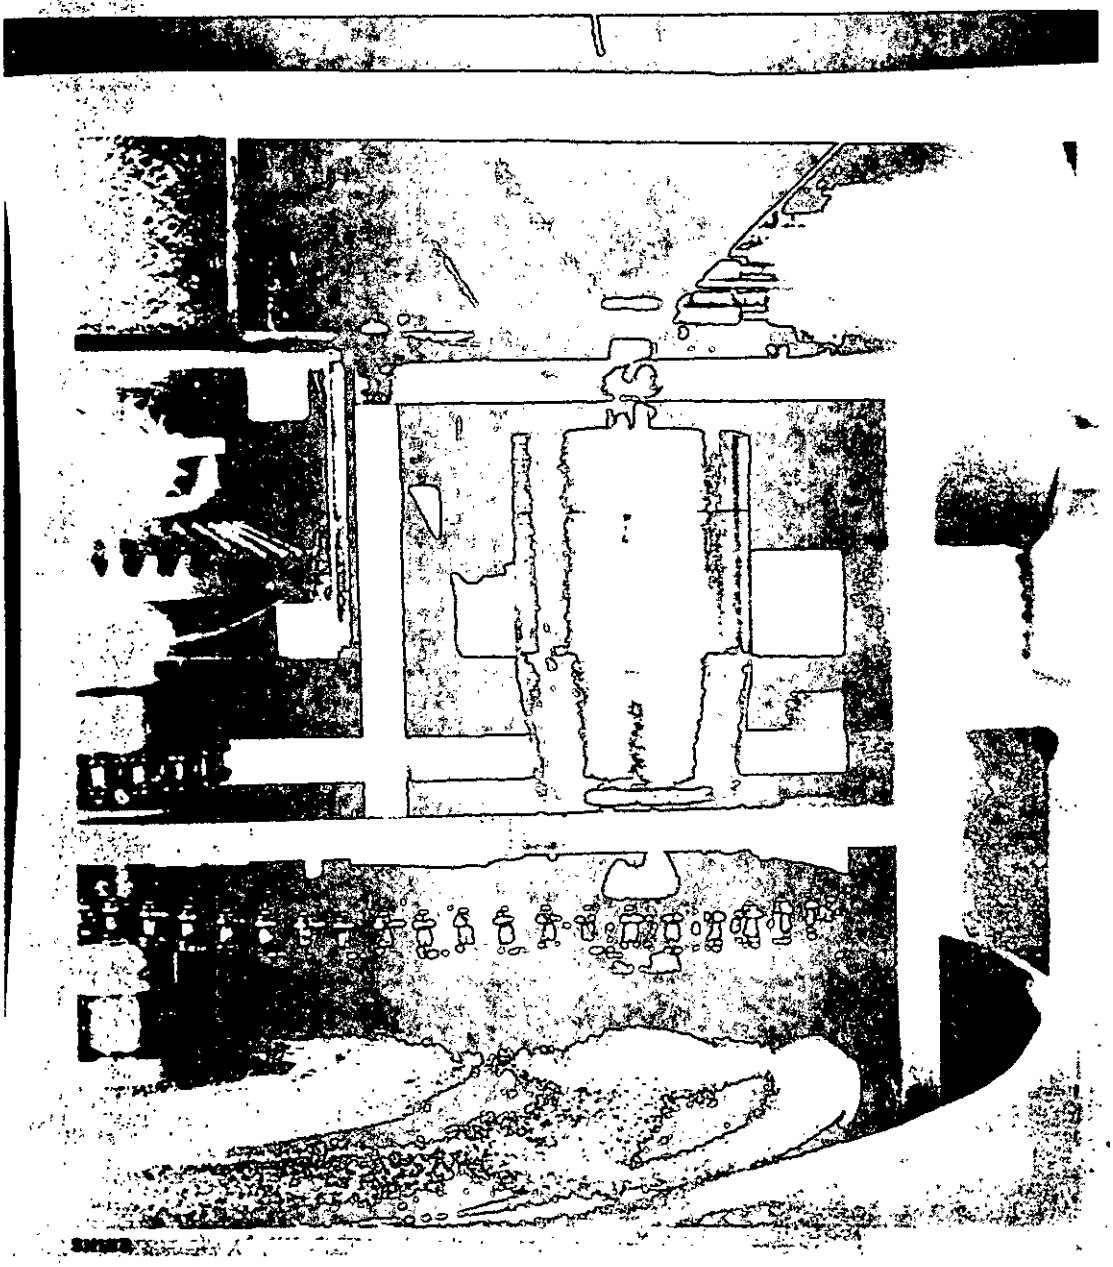


Figure 3 - Detail of distributor of abrasive grit.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

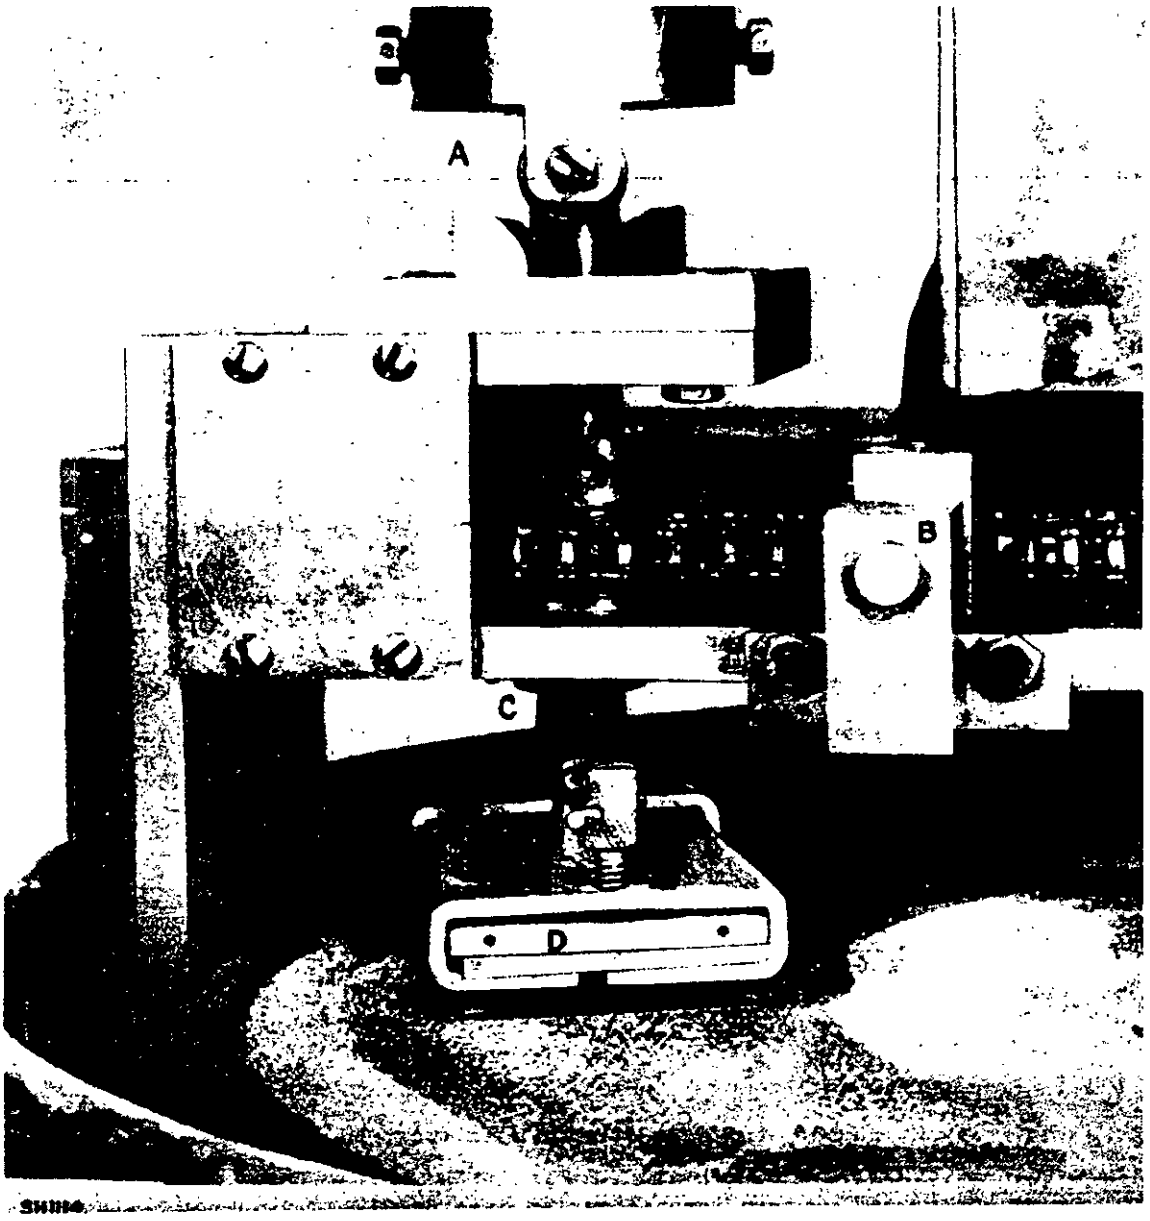

A - Cam
B - Chain idler
C - Universal joint
D - Specimen holder

Figure 4 - Detail of cam and specimen holder.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

4.6.16.2 Procedure. The steel disk revolves while the weighted specimen of tile in holder is lifted and dropped by a cam while it is being revolved. When the specimen is dropped through motion of the cam, it falls a distance of 1/16 inch and meets disk with impact simulating the fall of a foot on the deck surface. Foot action is further simulated in that the revolving specimen contacts the disk with a sliding and twisting motion until lifted clear by the cam. Continuous rotation of the specimen introduces the element of wear in all directions on the tile. Free abrasive grit of No. 80 aluminum oxide is fed at a steady rate from the hopper and distributed uniformly on the steel disk in the path of the specimen. The revolving motions of the steel disk and the test specimen keep the abrasive grit circulating to the outer side of the path of the specimen. The grit falls from the edge of the steel disk into hopper from which it is collected and then screened to eliminate undersized particles before replacement in the upper feeding hopper.

4.7 Inspection of preparation for delivery. Packing and marking shall be examined to determine conformance with section 5 of this specification.

5. PREPARATION FOR DELIVERY

(The preparation for delivery requirements specified herein apply only for direct Government procurements.)

5.1 Packaging. Not applicable.

5.2 Packing. Packing shall be level A, B, or C, as specified (see 6.1.1).

5.2.1 Level A. Forty-five 12-inch or eighty 9-inch tiles shall be packed in containers conforming to class 2 of PPP-B-636. All corners and edge seams, and manaufacturer's joint shall be waterproofed in accordance with the appendix to PPP-B-636.

5.2.2 Level B. Forty-five 12-inch or eighty 9-inch tiles shall be packed in containers conforming to class 1 of PPP-B-636, and closed in accordance with the appendix to PPP-B-636.

5.2.3 Level C. Packing shall be accomplished in a manner which will insure acceptance by common carrier, at lowest rate, and will afford protection against physical damage during direct shipment from the supply source to the using activity for early installation. The shipping containers or method of packing shall conform to the Uniform Freight Classification Rules and Regulations or other carrier regulations as applicable to the mode of transportation and may conform to the supplier's commercial practice when such meets these requirements.

5.3 Marking. In addition to any special marking required by the contract or order (see 6.1.1), shipping containers shall be marked for shipment in accordance with MIL-STD-129.

6. NOTES

6.1 Ordering data.

6.1.1 Procurement requirements. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Size of tile desired (see 3.4).
(c) Thickness (see 3.5).
(d) Color and pattern identification (see 3.18).
(e) Level of packing (see 5.2).
(f) Special marking, if required (see 5.3).

6.1.2 Contract data requirements. When this specification is used in a procurement invoking the provisions of Armed Services Procurement Regulations (ASPR) paragraph 7-104.9(n) and which incorporates a DD Form 1423 Contract Data Requirements List (CDRL) the data requirements identified below will be developed as specified in the cited Data Item Description (DID) and delivered in accordance with such CDRL. When the ASPR provisions are not invoked, the data specified below shall be delivered in accordance with the contract requirements.

Specification paragraph	Data requirement	Service	Applicable DID	Options
4.4.1	First article test report	SH	UDI-T-23450	-------

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

(Copies of DID's required by the supplier in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer. Unless otherwise specified, the issue in effect on date of invitation for bids or request for proposal shall apply.)

6.2 First article inspection.

6.2.1 Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection as to those bidders offering a product which has been previously procured or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending procurement.

6.3 Management control system document. The following management control system document should be included on DD Form 1660:

(a) MIL-C-45662 (see 4.3).

6.4 THE MARGINS OF THIS SPECIFICATION ARE MARKED "#" TO INDICATE WHERE CHANGES (ADDITIONS, MODIFICATIONS, CORRECTIONS, DELETIONS) FROM THE PREVIOUS ISSUE HAVE BEEN MADE. THIS WAS DONE AS A CONVENIENCE ONLY AND THE GOVERNMENT ASSUMES NO LIABILITY WHATSOEVER FOR ANY INACCURACIES IN THESE NOTATIONS. BIDDERS AND CONTRACTORS ARE CAUTIONED TO EVALUATE THE REQUIREMENTS OF THIS DOCUMENT BASED ON THE ENTIRE CONTENT IRRESPECTIVE OF THE MARGINAL NOTATIONS AND RELATIONSHIP TO THE LAST PREVIOUS ISSUE.

Preparing activity:
Navy - SH
(Project 7220-N074)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commander
Naval Air Systems Command (AIR 51122)
Washington, DC 20361

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil - Downloaded: 2026-10-18T11:59Z
Check the source to verify that this is the current version before use.