MILITARY SPECIFICATION

HOSE ASSEMBLY, ELASTOMER:

LIGHTWEIGHT COLLAPSIBLE; LIQUID FUEL

This specification is approved for use within the USA Belvoir Research, Development, and Engineering Center, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.


1. SCOPE

1.1 Scope. This specification covers lightweight collapsible, elastomer hose assembly for use with liquid fuels.

1.2 Classification. Hose assemblies shall be of the following sizes, as specified (see 6.2):

2-inch
3-inch

1.2.1 Part number. The definitive military part number for the hose assemblies (see 3.6 and 6.2) shall be as follows:

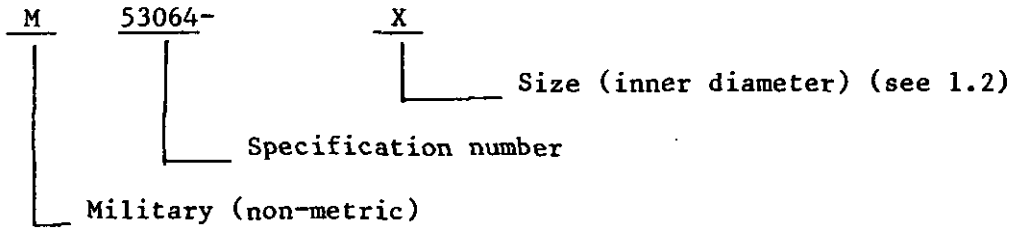

Example of part number: M53064-3 for a 3-inch hose assembly in accordance with this specification.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-TSE, Fort Belvoir, VA 22060-5606 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 4720
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards, form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DoDISS) and supplement thereto, cited in the solicitation.

SPECIFICATIONS

FEDERAL

VV-F-800	- Fuel Oil, Diesel.
WW-C-440	- Clamps, Hose, Low Pressure.

MILITARY

MIL-P-775	- Packaging of Hose, Hose Assemblies; Rubber, Plastic, Fabric, or Metal (Including Tubing) and Fittings, Nozzles and Strainers.
MIL-G-3056	- Gasoline, Automotive, Combat.
MIL-G-5572	- Gasoline, Aviation, Grades 80/87, 100/130, 115/45.
MIL-T-5624	- Turbine Fuel, Aviation, Grades JP-4 and JP-5.

STANDARDS

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-130	- Identification Marking.
MIL-STD-889	- Dissimilar Metals.

(Copies of specifications, and standards required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS shall be the issue of the non-government documents which is current on the date of the solicitation.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 380	- Rubber Hose.
D 381	- Existent Gum in Fuels by Jet Evaporation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

D 412 - Rubber Properties in Tension.
D 413 - Rubber Property - Adhesion to Flexible Substrate.
D 471 - Rubber Property - Effect on Liquids.
D 518 - Surface Cracking Resistance of Stitched Rubber Compounds.
D 1149 - Rubber Deterioration - Surface Ozone Cracking in a Chamber (Flat Specimen).
D 3389 - Coated Fabrics, Abrasion Resistance.
D 3951 - Standard Practices Commercial Packaging.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Nongovernment standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Description. The hose assembly shall consist of lightweight collapsible hose made up of a tube, reinforcement, and cover, with couplings on each end, for use with hydrocarbon fuels.

3.2 First article. Unless otherwise specified (see 6.2), a sample shall be subjected to first article inspection (see 4.3 and 6.3). Any changes or deviations of hose assemblies from the approved first article during production will be subject to the approval of the contracting officer. Approval of the first article will not relieve the contractor of his obligation to furnish hose assemblies conforming to this specification.

3.3 Materials. Materials shall be as specified herein. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification.

3.3.1 Material deterioration prevention and control. The hose assemblies shall be fabricated from compatible materials, inherently corrosion resistant or treated to provide protection against the various forms of corrosion and deterioration that may be encountered in any of the applicable operation and storage environments to which the hose assemblies may be exposed.

3.3.1.1 Dissimilar metals. Dissimilar metals shall not be used in intimate contact with each other unless protected against galvanic corrosion. Dissimilar metals and methods of protection are defined and detailed in MIL-STD-889. However, the static wire and appurtentant lugs or terminals shall be similar metal(s) to the metal of the hose coupling, and not dissimilar metals protected against galvanic corrosion.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.3.1.2 Identification of materials and finishes. The contractor shall identify the specific material, material finish, or treatment for use with component and subcomponent, and shall make information available, upon request, to the contracting officer or designated representative.

3.3.2 Recovered materials. For the purpose of this requirement, recovered materials are those materials which have been collected from solid waste and reprocessed to become a source of raw materials, as distinguished from virgin raw materials. The components, pieces and parts incorporated in the hose assembly may be newly fabricated from recovered materials to the maximum extent practicable, provided the hose assembly produced meets all other requirements of this specification. Used, rebuilt or remanufactured components, pieces and parts shall not be incorporated in the hose assembly.

3.4 Design and construction.

3.4.1 Hose. The hose shall consist of a compounded elastomer inner tube, one or more plies of synthetic fiber reinforcement material, static wire, and compounded elastomer cover. The hose shall not leak. The color of the hose shall be black except for a distinctive color lay-line.

3.4.2 Tube. The tube shall be fabricated from an elastomer which is resistant to hydrocarbon fuels, and shall not have any deleterious effects upon any type and grade of fuel conforming to MIL-G-3056 (automotive gasoline), MIL-G-5572 (aviation gasoline), MIL-T-5624 (jet fuel), or VV-F-800 (diesel fuel). The tube shall be smooth and free from pits.

3.4.3 Cover. The cover shall be of an elastomer compounded for fuel, oil, and ozone resistance. The cover shall be uniform in thickness.

3.4.4 Static wire. The static wires shall be embedded within or between the plies to form an angle of not less than 45 degrees to the longitudinal axis of the hose or woven along with the longitudinal yarn. The wires shall not break when the hose is coiled, or subjected to internal or external pressure. The static wire shall be either stainless steel or coated copper. Not less than 0.50 inch of each wire shall be in intimate contact with the couplings such that the resistance between the couplings shall not exceed 1.5 ohms per linear foot of hose.

3.4.5 Color lay-line. A distinctive color lay-line shall be marked on the outer cover of the hose. It shall be not less than 0.25 inch wide and shall be continuous for the full length of the hose. Handling, bending, fuel, or environmental effects shall not adversely affect the lay-line.

3.4.6 Reinforcement. The reinforcement of the hose shall be of a carcass of synthetic filament warp yarns interwoven with fillers of synthetic filament yarns or shall be of one or more plies of woven, braided or spiraled synthetic fiber cord. The reinforcement material shall be free of dirt, knots, lumps, irregularities of twist, or other defects. The reinforcement shall be evenly applied and thoroughly impregnated with elastomer so that the plies are bonded to their adjacent layers, tube, and cover, so as to produce a unified hose wall.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.4.7 Fittings and couplings.

3.4.7.1 Ball valve/sexless coupling. Coupling shall be of a sexless configuration mounted on a 360 degree swivel to permit convenient positioning of the ball valve handles after connection. Valve shall be capable of being opened and closed without tools, when the system is pressured up to 50 psi. The valve shall have a positive interlock with the disconnect mechanism, preventing disconnect when the valve is open. Ball size shall be the same as hose inside diameter. The valve control shall be provided with a double-ended arrow showing direction of operations and labeled at each end to indicate the functional result (i.e. "open", "close", etc.). The valve shall be operable ty personnel wearing arctic mittens.

3.4.7.2 Band fittings. Each coupling shall be banded to the hose by bands conforming to WW-C-440. There shall be 2 bands for each end of every hose. Each band shall be 6.25 inch.

3.5 Physical and chemical properties.

3.5.1 Dimensions and weight. Length of hose assembly shall be as specified (see 6.2d). Hose dimensions and weight shall be as specified in table I.

TABLE I. Dimensions and weight.

Hose diameter (inner diameter) +0.10 inch -0.03 inch	Weight per linear foot (without couplings) ±0.10 lb
2-inches	1.0 lb
3-inches	1.25 lb

3.5.2 Hydrostatic pressure. When tested as specified in 4.6.2.1, at the appropriate proof pressure from table II, the hose assembly shall not leak or show any imperfections in either the hose or couplings. There shall be no indication of slipping or pull-out of the hose from fitting or coupling. The length of the hose shall not change more than plus or minus 2 percent.

TABLE II. Pressures for hose assembly.

Size inner diameter (I.D.)	Operating pressure (psi)	Proof pressure (min)(psi)	Burst pressure (min)(psi)
2-inches	75	200	300
3-inches	75	200	300

3.5.3 Minimum burst. When tested as specified in 4.6.2.2, each size hose assembly shall have a minimum burst pressure as specified in table II.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.5.4 Tensile strength. When tested in accordance with 4.6.2.3 the tensile strength of the tube shall be not less than 1250 pounds per square inch (psi), and the tensile strength of the cover shall be not less than 1500 psi.

3.5.5 Tensile strength after immersion. When tested in accordance with 4.6.2.4, the tensile strength of the tube and cover after immersion shall be not less than 40 percent of original tensile strength or not less than 1250 psi.

3.5.6 Ultimate elongation. The ultimate elongation of the tube and cover shall be not less than 300 percent, and the elongation after immersion shall be not less than 200 percent.

3.5.7 Adhesion.

3.5.7.1 Original adhesion. When tested in accordance with 4.6.2.7.1, the adhesion between the tube and plies, between the plies, and between the cover and plies shall be not less than 10 pounds force (lbf).

3.5.7.2 Adhesion after immersion. When tested in accordance with 4.6.2.7.2, the adhesion between the tube and plies, between the plies, and between the cover and plies shall be not less than 6 lbf.

3.5.8 Low temperature flexibility. When the hose assembly is tested as specified in 4.6.2.8, there shall be no evidence of cracking, lack of flexibility, or other defects; and hose assembly shall not leak when tested at appropriate proof pressure from table II.

3.5.9 Ozone resistance. When tested in accordance with 4.6.2.9, the hose cover shall show no evidence of cracking, checking or other irregularities at the end of the exposure time when viewed under 7-power magnification.

3.5.10 Existent gum content. When tested as specified in 4.6.2.10, the remainder shall be not more than 20 milligrams per 100 milliliters of test fluid.

3.6 Identification marking. The hose assembly shall be identified in accordance with MIL-STD-130. Each length of hose shall be marked with the following information:

Date of Manufacture (quarter and year)
Contract Number
Manufacturer's Name and Trademark
Military Part Number
Working Pressure (specify)
Hose Assembly, Elastomer, Lightweight, Collapsible, Liquid Fuel

The hoses shall be marked in letters not less than 0.50-inch high such that handling, bending, water, oil, or environmental elements shall not adversely affect the markings. Hoses shall be marked in at least 10 foot intervals. Continuous branding shall be acceptable provided the pattern is repeated every 5 feet or less. Label color shall contrast with the background hose color. Military part number shall be as defined by 1.2 and 6.2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.7 Workmanship. The hose assembly shall conform to the quality requirements as specified herein. There shall be no cuts, nicks, bruises, blisters, lumps, or sharp edges on the hose assembly. The hose assembly shall be clean and smooth. The hose assembly shall have no other defects affecting appearance or serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).
c. Inspection of packaging (see 4.7).

4.3 First article inspection.

4.3.1 First article examination. The first article shall be examined as specified in 4.6.1, in the order shown. The presence of one or more defects shall be cause for rejection.

4.3.2 First article tests. The first article shall be subjected to the tests marked X in table III, column 1, in the order shown. Failure of any test shall be cause for rejection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

TABLE III. Hose assembly tests.

First article	Quality conformance	Individual	Test	Requirements paragraph	Test paragraph
X	X	X	Hydrostatic pressure.	3.5.2	4.6.2.1
X	X		Minimum burst.	3.5.3	4.6.2.2
X	X		Tensile strength.	3.5.4	4.6.2.3
X	X		Tensile strength after immersion.	3.5.5	4.6.2.4
X	X		Ultimate elongation.	3.5.6	4.6.2.5
X	X		Ultimate elongation after immersion.	3.5.6	4.6.2.6
X	X		Original adhesion.	3.5.7.1	4.6.2.7.1
X	X		Adhesion after immersion.	3.5.7.2	4.6.2.7.2
X	X1/		Low temperature flexibility.	3.5.8	4.6.2.8
X	X		Ozone resistance.	3.5.9	4.6.2.9
X	X		Existent gum content.	3.5.10	4.6.2.10
X	X		Electrical resistance.	3.4.4	4.6.2.11

1/ One lot testing required for each 10 lots submitted.

4.4 Quality conformance inspection.

4.4.1 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

4.4.2 Examination. Samples selected in accordance with 4.4.1 shall be examined as specified in 4.6.1. Failure of any examination shall be cause for rejection.

4.4.3 Tests. Samples selected in accordance with 4.4.1 shall be subjected to those tests marked "X" in table III, column 2. Test sections cut from hose shall be of sufficient length for the performance of their required tests. AQL shall be 1.0 percent defective.

4.4.3.1 Elastomer. Four test slabs, each 6 inches by 6 inches by 0.075 inch (±0.010 inch thick) of each elastomer used to fabricate the hose, shall be supplied with each lot.

4.5 Individual tests. Each hose assembly produced shall be subjected to those tests marked "X" in column 3 of table III.

4.6 Examination procedure.

4.6.1 Examination. The hose assembly shall be examined as specified herein for the following defects:

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

101. Material not as specified.
102. Materials not corrosion resistant or treated to be made corrosion resistant for the applicable storage and operating environment.
103. Dissimilar metals, as defined in MIL-STD-889, are not effectively insulated from each other.
104. Contractor does not have documentation available for identification of material, material finishes, or treatments.
105. Used, rebuilt, or remanufactured components, pieces or parts incorporated in the hose assembly.
106. Hose not as specified.
107. Dimensions and weight not as specified.
108. Fittings and couplings not as specified.
109. Hose cover scuffed, or bruised, so that braid is exposed.
110. Hose cover not clean and smooth.
111. Hose color lay-line not as specified.
112. Identification marking missing, incomplete, illegible, or not as specified.
113. Color of hose not as specified.
114. Workmanship not as specified.
115. Tube not as specified.

4.6.2 Tests.

4.6.2.1 Hydrostatic pressure. Each length of hose shall be subjected to the hydrostatic pressure tests of ASTM D 380 for elongation, twist, and proof pressure, using water as a test fluid. The test pressure shall be proof pressure as specified in table II. The electric bond shall be determined while full test pressure is applied. Elongation shall be 4 percent. Twist shall be 20 degrees per foot for 2-inch and 8 degrees per foot for 3-inch hose. Nonconformance to 3.4.4 and 3.5.2 shall constitute failure of this test.

4.6.2.2 Minimum burst. A sample of not less than 3 feet nor more than 6 feet shall be cut from hose selected in accordance with 4.4.1. The hose shall be subjected to the hydrostatic pressure test of ASTM D 380 for burst pressure, using water as a test fluid. The test pressure shall be the burst pressure as specified in table II. Nonconformance to 3.5.3 shall constitute failure of this test.

4.6.2.3 Tensile strength. The tensile strength of the tube and cover shall be determined in accordance with ASTM D 412. Nonconformance to 3.5.4 shall constitute a failure of this test.

4.6.2.4 Tensile strength after immersion. The tensile strength of the tube and cover after immersion shall be determined in accordance with ASTM D 471. Test temperature shall be 23 $\pm$2 °C; immersion period shall be 70 hours; immersion fluid shall be reference fuel D. Nonconformance to 3.5.5 shall constitute a failure of this test.

4.6.2.5 Ultimate elongation. The ultimate elongation of the tube and cover shall be determined in accordance with ASTM D 412. Nonconformance to 3.5.6 shall constitute a failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

4.5.2.6 Ultimate elongation after immersion. The ultimate elongation of the tube and cover after immersion shall be determined in accordance with ASTM D 471. Test temperature shall be 23 ±2 °C; immersion period shall be 70 hours; immersion fluid shall be reference fuel D. Nonconformance to 3.5.6 shall constitute a failure of this test.

4.6.2.7 Adhesion.

4.6.2.7.1 Original adhesion. Original adhesion shall be determined in accordance with the machine method of ASTM D 413. Nonconformance to 3.5.7.1 shall constitute a failure of this test.

4.6.2.7.2 Adhesion after fuel immersion. Adhesion after fuel immersion shall be determined in accordance with the machine method of ASTM D 413. Test samples shall have been immersed in reference fuel D of ASTM D 471 for 70 hours at 23 ±2 °C. Adhesion shall be determined within 15 minutes after removal of specimens from the test fluid. Nonconformance to 3.5.7.2 shall constitute a failure of this test.

4.6.2.8 Low temperature flexibility. Low temperature flexibility shall be determined in accordance with ASTM D 380, low-temperature test on complete hose. Temperature shall be -25 ±2 °F. Nonconformance to 3.5.8 shall constitute a failure of this test.

4.6.2.9 Ozone resistance. Specimens of the cover material used for the hose, prepared in accordance with ASTM D 518 procedure A, shall be mounted in a 20 percent elongated position and tested in accordance with ASTM D 1149. After conditioning for 24 hours in an ozone-free atmosphere, the mounted specimens shall be exposed for 72 hours at 40 ±1 °C to an atmosphere containing 50 ±10 parts per hundred million (pphm) of ozone. Upon completion of the test, the specimens shall be examined. Nonconformance to 3.5.9 shall constitute a failure of this test.

4.6.2.10 Existent gum content. A test specimen of hose not less than 14 inches long shall be stoppered with a 2-inch, non-corrosive plug, and clamped to prevent fluid loss. The sample shall then be filled to 2 inches from the top with reference fuel D of ASTM D 471, and the top shall be stoppered and clamped as above. The specimen shall be stored in a vertical position for 7 days at an ambient temperature of 100 °F. At the end of each 24 hour period, the fuel shall be agitated for 5 minutes by moving the hose back and forth from vertical to horizontal at a rate of 2 cycles per minute. At the end of the seven day storage period, the fuel shall be agitated in the same manner as above for 5 minutes and then immediately removed from the hose. The removed fuel shall be tested for existent gum content in accordance with the air jet solvent wash method of ASTM D 381. The value of existent gum of the control sample shall be subtracted from that of the test fluid to give value of existent gum content. Nonconformance to 3.5.10 shall constitute a failure of this test.

4.6.2.11 Electrical resistance. The electrical resistance of the hose shall be determined from coupling to coupling with an ohmmeter. Nonconformance to 3.4.4 shall constitute a failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

4.7 Inspection of packaging. Packaging shall be inspected in accordance with the quality assurance provision of MIL-P-775 and to determine compliance with the requirements of section 5.

5. PACKAGING

5.1 Preservation. The degree of preservation shall be level A or commercial, as specified, (see 6.2).

5.1.1 Level A. Each hose assembly shall be preserved in accordance with the level A preservation-packaging requirements of MIL-P-775.

5.1.2 Commercial. Commercial preservation shall be in accordance with ASTM D 3951.

5.2 Packing. The degree of packing shall be level A, B, or commercial, as specified (see 6.2).

5.2.1 Level A. The hose assembly shall be packed in accordance with level A packing requirements of MIL-P-775.

5.2.2 Level B. The hose assemblies shall be packed in accordance with the level B packing requirements of MIL-P-775.

5.2.3 Commercial. Commercial packing shall be in accordance with ASTM D 3951.

5.3 Marking.

5.3.1 Levels A and B. In addition to any special or identification markings required by the contract or purchase order, markings for levels A and B shall be in accordance with MIL-STD-129.

5.3.2 Commercial. Commercial marking shall be in accordance with ASTM D 3951. Additionally, each exterior container shall be marked with the cube and gross weight.

6. NOTES

6.1 Intended use. This lightweight, collapsible hose is intended for use with forward area refueling systems for discharge of liquid fuels such as automotive gasoline, aviation fuel, jet fuel, and diesel fuel.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number, and date of this specification
b. Size of hose assembly required (see 1.2).
c. Definitive military specification part number required (see 1.2).
d. When a first article is required for inspection and approval the number of units required (see 3.2).
e. Length of hose required (see 3.5.1).
f. Degree of preservation and packing required (see 5.1 and 5.2).
g. Any special marking (see 5.3.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

6.3 First article. When a first article inspection is required, the items should be a initial production. The first article should consist of one or more units. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, tests, and approval of the first article test results and disposition of the first article.

Custodian:
Army - ME

Preparing activity:
Army - ME

Project 4720-A722

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

DEPARTMENT OF THE ARMY
U.S. Army Belvoir Research,
Development and Engineering Center
ATTN: STRBE-TSE
Fort Belvoir, VA 22060-5606

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-H-53064(ME)	Hose Assembly, Elastomer: Lightweight Collapsible; Liquid Fu

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426

PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.