INCH-POUND

MIL-H-53064A(ME)
12 February 1992
SUPERSEDING
MIL-H-53064(ME)
20 May 1986

MILITARY SPECIFICATION

HOSE ASSEMBLY, ELASTOMER:

LIGHTWEIGHT, COLLAPSIBLE; LIQUID FUEL

This specification is approved for use within the USA Belvoir Research, Development, and Engineering Center, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a lightweight, collapsible, elastomer hose assembly for use with liquid fuels.

1.2 Classification. Hose assemblies shall be of the following sizes and classes, as specified (see 6.2):

Sizes I.D. (inside diameters):

2-inch
3-inch

Classes:

Class 1	- Coupling Halves, Quick-Disconnect, Cam-Locking Type, Hose Shank; Female Both Ends
Class 2	- Coupling Halves, Quick-Disconnect, Cam-Locking Type, Hose Shank; Male Both Ends
Class 3	- Couling Halves, Quick-Disconnect, Cam-Locking Type, Hose Shank; Female One End, Male Other End

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-TSE, Fort Belvoir, VA, 22060-5606 by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 4720

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards, form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

VV-F-800	- Fuel Oil, Diesel.
WW-C-440	- Clamps, Hose, Low Pressure.

MILITARY

MIL-H-775	- Hose, Hose Assemblies; Rubber, Plastic, Fabric, or Metal (Including Tubing) and Fittings, Nozzles and Strainers, Packaging of.
MIL-G-3056	- Gasoline, Automotive, Combat.
MIL-T-5624	- Turbine Fuel, Aviation, Grades JP-4 and JP-5.
MIL-C-27487	- Coupling Halves, Quick-Disconnect, Cam-Locking Type.

STANDARDS

FEDERAL

FED-STD-595	- Colors Used in Government Procurement.

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-130	- Identification Marking.
MIL-STD-889	- Dissimilar Metals.

(Unless otherwise indicated, copies of federal and military specifications and standards are available from the Standardization Documents Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS are the issues of the documents cited in the solicitation (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 380 - Rubber Hose.
D 381 - Existent Gum in Fuels by Jet Evaporation.
D 412 - Rubber Properties in Tension.
D 413 - Rubber Property - Adhesion to Flexible Substrate.
D 471 - Rubber Property - Effect of Liquids.
D 518 - Rubber Deterioration - Surface Cracking.
D 910 - Aviation Gasolines.
D 1149 - Rubber Deterioration - Surface Ozone Cracking in a Chamber (Flat Specimen).

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Non-Government standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Description. The hose assembly shall consist of lightweight collapsible hose made up of a tube, reinforcement, and cover, with a coupling on each end, for use with liquid hydrocarbon fuels.

3.2 First article. Unless otherwise specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.3.

3.3 Materials. Materials shall be as specified herein. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification.

3.3.1 Material deterioration prevention and control. The hose assemblies shall be fabricated from compatible materials, inherently corrosion resistant or treated to provide protection against the various forms of corrosion and deterioration that may be encountered in any of the applicable operating and storage environments to which the hose assemblies may be exposed.

3.3.1.1 Dissimilar metals. Dissimilar metals shall not be used in intimate contact with each other unless protected against galvanic corrosion. Dissimilar metals and methods of protection are defined and detailed in MIL-STD-889. However, the static wire and appurtenant lugs or terminals shall be similar metal(s) to the metal of the hose coupling, and not dissimilar metals protected against galvanic corrosion.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.3.1.2 Identification of materials and finishes. The contractor shall identify the specific material, material finish, or treatment for use with component and subcomponent, and shall make information available, upon request, to the contracting officer or designated representative.

3.3.2 Recovered materials. For the purpose of this requirement, recovered materials are those materials which have been collected from solid waste and reprocessed to become a source of raw materials, as distinguished from virgin raw materials. The components, pieces and parts incorporated in the hose assembly may be newly fabricated from recovered materials to the maximum extent practicable, provided the hose assembly produced meets all other requirements of this specification. Used, rebuilt or remanufactured components, pieces and parts shall not be incorporated in the hose assembly.

3.4 Design and construction.

3.4.1 Hose. The hose shall consist of a compounded elastomer inner tube, one or more plies of synthetic fiber reinforcement material, static wire, and compounded elastomer cover. The hose shall not leak. The color of the hose shall be sand matte in accordance with FED-STD-595, color chip 33446.

3.4.2 Tube. The tube shall be fabricated from an compounded elastomer which is resistant to liquid hydrocarbon fuels, and shall not have any deleterious effects upon any type and grade of fuel conforming to MIL-G-3056 (automotive gasoline), ASTM D 910 (aviation gasoline), MIL-T-5624 (jet fuel), or VV-F-800 (diesel fuel). The tube shall be smooth and free from pits.

3.4.3 Cover. The cover shall be of an elastomer compounded for fuel, oil, sunlight, water, and ozone resistance. The cover shall be uniform in thickness.

3.4.4 Static wire. The static wires shall be embedded within or between the plies to form an angle of not less than 45 degrees to the longitudinal axis of the hose or woven along with the longitudinal yarn. The wires shall not break when the hose is coiled, or subjected to internal or external pressure. The static wire shall be either stainless steel or coated copper. Not less than 1.0 inch nor greater than 1.5 inches of each wire shall be in intimate contact with the couplings such that the resistance between the couplings shall not exceed 1.5 ohms per linear foot of hose. The static wire shall not reach beyond the first hose band and in no case shall the wire protrude into the flow path.

3.4.5 Color lay-line. A longitudinal black lay-line shall be marked on the outer cover of the hose. It shall be not less than 0.125-inch wide and shall be continuous for the full length of the hose. The identification marking label (see 3.6) may substitute for the lay-line, provided they are continuous for the full length of the hose and are black in color. The lay-line shall remain clear, distinct and legible for the life of the hose. Handling, bending, fuel, or environmental effects shall not adversely affect the lay-line.

3.4.6 Reinforcement. The reinforcement of the hose shall be of a carcass of synthetic filament warp yarns interwoven with fillers of synthetic filament yarns

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

or shall be of one or more plies of woven, braided or spiraled synthetic fiber cord. The reinforcement material shall be free of dirt, knots, lumps, or irregularities of twist. The reinforcement shall be evenly applied and thoroughly impregnated with elastomer so that the plies are bonded to their adjacent layers, tube, and cover, so as to produce a unified hose wall.

3.4.7 Fittings and couplings.

3.4.7.1 Coupling halves (cam-locking type). Coupling halves shall be in accordance with MIL-C-27487, type II or VI, class 1 or 2, as applicable (see 1.2). The cam-lock couplings described herein are illustrated in figure 1.

3.4.7.1.1 Coupling caps. Coupling halves conforming to MIL-C-27487 shall be provided with the type IX dust cap or the type X dust plug conforming to MIL-C-27487. The caps and plugs shall be made captive to the couplings by means of a chain or similar attachment.

3.4.7.2 Band fittings. Each coupling shall be banded to the hose by bands conforming to WW-C-440. There shall be 2 bands for each end of every hose. Each band shall be 0.625-inch. The bands shall be covered with a non-vivid and non-reflective neoprene sleeve to protect the user.

3.5 Physical and chemical properties.

3.5.1 Diameter and weight. The length of hose assembly shall be as specified (see 6.2). Hose inside diameter and weight shall be as specified in table I.

TABLE I. Diameters and weight.

Hose Diameter (Inner diameter) +0.10-inch -0.03-inch	Weight per linear foot (without couplings) ±0.10 lb.
2 inches	0.60 pound (max)
3 inches	0.95 pound (max)

3.5.2 Hydrostatic pressure. When tested as specified in 4.6.2.1, at the proof pressure from table II, the hose assembly shall not leak or show any imperfections in either the hose or couplings. While under pressure, there shall be no indication of slipping or pull-out of the hose from the coupling. The length of the hose shall not change more than ±2 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

TABLE II. Pressure for hose assembly.

Size I.D. (inches)	Operating pressure (psi)	Proof pressure (psi) minimum	Burst pressure (psi) minimum
2	75	200	300
3	75	200	300

3.5.3 Minimum burst. When tested as specified in 4.6.2.2, each size hose assembly shall have a minimum burst pressure as specified in table II.

3.5.4 Tensile strength. When tested in accordance with 4.6.2.3 the tensile strength of the tube shall be not less than 1250 pounds per square inch (psi), and the tensile strength of the cover shall be not less than 1500 psi.

3.5.5 Tensile strength after immersion. When tested in accordance with 4.6.2.4, the tensile strength of the tube and cover after immersion shall be not less than 40 percent of original tensile strength or not less than 600 psi.

3.5.6 Ultimate elongation. The ultimate elongation of the tube and cover shall be not less than 300 percent, and the elongation after immersion shall be not less than 200 percent.

3.5.7 Adhesion.

3.5.7.1 Original adhesion. When tested as specified in 4.6.2.7.1, the adhesion between the tube and plies, between the plies, and between the cover and plies shall be not less than 10 pounds force (lbf).

3.5.7.2 Adhesion after immersion. When tested as specified in 4.6.2.7.2, the adhesion between the tube and plies, between the plies, and between the cover and plies shall be not less than 6 lbf.

3.5.8 Low temperature flexibility. When tested as specified in 4.6.2.8 and at a minimum pressure of 200 psi, there shall be no evidence of cracking, or lack of flexibility; and the hose assembly shall not leak.

3.5.9 Ozone resistance. When tested as specified in 4.6.2.9 and viewed under 7-power magnification, the hose cover shall show no evidence of cracking, checking or other irregularities at the end of the exposure time.

3.5.10 Existent and heptane-washed gum content. When tested as specified in 4.6.2.10, the existent gum content shall not be more than 20 milligrams per 100 milliliters of test fluid. When further tested as specified in 4.6.2.10, the heptane-washed gum content shall not be more than 5 milligrams per 100 milliliters.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

3.6 Identification marking. The hose assembly shall be identified in accordance with MIL-STD-130. Each length of hose shall be marked with the following information:

Date of Manufacture (quarter and year)
Contract Number
Manufacturer's Name and Trademark
PIN Number
Working Pressure (75 psi)
Hose Assembly, Elastomer, Lightweight, Collapsible, Liquid Fuel

The hoses shall be marked in letters not less than 0.18-inch high such that handling, bending, water, oil, or environmental elements shall not adversely affect the markings. Hoses shall be marked in at least 10-foot intervals. Continuous branding shall be acceptable provided the pattern is repeated every 5 feet or less. The label may be within the longitudinal lay-line, provided the width of the lay-line is not less than 0.20-inch greater than the height of the letters and the label is in contrast to the lay-line color. The label shall remain clear, distinct and legible for the life of the hose. Label color shall contrast with the background hose color. PIN (Part or Identifying) number shall be as defined by 6.4 (see 6.2).

3.6.1 Safety marking. The hose shall be marked at a maximum of 15 foot intervals with the following "CAUTION: DO NOT DRAG OVER IMPROVED SURFACES". The lettering shall be a minimum of 0.50-inch and be black Gothic capitals.

3.7 Workmanship. The hose assembly shall conform to the quality requirements as specified herein. There shall be no cuts, nicks, bruises, blisters, lumps, or sharp edges on the hose assembly. The hose assembly shall be clean and smooth. The hose assembly shall have no other defects affecting appearance or serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).
c. Inspection of packaging (see 4.7).

4.3 First article inspection.

4.3.1 First article examination. The first article shall be examined as specified in 4.6.1, in the order shown. The presence of one or more defects shall be cause for rejection.

4.3.2 First article tests. The first article shall be subjected to the tests marked "X" in column 1, table III, in the order shown. Failure of any test shall be cause for rejection.

TABLE III. Hose assembly tests.

First article	Quality conformance	Individual	Test	Requirements paragraph	Test paragraph
X	X	X	Hydrostatic pressure.	3.5.2	4.6.2.1
X			Minimum burst.	3.5.3	4.6.2.2
X	X		Tensile strength.	3.5.4	4.6.2.3
X	X		Tensile strength after immersion.	3.5.5	4.6.2.4
X	X		Ultimate elongation.	3.5.6	4.6.2.5
X	X		Ultimate elongation after immersion.	3.5.6	4.6.2.6
X	X		Original adhesion.	3.5.7.1	4.6.2.7.1
X	X		Adhesion after immersion.	3.5.7.2	4.6.2.7.2
X	X 1/		Low temperature flexibility.	3.5.8	4.6.2.8
X	X		Ozone resistance.	3.5.9	4.6.2.9
X	X		Existent and heptane-washed content.	3.5.10	4.6.2.10
X	X		Electrical resistance.	3.4.4	4.6.2.11

1/ One lot testing required for each 10 lots submitted.

4.4 Quality conformance inspection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

4.4.1 Sampling. Sampling for examination shall be in accordance with MIL-STD-105. Sample size shall be determined by table I and II-A. A lot shall be accepted when 0 defects are found, and rejected when 1 or more defects are found.

4.4.2 Examination. Samples selected in accordance with 4.4.1 shall be examined as specified in 4.6.1. Failure of any examination shall be cause for rejection.

4.4.3 Tests. Samples selected in accordance with 4.4.1 shall be subjected to those tests marked "X" in column 2, table III. Test sections cut from hose shall be of sufficient length for the performance of their required tests. Failure of any test shall be cause for rejection.

4.4.3.1 Elastomer. Four test slabs, each 6 inches by 6 inches by 0.075-inch (±0.010-inch thick) of each elastomer used to fabricate the hose, shall be supplied with each lot. Test slabs shall be fabricated under the same conditions of time, temperature, and pressure as used in hose production.

4.5 Individual tests. Each hose assembly produced shall be subjected to those tests marked "X" in column 3 of table III.

4.6 Examination procedure.

4.6.1 Examination. The hose assembly shall be examined as specified herein for the following defects:

101. Material not as specified (see 3.3).
102. Materials not corrosion resistant or treated to be made corrosion resistant for the applicable storage and operating environment (see 3.3.1).
103. Dissimilar metals, as defined in MIL-STD-889, are not effectively insulated from each other (see 3.3.1.1).
104. Contractor does not have documentation available for identification of material, material finishes, or treatment (see 3.3.1.2).
105. Used, rebuilt, or remanufactured components, pieces or parts incorporated in the hose assembly (see 3.3.2).
106. Hose not as specified (see 3.4.1).
107. Color of hose not as specified (see 3.4.1).
108. Tube not as specified (3.4.2).
109. Hose cover scuffed, or bruised, so that braid is exposed (see 3.4.3).
110. Hose cover not clean and smooth (see 3.4.3).
111. Hose color lay-line not as specified (see 3.4.5).
112. Fittings and couplings not as specified (see 3.4.7).
113. Dimensions and weight not as specified (see 3.5.1).
114. Identification marking missing, incomplete, illegible, or not as specified (see 3.6).
115. Workmanship not as specified (see 3.7).
116. Dust caps and plugs not made captive (where applicable).

4.6.2 Tests.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

4.6.2.1 Hydrostatic pressure. Each length of hose shall be subjected to the hydrostatic pressure tests of ASTM D 380 for elongation, twist, and proof pressure, using water as a test fluid. The test pressure shall be proof pressure as specified in table II. The electric bond shall be determined while full test pressure is applied. Elongation shall be ±2 percent. Twist shall be 20 degrees per foot for 2-inch and 8 degrees per foot for 3-inch hose. Nonconformance to 3.4.4 and 3.5.2 shall constitute failure of this test.

4.6.2.2 Minimum burst. A sample of not less than 3 feet nor more than 6 feet shall be cut from hose selected in accordance with 4.4.1. The hose shall be subjected to the hydrostatic pressure test of ASTM D 380 for burst pressure, using water as a test fluid. The test pressure shall be the burst pressure as specified in table II. Nonconformance to 3.5.3 shall constitute failure of this test.

4.6.2.3 Tensile strength. The tensile strength of the tube and cover shall be determined in accordance with ASTM D 412. Nonconformance to 3.5.4 shall constitute a failure of this test.

4.6.2.4 Tensile strength after immersion. The tensile strength of the tube and cover after immersion shall be determined in accordance with ASTM D 471. Test temperature shall be 23 ±2 °C; immersion period shall be 70 hours; immersion fluid shall be reference fuel D. Nonconformance to 3.5.5 shall constitute a failure of this test.

4.6.2.5 Ultimate elongation. The ultimate elongation of the tube and cover shall be determined in accordance with ASTM D 412. Nonconformance to 3.5.6 shall constitute a failure of this test.

4.6.2.6 Ultimate elongation after immersion. The ultimate elongation of the tube and cover after immersion shall be determined in accordance with ASTM D 471. Test temperature shall be 23 ±2 °C; immersion period shall be 46 hours; immersion fluid shall be reference fuel B. Nonconformance to 3.5.6 shall constitute a failure of this test.

4.6.2.7 Adhesion.

4.6.2.7.1 Original adhesion. Original adhesion shall be determined in accordance with the machine method of ASTM D 413. Nonconformance to 3.5.7.1 shall constitute a failure of this test.

4.6.2.7.2 Adhesion after fuel immersion. Adhesion after fuel immersion shall be determined in accordance with the machine method of ASTM D 413. Test samples shall have been immersed in reference fuel C of ASTM D 471 for 70 hours at 23 ±2 °C. Adhesion shall be determined within 15 minutes after removal of specimens from the test fluid. Nonconformance to 3.5.7.2 shall constitute a failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

4.6.2.8 Low temperature flexibility. Low temperature flexibility shall be determined in accordance with ASTM D 380, low-temperature test on complete hose. Temperature shall be -25 ±2 °F. Nonconformance to 3.5.8 shall constitute a failure of this test.

4.6.2.9 Ozone resistance. Specimens of the cover material used for the hose, prepared in accordance with ASTM D 518 procedure A, shall be mounted in a 20 percent elongated position and tested in accordance with ASTM D 1149. After conditioning for 24 hours in an ozone-free atmosphere, the mounted specimens shall be exposed for 72 hours at 40 ±1 °C to an atmosphere containing 50 ±10 parts per hundred million (pphm) of ozone. Upon completion of the test, the specimens shall be examined. Nonconformance to 3.5.9 shall constitute a failure of this test.

4.6.2.10 Existent and heptane-washed gum content. A test specimen of hose not less than 14 inches long shall be stoppered with a non-corrosive plug, and clamped to prevent fluid loss. The sample shall then be filled to 2 inches from the top with reference fuel D of ASTM D 471, and the top shall be stoppered and clamped as above. The specimen shall be stored in a vertical position for 7 days at an ambient temperature of 100 °F. At the end of each 24 hour period, the fuel shall be agitated for 5 minutes by moving the hose back and forth from vertical to horizontal at a rate of 2 cycles per minute. At the end of the seven day storage period, the fuel shall be agitated in the same manner as above for 5 minutes and then immediately removed from the hose. The removed fuel shall be tested for existent gum content in accordance with the air jet solvent wash method of ASTM D 381. A control sample of reference fuel D shall also be treated for existent gum content in accordance with the air-jet method of ASTM D 381. The value of existent gum of the control sample shall be subtracted from that of the test fluid to give value of existent gum content. The beakers containing the residue from the existent gum determination shall then be used to determine heptane-washed gum in accordance with ASTM D 381, procedures 10.8 through 10.12. A minimum of three specimens shall be used to report the average existent and heptane-washed gum content. Nonconformance to 3.5.10 shall constitute a failure of this test.

4.6.2.11 Electrical resistance. The electrical resistance of the hose shall be determined from coupling to coupling with an ohmmeter. Nonconformance to 3.4.4 shall constitute a failure of this test.

4.7 Inspection of packaging. Packaging shall be inspected in accordance with the quality assurance provision of MIL-H-775 and to determine compliance with the requirements of section 5.

5. PACKAGING

5.1 Preservation. Preservation shall be level A or C as specified (see 6.2). Each hose assembly shall be preserved in accordance with the level A or C requirements of MIL-H-775.

5.2 Packing. Packing shall be level A, B, C as specified (see 6.2). The hose assemblies preserved as specified in 5.1, shall be packed in accordance with the level A, B, or C requirements of MIL-H-775.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

5.3 Marking. In addition to any special marking specified in the contract or purchase order (see 6.2), marking shall be in accordance with MIL-STD-129.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. This lightweight, collapsible hose is intended for use with forward area refueling systems which discharge liquid fuels such as automotive gasoline, aviation fuel, jet fuel, and diesel fuel.


6.2 Acquisition requirement. Acquisition documents should specify the following:

a. Title, number, and date of this specification
b. Size of hose assembly required (see 1.2).
c. Class of coupling halves (see 1.2).
d. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
e. When a first article is not required for inspection (see 3.2).
f. Length of hose required (see 3.5.1).
g. PIN number (see 3.6 and 6.4).
h. Level of preservation and packing required (see 5.1 and 5.2).
i. Any special marking (see 5.3).

6.3 First article. When first article inspection is required, the item(s) should be an initial model. The first article should consist of one or more units. The contracting officer should also include specific instructions in acquisition documents regarding arrangements for examinations, approval of the first article test results and disposition of the first articles. Invitation for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract. Bidders should not submit alternate bids unless specifically requested to do so in the solicitation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

6.4 Part or identifying system. The part or identifying number (PIN) of hose assemblies covered by this specification shall be designed in the following form (see 3.6 and 6.2).

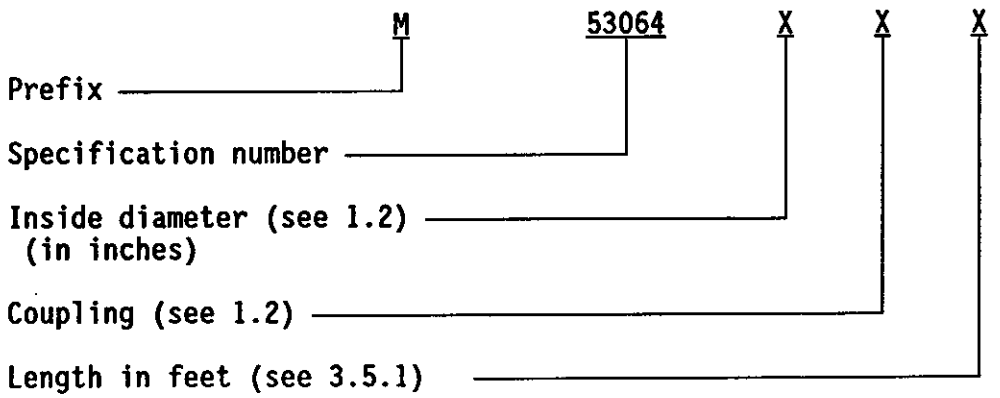

Example of part number: M53064-3-50-3 for a 3-inch diameter 50 foot long hose assembly with quick disconnect, cam-locking type coupling, hose shank; female on one end and, male other end, in accordance with this specification.

6.5 Subject term (key word) listing.

Couplings
Cover
Fuels, liquid
Tube

6.6 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Custodian:
Army - ME

Preparing activity:
Army - ME

Project 4720-A034

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

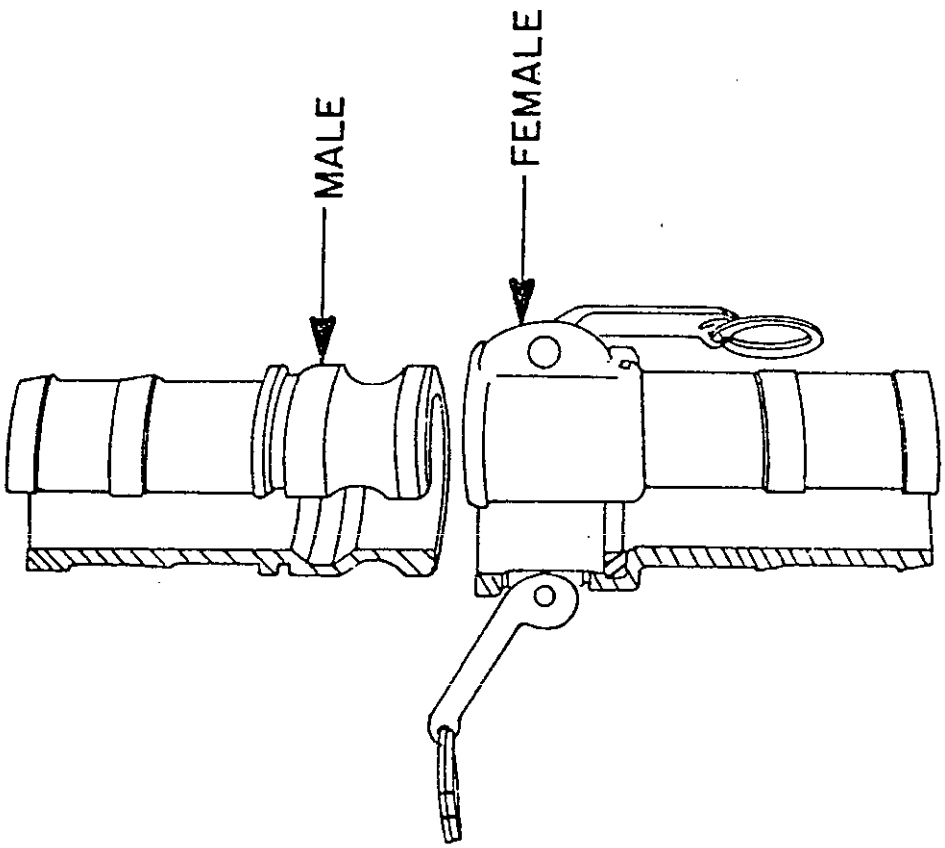


FIGURE 1. COUPLING HALVES, QUICK DISCONNECT, CAM-LOCKING TYPE, HOSE SHANK.

X-3128

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-H-53064A(ME)	2. DOCUMENT DATE (YYMMDD) 920212

3. DOCUMENT TITLE
Hose Assembly, Elastomer: Lightweight, Collapsible; Liquid Fuel

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (if applicable) (2) AUTOVON	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. NAME Carolyn B. Johnson	b. TELEPHONE (Include Area Code) (1) Commercial (703) 704-3468 (2) AUTOVON 654-3468
c. ADDRESS (Include Zip Code) US Army Belvoir RDE Center ATTN: STRBE-TSE Fort Belvoir, VA 22060-5606	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:57Z
Check the source to verify that this is the current version before use.