INCH-POUND

A-A-55759A
5 May 2011
SUPERSEDING
A-A-55759
12 September 1995

COMMERCIAL ITEM DESCRIPTION

RUBBER, SILICONE; SHEET, SOLID, SHAPE 15

The General Services Administration has authorized the use of this Commercial Item Description for all Federal Agencies.

1. SCOPE. This commercial item description (CID) covers a silicone rubber strip, shape 15 (see figure 1).

2. CLASSIFICATION. The silicone rubber will be of the following classes and grades as specified. The designated grade number corresponds to the nominal Shore Durometer A hardness value.

Class 1A – Low temperature resistant
Grade – 40, 50, 60, 70, and 80

Class 1B – Low temperature resistant and low compression set at high temperature
Grade – 40, 50, 60, 70, and 80

Class 2A – High temperature resistant
Grade – 25, 40, 50, 60, 70, and 80

Class 2B – High temperature resistant and low compression set
Grade – 25, 40, 50, 60, 70, and 80

Class 3A – Low temperature, tear and flex resistant
Grade – 30, 50, and 60

Class 3B – Tear and flex resistant
Grade – 30, 50, 60, 70, and 80

Comments, suggestions, or questions on this document should be addressed to Defense Supply Center Philadelphia (DSCP), ATTN: DSCP-NASA, 700 Robbins Avenue, Philadelphia, PA 19111-5096 or e-mail to dscpg&inspecomments@dla.mil . Since contact information can change, you may want to verify the currency of this address information using ASSIST Online database at https://assist.daps.dla.mil .

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.

3. SALIENT CHARACTERISTICS.

3.1 Dimensional and physical requirements. Dimensional and physical requirements shall conform to figure 1. Dimensional tolerance shall conform to the applicable commercial tolerance specified in CID A-A-59588.

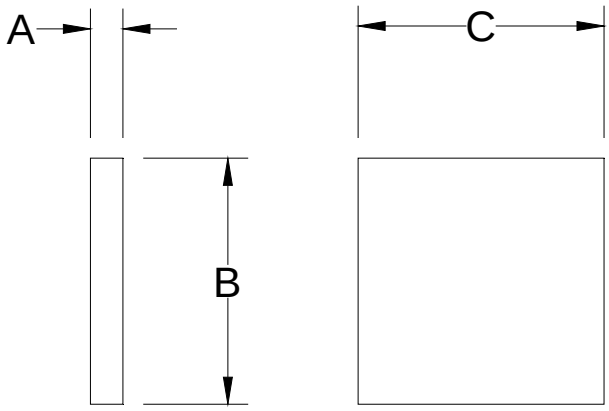

Figure 1. Dimensional and physical requirements.

Table I. Dash sizes and dimensions.

DASH SIZE	A THICKNESS	B WIDTH	C LENGTH	TEMP RATING IN º F	NHR	MIN TENSILE STRENGTH P.S.I	COLOR
001-D-5	0.015	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
002-D-6	0.016	36.000	36.000	-80 to 425	55.0 to 65.0	650	Gray
003-A-4	0.020	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
004-F-5	0.020	36.000	36.000	-94 to 400	45.0 to 55.0	1200	Natural
005-D-5	0.031	12.000	12.000	-80 to 425	45.0 to 55.0	700	Natural
006-A-7	0.031	24.000	36.000	-100 to 425	65.0 to 75.0	600	Gray
007-F-3	0.031	24.000	60.000	-94 to 400	25.0 to 35.0	1000	Natural
008-A-4	0.031	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
009-B-4	0.031	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
010-C-4	0.031	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
011-C-7	0.031	36.000	36.000	-80 to 425	65.0 to 75.0	650	Natural
012-D-2	0.031	36.000	36.000	-80 to 425	15.0 to 30.0	700	Natural
013-D-4	0.031	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
014-D-6	0.031	36.000	36.000	-80 to 425	55.0 to 65.0	650	Natural
015-D-7	0.031	36.000	36.000	-80 to 425	65.0 to 75.0	650	Natural
016-E-3	0.031	36.000	36.000	-130 to 400	20.0 to 35.0	850	Natural
017-E-5	0.031	36.000	36.000	-130 to 400	45.0 to 55.0	1200	Gray
018-E-6	0.031	36.000	36.000	-130 to 400	55.0 to 65.0	1100	Natural
019-F-5	0.031	36.000	36.000	-94 to 400	45.0 to 55.0	1200	Natural
020-A-5	0.040	36.000	36.000	-100 to 400	45.0 to 55.0	700	Natural
021-D-6	0.062	10.000	10.000	-80 to 425	55.0 to 65.0	650	Natural
022-D-5	0.062	12.000	120.000	-80 to 425	45.0 to 55.0	700	Natural
023-B-4	0.062	24.000	24.000	-100 to 425	35.0 to 45.0	700	Natural
024-B-4	0.062	24.000	24.000	-100 to 400	35.0 to 45.0	700	Natural
025-C-4	0.062	24.000	24.000	-80 to 425	35.0 to 45.0	700	Natural
026-C-5	0.062	24.000	24.000	-80 to 425	45.0 to 55.0	700	Natural
027-C-6	0.062	24.000	24.000	-80 to 425	55.0 to 65.0	650	Black

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.

Table I. Dash sizes and dimensions – Continued.

DASH SIZE	A THICKNESS	B WIDTH	C LENGTH	TEMP RATING IN ° F	NHR	MIN TENSILE STRENGTH P.S.I	COLOR
028-D-5	0.062	24.000	24.000	-80 to 425	45.0 to 55.0	700	Natural
029-E-5	0.062	24.000	24.000	-130 to 400	45.0 to 55.0	1200	Natural
030-F-5	0.062	24.000	48.000	-94 to 400	45.0 to 55.0	1200	Gray
031-A-4	0.062	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
032-C-4	0.062	36.000	36.000	-80 to 400	35.0 to 45.0	700	Natural
033-C-5	0.062	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
034-C-8	0.062	36.000	36.000	-80 to 425	75.0 to 85.0	650	Natural
035-D-2	0.062	36.000	36.000	-80 to 425	15.0 to 30.0	700	Natural
036-D-4	0.062	36.000	36.000	-80 to 425	35.0 to 45.0	700	Olive drab
037-D-5	0.062	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
038-D-6	0.062	36.000	36.000	-80 to 425	55.0 to 65.0	650	Natural
039-F-3	0.062	36.000	36.000	-94 to 400	25.0 to 35.0	1000	Natural
040-F-5	0.062	36.000	36.000	-94 to 400	45.0 to 55.0	1200	Natural
041-F-6	0.062	36.000	36.000	-94 to 400	45.0 to 55.0	1200	White
042-C-5	0.062	36.000	36.000	-80 to 425	45.0 to 55.0	700	Gray
043-E-3	0.062	36.000	36.000	-130 to 400	20.0 to 35.0	850	Natural
044-E-5	0.062	36.000	A/A	-130 to 400	45.0 to 55.0	1200	Natural
045-B-4	0.062	40.000	72.000	-100 to 425	35.0 to 45.0	700	Natural
046-A-5	0.062	24.000	24.000	-100 to 425	45.0 to 55.0	700	Natural
047-B-4	0.080	36.000	36.000	-100 to 425	35.0 to 45.0	700	Black
048-C-5	0.093	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
049-B-4	0.093	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
050-C-4	0.093	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
051-C-5	0.093	36.000	36.000	-80 to 425	45.0 to 55.0	700	Black
052-D-4	0.093	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
053-D-5	0.093	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
054-F-3	0.093	36.000	36.000	-94 to 400	25.0 to 35.0	1000	Natural
055-F-6	0.093	36.000	36.000	-94 to 400	55.0 to 65.0	1200	Natural
056-F-6	0.093	36.000	A/A	-130 to 425	20.0 to 35.0	1200	Natural
057-D-5	0.100	36.000	36.000	-80 to 425	45.0 to 55.0	700	White
058-D-7	0.125	12.000	12.000	-80 to 425	65.0 to 75.0	650	Natural
059-C-8	0.125	12.000	24.000	-80 to 400	75.0 to 85.0	650	Black
060-A-5	0.125	24.000	24.000	-100 to 325	45.0 to 55.0	700	Natural
061-A-4	0.125	24.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
062-A-6	0.125	36.000	36.000	-100 to 425	55.0 to 65.0	650	Natural
063-C-2	0.125	36.000	36.000	-80 to 425	15.0 to 30.0	700	Natural
064-C-5	0.125	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
065-C-6	0.125	36.000	36.000	-80 to 425	55.0 to 65.0	650	Black
066-D-5	0.125	36.000	36.000	-80 to 425	45.0 to 55.0	700	White
067-F-3	0.125	36.000	36.000	-94 to 400	25.0 to 35.0	1000	Black
068-F-5	0.125	36.000	36.000	-94 to 400	55.0 to 65.0	1200	Natural
069-F-6	0.125	36.000	36.000	-94 to 400	55.0 to 65.0	1200	Natural
070-F-8	0.125	36.000	36.000	-94 to 400	75.0 to 85.0	800	Natural
071-E-3	0.125	36.000	A/A	-130 to 425	20.0 to 35.0	850	Natural
072-C-8	0.125	48.000	48.000	-80 to 425	75.0 to 85.0	650	White
073-D-5	0.150	24.000	24.000	-80 to 425	45.0 to 55.0	700	White
074-D-4	0.180	36.000	36.000	-80 to 425	35.0 to 45.0	700	White

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.

Table I. Dash sizes and dimensions – Continued.

DASH SIZE	A THICKNESS	B WIDTH	C LENGTH	TEMP RATING IN ° F	NHR	MIN TENSILE STRENGTH P.S.I	COLOR
075-C-6	0.188	36.000	36.000	-80 to 425	55.0 to 65.0	650	Natural
076-A-4	0.250	A/A	A/A	-100 to 425	35.0 to 45.0	700	Natural
077-C-5	0.250	12.000	12.000	-80 to 425	45.0 to 55.0	700	Natural
078-A-6	0.250	36.000	36.000	-100 to 425	55.0 to 65.0	650	Natural
079-C-5	0.250	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
080-D-4	0.250	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
081-D-6	0.250	36.000	36.000	-80 to 425	55.0 to 65.0	650	Olive drab
082-F-5	0.250	36.000	36.000	-94 to 400	45.0 to 55.0	1200	Natural
083-F-8	0.250	36.000	36.000	-94 to 400	75.0 to 85.0	800	Natural
084-C-6	0.250	36.000	36.000	-80 to 425	55.0 to 65.0	650	Natural
085-E-3	0.250	48.000	48.000	-130 to 400	20.0 to 35.0	850	Natural
086-E-5	0.281	36.000	36.000	-130 to 400	45.0 to 55.0	1200	Natural
087-C-5	0.320	12.000	12.000	-80 to 425	45.0 to 55.0	700	Natural
088-B-5	0.393	11.790	11.790	-100 to 425	45.0 to 55.0	700	Natural
089-F-5	0.438	24.000	24.000	-94 to 400	45.0 to 55.0	1200	Gray
090-F-5	0.625	24.000	24.000	-94 to 400	45.0 to 55.0	1200	Natural
091-C-4	0.625	36.000	36.000	-80 to 425	35.0 to 45.0	700	White
092-F-5	0.750	24.000	48.000	-94 to 400	45.0 to 55.0	1200	Gray
093-F-6	1.000	24.000	24.000	-94 to 425	55.0 to 65.0	1200	Natural
094-C-4	1.250	36.000	36.000	-80 to 425	35.0 to 45.0	700	Natural
095-F-3	0.080	36.000	A/A	-94 to 400	25.0 to 35.0	1000	Gray
096-B-4	0.125	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
097-B-4	0.250	36.000	36.000	-100 to 425	35.0 to 45.0	700	Natural
098-D-5	0.050	36.000	36.000	-80 to 425	45.0 to 55.0	700	Natural
099-B-6	0.031	36.000	36.000	-100 to 425	55.0 to 65.0	650	Gray

Notes:
1. Unless otherwise noted, dimensions are in inches.
2. Surface condition: Smooth.
3. Surface condition location: One side.
4. Color location: Both sides.
5. NHR: Nonmetallic hardness rating, Shore Durometer A.
6. Minimum tensile strength: psi
7. A/A: Any acceptance

3.2 Material. Material shall be silicone rubber formulated and processed to meet the physical and mechanical properties per the specified class and grade, when tested in accordance with ASTM test methods specified in Table I of CID A-A-59588.

3.3 Color. Unless otherwise specified, the color of the silicone rubber shall be the natural color of the compound furnished.

3.4 Workmanship. The end product shall be clean, smooth finished, and free from dirt, flash or rough edges.

3.5 Marking. Unless otherwise specified (see ordering data), sheet material and strips (cut from sheet) shall be marked with the following information: Basic CID number, class, grade, designations, and the supplier's designations. The class and grade designations separated by a

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.

dash, shall be enclosed within parentheses. The markings shall be legible and placed in rows of constantly 5 inches apart. The supplier's designation (compound number) shall appear immediately below the constantly recurring description symbols. The symbols shall be legible and shall be not less than 3/8 inches high. The symbols shall be applied by suitable means, using a black colored marking fluid to mark white colored silicones and a white colored marking fluid to mark other than white colored silicones. The marking shall not be obliterated by normal handling or by the action of petroleum-based oils.

3.6 Metric products. Products manufactured to metric dimensions will be considered on an equal basis with those manufactured using inch-pound units, provided they fall within specified tolerances using conversion tables contained in the latest revision of ASTM SI 10, and all other requirements of this commercial item description are met. If a product is manufactured to metric dimensions and those dimensions exceed the tolerances specified in the inch-pound units, a request should be made to the contracting officer to determine if the product is acceptable.

4. REGULATORY REQUIREMENTS. The offeror/contractor is encouraged to use recovered materials to the maximum extent practicable, in accordance with paragraph 23.403 of the Federal Acquisition Regulation (FAR).

5. PRODUCT CONFORMANCE.

5.1 Product conformance. The products provided shall meet the salient characteristics of this commercial item description, conform to the producer's own drawings, specifications, standards, and quality assurance practices, and be the same product offered for sale in the commercial market. The government reserves the right to require proof of such conformance.

6. PACKAGING. Preservation, packing, and marking shall be as specified in the contract or order.

7. NOTES.

7.1 Part identification number (PIN): the following part identification numbering procedure is for government purposes and does not constitute a requirement for the contractor. The PINs to be used for items acquired to this description are created as follows: Basic CID number + dash size from Table I. Do not use unassigned dash size.

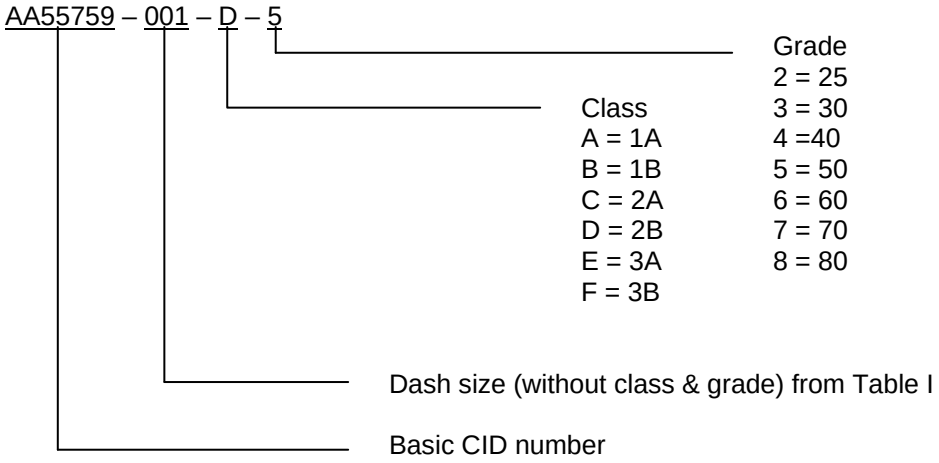

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.

7.2 Ordering data. The contract or order should specify the following:

a. Title, number, and date of this CID.
b. Dash size from Table I.
c. Marking if different (see 3.5).
d. Packaging requirements.

7.3 Source of documents.

7.3.1 ASTM SI10 is available from the ASTM International, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959 or online at http://www.astm.org .

7.3.2 FAR. The Federal Acquisition Regulation is available from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402 or online at http://www.arnet.gov/far .

7.3.3 Government documents. Federal and military documents are available online at https://assist.daps.dla.mil/quicksearch/ or from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.

7.4 Utilization caution. Use of this material in items that may come in contact with human skin, food, or portable water is not recommended without prior approval of the appropriate medical service.

7.5 Key words.

Class
Flex resistant
Grade
Low compression

7.6 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Military interests:

Custodians:
Army – MR
Navy – AS
Air Force - 11

Preparing activity:
DLA - IS

(Project 9320-2011-012)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.daps.dla.mil .

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T09:56Z
Check the source to verify that this is the current version before use.