INCH-POUND

MIL-DTL-17/139D
19 June 2015
SUPERSEDING
MIL-C-17/139C
23 November 1988

MILITARY SPECIFICATION SHEET

CABLE, RADIO FREQUENCY, FLEXIBLE, COAXIAL, 95 OHMS, M17/139-00001

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-DTL-17.

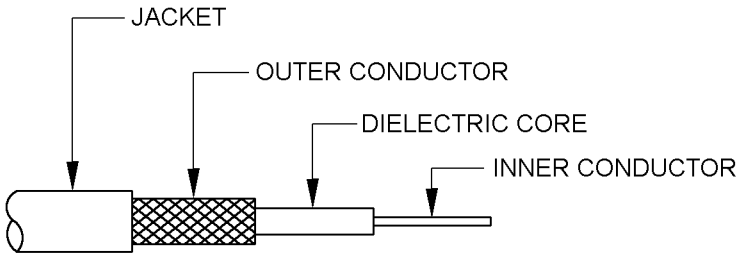


FIGURE 1. Configuration.

TABLE I. Description.

Components	Construction details
Inner conductor	Seven strands of silver-coated, beryllium copper, C17200 1/, 0.004 inch each. Overall diameter: 0.012 inch ±0.001. Alternate Seven strands of silver-coated, beryllium copper, CS95, 0.004 inch each. Overall diameter: 0.012 inch ±0.001.
Dielectric core	Type F-1: Solid extruded PTFE. Diameter: 0.102 inch ±0.003.
Outer conductor	Single braid of AWG No. 38, silver-coated cadmium bronze C16200 1/. (Or equivalent see MIL-DTL-17 3.4) Diameter: 0.124 inch, maximum. Coverage: 91.0% nominal. Carriers: 16 Ends: 7 Picks/inch: 12.0% ±10.
Jacket	Type XIII: PFA. Diameter: 0.141 inch ±0.004.

1/ Reference C16200 in accordance with ASTM B105 and C17200 in accordance with ASTM B197/B197M.

AMSC N/A

FSC 6145

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:18Z
Check the source to verify that this is the current version before use.

ENGINEERING INFORMATION:

Continuous working voltage: 1,100 V rms, maximum.
Operating frequency: 3 GHz, maximum.
Velocity of propagation: 69.5 percent, nominal.
Operating temperature range: -55° to +200°C.
Inner conductor properties:
DC resistance (maximum at 20°C): 40 ohms per 100 feet.
Elongation: 8 percent, minimum.
Tensile strength: 80 $klb_f/inch^2$, minimum.

Engineering note: This cable useful in high temperature, high tensile strength applications (see connector series “TNC” and “BNC” per MIL-PRF-39012.)


REQUIREMENTS:

Dimensions, configuration, and descriptions: See figure 1 and table I.
Environmental and mechanical:
Visual and mechanical: Applicable.
Out-of-roundness: Applicable.
Eccentricity: 10 percent, maximum.
Adhesion of conductors:
Inner conductor to core: 1.5 pounds, minimum; 4 pounds, maximum.
Aging stability: Not applicable.
Stress-crack resistance: +230°C ± 5°C; mandrel size 7 times the cable diameter.
Outer conductor integrity: Not applicable.
Cold bend: -55°C ± 2°C.
Dimensional stability: +200°C ± 5°C.
Inner conductor from core: .187 inch, maximum.
Inner conductor from jacket: .250 inch, maximum.
Contamination: Not applicable.
Bendability: Not applicable.
Weight: 1.94 pounds per 100 feet, maximum.
Flammability: Applicable.

ELECTRICAL:

Continuity: Applicable.
Spark test: 2,000 Vrms, minimum.
Voltage withstanding: 2,000 V rms, minimum.
Insulation resistance: 5,000 megohms, minimum.
Corona extinction voltage: 1,500 V rms, minimum.
Characteristic impedance: 95 ohms ± 5.
Attenuation: 18 dB per 100 feet, maximum at .4 GHz.
Structural return loss: Not applicable.
Capacitance: 17.4 pF per foot, maximum.
Capacitance stability: Not applicable.
Capacitance unbalance: Not applicable.
Transmission unbalance: Not applicable.
Phase stability: Not applicable.
Mechanically induced noise voltage: Not applicable.
Time delay: Not applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:18Z
Check the source to verify that this is the current version before use.

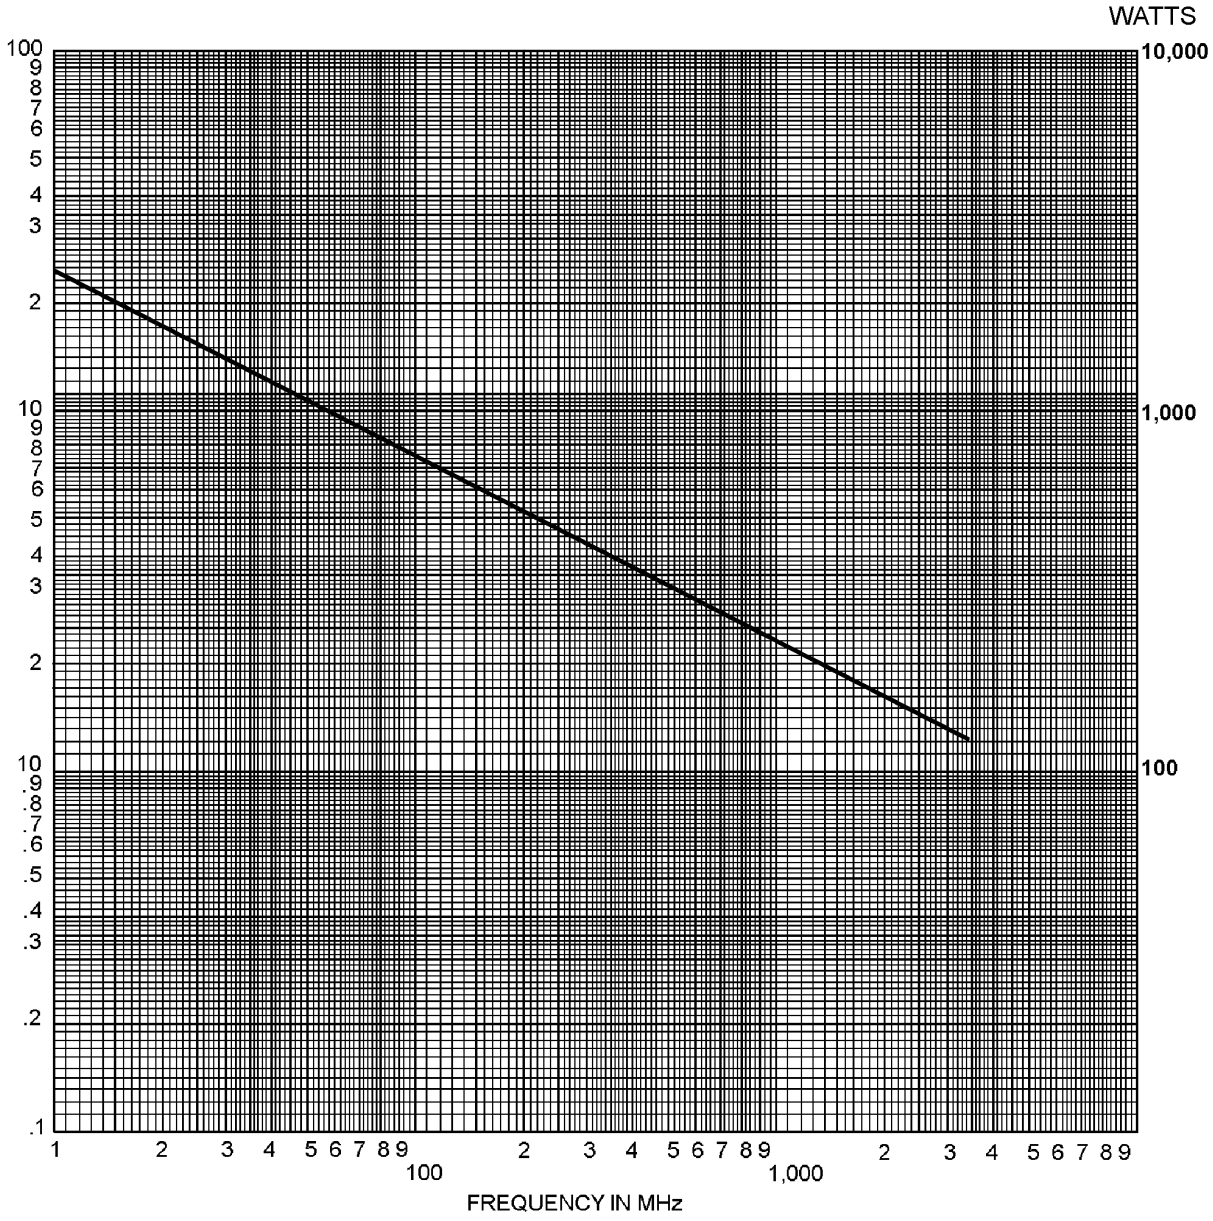

MAX POWER _____

Power rating for information only.

FIGURE 2. Power rating at 25°C sea level.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:18Z
Check the source to verify that this is the current version before use.

Part or Identifying Number (PIN): M17/139-00001.

Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Referenced documents. In addition to MIL-DTL-17, this document references the following:

MIL-PRF-39012 ASTM B105 ASTM B197/B197M

CONCLUDING MATERIAL

Custodians:
Army – CR
Navy – EC
Air Force – 85
DLA - CC

Preparing activity:
DLA - CC

(Project 6145-2015-026)

Review activities:
Army – AT, CR4, MI
Navy – AS, MC, OS, SH
Air Force – 19, 99

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-15T16:18Z
Check the source to verify that this is the current version before use.