INCH-POUND
MIL-DTL-43566D
10 October 2019
SUPERSEDING
MIL-T-43566C
1 August 1990

DETAIL SPECIFICATION

TAPE, TEXTILE, COTTON OR POLYESTER, GENERAL PURPOSE, NATURAL OR IN COLORS

This specification is approved for use by all Departments and Agencies of the Department of Defense (DoD).

1. SCOPE

1.1 Scope. This specification covers lightweight general purpose, cotton or polyester textile tape in natural or in colors.

1.2. Classification. The tape covers the following types and classes, as specified.

1.2.1 Types.

Type I - Lightweight tape
Type Ia - Extra lightweight tape

1.2.2 Classes.

Class 1 - Natural
Class 1a - Natural, water repellent and mildew resistant
Class 1b - Natural, water repellent and mildew and rot resistant
Class 2 - Bleached
Class 3 - Dyed
Class 4 - Dyed, water repellent and mildew and rot resistant
Class 8 - Dyed, water repellent

Comments, suggestions, or questions on this document should be addressed: ATTN: DLA Troop Support, 700 Robbins Street, Philadelphia, PA 19111-5096. Since contact information can change, verify the currency of the address information using Acquisition Streamlining and Standardization Information System (ASSIST) online database https://assist.dla.mil.

AMSC N/A FSC 8315

DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2. Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-3064 - Evaluation of Quality of Textile Materials

(Copies of this document are available online at https://quicksearch.dla.mil.)

2.2.2 Other government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

ENVIRONMENTAL PROTECTION AGENCY (EPA)

Federal Insecticide, Fungicide and Rodenticide Act (FIFRA)
(40 CFR Part 162) State Registration of Pesticide Products

Federal Insecticide, Fungicide and Rodenticide Act (FIFRA)
FIFRA as amended by the Food Quality Protection Act of 1996 and the
Pesticide Registration Improvement Act

(Copies of these documents are available online at https://www.epa.gov/pesticides.)

FEDERAL TRADE COMMISSION

Rules and Regulations under the Textile Fiber Products Identification Act

(Copies of this document are available online at https://www.ftc.gov.)

2.3 Non-government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

AMERICAN ASSOCIATION OF TEXTILES CHEMISTS AND COLORISTS (AATCC)

AATCC Evaluation Procedure 1 - Gray Scale for Color Change
AATCC Evaluation Procedure 2 - Gray Scale for Staining
AATCC Evaluation Procedure 8 - AATCC 9-Step Chromatic Transference Scale Rating
AATCC Evaluation Procedure 9 - Visual Assessment of Color Difference of Textiles
AATCC Test Method 8 - Colorfastness to Crocking: Crockmeter Method
AATCC Test Method 20 - Fiber Analysis: Qualitative
AATCC Test Method 30 - Antifungal Activity, Assessment on Textile Materials: Mildew and Rot Resistance of Textile Materials
AATCC Test Method 61 - Colorfastness to Laundering: Accelerated
AATCC Test Method 70 - Water Repellency: Tumble Jar Dynamic Absorption Test
AATCC Test Method 81 - pH of the Water Extract from Wet Processed Textiles
AATCC Test Method 169 - Weather Resistance of Textiles: Xenon Lamp Exposure

(Copies of these documents are available online at https://www.aatcc.org.)

AMERICAN SOCIETY FOR QUALITY

ASQ/ANSI Z1.4 – Sampling Procedures and Tables for Inspection by Attributes

(Copies of this document are available online at https://asq.org.)

ASTM INTERNATIONAL

ASTM D1907/D1907M - Standard Test Method for Linear Density of Yarn (Yarn Number) by the Skein Method
ASTM D3775 - Standard Test Method for End (Warp) and (Pick) Filling Count of Woven Fabrics
ASTM D3776/D3776M - Standard Test Method for Mass per Unit Area (Weight) of Fabric
ASTM D5035 - Standard Test Method for Breaking Force and Elongation of Textile Fabrics (Strip Method)

(Copies of these documents are available online at https://www.astm.org.)

INFORMA HEALTHCARE

Repeat Insult Patch Test – Modified Draize Procedure
Principles and Methods of Toxicology, A. Wallace Hayes (editor)

(Copies of these document are available online at https://www.crcpress.com)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2) a sample of the tape shall be subjected to first article inspection (see 4.3).

3.2 Recycled, recovered, environmentally preferable, or biobased materials. Recycled, recovered, environmentally preferable, or biobased materials should be used to the maximum extent possible, provided that the material meets or exceeds the operational and maintenance requirements, and promotes economically advantageous life cycle costs.

3.3 Material.

3.3.1 Cotton yarns. The tape shall be made from either carded or combed cotton yarn, except that the catch cord thread on the shuttleless loom shall be combed long-staple mercerized cotton yarn. The yarns shall be spun and twisted into ply yarns as specified in Tables I and II.

3.3.2 Polyester yarn (alternate for Type Ia, Class 2 tape only). When Type Ia, Class 2 tape is specified, textured multi-filament polyester yarns in the sizes specified in Table II may be used. The yarn shall be in its natural state (bleaching is not required).

3.4 Tape construction.

3.4.1 Type I tape. The Type I tape shall conform to the requirements specified in Table I. The width of the tape shall be as specified (see 6.2). The weave for Type I shall be composed of two ground warps (face and back), a binder warp, and filling. The face warp shall be a plain weave with picks that show on the face. The back warp shall be a plain weave with the picks that show on the back. The binder warp ends shall weave one up and one down. There shall be a minimum of six ground warp ends in each selvage edge weaving plain. When latch type shuttleless looms are utilized, the filling yarns shall traverse the full width of the tape and shall be held at the edge by an extra catch-cord end interlacing with the filling yarns, in a method depicted in Figure 1 or 2. When bobbin type shuttleless looms are utilized, interlacing of the catch-cord and filling shall occur within the selvage area before the first binder end (see Figure 3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

TABLE I. Type I tape requirements.

Width (inches)		Weight per linear yard, ounces (min.)	Yarns (min.)			Breaking strength (min.)		Yarn sizes (± 3 percent)		
	Tol.		Warp, face and back	Warp Binder	Filling yarns per inch 1/	Warp full width (lbs.)	Filling (jaws 1-inch apart) (lbs.) 2/	Warp (face and back) 3/	Warp (binder)	Filling 1/
3/8	-1/32, +1/16	0.13	37	7	42 or 84	50		16/2	20/2	20/2 or 40/2
1/2		0.17	49	10	42 or 84	70		16/2	20/2	20/2 or 40/2
5/8		0.21	61	13	42 or 84	85		16/2	20/2	20/2 or 40/2
3/4		0.26	69	15	42 or 84	100		16/2	20/2	20/2 or 40/2
7/8		0.30	77	17	42 or 84	115		16/2	20/2	20/2 or 40/2
1		0.34	89	20	42 or 84	130		16/2	20/2	20/2 or 40/2
1-1/8		0.45	97	22	46 or 92 4/	145		16/2	20/2	16/2, 30/2 or 32/2 4/
1-1/4		0.43	109	25	42 or 84	165		16/2	20/2	20/2 or 40/2
1-1/2		0.51	129	30	42 or 84	190		16/2	20/2	20/2 or 40/2
2	±1/16	0.68	169	40	42 or 84	250		16/2	20/2	20/2 or 40/2
2-1/2		0.86	209	50	42 or 84	300		16/2	20/2	20/2 or 40/2
3	±3/32	1.02	249	60	42 or 84	360	80	16/2	20/2	20/2 or 40/2

1/ 42 yarns per inch (1 yarn per shed) of 20/2 ply, or 84 yarns per inch (2 yarns per shed) of 40/2 ply.

2/ When bobbin type shuttleless looms are used, the point of interlacing the filling with the catch-cord shall be within the area to be ruptured.

3/ The yarn for the catch-cord shall be combed long-staple mercerized cotton yarn no finer than 40/2 for the bobbin type edge and no finer than 50/2 for the latch needle type edge. The color of the catch-cord (either type) shall be the color of the tape.

4/ 46 yarns per inch (1 yarn per shed) of 16/2 ply or 92 yarns per inch (2 yarns per shed) of 32/2 ply or 30/2 ply.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

3.4.2 Type Ia, tape. The Type Ia tape shall conform to the requirements specified in Table II. The width of the tape shall be as specified (see 6.2). The weave for Type Ia shall be plain weave. When latch-type shuttleless looms are utilized, the filling yarn shall traverse the full width of the tape and shall be held by an extra catch-cord end interlacing with the filling yarn, in a method depicted in Figure 1 or 2. When bobbin type shuttleless looms are utilized, interlacing of the catch-cord and filling shall occur within the first four ends of warp yarn at the edge (see Figure 3).

TABLE II. Type Ia tape requirements.

Characteristics	Cotton	Polyester
Width, inches (± 1/16)	2	2
Weight, ounces per linear yard, (min.)	0.45	0.38
Yarns (min.)		
Warp, full width	159	159
Filling, per inch	32 or 64 1/	16 2/
Breaking strength, (lbs.)		
Warp, full width (min.)	235	500
Yarn size, (±3 percent)		
Cotton:		
Warp	20/2 3/	-
Filling	20/2 or 40/2 1/	-
Polyester (denier) 4/		
Warp	-	450 5/
Filling	-	300

1/ 32 yarns per inch (1 yarn per shed) of 20/2 ply, or 64 yarns per inch (2 yarns per shed of 40/2 ply.
2/ Two picks per shed
3/ The cotton yarn for the catch-cord shall be combed long-staple mercerized cotton yarn no finer than 40/2 for the bobbin type edge and no finer than 50/2 for the latch needle type edge. The color of the catch-cord (either type) shall be the color of the tape.
4/ Nominal denier, plied or singles.
5/ The polyester yarn for the catch-cord shall be no finer than 150 denier.

3.4.3 Color.

3.4.3.1 Classes 1, 1a and 1b. The tape shall be unbleached natural.

3.4.3.2 Class 2. The tape for Class 2 shall be bleached white.

3.4.3.3 Classes 3, 4 and 8. The tape shall be dyed to the color specified in the contract or procurement document (see 6.2). Unless otherwise specified, when the tape conforming to Classes 4 and 8 is required, the shade of the dyed tape prior to the application of the finish shall match the standard sample. The shade of the tape, Classes 4 and 8, after finishing shall be that resulting from

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

the combination of the base shade (before finishing) and the color imparted by the finish. Unless otherwise specified, the use of coloring matter as a component of the finish shall not be permitted.

3.4.3.3.1 Visual shade matching (Classes 3, 4 and 8). The color and appearance of the dyed tapes shall match the standard sample (see 6.4) when tested as specified in 4.6.

3.4.3.3.2 Labile sulfur. Dyes and compounds containing elementary sulfur capable of oxidation to sulfuric acid shall not be used. The dyed tape shall be "Free" of labile sulfur when tested as specified in 4.6.

3.4.3.4 Colorfastness of Classes 3, 4 and 8 tapes. The finished tapes shall conform to the colorfastness requirements listed below in Table III when tested as specified in 4.6.

TABLE III. Colorfastness requirements.

Classes	Laundering (3) cycles) (color change and staining) (min.)	Accelerated weathering (40 AFU or 170 kJ/(m^2nm)@420 nm) 1/, (min.)	Crocking (wet and dry) (min.)
Class 3	3	3	3.5 2/
Class 4	3	3	1.5
Class 8	3	3	3.5

1/ AFU - AATCC Fading Units

2/.. When very dark colors are specified the color staining rating shall be a minimum of 3.0.

3.5 Finish. As specified, Classes 1a, 1b, 4 and 8 tape shall be treated with a mildew or rot resistant, water resistant treatment or a combination thereof.

3.5.1 Water repellency (Classes 1a, 1b, 4 and 8). Classes 1a, 1b, 4 and 8 shall be treated with a water repellent finishing treatment and shall have a dynamic absorption of no greater than 40 percent when tested as specified in 4.6.

3.5.2 Mildew resistant treatment (Class 1a). The tape shall be treated with an organic mildew inhibitor that is Environmental Protection Agency (EPA) registered under the Federal Insecticide, Fungicide and Rodenticide Act (FIFRA) and the observable fungi shall be no greater than "Microscopic Growth" (visible only under the microscope) after leaching when tested as specified in 4.6.

3.5.3 Mildew and rot resistant treatment (Class 1b and 4). The tape shall be treated with an organic mildew inhibitor that is EPA registered under the FIFRA and it shall retain a 75 percent breaking strength after 12 weeks of soil burial exposure after leaching when tested as specified in 4.6. The observable fungi shall be no greater than "Microscopic Growth" (visible only under the microscope) after leaching when tested as specified in 4.6.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

3.5.4 pH. The pH value of the water extract of the finished Classes 1b, 4 and 8 tapes shall be not less than 5.5 and not greater than 8.5 when tested as specified in 4.6.

3.6 Curvature. The finished tape shall show no more lateral curvature than 1/4 inch within a yard when tested as specified in 4.6 (see Figure 4).

3.7 Length and put-up. Unless otherwise specified (see 6.2), the tape length shall as specified in the contract.

3.8 Fiber identification. Each tape spool shall be labeled or ticketed for fiber content in accordance with the Rules and Regulations under the Textile Fiber Products Identification Act.

3.9 Toxicity. The finished tape shall not present a health hazard and shall show compatibility with prolonged direct skin contact when tested as specified in 4.6.4. The use of chemicals recognized by the EPA as human carcinogens shall be prohibited.

3.10 Workmanship. The finished tape shall conform to the quality of product established on this specification. The occurrence of defects as specified in 4.5 shall not exceed the quality acceptance levels as specified in the contract or purchase order.

4. VERIFICATION

4.1 Classification of inspection. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3)
b. Conformance inspection (see 4.4)

4.2 Inspection conditions. Unless otherwise specified, excluded, amended, modified or qualified in this specification or applicable procurement documents (see 6.2), all inspections shall be performed in accordance with all the requirements of referenced documents.

4.3 First article inspection. A first article, submitted in accordance with 3.1, shall be inspected, examined for appearance and finished defects listed in 4.5 and tested for the characteristics as specified in 4.6.

4.4 Conformance inspection. Conformance inspection shall include the visual examination of 4.5 and the tests of 4.6. Sampling for inspection shall be performed in accordance with ASQ/ANSI Z1.4 and with acceptance quality limits (AQLs) as specified in the contract and/or order, except where otherwise indicated (see 6.2).

4.5 Visual examination. Each spool in the sample shall be examined yard by yard for defects in accordance with MIL-STD-3064, Type IV, except the defects specified in Table IV of this document shall also be scored four (4) points for each yard in which they occur.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

TABLE IV. Defects that score four (4) points.

Defect Description
Catch-cord missing (applicable to shuttleless looms only)
Catch-cord not interlacing with filling (bobbin looms only)
Uneven application of treatment (Classes 1a, 1b, 4 and 8)
Clearly noticeable crystallization of mildew inhibitor (Classes 1a, 1b, and 4)

4.5.1 Spool identification and marking examination. During the yard-by-yard examination each spool in the sample shall be examined for defects as specified in MIL-STD-3064.

4.5.2 Shade variation examination. During the yard-by-yard examination, each spool in the sample shall be examined for shade variation as specified in MIL-STD-3064.

4.5.3 Length examination (individual and total yardage). During the yard-by-yard examination, each spool in the sample shall be examined for length as specified in MIL-STD-3064.

4.6 End item testing. The tape shall be tested for the characteristics listed in Table V. The methods of testing specified, wherever applicable and as listed in Table V shall be followed. All test reports shall contain the individual values utilized in expressing the final results. The sample unit shall be eight (8) linear yards of the finished tape for all physical tests. The lot shall be unacceptable if one (1) or more sample units fail to meet any requirement specified. The sample size shall be in accordance with the following:

Lot size (yards)	Sample size (sample units)
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

THIS SPACE LEFT INTENTIONALLY BLANK

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

TABLE V. End item tests.

Characteristic	Requirement Reference	Test method
Fiber content	3.3	AATCC 20 (see 6.5)
Weight, per linear yard: Type I Type Ia	 Table I Table II	ASTM D3776/D3776M, Opt D
Breaking strength Type I Type Ia	 Table I Table II	ASTM D5035
Yarn size	Table I and II	ASTM D1907/D1907M
Polyester (denier) (Type Ia, Class 2 only)	Table II	ASTM D1907/D1907M
Width, (inches): Type I Type Ia	 Table I Table II	Calibrated precision ruler
Count: Type I: Warp (face and back) Binder warp Type Ia: Warp, full width Type I and Ia: Filling, yarns per inch	 3.4.1 3.4.2 3.4.1 and 3.4.2	ASTM D3775
Weave: Type I Type Ia	 3.4.1 3.4.2	Visual
Visual shade matching	3.4.3.3.1	4.6.1
Labile sulfur	3.4.3.3.2	4.6.2
Colorfastness: Laundering (3 cycles) Accelerated weathering Crocking (wet and dry)		 AATCC 61, Option 2, 1/ AATCC 169, Option 1 2/ AATCC 8, 3/
Dynamic absorption	3.5.1	AATCC 70
Mildew resistance, Class 1a (observed fungus growth), 5/ After leaching 6/	3.5.2	AATCC 30, Test III, 4/
Rot resistance, Class 1b and 4, (percent strength retained), 8/ After leaching, 6/	3.5.3	AATCC 30, Test I, 4/, 7/
pH(Classes 1a,1b, 4 and 8)	3.5.4	AATCC 81
Curvature	3.6	4.6.3
Toxicity	3.9	4.6.4

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

1/ Rated using the AATCC Evaluation Procedure 1, Gray Scale for Color Change and AATCC Evaluation Procedure 2, Gray Scale for Staining.
2/ Rated using the AATCC Evaluation Procedure 1, Gray Scale for Color Change
3/ Rated using the AATCC Evaluation Procedure 8, AATCC 9-Step Chromatic Transference Scale
4/ Five (5) specimens shall be evaluated.
5/ AATCC 30, Test III will be required for First Article and lot testing(see 6.5).
6/ Leaching shall be conducted in accordance with procedure in Appendix A1 of AATCC 30, prior to testing.
7/ The samples shall be evaluated for breaking strength using ASTM D5035 before soil burial exposure and after leaching and soil burial exposure to calculate the percent strength retained from soil burial exposure. It shall be calculated as follows:

Percent strength retained = $100-((O-F/O)\ x100)$
Where:
O = Original (treated) breaking strength before soil burial exposure
F = Final breaking strength after leaching and solid burial exposure

8/ AATCC 30, Test I shall be required for First Article only.

4.6.1 Visual shade matching evaluation. The color and appearance of the dyed tape shall match the standard sample when viewed using the AATCC Evaluation Procedure 9, Option C (see 6.6) with sources simulating artificial daylight D75 illuminant with a color temperature of 7500 (± 200) K illumination of 100 (± 20) foot candles, and shall be a good match to the standard sample under incandescent A illuminant with a color temperature of 2856 (± 200) K.

4.6.2 Presence of labile sulfur test. In the determination of presence of labile sulfur in textile materials with lead acetate, two 1.50 (± 0.01) gram samples from each material submitted for evaluation shall be tested. Each of the two samples shall be cut into very small pieces and placed into separate test tubes. The samples shall be submersed in a stannous chloride solution that contains 100 grams of stannous chloride crystals ACS in 100 milliliters of hydrochloric acid ACS (35 percent concentration) and 50 milliliters of distilled water. A filter paper wet out with a 5.0 percent lead acetate solution shall be placed over the top of the test tube. The lead acetate solution contains 5.0 grams of lead acetate CP reagent grade and enough distilled water to make up a 100 milliliter solution; if the solution is not clear add a few drops (one at a time) of glacial acetic acid until the solution is clear. The test tube containing the textile sample, stannous chloride and wet filter paper shall be heated over a low flame until the solution is boiling. The solution shall not be heated for more than 15 seconds. A brown to black stain on the filter paper shall be rated as follows:

Free - The filter paper shows no discoloration or staining of any kind.
Slight - The filter paper shows a light tan to light brown discoloration stain.
Moderate - The filter paper shows a dark brown discoloration stain.
Severe - The filter paper shows a black color stain.

The rating shall be recorded. The results shall be recorded as “pass” or “fail”.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

4.6.3 Measurement of curvature. The test specimen shall be a full width minimum of 40 inches length of tape. The specimen shall not be stretched, smoothed, or otherwise changed from its original condition prior to testing. Five (5) specimens shall be tested from each sample unit. The following apparatus shall be used to conduct the testing:

a. A sheet of plexiglass 45 inches by 5 inches by 1/4 weighing approximately 35 ounces.
b. A straight edge ruler – a straight edge measuring 36 in length capable of measuring to 1/32 of an inch.
c. A roller – a roller one (1) inch in diameter, weighing 1-1/2 pounds.

The specimens shall be laid flat on a smooth horizontal flat surface without tension and allowed to reach equilibrium at standard textile conditions. After reaching equilibrium, a weight shall be placed at the end of the tape. The roller shall be placed on the specimen at the end of the tape where the weight is located. The specimen shall be approximately in the center of the roller. The roller shall be rolled along the length of the specimen, care being taken to keep the specimen in the center of the roller and not exert any pressure on the roller. When the roller has passed over the length of the tape, the plastic sheet shall be placed on the specimen for a period of one (1) hour. Without moving the plastic sheet on the specimen, the straight edge shall be placed on the plastic sheet so that both ends are aligned perpendicular with the outermost edge of the specimen. Determine the highest degree of curvature of the specimen from the straight edge by measuring to the nearest 1/32 of an inch perpendicularly from the straight edge (see Figure 4). Record the highest measurement. The results of each determination from each sample unit shall be recorded.

4.6.4 Toxicity test. When required, (see 6.2) an acute dermal irritation study and a skin sensitization study shall be conducted. When the results of these studies indicate the material is not a sensitizer or irritant, a Repeat Insult Patch Test shall be performed in accordance with the Modified Draize Procedure (see 2.3). If toxicity requirement (see 3.9) can be demonstrated with historical use data on the finishing treatments used, toxicity testing may not be required (see 6.2).

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

6.1 Intended use. The tape is for use in the manufacturing of military tentage, clothing and equipage items.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.
b. Type and class of tape required (see 1.2).
c. The specific issue of individual documents referenced (see 2.2).
d. When first article is required (see 3.1)
e. Conformance inspection acceptance quality limits (AQL) (see 4.4)
f. Inspection conditions (see 4.2)
g. When toxicity testing is required (see 4.6.4)
h. Packaging (see 5.1)

6.3 First article. When first article inspection is required (see 3.1), it will be inspected and approved under the appropriate provisions of FAR 52.209-4. The first article should be a preproduction sample. The contracting officer should specify the appropriate type of first article and the number of units to be furnished. The contracting officer should include specific instructions in acquisition documents regarding arrangements for selection, inspection, and approval of the first article.

6.4 Standard sample. For access to standard samples and pattern drawings, address the contracting activity issuing the invitation for bids or request for proposal.

6.5 Certificate of compliance. The contracting activity may select to accept a certificate of compliance for stated requirement after first article testing.

6.6 Visual shade matching. In 2019, Option A of the AATCC Evaluation Procedure 9, Visual Assessment of Color Difference in Textiles was changed to Option C. NOTE: In case of confusion, the viewing geometry should be “The specimen plane and illumination source shall be parallel to each other and aligned so that the light flux is incident at the center of the specimen plane, which is set at 35 (±) 5º angle relative to the horizontal. The observer shall view the specimens at a 90º angle, relative to the plane of the specimens”.

6.7 Subject term (key word) listing.

Dynamic absorption test
Microscopic growth
Rot resistance
Soil burial

6.8 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

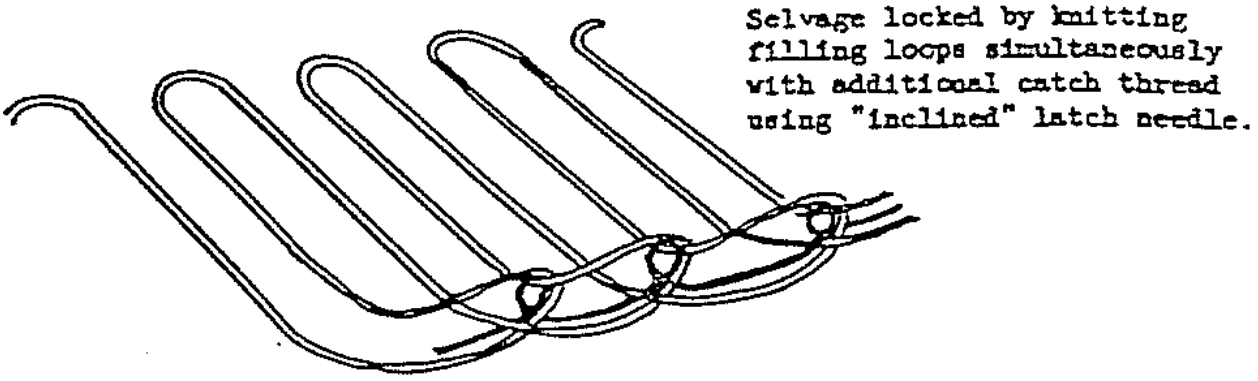


FIGURE 1. Catch-cord diagram.

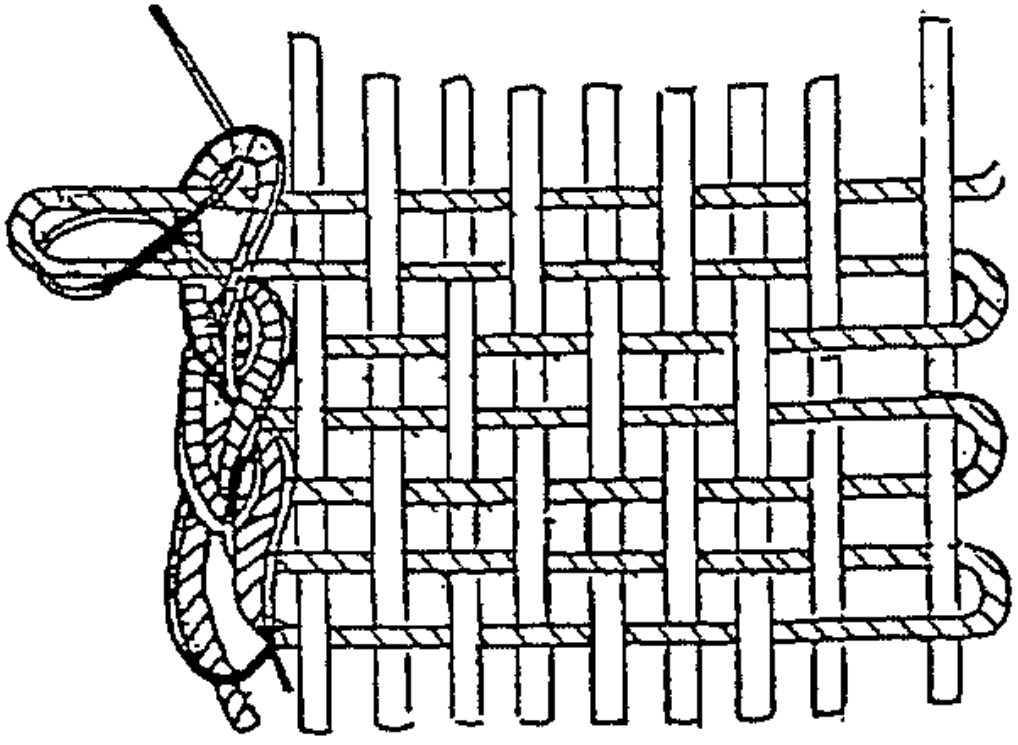


FIGURE 2. Catch-cord diagram.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

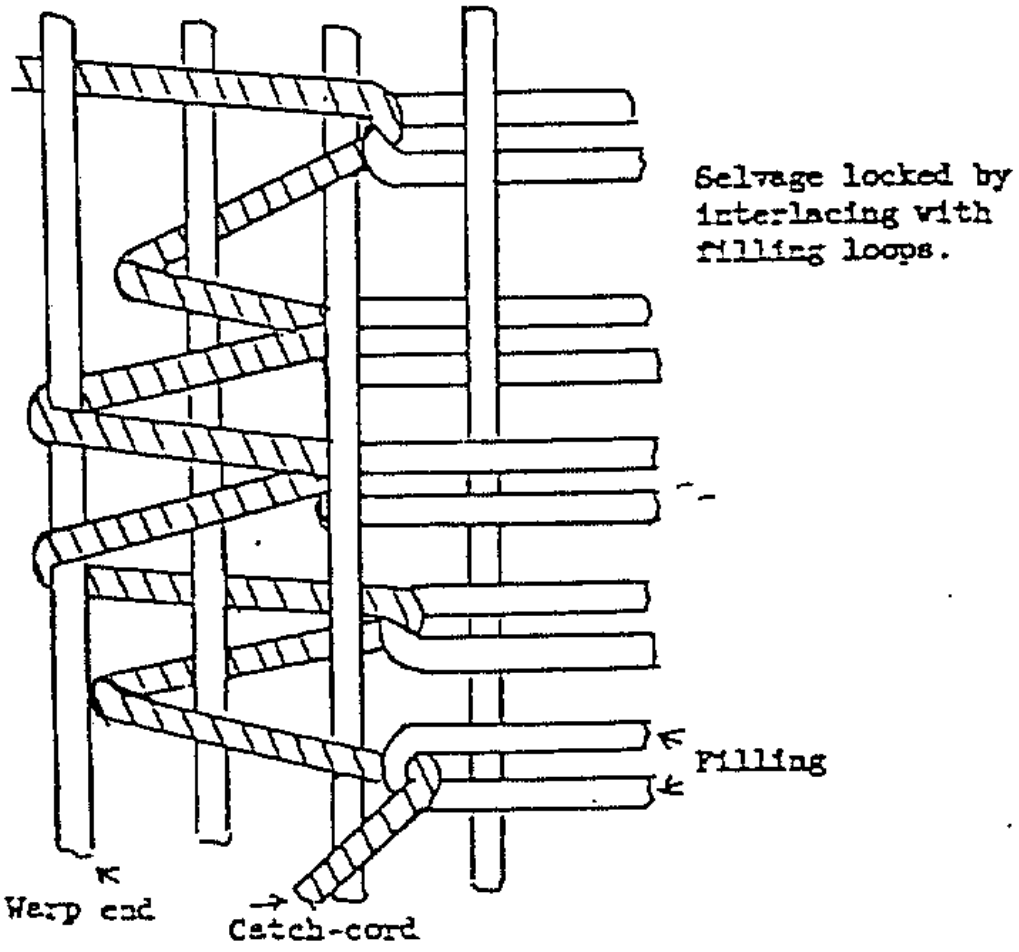


FIGURE 3. Catch-cord diagram.

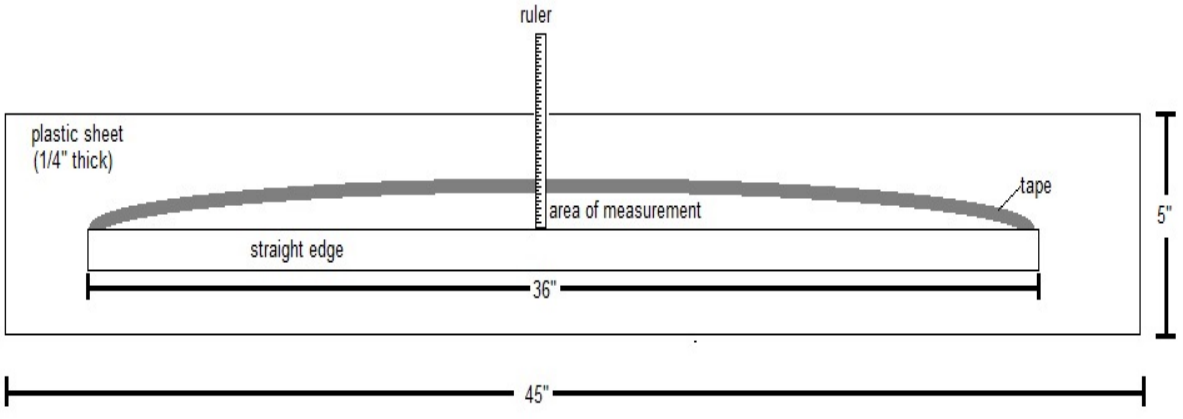


FIGURE 4. Measurement of curvature. (see 4.6.3)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.

Custodians:
Army - GL
Navy - NU
Air Force - 11

Preparing activity:
DLA-CT

Review activities:
Army - MD
Navy - MC

(Project 8315-2019 -008)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using ASSIST online database at https://assist.dla.mil

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:43Z
Check the source to verify that this is the current version before use.