MILITARY SPECIFICATION

PAPER, RECORDING, FACSIMILE (ELECTROSENSITIVE)

This specification is mandatory for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a single copy, dry process, electrosensitive recording paper in roll form, which makes visible record at any point subjected to electrical energy (see 6.1).

1.2 Classification. The electrosensitive recording paper covered by this specification shall be of one grade and shall be of the following sizes, as specified (see 3.3.1 and 6.2):

Size 1 - 550 feet long.

Size 2 - 275 feet long

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issue in effect on the date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

UU-P-31 - Paper, General Specifications and Methods of Testing.

PPP-B-636 - Box, Fiberboard.

PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, for Sealing and Securing.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

STANDARDS

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

MIL-STD-129 - Marking for Shipment and Storage.

(Copies of specifications and standards required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

USA STANDARDS INSTITUTE

PH 1.32-59 - American Standard Methods for Determining the Dimensional Change Characteristics of Photographic Films and Papers.

(Application for copies should be addressed to the United States of America Standards Institute, 10 East 40th Street, New York, New York.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Bid sample approval. Unless otherwise specified (see 6.2), the bidder shall submit, with his bid, one roll of electrosensitive recording paper representing the item he proposes to bid on and furnish to the Government if he receives award of the contract. The purpose of the bid sample is to

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

assist the Government to determine the capability of bidders to conform to all the requirements of this specification. The submission of an acceptable bid sample under this requirement shall not be construed as relieving the supplier from subsequently meeting all requirements of this specification on all deliveries.

3.2 Materials. The single copy, dry process, front grounding, electrosensitive recording paper furnished under this specification shall be made from such materials as are necessary to insure compliance with the requirements of this specification and be entirely suitable for the purpose intended.

3.2.1 Toxicity. Emission of particulate matter or gases while recording shall be non-toxic and shall have no adverse effect on the health of personnel when used for its intended purpose (see 6.3).

3.3 Design and construction. The dry process electrosensitive recording paper shall consist of a suitable base back sheet coated with such materials as are necessary to conform to the physical and performance requirements of this specification. No special handling or conditioning shall be required before or after its use; and, the finished copy shall be direct reading for immediate use, without processing or developing. Construction of all components and assemblies shall be in accordance with the requirements as specified herein.

3.3.1 Roll assembly. The electrosensitive recording paper shall be 10-1/4 inches plus or minus 1/64 inch wide and shall be 550 feet plus or minus 10 feet long for size 1 and 275 feet plus or minus 5 feet long for size 2 (see 6.2). The paper shall be uniformly and smoothly wound with the sensitive side in, on a 1-1/2 inch plus 1/64 minus 1/32 of an inch inside diameter (I.D.) fiber core. Maximum outside diameter of the size 1 roll shall be 6 inches. Maximum outside diameter of the size 2 roll shall be 4-3/16 inches. The core shall be flush or maximum 1/16 inch underflush with either end of the roll. The ends of each core shall be fitted with easily removable plugs. A 6 foot

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

long, 1/4 inch wide, blue warning stripe shall extend 5/8 inch in from either edge on the sensitive side of the paper at the end of the roll adjacent to the core. The edges of the roll shall be clean cut, even, and dust free; with the edges of all layers in the same plane, perpendicular to the axis of the roll (plus or minus 1 degree). The paper shall fall free at the core end when used and shall be held tightly at the outer end by tape commercially used for the purpose. Each roll shall be identified by a mill roll number marked on the core. No splices shall be permitted.

3.4 Physical requirements.

3.4.1 Writing quality. The electrosensitive recording paper shall have a matte surface capable of being easily written on by either pencil or ball point pen when tested as specified in 4.3.3.

3.4.2 Curl. The electrosensitive recording paper shall have a maximum curl of 15 millimeters when tested as specified in 4.3.3.

3.4.3 Wrinkling. The electrosensitive recording paper shall show no evidence of wrinkling when tested as specified in 4.3.3.

3.4.4 Coating peeling. The electrosensitive recording paper shall show no evidence of coating peeling when tested as specified in 4.3.3.

3.4.5 Folding endurance. The electrosensitive recording paper shall be capable of a minimum of 30 double folds when tested as specified in 4.3.3.

3.4.6 Tensile strength. The electrosensitive recording paper shall have a minimum tensile breaking strength of 17 lbs/inch width in the machine direction and 6 lbs/inch width in the across the machine direction when tested as specified in 4.3.3.

Source: https://assist.dla.mil -- Downloaded: 20260-21T21:41Z
Check the source to verify that this is the current version before use.

3.4.7 Tear strength. The electrosensitive recording paper shall have a minimum tear resistance of 16 grams in the machine direction and 21 grams in the across the machine direction when tested as specified in 4.3.3.

3.4.8 Burst (MULLEN) strength. The electrosensitive recording paper shall have a minimum bursting strength of 8 psi when tested as specified in 4.3.3.

3.4.9 Dimensional stability. The electrosensitive recording paper shall have a maximum dimensional expansion of 1.25 percent in the machine direction and 2.50 percent in the across the machine direction when tested as specified in 4.3.3.

3.5 Performance requirements.

3.5.1 Recording density characteristics. When tested as specified in 4.3.3, the density recording values shall lie between the boundaries indicated in figure 1. In addition, the voltage required to produce a density recording value of 0.10 above surface density shall not exceed 100 volts, and the voltage required to produce a density recording value of 0.40 above surface density shall not be less than 110 volts nor more than 155 volts. The relative speed shall not be less than 115 nor more than 175, and the density differential shall not be less than 46 nor more than 100. The maximum density achieved shall be at least 1.0 above surface density.

3.5.1.1 Color of record. The color of record shall appear in shades of gray.

3.5.2 Unwritten surface density. The coated surface density of the unwritten electrosensitive recording paper shall not be less than 0.15 nor more than 0.30 when tested as specified in 4.3.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

3.5.3 Storage stability. The electrosensitive recording paper shall not discolor or change recording characteristics when tested as specified in 4.3.3.

3.5.4 Permanency of record. Recordings on the electrosensitive recording paper shall be easily readable when tested as specified in 4.3.3.

3.5.5 Definition. When tested as specified in 4.3.3, all lines shall be well defined, without sludging in the form of gum or stylus buildup resulting in a change of recording characteristics, and the adjacent lines shall be capable of being resolved from one another.

3.5.6 Abrasiveness. When tested as specified in 4.3.3, stylus wear shall be a maximum of 8 mils.

3.6 Workmanship. The finished items shall be clean, free from holes, wrinkles, creases, tears, ply separation, warp, fluff, paper dust, lint, or grit. Coatings shall be completely and uniformly applied, free from coating streaks, pinholes, dirt, abrasive marks, scratches, spots, mottling, blisters, or any other defect that may affect serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Bid sample inspection. The bid sample specified in 3.1 shall be inspected to determine compliance with all the requirements of this specification.

4.3 Inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except when otherwise indicated hereinafter. For purposes of sampling, an inspection lot for examinations and tests shall consist of all the rolls of one size of electrosensitive recording paper submitted for inspection and delivery at one time.

4.3.1 Inspection of materials and components. In accordance with 4.1 above, components and materials shall be inspected and tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, or qualified in this specification or applicable purchase documents. In addition, it shall be the responsibility of the supplier to have his product tested by a qualified laboratory and to certify that the particle matter and gases emitted while recording are non-toxic.

4.3.2 Inspection of the end item.-

4.3.2.1 Examination of the end item. The end item shall be examined for the defects listed in the applicable subparagraphs. The lot size for purposes of determining the sample size shall be expressed in units of rolls of electro-sensitive recording paper for the examinations in 4.3.2.2 and 4.3.2.3, and in units of shipping containers for examination under 4.3.2.4.

4.3.2.2 Examination for workmanship. The sample unit for this examination shall be one linear foot, full roll width. No sample unit shall be taken from

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the currentversion before use.

the first or last convolution of a roll. Inspection level I shall apply and the acceptable quality level (AQL) shall be 1.0, expressed in defects per hundred units.

Examine	Defect
Workmanship	Holes, wrinkles, tears, creases, ply separation, warp, fluff, paper dust, lint, grit, or foreign matter, affecting serviceability.
	Not completely or evenly coated.
	Coating contains streaks, pin holes, dirt, abrasion marks, scratches, spots, mottling, or blisters, affecting serviceability.

4.3.2.3 Examination for dimensional, assembly, and identification marking defects. The sample unit for this examination shall be one roll. The inspection level shall be S-2 and the acceptable quality level, expressed in defects per hundred units, shall be 2.5 for the major classification, and 6.5 for major and minor defects combined.

Examine	Defect	Classification Major	Classification Minor
Dimension	Width of paper not as specified	X	
	Length of paper not as specified		X
	Dimensions of core not as specified.	X	
	Core underflush or extending more than specified.	X	
	Outside diameter of roll exceeds maximum tolerance.		X

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the currentversion before use.

Examine	Defect	Classification Major	Minor
Assembly	Not wound on fibre core.		X
	Core cracked, broken, chipped, mutilated or collapsed.	X	
	Core plug(s) missing from end(s) of roll.		X
	Core plug(s) not easily removable from roll end(s).		X
	Material not wound uniformly and smoothly causing soft uneven edges.	X	
	Edges not clean cut or even.		X
	Edges of all layers in the same plane not perpendicular to the axis of the roll.	X	
	Paper not wound with sensitive side in.	X	
	Material blocks or adheres to itself during unwinding.	X	
	Roll not continuous; tear or break within roll.	X	
	Any splice within a roll.	X	
	Warning signal missing or not as specified.	X	
	Paper does not fall free at core end.	X	
	Paper not held tightly at outer end by tape, as specified.		X
Identification marking	Mill roll identification number not marked as specified on fibre core.		X

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

4.3.2.4 Examination of preparation for delivery. An examination shall be made to determine that markings, materials, workmanship, and contents comply with the requirements of Section 5 of this specification. The sample unit shall be one shipping container fully packed, selected just prior to the closing operation. Closed shipping containers shall be examined for closure defects. The lot size shall be the number of containers in the end item inspection lot. The inspection level shall be S-2 and the acceptable quality level (AQL) shall be 2.5, expressed in defects per hundred units.

Examine	Defect
Markings (exterior and interior container)	Not in accordance with contract requirements.
	Omitted; incorrect; incomplete; illegible; of improper size, location, sequence or method of application.
Materials	Any nonconforming component; component missing, damaged or otherwise defective, affecting serviceability.
Workmanship	Open and noncontinuous heat sealed seams and closure of polyethylene bags.
	Inadequate application of components such as: incomplete closure of container flaps, loose or inadequate sealing, improper taping, strapping or stapling.
	Bulged or distorted container.
Contents (exterior and interior container)	Contents per interior container more or less than specified.
	Contents of shipping container less than 5,500 linear feet.
	Contents of shipping container has less than eight 550 foot rolls (size 1 only).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

4.3.3 Testing of the end item.- The end item shall be tested for the characteristics specified in table I. The methods of testing specified in UU-P-31, wherever applicable, and as listed in table I shall be followed. The sample unit for testing shall be a complete roll, randomly chosen. The lot size for purposes of determining the sample size shall be expressed in units of rolls of paper of one size. The sample size shall be S-1. The lot shall be unacceptable if any sample unit fails to meet any test requirement specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS FOR TESTING OF THE END ITEM

TABLE I

CHARACTERISTIC	Specification Reference		Requirements Applicable To		Number Determinations Per sample Unit	Results Reported As		[illegible]	[illegible]
	Requirement	Test Method or par. no.	Individ Unit	Lot Aver		Pass or Fail	Numerically to Nearest		
Physical requirements									
Writing	3.4.1	4.4.1	X		1	X			
Curl	3.4.2	4.4.2	X		1	X			
Wrinkling	3.4.3	4.4.3	X		1	X			
Coating peeling	3.4.4	4.4.3	X		1	X			
Folding endurance	3.4.5	131 1/	X		Average of 10 in each direction		0.1		
Tensile strength	3.4.6	171 1/	X		Average of 10 in each direction		1.0 percent		
Tear strength	3.4.7	170 1/	X		Average of 10 in each direction		1.0 gram		
Burst (Mullen) strength	3.4.8	112 1/	X		Average of 10 in each direction		0.01 points		
Dimensional stabil[illegible]	3.4.9	4.4.4	X		Average of 10 in each direction		0.01 percent		

QMRE Form 598
10 Oct 1961

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS FOR TESTING OF THE END ITEM

TABLE I (cont'd)

CHARACTERISTIC	Specification Reference		Requirements Applicable To		Number Determinations Per sample / Unit	Results Reported As			
	Requirement	Test Method or par. no.	Individ Unit	Lot Aver		Pass or Fail	Numerically to Nearest		
Performance									
Recording density characteristics									
Voltage required to produce a density of 0.10 and 0.40	3.5.1	4.4.5	X		Average of 5		1.0 volt		
Relative speed	3.5.1	4.4.5	X		Average of 5		1.0		
Density differential	3.5.1	4.4.5	X		Average of 5		1.0		
Unwritten surface density	3.5.2	4.4.5	X		Average of 5		0.01 reading		
Storage stability	3.5.3	4.4.6	X		1	X			
Permanency of record	3.5.4	4.4.6	X		1	X			
Definition	3.5.5	4.4.7	X		1	X			
Abrasiveness	3.5.6	4.4.8	X		Average of 2		1.0 mil		

1/ Tests are performed in accordance with UU-P-31.

QMRE Form 598
10 Oct 1961

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

4.4 Test procedures.-

4.4.1 Writing test.- Using normal writing pressure, write all the letters of the alphabet (size of letters not to exceed 1/8 inch) on the coated surface with a 2H pencil and a ball point pen. Difficulty in distinguishing any letter shall be considered non-compliance with 3.4.1.

4.4.2 Curl test.- Two sheets, 8 inches by 10 inches, cut from a roll, shall be placed on a flat surface; one sheet coated-side up and the other coated-side down. The assembly shall then be conditioned for 24 hours in a chamber at a relative humidity of 50 percent plus or minus 5 percent and a temperature of 73.5 degrees F. plus or minus 3 degrees F. At the end of the period, measure the greatest lift from the flat surface to any part of the sheet. Any lift exceeding 15 millimeters shall be considered non-compliance with 3.4.2.

4.4.3 Wrinkling and coating peeling test.- Two sheets approximately 10 square inches in area shall be torn in half with a tearing motion from the bottom side towards the coated surface. Any evidence of paper wrinkling or peeling or frilling of the torn edge shall be considered non-compliance with 3.4.3 or 3.4.4 respectively.

4.4.4 Dimensional stability test.- Specimens shall be cut into forms for use with a Pin Gage or Optical Gage as specified in U.S.A. Standard No. PH 1.32-1959. The specimens shall be conditioned for at least 3-1/2 hours at a temperature of 73.5 degrees F. plus or minus 3 degrees F. and at a relative humidity of 20 percent plus or minus 2 percent and then measured as specified in the U.S.A. Standard. The specimens shall then be reconditioned for at least 3-1/2 hours at a temperature of 73.5 degrees F. plus or minus 3 degrees F. and a relative humidity of 70 percent plus or minus 2 percent and again measured as specified in

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

en ... if the testing program covers a large number of ... shape of the specim...

the U.S.A. Standard. The difference between the two measurements shall be used to calculate the percent dimensional change. Any sample unit having a dimensional expansion greater than 1.25 percent in the machine direction or 2.50 percent in the across the machine direction will be considered non-compliance with 3.4.9.

4.4.5 Recording density characteristics and unwritten surface density test.- Sample density recordings shall be made at each of nine voltages; 100, 125, 150, 175, 200, 225, 250, 275, and 300 volts under the following conditions:

(a) A GS 65387 Sonar Data Recorder or equivalent shall be used (see 6.4).

(b) An adjustable, regulated, D.C. power supply capable of supplying a range of 50 to 600 volts to the stylus shall be used. The power supply shall be connected with the positive terminal grounded to the frame and the negative terminal connected through a series 2.2K, plus or minus 1 percent, resistor and an ammeter to the recording stylus. A vacuum tube voltmeter shall measure voltage from the power supply to frame ground.

(c) The recorder shall be equipped with a 10 mil, plus or minus 1 mil, diameter hard drawn tungsten wire stylus honed flat and polished.

(d) Stylus pressure shall be 15 grams plus or minus 1/2 gram.

(e) The stylus shall be positioned in such a manner that it is perpendicular to the paper being recorded.

(f) Each density of recording measurement shall be made on a recorded area greater than the area of the aperture of the reflectometer being used.

(g) Five density measurements shall be made equidistant across the center 8 inches of the writing area with a reflectometer, calibrated by using standard grey scale chips covering the range of measurements, by comparing the light reflected from the unwritten coated surface and recorded areas. The density of

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

recording is the difference between the reading for the recorded area and the unwritten coated surface. The average of the 5 density readings shall be determined.

(h) For each sample tested, plot density of recording versus writing voltage. Draw a smooth curve through the plotted data and make the following calculations:

1. The relative speed(S) for each sample shall be calculated by using the following formula:

$$S = \frac{280}{E_{0.8}} \times 100$$

Where $E_{0.8}$ is the voltage read from the curve at which the density is 0.8.

2. The density differential (R) for each sample shall be calculated by using the following formula:

$$R = (D_{200} - D_{100}) \times 100$$

Where:
D_{200} is the density read from the curve at 200 volts.
D_{100} is the density read from the curve at 100 volts.

4.4.5.1 The color of record not appearing in shades of gray shall be considered non-compliance with 3.5.1.1. An unwritten coated surface density of less than 0.15 or more than 0.30 (average of 5 readings per 80 square inch sample) shall be considered non-compliance with 3.5.2.

4.4.5.2 Compliance with 3.5.1 shall be based on the following:

(a) Any density recording value which does not lie between the boundaries indicated in figure 1 shall be considered non-compliance.

(b) Any voltage in excess of 100 volts required to produce a density of recording of 0.10 above surface density shall be considered non-compliance.

(c) Any voltage less than 110 volts or more than 155 volts required to produce a density of recording of 0.40 above surface density shall be considered non-compliance.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

(d) Any calculated relative speed less than 115 or more than 175 shall be considered non-compliance.

(e) Any calculated density differential less than 46 or more than 100 shall be considered non-compliance.

(f) A maximum density value obtained of less than 1.0 above surface density shall be considered non-compliance.

4.4.6 Storage stability and permanency of record test.- Five recorded samples having an area of at least 80 square inches and a roll of the unwritten electro-sensitive recording paper at least 5 inches wide by 20 feet long shall be conditioned for at least 30 days in a chamber maintained at a temperature of 120 degrees F. plus or minus 5 degrees F. and a relative humidity of 90 percent plus or minus 2 percent. The air within the chamber shall be uniformly and freely circulated around each test specimen with a velocity of not less than 1/10 foot per second. Any discoloration or change of recording density characteristics of the unwritten paper (see 4.4.5) shall be considered non-compliance with 3.5.3. Inability to easily read the recording on the recorded samples shall be considered non-compliance with 3.5.4.

4.4.7 Definition tests.- Three feet of single line recording, under conditions as established in 4.4.5, at a density of at least 0.70 above surface density shall be made with a freshly honed and polished stylus and examined with a 4X magnifying glass. Any line not well defined; or, sludging in the form of gum or stylus build-up resulting in a change of the recorded line characteristic shall be considered non-compliance with 3.5.5. In addition, under conditions established in 4.4.5, apply to the stylus a negative D.C. voltage 100 percent modulated with a 1020 cps sine wave, synchronized with the stylus sweep. The peak

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

value shall be equal to the voltage required to achieve a density of 1.0 above surface density. This will result in 85 parallel lines per inch (counted in the direction of the stylus sweep) being written in the direction of paper travel (see figure 2). Any adjacent line that cannot be resolved from one another under a 4X magnifying glass shall be considered non-compliance with 3.5.5.

4.4.8 Abrasiveness test.- Record 25 thousand feet of lines at a density of at least 0.70 above surface density under conditions as established in 4.4.5. Stylus wear in excess of 8 mils shall be considered non-compliance with 3.5.6.

5. PREPARATION FOR DELIVERY

5.1 Packaging.- Packaging shall be level A or C as specified (see 6.2).

5.1.1 Level A.-

5.1.1.1 Unit packaging.- Each roll of electrosensitive recording paper, assembled as specified in 3.3.1, shall be unit packaged in a close-fitting flat or square style clear polyethylene film bag of 0.0015-inch thickness (± 20 percent tolerance). The polyethylene bag shall be formed with heat sealed seams that are straight and continuous and parallel to each other and the formed edges of the bags. The opening of the plastic bag shall be heat sealed or secured with a mechanical twist tie (paper or plastic covered soft steel wire, aluminum band, etc.). Prior to or during the closure operation, excess air within the bag shall be expelled.

5.1.1.2 Interior packaging.- Each roll of electrosensitive recording paper, unit packaged as specified in 5.1.1.1, shall be interior packaged in a fiberboard box conforming to style RSC (end opening), type CF, class domestic, variety SW, grade 175 of PPP-B-636. The top and bottom flaps of the box shall be secured with 2-inch minimum width gummed paper tape conforming to type III, grade B of PPP-T-45.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

5.1.2 Level C.- Each roll of electrosensitive recording paper shall be packaged to afford adequate protection against deterioration and physical damage during shipment from the supply source to the first receiving activity. The supplier may use his standard practice when it meets this requirement.

5.2 Packing.- Packing shall be level A, B or C as specified (see 6.2).

5.2.1 Level A.- Ten size 1 rolls or 20 size 2 rolls of electrosensitive recording paper, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, grade V2s of PPP-B-636. Alternatively, when there are less than 10 size 1 rolls, a minimum of 8 size 1 rolls and a maximum of 4 size 2 rolls (to yield 5500-feet of the product) may be packed within the same container. Each shipping container shall be closed, waterproofed and reinforced in accordance with the appendix of the container specification.

5.2.2 Level B.- Ten size 1 rolls or 20 size 2 rolls of electrosensitive recording paper, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, type CF (variety SW) or SF, class domestic, grade 275 of PPP-B-636. Alternatively, when there are less than 10 size 1 rolls, a minimum of 8 size 1 rolls and a maximum of 4 size 2 rolls (to yield 5500-feet of the product) may be packed within the same container. Each shipping container shall be closed in accordance with the method II, as specified in the appendix of the container specification.

5.2.2.1 When specified (see 6.2), the shipping container shall be grade V3c or V3s fiberboard box fabricated in accordance with PPP-B-636 and closed in accordance with the appendix of the box specification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

5.2.3 Level C.- Rolls of electrosensitive recording paper, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. Containers shall be in accordance with rules or regulations of carriers applicable to the mode of transportation.

5.3 Marking.- In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with MIL-STD-129. Each interior box shall be identified by a mill roll number corresponding to the number on the fibre core.

6. NOTES

6.1 Intended use.- The dry process, electrosensitive recording paper covered by this specification is intended for use with sonar data recorders.. Size 1 is intended for use with AN/FQQ Sonar Data Recorders; Size 2 is intended for use with AN/FQQ Sonar Data Recorders and with AN/BQH-2C and AN/UQM-4 Analyzer Recorders.

6.2 Ordering data.- Procurement documents should specify the following:

a. Title, number, and date of this specification.

b. Size required (see 1.2 and 3.3.1).

c. Whether bid sample approval is waived (see 3.1).

d. Selection of the applicable levels of packaging and packing (see 5.1 and 5.2).

e. When weather-resistant grade V3c or V3s fiberboard shipping containers are required for level B packing (see 5.2.2.1).

6.3 Toxicity.- Questions pertaining to the adverse effect of materials on the health of personnel should be referred by the procuring activity to the appropriate departmental medical service who will act as an advisor to the procuring agency (see 3.2.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

6.4 Information concerning availability of specifications for GS 65387 Recorder may be obtained from Naval Electronics Systems Command, Code EPO3, 5805 Leesburg Pike, Baileys Crossroads, Virginia 22041.

Custodians:

Army - GL
Navy - SH

Preparing activity:

Army - GL

Project No. 7530-0138

Review activities:

Army - GL
Navy - SH

Review information is current as of the date of this document. For future coordination of changes to this document, draft circulation should be based on the information in the current Federal Supply Classification Listing of DOD Documents.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

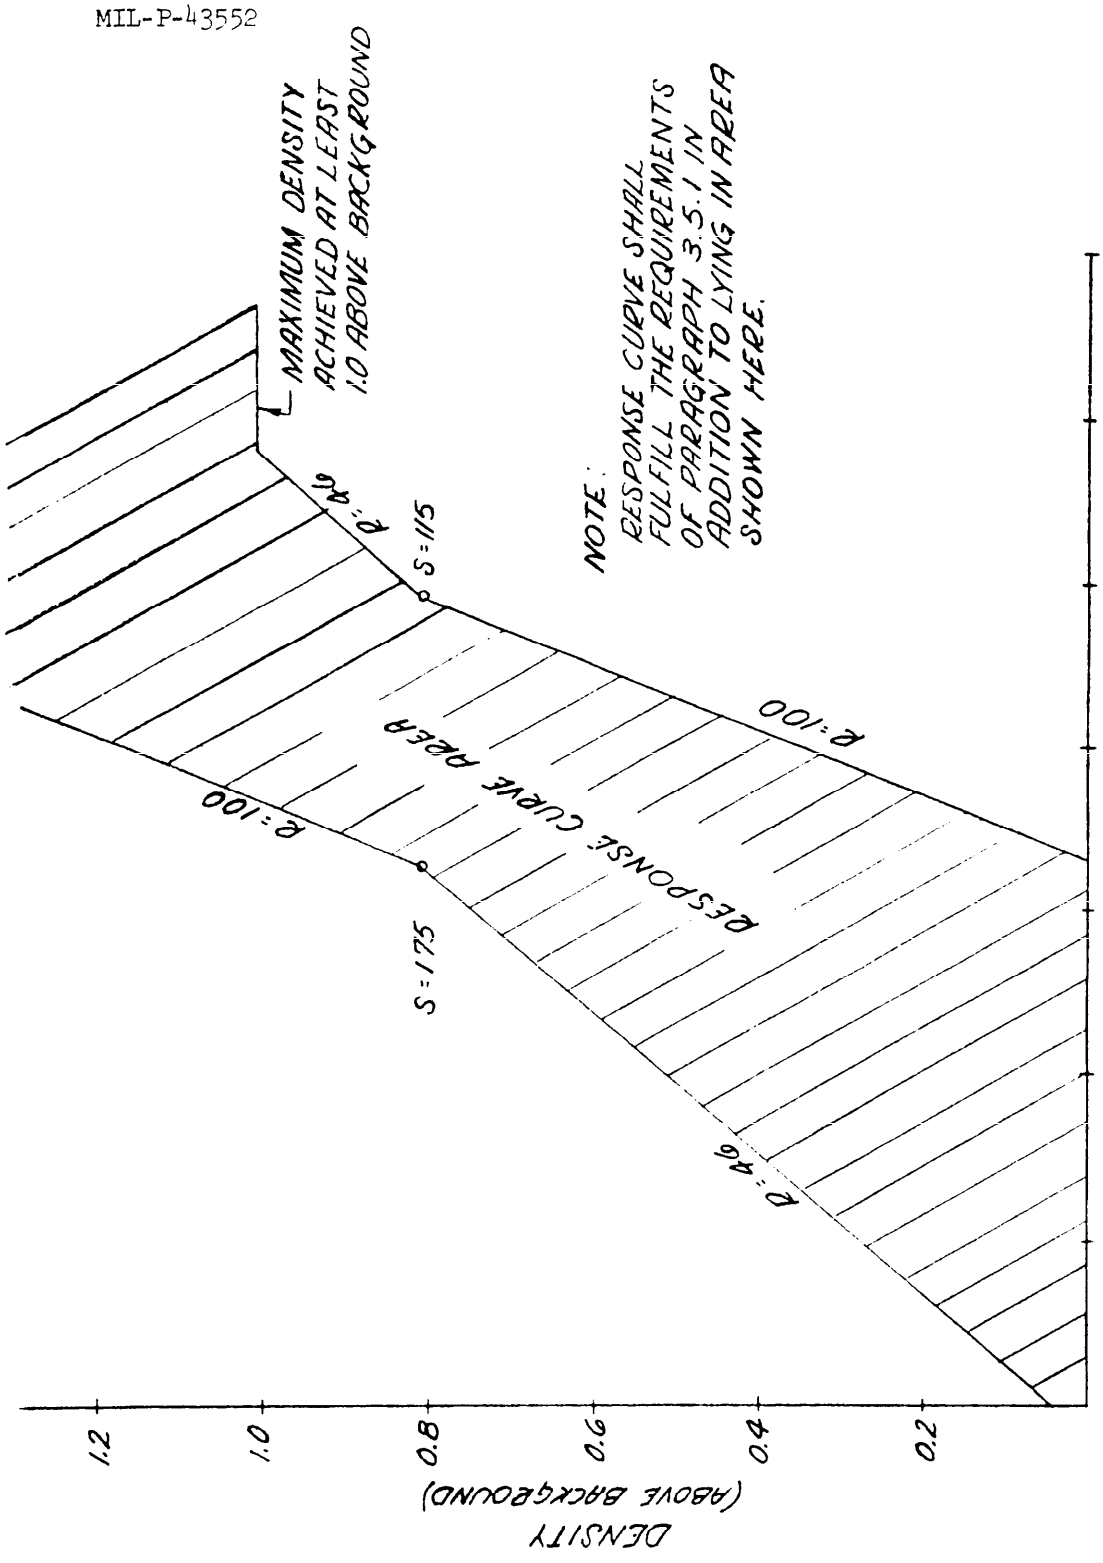


FIGURE 1. RESPONSE OF ELECTROSENSITIVE PAPER

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

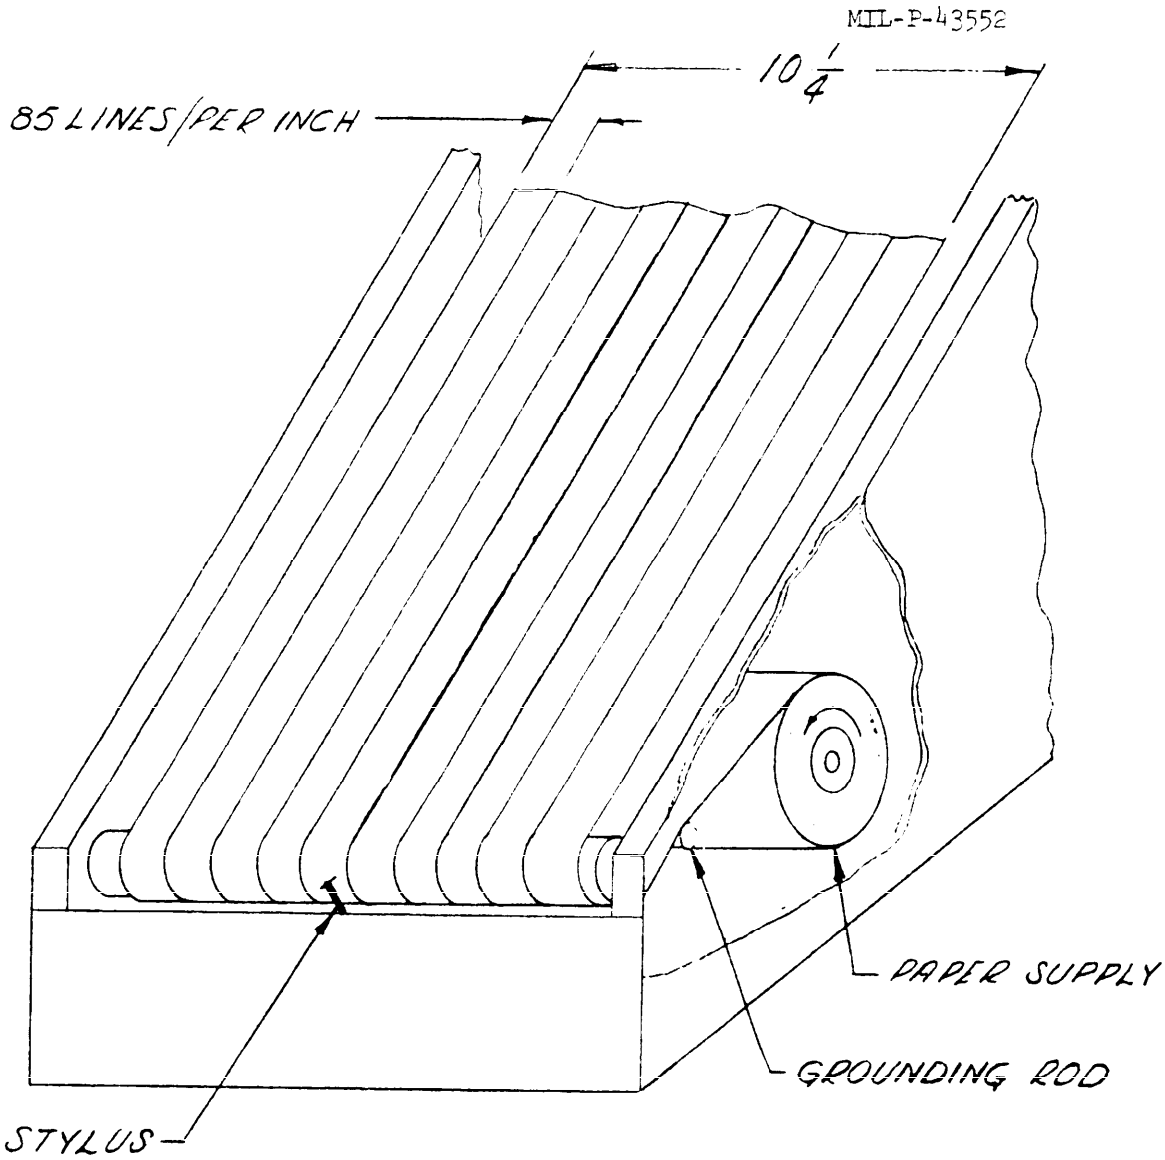


FIGURE 2: DEFINITION TEST OF PAPER RECORDING ELECTRO SENSITIVE

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION

Paper, Recording, Facsimile (Electrosensitive) - MIL-P-43552

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*

DATE

DD FORM 1 JAN 66 1426

REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 202610-21T21:41Z
Check the source to verify that this is the current version before use.

FOLD

DEPARTMENT OF THE ARMY
U. S. Army Natick Laboratories
Natick, Massachusetts 01760

POSTAGE AND FEES PAID
DEPARTMENT OF THE ARMY

OFFICIAL BUSINESS

Commanding General
U. S. Army Natick Laboratories
ATTN: AMXRES-EQS
Natick, Massachusetts 01760

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T21:41Z
Check the source to verify that this is the current version before use.