MILITARY SPECIFICATION

CLEANING COMPOUND, AIRCRAFT SURFACE, LOW TEMPERATURE

1. SCOPE

1.1 This specification covers the requirements for one grade of cleaning compound of the solvent base type to be used for cleaning aircraft surfaces at temperatures from +32° to 0°F.

2. APPLICABLE DOCUMENTS

* 2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

Federal

O-T-236	Tetrachloroethylene (Perchloroethylene), Technical Grade
O-T-634	Trichloroethylene, Technical
P-D-680	Dry Cleaning Solvent
QQ-A-250/4	Aluminum Alloy, 2024, Plate and Sheet
QQ-A-250/5	Aluminum Alloy, Alclad 2024, Plate and Sheet
QQ-A-250/13	Aluminum Alloy, Alclad 7075, Plate and Sheet
QQ-M-44	Magnesium Alloy Sheet and Plate (AZ31B)
QQ-P-416	Plating, Cadmium (Electrodeposited)
SS-P-821	Pumice, Ground, Abrasive
JJJ-C-561	Cotton, Sterile (Purified) and Nonsterile
PPP-D-729	Drum, Metal, 55-Gallon (For Shipmen of Noncorrosive Materials)

Military

MIL-E-9500	Ethylene Glycol, Technical
MIL-E-50011	Ethanolamines (Monoethanolamine, Diethanolamine, and Triethanolamine), Technical

STANDARDS

Federal

Fed. Test Method Standard No. 141	Paint, Varnish, Lacquer, and Related Materials; Methods of Inspection, Sampling, and Testing

Source: https://assist.dla.mil -- Downloaded: 202610-20T11:23Z
Check the source to verify that this is the current version before use.

STANDARDS

Military

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	Marking for Shipment and Storage
MS-35206	Screw, Machine-pan Head, Cross-recessed, Carbon Steel, Cadmium Plated UNC-2A
MS-35218	Screw, Machine-pan Head, Cross-recessed, Aluminum Alloy, Anodized, UNC-2A
MS-51957	Screw, Machine-pan Head, Cross-recessed, Corrosion Resisting Steel, Passivated UNC-2A

USAF ANA

AN340	Nut, Plain, Hexagon, Nonstructural, Coarse Thread
AN960	Washer, Flat

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

American Society for Testing and Materials (ASTM) Standards

D 92	Flash and Fire Points by Cleveland Open Cup
D 97	Pour Point
D 270	Sampling Petroleum and Petroleum Products

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pa. 19103.)

Consolidated Classification Committee

Uniform Freight Classification Rules

(Application for copies should be addressed to the Consolidated Classification Committee, 202 Chicago Union Station, Chicago Ill. 60606.)

Source: https://assist.dla.mil -- Downloaded: 202640-20T11:23Z
Check the source to verify that this is the currentversion before use.

3. REQUIREMENTS

3.1 Materials. The ingredient materials used in the manufacture of the cleaning compound shall be of high quality and shall conform to the requirements specified herein.

3.1.1 Toxic products and formulations. The material shall have no adverse effect on health of personnel when used for its intended purpose. Questions pertinent to this effect shall be referred by the procuring activity to the appropriate department medical service who will act as an advisor to the procuring activity.

3.1.2 Certification. The manufacturer shall certify that the ingredient materials have been included in the proportions specified in 3.2.

3.2 Chemical composition. The chemical composition of the cleaning compound shall conform to the limits of table I.

Table I. Chemical composition.

Ingredient Material	Percent	
	By Volume	By Weight
Petroleum solvent (See table II and 6.3.)	72.08 ± 0.5	67.96 ± 0.5
Diethylamine (See table III.)	0.85 ± 0.05	0.73 ± 0.05
Triethanolamine (See 3.3.1.1.)	1.08 ± 0.1	1.48 ± 0.1
Oleic acid (See table IV.)	5.42 ± 0.1	5.63 ± 0.1
Sodium heptadecyl sulfate-25% active anionic (See table V and 6.4.)	1.23 ± 0.1	1.56 ± 0.1
Ethylene glycol (See 3.3.1.2.)	0.66 ± 0.05	0.90 ± 0.05
Fatty alkylol amide condensate-100% active nonionic (See table VI and 6.5.)	15.28 ± 0.5	13.26 ± 0.5
Tertiary-alkyl primary amine (18-22 carbon) (See table VII and 6.6.)	3.40 ± 0.1	3.48 ± 0.1

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T11:23Z
Check the source to verify that this is the current version before use.

3.3 Properties

3.3.1 Ingredient materials. - The properties of the ingredient materials shall be as specified in tables II through VII, 3.3.1.1, and 3.3.1.2 (See 6.3 through 6.6).

Table II. Properties of petroleum solvent ingredient.

Property	Requirement
API gravity (60°/60° F)	49.9 to 52.3
Specific gravity (60°/60° F)	0.7700 to 0.7800
Color (Saybolt) (min)	+30
Doctor test (standard)	Sweet
Aniline cloud point (° F) (max)	196° F
Kauri-butanol value	21 to 24
Flash point (tag closed cup) (min)	185° F
Bromine number (max)	.5
Sulfur (% by wt) (max)	(.0015
Distillation range	
Initial point (min)	420° F
50% point (max)	450° F
Dry point (max)	475° F

Table III. Properties of diethylamine ingredient.

Property	Requirement
Specific gravity (20°/20° C)	0.70 to 0.71
Distillation range	53.0° to 59.5° C
Refractive index (18° C) (max)	1.387
Flash point (Cleveland open cup) (min)	5° F
Assay (% by wt) (min)	98
Freezing point (max)	-49.8° C
pH of 0.01N aqueous solution (max)	11.1

Table IV. Properties of oleic acid ingredient.

Property	Requirement
Unsaponifiables (max)	1%
Acid value	196 to 204
Saponification value	197 to 206
Cloud point	35° to 43° F

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T11:23Z
Check the source to verify that this is the current version before use.

Table V. Properties of sodium heptadecyl sulfate ingredient.

Property	Requirement
Active ingredient (% by wt)	25 to 2.
Specific gravity (20°/20° C)	1.044 to 1.048
pH of 0.1% aqueous solution (max)	5.3
Alkalinity (as Na_2CO_3, % by wt)	0.4 to 0.1
Color (pt-co scale) (max)	150
Iron (ppm) (max)	0.5

Table VI. Properties of fatty alkylol amide condensate ingredient.

Property	Requirement
Specific gravity (60°/60° F)	0.978 to 0.982
pH of 1% aqueous solution (max)	9.3
Refractive index (20° C)	1.472 to 1.477

Table VII. Properties of tertiary-alkyl primary amine ingredient.

Property	Requirement
Boiling range (5 to 70%, 760 mm)	265° to 305° C
Specific gravity (25°/25 C)	0.838 to 0.842
Refractive index (25° C)	1.455 to 1.457
Flash point (tag open cup) (min)	265° F
Carbon chain length (tertiary)	18 to 22
Neutral equivalent (vacuum distillation) (max)	315
Color (varnish scale) (max)	11

* 3.3.1.1 Triethanolamine. - The triethanolamine ingredient shall conform to MIL-E-50011.

3.3.1.2 Ethylene glycol. - The ethylene glycol ingredient shall conform to MIL-E-9500.

3.3.2 Cleaning compound. - The properties of the cleaning compound shall be as specified in table VIII.

Source: https://assist.dla.mil -- Downloaded: 20260-20T11:23Z
Check the source to verify that this is the current version before use.

Table VIII. Properties of the cleaning compound.

Property	Requirement
Appearance and condition at 77° ± 2° F	Homogeneous, clear, yellow to pale amber, free flowing fluid
Appearance and condition at 0° ± 2° F	Homogeneous, viscous, free flowing, clear liquid
Specific gravity (25°/25° C)	0.820 to 0.832
Flash point (Cleveland open cup) (min)	180° F
Pour point (min)	-30° F
Temperature stability:	
Cold stability (-65° ± 3° F)	No separation nor precipitation
Heat stability (110° ± 3° F)	No separation nor precipitation
Corrosion:	Maximum weight loss per panel (1 by 2 by .032 in.) mg
Clad aluminum alloy (2024-T3)	1.0 mg
Clad aluminum alloy (7075-T6)	1.0 mg
Cadmium-plated steel	3.0 mg
Magnesium alloy (AZ31-H)	2.0 mg
Magnesium and aluminum alloy (2024-T3) couple	Mg 2.0 mg and Al 1.0 mg

3.4 Workmanship. - The ingredient materials shall be assembled and processed in accordance with high-grade commercial practice to produce a cleaning compound uniform in quality and free of foreign matter.

4. QUALITY ASSURANCE PROVISIONS

* 4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to specified requirements. Inspection records of the examination and tests shall be kept complete and available as specified in the contract or order.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T11:23Z
Check the source to verify that this is the current version before use.

4.1.1 Except where otherwise indicated, the provisions of this section are applicable to the cleaning compound. The quality assurance of ingredient materials covered by applicable specifications shall be in accordance with such specifications. Sampling and inspection of ingredient materials not covered by separate specification shall be as specified herein.

4.2 Toxicological data and formulations. The materials to be used are not harmful to the health of personnel when used for its intended purpose. If necessary, the supplier shall furnish toxicological data to evaluate the safety of the material for the proposed use.

4.3 Sampling.

4.3.1 Ingredient materials. Sampling of ingredient materials not covered by this specification shall be in accordance with ASTM D 270. The samples so selected shall be subjected to test as specified in 4.5.1 prior to compounding.

4.3.2 Cleaning compound. A 1-gallon sample of the cleaning compound shall be selected in accordance with method 1021, Fed. Test Method Standard No. 141. The samples shall be subjected to all tests specified in 4.5, except 4.5.1.

4.3.3 Filled containers. A random sample of filled containers shall be selected in accordance with MIL-STD-105 at inspection level and acceptance quality level of 2.5 percent defective to verify compliance with this specification in regard to fill, closure, marking, and other requirements not involving tests.

4.4 Examinations.

4.4.1 Sample examination. Each sample selected in accordance with 4.3.2 shall be visually examined for compliance with 3.4.

4.4.2 Examination of filled containers for delivery. Each sample selected in accordance with 4.3.3 shall be visually examined for defects of construction of the container and the closure, for evidence of leakage, for unsatisfactory markings, and all other preparation for delivery requirements (see 5.1). Each sample filled container shall be weighed to determine the amount of contents. Any container in the sample having one or more defects, or under the required fill, shall be rejected, and if the number of defective containers in any sample exceeds the acceptance number for the specified sampling plan of MIL-STD-105, the lot represented by the sample shall be rejected. Rejected lots may be resubmitted for acceptance, provided the contractor has removed or reworked all nonconforming products.

Source: https://assist.dla.mil -- Downloaded: 202640-20T11:23Z
Check the source to verify that this is the current version before use.

4.5 Tests.

4.5.1 Properties of ingredients. The properties of ingredient materials not covered by separate specifications shall be determined by any standard laboratory method acceptable to the procuring activity.

4.5.1.1 Certified test report. The manufacturer shall prepare a certified test report showing that all ingredient materials conform to the applicable requirements of section 3.

4.5.2 Appearance and condition.

4.5.2.1 At $77^{\circ} \pm 2^{\circ}F$ ($25^{\circ} \pm 1^{\circ}C$). A 100 milliliter (ml) of the cleaning compound shall be placed in a 100-ml glass-stoppered, graduated mixing cylinder. The compound shall stand for 24 hours at $77^{\circ} \pm 2^{\circ}F$ ($25^{\circ} \pm 1^{\circ}C$). At the end of this period, the compound shall be visually examined under normal room lighting. The compound shall be a clear, yellow to pale amber fluid that shows no separation nor layering.

4.5.2.2 At $0^{\circ} \pm 2^{\circ}F$ ($-17.2^{\circ} \pm 1^{\circ}C$). The test specified in 4.5.2.1 shall be formed on a separate sample of cleaning compound, except the exposure temperature shall be $0^{\circ} \pm 2^{\circ}F$ ($-17.2^{\circ} \pm 1^{\circ}C$). At the end of the exposure period, the cleaning compound shall be a clear, yellow to pale amber, viscous but free-flowing fluid that shows no separation nor layering.

4.5.3 Specific gravity. Specific gravity shall be determined by any laboratory method accurate to within $\pm$ 0.01 units at $77^{\circ}F$ ($25^{\circ}C$).

* 4.5.4 Flash point. Flash point shall be determined in accordance with ASTM D 92.

* 4.5.5 Pour point. Pour point shall be determined in accordance with ASTM D 97.

4.5.6 Temperature stability.

4.5.6.1 Cold stability. A 100 ml of the cleaning compound shall be placed in a 100 ml, graduated mixing cylinder and loosely glass stoppered. The cylinder shall be placed in a cold chamber at $65^{\circ} \pm 3^{\circ}F$ ($-54^{\circ} \pm 2^{\circ}C$) and maintained at that temperature for 48 hours. At the end of the test period, the cylinder shall be removed from the cold chamber and allowed to return to $77^{\circ} \pm 2^{\circ}F$ ($25^{\circ} \pm 1^{\circ}C$). Upon visual examination, the compound shall show no evidence of separation, layering, nor precipitation after reaching ambient temperature.

Source: https://assist.dla.mil -- Downloaded: 20260-20T11:23Z
Check the source to verify that this is the current version before use.

4.5.6.2 Heat stability. A 100 ml of the cleaning compound shall be placed in a 100 ml, graduated mixing cylinder and glass stoppered. The cylinder shall be placed in an oven maintained at 110° ± 3°F (43° ± 2°C) for 6 hours. At the end of the test period, there shall be no visual evidence of separation, layering, nor precipitation of the compound.

4.5.7 Corrosion.

4.5.7.1 Selection of test panels. Test panels (1x2x .032 inches) shall be taken as follows:

a. Two each from clad aluminum alloy conforming to T3 of QQ-A-250/5.
b. Two each from clad aluminum alloy conforming to T6 of QQ-A-250/13.
c. Two each from steel cadmium plated in accordance with Class 1, Type I of QQ-P-416.
d. Two each from bare aluminum alloy conforming to T3 of QQ-A-250/4.
e. Four each from magnesium alloy conforming to condition H of QQ-M-44.

* 4.5.7.2 Preparation of test panels. The test panels selected in accordance with 4.5.7.1 shall be prepared as follows:

a. Drill the bare aluminum alloy panels (QQ-A-250/4) and two of the magnesium alloy panels (QQ-M-44) as shown in figure 1.
b. Remove ink markings and grease from all aluminum panels by immersion in trichloroethylene conforming to O-T-634 or perchloroethylene conforming to O-T-236 and rubbing dry with a clean wiping cloth.
c. Remove the factory applied protective film from the magnesium panels by a 15 minute immersion in a near-boiling aqueous solution of 25 percent by weight chromic acid and 1 percent by weight silver nitrate, followed by a thorough rinse with distilled water.
d. Polish all test panels with pumice conforming to Grade FFF, (or finer) of SS-P-821, carried on pads of nonsterile absorbent cotton conforming to JJJ-C-561, moistened with a 50 percent solution of isopropyl alcohol and distilled water.
e. Polish the magnesium alloy and cadmium plated panels only enough to remove residual chemical or oxide film from the surfaces.
f. Rinse all panels thoroughly with distilled water; follow with a warm denatured alcohol or acetone rinse, and flash dry.
g. Permanently mark the panels for identification. Weigh analytically.

* 4.5.7.3 Single panel corrosion test. The clad-aluminum, cadmium-plated-steel, and two magnesium alloy (not drilled) panels shall be placed singly in 2-oz widemouthed, tall form, glass, screw-top bottles.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T11:23Z
Check the source to verify that this is the current version before use.

Sixty ml of the cleaning compound shall be added to each bottle, tightly capped, and tested as follows:

a. Place bottles in an oven at 140° ± 3°F (60° ± °C).
b. Maintain at this temperature for 24 hours.
c. Remove panels from the bottles, wash in petroleum solvent conforming to P-D-680, rinse in warm denatured alcohol or acetone, and flash dry.
d. Reweigh panels and calculate weight losses.

4.5.7.4 Dissimilar metal corrosion test.

4.5.7.4.1 Coupling of test panels. The bare aluminum alloy panels and the two drilled magnesium alloy panels (see 4.5.7.2) shall be positioned and assembled as shown on figure 2. The assembles shall be tightened with a torsion screw driver to 6 inch-pounds torque (see 6.7). The contact area between the dissimilar metals shall be approximately 1-square inch. Each couple shall be checked to assure good electrical continuity.

* 4.5.7.4.2 Test procedure. Each couple shall be placed in individual, 4-oz, widmouthed, tall form, glass, screw-top bottles. One hundred twenty ml of the cleaning compound shall be added to each bottle, tightly capped and tested as follows:

a. Place the bottles in an oven at 140° ± 4°F (60° ± 2°C).
b. Maintain at this temperature for 24 hours.
c. Remove couples from the bottles, disassemble, wash in petroleum solvent conforming to P-D-680, rinse in warm denatured alcohol or acetone, and flash dry.
d. Reweigh panels and calculate weight losses.

4.6 Rejection. Failure of any sample to meet the specified tests shall be cause for rejection of the lot represented.


5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C as specified (see 6.2).

5.1.1 Level A. Unless otherwise specified, the cleaning compound shall be packaged in 55-gallon drums conforming to PPP-D-729.

5.1.2 Level C. Unless otherwise specified, packaging shall be in accordance with the manufacturer's commercial practice.


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T11:23Z
Check the source to verify that this is the current version before use.

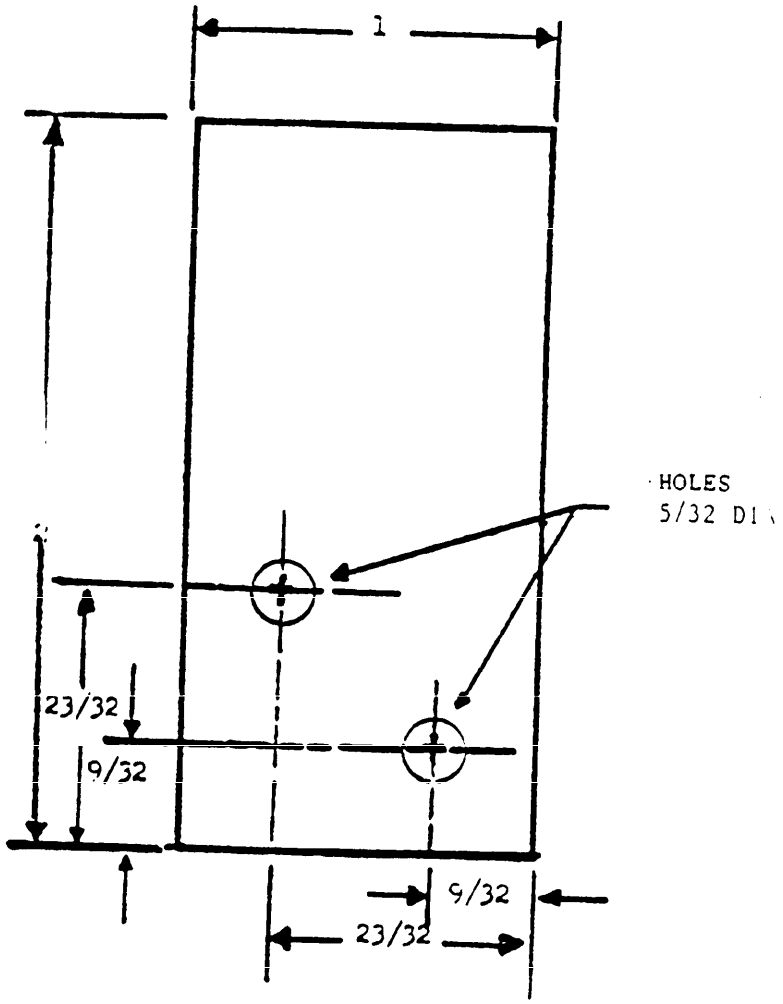

DIMENSIONS IN INCHES, UNLESS OTHERWISE SPECIFIED.
TOLERANCES: DIMENSIONS SHOWN SHALL BE NOMINAL EXCEPT THAT TOLERANCES FOR THE 2 BOLT HOLES SHALL BE WITHIN LIMITS THAT WILL PERMIT ASSEMBLY OF THE PANELS AS SHOWN ON FIGURE 2.

FIGURE 1. DIMENSIONS FOR DISSIMILAR METAL TEST PANELS

Source: https://assist.dla.mil -- Downloaded: 20260-20T11:23Z
Check the source to verify that this is the current version before use.

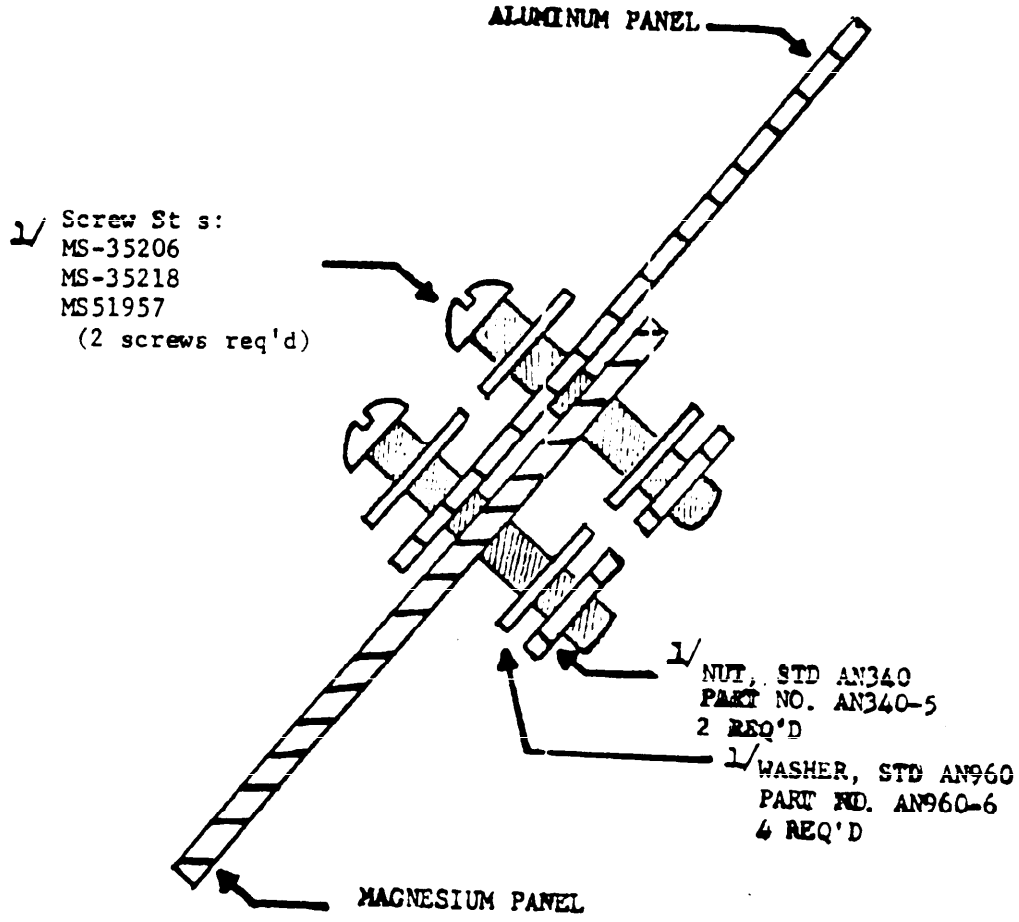

1/ EXCEPT CADMIUM PLATING SHALL BE CLASS 1, TYPE I OF SPECIFICATION QQ-P-416.

FIGURE 2. COUPLING OF DISSIMILAR METAL TEST PANELS

Source: https://assist.dla.mil -- Downloaded: 202610-20T11:23Z
Check the source to verify that this is the currentversion before use.

5.2 Packing. Packing shall be levels A, B, or C as specified (see 6.2).

5.2.1 Levels A and B. Cleaning compound packaged in accordance with 5.1.1 will require no overpacking.

5.2.2 Level C. The compound packaged in accordance with 5.1.2 shall be packed to afford protection against damage during direct shipment from the supply source to the first receiving activity for immediate use. Containers shall comply with Consolidated Freight Classification Rules or other common carrier regulations applicable to the mode of transportation.

5.3 Marking. Containers shall be marked in accordance with MIL-STD-129. The shipment marking nomenclature shall be: Cleaning Compound, Aircraft Surface, Low Temperature.

5.3.1 Additional marking. Each container shall be marked with the following:

USING INSTRUCTIONS

1. Spray the surface until a thin, continuous film of the compound has been deposited.
2. Brush the treated surface with 10 to 12 inch diameter round, soft bristle brushes.
3. After the compound has been on the surface for a minimum of 10 minutes, spray a thin coating of rinse fluid over the surface and repeat the brusing.
4. Flush the compound from the surface by means of a high-pressure spray of the rinse fluid and allow to air dry.
5. In the absence of spray equipment, steps 1 and 2 may be combined by applying the compound with a brush.

6. NOTES

6.1 Intended use. The cleaning compound covered by this specification is intended for use in cleaning aircraft surfaces at temperatures between $\pm 32^{\circ}$ and 0°F. After application of the cleaning compound, the surfaces are to be rinsed with either fluid conforming to MIL-A-8243 or solvent conforming to P-D-680, Type II.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number and date of this specification.
b. Responsibility for inspection records (see 4.2).
c. Applicable levels of packaging or packing (see section 5).

Source: https://assist.dla.mil -- Downloaded: 202610-20T11:23Z
Check the source to verify that this is the current version before use.

6.2.1 Unit of purchase. Unit of purchase is the U. S. Gallon of 231 cubic inches at 15.6°C (60°F).

6.3 Soltrol 170, produced by Phillips Petroleum Co. Bartlesville, Oklahoma, is known to meet the requirements of table II.

6.4 Tergitol 7, produced by Union Carbide Chemical Co., 100 E. 42nd St., New York, New York, is known to meet the requirements of table V.

6.5 Aerosol O, manufactured by Ciegy Chemical Corp., Ardsley, N.Y., is known to meet the requirements of table VI.

6.6 Primene JMT, manufactured by Rohm & Haas Co., Philadelphia, Pa., is known to meet the requirements of table VII.

6.7 The torsion screw driver specified in 4.5.7.4.1 should be of a 0 to 12 inch-pound torque type. A screw driver of this type, manufactured by Apco-Mossberg Co., Attleboro, Mass., had been found to be satisfactory.

6.8 Marginal indicia. Asterisks (*) are used in this revision to identify changes (additions, deletions) with respect to the previous issue.

Custodian:
Air Force - 11

Review activity:
Air Force - 68, 84

Preparing activity:
Air Force - 11

Project Nr.: 6850-F435

Source: https://assist.dla.mil -- Downloaded: 20260-20T11:23Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil - Downloaded: 2026-02-10T11:23Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE AIR FORCE

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 73236 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE AIR FORCE

4950/TZSM
Wright-Patterson AFB, OH 45433

Source: https://assist.dla.mil -- Downloaded: 20260-20T11:23Z
Check the source to verify that this is the current version before use.