MILITARY SPECIFICATION

HOSE ASSEMBLY, TETRAFLUOROETHYLENE TUBE, NONCOLLAPSIBLE, HIGH TEMPERATURE

This specification is approved for use by the Naval Sea Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers tetrafluoroethylene (TFE) hose assemblies for low pressure, vacuum steam systems in marine piping systems. They may be used for other systems where the pressure, temperature, and vacuum conditions do not exceed the limitations of the hose.

2. APPLICABLE DOCUMENTS

2.1 Issues of documents. The following documents, of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

MILITARY

MIL-P-775 - Packaging of Hose, Hose Assemblies; Rubber, Plastic Fabric or Metal (Including Tubing); And Fittings, Nozzles, and Strainers.
MIL-S-901 - Shock Tests, H.I. (High-Impact); Shipboard Machinery, Equipment and Systems, Requirements for.
MIL-I-45208 - Inspection System Requirements.

STANDARD

MILITARY

MIL-STD-167-1 - Mechanical Vibrations of Shipboard Equipment (Type I - Environmental and Type II - Internally Excited).

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

A167 - Stainless and Heat-Resisting Chromium-Nickel Steel Plate, Sheet and Strip.
A269 - Seamless and Welded Austenitic Stainless Steel Tubing for General Service.
A276 - Stainless and Heat-Resisting, Steel Bars and Shapes.
A296 - Corrosion-Resistant Iron-Chromium, Iron-Chromium-Nickel and Nickel-Base Alloy Castings for General Application.
A313 - Chromium-Nickel Stainless and Heat-Resisting Steel Spring Wire.
A494 - Nickel and Nickel Alloy Castings.
B16.5 - Steel Pipe Flanges and Flanged Fittings.
B164 - Nickel-Copper Alloy Rod and Bar.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Naval Sea Systems Command, SEA 3112, Department of the Navy, Washington, DC 20362 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Qualification. Hose assemblies furnished under this specification shall be products which are qualified for listing on the applicable qualified products list at the time set for opening of bids (see 4.3 and 6.3).

3.2 Material. Materials for the hose assembly components shall be as shown on table I.

TABLE I. Materials.

Component	Material	Specification
Hose tube	Tetrafluoroethylene (TFE)	Virgin material only
End fitting	Stainless steel	ASTM A276, type 316 or 304 ASTM A269, grade 316 or 304
Elbow	Stainless steel	ASTM A269, grade 316 or 304 ASTM A296, grade CF-8M or CF-8
Reinforcing wire	Stainless steel	ASTM A313, type 304
Support coil	Stainless steel	ASTM A313, type 302
Flange	Monel	ASTM B164, class A ASTM A494, alloy M-35
Identification tag	Stainless steel	ASTM A167, type 301

3.2.1 Recovered materials. Unless otherwise specified herein, all equipment, material, and articles incorporated in the products covered by this specification shall be new and shall be fabricated using materials produced from recovered materials to the maximum extent practicable without jeopardizing the intended use. The term "recovered materials" means materials which have been collected or recovered from solid waste and reprocessed to become a source of raw materials, as opposed to virgin raw materials. None of the above shall be interpreted to mean that the use of used or rebuilt products is allowed under this specification unless otherwise specifically specified.

3.2.1.1 TFE shall be virgin material.

3.3 Construction.

3.3.1 Hose assemblies. Hose tube shall consist of a TFE/innerlayer bonded to an outer-layer of fiberglass cloth. The hose shall meet the requirements of table II. The tube shall be of a convoluted construction and shall be reinforced externally with one or more layers of stainless steel wire braid.

3.3.1.1 Leg length. Unless otherwise specified (see 6.2.1(b)), leg length shall be in accordance with figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

TABLE II. Mechanical properties.

Size nominal	Working pressure	Proof pressure	Burst at 70°F minimum	Bend radius minimum	TFE wall thickness	Collapse pressure (external)	Support coil strap size	Vacuum in Hg	Reduction in volume	Maximum temperature °F
Inches	lb/in^2	lb/in^2	lb/in^2	Inch	Mils	lb/in^2	Inch		Maximum	
2	500	1000	2000	10	60	350	0.040 x 0.500	29	20 percent	380

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

3.3.2 End fittings. End fittings shall be of the materials specified in table I and shall be permanently attached by swaging or crimping.

3.3.2.1 Flanges. Flanges shall be in accordance with ASTM B16.5, 150 pounds or 600 pounds as specified (see 6.2.1).

3.3.3 Elbows. Elbow fitting hose assembly shall be of the materials specified in table I and shall be permanently attached by swaging or crimping.

3.3.4 Internal support coil. Internal support coil shall be of the material specified in table I and of the strap size specified in table II. Coil shall be fabricated in accordance with figure 2.

3.3.5 Identification tag. Identification tag of the material specified in table I and containing the following information shall be securely attached to each hose assembly:

(a) Number of this specification.
(b) Contractor's drawing number.
(c) Contractor's piece mark.
(d) Contract or order number.
(e) Contractor's name or trademark.

3.4 Physical and mechanical requirements.

3.4.1 Examination. When examined in accordance with 4.5 the hose assembly shall be free of oil and dirt. There shall be no weld spatter. Reinforcing braid shall be even and uniform with no broken or missing wires. Crimp or swage marks on the fittings shall be uniform in appearance indicating a firm marriage of the fitting to the hose.

3.4.2 Oven aging. There shall be no evidence of degradation of the hose after oven aging to 380°F in accordance with 4.6.1.

3.4.3 Proof pressure. When subjected to the proof pressure specified in table II, hose assembly shall not rupture, leak or show any other degradation when tested as specified in 4.6.2.

3.4.4 Vacuum. There shall be no evidence of hose collapse, leakage or other degradation of the hose when tested in accordance with 4.6.3.

3.4.5 Hose collapse. When tested in accordance with 4.6.4, there shall be no failure such as leakage of the hose liner and the internal volume of the hose shall not reduce by more than that specified in table II when pressurized externally to the collapse pressure specified in 4.6.4.

3.4.6 Bend radius. There shall be no wire breakage, coupling separation or other degradation when the hose assembly is tested in accordance with 4.6.5.

3.4.7 Flexibility. When tested as specified in 4.6.6, the torque to deflect the hose shall not exceed that specified in table III. All points on the torque deflection curve must not exceed those specified in table III.

TABLE III. Maximum deflection torque.

Size (inch)	Torque to deflect (in-lbs)			
	1/2-inch	1 inch	1-1/2 inch	2 inches
2	152	198	242	286

3.4.8 Flex cycling. There shall be no sign of hose degradation when the hose assembly is tested in accordance with 4.6.7.

3.4.9 Pressure vacuum cycling. There shall be no evidence of degradation of the hose assembly when the assembly is tested in accordance with 4.6.8.

3.4.10 Noise transmission characteristics. When tested in accordance with 4.6.9, noise transmission characteristics shall be recorded and presented as Blocked Force transmissibility. In this form, the structureborne transmission of dynamic forces through the hose is characterized in the frequency range between 20 and 5000 Hz without influence from any other structure or piping. The transmissibility level criteria, shown in figures

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

3 and 4, denote maximum allowable dynamic force transmission through the hose assembly for pressurized and vacuum conditions. The Blocked Force transmissibility response characteristics of the hose assembly shall be not greater than the allowable transmissibility criteria level in any of the five frequency bands.

3.4.11 Shock. There shall be no evidence of degradation of the hose assembly after high impact shock testing in accordance with 4.6.10.

3.4.12 Vibration. There shall be no evidence of degradation of the hose assembly when tested in accordance with 4.6.11.

3.4.13 Examination. After completion of the requirements of 3.4.1 through 3.4.12 there shall be no evidence of hose degradation when examined in accordance with 4.6.12.

3.4.14 Burst. When tested in accordance with 4.6.13 the hose shall not burst at a pressure less than that specified in table II.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements, as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Inspection system. The contractor shall provide and maintain an inspection system acceptable to the Government for supplies and services covered by this specification. The inspection system shall be in accordance with MIL-I-45208 (see 6.2.1).

4.2 Classification of inspections. Inspection requirements specified herein are classified as follows:

(a) Qualification inspection (see 4.3).
(b) Quality conformance inspection (see 4.4).

4.3 Qualification tests. Qualification tests shall be conducted at a laboratory satisfactory to the Naval Sea Systems Command (NAVSEA). Qualification shall consist of the examination and tests specified in table IV and shall be conducted in the order listed.

4.3.1 Sampling for qualification. A test sample consisting of two hose assemblies is required for qualification testing. One assembly shall be straight, measuring 36 inches long end to end. This assembly is not an item of production and shall be used only for the examination, proof pressure, vacuum, and hose collapse tests specified in 4.5, 4.6.2, 4.6.3, and 4.6.4. The other assembly shall be a 90 degree (dogleg) configuration, the production item, in accordance with figure 1 and shall be subjected to all the tests specified in table IV, except for the hose collapse test. The 36 inch straight hose assembly is required to preclude the fabrication of a costly test chamber to collapse test the dogleg production item.

4.4 Quality conformance tests. Each hose assembly submitted for delivery shall be examined and tested in accordance with the quality conformance inspection of table IV.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

TABLE IV. Qualification and quality conformance test sequence.

Tests	Test duration	Qualification	Quality conformance inspection	Requirement paragraph	Test paragraph
Examination	-----	X	X	3.4.1	4.5
Oven aging	24 hours	X	-	3.4.2	4.6.1
Proof pressure	5 minutes	X	X	3.4.3	4.6.2
Vacuum	5 minutes	X	X	3.4.4	4.6.3
Hose collapse	-----	-	-	3.4.5	4.6.4
Bend radius	-----	X	-	3.4.6	4.6.5
Flexibility	-----	X	-	3.4.7	4.6.6
Flex cycling	110,000 cycles	X	-	3.4.8	4.6.7
Pressure-vacuum cycling	2,000 cycles	X	-	3.4.9	4.6.8
Proof pressure	30 minutes	X	-	3.4.3	4.6.2
Vacuum	30 minutes	X	-	3.4.4	4.6.3
Noise transmission	-----	X	-	3.4.10	4.6.9
High shock	-----	X	-	3.4.11	4.6.10
Proof pressure	5 minutes	X	-	3.4.3	4.6.2
Vacuum	5 minutes	X	-	3.4.4	4.6.3
Vibration	510 hours	X	-	3.4.12	4.6.11
Proof pressure	5 minutes	X	-	3.4.3	4.6.2
Vacuum	5 minutes	X	-	3.4.4	4.6.3
Examination after test	-----	X	X	3.4.13	4.6.12
Burst	-----	X	-	3.4.14	4.6.13

4.5 Examination. Each hose assembly shall be visually examined. Wire braiding shall be even with no broken or missing wires. Assemblies shall be complete with no missing components. There shall be no oil, grease, weld spatter or other manufacturing debris. Assemblies rejected because of cleanliness may be resubmitted after recleaning. The hose tube shall be free of cuts and gouges.

4.6 Tests.

4.6.1 Oven aging. Hose assembly designated in table IV shall be oven aged at 380°F for a period of 24 hours.

4.6.2 Proof pressure. When proof pressure testing, the hose assemblies shall be tested to twice the rated working pressure of the hose, with the pressure being held for the time indicated in table IV.

4.6.3 Vacuum. When vacuum testing, the hose assemblies shall be tested to 29 inches Hg vacuum for the time indicated in table IV.

4.6.4 Hose collapse. Hose assembly designated for the collapse test shall be rigged in a pressure vessel similar to that shown on figure 5. Hose assembly shall be filled with clear water with the volume of water to fill the hose recorded. The pressure vessel shall then be filled with a dye colored water and pressurized. Hose collapse shall be measured at 15 pounds per square inch (lb/in^2), and the maximum collapse pressure specified in table II and is calculated as the percentage of the water within the hose assembly that is displaced due to external pressurization. The water within the hose shall be examined for dye indicating hose leakage.

4.6.5 Bend radius determination. Hose assembly shall be bent to the radius specified in table II. Bend radius is measured to the outside diameter surface nearest to the pivot point in lieu of the hose centerline.

4.6.6 Flexibility test (force deflection). One end of the 90 degree dogleg hose assembly shall be anchored. The assembly shall be filled with water and pressurized at rated working pressure specified in table II. The free end of the assembly shall be deflected from 0 through 2 inches and the force to deflect shall be measured and recorded at 1/2-inch intervals. The direction of the applied force shall be along the axis of the free end. This force shall be converted to the torque required based on the minimum hose leg length specified in figure 1. A torque deflection curve shall be developed from the data.

4.6.7 Flex cycling. Each test sample shall be flex tested as follows: One end of the configuration, 90 degree dogleg bend, shall be fixed. The other end shall be orbited in a circular motion having a 1 inch radius at a frequency of one cycle for a total of 110,000

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

cycles. 55,000 cycles shall be at ambient temperature and 55,000 cycles shall be at 380°F. Pressure shall be atmospheric. Additionally, once every 4 hour the hose configuration shall be pressure cycled 25 times between 35 lb/in^2 and 29 inch Hg vacuum and then returned to the flexing test. Temperature equilibrium is not required during pressure cycling. Test fluid shall be Monsanto Therminol 55 or equal.

4.6.8 Pressure/vacuum cycling. Following the flexure testing, each test sample shall be subjected to 29 inch Hg vacuum and 380°F and held for 30 minutes. The configuration shall then be pressure cycled 25 times between 29 inch Hg vacuum, and 35 lb/in^2, followed by another 30 minute hold period at 29 inch Hg vacuum and 380°F. This sequence of hold periods and 25 pressure cycles shall be repeated until a total of 1000 pressure/vacuum cycles have been accumulated. The configuration shall then be pressurized to 35 lb/in^2 and 380°F for 30 minutes followed by 25 pressure/vacuum cycles between 35 lb/in^2 and 29 inch Hg vacuum. This second sequence of 30 minute hold periods and 25 pressure cycles shall be repeated until another 1000 pressure cycles have been accumulated. Test fluid shall be Monsanto Therminol 55 or equal.

4.6.9 Noise transmission evaluation. The hose test sample shall be subjected to noise transmission evaluation in accordance with 4.6.9.1 and 4.6.9.2.

4.6.9.1 Definition of acceptance criteria. The procedure involves the determination of structureborne noise transmission through the hose configuration in terms of force transmissibility for a range of frequency from 20 to 5000 Hz. Force transmissibility is defined as the magnitude of dynamic forces developed at the output end of the hose configuration with that end "blocked" in such a manner that it is immovable, ratioed to the dynamic forces applied to the input of the hose. If the ratio exceeds one (0 dB), the hose configuration amplifies the transmitted input forces and if the ratio is less than one (0 dB), the hose reduces the input forces. The resulting transmissibility response shall be compared to the acceptance criteria "Maximum Allowable Dynamic Force Transmissibility" shown in figures 3 and 4.

4.6.9.2 Description of procedures. The DTNSRDC blocked force transmissibility procedure relies upon mechanical impedance and mobility techniques and specialized electronic instrumentation to define the structureborne noise transmission. The hose assembly, with ends blanked-off and at rated pressure specified in table II is supported free from all constraints by "shock cord", as shown in figure 6. A minimum of two vibration transmission paths can approximate the total structureborne transmission through the hose, those paths being represented by four impedance measurements (two driving point and two transfer impedance) measured at the input and output flanges of the hose configuration, designated by terminals 1, 2, 3, and 4, (see figure 6). An electro-magnetic shaker/impedance head unit is sequentially attached to terminals 1 and 2 at the input end of the hose configuration and imparts to the hose at each terminal, a swept sinusoidal excitation from 20 to 5000 Hz. The impedance head senses the dynamic force applied to the hose and the acceleration response of the hose at the same input terminal. The dynamic force and resulting acceleration signals are electronically processed to convert the acceleration to velocity and to ratio the force with the velocity to obtain "driving point impedance" defined as follows:

$$\frac{F1}{V1} = Z_{11} \text{ and } \frac{F2}{V2} = Z_{22}$$

To complete the measurements, two transfer impedance responses are required and are obtained by sensing the applied dynamic forces with the impedance head at each of the two input terminals, 1 and 2, and the resulting acceleration responses at the two output terminals, 3 and 4. The signals are again electronically processed and ratioed to yield transfer impedance defined as follows:

$$\frac{F1}{V3} = Z_{13} \text{ and } \frac{F2}{V4} = Z_{24}$$

The four free impedance responses are used with equations of motion of the hose in terms of the mobilities (inverse free impedances) at the hose input and output terminals. Mathematical boundary conditions are applied to the output terminals, described by the equations, to simulate a rigid termination to the hose. Computation of the dynamic forces developed at the blocked hose output ratioed to the computed input forces, yields a blocked force transmissibility which describes the structureborne transmission characteristics of the hose only, independent of all other influencing factors.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

4.6.10 High impact shock test. The designated sample hose assembly shall be subjected to three mechanical shock blows in each of three mutually perpendicular axis. With the assembly supported as for service, one end shall be rigidly fixed and the other end attached to the shock test table. The hose assembly shall be full of water and pressurized to its rated working pressure specified in table II. Shock tests shall be in accordance with MIL-S-901, grade A and as specified herein.

4.6.11 Vibration test. The designated hose assembly shall be vibrated in each of three mutually perpendicular axis in accordance with MIL-STD-167-1. The hose assembly shall be supported as for service with one end rigidly fixed and the other end attached to the vibration machine. The assembly shall be vibrated 50 percent of the total time for each axis filled with water and pressurized to its maximum working pressure specified in table II and 50 percent at 29 inch Hg vacuum.

4.6.11.1 Resonant frequency and magnification factor determination. The hose assembly shall be vibrated through the frequency range of 10 to 300 Hz to determine resonant frequency and magnification factor.

4.6.11.1.1 A constant force level (that required to produce 10 mils double amplitude at 10 Hz), shall be used for resonant frequency checks to provide comparative data.

4.6.11.1.2 Magnification factor shall be determined by dividing the amplitude (in mils) at the resonant frequency by the theoretical amplitude that would occur if there were no resonance at that frequency. The latter value shall be determined by connecting the low points of the amplitude-frequency curve that occur on either side of the resonant peak and using the amplitude at the point of intersection with the resonant frequency.

4.6.11.2 The assembly shall then be vibrated for 170 hours per axis at a frequency of 33 cycles with a plus or minus 0.030 inch peak amplitude.

4.6.12 Examination after test. At this point the hose assembly shall be thoroughly examined for evidence of coupling slippage, excessive wire breakage, deterioration of tube and other signs of degradation. Discoloration of the assembly or randomly broken wires are not considered cause for failure.

4.6.13 Burst test. The hose assembly shall be subjected to increasing internal hydrostatic pressure until failure occurs. Pressure shall be increased at a rate of not less than 1000 lb/in^2 or more than 10,000 lb/in^2 per minute.

4.7 Inspection of preparation for delivery. Preservation-packaging, packing, and marking shall be inspected for compliance with section 5 of this document.

5. PACKAGING

(The preparation for delivery requirements specified herein apply only for direct Government acquisitions.)

5.1 Preservation-packaging, packing, and marking. Hose assemblies shall be preserved-packaged level A or C, packed level A, B, or C as specified (see 6.2.1), and marked in accordance with MIL-P-775.

6. NOTES

6.1 Intended use. Hose assemblies acquired under this specification are intended for service in high temperature, low pressure or high vacuum shipboard steam systems.

6.2 Ordering data.

6.2.1 Acquisition requirements. Acquisition documents should specify the following:

(a) Title, number, and date of this specification.
(b) Leg lengths (see 3.3.1.1).
(c) One hundred and fifty or 600 pound flanges in accordance with ASTM B16.5 (see 3.3.2.1).
(d) Level of quality desired in accordance with MIL-I-45208 (see 4.1.1).
(e) Preservation, packaging, packing, marking if other than specified in section 5 (see 5.1).


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

6.3 With respect to products requiring qualification, awards will be made only for products which are at the time set for opening of bids, qualified for inclusion in applicable Qualified Products List QPL 24592 whether or not such products have actually been so listed by that date. The attention of the manufacturers is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. The activity responsible for the Qualified Products List is the Naval Sea Systems Command, SEA 3112, Department of the Navy, Washington, DC 20362, and information pertaining to qualification of products may be obtained from that activity. Application for Qualification tests shall be made in accordance with "Provisions Governing Qualification SD-6" (see 6.3.1).

6.3.1 Copies of "Provisions Governing Qualification SD-6" may be obtained upon application to Commanding Officer, Naval Publications and Forms Center, 5801 Tabor Avenue, Philadelphia, PA 19120.

Preparing activity:
Navy - SH
(Project 4720-N516)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

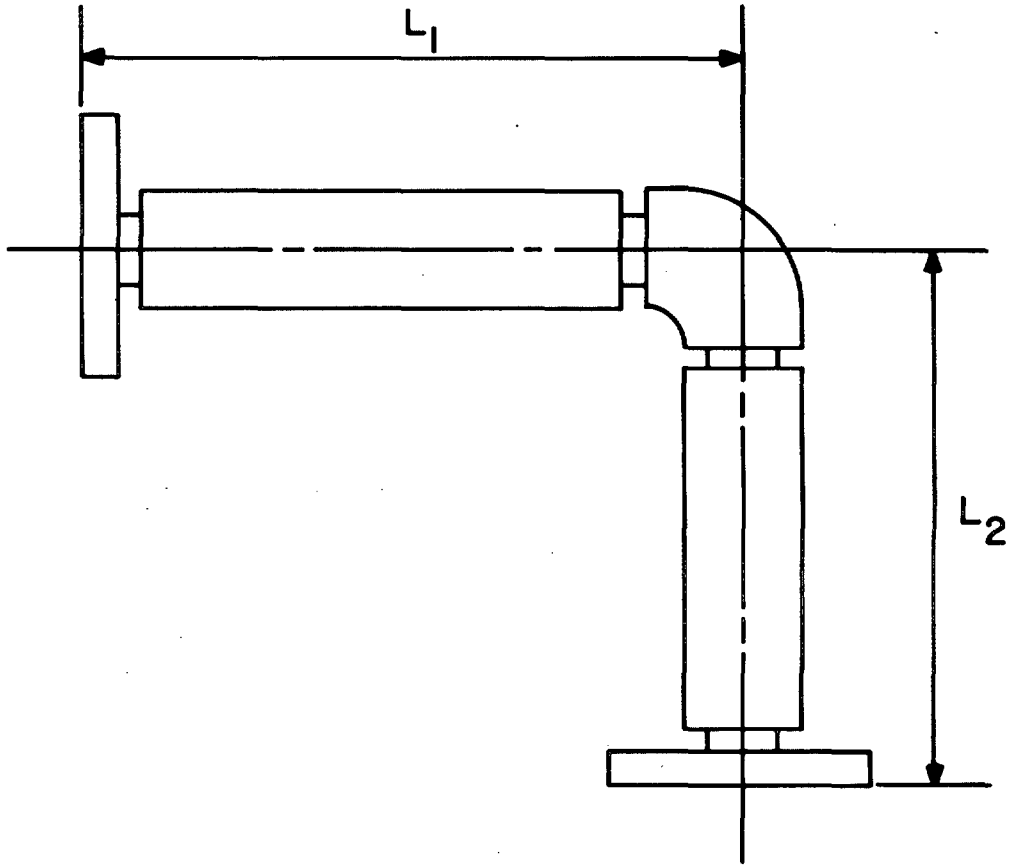


HOSE DIA.(IN.)	L_1 (IN. MIN)	L_2 (IN. MIN)
2	21 ± 1/4	21 ± 1/4

SH11309

FIGURE 1. Hose assembly.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

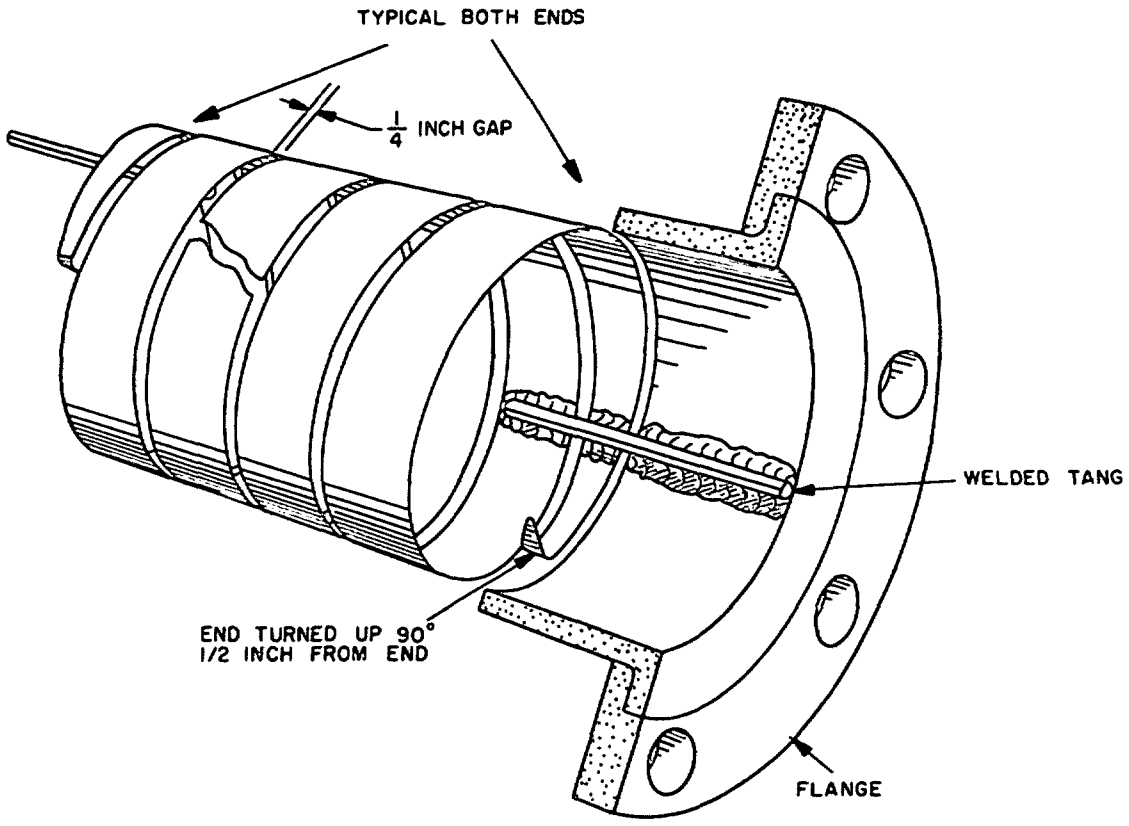

SH11391

FIGURE 2. Support coil attachment to end fitting.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

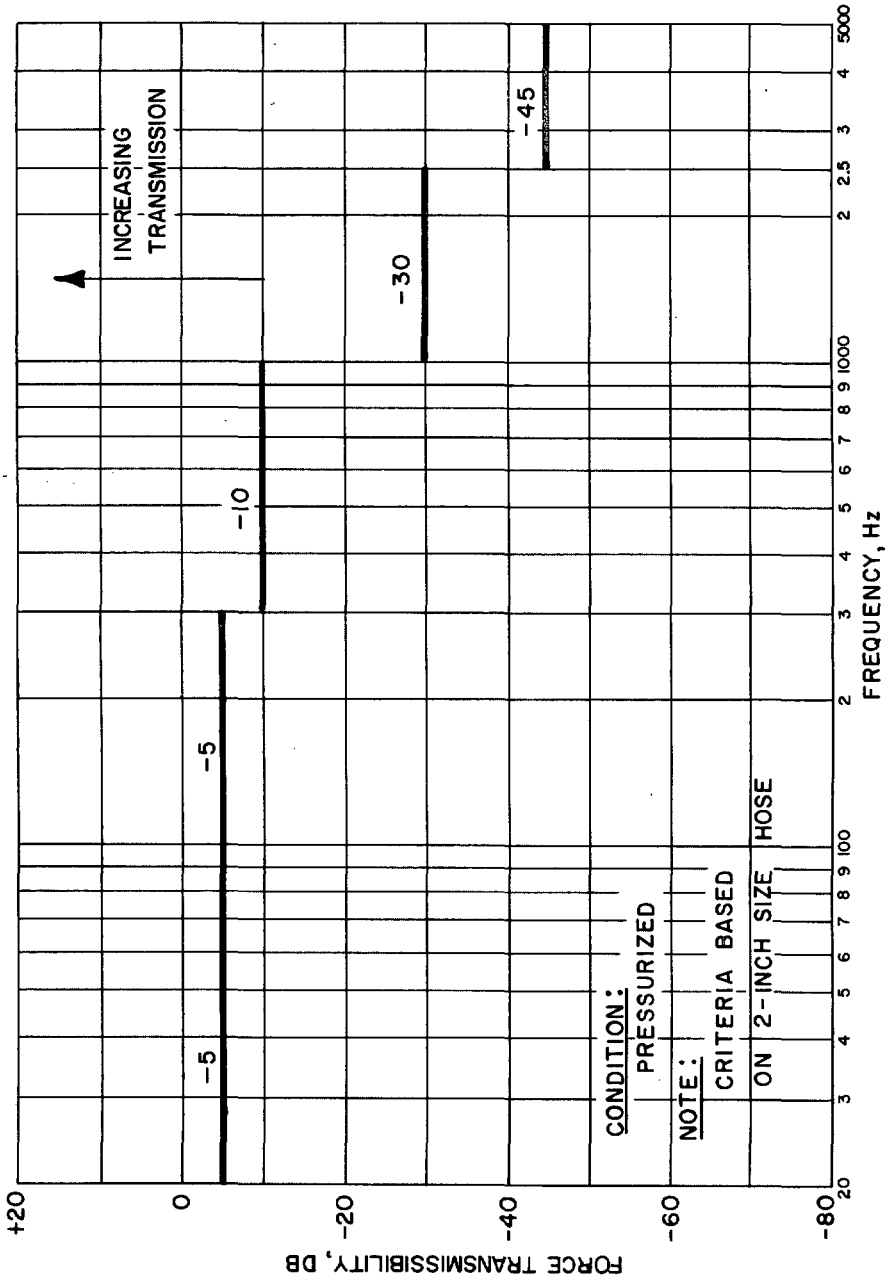

SH11392

FIGURE 3. Maximum allowable dynamic force transmissibility (for hose pressurized).


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

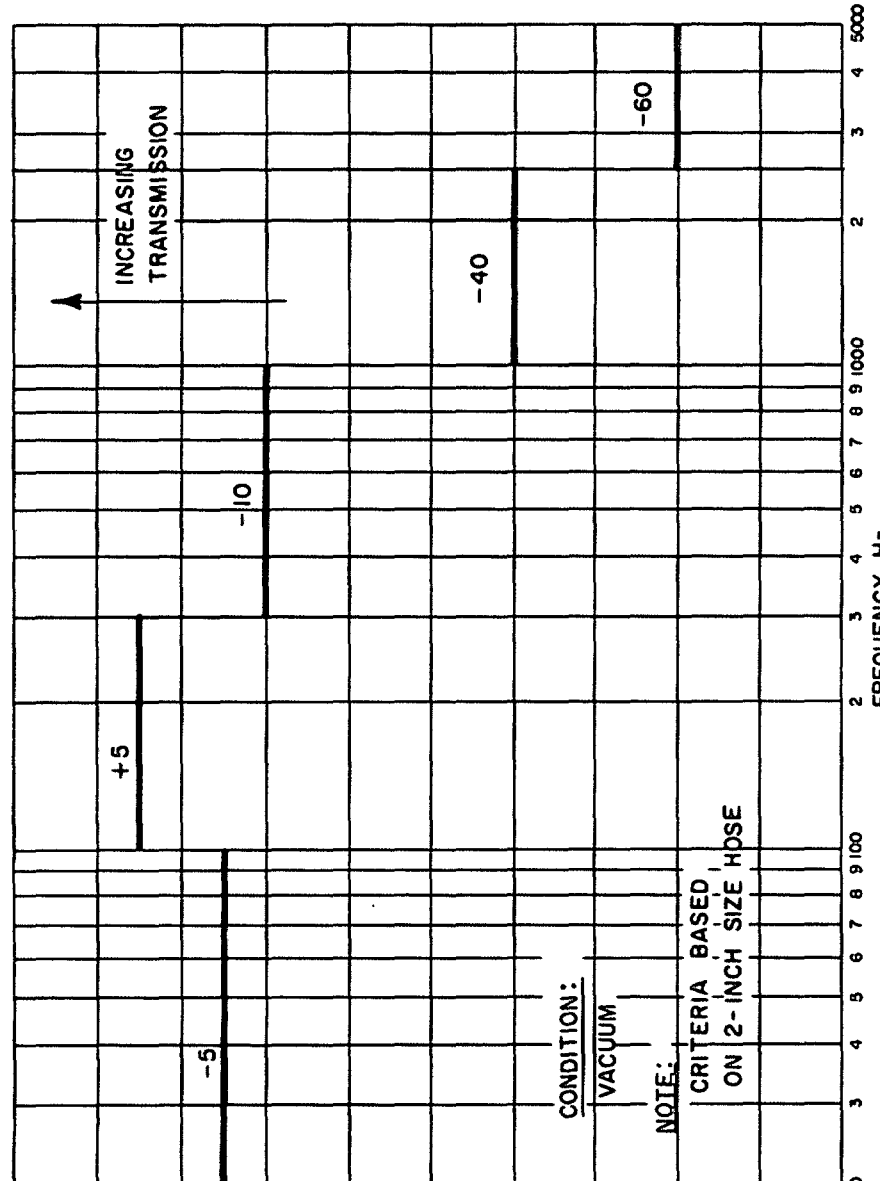

SH11393

FIGURE 4. Maximum allowable dynamic force transmissibility (for hose under vacuum).


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

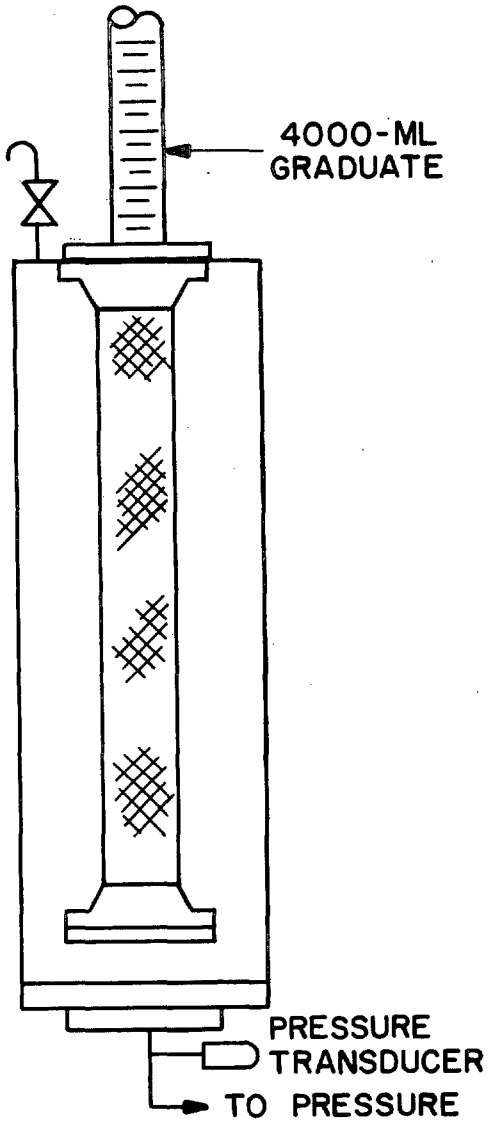

SH11394

FIGURE 5. Test rig for collapse test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

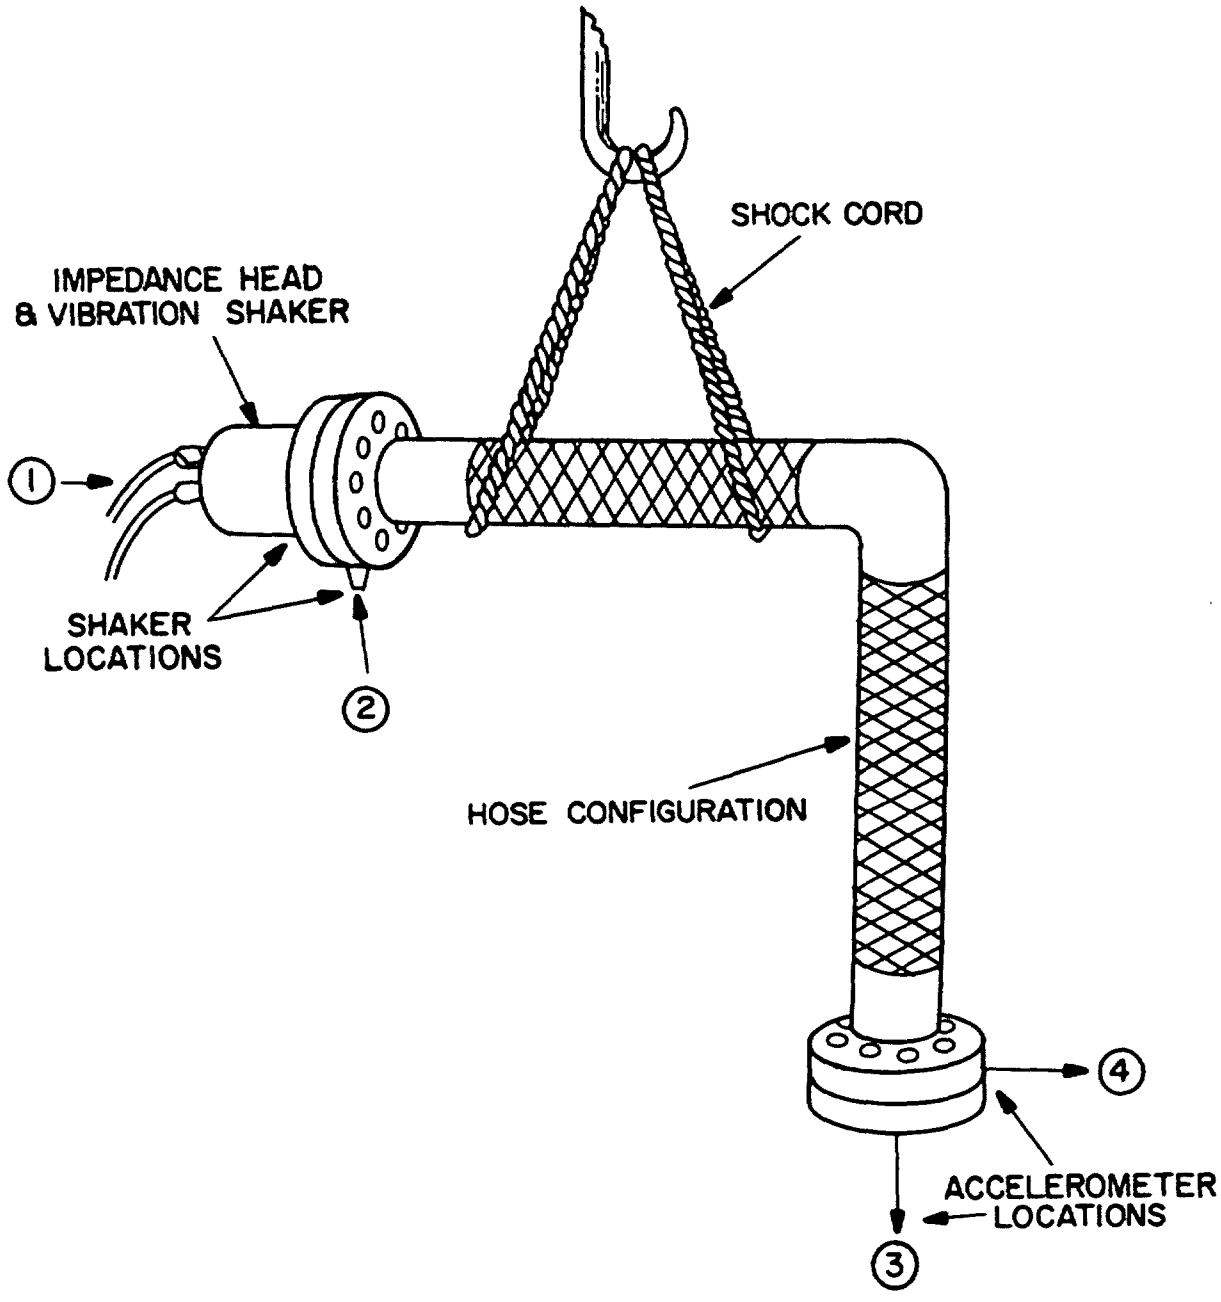

SH11395

FIGURE 6. Evaluation method for hose transmissibility.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. *If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.*

DOCUMENT IDENTIFIER AND TITLE

MIL-H-24592(SH)

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO *(If "Yes", in what way?)*

4. REMARKS

SUBMITTED BY *(Printed or typed name and address - Optional)*

TELEPHONE NO.

DATE

DD FORM 1 JAN 72 1426 REPLACES EDITION OF 1 JAN 66 WHICH MAY BE USED S/N 0102-014-1802

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T23:11Z
Check the source to verify that this is the current version before use.