[INCH-POUND]

A-A-1728A
May 29, 1992
SUPERSEDING
A-A-1728
August 7, 1981

COMMERCIAL ITEM DESCRIPTION

BAG, PLASTIC (BREAD)

The General Services Administration has authorized the use of this Commercial Item Description in preference to Size B of Military Specification MIL-B-43706.

This description covers plastic bags furnished on metal wickets for use by automatic bread packaging machines.

1. SALIENT CHARACTERISTICS:

A) Construction. The bags furnished under this description shall be fabricated from colorless, transparent, plastic film which meets the requirements of the Federal Food, Drug and Cosmetic Act for use in direct contact with food. The plastic film shall have the physical characteristics listed in Table I.

Table I

Characteristic	Requirement	ASTM Test Method
Impact Resistance	Not less than 60 g	D 1709, Method A
Kinetic Coefficient of Friction	Not more than 0.5	D 1894
Water Vapor Transmission Rate	Not more than 25 g/m^2 x day	E 96 or F 1249

DISTRIBUTION STATEMENT A: Approved for public release; distribution is unlimited.

FSC 8105

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.

Bags shall be constructed as shown in Figure 1. Bags shall be furnished on metal wickets. The wickets shall have 2 arms which will fit the 3/8 inch diameter holes in the bag lip. Each wicket shall contain 750 bags.

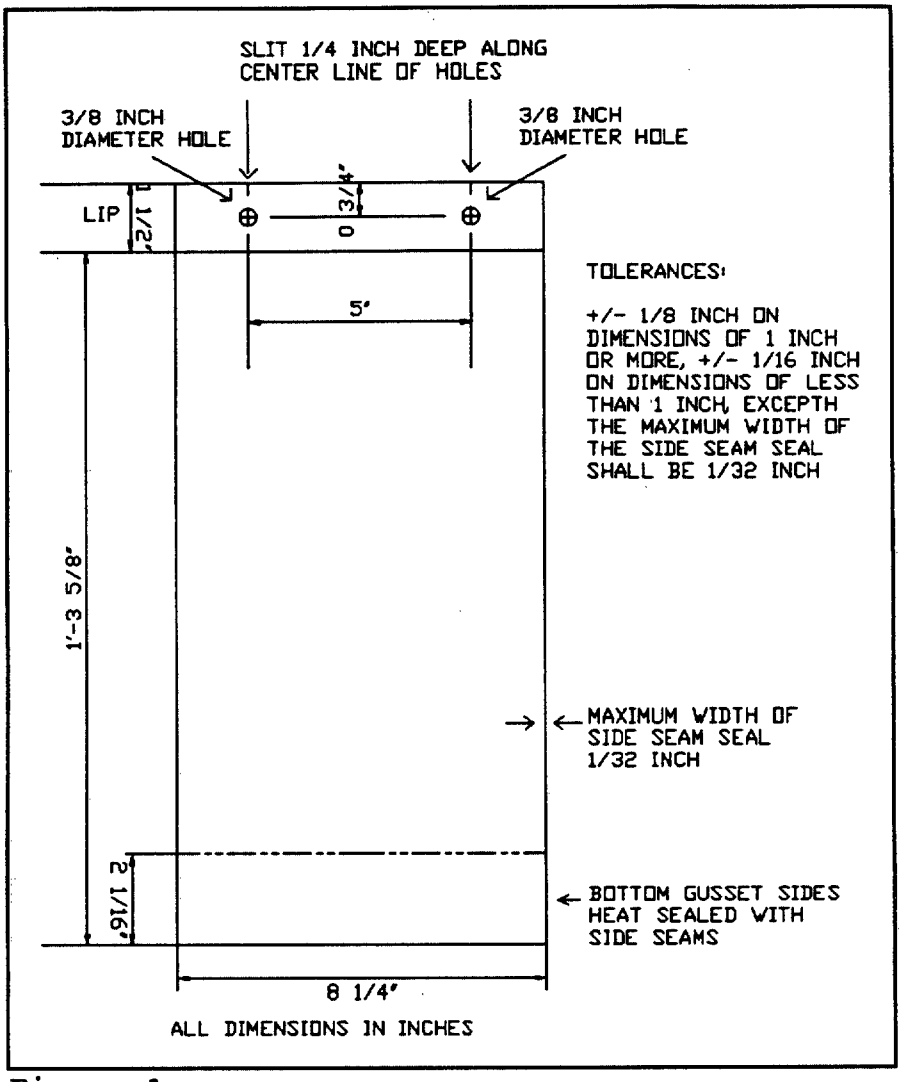


Figure 1

B) Workmanship. The bags shall be uniformly made, free from pinholes, tears, cuts, creases, wrinkles, extraneous matter, or other defects which may impair their serviceability or appearance. The side seams of the bags shall pass the Heat-Sealed Seam Test specified in Section 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.

2. QUALITY ASSURANCE:

A) Responsibility for Inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the Commercial Item Description where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

B) Sampling. Bags, shipping containers, and pallets shall be sampled in accordance with MIL-STD-105. If the bags are made directly from plastic resin in a continuous process, a sample of 10 bags shall be taken to test the physical characteristics specified in Table I.

C) Examination of the end item for construction and workmanship. The lot size shall be expressed in units of bags. The sample unit shall be 1 bag. The Inspection Level shall be S-2, the AQL shall be 2.5 percent defective.

D) Heat-Sealed Seam Test. The sample unit shall be 1 bag. The Inspection Level shall be S-1, the AQL shall be 2.5 percent defective. The test shall be performed as specified by Method 2024 of FED-STD-101. The total weight applied to the specimen shall be 260 $\pm$ 10 grams. One specimen shall be tested from each side seam of each sample unit. No specimens shall be taken within 3 inches of the gusset. Any specimen that shows partial or complete delamination or rupture after hanging for 5 $\pm$ 1 minutes constitutes a defect.

E) Examination of packaging, packing, marking, and palletization. The lot size for packaging, packing, and marking shall be expressed in units of issue of bags; for palletization the lot size shall be expressed in pallets. The sample unit shall be one fully prepared shipping container for packaging, packing, and marking; for palletization the sample unit shall be one fully prepared pallet. For all examinations the Inspection Level shall be S-2 and the AQL shall be 4.0 percent defective.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.

3. REGULATORY REQUIREMENTS:

The offeror/contractor is encouraged to use recovered materials in accordance with Public Law 94-580, as amended, to the maximum extent practicable.

4. PACKAGING, PACKING, AND MARKING:

Packaging, packing, and marking shall be as specified by ASTM D 3951. The unit package quantity shall be specified in the contract or order. Government marking requirements shall apply to unit containers, intermediate containers, and shipping containers.

5. REFERENCED DOCUMENTS:

The issues of the referenced documents in effect on the date of the solicitation for offers or request for proposals shall be used to determine conformance with the requirements of this Commercial Item Description.

A) Public Law

Public Law 94-580 - Resource Conservation and Recovery Act,
(Part of U. S. Code, Title 42)

Available from:

Congressional Sales Office
U. S. Government Printing Office
Washington, DC 20402

B) Federal Standard

FED-STD-101 - Test Procedures for Packaging Materials

[Activities outside the Federal Government may obtain copies of Federal specifications, standards, and Commercial Item Descriptions from the GSA Specifications Unit (3FBP-W),
7th and D Streets, S. W., Washington, DC 20407.]

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.

C) Military Standard

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes

Available from:

Standardization Documents Order Desk
Building 4D
700 Robbins Avenue,
Philadelphia, PA 19111-5094.

D) Other Publications

ASTM D 1709 - Standard Test Methods for Impact Resistance of Polyethylene Film By the Free Falling Dart Method

ASTM D 1894 - Standard Test Method for Static and Kinetic Coefficients of Friction of Plastic Film and Sheeting

ASTM D 3951 - Standard Practice for Commercial Packaging

ASTM E 96 - Standard Test Methods for Water Vapor Transmission of Materials

ASTM F 1249 - Standard Test Method for Water Vapor Transmission Rate Through Plastic Film and Sheeting Using a Modulated Infrared Sensor

Available from:

ASTM
1916 Race Street,
Philadelphia, PA 19103.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.

6. NOTES:

Purchasers shall specify:

A) Number of bags per unit package;

B) Whether bar code marking is required;

C) Whether palletization is required.

MILITARY INTERESTS:

Military Coordinating Activity

Army - GL

PREPARING ACTIVITY:

GSA-FSS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T08:16Z
Check the source to verify that this is the current version before use.