INCH-POUND

MIL-DTL-16878/2C
11 August 2000
SUPERSEDING
MIL-W-16878/2B(NAVY)
11 September 1992

DETAIL SPECIFICATION SHEET

WIRE, ELECTRICAL, POLYVINYL CHLORIDE (PVC) INSULATED, 105 °C, 1000 VOLTS (NOT FOR NAVY SHIPBOARD USE)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-DTL-16878G.

REQUIREMENTS.

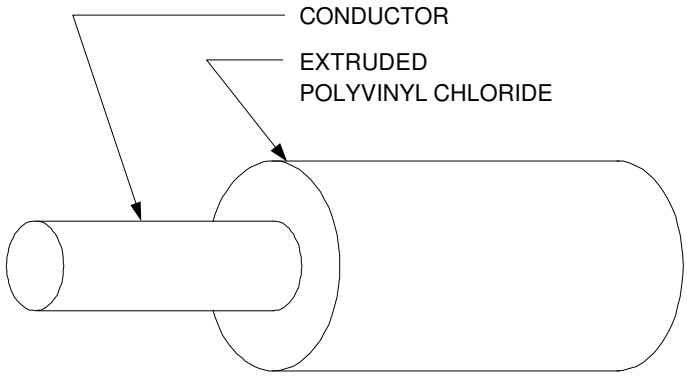

FIGURE 1. Wire configuration.

Note: Not for Navy shipboard use or use in aerospace applications.

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:26Z
Check the source to verify that this is the current version before use.

TABLE I. Wire configuration and dimensions.

PIN [1/]	Wire size	Stranding	Conductor		Conductor diameter (nominal) (inch)	Finished wire diameter (inch)	
			Material [2/, 3/]	Coating		Min	Max
M16878/2BDA*	26	1 X 26	Copper	Tin	.016	.046	.054
M16878/2DDA*	26	1 X 26	H.S.C.A.	Silver	.016	.046	.054
M16878/2CDA*	26	1 X 26	C.C. steel	Tin	.016	.046	.054
M16878/2BDB*	26	7 X 34	Copper	Tin	.019	.049	.057
M16878/2DDB*	26	7 X 34	H.S.C.A.	Silver	.019	.049	.057
M16878/2BDE*	26	19 X 38	Copper	Tin	.021	.049	.057
M16878/2DDE*	26	19 X 38	H.S.C.A.	Silver	.021	.049	.057
M16878/2BEA*	24	1 X 24	Copper	Tin	.020	.050	.058
M16878/2DEA*	24	1 X 24	H.S.C.A.	Silver	.020	.050	.058
M16878/2CEA*	24	1 X 24	C.C. steel	Tin	.020	.050	.058
M16878/2BEB*	24	7 X 32	Copper	Tin	.024	.054	.062
M16878/2DEB*	24	7 X 32	H.S.C.A.	Silver	.024	.054	.062
M16878/2BEE*	24	19 X 36	Copper	Tin	.026	.054	.062
M16878/2DEE*	24	19 X 36	H.S.C.A.	Silver	.026	.054	.062
M16878/2BFA*	22	1 X 22	Copper	Tin	.025	.055	.064
M16878/2DFA*	22	1 X 22	H.S.C.A.	Silver	.025	.055	.064
M16878/2CFA*	22 [4/]	1 X 22	C.C. steel	Tin	.025	.055	.064
M16878/2BFB*	22	7 X 30	Copper	Tin	.030	.060	.068
M16878/2DFB*	22	7 X 30	H.S.C.A.	Silver	.030	.060	.068
M16878/2BFE*	22	19 X 34	Copper	Tin	.033	.060	.068
M16878/2DFE*	22	19 X 34	H.S.C.A.	Silver	.033	.060	.068
M16878/2BGA*	20	1 X 20	Copper	Tin	.032	.062	.070
M16878/2DGA*	20	1 X 20	H.S.C.A.	Silver	.032	.062	.070
M16878/2BGB*	20	7 X 28	Copper	Tin	.038	.068	.076
M16878/2DGB*	20	7 X 28	H.S.C.A.	Silver	.038	.068	.076
M16878/2BGC*	20	10 X 30	Copper	Tin	.038	.068	.076
M16878/2DGC*	20	10 X 30	H.S.C.A.	Silver	.038	.068	.076
M16878/2BGE*	20	19 X 32	Copper	Tin	.041	.068	.076
M16878/2DGE*	20	19 X 32	H.S.C.A.	Silver	.041	.068	.076
M16878/2BHA*	18	1 X 18	Copper	Tin	.040	.070	.079
M16878/2BHB*	18	7 X 26	Copper	Tin	.049	.079	.087
M16878/2BHD*	18	16 X 30	Copper	Tin	.047	.077	.085
M16878/2BHE*	18	19 X 30	Copper	Tin	.051	.079	.087
M16878/2BJA*	16	1 X 16	Copper	Tin	.051	.080	.089
M16878/2BJE*	16	19 X 29	Copper	Tin	.059	.089	.097
M16878/2BJF*	16	26 X 30	Copper	Tin	.062	.092	.100

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:26Z
Check the source to verify that this is the current version before use.

TABLE I. Wire configuration and dimensions - Continued.

PIN [1/]	Wire size	Stranding	Conductor		Conductor diameter (nominal) (inch)	Finished wire diameter (inch)	
			Material [2/, 3/]	Coating		Min	Max
M16878/2BKA*	14	1 X 14	Copper	Tin	.064	.094	.102
M16878/2BKE*	14	19 X 27	Copper	Tin	.072	.102	.110
M16878/2BKH*	14	41 X 30	Copper	Tin	.080	.110	.118
M16878/2BLA*	12 [4/]	1 X 12	Copper	Tin	.081	.110	.119
M16878/2BLE*	12	19 X 25	Copper	Tin	.091	.121	.129
M16878/2BLG*	12	37 X 28	Copper	Tin	.089	.119	.127
M16878/2BLJ*	12	65 X 30	Copper	Tin	.098	.128	.136

Notes:
1/ PIN stands for part or identifying number (see figure 2).
2/ H.S.C.A. stands for high-strength copper alloy.
3/ C.C. stands for copper-clad.
4/ Inactive for new design.

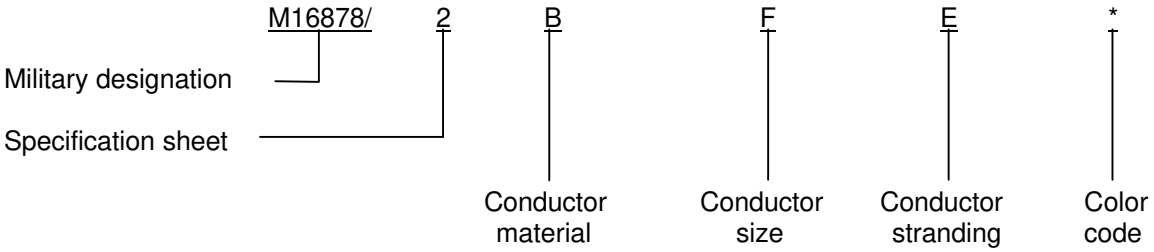

FIGURE 2. Example of PIN (see MIL-DTL-16878G).

Configuration and dimensions:	See figure 1 and table I
Operating voltage:	Up to 1000 volts
Operating temperature:	Up to 105 °C
Insulation:	Extruded polyvinyl chloride
Spark test voltage:	5.0 kV
Impulse dielectric test voltage:	10.0 kV, or 7.1 kV using the 3.0 kHz spark test
Dielectric withstanding voltage:	3.0 kV
Insulation resistance:	IR = K log10 D/d
	Where: IR = Minimum insulation resistance in megohms per 1000 feet at 20 °C
	K = 2,000
	D = Maximum average diameter of finished wire
	d = Conductor diameter
Cold bend:	Condition 4 hours at -54±1 °C (see table II)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:26Z
Check the source to verify that this is the current version before use.

TABLE II. Cold bend mandrel sizes.

Wire size	Cold bend mandrel diameter (inches, maximum)
26 through 16	2
14, 12	3

Surface resistance:	Not required
Heat resistance:	Condition at 150 °C
Heat aging:	25 percent change (maximum) in 96 hours at 135 °C
Insulation tensile strength:	1800 pounds force per square inch (minimum)
Insulation elongation:	100 percent (minimum)

CHANGES FROM PREVIOUS ISSUE. Marginal notations are not used in this revision to identify changes with respect to the previous issues due to the extensiveness of the changes.

CONCLUDING MATERIAL

Custodians:
Navy - SH
Air Force - 11
DLA - CC

Preparing activity:
DLA - CC

(Project 6145-2193-002)

Review activity:
Navy - AS

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:26Z
Check the source to verify that this is the current version before use.