INCH-POUND
MIL-W-16878/11B(NAVY)
11 September 1992
SUPERSEDING
MIL-W-16878/11A(NAVY)
10 August 1981

MILITARY SPECIFICATION SHEET

WIRE, ELECTRICAL, FLUORINATED ETHYLENE PROPYLENE (FEP) INSULATED, 200°C, 600 VOLTS

This specification is approved for use by the Department of the Navy and is available for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation: MIL-W-16878.

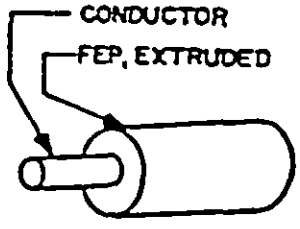


FIGURE 1. Construction.

AMSC N/A FSC 6145
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:28Z
Check the source to verify that this is the current version before use.

TABLE I. Construction details.

PIN 3/	Wire size	Strand-ing	Conductor		Conductor diameter (nominal) (inch)	Finished wire diameter (inch)	
			Material 2/	Coating		Min	Max
M16878/11-BAA*	32	1 X 32	Copper	Silver	0.0080	0.024	0.032
M16878/11-CAA*	32	1 X 32	C.C. steel	Silver	.0080	.024	.032
M16878/11-BAB*	32	7 X 40	Copper	Silver	.010	.026	.034
M16878/11-BBA*	30	1 X 30	Copper	Silver	.0100	.026	.034
M16878/11-CBA*	30	1 X 30	C.C. steel	Silver	.0100	.026	.034
M16878/11-BBB*	30	7 X 38	Copper	Silver	.012	.028	.036
M16878/11-BCD*	28	1 X 28	Copper	Silver	.0126	.029	.037
M16878/11-CCA*	28	1 X 28	C.C. steel	Silver	.0126	.029	.037
M16878/11-BCB*	28	7 X 36	Copper	Silver	.015	.031	.039
M16878/11-BDA*	26	1 X 26	Copper	Silver	.0159	.032	.040
M16878/11-CDA*	26	1 X 26	C.C. steel	Silver	.0159	.032	.040
M16878/11-BDB*	26	7 X 34	Copper	Silver	.019	.035	.043
M16878/11-BDE*	26	19 X 38	Copper	Silver	.020	.035	.043
M16878/11-BEA*	24	1 X 24	Copper	Silver	.0201	.036	.044
M16878/11-CEA*	1/ 24	1 X 24	C.C. steel	Silver	.0201	.036	.044
M16878/11-BEB*	24	7 X 32	Copper	Silver	.024	.040	.048
M16878/11-BEE*	24	19 X 36	Copper	Silver	.025	.040	.048
M16878/11-BFA*	22	1 X 22	Copper	Silver	.0254	.041	.050
M16878/11-CFA*	1/ 22	1 X 22	C.C. steel	Silver	.0254	.041	.050
M16878/11-BFB*	22	7 X 30	Copper	Silver	.030	.046	.054
M16878/11-BFE*	22	19 X 34	Copper	Silver	.032	.046	.054
M16878/11-BGA*	20	1 X 20	Copper	Silver	.0320	.048	.056
M16878/11-BGB*	20	7 X 28	Copper	Silver	.038	.054	.062
M16878/11-BGE*	20	19 X 32	Copper	Silver	.040	.054	.062
M16878/11-BHA*	18	1 X 18	Copper	Silver	.0403	.056	.066
M16878/11-BHB*	18	7 X 26	Copper	Silver	.048	.064	.074
M16878/11-BHE*	18	19 X 30	Copper	Silver	.050	.064	.074
M16878/11-BJA*	16	1 X 16	Copper	Silver	.0508	.067	.081
M16878/11-BJE*	16	19 X 29	Copper	Silver	.057	.073	.087
M16878/11-BKA*	14	1 X 14	Copper	Silver	.0641	.080	.094
M16878/11-BKE*	14	19 X 27	Copper	Silver	.072	.088	.102
M16878/11-BLE*	12	19 X 25	Copper	Silver	.091	.107	.121
M16878/11-BMG*	10	37 X 26	Copper	Silver	.111	.127	.141
M16878/11-BNL*	8	133 X 29	Copper	Silver	.169	.185	.199

1/ Inactive for new design.
2/ C.C. stands for copper-clad.
3/ PIN stands for part or identifying number.

Source: https://assist.dla.mil -- Downloaded: 202610-18T09:28Z
Check the source to verify that this is the current version before use.

ADDITIONAL REQUIREMENTS:

Visual and mechanical examination: Required.
Spark test: 3.4 kV.
Impulse dielectric test: 6.5 kV.
Dielectric withstanding voltage: 2.0 kV.
Insulation resistance: $IR = K \log_{10} D/d$

Where: IR = Minimum insulation resistance in megohms per 1000 feet at 20°C.
K = 50,000.
D = Maximum average diameter of finished wire.
d = Conductor diameter.

Cold bend: Condition 4 hours at minus 65 ± 1°C (see table II).


TABLE II. Cold bend mandrel sizes.

Wire size	Cold bend mandrel (maximum diameter in inches)
32 through 16	1
14 through 10	2
8	3

Concentricity: 70 percent (minimum).
Surface resistance: Not required.
Wrap back: Not required.
Heat resistance: Condition at 230°C.
Flammability: Meets requirements of UL VW1 Flame Test.
Shrinkage: Required.
Toxicity: Meets requirements of concentration levels specified in MIL-E-917.
Heat aging: Not required.
Insulation tensile strength: 2000 pounds force per square inch (minimum).
Insulation elongation: 100 percent (minimum).
Marking and stripe durability: Required.
Fungus resistance: Not required.
Maximum dc resistance of finished wire: See table I of MIL-W-16878.
Identification of product: Required for wire sizes 22 AWG and larger.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:28Z
Check the source to verify that this is the current version before use.

PIN example (see MIL-W-16878):

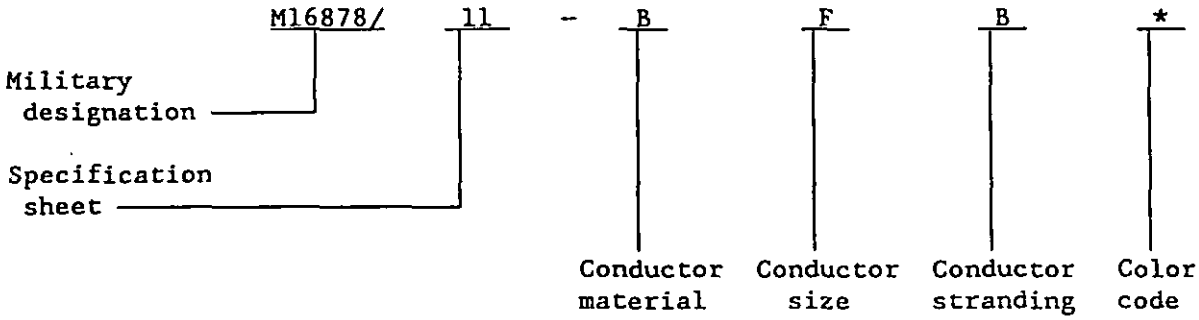

Revision letters are not used to denote changes due to the extensiveness of the changes.

Preparing activity:
Navy - SH
(Project 6145-N330-10)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T09:28Z
Check the source to verify that this is the current version before use.