MIL-D-17951B(SHIPS)
25 October 1961
SUPERSEDING
MIL-D-17951A(SHIPS)
14 April 1959

MILITARY SPECIFICATION

DECK COVERING, LIGHTWEIGHT, NONSLIP, SILICON CARBIDE PARTICLE COATED FABRIC, AND SEALING COMPOUND

1. SCOPE

1.1 This specification covers lightweight, nonslip silicon carbide particle coated fabric deck-covering for decks aboard Naval vessels.

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issue in effect on date of invitation for bids, form a part of this specification to the extent specified herein:

SPECIFICATIONS

MILITARY

MIL-P-116 - Preservation, Methods of.
MIL-L-15016 - Lubricating Oil, General Purpose.

STANDARDS

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of specifications, standards, drawings and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

FSC 7220

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

2.2 Other publications. - The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated the issue in effect on date of invitation for bids shall apply.

OFFICIAL CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules.

(Application for copies should be addressed to the Official Classification Committee, 1 Park Avenue at 33rd Street, New York 16, New York.)

3. REQUIREMENTS

3.1 Material. -

3.1.1 The deck covering shall consist of a fabric backing uniformly coated on one surface with silicon carbide particles, approximately number 60 grit (medium grade flint abrasive designations), bonded to the fabric with a resin or similar material. The back of the fabric shall be coated with a pressure-sensitive type of adhesive, covered with a removable protective liner.

3.1.2 Adhesive and liner. - The adhesive shall be pressure-sensitive, coated to cover the back side of the deck covering, and shall adhere immediately to smooth, clean, dry deck surfaces, without wrinkling, curling, breaking or lifting. A suitable liner shall be used to cover the adhesive film for protection against foreign matter until applied.

3.2 Application. - Deck covering shall maintain a firm adherence to deck surfaces and shall protect metal deck surfaces from corrosion.

3.3 Liner removal. - The average amount of effort required to pull liner away from the adhesive film shall be as shown in table I (see 4.5.2 and 4.5.2.1).

Table I - Removal of liner.

Condition	Maximum effort required to pull liner away from adhesive film
	Ounces
As received	60
After 7 days aging at 150°F. ± 5°F.	60

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

3.3.1 Liner and adhesive transfer. - There shall be no transfer of fragments of liner material to the adhesive surface, or adhesive to liner surface, when the protective liner is stripped away at a rate of 1 foot per second (see 4.5.2.2).

3.4 Adhesion. -

3.4.1 Shear strength. - The deck-covering, when applied to stainless steel plates, shall conform to table II (see 4.5.3.1).

Table II - Shear adhesive strength.

Temperature	Minimum amount of weight in pounds capable of being supported for 1 minute	
	No aging	After 7 days aging
Degrees F.	Pounds	Pounds
80 ± 5	10	10

3.4.2 Strip strength. - The deck-covering, when applied to high tensile steel and galvanized steel plates, shall conform to table III (see 4.5.3.2).

Table III - Strip adhesive strength.

Drying time	Temperature	Adhesive strength (load at separation, pounds) (min.)
48 hours	80° ± 5°F.	0.75

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

3.5 Thickness and weight. - Deck-covering shall be not greater than 0.080 inch thick when applied to the steel decks, and shall weigh not more than 5 ounces per square foot (see 4.5.4).

3.6 Resistance to detergent solution. - Deck-covering shall not soften, stain, streak, nor show any appreciable loss in color when cleaned at regular intervals with detergents (see 4.5.5).

3.7 Nonslip properties. - When tested as specified in 4.5.6, the material shall show factors of friction not less than those shown in table IV.

Table IV - Nonslip properties.

Property	Contacting surface condition		
	Dry	Wet	Oily
Factor of static friction:			
Leather	0.60	0.60	----
Rubber	.60	.60	0.60
Factor of sliding friction:			
Leather	.40	.40	----
Rubber	.50	.60	0.30

3.8 Fire resistance. - The deck-covering, when tested in accordance with 4.5.7, shall exhibit linear damage no greater than 8 inches. The combustion plus ignition time shall not exceed 4 minutes.

3.9 Size. - Deck-covering shall be furnished in treads 6 by 24 inches, 8 by 30 inches, or in rolls 1-1/2, 6, 8, 14 and 24 inches wide and 96 feet long, as specified (see 6.1).

3.10 Color. - When color is required for deck-covering, the cover shall be as specified (see 6.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

3.11 Sealing compound. - The sealing compound shall be of a cold-setting type, ready for use, shall have no deleterious effect on the metal deck surfaces or on the decking material to which applied, and shall be capable of being stored in airtight metal containers for a period of one year without deterioration.

3.11.1 Solids content. - The sealing compound shall have a total solids content of not less than 20 percent (see 4.5.8.1).

3.11.2 Ash content. - The ash content on the solids of the sealing compound shall be not more than 4 percent (see 4.5.8.2).

3.11.3 Viscosity. - The sealing compound shall have a viscosity of not less than 60 nor more than 160 seconds (see 4.5.8.3).

3.11.4 Quantity. - Sealing compound shall be furnished in the quantity as specified (see 6.1).

3.11.5 Labeling. - Each container shall be clearly labeled with directions for application and with the following information:

(a) Brand name.
(b) Preparation of surface, including cleaning agents and primers, if required.
(c) Method of application.
(d) Limit of safe storage.
(e) Safety precautions during application and storage.

3.12 Workmanship. - Workmanship shall be first class in every respect.

4. QUALITY ASSURANCE PROVISIONS

4.1 The supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own or any other inspection facilites and services acceptable to the Government. Inspection records of the examination and tests shall be kept complete and available to the Government as specified in the contract or order. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.2 Lot. -

4.2.1 Deck covering. - A lot shall consist of not more than 10,000 square feet of deck covering offered for delivery at one time.

4.2.2 Sealing compound. - A lot shall consist of sealing compound from one manufacturing batch offered for delivery at one time.

4.3 Sampling. -

4.3.1 Sampling for visual and dimensional examination of treads. - Sample treads shall be selected at random from each lot of deck-covering with lot acceptance based on table V in accordance with Standard MIL-STD-105 (see 4.4.1).

Table V - Sampling for visual and dimensional examination of treads AQL (approx.) = 2.5 percent defective.

Number of deck-covering treads in lot	Number of deck-covering treads in sample	Acceptance number (defectives)	Rejection number (defectives)
110 and under	10	0	1
111 to 300	15	1	2
301 to 500	25	1	2
501 to 1300	35	2	3
1301 to 3200	50	3	4
3201 and over	75	4	5

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.3.2 Sampling for visual and dimensional examination of material in rolls. - From each lot of deck-covering sample rolls shall be selected at random with lot acceptance based on table VI in accordance with Standard MIL-STD-105 (see 4.4.1).

Table VI - Sampling for visual and dimensional examination of rolls AQL (approx.) = 2.5 percent defective.

Number of rolls in lot	Number of rolls in sample	Acceptance number (defectives)	Rejection number (defectives)
15 and under	5	0	1
16 to 40	7	0	1
41 to 65	10	0	1
66 to 110	15	1	2
110 and over	25	1	2

4.3.3 Sampling for examination of sealing compound containers. - From each lot of sealing compound, a random sample of filled containers shall be selected with lot acceptance based on table VII in accordance with Standard MIL-STD-105 (see 4.4.2).

Table VII - Sampling for examination of sealing compound containers.

Number of containers in inspection lot	Number of containers in sample	Acceptance number (defectives)	Rejection number (defectives)
15 and under	5	0	1
16 to 40	7	0	1
41 to 65	10	0	1
66 to 110	15	1	2
Over 110	25	2	3

4.3.4 Sampling for tests of deck-covering. - Four representative 6 by 24 inch samples of deck-covering shall be selected from each lot for tests. The samples selected shall be subjected to the tests specified in 4.5. If any sample fails any test the lot shall be rejected.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.3.5 Sampling for tests of sealing compound. - A representative 1-quart sample of sealing compound from each lot shall be selected for the tests specified in 4.5. If the lot is offered for delivery in containers, the sample shall be taken at random from five containers, unless the lot is contained in fewer than five containers, in which case each container shall be sampled. The sample shall be kept in a tightly closed container to prevent evaporation. If any sample fails any test the lot shall be rejected.

4.4 Examination. -

4.4.1 Visual and dimensional examination of deck-covering. - Each of the sample treads or rolls selected in accordance with 4.3.1 and 4.3.2 shall be visually and dimensionally examined to determine conformance with the requirements of this specification which do not require tests. Any roll or tread in the sample containing one or more visual or dimensional defects shall be rejected, and if the number of defective rolls or treads in any sample exceeds the acceptance number for that sample, the lot represented by the sample shall be rejected.

4.4.2 Examination of sealing compound containers. - Each sample filled container selected in accordance with 4.3.3 shall be examined for defects of the container and the closure, for evidence of leakage, and for unsatisfactory markings. Each sample filler container shall also be weighed to determine the amount of the contents. Any container in the sample having one or more defects or under required fill shall be rejected, and if the number of defective containers in any sample exceeds the acceptance number for that sample, the lot represented by the sample shall be rejected.

4.5 Test procedures. -

4.5.1 The surface of the steel plates to which the deck-covering is attached shall be free from all rust, scale and organic matter. The steel samples with deck-covering applied, including sealer shall be cured for 48 hours at room temperature before conducting tests. Unless otherwise specified in the contract or order, all tests are referred to atmospheric conditions at a temperature of 70° to 75° Fahrenheit (F.) and relative humidity of 65 ± 2 percent.

4.5.2 Liner removal. - Twenty specimens 1 by 7 inches shall be prepared from each lot of deck-covering. Ten specimens shall be tested immediately and ten specimens placed in an oven at 150° ± 5°F. for 7 days, cooled for 2 hours, and then tested in accordance with 4.5.2.1. The amount of effort required to pull liner away from adhesive film shall be determined for each of ten specimens, the results averaged, and the average of the ten results shall not exceed the maximum values specified in table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.5.2.1 Apparatus and procedure. - The apparatus shall be a pendulum type tensile testing machine. The test shall be made with the stressing jaw moving at a speed of 12 inches per minute. The liner of the 1- by 7-inch specimen of deck-covering shall be partially removed from one end sufficiently so that the free liner end may be placed in the stressing jaw and the deck-covering end placed in the fixed jaw. The maximum tension required to remove the remainder of the liner shall be taken as the amount of removal effort required for each specimen. The pawls of the pendulum arm shall be taped back in an open position. The scale shall be graduated to record results in ounces.

4.5.2.2 Liner and adhesive transfer. - The protective liner of a 6- by 24-inch tread shall be pulled away from the deck-covering at a speed of 1 foot per second. The liner and the decking material shall then be examined for signs of transfer of adhesive to the liner surface and for retention of liner fragments by the adhesive surface.

4.5.3 Adhesion. -

4.5.3.1 Shear strength. - Fifteen specimens 1 by 7 inches shall be prepared from each lot of deck-covering. Five specimens shall be tested immediately and ten specimens conditioned in an oven at 150°F ± 5°F. for 7 days, and tested in accordance with 4.5.3.1.1.

4.5.3.1.1 Procedure. - The protective liner shall be stripped back approximately 2 inches from one end of each 1- by 7-inch specimen as it is to be tested, care being taken to avoid any foreign matter coming in contact with the exposed adhesive film. With the use of a template such as shown on figure 1, the exposed end shall be adhered to a polished clean stainless steel plate so that exactly 1 square inch of the specimen has contact. The plate is then inserted in a jig and pressure applied by any suitable hydraulic or mechanical press to provide 65 pounds per square inch of pressure, in mounting test specimens. The specimen shall remain under this pressure for 1 minute. The ten specimens aged in oven at 150°F. ± 5°F. for 7 days, and the five specimens without aging shall be mounted in the above manner, and allowed to set at room temperature for 48 hours after which time five each of aged and unaged specimens shall be tested for adhesion at room temperature (80° ± 5°F.). The tests shall be made by fixing the steel plate in a vertical position leaving 6 inches of the specimen strip below to which a weight can be attached and suspended as shown on figure 2. Weight of the amount specified in table II shall be placed in the weight pan. The deck-covering shall be considered to have passed this test if at least three of each group of five specimens have been capable of supporting the weights specified for a period of 1 minute.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.5.3.2 Strip strength. - Eight samples of high tensile steel plates and 8 samples of galvanized steel plates each 10 by 16 inches by 1/8 inch thick, shall be prepared by buffing the surface on one side with a power driven flexible backed number 24 abrasive disk using such pressure as will just polish the surface of the metal. The buffed plates shall then be cleaned with a solvent. The deck-covering with protective liner removed, shall be applied to the clean steel plates by rolling five times in each direction with a roller traveling at approximately 7-1/2 feet per minute. The roller, as shown on figure 3 and figure 4 is composed of steel disks 7 inches in diameter and approximately 1/4 inch in thickness. The disks have a central hole 2 inches in diameter and are assembled on a 1/2 inch diameter rod, with a disk having a 5/8 inch hole fastened on each end. Accordingly, when the roller is pulled along by the handle the disks are free to aline themselves vertically such that they conform to local irregularities of the specimen surface in 1/4 inch steps. The 7 inch diamter roller results in a loading of 10 pounds per inch of width which approximates 65 pounds per square inch.

4.5.3.2.1 Procedure. -

4.5.3.2.1.1 Adhesion at room temperature (80° ± 5°F.). - Three specimens attached to high tensile steel and three specimens attached to galvanized steel plate prepared as specified in 4.5.3.2 shall be employed. The specimens shall be allowed to dry for a total of 48 hours, and immediately tested. The method of testing strip adhesion to metal shall be as shown on figure 5. Adhesive strength shall be taken as the highest load at which the separation in 1 minute does not exceed 1 inch. The average of the two highest values obtained on the three strips shall then be considered as the adhesive strength between the deck-covering and the metal.

4.5.4 Thickness and weight. - The deck-covering shall be applied to three 6 inch square, 0.025 inch (25 mils) thick steel plates which have been previously measured and weighed. When the material has set for 48 hours, the three test specimens including the steel plates, shall each be weighed to the nearest 0.1 ounce. The length and width shall be measured to the nearest 0.01 inch and the thickness to the nearest 0.001 inch. From the difference between the weight of the coated steel plate and the uncoated steel plate, the weight of the material shall be computed in ounces per square foot per thickness as applied. The thickness shall be determined by measuring the steel plates, with and without the coating, at 16 equally distributed points on the specimen, by means of a dial thickness gage and a template. The difference in thickness of the mounted steel plate and the coated steel plate shall be averaged to determine the thickness of the material. The final weight shall be the average of the three specimens.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.5.5 Resistance to detergent solution. - Specimens of deck-covering 6 by 2 inches shall be immersed for 1 hour in the solution specified herein so that a 3 inch section of the specimen is immersed in the solution and the upper half remains unexposed for purposes of comparison. The liquid solution shall be made by dissolving a detergent in tepid water to form a 1/2 of 1 percent solution, then adding lamp-black until the solution is dark gray. After immersion, the specimen shall be rinsed for 1 minute with tap water at 140°F. and dried with an air jet. The specimen shall then be examined for softening, stains, streaking or loss of color.

4.5.6 Nonslip properties. - The factors of friction of the deck-covering against leather and rubber shall be determined, respectively. The leather shall be oak-tanned sole leather which has been sanded smooth with grade 0 garnet paper. The rubber shall be a vulcanized compound with a hardness range of 60 to 80 Durometer "A". Tests shall be made with the contact surfaces dry; wet with a solution of 4 percent sodium chloride in water; and oiled, using oil conforming to symbol 3042 of Specification MIL-L-15016. The leather and rubber shall be cut to a size 2 by 4 inches and mounted on a block of the same size. A load of 33 pounds shall be applied uniformly over the 2- by 4-inch block during the test. A pendulum-type tensile testing machine shall be used to measure the force required to move the weight block on the deck-covered surface. The moving jaw of the tensile testing machine shall be set to move at the rate of 7-1/2 feet per minute. Approximately one cup of the salt water solution shall be poured over the deck-covering surface in making the wet test. For the oil test the oil shall be applied to the center of the leather or rubber sample and on the deck-covering surface sufficient to spread evenly over the entire surface.

4.5.7 Fire-resistance test. -

4.5.7.1 Apparatus. - The fire-resistance of the deck-covering shall be determined by an apparatus as shown on figure 6, which consists of communicating horizontal and vertical flues constructed of asbestos board sheets supported on an angle-iron frame, with the exception of the horizontal bottom plate, which is steel. The enclosure shall be 36 inches long overall; the flue shall be 8 inches wide by 6 inches high. The bottom plate shall be cut away 3 inches from the firing end to provide clearance for the flames of four open blast gas burners. Details of the fire-resistance apparatus are shown on figures 7 and 8.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.5.7.2 Procedure. - The deck-covering shall be prepared in the usual manner on a 1/8 inch mild steel plate 31-1/2 inches long by 7 inches wide, with longitudinal flanges for mounting in the horizontal flue. The plate shall be secured in the flue, 2 inches above the bottom plate and with the inner end spaced 3 inches from the flue end, to permit hot gases passing beneath the test plate to be vented through the vertical flue. The four open blast burners shall be located side by side and parallel to the front end of the test plate, on 1-3/4 inch centers, equidistant from each side of the flue. The center of the burners shall be located 4 inches below the bottom surface of the test plate, and shall be 1/2 inch in front of the firing end of the test plate. The gas used shall be commercial propane having a heating vlue of 2550 British thermal unit (B.t.u.) per cubic feet at a temperature of 60°F. and atomspheric pressure of 30 inches of mercury. The gas and air shall be supplied to a common manifold at a rate of 9.6 and 150 cubic feet per hour respectively, when referred to standard conditions of 60°F. and 30 inches of mercury. The burner flames shall be applied to the test plate for four minutes and then immediately removed. A draft of 0.06 (+0.01 -0.00) inch of water shall be maintained in the flue of the apparatus for the duration of the test.

4.5.7.2.1 Combustion plus ignition time, and linear damage shall be noted. These quantities are defined as follows:

(a) Combustion plus ignition time. - The time taken from the initial application of burner flames until all flaming of the specimen ceases.
(b) Linear damage. - The length of specimen permanently damaged by burning, charring, blistering or embrittlement. This measurement shall be taken after all flaming ceases.

4.5.8 Sealing compound tests. -

4.5.8.1 Determination of solids content. - The total solids content shall be determined as follows:

Approximately 10 grams (gm) of the compound shall be placed in a low-form weighing bottle, 60 millimeters (mm) wide by 30 mm high. The bottle shall be covered and weighed. The cover shall be removed and all solvent evaporated at 70°C. (approximately 4 hours required). The bottle shall then be placed in a desiccator to cool, and to be weighed.

$$\text{Percentage of total solids} = \frac{\text{weight of residue}}{\text{weight of sample}} \times 100$$

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

4.5.8.2 Determination of ash content. - Take a porcelain crucible or dish. Add 10 to 25 milliliters (mℓ) of compound, carefully weighing the amount added. Place on a stone slab on the floor of a hood. Ignite by playing the flame of a burner on the surface of the sealer and allow to burn quietly until most of the compound is burned off; then transfer to a muffle or over a flame and continue heating at a low temperature (not over a dull red) until all carbonaceous matter is consumed. Cool, weigh and compute in percentage of ash.

4.5.8.3 Viscosity. -

4.5.8.3.1 Apparatus. - The apparatus shall be a Ford cup type viscosimeter and shall consist of a heavy polished metal cup with a conical bottom fitted with a standard 1/4 inch diameter orifice. The cup shall be provided with an overflow well at the top and the tip shall be protected by a cylindrical jacket extending 1/4 inch below the orifice. The cup shall be held in a ring support during the test.

4.5.8.3.2 Method of test. - The cup shall be filled by holding the index finger over the orifice until the cement just overflows. The finger shall then be released, and the time noted at the first evidence of a break in flow of the cement through the orifice. The test shall be conducted at a temperature of 80° ± 5°F. The viscosity shall be taken as the average of three tests.

4.6 Inspection of preparation for delivery. - Sample packs shall be selected and inspected in accordance with Specification MIL-P-116 to verify conformance to the requirements of section 5 herein.

5. PREPARATION FOR DELIVERY

5.1 Domestic shipment and early material use. -

5.1.1 Packing. - Packing shall be accomplished in a manner which will insure acceptance by common carrier and will afford protection against physical damage during direct shipment from the supply source to the using acticity for early use. The shipping containers or method of packing shall confrom to the Unifrom Freight Classification Rules and Regulations or other carrier regulations as applicable to the mode of transportation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

5.1.2 Marking. - Shipment marking information shall be provided on interior packaged and exterior shipping containers in accordance with the contractor's commercial practice. The information shall include nomenclature, Federal stock number or manufacturer's part number, contract or order number, contractor's name and destination.

5.2 Domestic shipment and storage or overseas shipment requirements. - The requirements and levels of packaging, packing and marking for shipment shall be specified by the procuring acticity (see 6.1).

(5.2.1 The following provides various levels of protection during domestic shipment and storage or overseas shipment, which may be required when procurement is made.

5.2.1.1 Packaging. -

5.2.1.1.1 Level A. - Deck-covering and sealer shall be packaged as follows:

5.2.1.1.1.1 Deck-covering. - Deck-covering of like kind and size and in quantities specified shall be packaged in fiberboard boxes conforming to Specification PPP-B-636 (class 2). Box closure shall be as specified in the appendix to the box specification. All corner and edge seams and manufacturer's joints shall be sealed with a minimum 1-1/2 inch wide tape conforming to Specification PPP-T-76.

5.2.1.1.1.2 Sealer. - Sealer shall be furnished in 5-ounce metal collapsible tubes, 1 gallon cans or in 5 gallon pails as specified.

5.2.1.1.1.2.1 Collapsible tubes. - Five-ounce collapsible tubes shall conform to type II, class B of Specification U-M-186. Each tube shall be placed in folding or set-up paperboard box conforming to Specification PPP-B-566 or PPP-B-676 at the option of the contractor. Box closure shall be as specified in the appendix to the applicable box specification.

5.2.1.1.1.2.2 One-gallon cans. - One-gallon cans shall conform to type V, class 2 of Specification PPP-C-96. Exterior plan B coating and side seam striping shall be required. Cans shall be provided with wire handles which shall be galvanized or protectively coated to resist corrosion. After filling, the plugs shall be spot soldered to the friction ring at three points, spaced equidistant from each other around the periphery of the plug.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

5.2.1.1.1.2.3 Five-gallon pails. - Five-gallon pails shall conform to type II of Specification PPP-P-704.

5.2.1.1.2 Level C. - Deck-covering and sealer shall be packaged in such a manner than will afford adequate protection against physical damage during shipment from supply source to the first receiving activity for immediate use. This may conform to the supplier's commercial practice, when such meets the requirements of this level.

5.2.1.2 Packing. -

5.2.1.2.1 Level A. - Deck-covering shall be packed in containers conforming to any one of the following specifications at the option of the supplier:

Specification	Type or class
PPP-B-576	Class 2
PPP-B-585	Class 3 use
PPP-B-591	Overseas type
PPP-B-601	Overseas type
PPP-B-621	Class 2
PPP-B-636	Class 2, grade 3
PPP-B-640	Class 2

Shipping containers shall have caseliners conforming to Specification MIL-L-10547. Caseliners shall be closed and sealed in accordance with the appendix to Specification MIL-L-10547. Caseliners for class 2 fiberboard boxes conforming to Specification PPP-B-636 may be omitted provided all corners and edge seams and manufacturer's joints are sealed with a minimum 2 inch wide tape conforming to Specification PPP-T-76. Boxes shall be closed, strapped or banded in accordance with the applicable box specification or appendix thereto. The gross weight of wood or wood-cleated boxes shall not exceed 200 pounds.

5.2.1.2.1.1 Sealer. -

5.2.1.2.1.1.1. Collapsible tubes. - Collapsible tubes shall be packed for export shipment in accordance with the requirements of Specification U-M-186.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

5.2.1.2.1.1.2 One- and 5-gallon containers. - One-gallon cans shall be arranged and packed for overseas shipment in accordance with the appendix to Specification PPP-C-96. Five-gallon pails shall require no additional packing. Five-gallon pails may be palletized if specified.

5.2.1.2.2 Level B. - Deck-covering shall be packed in boxes conforming to any one of the following specifications at the option of the supplier.

Specification	Type or class
PPP-B-576	Class 1
PPP-B-585	Domestic type
PPP-B-591	Domestic type
PPP-B-601	Domestic type
PPP-B-621	Class 1
PPP-B-636	Class 2
PPP-B-640	Class 1

Box closures shall be as specified in the applicable box specification or appendix thereto. The gross weight of wood or wood-cleated boxes shall not exceed 200 pounds.

5.2.1.2.2.1 Sealer. -

5.2.1.2.2.1.1 Collapsible tubes. - Collapsible tubes shall be packed for domestic shipment in accordance with Specification U-M-186.

5.2.1.2.2.1.2 One- and 5-gallon containers. - One-gallon cans shall be arranged and packed for domestic shipment in accordance with the appendix to Specification PPP-C-96. Five-gallon pails shall require no additional packing. Five-gallon pails may be palletized when specified.

5.2.1.2.3 Pallets. - Five-gallon pails shall be palletized in accordance wtih Standard MIL-STD-147 when specified.

5.2.1.3 Marking. - In addition to the labeling specified in 3.11.5 and any special marking required by the contract or order, unit and interior packages, shipping containers and palletized unit loads shall be marked in accordance with Standard MIL-STD-129.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

6. NOTES


6.1 Ordering data. - Procurement documents should specify the following:

(a) Title, number and date of this specification.
(b) Size of treads or width of rolls required (see 3.9).
(c) Color of deck-covering, when required (see 3.10).
(d) Quantity of sealing compound required (see 3.11.4).
(e) Packaging, packing or marking requirements other than those required by 5.1 (see 5.2).

Notice. - When Government drawings, specifications or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished or in any way supplied the said drawings, specifications or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

Preparing activity:
Navy - Ships
(Project 7220-N009Sh)

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

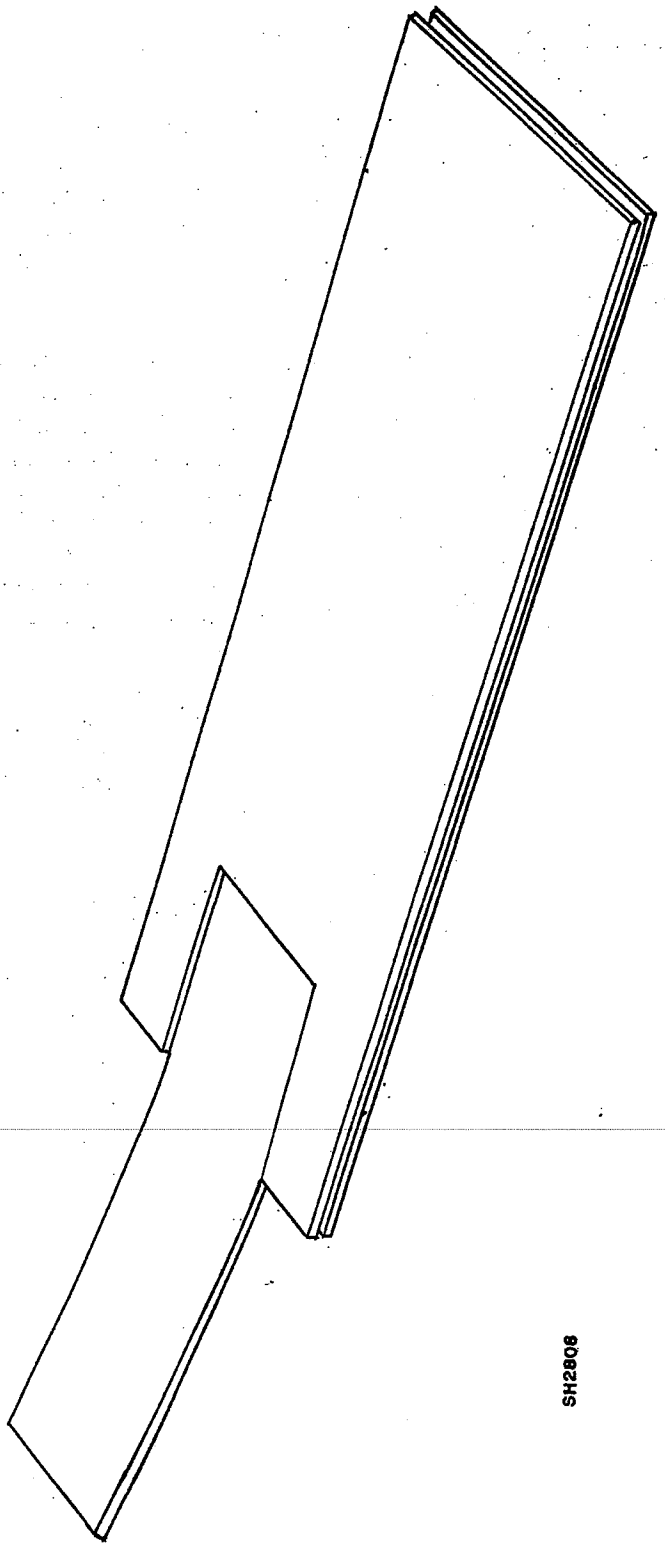

SH2808

Figure 1 - Template.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.


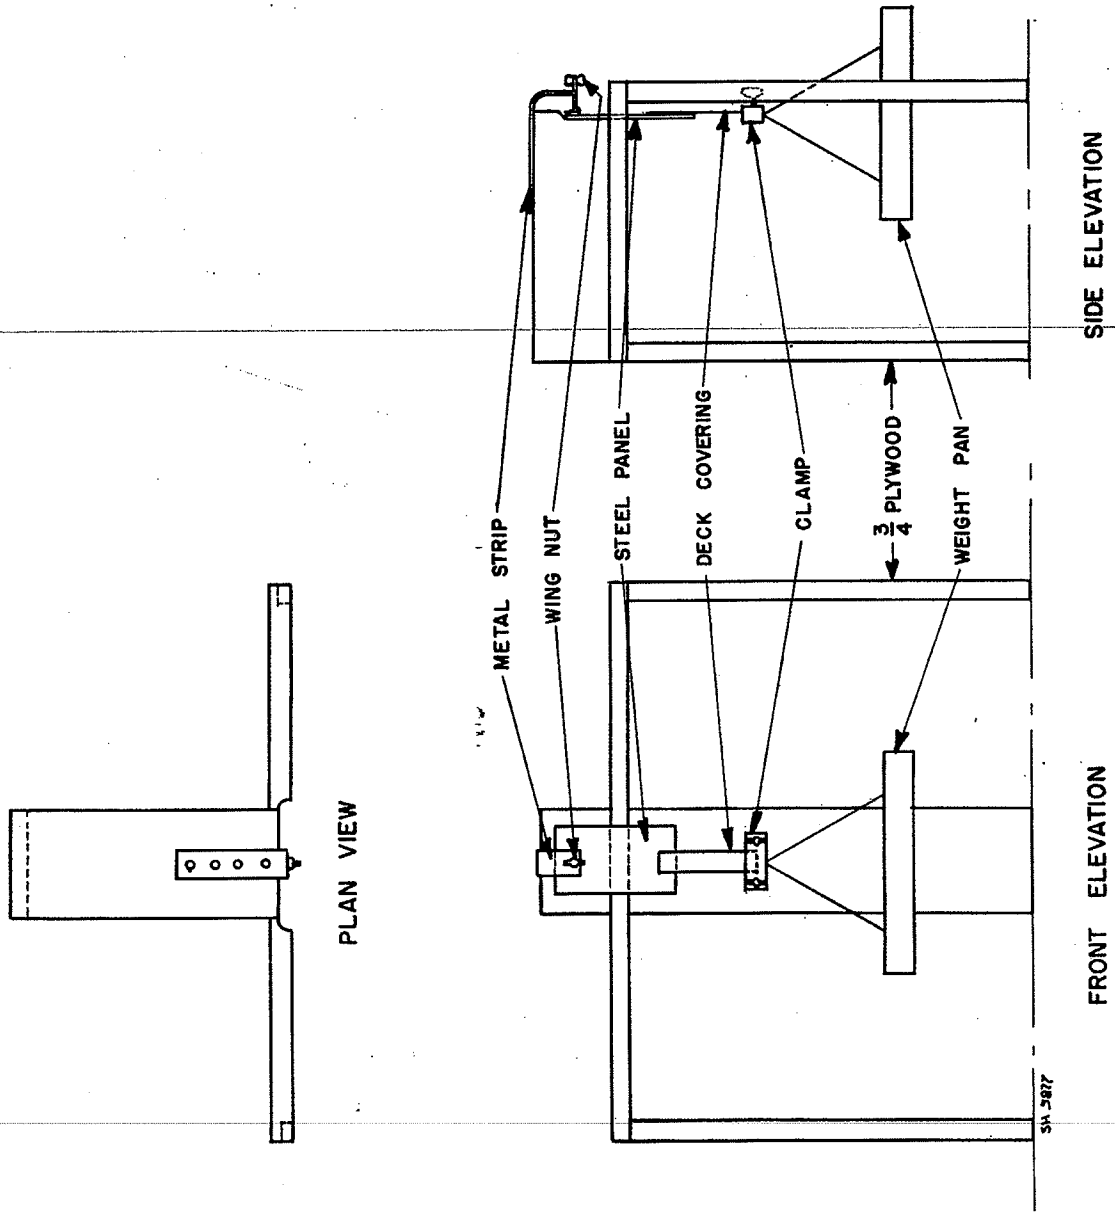


Figure 2 - Adhesion testing machine.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

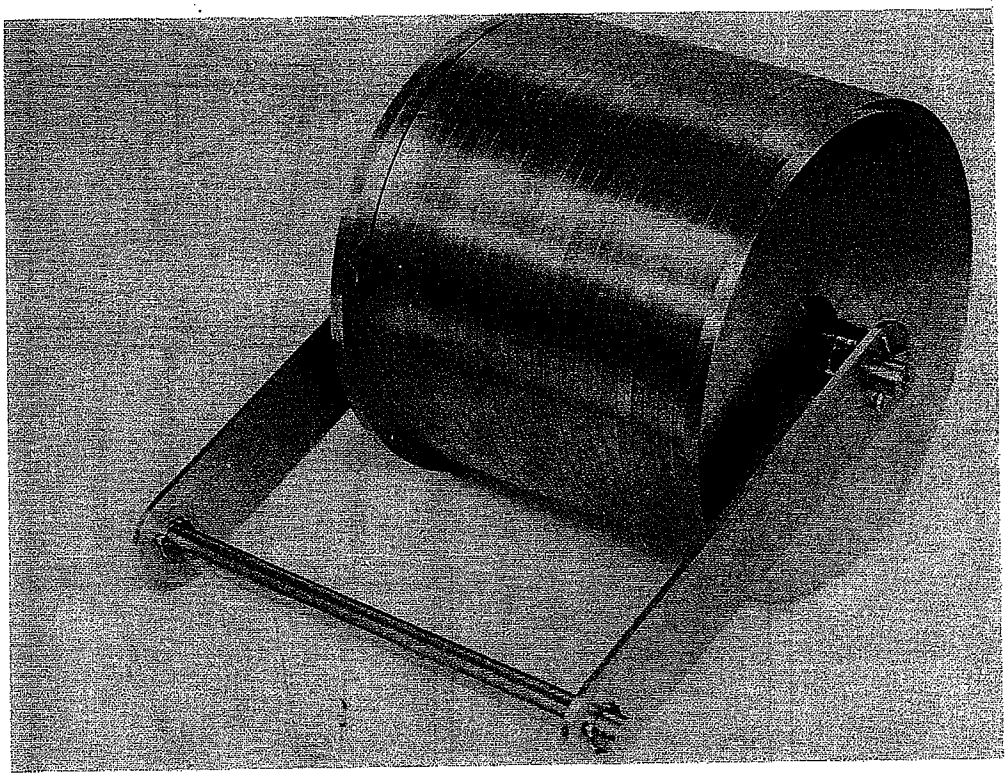

SH2809

Figure 3 - Multidisk roller for preparation of strip adhesion strength specimens assembled view.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

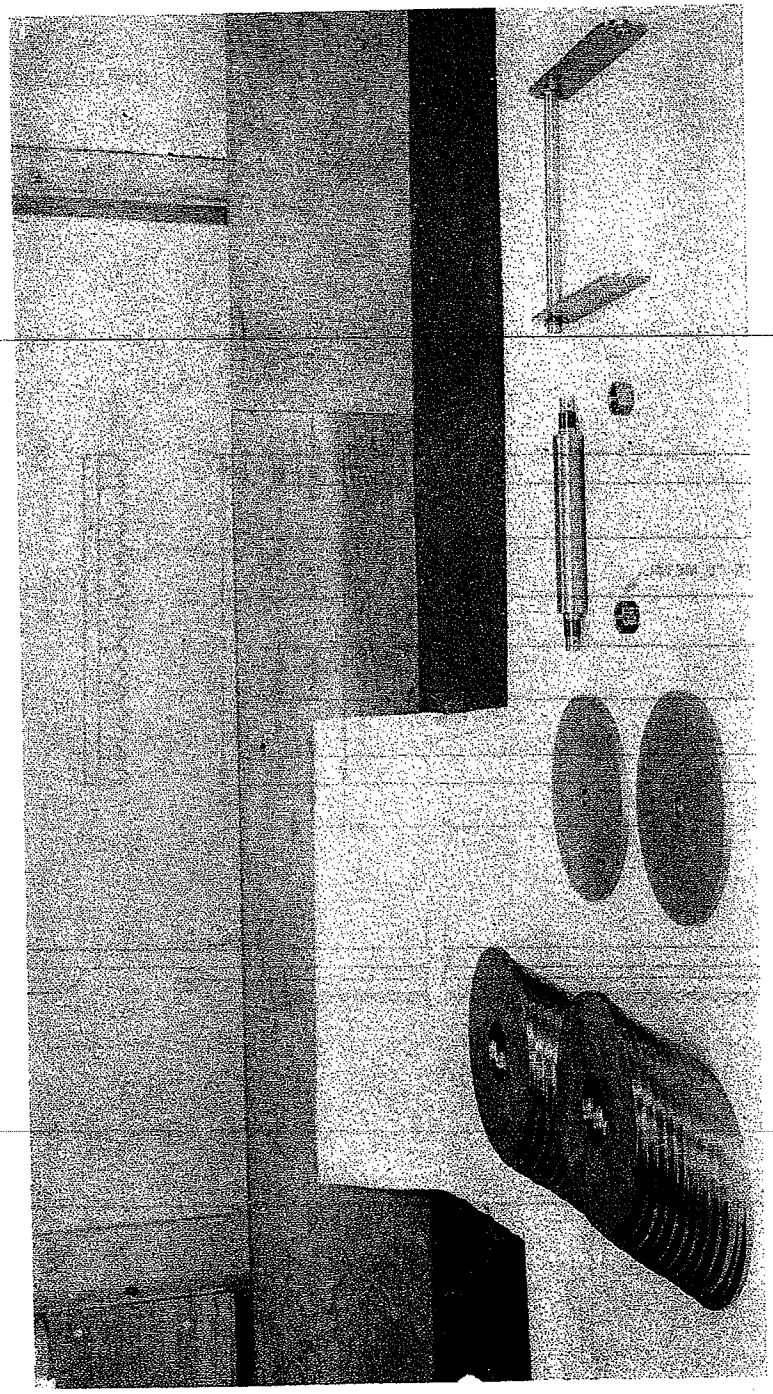

SH2810

Figure 4 - Multidisk roller for preparation of strip ashesion strength specimens disassembled view.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.


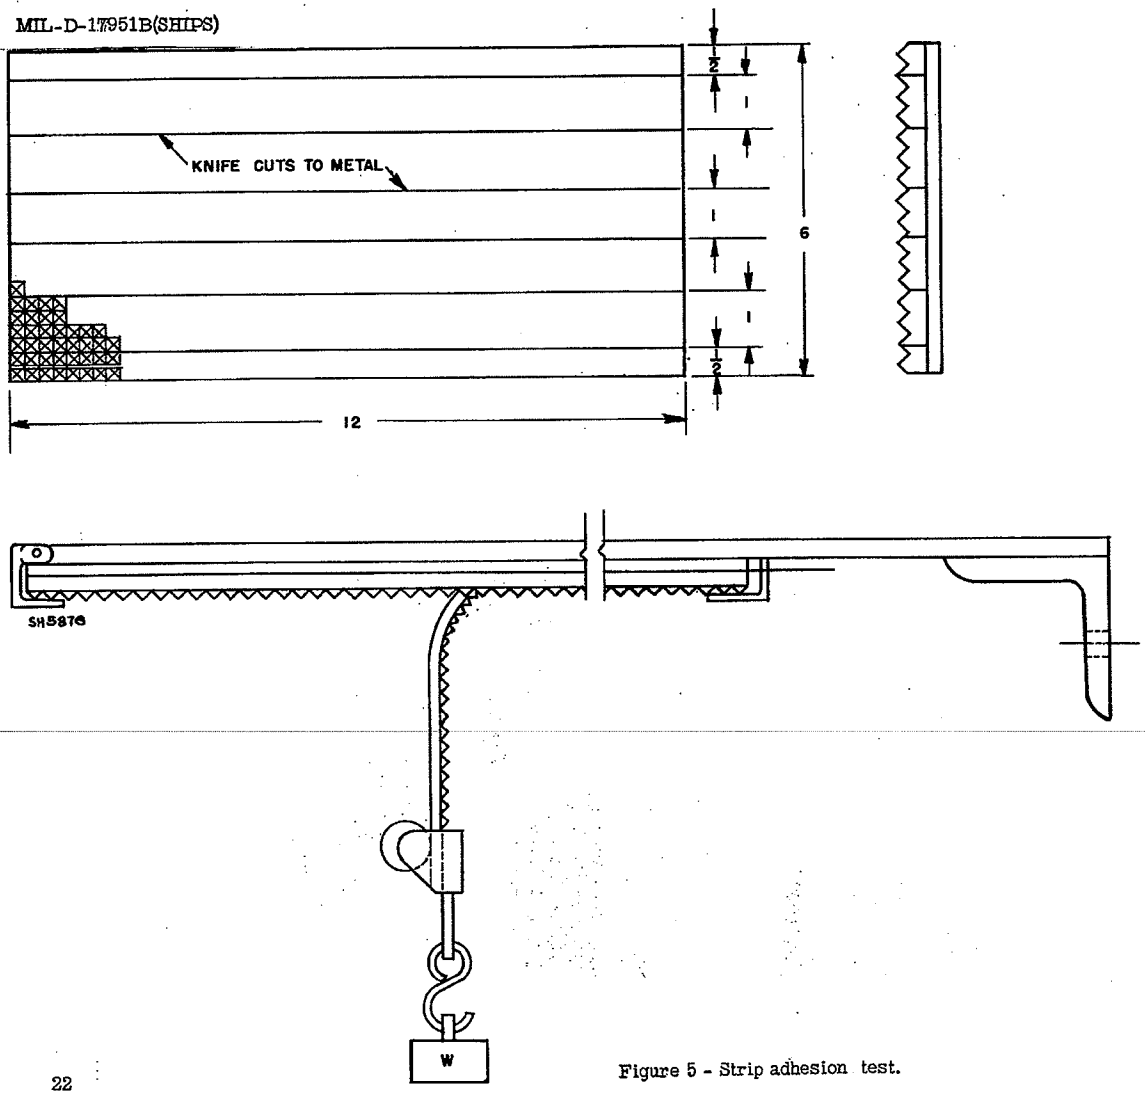


Figure 5 - Strip adhesion test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

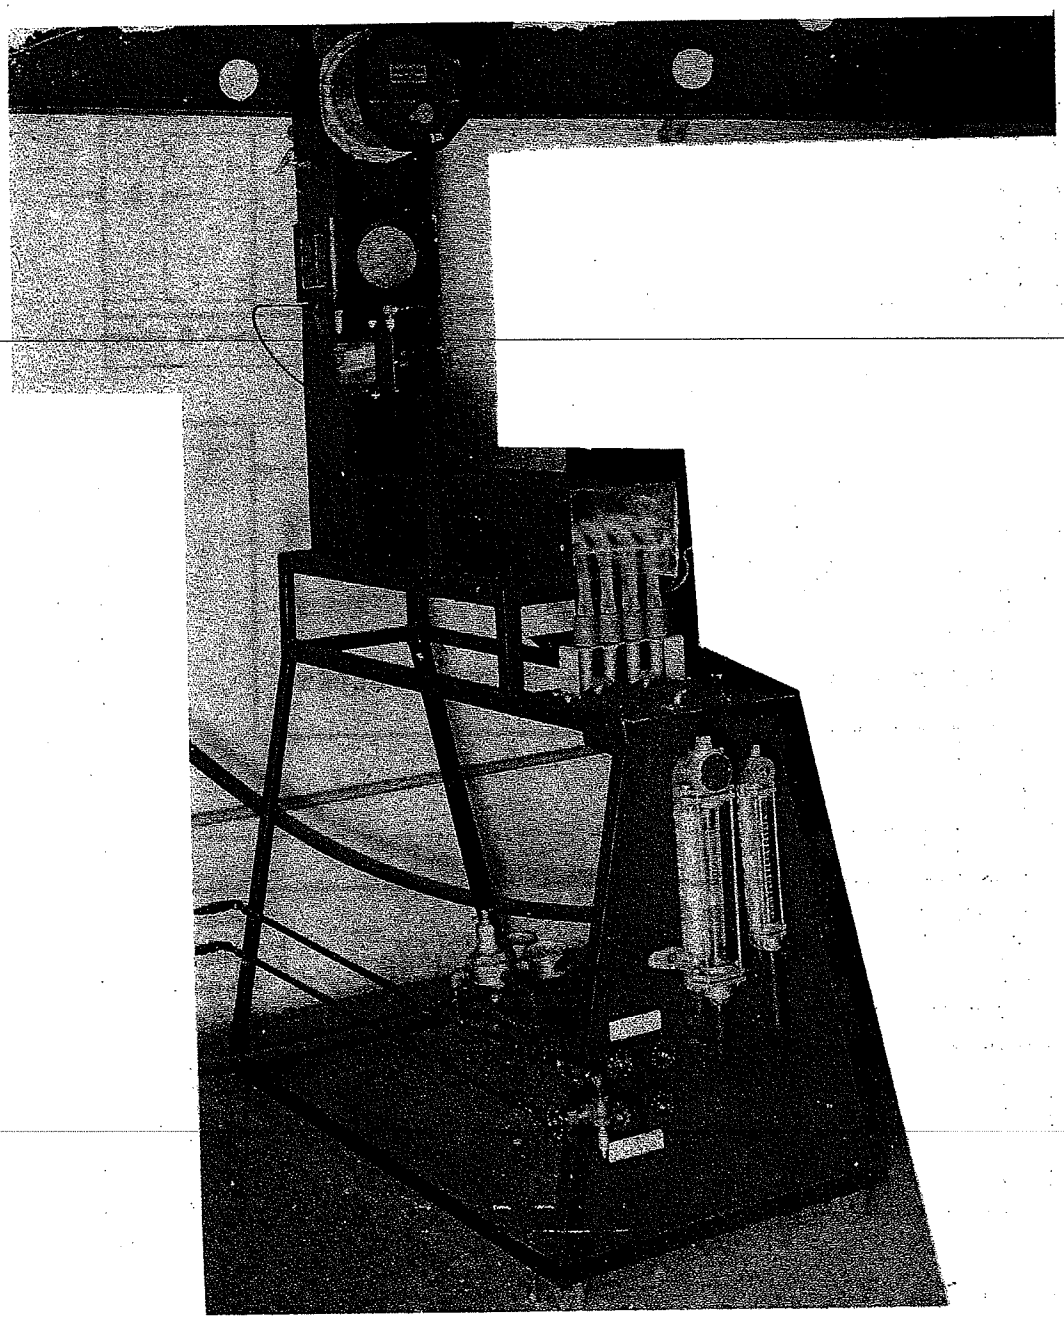

SH2811

Figure 6 - Fire-resistance test apparatus.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

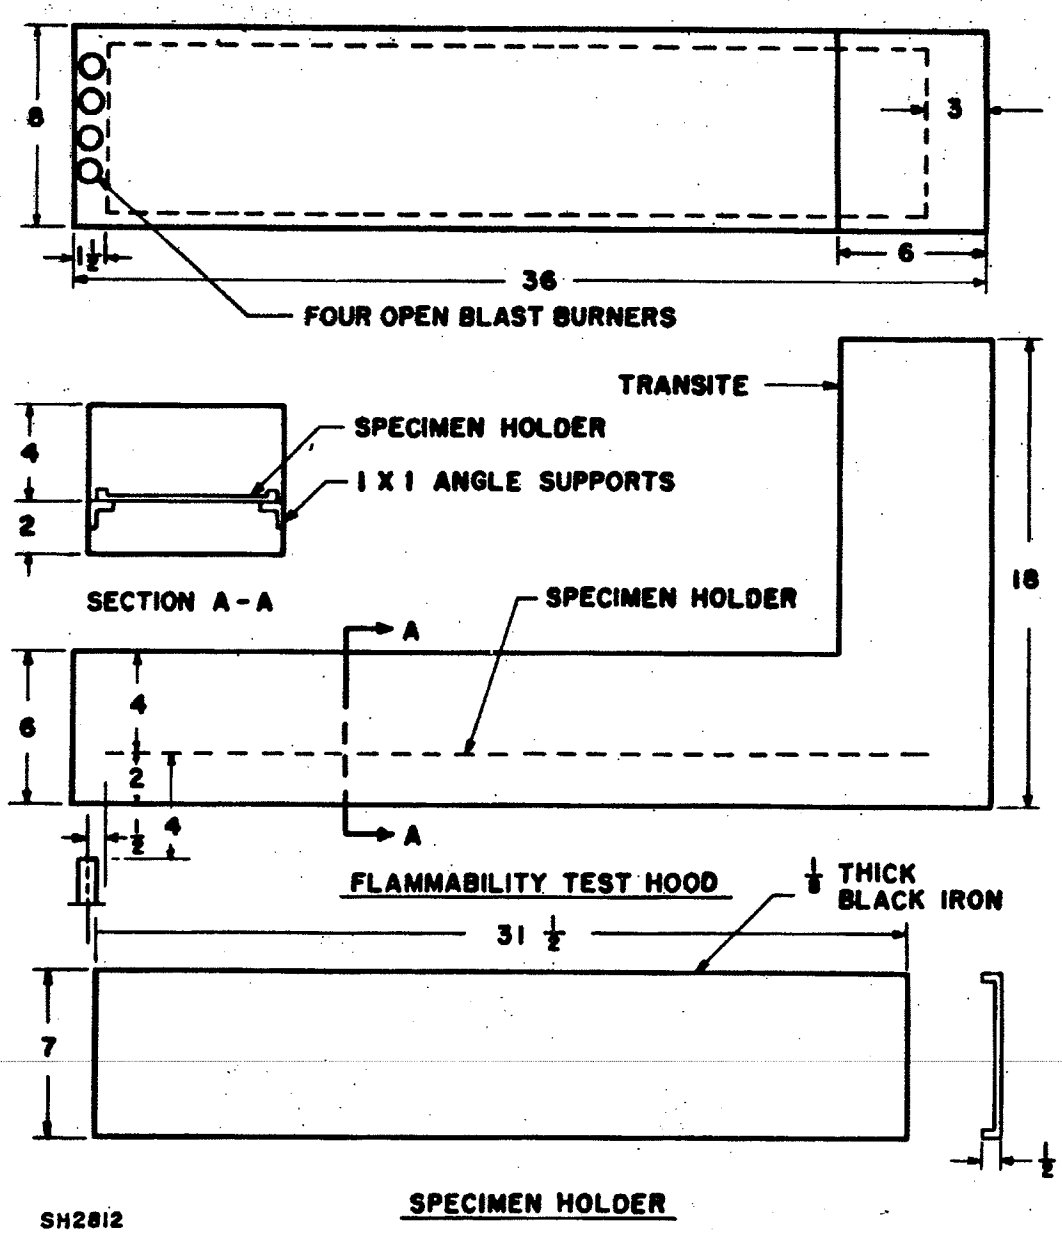


Figure 7 - Detail of fire-resistance test apparatus.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

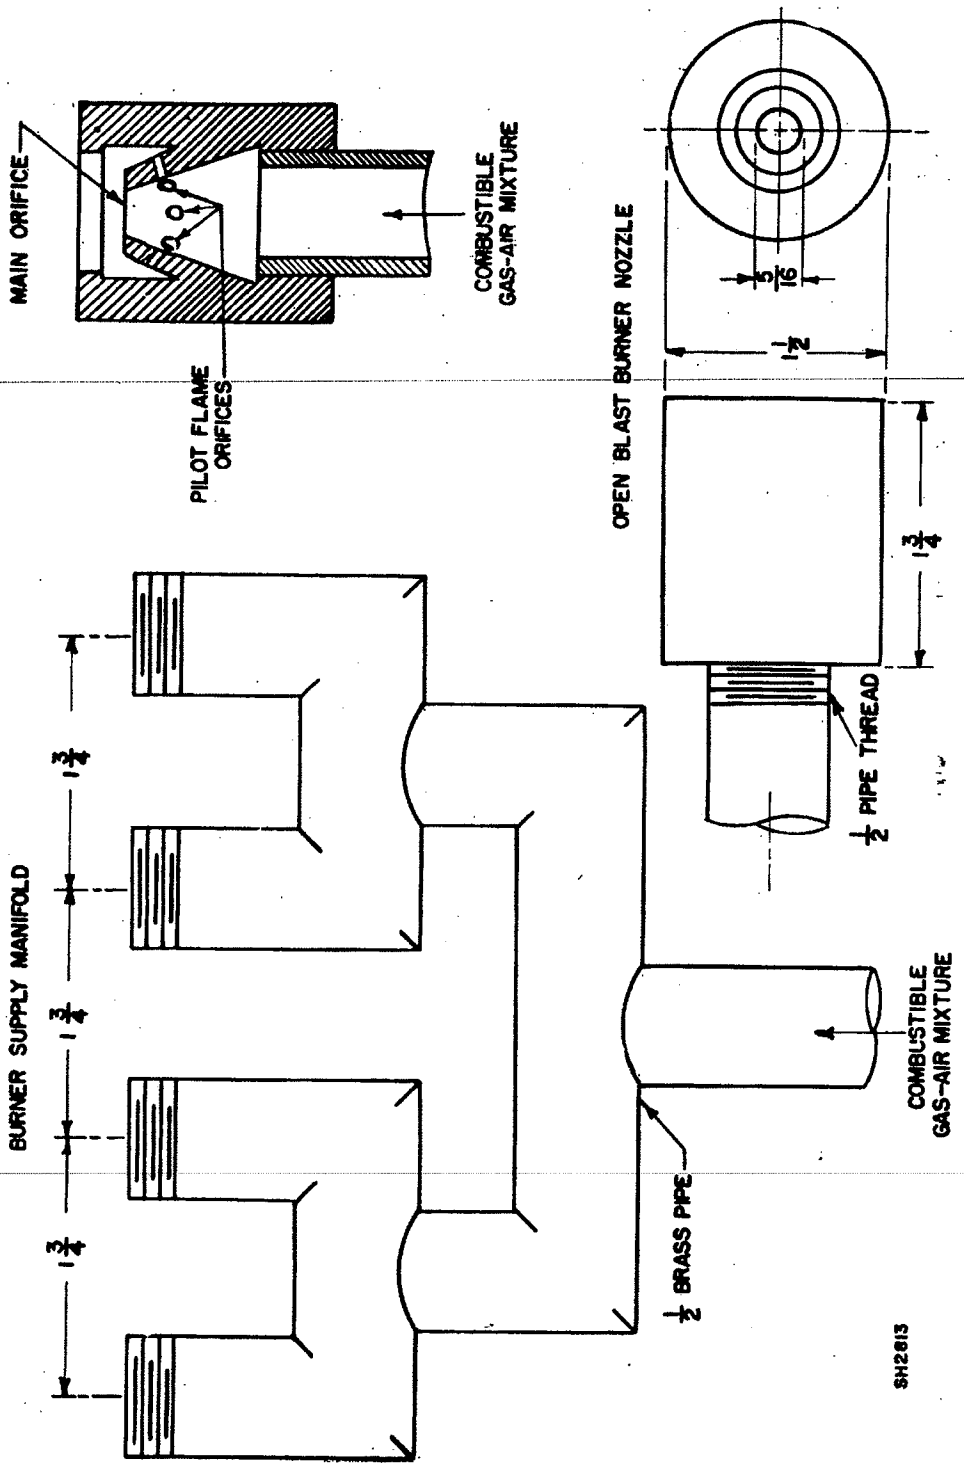


Figure 8 - Burner supply manifold and open blast burner nozzle.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Instructions

This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost.

Comments and the return of this form will be appreciated.

Fold on dotted lines on reverse side, staple in corner, and send to Bureau of Ships, Specifications and Standardization Branch, Washington 25, D. C.

Specification

Organization	City	State

Contract No.

Quantity of Items Procured	Dollar Amount $

Material procured under a direct Government contract ☐ or a subcontract ☐

1. Has any part of the specification created problems or required interpretation in procurement?
   a. Give paragraph number and wording.

   b. Recommendations for correcting the deficiencies.

2. Comment on any specification requirement considered too rigid.

3. Is the specification restrictive? ☐ Yes ☐ No If the answer is "Yes", in what way?

4. Remarks (Attach any pertinent data which may be of use in improving this specification.)

Place this form and papers in an envelope and send to the Bureau.

Submitted by (Print name and activity)	Date

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.

Fold

DEPARTMENT OF THE NAVY
BUREAU OF SHIPS
WASHINGTON 25, D. C.

OFFICIAL BUSINESS

POSTAGE AND FEES PAID
NAVY DEPARTMENT

CHIEF, BUREAU OF SHIPS
SPECIFICATIONS AND STANDARDIZATION BRANCH
DEPARTMENT OF THE NAVY
WASHINGTON 25, D. C.

Fold

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T10:48Z
Check the source to verify that this is the current version before use.