MILITARY SPECIFICATION
SEMICONDUCTOR DEVICE, DIODE, SILICON
JAN1N5624 THROUGH JAN1N5627
AND JANTX1N5624 THROUGH JANTX1N5627

1. SCOPE

1.1 Scope - This specification covers the detail requirements for silicon, general purpose semiconductor diodes for use as power rectifiers in equipment circuits (see 6.2). The prefix "TX" identifies devices meeting the special process-conditioning, testing, and screening requirements in 4.5 herein.

1.2 Physical dimensions - See Figure 1.

1.3 Characteristics and ratings -

TYPE	V_R	V_{RM} (wkg)	I_O @ T_A= -65°C to +55°C 1/3/	I_O @ T_A =100°C 2/3/	if (surge) @ I_o=2.5A T_A=+100°C tp=8.3msec	θj-L (.375 from body) (Max)	t_{rr}
	Vdc	V	Adc	Adc	adc	°C/Watt	μsec
1N5624	200	200	3.5	2.5	125	18	5
1N5625	400	400	3.5	2.5	125	18	5
1N5626	600	600	3.5	2.5	125	18	5
1N5627	800	800	3.5	2.5	125	18	5

OPERATING TEMPERATURE: T_A=65°C to +200°C

STORAGE TEMPERATURE: T_A=-65°C to +200°C

BAROMETRIC PRESSURE, REDUCED (high altitude operation):

1N5624, 1N5625, 1N5626 = 8mm Hg (100,000 ft.)
1N5627 = 33mm Hg (70,000 ft.)


1/ From 3.5A at T_A=+55°C to 2.5A at T_A=+100°C, derate linearly at 0.022A/°C.

2/ From 2.5A at T_A=+100°C, to 0A at T_A=+200°C, derate linearly at 0.025/°C.

3/ No heat sinking or forced air shall be allowed across the body for the I_O ratings.

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

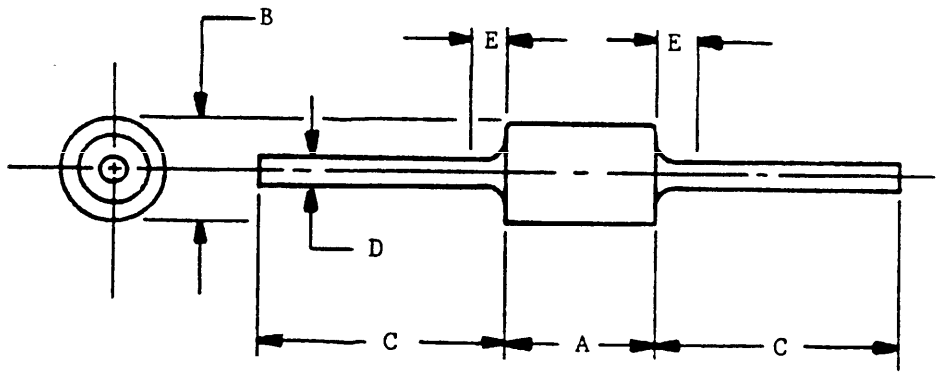

DIMENSIONS					NOTES
LTR	INCHES		MILLIMETERS		
	MIN.	MAX.	MIN.	MAX.	
A	.200	.260	5.080	6.600	1, 3
B	.160	.230	4.064	5.840	1
C	.90	1.25	22.86	31.75	1, 2
D	.049	.053	1.24	1.35	1, 2
E	-0-	.030	-0-	.762	1, 4

NOTES:

1. Metric equivalents (to the nearest .01mm) are given for general information only and are based upon 1 inch = 25.4 mm.
2. Both leads shall be within the specified limits.
3. See paragraph 3.5 for marking requirements.
4. The lead diameter is uncontrolled in this area.

FIGURE 1. Outline and Dimensions

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATION

MILITARY

MIL-S-19500 - Semidonductor Devices, General Specification For.

STANDARD

MILITARY

MIL-STD-750 - Test methods for semiconductor devices.
MIL-STD-202 - Test methods for electric and electrical component parts.

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring agency or as directed by the contracting officer. Both the title and number or symbol should be stipulated when requesting copies.)

3. REQUIREMENTS

3.1 General - Requirements for diodes shall be in accordance with Specification MIL-S-19500 and as otherwise specified herein.

3.2 Abbreviations, symbols, and definitions - The abbreviations, symbols, and definitions used herein are defined in MIL-S-19500.

3.3 Design and construction - The diodes shall be of the design, construction, and physical dimensions specified in Figure 1 and as otherwise specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

3.3.1 Operating position - The diodes shall be capable of proper operation in any position.

3.4 Performance characteristics - The diode performance characteristics shall be as specified in Tables I, II, and III.

3.4.1 Process-conditioning, testing, and screening for "TX" types - The procedure for process-conditioning, testing and screening the "TX" types shall be as specified in 4.5 through 4.5.8.

3.5 Marking - The following marking specified in MIL-S-19500 may be omitted at the option of the manufacturer:

(a) Manufacturer's identification
(b) Country of origin
(c) Component designation (1N)
(d) Inspection lot identification code

3.5.1 Type designation - It is permissible to have the type designation on more than one line as follows:

J5	or	JX5	Illustration shows marking for typical 1N5624 device.
624		624	

3.5.2 Polarity - The polarity shall be indicated with a contrasting color band to derate the cathode end.

4. Quality assurance provisions

4.1 Sampling and inspection - Sampling and inspection shall be in accordance with MIL-S-19500 and as specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

4.2 Qualification inspection - Qualification inspection shall consist of the examinations and tests specified in Tables I, II, and III.

4.2.1 Group A inspection - Group A inspection shall consist of the examinations and tests shown in Table I and shall be performed on an inspection sublot of each type.

4.2.2 Group B inspection - Group B inspection shall consist of the examinations and tests shown in Table II. Subgroups 1, 2, 3, and 4 of Group B inspection and Subgroup 2 of Group C inspection may be performed on an inspection sublot of any type to qualify all types. Subgroups 6 and 7 of Group B inspection shall be performed on an inspection sublot of the highest voltage type being qualified. Subgroup 1 of Group C shall be performed on the highest voltage type within a barometric pressure group to qualify that type and all lower voltage types within this barometric pressure group. Subgroup 3 of Group C shall be performed on an inspection sublot for each voltage type of the highest and lowest voltage units being qualified.

4.2.3 Qualification testing - The non TX types shall be used for qualification testing. At the manufacturers request to the qualifying activity, qualification will be extended to include the TX type of the device.

4.3 Quality conformance inspection - Quality conformance inspection shall consist of the examinations and tests specified in Tables I, II, III, and IV.

4.3.1 Group A inspection - Group A inspection shall consist of the examinations and tests specified in Table I. Group A inspection shall be conducted on an inspection sublot of each type.

4.3.2 Group B inspection - Group B inspection shall consist of the examinations and tests specified in Table II. Group B inspection may be done on a lot basis with the exception of subgroups 6 and 7. For subgroups 6 and 7, subgroups of the highest and lowest voltage types present in the lot shall be used to accept that type and all intermediate voltage types.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

4.3.3 Group C inspection - Group C inspection shall consist of the examinations and tests specified in Table III and shall be performed on every 10th lot or every 6 months, whichever comes first. Group C inspection may be performed on a lot basis with the exception of subgroup 1 which shall be performed on a sublot of the highest voltage type within a barometric pressure group, to accept that type and all lower voltage types within this barometric pressure group. If a lot contains a higher voltage type than has previously been accepted to subgroup 1 in the current 6 month period, this higher voltage type shall be subjected to subgroup 1 inspection.

4.4 Methods of examination and test - Methods of examination and test shall be as specified in Tables I, II, III, IV, and as follows.

4.4.1 Reverse recovery time - The reverse recovery time shall be measured in the circuit of Figure 2 or equivalent. The pulse generator shall have a pulse repetition frequency of 1 KHz maximum and a pulse width of 10 nsec minimum. The recovery conditions shall be as follows: 0.5 amp forward current to 1.0 amp reverse current. The recovery time shall be measured when the rectifier recovers to -0.25 amps. Point of contact on leads shall be no less than 3/8" from the diode body.

4.4.2 Thermal impedance - Thermal impedance shall be measured in accordance with general requirements of Standard MIL-STD-750, Method 3151, Figure 4A and 4B herein and as specified herein. The high temperature point shall be 100°C. The low temperature test shall be performed at room ambient conditions with the device mounted in an infinite heat sink. The heat sink shall be attached to the lead at a point that is .375 inches from thebody of the device. The rectifier under test shall be protected in such a manner that no draft or forced-air flow shall flow across the body of the device. The procedure will be as shown in Figure 4A.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

4.4.3 Scope display - The sample devices under Table II, Group B inspection, Subgroup 5 shall be tested to the following requirements. The devices shall be subjected to scope display evaluation as described in paragraph 4.5.7 herein with the additional following requirements. I_R over the knee shall be equal to or greater than 50 micro amps. Any device exhibiting rejection characteristics as described in paragraph 4.5.7 shall be considered a failure.

4.4.4 Steady state operation life test - This test shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction, followed by a half-sine waveform of the specified average rectifier current. The forward conduction angle of the rectified current shall not be greater than 180° nor less than 150° and the power shall be equal to or greater than that of a half-sine wave. Mounting method shall utilize a clip type connection; no heat sink nor forced-air flow across the body of the device shall be employed.

4.4.5 Resistance to solvents - Diodes shall be subjected to tests in accordance with Method 215 of MIL-STD-202. The following details shall apply:

(a) All areas of the diode body where marking has been applied shall be brushed.

(b) After subjection to the tests, there shall be no evidence of mechanical damage to the device and markings shall have remained legible.

4.5 Process-conditioning, testing, and screening for "TX" devices - The procedure for process-conditioning, testing, and screening the "TX" types shall be in accordance with 4.5.8 and Figure 3. Process conditioning shall be conducted on 100 percent of the lot prior to submission of the lot to the tests specified in Tables I, II, and III. (At the option of the manufacturer, the non TX types may be subjected to process-conditioning and testing.)

Source: https://assist.dla.mil -- Downloaded: 2026l0-19T01:47Z
Check the source to verify that this is the currentversion before use.

4.5.1 Quality assurance records and determinants - The manufacturer shall maintain and make available for perusal and review at any time, during a period of three (3) years minimum, to any authorized Government Representative or other contracting customer concerned, complete lot-by-lot records for these devices. All devices that fail to meet the process-conditioning, testing and screening requirements specified herein shall be removed from the respective lot and the test-failure identity and quantity removed shall be recorded in the permanent lot history.

4.5.2 High temperature storage - The devices shall be stored for at least twenty-four (24) hours at a minimum temperature (T_A) of +200°C.

4.5.3 Thermal shock (temperature cycling) - The semiconductor diodes shall be subjected to temperature cycling (thermal shock) in accordance with MIL-STD-750, Method 1051, Test Condition C, except that cycling duration shall be ten (10) continuous cycles and exposure time at temperature extremes shall be fifteen (15) minutes minimum.

4.5.4 Acceleration - All devices shall be subjected to the acceleration test in accordance with MIL-STD-750, Method 2006, with the following exceptions: The test shall be performed onetime in the Y_1 orientation only, at a peak level of 10,000G minimum. The one-minute hold-time requirement shall not apply.

4.5.5 Hermetic seal tests - All devices shall be subjected to hermetic seal tests (fine leak followed by gross leak) with test conditions as specified in 4.5.5.1, 4.5.5.2, or 4.5.5.3.

4.5.5.1 Fine Leak Test - All devices shall be fine-leak tested in accordance with MIL-STD-750, Method 1071, test condition G or H.

4.5.5.2 Gross leak test (bubble) - All devices shall be tested for gross leaks in accordance with MIL-STD-750, Method 1071, test condition D, except that the solution may be any suitable non-corrosive liquid at a minimum temperature of 100°C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

4.5.5.3 Gross leak test (penetrant dye) - All devices shall be tested for gross leaks in accordance with MIL-STD-750, Method 1071, test condition E. After the alcohol rinse and drying cycle, non-transparent devices shall be examined by placing them on a clean white platter and observing for any evidence of dye.

4.5.6 Burn-in conditioning, tests, and evaluation (screening) - To enable proper evaluation of the diodes conditioned and tested in accordance with the following requirements, each diode and lot shall be handled or identified in such manner that delta data/results for each individual diode and lot can be ascertained and recorded.

4.5.6.1 Pre burn-in measurements - The diodes shall be tested for the characteristics V_F and I_R (at room ambient T_A), listed in Table IV below, and the values found shall be recorded. Those diodes that fail to meet the specified limits shall be rejected and removed from the lot.

4.5.6.2 Burn-in conditioning - The diodes shall be energized and operated for 164 hours minimum, under the following conditions and those specified in 4.3.6 herein.

T_A=+55°C
I_O=3.5A
V_{RM}(wkg) = full rated (see paragraph 1.3)
f=60Hz

4.5.6.3 Post burn-in tests and measurements - After burn-in conditioning, the diodes shall be permitted to return to room ambient temperature (thermal equilibrium) and shall be retested, within a maximum total elapsed time of eight (8) hours, for the characteristics V_F and I_R, and I_R at T_A = 150°C, per Table IV herein. The values for V_F and I_R on each individual diode shall not exceed the following delta limits:

$\Delta V_F = \pm 0.1$ Vdc

ΔI_R (at T_A=room ambient): +250nA, maximum

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

4.5.7 Scope-display evaluation -

(a) The breakdown characteristics, at rated V_R (at room ambient temperature), of the device shall be viewed graphically on an oscilloscope of display sensitivity: 20μA/cm (max.) vertical, 200V/cm (max.) horizontal.

(b) Each device, when viewed on the oscilloscope, shall present sharp knee characteristics. Any discontinuity or dynamic instability of the trace shall be cause for rejection.

4.5.8 Process-conditioning evaluation (screening) - Those diodes whose measured characteristics exceed the delta (Δ) limits specified in 4.5.6.3 above, or the limits of Table IV or fail scope-display evaluation (see 4.5.7 above), shall be rejected and removed from the lot. Where a total of 10% or more of the diodes subjected to the burn-in test are found to exceed those limits, the entire lot shall be considered non-acceptable as "TX" Devices.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 1			5	5				
Visual and mechanical examination	2071				---	---	---	---
Subgroup 2			5	3				
Forward Voltage	4011	DC Current I_F=3.5 Adc						
1N5624					V_F	0.6	1.0	Vdc
1N5625					V_F	0.6	1.0	Vdc
1N5626					V_F	0.6	1.0	Vdc
1N5627					V_F	0.6	1.0	Vdc
Reverse current	4016	DC method						
1N5624		V_R=200Vdc			I_R	---	1.0	μAdc
1N5625		V_R=400Vdc			I_R	---	1.0	μAdc
1N5626		V_R=600Vdc			I_R	---	1.0	μAdc
1N5627		V_R=800Vdc			I_R	---	1.0	μAdc
Reverse current (high temp.)	4016	T_A=+150°C DC method						
1N5624		V_R=200Vdc			I_R	---	100	μAdc
1N5625		V_R=400Vdc			I_R	---	100	μAdc
1N5626		V_R=600Vdc			I_R	---	100	μAdc
1N5627		V_R=800Vdc			I_R	---	100	μAdc
Reverse recovery time		Test circuit and test conditions nomograph per figure 3 herein. (paragraph 4.4.1)						
1N5624					t_{rr}	---	5	μsec
1N5625					t_{rr}	---	5	μsec
1N5626					t_{rr}	---	5	μsec
1N5627					t_{rr}	---	5	μsec

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Breakdown Voltage	4021							
1N5624		I_R=50 μA			BV	240	---	Vdc
1N5625		I_R=50 μA			BV	460	---	Vdc
1N5626		I_R=50 μA			BV	660	---	Vdc
1N5627		I_R=50 μA			BV	880	---	Vdc

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE II. Group B inspection

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 1			5	5				
Physical dimensions	2066	(see Figure 1)			---	---	---	---
Subgroup 2			10	10				
Solderability	2026							
Soldering heat	2031	20 cycles per lead dwell time =30 sec.			---	---	---	---
Temperature cycling	1051	Test Condition C 10 cycles			---	---	---	---
Thermal shock (glass strain)	1056	Test Condition B low temp.-65°C high temp.+200°C			---	---	---	---
Seal (leak rate)	1071	Test Condition G or H for fine leaks. Test condition D or E for gross leaks. (paragraph 4.5.5)					$1X10^{-8}$ ATM cc/sec $1X10^{-4}$ ATM cc/sec	
Moisture resistance	1021	No initial conditioning			---	---	---	---
End-point tests:								
Same as established in Table IV.								

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE II. Group B inspection - continued

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 3			10	10				
Shock	2016	Non-operating 2500G, 5 blows of 0.5 msec each in orientations X_1, Y_1, Y_2 (total=15 blows)						
Vibration variable frequency	2056				---	---	---	---
Constant acceleration	2006	20,000G orientations X_1, Y_1, Y_2			---	---	---	---
End-point tests:								
Same as established in Table IV								
Subgroup 4			10	10				
Terminal strength (lead fatigue)	2036	Test Condition E			---	---	---	---
(No End-points)		Weight = 2 lbs. + 1 oz.						

Source: https://assist.dla.mil -- Downloaded: 202610-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE II. Group B inspection - Continued

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 5			10	5				
Thermal resistance	3151	Paragraph 4.4.2			θ j-L	---	18	°C/W
Surge current	4066	i_f(surge=125A) 10 surges of 8.3 msec each at 1-minute intervals Superimpose on: I_O=2.5 Adc V_{RM}(wkg)=rated (for each type), at T_A=+100°C			---	---	---	---
Scope display/ internal arcing		Paragraph 4.5.7						
End-point tests:								
Same as established in Table IV								
Subgroup 6			λ =5	λ=3				
High temperature life (non-operating)	1031	T_A=+200°C			---	---	---	---
End-point tests:								
Same as established in Table IV herein plus scope display evaluation								

Source: https://assist.dla.mil -- Downloaded: 202610-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE II. Group B inspection - Continued

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 7			$\lambda=5$	$\lambda=5$				
Steady state operation life	1026	T_A=55°C I_O=3.5 Adc f=60 H_z V_{RM}(wkg)=rated (for each type) Paragraph 4.4.4			---	---	---	---
End-point tests: Same as established in Table IV plus scope display evaluation								

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE III. Group C inspection

Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 1			7	5				
Barometric pressure reduced (altitude operation)	1001	For 1N5624,5,6 Pressure=8 mm Hg For 1N5627 Pressure=33 mm Hg t=1 min. minimum Paragraph 1.3			---	---	---	---
Measurement during test:								
Reverse Current	4016	V_R=rated (for each type) T_A=room ambient			I_R	---	1.0	μAdc
Subgroup 2			10	7				
Salt atmosphere (corrosion)	1041	---			---	---	---	---
Subgroup 3			7	5				
Low temperature operation:		T_A=65°C						
Forward voltage	4011	I_F=3.5 Adc			V_F	---	1.5	Vdc
Breakdown voltage	4021							
1N5624		I_R=50 A			BV	200	---	Vdc
1N5625		I_R=50 A			BV	400	---	Vdc
1N5626		I_R=50 A			BV	600	---	Vdc
1N5627		I_R=50 A			BV	800	---	Vdc

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE III. Group C inspection - Continued


Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Subgroup 4 Temperature cycling End-point tests: Same as established in Table IV	1051	Test Condition C-1	10	7				

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

TABLE IV. Test and measurements


Examination or Test	MIL-STD-750		LTPD		Symbol	Limits		
	Method	Details	Non TX	TX		Min.	Max.	Unit
Forward voltage	4011	I_F=3.5 Adc						
1N5624					V_F	0.6	1.1	Vdc
1N5625					V_F	0.6	1.1	Vdc
1N5626					V_F	0.6	1.1	Vdc
1N5627					V_F	0.6	1.1	Vdc
Reverse current	4016							
1N5624		V_R=200Vdc			I_R	---	1.0	μAdc
1N5625		V_R=400Vdc			I_R	---	1.0	μAdc
1N5626		V_R=600Vdc			I_R	---	1.0	μAdc
1N5627		V_R=800Vdc			I_R	---	1.0	μAdc

Source: https://assist.dla.mil -- Downloaded: 202610-19T01:47Z
Check the source to verify that this is the current version before use.

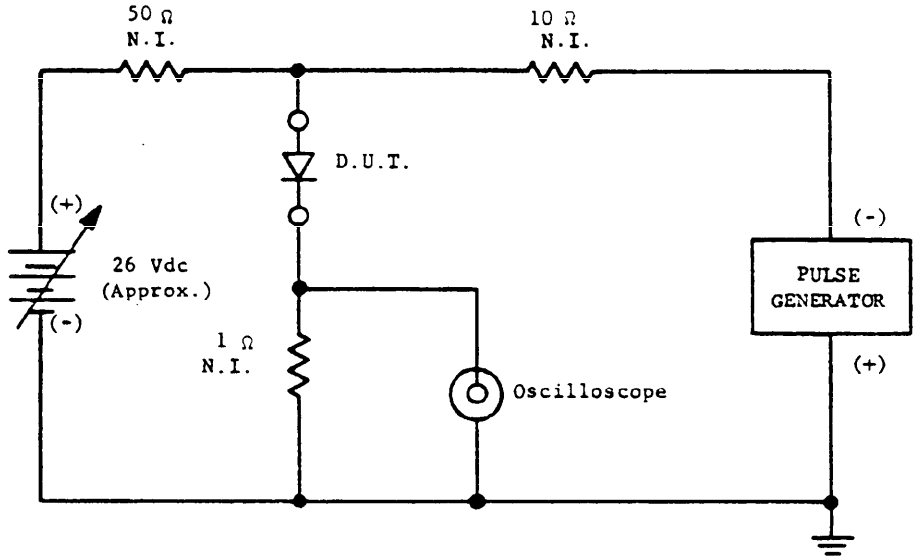

NOTES:

1. Oscilloscope: Rise time ≤ 7 nsec; input impedance = 1 Meg; 22 pf
2. Pulse Generator: Rise time ≤ 10 nsec; source impedance = 50Ω

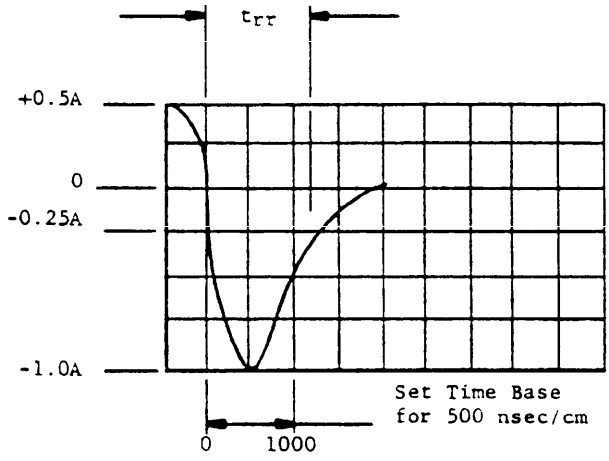

REVERSE RECOVERY TIME TEST CIRCUIT AND CHARACTERISTIC NOMOGRAPH

FIGURE 2

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.


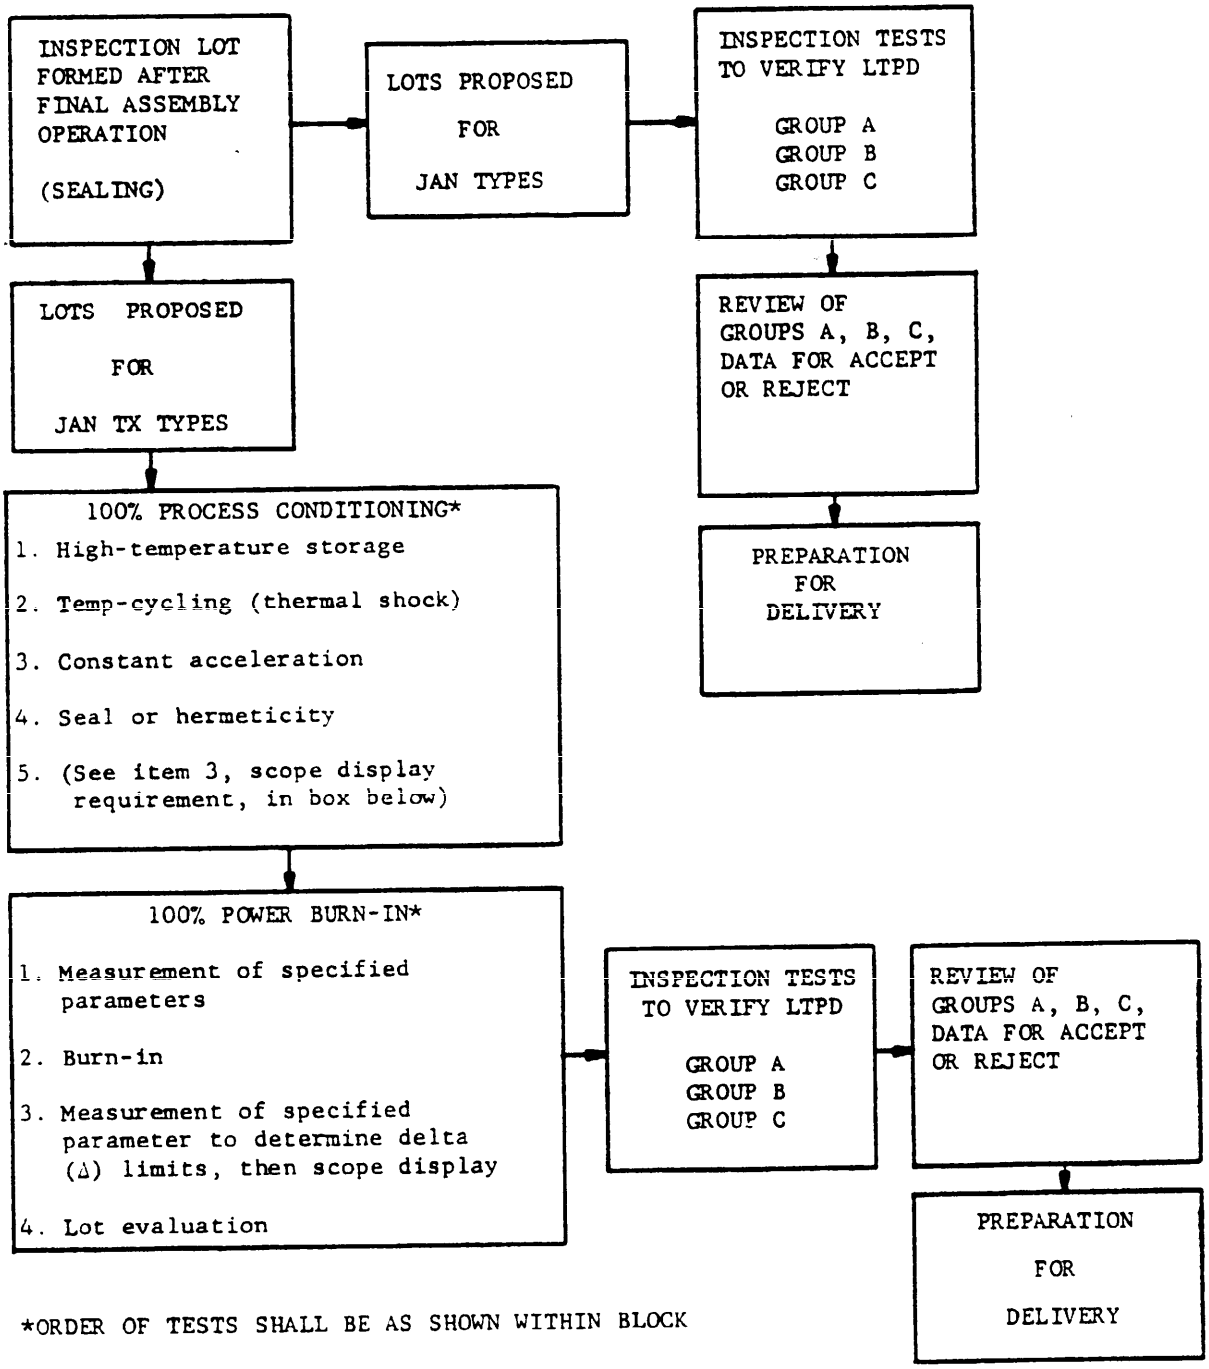


FIGURE 3. Flow Chart of non-TX and TX types

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

THERMAL RESISTANCE TEST
FUNCTIONAL BLOCK DIAGRAM

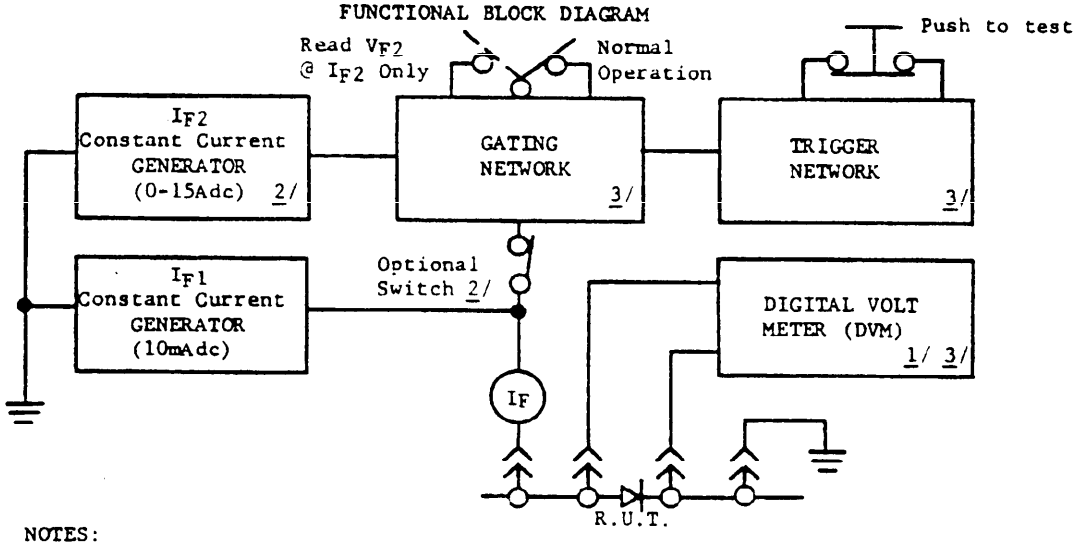

NOTES:

1/ The same D.V.M. must be used for all V_F readings.

2/ I_{F2} generator must be turned off or switched out of circuit for testing V_{F1} @ I_{F1} @ 100°C.

3/ The trigger network, gating network, and D.V.M. must be capable of operating within the time limits specified in the timing diagram. See Figure 4B.

PROCEDURE:

1. Place R.U.T. in high temperature test fixture. Read and record V_{F1} @ I_{F1} (10mAdc) @ T_A=100°C (See Notes 1 and 2).

2. Place R.U.T. in infinite heat sink mounting at room ambient conditions (approximately 25°C). R.U.T. shall be mounted as shown in mounting detail. See Figure 4B.

3. Apply I_{F2} (0-15A supply) and allow to stablize for $\geq$ 30 seconds. Depress push to test switch and read V_{F1} @ I_{F1}. Compare V_{F1} @ T_A (room ambient) reading with data recorded for V_{F1} @ T_A (100°C). (See timing diagram - Figure 4B.)

4. Gradually increase I_{F2} (taking readings as described in procedure 3 above) until V_{F1} @ T_A (room ambient) = V_{F1} @ T_A (100°C).

5. Read and record V_{F2} and I_{F2}.

6. Calculate


$$\theta = \frac{T_1 - T_2}{\text{Watts}} = \frac{T_A(100^\circ C) - T_A \text{ (room ambient)}}{V_{F2} \cdot I_{F2}}$$

$$\theta = \frac{75^\circ C}{V_{F2} \cdot I_{F2}} = \text{Thermal impedance junction to lead (.375 from body) in } ^\circ C/W.$$


o o

FIGURE 4A
See paragraph 4.4.2

Source: https://assist.dla.mil -- Downloaded: 202610-19T01:47Z
Check the source to verify that this is the current version before use.

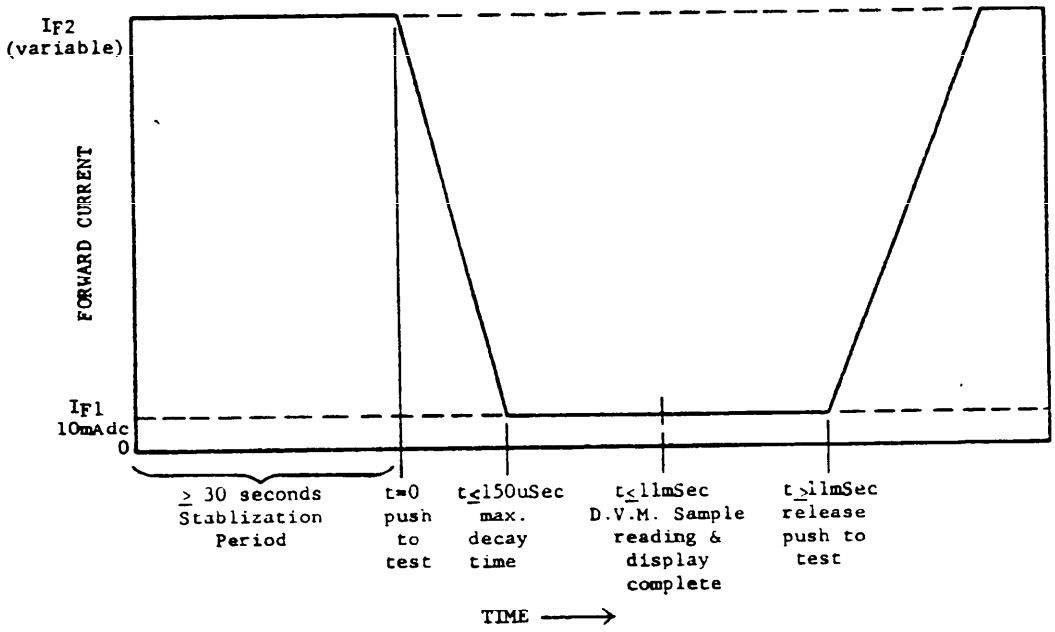

TIMING DIAGRAM
(See Note 3 and Procedure 3 and 4, Figure 4A)

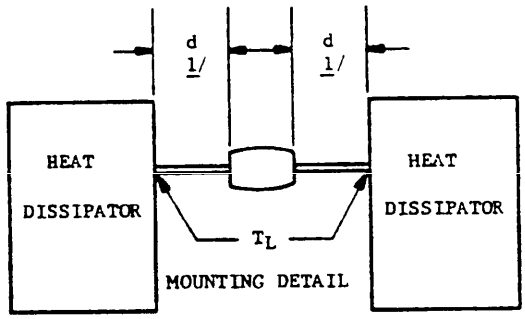

NOTES:

1/ d shall be measured from the body of the device. Exposed portion of leads shall be free of paint, grease, or other coatings of any kind.

*TYP. THERMAL IMPEDANCE CHART

d	θ j-L
INCHES	°C/W
0.000	10
0.250	15
0.375	18
0.500	21
0.750	27

*For Use as Application Information Only

FIGURE 4B

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

5. PREPARATION FOR DELIVERY

5.1 Preparation for delivery - Preparation for delivery and the inspection of preparation for delivery shall be in accordance with Specification MIL-S-19500.

6. NOTES

6.1 Notes - The notes included in Specification MIL-S-19500, with the following additions or exceptions, are applicable to this specification.

6.2 Application guidance - To insure proper equipment-circuit application, particular attention should be given to the differential voltage and reverse-recovery-time ratings pertinent to the individual diode types covered herein.

6.3 Ordering data -

(a) Lot inspection data: See Paragraph 4.3.

6.4 Procurement of TX types - See Paragraph 4.5.

6.5 Quality assurance for "TX" types - It is expected that where the permanent lot record, maintained as required in 4.4.1 herein, begins to show a condition of failures in excess of the LTPD rate specified herein, or a condition of entire lot rejection (see 4.5.8 herein) is recorded, the Government procuring activity will determine any additional monitoring controls and evaluation criteria needed to attain restoration of the prescribed (herein) quality assurance for acceptance of product.

6.6 Qualification - With respect to products requiring qualification, awards will be made only for such products as have, prior to the time set for opening of bids, been tested and approved for inclusion in Qualified Products List QPL-19500, whether or not such products have actually been so listed by that date. The activity responsible for the Qualified Products List is Rome Air Development Center, ATTN: EMNRB, Griffiss Air Force Base, New York 13440; however, information pertaining to the qualification of products may be obtained from the Defense Electronics Supply Center, 1507 Wilmington Pike, Dayton, Ohio 45401.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

BAROMETRIC PRESSURE, REDUCED (HIGH ALTITUDE OPERATION):

Custodian:

Air Force - 17

Review activities:
Air Force - 11, 70, 85

Preparing activity:

Air Force - 17

(Project 5961-F291)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.

SPECIFICATION ANALYSIS SHEET

Form Approved
Budget Bureau No. 22-R255

INSTRUCTIONS: This sheet is to be filled out by personnel, either Government or contractor, involved in the use of the specification in procurement of products for ultimate use by the Department of Defense. This sheet is provided for obtaining information on the use of this specification which will insure that suitable products can be procured with a minimum amount of delay and at the least cost. Comments and the return of this form will be appreciated. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments and suggestions submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or serve to amend contractual requirements.

SPECIFICATION

ORGANIZATION

CITY AND STATE

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE SPECIFICATION CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY SPECIFICATION REQUIREMENT CONSIDERED TOO RIGID

3. IS THE SPECIFICATION RESTRICTIVE?

☐ YES ☐ NO *(If "yes", in what way?)*

4. REMARKS *(Attach any pertinent data which may be of use in improving this specification. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity)*

SUBMITTED BY *(Printed or typed name and activity - Optional)*

DATE

DD FORM 1 JAN 66 1426

REPLACES EDITION OF 1 OCT 64 WHICH MAY BE USED.

Source: https://assist.dla.mil -- Downloaded: 2026\10-19T01:47Z
Check the source to verify that this is the current version before use.

FOLD

POSTAGE AND FEES PAID
Department of the Air Force

OFFICIAL BUSINESS

RADC (EMNRB)
Griffiss AFB NY 13440

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T01:47Z
Check the source to verify that this is the current version before use.