The documentation and process conversion measures necessary to comply with this revision shall be completed by 7 July 2000.

INCH-POUND

MIL-PRF-19500/609C
7 April 2000
SUPERSEDING
MIL-PRF-19500/609B
21 May 1997

PERFORMANCE SPECIFICATION

SEMICONDUCTOR DEVICE, DIODE, SILICON, SWITCHING
TYPES 1N6639, 1N6640, 1N6641, 1N6639US, 1N6640US, AND 1N6641US
JAN, JANTX, JANTXV, JANJ, AND JANS

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for controlled forward voltage switching diodes. Five levels of product assurance are provided for each device type as specified in MIL-PRF-19500.

1.2 Physical dimensions. See figure 1 (similar to D0-35) and figure 2 (D-5D).

1.3 Maximum ratings. T_A = +25°C.

Types	V_{BR}	V_{RWM}	I_O (1), (2)	I_{FSM} t_p= 1/120 s	T_{STG}, T_J	$R_{\theta JL}$ L = .375	$R_{\theta JEC}$ L = 0	$Z_{\theta JX}$
	V (pk)	V (pk)	mA	A (pk)	°C	°C/W	°C/W	°C/W
1N6639, 1N6639US	100	75	300	2.5	-65 to +175	160	50	25
1N6640, 1N6640US	75	50	300	2.5	-65 to +175	160	50	25
1N6641, 1N6641US	75	50	300	2.5	-65 to +175	160	50	25

(1) Derate at 3.0 mA/°C above T_L = +75°C for axial lead, L = 9.53 mm (.375 inch).
(2) Derate at 4.6 mA/°C above T_{EC} = +110°C for US suffix types.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: (ex. Defense Supply Center, Columbus, ATTN: DSCC/VAC, Post Office Box 3990, Columbus, OH 43216-5000), by using the Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5961

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics.. Unless otherwise specified, primary electrical characteristics at T_A = +25°C.

Types	V_{F4} I_F = 200 mA (pulsed)	V_{F5} I_F = 500 mA (pulsed)	I_{R1} at T_A = +25°C V_R = V_{RWM}	I_{R2} at T_A = +150°C V_R = V_{RWM}	t_{fr} I_F = 200 mA	t_{rr} I_{RM} = I_F = 10 mA	C_{T1} V_R = 0
	V dc	V dc	nA dc	µA dc	ns	ns	pF
1N6639, 1N6639US		1.2	100	100	10	4.0	2.5
1N6640, 1N6640US	1.0		100	100	10	4.0	2.5
1N6641, 1N6641US	1.1		100	100	10	5.0	3.0

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

DEPARTMENT OF DEFENSE

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

STANDARD


DEPARTMENT OF DEFENSE

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of the above specifications, standards, and handbooks are available from the Defense Automated Printing Service, Building 4D (NPM-DODSSP), 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein (except for related associated specifications or specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

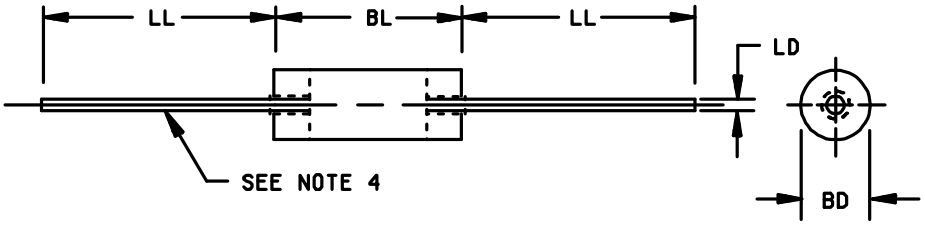


Symbol	Dimensions				Notes
	Inches		Millimeters		
	Min	Max	Min	Max	
BD	.056	.080	1.42	2.03	2, 3
BL	.130	.180	3.30	4.57	
LD	.018	.022	0.46	0.56	4
LL	1.00	1.50	25.40	38.10	

TYPES 1N6639, 1N6640, AND 1N6641

NOTES:
1. Metric equivalents are given for general information only.
2. The maximum dimension of BD shall apply for dimension BL
3. The minimum dimension of BD shall apply over at least 1.65 mm (.065 inch) of dimension BL.
4. The specified lead diameter applies in the zone between 1.27 mm (.050 inch) from the diode body to the end of the lead. Outside of this zone lead shall not exceed BD.

FIGURE 1. Physical dimensions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

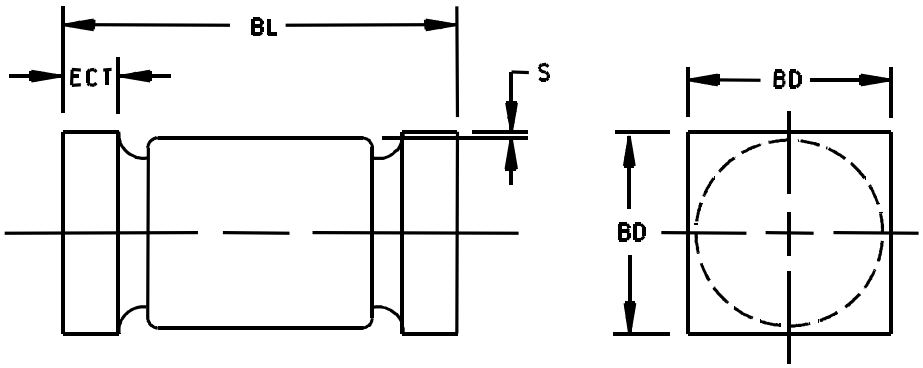

Symbol	Dimensions			
	Millimeters		Inches	
	Min	Max	Min	Max
BD	.070	.085	1.78	2.16
BL	.165	.195	4.19	4.95
ECT	.019	.028	0.48	0.71
S	.003	---	0.08	---

TYPES 1N6639US, 1N6640US, AND 1N6641US

FIGURE 2. Physical dimensions of surface mount family (D-5D).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 Associated specification. The individual item requirements shall be in accordance with MIL-PRF-19500 and as specified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified manufacturers list before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.4 Interface requirements and physical dimensions. The Interface requirements and physical dimensions shall be as specified in MIL-PRF-19500 and on figure 1 and figure 2 herein.

3.4.1 Lead finish. Lead finish shall be solderable as defined in MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.5).

3.4.2 Diode construction.

a. All devices shall be of metallurgically bonded, thermally matched, noncavity-double plug construction in accordance with the requirements of category I (see MIL-PRF-19500).

b. The 'US' version shall be structurally identical to the non-US versions except for end cap lead attachment.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500.

3.5.1 Marking for 'US' devices. For 'US' version devices only, all marking may be omitted from the body (except for 3.6), but shall be retained on the initial container.

3.6 Polarity. Alternatively, the polarity of all types shall be indicated with a contrasting color band to denote the cathode end. For 'US' suffix devices a minimum of three contrasting color dots spaced around the cathode end of the device may be used.

3.7 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.8 Electrical test requirements. The electrical test requirements shall be the subgroups specified in table I herein.

3.9 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3)

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500.

4.2.1 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table IX of MIL-PRF-19500, and table II herein. End point electrical measurements shall be as specified in table I, group A, subgroup 2 herein.

4.2.2 JANJ qualification. For JANJ qualification, 4.4.2.1 herein shall be performed as required by the qualifying activity.

4.2.3 JANJ devices. For JANJ level, 3.3.1 through 3.3.1.3 of MIL-PRF-19500 shall apply, except as modified herein. Supplier imposed requirements as well as alternate screens, procedures, and/or controls shall be documented in the QM plan and must be submitted to the Qualifying Activity for approval. When alternate screens, procedures, and/or controls are used, in lieu of the JANJ screens herein equivalency shall be proven and documented in the QM Plan. Radiation characterization may be submitted in the QM plan at the option of the manufacturer, however, paragraph 3.3.1.1 of MIL-PRF-19500 is not required. Die lot control and rework shall be in accordance with MIL-PRF-19500 paragraph 3.13 and D 3.13.2.1 for JANS level. Lot formation and conformance inspection requirements for JANJ shall be those used for JANTXV devices as a minimum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANS, JANJ, JANTXV and JANTX levels only). Screening shall be in accordance with MIL-PRF-19500 (table IV), and as specified herein. Specified electrical measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	JANS Level	JANJ Level	JANTXV and JANTX Level
1a 1b	Required Required	Not Required Required	Not Required Required (JANTXV only)
2	Not Required	Not Required	Not Required
3a 3b 3c (1)	Required Not Applicable Thermal impedance (see 4.3.2)	Required Not Applicable Thermal impedance (see 4.3.2)	Required Not Applicable Thermal impedance (see 4.3.2)
4	Not Applicable	Not Applicable	Not Applicable
5	Not Applicable	Not Applicable	Not Applicable
6	Not Applicable	Not Applicable	Not Applicable
7a 7b	Not Applicable Required	Not Applicable Required	Not Applicable Required
8	Required	Not Required	Not Required
9	I_{R1}	I_{R1}	Not Applicable
10	Method 1038, condition A	Method 1038, condition A	Method 1038, condition A
11	V_{F4} (1N6640, 1N6641) or V_{F5} (1N6639), I_{R1}; and $V_{(BR)}$ ΔI_{R1} ±15 nA dc or 100 percent of initial value whichever is greater.	V_{F4} (1N6640, 1N6641) or V_{F5} (1N6639), I_{R1}; and $V_{(BR)}$ ΔI_{R1} ±15 nA dc or 100 percent of initial value whichever is greater.	V_{F4} (1N6640, 1N6641) or V_{F5} (1N6639) and I_{R1}
12	Required See 4.3.1	Required T = 240 hours See 4.3.1	Required See 4.3.1
13	Subgroups 2 and 3 of table I herein; $\Delta I_{R1} \leq$ 100 percent of initial reading or 15 nA dc, whichever is greater. $\Delta V_{F4} \leq \pm$ 0.030 V dc for 1N6640, 1N6641), $\Delta V_{F5} \leq \pm$ 0.030 V dc for 1N6639. Reverse scope display evaluation (see MIL-STD-750, method 4023)	Subgroups 2 and 3 of table I herein; $\Delta I_{R1} \leq$ 100 percent of initial reading or 15 nA dc, whichever is greater. $\Delta V_{F4} \leq \pm$ 0.030 V dc for 1N6640, 1N6641), $\Delta V_{F5} \leq \pm$ 0.030 V dc for 1N6639. Reverse scope display evaluation (see MIL-STD-750, method 4023)	Subgroup 2 of table I herein; $\Delta I_{R1} \leq$ 100 percent of initial reading or 15 nA dc, whichever is greater. $\Delta V_{F4} \leq \pm$ 0.030 V dc for 1N6640, 1N6641), $\Delta V_{F5} \leq \pm$ 0.030 V dc for 1N6639. Reverse scope display evaluation (see MIL-STD-750, method 4023)
14a 14b	Not Applicable Optional	Not Applicable Optional	Not Applicable Optional
15	Required	Not Required	Not Required
16	Required	Required	Not Required
17	Not Required	Required Subgroup 2 of table I herein	Not Required

(1) Thermal impedance shall be performed any time after screen 3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

4.3.1 Power burn-in conditions. Power burn-in conditions are as follows (see 4.5.3):

Method 1038, condition B, T_A = room ambient as defined in 4.5 of MIL-STD-750. V_R = rated V_{RWM}; f = 50-60 Hz; I_O = 300 mA. An alternative of I_F (dc) = 300 mA may be used at T_A = room ambient as defined in 4.5 of MIL-STD-750.

4.3.2 Thermal impedance $Z_{\theta JX}$ measurements for screening. The $Z_{\theta JX}$ measurements shall be performed in accordance with MIL-STD-750, method 3101. The maximum limit and conditions for $Z_{\theta JX}$ in screening (table IV of MIL-PRF-19500) shall be derived statistically by each vendor by means of actual measurements which characterize the die attach process (not to exceed the group A limit.)

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with table V of MIL-PRF-19500, table I herein, and as specified herein. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2 herein. The following test conditions shall be used for $Z_{\theta JX}$, group A inspection.

a. I_H forward heating current ..... 1-2 A.
b. t_H heating time ..... 10 ms.
c. I_M measure current ..... 1 mA to 10 mA.
d. t_{MD} measurement delay time ..... 100 µs maximum.

The maximum limit for $Z_{\theta JX}$ under these test conditions is $Z_{\theta JX(max)}$ = 25°C/W.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in tables VIa (JANS) and VIb (JAN, JANTX, JANTXV, and JANJ) of MIL-PRF-19500 and paragraphs 4.4.2.1 and 4.4.2.2 herein. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2.

4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500.

Subgroup	Method	Conditions
B4	1037	$V_{(pk)}$ = rated V_{RWM} = V_R, T_A = room ambient as defined in 4.5 of MIL-STD-750, f = 50-60 Hz (see 4.5.1); t_{on} = t_{off} = 1 minute minimum; 2,000 cycles; I_O = 300 mA maximum; In lieu of ac conditions, a dc condition of I_F = 400 mA may be used.
B5	1027	Option 1: Adjust T_A or I_O to obtain a minimum T_J of +275°C, t = 96 hours. I_O = 300 mA minimum, V_R = rated V_{RWM}, f = 50-60 Hz (see 4.5.1),
B5	1027	Option 2: Adjust T_A or I_O to obtain a minimum T_J of +200°C, t = 1000 hours. I_O = 300 mA minimum, V_R = rated V_{RWM}, f = 50-60 Hz (see 4.5.1),
B6	3101 or 4081	L = .375 inch (9.53 mm); $R_{\theta JL}$ = 160°C/W maximum (see 4.5.4); $R_{\theta JEC}$ = 50°C/W maximum (see 4.5.4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

4.4.2.2 Group B inspection, table VIb (JAN, JANTX, JANTXV, and JANJ) of MIL-PRF-19500.

Subgroup	Method	Condition
B3	1027	T_A = room ambient as defined in 4.5 of MIL-STD-750; V (pk) = rated V_{RWM}; f = 50-60 Hz (see 4.5.1); I_O = 300 mA dc; adjust T_A to obtain a minimum T_J of +150°C.
B5	3101 or 4081	See 4.5.4.
B6	1032	T_A = +175°C.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2.

Subgroup	Method	Condition
C2	2036	Tension: Test condition A; weight 4 pounds, t = 15 seconds. Lead fatigue: Test condition E. NOTE: Not applicable for 'US' suffix types.
C6	1026	1,000 hours minimum at T_A = room ambient as defined in 4.5 of MIL-STD-750; V (pk) = rated V_{RWM}; f = 50-60 Hz (see 4.3.1); I_O = 300 mA dc; adjust T_A to obtain a minimum T_J of +150°C.

4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table IX of MIL-PRF-19500 and table II herein. Electrical measurements (end-points) shall be in accordance with table I, group A, subgroup 2 herein.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Life test. These tests shall be conducted with a half-sine waveform of the specified peak voltage impressed across the diode in the reverse direction followed by a half-sine waveform of the specified average rectified current. The forward conduction angle of the rectified current shall be neither greater than 180 degrees, no less than 150 degrees.

4.5.2 Forward-recovery voltage and time. Forward recovery shall be measured as the time interval between zero time and the point where the pulse has decreased to 110 percent of the steady-state value of V_F when I_F = 200 mA dc. The maximum rise time of the response detector shall be 1 ns.

4.5.3 Scope display. The reverse breakdown characteristics shall be viewed on an oscilloscope with display calibration factors of 20 μA per division and 20 V per division. Reverse current over the knee shall be at least 100 μA and less than 200 μA. Any discontinuity or dynamic instability of the trace shall be cause for rejection of that device.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

4.5.4 Thermal resistance. Thermal resistance measurement shall be performed in accordance with MIL-STD-750, method 3101 or 4081. Forced moving air or draft shall not be permitted across the devices during test. The maximum limit for $R_{\theta JL}$ under these test condition shall be $R_{\theta JL(max)}$ = 160°C/W and $R_{\theta JEC(max)}$ = 50°C/W. The following conditions shall apply:

I_H = 75 mA to 300 mA.

t_H = 25 seconds minimum.

I_M = 1 mA to 10 mA.

t_{MD} = 100 µs maximum.

LS = Lead spacing = 9.53 mm (.375 inch) as defined on figure 3.
LS = 0 for 'US' versions.

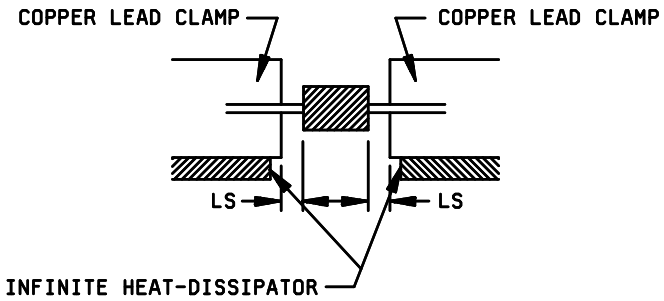


FIGURE 3. Mounting arrangement.

4.5.5 Pulse measurements. Conditions for pulse measurements shall be as specified in section 4 of MIL-STD-750.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/, 2/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Thermal impedance	3101	See 4.4.1	$Z_{\theta JX}$		25.0	°C/W
Forward voltage (1N6640, 1N6640US only)	4011	I_F = 1 mA dc pulsed	V_{F1}	0.540	0.620	V dc
Forward voltage (1N6640, 1N6640US only)	4011	I_F = 50 mA dc pulsed	V_{F2}	0.760	0.860	V dc
Forward voltage (1N6640, 1N6640US only)	4011	I_F = 100 mA dc pulsed	V_{F3}	0.820	0.920	V dc
Forward voltage	4011	I_F = 200 mA dc pulsed	V_{F4}			
1N6640, 1N6640US				0.870	1.00	V dc
1N6641, 1N6641US				0.870	1.10	V dc
Forward voltage (1N6639, 1N6639US only)	4011	I_F = 500 mA dc pulsed	V_{F5}		1.20	V dc
Breakdown voltage	4021	$I_{(BR)}$ = 10 µA dc	V_{BR}			
1N6639, 1N6639US				100		V dc
1N6640, 1N6640US				75		V dc
1N6641, 1N6641US				75		V dc
Reverse current	4016	DC method;	I_{R1}			
1N6639, 1N6639US		V_R = 75 V dc			100	nA dc
1N6640, 1N6640US		V_R = 50 V dc			100	nA dc
1N6641, 1N6641US		V_R = 50 V dc			100	nA dc
Subgroup 3						
High temperature operation:		T_A = +150°C				
Reverse current	4016	DC method	I_{R2}			
1N6639, 1N6639US		V_R = 75 V dc			100	µA dc
1N6640, 1N6640US		V_R = 50 V dc			100	µA dc
1N6641, 1N6641US		V_R = 50 V dc			100	µA dc

See footnotes at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/, 2/	MIL-STD-750		Symbol	Limits		Unit
	Method	Conditions		Min	Max	
Subgroup 3 - continued.						
Low-temperature operation:		T_A = -55°C				
Forward voltage	4011	Pulsed	V_{F6}			
1N6639, 1N6639US		I_F = 500 mA pulsed			1.3	V dc
1N6640, 1N6640US		I_F = 200 mA pulsed			1.1	V dc
1N6641, 1N6641US		I_F = 200 mA pulsed			1.2	V dc
Subgroup 4						
Capacitance	4001	V_R = 0 V dc; V_{sig} = 50 mV(p-p), f = 1 MHz	C_{T1}			
1N6639, 1N6639US					2.5	V dc
1N6640, 1N6640US					2.5	V dc
1N6641, 1N6641US					3.0	V dc
Reverse recovery time	4031	Condition A, I_F = I_{RM} = 10 mA dc;	t_{rr}			
1N6639, 1N6639US					4.0	ns
1N6640, 1N6640US					4.0	ns
1N6641, 1N6641US					5.0	ns
Subgroup 5						
Not applicable						
Subgroup 6						
Surge current	4066	I_{FSM} = see 1.3; 10 surges at 1 per minute (maximum) surge; duration = 8.3 ms				
Electrical measurements		See table I, subgroup 2 herein.				
Subgroup 7						
Forward recovery voltage and time	4026	I_F = 200 mA dc (see 4.5.2)	V_{fr}		5.0	V(pk)
			t_{fr}		10.0	ns

1/ For sampling plan, see MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

TABLE II. Group E inspection (all quality levels) for qualification only.

Inspection	MIL-STD-750		Qualification inspection
	Method	Conditions	
Subgroup 1			22 devices, c = 0
Thermal shock (glass strain)	1056	Condition A; 2,000 cycles	
Hermetic seal	1071	Gross leak only	
Electrical measurement		See table I, group A, subgroup 2	
Subgroup 2			
Not applicable			
Subgroup 3			
Not applicable			
Subgroup 4			22 devices, c = 0
Thermal resistance, junction to lead	3101 or 4081	L = 9.53 mm (.375 inch) $R_{\theta JL}$ = 160°C/W maximum; $R_{\theta JEC}$ = 50°C/W; (see 4.5.4)	
Subgroup 5			15 devices, c = 0
Potted environment test	1054		

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. Packaging shall prevent mechanical damage of the devices during shipping and handling and shall not be detrimental to the device. When actual packaging of material is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Points' packaging activity within the Military Department or Defense Agency, or within the Military Departments' System Command. Packaging data retrieval is available from the managing Military Departments' or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Notes. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Issue of DODISS to be cited in the solicitation and, if required, the specific issue of individual documents referenced (see 2.2.1).

b. Lead finish (see 3.3.1).

c. Type designation and product assurance level.

d. Packaging requirements (see 5.1).

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List QML-19500 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center Columbus, DSCC-VQE, Columbus, OH 43216.

6.4 Substitution information. The 1N6640 (MIL-PRF-19500/609) is preferred type in lieu of the 1N4150 and 1N4150-1 (MIL-PRF-19500/231).

6.4.1 Cross reference substitution list. JANS level will no longer be built to MIL-PRF-19500/231. Devices in stock are acceptable provided the date code does not exceed 23 March 1994 (the date of implementation of MIL-S-19500/231F). The devices on this specification are required for space flight applications. A PIN for PIN replacement table follows, and these devices are directly interchangeable.

Non-preferred PIN	Preferred PIN
1N4150-1	1N6640

6.5 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

CONCLUDING MATERIAL

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA - NA
DLA - CC

Review activities:
Army - AR, MI, SM
Navy - AS, MC
Air Force - 19, 99

Preparing activity:
DLA - CC

(Project 5961-2226)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.

2. The submitter of this form must complete blocks 4, 5, 6, and 7.

3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER MIL-PRF-19500/609C	2. DOCUMENT DATE 7 April 2000

3. **DOCUMENT TITLE**
SEMICONDUCTOR DEVICE, DIODE, SILICON, SWITCHING TYPES 1N6639, 1N6640, 1N6641, 1N6639US, 1N6640US, AND 1N6641US JAN, JANTX, JANTXV, JANJ, AND JANS

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) COMMERCIAL DSN FAX EMAIL	7. DATE SUBMITTED

8. PREPARING ACTIVITY

a. Point of Contact Alan Barone	b. TELEPHONE Commercial 614-692-0510 DSN 850-0510 FAX 614-692-6939 EMAIL alan_barone@dscc.dla.mil
c. ADDRESS Defense Supply Center Columbus, ATTN: DSCC-VAC, 3990 East Broad Street, Columbus, OH 43213-1199	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Standardization Program Office (DLSC-LM) 8725 John J. Kingman, Suite 2533, Fort Belvoir, VA 22060-6221 Telephone (703) 767-6888 DSN 427-6888

DD Form 1426, Feb 1999 (EG) Previous editions are obsolete WHS/DIOR, Feb 99

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:06Z
Check the source to verify that this is the current version before use.