The documentation and process conversion measures necessary to comply with this document shall be completed by 9 November 2018.

INCH-POUND
MIL-PRF-19500/308E
9 August 2018
SUPERSEDING
MIL-PRF-19500/308D
15 October 2013

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, DIODE, SILICON, POWER RECTIFIER, FAST-RECOVERY
TYPES 1N3909, 1N3910, 1N3911, 1N3912, 1N3913, R AND A VERSIONS
JAN, JANTX, AND JANTXV

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

* 1.1 Scope. This specification covers the performance requirements for silicon, semiconductor fast recovery, power rectifier diodes. Three levels of product assurance (JAN, JANTX, and JANTXV) are provided for each device type as specified in MIL-PRF-19500.

* 1.2 Package outlines. The device package for the encapsulated device type are as follows: (DO-5) in accordance with figure1.

1.3 Maximum ratings.

Types	V_R	V_{RWM}	I_O 1/ T_C = 100°C	I_f (surge) at 1/120 s T_C = 100°C	t_{rr}	T_{STG}	T_{OP}
	V dc	V (pk)	A dc	A dc	ns	°C	°C
1N3909, R	50	50	30	300	200	-65	-65
1N3909A, AR	50	50	50	400	150	to +175	to +150
1N3910, R	100	100	30	300	200		
1N3910A, AR	100	100	50	400	150		
1N3911, R	200	200	30	300	200		
1N3911A, AR	200	200	50	400	150		
1N3912, R	300	300	30	300	200		
1N3912A, AR	300	300	50	400	150		
1N3913, R	400	400	30	300	200		
1N3913A, AR	400	400	50	400	150		

1/ Derate linearly, 2 percent of I_O per °C for T_C > 100°C.
Barometric pressure reduced (altitude operation): 8 mmHg.

1.4 Primary electrical characteristics. $R_{\theta JC}$ = 0.8°C/W maximum.

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@.dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

* 1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

* 1.5.1 JAN certification mark and quality level for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: “JAN”, “JANTX”, and "JANTXV".

* 1.5.2 Device type. The designation system for the device types of semiconductors covered by this specification sheet are as follows.

* 1.5.2.1 First number and first letter symbols. The semiconductors of this specification sheet use the first number and letter symbols "1N".

* 1.5.2.2 Second number symbols. The second number symbols for the semiconductors covered by this specification sheet are as follows: "3909", "3910", “3911”, “3912”, and "3913".

* 1.5.3 Suffix symbols. The following suffix letters are incorporated in the PIN in the order listed in the table as applicable:

R	Reversed (anode to stud) units shall be marked with an R following the last digit in the type number.
A	Indicates an I_f (surge) rating of 400 A dc.
AR	Indicates a reversed (anode to stud) I_f (surge) rating of 400 A dc.

2. APPLICABLE DOCUMENTS

* 2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in section 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

* 2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS


MIL-STD-750 - Test Methods for Semiconductor Devices.

* FED-STD-H28 Screw-Thread Standards

* (Copies of these documents are available online at http://quicksearch.dla.mil/.)

2.2 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this specification and the references cited herein, the text of this specification takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

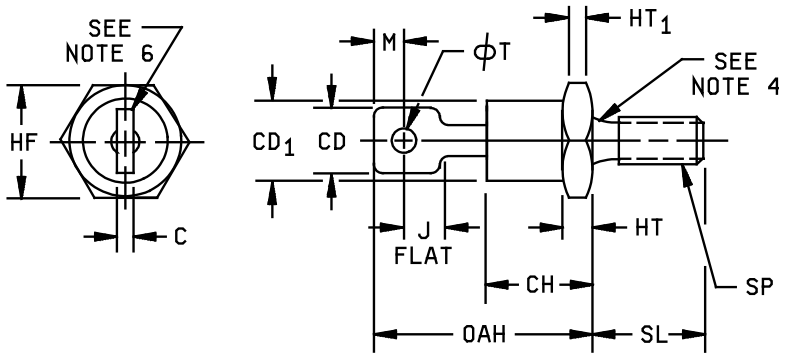

Ltr	Dimensions			
	Inches		Millimeters	
	Min	Max	Min	Max
C	0.030	0.080	0.76	2.03
CD	0.250	0.375	6.35	9.52
CD_1		0.667		16.94
CH		0.450		11.43
HF	0.669	0.688	16.99	17.48
HT	0.115	0.200	2.93	5.08
HT_1	0.060		1.53	
J	0.156		3.97	
M	0.030		0.77	
OAH	0.750	1.000	19.05	25.40
∅T	0.140	0.175	3.56	04.44
SL	0.422	0.453	10.72	11.50
SP	.250-28 UNF-2A THD NF optional		6.35-28 UNF-2A THD NF optional	

NOTES:
1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. Units must not be damaged by torque of 30 inch-pounds applied to 0.250-28 UF-2B nut assembled on thread.
4. Diameter of unthreaded portion 0.249 inch (6.32 mm) max and 0.220 inch (5.59 mm) minimum.
5. Complete threads to extend to within 2.5 threads of seating plane.
6. Angular orientation for this terminal is underlined, however the major surfaces over dimension CD shall be flat and the minimum distance from the hole to any point on the periphery shall be 0.030 inch (0.76 mm) outside dimension J.
7. Max pitch diameter of plated threads shall be basic pitch diameter 0.2268 inch (5.76 mm) reference FED-STD-H28.
8. (Screw Thread Standards for Federal Services.)
9. A chamfer or undercut on one or both ends of the hex portion is optional: Minimum bas diameter at seating plane. 0.600 inch (15.24 mm).
10. Reversed (anode to stud) units shall be marked with an R following the last digit in the type number.

FIGURE 1. Physical dimensions (DO-5).

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturers list before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.4 Interface requirements and physical dimensions. The Interface requirements and physical dimensions shall be as specified in MIL-PRF-19500 and figure 1 (DO-5) herein.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500. Where a choice of lead finish is desired, it shall be specified in the contract or purchase order (see 6.2).

3.4.2 Diode construction. These devices shall be constructed in a manner and using materials which enable the diodes to meet the applicable requirements of MIL-PRF-19500 and this document.

3.5 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I herein.

3.6 Electrical test requirements. The electrical test requirements shall be as specified in table I herein.

3.7 Marking. Marking shall be in accordance with MIL-PRF-19500. Manufacturer's identification and date code shall be marked on the devices. Initial container package marking shall be in accordance with MIL-PRF-19500.

3.7.1 Polarity. The polarity shall be indicated by a graphic symbol with the arrow pointing toward the negative end for forward bias. The reversed units shall also be marked with an R following the last digit in the type number.

3.8 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of Inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3)

c. Conformance inspection (see 4.4).

4.1.1 Sampling and inspection. Sampling and inspection shall be in accordance with MIL-PRF-19500 and herein, except lot accumulation period shall be 3 months in lieu of 6 weeks.

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not require the performance of table II tests, the tests specified in table II herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

* 4.3 Screening. Screening shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen	JANTX and JANTXV levels
3b 1/ 3c	Surge, see 4.3.1 Thermal impedance, see 4.3.2
4	Not applicable
9	V_{F2} and I_{R1} 2/
10	MIL-STD-750, method 1038, test condition A, t = 48 hours, T_A = +150°C (min)
11 3/	Subgroup 2 of table I herein V_{F2} and I_{R1}; ΔV_{F2} = ±0.1 v(pk); ΔI_{R1} = ±5 μA dc or 100 percent from the initial value, whichever is greater.
12	Not applicable
13	Not applicable

1/ Surge shall precede thermal impedance. These tests shall be performed anytime after screen 3 and before screen 9.
2/ I_{R1} measurement shall not be indicative of an open condition.
3/ PDA of screen 13 shall apply to screen 11.

4.3.1 Surge current. Surge current, see MIL-STD-750, method 4066. I_O = 0; $V_{RM}(w)$ = 0; Non-A version, $I_{F(surge)}$ = 400 A; A version, $I_{F(surge)}$ = 500 A; six surges; T_A = 25°C; t_p = 8.3 ms

* 4.3.2 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3101 of MIL-STD-750. The thermal response conditions and maximum thermal response limit shall be derived by each vendor. The chosen thermal response measurement and conditions for each device in the qualification lot shall be submitted in the qualification report and a thermal response curve shall be plotted. The chosen thermal response values shall be considered final after the manufacturer has had the opportunity to test five consecutive lots. Heating current (I_H) ≥ rated I_O; t_H = 150 to 400 ms; 50 mA ≤ I_M ≤ 250 mA.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500, and as specified herein.

* 4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500, and table I herein.

* 4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500 and 4.4.2.1 herein. Delta measurements shall be in accordance with table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

4.4.2.1 Group B inspection, table E-VIb (JAN, JANTX and JANTXV) of MIL-PRF-19500.

Subgroup	Method	Condition
B2	4066	Non-A version devices: T_C = 100°C; V_R = Rated V_{RM} (see 1.3), six surges. 1 surge per minute maximum. t_p = 8.3 ms. i_f (surge) = 300 A; I_O = 30 A dc
B2	4066	A version devices: T_C = 100°C; V_R = Rated V_{RM} (see 1.3), six surges. 1 surge per minute maximum. t_p = 8.3 ms. i_f (surge) = 400 A; I_O = 50 A dc
B3	1037	0.25 Rated $I_O \leq I_O$ applied $\leq$ Rated I_O (see 4.5.1) 2,000 cycles, $T_A \leq 35°C$. For irradiated devices, include t_{rr} as an end-point measurement.
B3	1038 or 1049	Condition A; 340 hrs.

* 4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VII of MIL-PRF-19500 and 4.4.3.1 herein. Delta measurements shall be in accordance with table III herein.

4.4.3.1 Group C inspection, table E-VII of MIL-PRF-19500.

Subgroup	Method	Condition
C2	2036	Test condition F, method B, Weight = 15 pounds, t = 15s.
C2	2036	Test condition D1, seal torque = 3 pound-inches, t = 15s.
C2	2036	Test condition D2, stud torque = 30 pound-inches, t = 15s.
C6	1037	0.25 Rated $I_O \leq I_O$ applied $\leq$ Rated I_O (see 4.5.1) 6,000 cycles. $T_A \leq 35°C$. For irradiated devices, include t_{rr} as an end-point measurement.

* 4.4.4 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-IX of MIL-PRF-19500. Delta measurements shall be in accordance with table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows:

4.5.1 DC intermittent operation life. A cycle shall consist of an “on” period, when power is applied suddenly, not gradually, to the device for the time necessary to achieve a delta case temperature of 85°C +15°C, -5°C followed by an “off” period, when the power is suddenly removed, for cooling. Auxiliary (forced) cooling is permitted during the “off” period only. The heating time is such that 30 s $\leq t_{heating} \leq$ 60 s. $P = V_F \times I_F$ or $P = V_{F(pk)} \times I_{av}$ if using sine wave current. DC full wave current (or equivalent half sine wave current) shall be used for the power required during the “on” period and equivalent half sine wave is permissible.

Within the time interval of 50 cycles before to 500 cycles after the termination of the test, the sample units shall be removed from the specified test conditions and allowed to reach room ambient conditions. Specified end-point measurements for qualification and quality conformance inspections shall be completed within 96 hours after removal of sample units from the specified test conditions. Additional readings may be taken at the discretion of the manufacturer.

4.5.2 Reverse recovery time. The reverse recovery time shall be measured in the circuit of figure 2 or equivalent. Care should be exercised to minimize stray inductances in the test circuit and to ensure the total resistance of the reverse current loop can be adjusted sufficiently low so that more than 2 amperes will flow if not blocked by the diode being tested. Switch SW shall be activated and the regulated voltage source adjusted to achieve the following characteristics of the waveform.

a. The di/dt shall be the specified value between the forward 0.5 ampere point and the reverse 0.2 ampere point.

b. The i_r(rec) shall be the maximum value obtainable, except when it exceeds 2 amperes.

The reverse-recovery time shall then be determined from the current waveform as shown on figure 3.

4.5.3 Pulse measurements. Conditions for pulse measurements shall be as specified in section 4 of MIL-STD-750.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

	Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
	Subgroup 1						
	Visual and mechanical inspection	2071					
	Subgroup 2						
*	Thermal impedance 3/	3101	See 4.3.2	$Z_{\theta JX}$			°C/W
*	Forward voltage	4011	Condition B, $t_P \leq 8.3$ ms, duty cycle ≤ 2 percent pulse; $i_f = 50$ A(pk)	V_{F2}		1.40	V (pk)
	Reverse current	4016	DC method, V_R = rated V_R (see 1.3)	I_{R1}	---	15	µA dc
	Subgroup 3						
	High temperature operation:		$T_C = 150°C$				
	Reverse current	4016	DC method, V_R = rated V_R (see 1.3)	I_{R2}	---	6.0	mA dc
	Subgroup 4						
	Reverse recovery time	4031	$I_F = 1$ A dc; $V_R = 30$ V dc; di/dt = -25 A/µs $i_r(rec) \leq 2$ A(pk) See 4.5.2 See figure 2 and figure 3				
	Non A-versions			t_{rr}	---	200	ns
	A-versions			t_{rr}	---	150	ns
	Subgroup 5						
*	Forward voltage	4011	Condition B, $I_F = I_{F(surge)}$, $t_p = 800$ µs	V_{F1}		2.75	V dc
*	Forward voltage	4011	Condition B, $I_F = I_{F(surge)}$ $t_p = 8.3$ ms	V_{F1}		2.55	V dc

1/ For sampling plan, see MIL-PRF-19500.

2/ V_{F1} shall be performed with either $t_p = 800$ µs or $t_p = 8.3$ ms.

* 3/ For end-point measurements, this test is required for the following subgroups:
Group B, subgroups 2 and 3 (JAN, JANTX, and JANTXV).
Group C, subgroup 2 and 6.
Group E, subgroup 1

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

* TABLE II. Group E inspection (all quality levels) for qualification and requalification only.

Inspection	MIL-STD-750		Sample plan
	Method	Conditions	
Subgroup 1			n = 45, c = 0
* Thermal Shock	1056	Condition B, 0°C to 100°C, 100 cycles.	
Hermetic seal	1071		
Electrical tests		See table I, subgroup 2	
Subgroup 2			n = 45, c = 0
HTRB	1038	Condition A; 1,000 hrs.	
Electrical end-points		See table I, subgroup 2	
Subgroup 4			
Thermal impedance curves		See MIL-PRF-19500, table E-IX, group E, subgroup 4.	
Subgroup 5			n = 22, c = 0
Barometric Pressure	1001	t = 60 s, While the test is being performed, I_R shall be monitored and shall not exceed group A limits. T_C = 25°C. 1N3912, 8 mmHg; V = 300 Vdc. 1N3913, 8 mmHg; V = 400 Vdc.	
Subgroup 6			
ESD	1020		

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.


* TABLE III. Groups A, B, C and E delta electrical end-point measurements. 2/ 3/ 4/

Step	Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
		Method	Conditions		Min	Max	
* 1.	Reverse current leakage	4016	DC method, V_R = rated V_R, (see 1.3), pulsed (see 4.5.3).	ΔIR	$\leq \pm 100$ percent of initial value or ± 50 nA, whichever is greater.		

1/ Devices which exceed the group A limits for this test shall be rejected.
2/ The delta electrical measurements for table E-VIb (JAN, JANTX and JANTXV) of MIL-PRF-195000 are as follows:
a. Subgroup 3, see table III herein, step 1.
3/ The delta electrical measurements for table E-VII of MIL-PRF-195000 are as follows:
a. Subgroup 2, see table III herein, step 1.
b. Subgroup 6, see table III herein, step 1.

4/ The delta electrical measurements for table E-IX of MIL-PRF-19500 are as follows:
a. Subgroup 1, see table III herein, step 1.
b. Subgroup 2, see table III herein, step 1.


Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

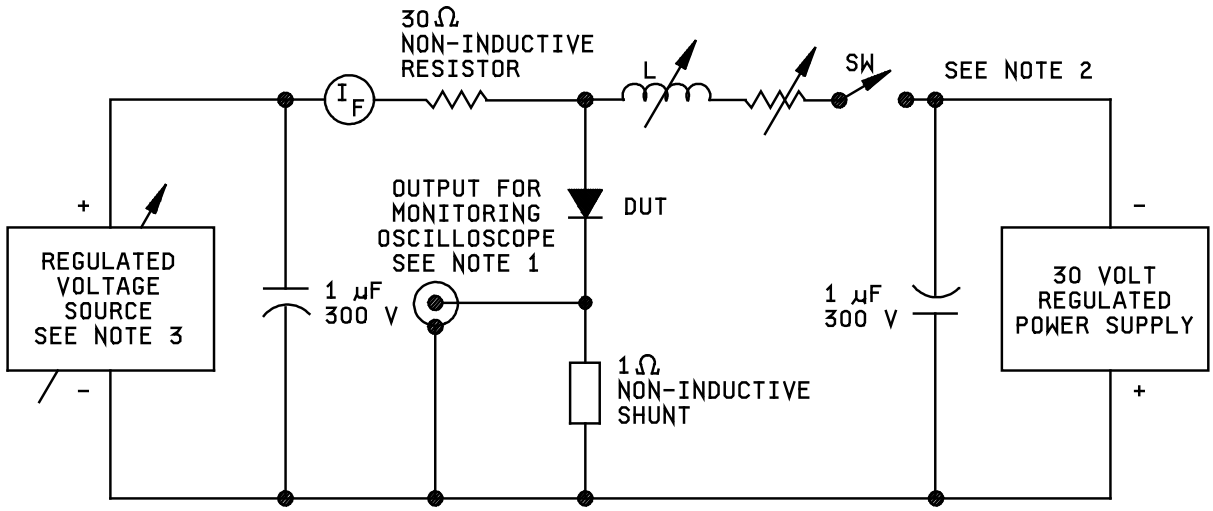

NOTES:

1. Monitoring oscilloscope requirements: $t_r \leq 14$ ns, $R_{in} \geq 9$ MΩ, $C_{in} \leq 12$ pF, L_{in} (series) ≤ 0.5 µH.
2. SW characteristics: Mercury-wetted make-before-break relay switched at a 60 Hz rate. The relay should conduct for approximately 640 µs and be open for approximately 7.7 ms. (C.P. Clare HGP 1004 or equivalent.)
3. Voltage source characteristics: Output impedance ≤ 0.5 Ω from 0 to 2 kHz.

FIGURE 2. Reverse recovery test circuit.

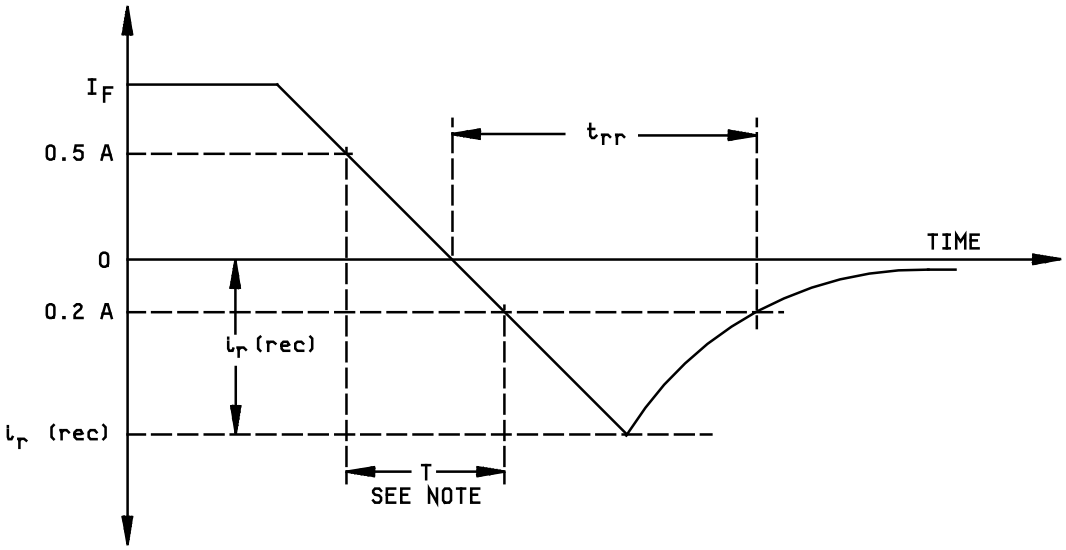

NOTE:

Adjust L and R in accordance with 4.5.2 to achieve T = 0.028 µs (L = 1.2 µH). Then $\frac{di}{dt} = \frac{-0.7}{.028} = \frac{-25A}{\mu s}$.

FIGURE 3. Reverse recovery current waveform through device under test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements should be as specified in the contract or order (see 6.2). When actual packaging of material is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Points' packaging activity within the Military Department or Defense Agency, or within the Military Departments' System Command. Packaging data retrieval is available from the managing Military Departments' or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Notes. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).


c. Lead finish (see 3.4.1).

* d. The complete Part or Identifying Number (PIN), see title and section 1

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturer's List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

* 6.4 PIN construction example.

* 6.4.1 Encapsulated devices The PINs for encapsulated devices are constructed using the following form.

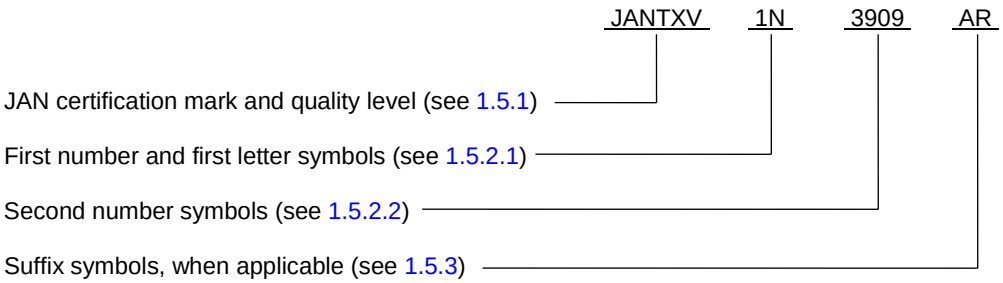

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.

* 6.5 List of PINs. The following is a list of possible PINs available on this specification sheet.

PINs for types 1N3909, 1N3910, 1N3911, 1N3912, 1N3913, R AND A VERSIONS.		
JAN1N3909 JAN1N3910 JAN1N3911 JAN1N3912 JAN1N3913	JANTX1N3909 JANTX1N3910 JANTX1N3911 JANTX1N3912 JANTX1N3913	JANTXV1N3909 JANTXV1N3910 JANTXV1N3911 JANTXV1N3912 JANTXV1N3913
JAN1N3909A JAN1N3910A JAN1N3911A JAN1N3912A JAN1N3913A	JANTX1N3909A JANTX1N3910A JANTX1N3911A JANTX1N3912A JANTX1N3913A	JANTXV1N3909A JANTXV1N3910A JANTXV1N3911A JANTXV1N3912A JANTXV1N3913A
JAN1N3909R JAN1N3910R JAN1N3911R JAN1N3912R JAN1N3913R	JANTX1N3909R JANTX1N3910R JANTX1N3911R JANTX1N3912R JANTX1N3913R	JANTXV1N3909R JANTXV1N3910R JANTXV1N3911R JANTXV1N3912R JANTXV1N3913R
JAN1N3909AR JAN1N3910AR JAN1N3911AR JAN1N3912AR JAN1N3913AR	JANTX1N3909AR JANTX1N3910AR JANTX1N3911AR JANTX1N3912AR JANTX1N3913AR	JANTXV1N3909AR JANTXV1N3910AR JANTXV1N3911AR JANTXV1N3912AR JANTXV1N3913AR

* 6.6 Changes from previous issue. The margins of this specification are marked with asterisks to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the previous issue.

Custodians:
Army - CR
Navy - EC
Air Force - 85
DLA - CC

Review activities:
Army - AR, MI, SM
Navy - AS, CG, MC, OS
Air Force - 19, 99

Preparing activity:
DLA - CC

(Project 5961-2018-073)

* NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T14:14Z
Check the source to verify that this is the current version before use.