MIL-H-28596B
14 October 1981
SUPERSEDING
MIL-H-28596A(NAVY)
3 August 1973,
and ZZ-H-541C
22 August 1967

MILITARY SPECIFICATION

HOSE AND HOSE ASSEMBLY, RUBBER, STEAM

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers braided or wrapped rubber hose for conveyance of saturated steam.

1.2 Classification.

1.2.1 Types and grades. Hose furnished under this specification shall be of the following types and grades, as specified (see 6.2).

Type I - Braided wire reinforced construction.

Grade A - Multiple braid reinforcement; for working pressure and temperatures up to 200 pounds per square inch gage (psig) and 388° Fahrenheit (F).
Grade B - Single braid reinforcement; for working pressures and temperatures up to 100 psig and 338°F.

Type II - Wrapped fabric construction; for working pressures and temperatures up to 75 psig and 320°F.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation, form a part of this specification to the extent specified herein.

SPECIFICATION

MILITARY

MIL-P-775 - Packaging of Hose, Hose Assemblies; Rubber, Plastic, Fabric, or Metal (Including Tubing): and Fittings, Nozzles, and Strainers.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commanding Officer (Code 156), Naval Construction Battalion Center, Port Hueneme, CA 93043, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 4720

Source: https://assist.dla.mil -- Downloaded: 20260-20T13:21Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FED STD H28 - Screw-Thread Standards for Federal Services.
FED STD No. 162 - Hose, Rubber, Visual Inspection Guide for.
FED STD No. 601 - Rubber, Sampling and Testing.

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of specifications, standards, handbooks, drawings, and publications required by manufacturers in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D380 - Testing Rubber Hose.
D412 - Tension Testing of Vulcanized Rubber.
D413 - Rubber Property - Adhesion to Flexible Substrate.
D518 - Rubber Deterioration - Surface Cracking.
D573 - Rubber Deterioration in Air Oven.
D1149 - Rubber Deterioration - Surface Ozone Cracking in a Chamber (Flat Specimens).

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), the contractor shall furnish a complete hose length or hose assembly for the first article inspection and approval (see 4.2.1 and 6.4).

3.2 Materials. Materials used shall be free from defects which would adversely affect the performance or maintainability of individual components or of the overall assembly. Materials not specified herein shall be of the same quality used for the intended purpose in commercial practice. Unless otherwise specified herein, all equipment, material, and articles incorporated in the work covered by this specification are to be new and fabricated using

Source: https://assist.dla.mil -- Downloaded: 20260-20T13:21Z
Check the source to verify that this is the current version before use.

materials produced from recovered materials to the maximum extent possible without jeopardizing the intended use. The term "recovered materials" means materials which have been collected or recovered from solid waste and reprocessed to become a source of raw materials, as opposed to virgin raw materials. None of the above shall be interpreted to mean that the use of used or rebuilt products are allowed under this specification unless otherwise specified.

3.2.1 Rubber. Rubber compounds, either natural or synthetic or combinations thereof used in the construction of the hose, shall be heat resistant. In addition, the cover shall be resistant both to abrasion and ozone cracking.

3.2.2 Wire reinforcement. Reinforcement wire shall be high-strength steel wire braid of a quality to withstand shock, vibration, and flexing. The wire shall be copperized or brass plated. Treatment may be applied to the wire to increase the adhesion to rubber, if necessary, to improve steam resistance.

3.2.3 Coupling components. Unless otherwise specified (see 6.2), all coupling components, except washers, and soft metal contact surface inserts, shall be cold-rolled steel bar stock, or malleable iron, and shall be protected with a corrosion-resisting coating.

3.3 Length. Unless otherwise specified (see 6.2), the hose shall be furnished in 50 foot lengths, ±1 percent, exclusive of the couplings.

3.4 Sizes. Hoses furnished under this specification shall be of the sizes listed in table I and as specified (see 6.2).

TABLE I. Physical requirements.

Size, inside diameter (inches)	1/2	3/4	1	1-1/4	1-1/2	2	2-1/2
Inside diameter tolerance (inch)							
Type I, grade A & B	+0.039	+0.039	+0.047	+0.063	+0.063	+0.063	+0.078
	-0.016	-0.016	-0.016	-0.016	-0.016	-0.016	-0.016
Type II	±0.031	±0.031	±0.031	±0.031	±0.031	±0.063	±0.063
Outside diameter							
Type I, grade A (see note 1)	-	-	-	-	-	-	-
Type I, grade B (see note 2)	1-1/16	1-11/32	1-19/32	-	-	-	-
Type II	1-3/16	1-1/2	1-7/8	2-1/8	2-3/8	3	-
Outside diameter tolerance (inch)							
Type I, grade A (see note 1)	-	-	-	-	-	-	-
Type I, grade B	±1/32	±1/32	±3/64	-	-	-	-
Type II	±1/16	±1/16	±1/16	±1/16	±1/16	±1/16	-
Thickness, minimum							
Tube							
Type I	0.125	0.125	0.125	0.125	0.125	0.125	0.125
Type II	0.125	0.125	0.125	0.125	0.125	0.125	-

Source: https://assist.dla.mil -- Downloaded: 202610-20T13:21Z
Check the source to verify that this is the currentversion before use.

3.4 Physical requirements - Continued.

Size, inside diameter (inches)	1/2	3/4	1	1-1/4	1-1/2	2	2-1/2
Cover							
Type I, grade A (see note 3)	0.065	0.065	0.065	0.065	0.065	0.065	0.065
Type I, grade B	0.060	0.060	0.060	-	-	-	-
Type II	0.063	0.063	0.063	0.063	0.063	0.063	-
Number of wire braids minimum							
Type I, grade A	2	2	2	2	2	2	2
Type I, grade B	1	1	1	-	-	-	-
Fabric plies, minimum (type II only)	4	4	5	5	5	6	-
Hydrostatic proof pressure minimum psi							
Type I, grade A	1250	1250	1250	1250	1250	1250	1250
Type I, grade B	900	900	900	-	-	-	-
Type II	400	400	400	350	350	300	-
Hydrostatic burst pressure minimum							
Type I, grade A	2000	2000	2000	2000	2000	2000	2000
Type I, grade B	1800	1800	1800	-	-	-	-
Type II	875	875	875	800	800	750	-
Maximum twist at proof pressure							
Type I only	One turn in each 50 foot length.						
Maximum change in length at proof pressure							
Type I only	± 4 percent						

Note 1 - Outside diameters of type I, grade A hose are optional, due to use of optional breaker plies, but shall be suitable for use with couplings of same nominal size of the hose.

Note 2 - Larger sizes than 1 inch inside diameter for type I, grade B hose are not considered structurally sound.

Note 3 - When a textile braid is used as a breaker ply in type I, grade A hose, it shall be considered a part of the cover for the purpose of thickness measurements.

3.5 Construction. The hose shall consist of a heat-resistant natural or synthetic rubber tube, plies of fabric or wire braid reinforcements embedded in rubber, and a heat-resistant, abrasion-resistant, and ozone-resistant rubber cover. The construction specified represents minimum requirements and is not intended to bar hose having improved properties which meet the requirements of this specification.

3.5.1 Adherence. For type I hose, the rubber between each layer of braid shall be homogeneously connected to the other layers and be thick enough to

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T13:21Z
Check the source to verify that this is the current version before use.

constitute a visible layer. For type II hose, the fabric shall be well frictioned with a rubber compound. The plies of frictioned fabric shall adhere to each other and, at the same time adhere to the inner tube and to the outer cover.

3.5.2 Carcass. The carcass, which shall consist of alternate layers of rubber and reinforcing material, shall meet the following minimum requirements for the type of hose specified.

3.5.2.1 Type I. Type I hose shall contain not less than the minimum number of wire braids specified in table I. Additional plies of wrapped or braided fabric shall be used, as necessary, to increase heat resistance and improve adherence.

3.5.2.2 Wire reinforcement. The wire reinforcement braid shall be of a size and tensile strength that will prevent rupture of the hose below the specified bursting pressure. The wire shall be evenly and firmly braided, and shall be applied in such a manner that the twist and the elongation or contraction of the hose under hydrostatic proof test pressure shall be no greater than the limits specified in Table I.

3.5.2.3 Type II. Type II hose shall contain not less than the minimum number of fabric plies specified in table I. Each ply shall be wrapped spirally, without sewing, on a bias of 45° with the edges lapped at least 1/2 inch.

3.5.3 Cover. The cover shall be of the perforated type and shall be made of a natural or synthetic rubber resistant to heat, ozone, and abrasion. The rubber shall not show signs of cracking, blistering, or flaking after the accelerated aging tests specified herein.

3.6 Couplings. When specified (see 6.2), the hose shall be fitted with couplings. The couplings shall be of the long shank, interlocking clamp type, having fingers or lugs on each half of the clamp to grip a collar on the stem to prevent the stem shank from being pulled forward in relation to the clamp. Each clamp half shall also interlock with the other half. The coupling shall consist of a stem with a serrated or grooved shank end, a raised continuous collar, and a two-part interlocking-type clamp with clamping bolts. Hose smaller then 1-inch inside diameter shall be provided with not less than two clamping bolts; all other couplings shall have four clamping bolts. Two male couplings or one female and one male coupling shall be provided.

3.6.1 Threads. Any piece of section of the coupling that is threaded shall have the threads in conformance with FED STD H28.

3.7 Physical requirements. The hose shall meet the minimum requirements specified in tables I, II, and III.

Source: https://assist.dla.mil -- Downloaded: 20260-20T13:21Z
Check the source to verify that this is the current version before use.

TABLE II. Rubber strength and adherence requirements for type I hose, grades A and B.

	Initial value	After oven aging	After steam exposure aging
Tensile strength, minimum			
Tube, psi	900	-	*50
Cover, psi	900	800	*50
Elongation, minimum			
Tube, percent	250	-	-
Cover, percent	250	200	-
Adhesion, minimum			
Cover to reinforcement, lb	12	10	-
Tube to reinforcement, lb	12	-	-

*Note - Minimum percent of initial value.

TABLE III. Rubber strength and adherence requirements for type II hose.

Size, inside diameter, (inches)	1/2	3/4	1	1-1/4	1-1/2	2
Tensile strength, minimum after steaming:						
Cover, psi	600	600	600	600	600	600
Tube, psi	550	550	550	550	550	550
The change from the tensile strength before steaming shall not exceed 40 percent.						
Ultimate elongation after steaming:						
Tube, percent	300	300	300	300	300	300
Cover, percent	200	200	200	200	200	200
The change from the elongation before steaming shall not exceed 40 percent.						
Adhesion (friction):						
Before steaming:						
Between plies of fabric minimum, lb	18	18	18	18	18	18
Between tube and fabric minimum, lb	15	15	15	15	15	15
Between cover and fabric, minimum, lb	15	15	15	15	15	15
After steaming:						
Between plies of fabric, minimum, lb	12	12	12	12	12	12
Between tube and fabric, minimum, lb	10	10	10	10	10	10
Between cover and fabric, minimum, lb	10	10	10	10	10	10

3.8 Ozone resistance. The rubber cover of the hose shall show no visible cracking under 7X magnification after testing in accordance with 4.6.5.

Source: https://assist.dla.mil -- Downloaded: 202610-20T13:21Z
Check the source to verify that this is the current version before use.

3.9 Steam resistance. When tested as specified in 4.6.4, the hose shall reveal no flaws, such as blistering, cracking of the cover, cracking, flaking, or pitting of the tube, and no delamination of body components, or cracks through the cover exposing reinforcement.

3.10 Identification marking. Each length of hose shall be marked in a color that contrasts with the color of the hose cover. Marking shall be accomplished either by in-laying a rubber or suitable material brand or by applying a suitable composition ink, bonding the marking onto the cover so that the marking cannot be removed except by mechanical means. The marking shall consist of the manufacturer's name or trademark, the quarter and year of manufacture, the working pressure, and the word "steam". An alternative method of marking may be by the application of a continuous embossed strip along the entire length, vulcanizing the hose and by the subsequent removal of the strip, leaving a continuous relief identification area. Identification shall be the manufacturer's name or trademark, the working pressure, and the word "steam" repeated at maximum intervals of 36 inches. When the marking is accomplished by this alternative method, no color contrast is required. Letters shall be at least 0.25 inch high.

3.10.1 Marking tag. A marking tag shall be wired near each end fitting (two tags per length of hose), advising users of all safety precautions to be followed in the use of the hose. The following shall be included on the tag:

(a) Hose clamps shall be checked for proper application and shall be retightened, as necessary, prior to being placed into service. Be sure that clamps are interlocked over the collar on the nipple and that each clamp half interlocks with the other.
(b) Hose clamps shall be tightened after the first several hours of steaming of the hose and periodically thereafter.
(c) The importance of taking up evenly on all bolts to prevent cocking of the hose clamp shall be emphasized.
(d) Other operational and maintenance suggestions considered necessary by the hose and end-fitting manufacturers.

3.11 Workmanship. The finished hose shall be uniform in thickness. The inner tube shall be free from pits, cracks, and blisters. The cover shall be free from pits, cracks, and blisters. Couplings shall be securely attached to hose ends. The quality of workmanship shall be such as to produce hose that is in accordance with the requirements of this specification and is so constructed as to insure proper functioning of all parts of the unit.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 202610-20T13:21Z
Check the source to verify that this is the current version before use.

4.2 Classification of inspection. Inspection requirements shall be classified as follows:

(a) First article inspection (see 4.2.1).
(b) Quality conformance inspection (see 4.2.2).

4.2.1 First article inspection. First article inspection shall be performed on one sample hose length when a first article sample is required (see 3.1, 6.2, and 6.4). This inspection shall include the examination of 4.5 and the tests of 4.6. The first article may be a standard production item from the contractor's current inventory provided the unit meets the requirements of this specification and is representative of the design, construction, and manufacturing technique applicable to the remaining units to be furnished under the contract.

4.2.2 Quality conformance inspection. Quality conformance inspection shall be performed on the sample hose lengths selected in accordance with 4.4. This inspection shall include the examination of 4.5, the tests of 4.6, and the packaging inspection of 4.7.

4.3 Inspection lot. All hose and hose assemblies of the same type and size offered to the Government at one time shall be considered a lot for the purpose of inspection.

4.4 Sampling. A random sample of hose lengths shall be selected from each lot in accordance with MIL-STD-105.

4.4.1 Sampling for examination. Examination of the hose shall be based on inspection level II and an Acceptable Quality Level (AQL) of 1.5 percent defective for major defects and 2.5 percent defective for minor defects.

4.4.2 Sampling for tests. Tests of the hose shall be based on inspection level S-3 with an AQL of 4.0 percent defective. A representative sample 3 feet in length shall be cut from lengths selected from each lot. If hose is ordered with couplings (see 3.6), the contractor shall re-attach couplings to the remaining length from which the 3 foot length was cut. After the couplings have been re-attached, the remaining length of the hose shall be used to conduct the hydrostatic proof pressure test specified in 4.6.1. When the remaining length has passed the hydrostatic proof test, it shall be accepted as a full length of hose.

4.5 Examination. Each of the sample hose lengths selected in accordance with 4.4.1 shall be visually and dimensionally examined to determine conformance with all the requirements of this specification not involving tests. The classification of defects in Fed. Std. No. 162 shall be used to determine and evaluate defects through visual inspection.

4.6 Tests. Sample hose sections selected in accordance with 4.4.2 shall be subjected to the applicable test specified in table IV and 4.6.1 through 4.6.7.

Source: https://assist.dla.mil -- Downloaded: 20260-20T13:21Z
Check the source to verify that this is the current version before use.

TABLE IV. Tests.

Test	Reference paragraph	Test Method No.
Hose length	4.6.6	2411 1/
Hose size, inside diameter	3.7	2221 1/
Thickness of tube and cover	3.7	2011 1/
Tensile strength and ultimate elongation	3.7	ASTM D412
Aging (type I only)	4.6.3	ASTM D573
Steam exposure	4.6.4	
Adhesion	4.6.7	ASTM D413
Proof pressure	4.6.1	ASTM D380
Burst pressure	4.6.2	ASTM D380
Ozone resistance	4.6.5	ASTM D1149
Maximum twist at proof pressure	3.7	ASTM D380

1/ Method in Fed Std Test Method No. 601.

4.6.1 Hydrostatic proof test, coupled assemblies. When hose is ordered with couplings, samples selected in accordance with 4.4.2 after couplings have been re-attached, shall be subjected to the hydrostatic proof test pressure specified in table I in accordance with ASTM D380. Water shall be used as the test media. Leakage or other evidence of defects shall be cause for rejection.

4.6.2 Burst test. Hose samples selected in accordance with 4.4.2 shall be subjected to the hydrostatic straight bursting test of ASTM D380. Water shall be used as the test media. Failure of the hose at a pressure below the minimum burst pressure specified in table I shall be cause for rejection of the lot.

4.6.3 Accelerated aging test. Hose samples selected in accordance with 4.4.2 shall be subjected to accelerated aging in accordance with ASTM D573, except that the time for aging shall be 36 hours at a temperature of 248°F. After aging, the tensile strength and the ultimate elongation shall be not less than the values specified in table II. The die for cutting the specimen shall be die F of ASTM D412.

4.6.4 Steam resistance test. A 3-foot hose length sample selected in accordance with 4.4.2 shall be used for the following steam test:

(a) The outer surface of the hose shall be visually examined for imperfections. The inner surface of the hose shall be examined for surface imperfections by use of a source of light which shall be held at one end while the hose is looked through from the other end. The condition of the tube surface shall be recorded.
(b) Clamp test hose horizontally between two steam manifolds similar to the manifolds shown in Figure 1, and subject it to steam at the pressure and temperature specified in table V for periods of 24 hours, until a total time of 168 hours has elapsed.
(c) At the end of each steaming period (not more than 24 hours), the pressure shall be released in order that pressure be returned to atmospheric conditions within a time of 1 minute or less. Care shall be taken to insure that condensation will not be drained from the hose. The hose shall remain at atmospheric conditions

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T13:21Z
Check the source to verify that this is the current version before use.

for at least 30 minutes, after which the steam pressure shall again be raised and held another 24 hours during the steaming period. The above cycle shall be repeated until the hose has been subjected to 168 hours of steam pressure.

(d) Upon completion of 168 hours of steaming, the hose shall be removed from the test apparatus and the outer and inner tube surfaces shall be examined (see 4.6.4(a)) for signs of damage. Except for indentation resulting from clamping, any flaking, peeling, blistering, or cracking of the cover or tube shall be cause for rejection.

(e) If the hose passes the above visual examination, the hose shall be cooled to 70° ±5°F. The hose shall then be bent in a 180° arc around a 20-inch mandrel (see Figure 2) and the outer cover examined for any signs of cracking.

TABLE V. Steam pressure and temperature for exposure.

Hose type/grade	steam pressure (psi)	Temperature °F
Type I, grade A	200	388
Type I, grade B	100	338
Type II	75	320

4.6.5 Resistance to ozone. The sample of cover stock shall be tested for ozone resistance in accordance with procedure B of ASTM D518 and D1149, except that after conditioning for 24 hours in an ozone-free atmosphere the looped sample shall be exposed for 72 hours at 104°F ±2°F to an atmosphere containing 50 parts per hundred million of ozone.

4.6.6 Hose length measurement. Each hose selected in accordance with 4.4.2 shall be measured for length in accordance with method 2411 of Fed. Std. Test Method No. 601.

4.6.7 Adhesion. The adhesion of the tube and cover to the reinforcement, and of the plies of reinforcement to each other, shall be determined in accordance with ASTM D413, with ring specimens, using either the static-mass or machine method.

4.7 Packaging inspection. The preservation, packing, and marking of the hose shall be inspected to verify conformance to the requirements of Section 5 of this specification.

5. PACKAGING

5.1 Preservation-packaging, packing, and marking. The hose shall be preserved, packaged, packed, and marked in accordance with MIL-P-775 with the level of preservation-packaging and level of packing as specified (see 6.2).

6. NOTES

6.1 Intended use. Hose and hose assembly covered by this specification are intended for general steam applications and not to convey steam into food service equipment.

Source: https://assist.dla.mil -- Downloaded: 20261O-20T13:21Z
Check the source to verify that this is the current version before use.

6.1.1 Type I. Type I hose shall be suitable for heavy-duty, high-pressure, shock-resistant, flexible applications.

6.1.2 Type II. Type II hose shall be suitable for general service as a steam hose for working pressures up to 75 psig.

6.2 Ordering data. Acquisition documents shall specify the following:

(a) Title, number, and date of this specification.
(b) Type and grade of hose required (see 1.2.1).
(c) If first article is required for inspection and approval (see 3.1, 4.2.1, and 6.4).
(d) When couplings are required, type of couplings, and material if different (see 3.2.3 and 3.6).
(e) Length and size of hose required (see 3.3 and 3.4).
(f) Level of preservation-packaging and level of packing required (see 5.1)

6.3 Contract data requirements. When this specification is used in an acquisition which incorporates a DD Form 1423 and invokes the provisions of paragraph 7-104.9(n) of the Defense Acquisition Regulations (DAR), the data requirements will be developed as specified by an approved Data Item Description (DD Form 1664) and delivered in accordance with the Contract Data Requirements List (DD Form 1423) incorporated into the contract. When the provisions of DAR 7-104.9(n) are not invoked, the data shall be delivered in accordance with the contract requirements.

6.4 First article. When a first article is required, it shall be tested and approved under the appropriate provisions of paragraph 7-104.55 of the DAR. The first article should be a first production item consisting of one complete hose assembly or it may be a standard production item from the contractor's current inventory as specified in 4.2.1. The contracting officer should include specific instructions in all acquisition instruments regarding arrangement for examination, tests, and approval of the first article.

6.5 Definitive specification part number. The specification part number is a definitive part number which will be formulated to identify each item covered by this specification. The part number will be formulated by selecting from the requirement options available in this specification as follows:

Hose assembly

Definitive Military Specification Part Number	M28596	X	X	X	XX
Military Specification Number					
Hose Type/Grade Code Number (see 6.5.1)					
Hose Assembly Coupling Code Letter (see 6.5.2)					
Hose Size Code Number (see 6.5.3).					
Length in Feet					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T13:21Z
Check the source to verify that this is the current version before use.

Hose

Definitive Military Specification Part Number	M28596	X	X	XX
Military Specification Number				
Hose Type/Grade Code Number (see 6.5.1)				
Hose Size Code Number (see 6 5 3)				
Length in Feet				

6.5.1 Hose type/grade. Hose type and hose grade are designated by a one digit code number (see table VI).

TABLE VI. Hose type/grade code number.

Hose type/grade Code number	1	2	3
Hose type/grade	Type I Grade A	Type I Grade B	Type II

6.5.2 Hose assembly coupling. Hose coupling type for each end is designated by one code letter (see table VII).

TABLE VII. Hose assembly coupling code letter.

Hose assembly coupling code letter	Hose coupling type 1st end	2nd end
A	Male	Female
B	Male	Male

6.5.3 Hose size. Hose size is designated by a one digit code number (see table VIII).

TABLE VIII. Hose size code number.

Hose size Code number	1	2	3	4	5	6	7
Hose inside diameter inches	1/2	3/4	1	1-1/4	1-1/2	2	2-1/2

6.6 Cross-reference of classifications. The following hoses were previously classified as indicated:

New	Old
MIL-H-28596B Type I, grade A	MIL-H-28596A(NAVY)
MIL-H-28596B Type I, grade A	ZZ-H-541C Type I, grade A
Type I, grade B	Type I, grade B
Type II	Type II

6.7 Supersession data. This specification includes the requirements of ZZ-H-541C, dated August 22, 1967.

Source: https://assist.dla.mil -- Downloaded: 202640-20T13:21Z
Check the source to verify that this is the current version before use.

6.8 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue, due to the extensiveness of the changes.

Custodians:

Army - ME
Navy - YD
Air Force - 99

Review activities:

Navy - SH
DLA - CS

User activities:

Army - CE
Navy - OG

Preparing activity:

Navy - YD

Project No. 4720-N409

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T13:21Z
Check the source to verify that this is the current version before use.

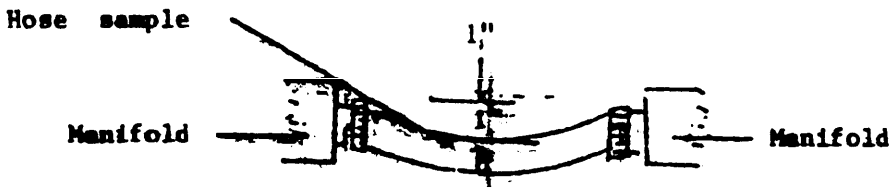


FIGURE 1. Horizontal steam rack.

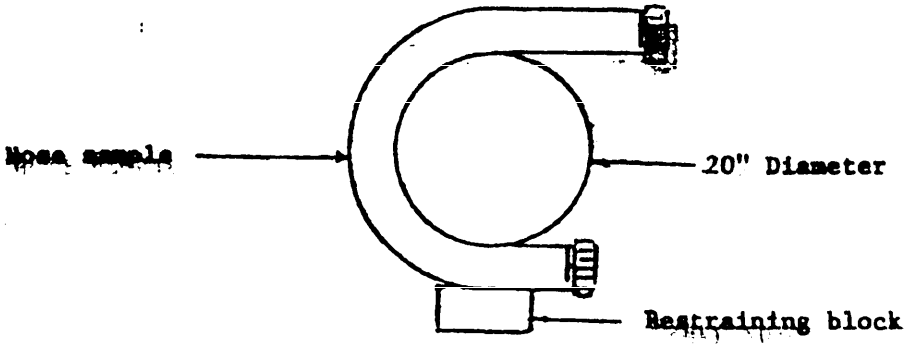


FIGURE 2. 180° bend.

Source: https://assist.dla.mil -- Downloaded: 20260-20T13:21Z
Check the source to verify that this is the current version before use.