The documentation and process conversion measures necessary to comply with this document shall be completed by 31 August 2023.

INCH-POUND

MIL-PRF-19500/395L
w/AMENDMENT 3
31 May 2023
SUPERSEDING
MIL-PRF-19500/395L
w/AMENDMENT 2
28 February 2019

PERFORMANCE SPECIFICATION SHEET

# TRANSISTOR, NPN, SILICON, SWITCHING, ENCAPSULATED (THROUGH-HOLE AND SURFACE MOUNT) TYPES 2N3735 AND 2N3737 QUALITY LEVELS JAN, JANTX, JANTXV, JANS, JANHC, JANKC

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

## 1. SCOPE

1.1 Scope. This specification covers the performance requirements for NPN, silicon, switching transistors. Four levels of product assurance (JAN, JANTX, JANTXV and JANS) are provided for each device type as specified in MIL-PRF-19500. RHA level designators "M", "D", "P", "L", "R", "F", "G" and "H" are appended to the device prefix to identify devices, which have passed RHA requirements.

1.2 Physical dimensions. See figure 1 (TO-39 and TO-5), figure 2 (TO-46), and figure 3 (2N3737UB). The dimensions and topography for JANHC and JANKC unencapsulated die is as follows: The A version die in accordance with figure 4.

1.3 Maximum ratings. Unless otherwise specified, $T_C$ = +25°C.

| Types | $P_T$ $T_A$ = +25°C | $P_T$ $T_C$ =+25°C | $P_T$ $T_{SP}$ =+25°C | $R_{\theta JA}$ | $R_{\theta JC}$ | $R_{\theta JSP}$ | $T_J$ and $T_{STG}$ |
|---|---|---|---|---|---|---|---|
| | W | W | W | °C/W | °C/W | °C/mW | °C |
| 2N3735, 2N3735L | 1.0 (1) | 2.9 (2) | N/A | 175 | 60 | N/A | -65 to +200 |
| 2N3737 | 0.5 (3) | 1.9 (4) | N/A | 350 | 88 | N/A | -65 to +200 |
| 2N3737UB | 0.5 (5) | N/A | 1.9 (4) | 325 (6) | N/A | 88 (6) | -65 to +200 |

| Types | $V_{CBO}$ | $V_{CEO}$ | $V_{EBO}$ | $I_C$ |
|---|---|---|---|---|
| | V dc | V dc | V dc | A dc |
| 2N3735, 2N3735L, 2N3737, 2N3737UB | 75 | 40 | 5 | 1.5 |

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, ATTN: VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A

FSC 5961

* DISTRIBUTION STATEMENT A. Approved for public release. Distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

1.3 Maximum ratings. Unless otherwise specified, $T_C$ = +25°C. Continued.

(1) Derate linearly at 5.71 mW/°C above $T_A$ = +25°C.
(2) Derate linearly at 16.6 mW/°C above $T_C$ = +25°C.
(3) Derate linearly at 2.86 mW/°C above $T_A$ = +25°C.
(4) Derate linearly at 11.3 mW/°C above $T_C$ = +32.8°C.
(5) Derate linearly at 3.07 mW/°C above $T_A$ = +37.5°C.
(6) $T_A$ = +55°C for UB on printed circuit board (PCB), PCB = FR4 .0625 inch (1.59 mm) 1 - layer 1 Oz Cu, horizontal, still air, pads (UB) = .034 inch (0.86 mm) x .048 inch (1.22 mm), $R_{\theta JA}$ with a defined thermal resistance condition included is measured at $P_T$ = 500 mW.

1.4 Primary electrical characteristics.

| Limits | $h_{FE3}$ (1) | $\|h_{fe}\|$ | $V_{CE(sat)}$ | $C_{obo}$ | Pulse response | | |
|---|---|---|---|---|---|---|---|
| | $V_{CE}$ = 1.0 V dc<br>$I_C$ = 0.5 A dc | $V_{CE}$ = 10 V dc<br>$I_C$ = 50 mA dc<br>f = 100 MHz | $I_C$ = 500 mA dc<br>$I_B$ = 50 mA dc | $V_{CB}$ = 10 V dc<br>$I_E$ = 0<br>100 kHz ≤ f ≤ 1 MHz | $t_d$ | $t_r$ | $t_{off}$ |
| | | | V dc | pF | ns | ns | ns |
| Min | 40 | 2.5 | | | | | |
| Max | 140 | 6.0 | 0.5 | 9 | 8.0 | 40 | 60 |

(1) Pulsed (see 4.5.1).

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

1.5.1 JAN certification mark and quality level designators.

1.5.1.1 Quality level designators for encapsulated devices. The quality level designators for encapsulated devices that are applicable for this specification sheet from the lowest to the highest level are as follows: "JAN", "JANTX", "JANTXV", and "JANS".

1.5.1.2 Quality level designators for unencapsulated devices (die). The quality level designators for unencapsulated devices (die) that are applicable for this specification sheet from the lowest to the highest level are as follows: "JANHC" and "JANKC".

1.5.2 Radiation hardness assurance (RHA) designator. The RHA levels that are applicable for this specification sheet from lowest to highest for JANS quality levels are as follows: "M", "D", "P", "L", "R", "F", "G", and "H". The RHA levels that are applicable for this specification sheet from lowest to highest for JANTXV quality levels are as follows: "R" and "F".

1.5.3 Device type. The designation system for the device types of transistors covered by this specification sheet are as follows.

1.5.3.1 First number and first letter symbols. The transistors of this specification sheet use the first number and letter symbols "2N".

1.5.3.2 Second number symbols. The second number symbols for the transistors covered by this specification sheet are as follows: "3735" and "3737".



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

1.5.4 Suffix symbols. The following suffix letters are incorporated in the PIN for this specification sheet.

| | |
|---|---|
| | A blank second suffix symbol indicates a through-hole mount package TO-39 metal can (2N3735) (see figure 1), or a through-hole mount package TO-46 metal can (2N3737) (see figure 2). |
| L | Indicates a through-hole mount package TO-5 metal can with longer lead lengths than blank second suffix symbol device (2N3735L) (see figure 1). |
| UB | Indicates a 4 pad surface mount package. The metal lid is connected to pad 4 (2N3737UB) (see figure 3). |

1.5.5 Lead finish. The lead finishes applicable to this specification sheet are listed on QPDSIS-19500. The lead finish designator shall be separated from the main PIN by a dash.

1.5.6 Die identifiers for unencapsulated devices (manufacturers and critical interface identifiers). The manufacturer die identifier applicable for this specification sheet are "A".

* 1.6 Radiation features. The following radiation features are applicable for RHA devices supplied to this specification sheet.

* 1.6.1 Maximum total ionizing dose (TID). The maximum TID that RHA devices were tested to in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750 are as follows:

For device type 2N3735, 2N3737, and 2N3737UB: ..... 300 krads(Si) 1/

* 1/ The manufacturers supplying these device types have performed characterization testing in accordance with condition A (dose rate = 50 to 300 rad(Si)/s) of method 1019 of MIL-STD-750. The radiation end point limits are guaranteed only to a maximum TID level of 300 krads(Si).

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Copies of these documents are available online at https://quicksearch.dla.mil.

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

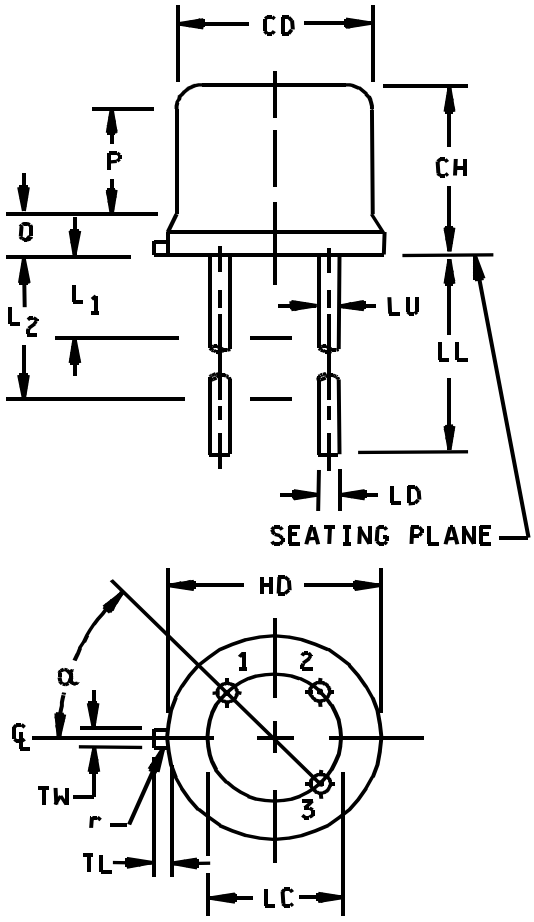



FIGURE 1. Physical dimensions TO-39, TO-5.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

2N3735 Dimensions, TO-39

| Symbol | Dimensions | | | | Notes |
|---|---|---|---|---|---|
| | Inches | Inches | mm | mm | |
| | Min | Max | Min | Max | |
| CD | .305 | .355 | 7.75 | 9.02 | |
| CH | .240 | .260 | 6.10 | 6.60 | |
| HD | .355 | .370 | 9.02 | 9.40 | |
| LC | .200 TP | | 5.08 TP | | 6 |
| LD | .016 | .021 | 0.41 | 0.53 | 7 |
| LL | .500 | .750 | 12.70 | 19.05 | 7 |
| LU | .016 | .019 | 0.41 | 0.48 | 7 |
| $L_1$ | | .050 | | 1.27 | 7 |
| $L_2$ | .250 | | 6.35 | | 7 |
| P | .100 | | 2.54 | | |
| TL | .029 | .045 | 0.74 | 1.14 | 3 |
| TW | .028 | .034 | 0.71 | 0.86 | 9 |
| Q | | .040 | | 1.02 | 4 |
| r | | .010 | | 0.25 | 10 |
| $\alpha$ | 45° TP | | 45° TP | | 6 |

2N3735L Dimensions, TO-5

| Symbol | Dimensions | | | | Notes |
|---|---|---|---|---|---|
| | Inches | Inches | mm | mm | |
| | Min | Max | Min | Max | |
| CD | .305 | .355 | 7.75 | 9.02 | |
| CH | .240 | .260 | 6.10 | 6.60 | |
| HD | .355 | .370 | 9.02 | 9.40 | |
| LC | .200 TP | | 5.08 TP | | 6 |
| LD | .016 | .021 | 0.41 | 0.53 | 7 |
| LL | 1.500 | 1.750 | 38.10 | 44.45 | 7 |
| LU | .016 | .019 | 0.41 | 0.48 | 7 |
| $L_1$ | | .050 | | 1.27 | 7 |
| $L_2$ | .250 | | 6.35 | | 7 |
| P | .100 | | 2.54 | | |
| TL | .029 | .045 | 0.74 | 1.14 | 3 |
| TW | .028 | .034 | 0.71 | 0.86 | 9 |
| Q | | .040 | | 1.02 | 4 |
| r | | .010 | | 0.25 | 10 |
| $\alpha$ | 45° TP | | 45° TP | | 6 |

FIGURE 1. Physical dimensions (TO-39, TO-5) - Continued.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.


NOTES:
1. Dimensions are in inches. Lead 1 is emitter, lead 2 is base, and lead 3 is collector.
2. Millimeters are given for general information only.
3. Symbol TL is measured from HD maximum.
4. Details of outline in this zone are optional.
5. Symbol CD shall not vary more than .010 inch (0.25 mm) in zone P. This zone is controlled for automatic handling.
6. Leads at gauge plane .054 inch (1.37 mm) +.001 inch (0.03 mm) -.000 inch (0.00 mm) below seating plane shall be within .007 inch (0.18 mm) radius of TP relative to tab. Device may be measured by direct methods or by gauge.
7. Symbol LU applies between $L_1$ and $L_2$. Dimension LD applies between $L_2$ and LL minimum.
8. Lead number three is electrically connected to case.
9. Beyond r maximum, TW shall be held for a minimum length of .011 inch (0.28 mm).
10. Symbol r applied to both inside corners of tab.

* FIGURE 1. Physical dimensions (TO-39, TO-5) - Continued.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

| Ltr. | Dimensions | | | | Notes |
|---|---|---|---|---|---|
| | Inches | Inches | mm | mm | |
| | Min | Max | Min | Max | |
| CD | .178 | .195 | 4.52 | 4.95 | |
| CH | .065 | .085 | 1.65 | 2.16 | |
| HD | .209 | .230 | 5.31 | 5.84 | |
| LC | .100 TP | | 2.54 TP | | 5 |
| LD | .016 | .021 | 0.41 | 0.53 | |
| LL | .500 | 1.750 | 12.70 | 44.45 | 6 |
| LU | .016 | .019 | 0.41 | 0.48 | 6 |
| $L_1$ | | .050 | | 1.27 | 6 |
| $L_2$ | .250 | | 6.35 | | 6 |
| Q | | .040 | | 1.02 | 3 |
| TL | .028 | .048 | 0.71 | 1.22 | 8 |
| TW | .036 | .046 | 0.91 | 1.17 | 4 |
| r | | .010 | | 0.25 | 9 |
| α | 45° TP | | 45° TP | | 5 |

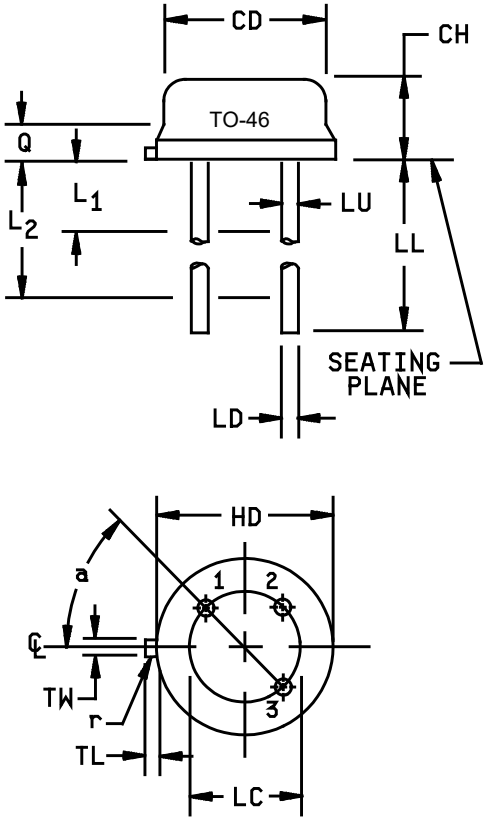



NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Symbol TL is measured from HD maximum.
4. Details of outline in this zone are optional.
5. Leads at gauge plane .054 inch (1.37 mm) +.001 inch (0.03 mm) -.000 inch (0.00 mm) below seating plane shall be within .007 inch (0.18 mm) radius of TP relative to tab. Device may be measured by direct methods or by gauge.
6. Symbol LU applies between $L_1$ and $L_2$. Dimension LD applies between $L_2$ and LL minimum.
7. Lead number three is electrically connected to case.
8. Beyond r maximum, TW shall be held for a minimum length of .011 inch (0.28 mm).
9. Symbol r applied to both inside corners of tab.
* 10. Lead 1 is emitter, lead 2 is base, and lead 3 is collector.

FIGURE 2. Physical dimensions - TO-46 2N3737.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

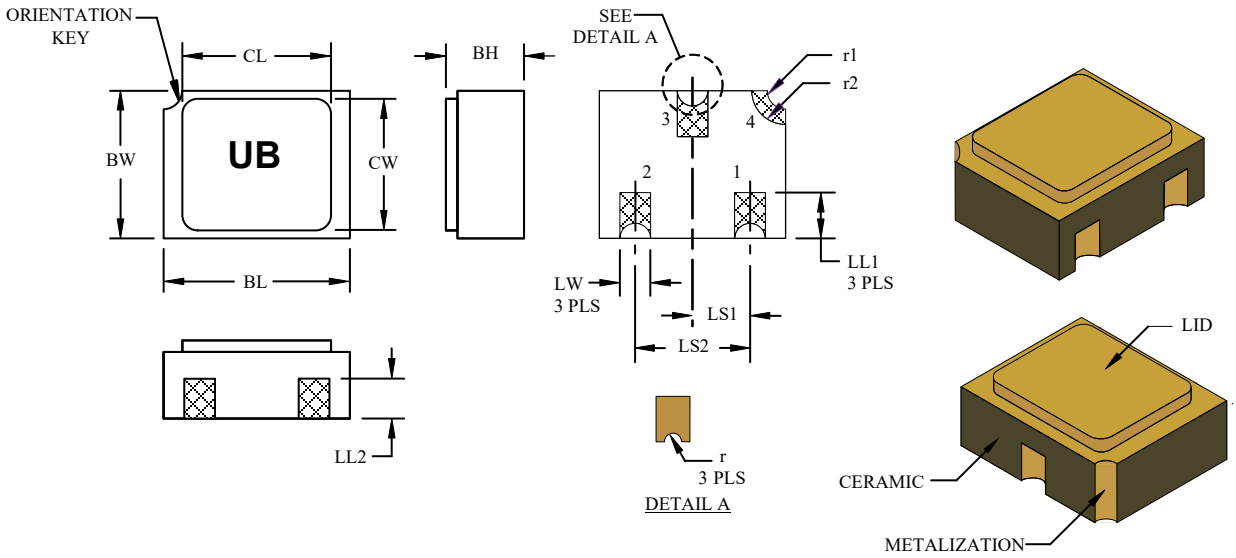



| Symbol | Dimensions | | | | Note |
|---|---|---|---|---|---|
| | Inches | Inches | mm | mm | |
| | Min | Max | Min | Max | |
| BH | .046 | .056 | 1.17 | 1.42 | |
| BL | .115 | .128 | 2.92 | 3.25 | |
| BW | .085 | .108 | 2.16 | 2.74 | |
| CL | | .128 | | 3.25 | |
| CW | | .108 | | 2.74 | |
| LL1 | .022 | .038 | 0.56 | 0.96 | |
| LL2 | .017 | .035 | 0.43 | 0.89 | |
| $LS_1$ | .036 | .040 | 0.91 | 1.02 | |
| $LS_2$ | .071 | .079 | 1.81 | 2.01 | |
| LW | .016 | .024 | 0.41 | 0.61 | |
| r | | .008 | | .203 | |
| r1 | | .012 | | .305 | |
| r2 | | .022 | | .559 | |

NOTES:
1. Dimensions are in inches.
2. Millimeters are given for general information only.
3. Hatched areas on package denote metallized areas.
4. Lid material: Kovar.
5. Pad 1 = Base, Pad 2 = Emitter, Pad 3 = Collector, Pad 4 = Shielding connected to the lid.

FIGURE 3. Physical dimensions for 2N3737UB, surface mount.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

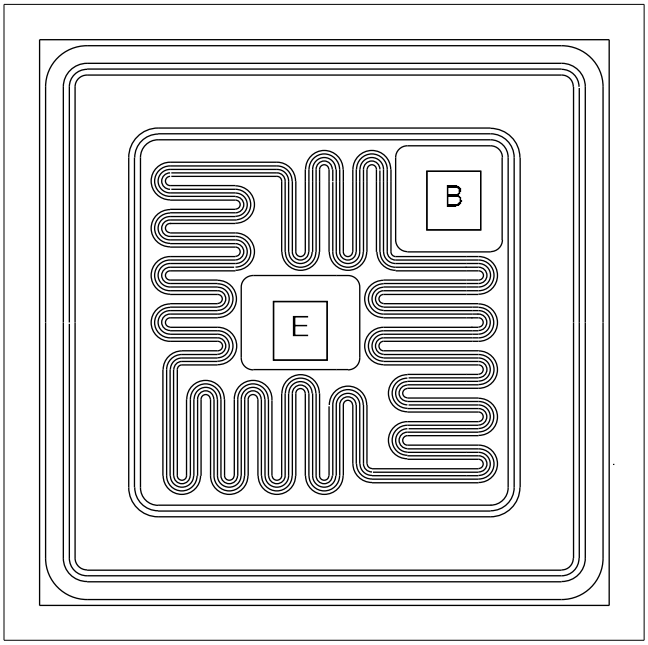


NOTES:
1. Chip size: .027 x .027 inch ±.002 inch ( 0.686 mm x 0.686 mm ±0.051 mm).
2. Chip thickness .008 ±.0015 inch (0.203 mm ±0.038 mm).
3. Top metal: Aluminum, 22,000 Å minimum, 24,500 Å nominal for JANHC and JANKC.
* 4. Back metal: Gold 4,000 Å minimum, 5,000 Å nominal for JANHC and JANKC.
* 5. Glassivation: Silox 5,000 Å minimum, 6,000 Å nominal for JANHC and JANKC.
6. Backside: Collector.
7. Bonding pad: B = .0045 x .0045 inch (0.114 mm x 0.114 mm).
   E = .004 x .005 inch (0.102 mm x 0.127 mm).

FIGURE 4. Physical dimensions for JANHC and JANKC (A-version) die dimensions.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturer's list (QML) before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

3.4 Interface and physical dimensions. Interface and physical dimensions shall be as specified in MIL-PRF-19500, and on figure 1 (TO-39, TO-5), figure 2 (TO-46), figure 3 (UB), and figure 4 (JANHC and JANKC version A) herein.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2).

3.5 Radiation hardness assurance (RHA). Radiation hardness assurance requirements and test levels shall be as defined in MIL-PRF-19500.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be as specified in table I.

3.8 Marking. Marking shall be in accordance with MIL-PRF-19500, except for the UB suffix package. Marking on the UB package shall consist of an abbreviated part number, the date code, and the manufacturers symbol or logo. The prefixes JAN, JANTX, JANTXV, and JANS can be abbreviated as J, JX, JV, and JS respectively. The "2N" prefix and the "UB" suffix can also be omitted. The radiation hardened designator M, D, P, L, R, F, G, or H shall immediately precede (or replace) the device "2N" identifier (depending upon degree of abbreviation required).

3.9 Workmanship. Switching transistor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4 and table I, table II, table III and table IV).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table IV tests, the tests specified in table IV herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANTX, JANTXV and JANS levels only). Screening shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

| Screen | Measurements for JANS level | Measurements for JANTX and JANTXV levels |
|---|---|---|
| (1) 3c | Thermal impedance, method 3131 of MIL-STD-750 (see 4.3.2). | Thermal impedance, method 3131 of MIL-STD-750 (see 4.3.2). |
| 9 | $I_{CBO2}$ and $h_{FE3}$. | Not applicable. |
| 11 | $I_{CBO2}$; $h_{FE3}$;<br>$\Delta I_{CBO2}$ = 100 percent or 25 nA dc, whichever is greater;<br>$\Delta h_{FE3}$ = ±15 percent of initial value. | $I_{CBO2}$ and $h_{FE3}$. |
| 12 | See 4.3.1. | See 4.3.1. |
| 13 | Subgroups 2 and 3 of table I herein;<br>$I_{CBO2}$ = 100 percent or 25 nA dc, whichever is greater;<br>$\Delta h_{FE3}$ = ±15 percent of initial value. | Subgroup 2 of table I herein;<br>$\Delta I_{CBO2}$ = 100 percent or 25 nA dc, whichever is greater;<br>$\Delta h_{FE3}$ = ±15 percent of initial value. |

(1) Shall be performed anytime after temperature cycling, screen 3a; and does not need to be repeated in screening requirements for JANTX and JANTXV.

4.3.1 Power burn-in conditions. Power burn-in conditions are as follows: $V_{CB}$ = 10 - 30 V dc. Power shall be applied to achieve $T_J$ = +135°C minimum using a minimum $P_D$ = 75 percent of $P_T$ maximum, $T_A$ ambient rated as defined in 1.3. NOTE: No heat sink or forced air cooling on the devices shall be permitted. With approval of the qualifying activity and preparing activity, alternate burn-in criteria (hours, bias conditions, $T_J$, and mounting conditions) may be used for JANTX and JANTXV quality levels. A justification demonstrating equivalence is required. In addition, the manufacturing site's burn-in data and performance history will be essential criteria for burn-in modification approval.

4.3.2 Thermal impedance. The thermal impedance measurements shall be performed in accordance with method 3131 of MIL-STD-750 using the guidelines in that method for determining $I_M$, $I_H$, $t_H$, $t_{SW}$ (and $V_H$ where appropriate). The thermal impedance limit used in screen 3c and table I, subgroup 2 shall be set statistically by the supplier. See table IV, group E, subgroup 4 herein.

4.3.3 Screening (JANHC and JANKC). Screening of JANHC and JANKC die shall be in accordance with MIL-PRF-19500 Discrete Semiconductor Die/Chip Lot Acceptance". Burn-in duration for the JANKC level follows JANS requirements; the JANHC follows JANTX requirements.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500, and as specified herein. If alternate screening is being performed in accordance with MIL-PRF-19500, a sample of screened devices shall be submitted to and pass the requirements of subgroups 1 and 2 of table I herein, inspection only (table E-VIB of MIL-PRF-19500, group B, subgroup 1 is not required to be performed since solderability and resistance to solvents testing is performed in table I herein).

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500, and table I herein.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VIA (JANS) of MIL-PRF-19500. Delta requirements shall be in accordance with table II herein; delta requirements only apply to subgroups B4 and B5. See table E-VIC of MIL-PRF-19500 and 4.4.2.2 for JAN, JANTX, and JANTXV group B testing. Delta requirements for JAN, JANTX, and JANTXV shall be after each step in 4.4.2.2 and shall be in accordance with table II herein.

4.4.2.1 Quality level JANS (see table E-VIA of MIL-PRF-19500).

| Subgroup | Method | Condition |
|---|---|---|
| B3 | 2037 | Test condition D. |
| B4 | 1037 | $V_{CB}$ = 10 - 30 V dc. |
| B5 | 1027 | (NOTE: If a failure occurs, resubmission shall be at the test conditions of the original sample). $V_{CB}$ = 10 V dc; $P_D$ ≥ 100 percent of maximum rated $P_T$ (see 1.3).<br><br>Option 1: 96 hours minimum, sample size in accordance with table E-VIA of MIL-PRF-19500, adjust $T_A$ or $P_D$ to achieve $T_J$ = +275°C minimum.<br><br>Option 2: 216 hours, sample size = 45, c = 0; adjust $T_A$ or $P_D$ to achieve $T_J$ = +225°C minimum. |
| B6 | | Not applicable. |

4.4.2.2 Quality level JAN, JANTX, and JANTXV (see table E-VIC (small die flow)). Separate samples may be used for each step. In the event of a group B failure, the manufacturer may pull a new sample at double size from either the failed assembly lot or from another assembly lot from the same wafer lot. If the new “assembly lot” option is exercised, the failed assembly lot shall be scrapped.

| Step | Method | Condition |
|---|---|---|
| 1 | 1026 | Steady-state life: 1,000 hours minimum, $V_{CB}$ = 10 V dc, power shall be applied to achieve $T_J$ = +150°C minimum using a minimum of $P_D$ = 75 percent of maximum rated $P_T$ as defined in 1.3. n = 45 devices, c = 0. The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours. |
| 2 | 1048 | Blocking life, $T_A$ = +150°C, $V_{CB}$ = 80 percent of rated voltage, 48 hours minimum. n = 45 devices, c = 0. |
| 3 | 1032 | High temperature life (non-operating), t = 340 hours, $T_A$ = +200°C. n = 22, c = 0. |

4.4.2.3 Group B sample selection. Samples selected from group B inspection shall meet all of the following requirements:

a. For JAN, JANTX, and JANTXV samples shall be selected randomly from a minimum of three wafers (or from each wafer in the lot) from each wafer lot. For JANS, samples shall be selected from each inspection lot. See MIL-PRF-19500.

b. Shall be chosen from an inspection lot that has been submitted to and passed table I, subgroup 2, conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for life test (subgroups B4 and B5 for JANS, and group B for JAN, JANTX, and JANTXV) may be pulled prior to the application of final lead finish.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the tests and conditions specified for subgroup testing in table E-VII of MIL-PRF-19500, and in 4.4.3.1 (JANS) and 4.4.3.2 (JAN, JANTX, and JANTXV) herein for group C testing. Delta requirements shall be in accordance with table II herein; delta requirements only apply to subgroup C6.

4.4.3.1 Quality level JANS (see table E-VII of MIL-PRF-19500).

| Subgroup | Method | Condition |
|---|---|---|
| C2 | 2036 | Test condition E (not applicable to 2N3737UB). |
| C6 | 1026 | $V_{CB}$ = 10 - 30 V dc; 1,000 hours; power shall be applied to achieve $T_J$ = +150°C minimum, using a minimum of $P_D$ = 75 percent of maximum rated $P_T$ as defined in 1.3. n = 45 devices, c = 0 The sample size may be increased and the test time decreased as long as the devices are stressed for a total of 45,000 device hours minimum, and the actual time of test is at least 340 hours. |

4.4.3.2 Quality level JAN, JANTX, and JANTXV (see table E-VII of MIL-PRF-19500).

| Subgroup | Method | Condition |
|---|---|---|
| C2 | 2036 | Test condition E (not applicable to 2N3737UB). |
| C5 | 3131 | $R_{\theta JA}$ and $R_{\theta JC}$ only, as applicable (see 1.3 and 4.5.2). |
| C6 | | Not applicable. |

4.4.3.3 Group C sample selection. Samples for subgroups in group C shall be chosen at random from any inspection lot containing the intended package type and lead finish procured to the same specification which is submitted to and passes table I tests herein for conformance inspection. When the final lead finish is solder or any plating prone to oxidation at high temperature, the samples for C6 life test may be pulled prior to the application of final lead finish. Testing of a subgroup using a single device type enclosed in the intended package type shall be considered as complying with the requirements for that subgroup.

4.4.4 Group D inspection.
Confo
mance inspection for hardness assured JANS and JANTXV types shall include the group D tests specified in table III herein. These tests shall be performed as required in accordance with
MIL-PRF-19500 and method 1019 of MIL-STD-750, for total ionizing dose or method 1017 of MIL-STD-750 for neutron fluence as applicable (see 6.2 herein), except group D, subgroup 2 may be performed separate from other subgroups. Alternate package options may also be substituted for the testing provided there is no adverse effect to the fluence profile.

4.4.5 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-IX of MIL-PRF-19500 and as specified in table IV herein. Delta measurements shall be in accordance with the applicable steps table II.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Thermal resistance. Thermal resistance measurement shall be performed in accordance with method 3131 of MIL-STD-750 using the guidelines in that method for determining $I_M$, $I_H$, and $t_H$. Measurement delay time $t_{MD}$ = 70 ms max.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

| Inspection 1/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 1 2/ | | | | | | |
| Visual and mechanical examination 3/ | 2071 | | | | | |
| Solderability 3/ 4/ | 2026 | n = 15 leads, c = 0 | | | | |
| Resistance to solvents 3/ 4/ 5/ | 1022 | n = 15 devices, c = 0 | | | | |
| Salt atmosphere (corrosion) | 1041 | n = 6 devices, c = 0, (For laser marked devices only) | | | | |
| Temp cycling 3/ 4/ | 1051 | Test condition C, 25 cycles<br>n = 22 devices, c = 0 | | | | |
| Hermetic seal 4/ 6/<br>Fine leak<br>Gross leak | 1071 | n = 22 devices, c = 0 | | | | |
| Electrical measurements 4/ | | Table I, subgroup 2 | | | | |
| Bond strength 3/ 4/ | 2037 | Precondition<br>$T_A$ = +250°C at t = 24 hrs or<br>$T_A$ = +300°C at t = 2 hrs<br>n = 11 wires, c = 0 | | | | |
| Decap internal visual (design verification) 4/ | 2075 | n = 4 devices, c = 0 | | | | |
| Subgroup 2 | | | | | | |
| Thermal impedance 7/ | 3131 | See 4.3.2 | $Z_{\theta JX}$ | | | °C/W |
| Breakdown voltage collector to emitter | 3011 | Bias condition D; $I_C$ = 10 mA dc, pulsed (see 4.5.1) | $V_{(BR)CEO}$ | 40 | | V dc |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CBO}$ = 75 V dc | $I_{CBO1}$ | | 10 | µA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EBO}$ = 5 V dc | $I_{EBO1}$ | | 10 | µA dc |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CB}$ = 30 V dc | $I_{CBO2}$ | | 250 | nA dc |
| Collector to emitter cutoff current | 3041 | Bias condition A; $V_{CE}$ = 30 V dc<br>$V_{EB}$ = 2.0 V dc | $I_{CEX1}$ | | 200 | nA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EB}$ = 4.0 V dc | $I_{EBO2}$ | | 100 | nA dc |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 1.0 V dc; $I_C$ = 10 mA dc | $h_{FE1}$ | 35 | | |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 1.0 V dc; $I_C$ = 150 mA dc, pulsed (see 4.5.1) | $h_{FE2}$ | 40 | | |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 1.0 V dc; $I_C$ = 500 mA dc, pulsed (see 4.5.1) | $h_{FE3}$ | 40 | 140 | |

See footnotes at end of table.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

| Inspection 1/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 2 – continued | | | | | | |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 1.5 V dc; $I_C$ = 1.0 A dc, pulsed (see 4.5.1) | $h_{FE4}$ | 20 | 80 | |
| Collector to emitter voltage (saturated) | 3071 | $I_C$ = 10 mA dc, $I_B$ = 1.0 mA dc | $V_{CE(sat)1}$ | | 0.2 | V dc |
| Collector to emitter voltage (saturated) | 3071 | $I_C$ = 150 mA dc, $I_B$ = 15 mA dc, pulsed (see 4.5.1) | $V_{CE(sat)2}$ | | 0.3 | V dc |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 5.0 V dc; $I_C$ = 1.5 A dc, pulsed (see 4.5.1) | $h_{FE5}$ | 20 | | |
| Collector to emitter voltage (saturated) | 3071 | $I_C$ = 500 mA dc, $I_B$ = 50 mA dc, pulsed (see 4.5.1) | $V_{CE(sat)3}$ | | 0.5 | V dc |
| Collector to emitter voltage (saturated) | 3071 | $I_C$ = 1.0 A dc, $I_B$ = 100 mA dc, pulsed (see 4.5.1) | $V_{CE(sat)4}$ | | 0.9 | V dc |
| Base to emitter saturated voltage | 3066 | Test condition A, $I_C$ = 10 mA dc, $I_B$ = 1.0 mA dc | $V_{BE(sat)1}$ | | 0.8 | V dc |
| Base to emitter saturated voltage | 3066 | Test condition A, $I_C$ = 150 mA dc, $I_B$ = 15 mA dc, pulsed (see 4.5.1) | $V_{BE(sat)2}$ | | 1.0 | V dc |
| Base to emitter saturated voltage | 3066 | Test condition A, $I_C$ = 500 mA dc, $I_B$ = 50 mA dc, pulsed (see 4.5.1) | $V_{BE(sat)3}$ | | 1.2 | V dc |
| Base to emitter saturated voltage | 3066 | Test condition A, $I_C$ = 1.0 A dc, $I_B$ = 100 mA dc, pulsed (see 4.5.1) | $V_{BE(sat)4}$ | 0.9 | 1.4 | V dc |
| Subgroup 3 | | | | | | |
| High-temperature operation: | | $T_A$ = +150°C | | | | |
| Collector to emitter cutoff current | 3041 | Bias condition A; $V_{CE}$ = 30 V dc, $V_{EB}$ = 2.0 V dc | $I_{CEX2}$ | | 250 | µA dc |
| Low-temperature operation: | | $T_A$ = -55°C | | | | |
| Forward current transfer ratio | 3076 | $V_{CE}$ = 1.0 V dc; $I_C$ = 500 mA dc, pulsed (see 4.5.1) | $h_{FE6}$ | 15 | | |

See footnotes at end of table.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

| Inspection 1/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 4 | | | | | | |
| Magnitude of common - emitter small-signal short-circuit forward current transfer ratio | 3306 | $V_{CE}$ = 10 V dc; $I_C$ = 50 mA dc; f = 100 MHz | $\|h_{fe}\|$ | 2.5 | 6.0 | |
| Open circuit output capacitance | 3236 | $V_{CB}$ = 10 V dc, $I_E$ = 0, 100 kHz ≤ f ≤ 1 MHz | $C_{obo}$ | | 9.0 | pF |
| Input capacitance (output open circuited) | 3240 | $V_{EB}$ = 0.5 V dc, $I_C$ = 0, 100 kHz ≤ f ≤ 1 MHz | $C_{ibo}$ | | 80 | pF |
| Pulse response: | | | | | | |
| Delay response | 3251 | Test condition A; $V_{CC}$ = 30 V dc, $V_{BE}$ = 2 V dc, $I_C$ = 1.0 A dc, $I_{B1}$ = 100 mA dc, (see figure 5) | $t_d$ | | 8.0 | ns |
| Rise time | 3251 | Test condition A; $V_{CC}$ = 30 V dc, $V_{BE}$ = 2 V dc, $I_C$ = 1.0 A dc, $I_{B1}$ = 100 mA dc, (see figure 5) | $t_r$ | | 40 | ns |
| Turn-off time | 3251 | Test condition A; $V_{CC}$ = 30 V dc, $I_C$ = 1.0 A dc, $I_{B1}$ = -$I_{B2}$ = 100 mA dc, (see figure 6) | $t_{off}$ | | 60 | ns |
| Subgroups 5, 6 and 7 | | | | | | |
| Not applicable | | | | | | |

1/ For sampling plan, unless otherwise specified see MIL-PRF-19500.
2/ For resubmission of failed subgroup table I, double the sample size of the failed test or sequence of tests. A failure in table I, subgroup 1 shall not require retest of the entire subgroup. Only the failed test shall be rerun upon submission.
3/ Separate samples may be used.
4/ Not required for JANS devices.
5/ Not required for laser marked devices.
6/ This hermetic seal test is an end-point to temp-cycling in addition to electrical measurements.
7/ For end-point measurements, this test is required for the following subgroups: Group B, subgroups 3, 4, and 5 (JANS); group B, see 4.4.2.2 herein, after each step (JAN, JANTX, and JANTXV); group C, subgroup 2 and 6, group E, subgroup 1.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE II. Groups B and C delta measurements. 1/ 2/ 3/

| Step | Inspection | MIL-STD-750 | | Symbol | Limits | Limits | Unit |
|---|---|---|---|---|---|---|---|
| | | Method | Conditions | | Min | Max | |
| 1. | Collector to base cutoff current | 3036 | Bias condition D, $V_{CB}$ = 30 V dc | $\Delta I_{CBO2}$ | 100 percent of initial value or 25 nA dc, whichever is greater. | | |
| 2. | Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc, $I_C$ = 500 mA dc, pulsed (see 4.5.1) | $\Delta h_{FE3}$ | ±25 percent change from initial value. | | |
| 3. | Collector to emitter voltage (saturated) | 3071 | $I_C$ = 500 mA dc, $I_B$ = 50 mA dc, pulsed (4.5.1 ) | $\Delta V_{CE(SAT)3}$ | ±50 mV dc, change from previous measured value. | | |

1/ The delta measurements for table E-VIA (JANS) of MIL-PRF-19500 are as follows:
   a. Subgroup 4, see table II herein, step 3.
   b. Subgroup 5, see table II herein, step 3.
2/ The delta measurements for 4.4.2.2 (JAN, JANTX, JANTXV) are as follows: See table II herein, steps 1 and 2.
3/ The delta measurements for table E-VII of MIL-PRF-19500 are as follows: Subgroup 6, see table II herein, steps 1 and 2 for (JANS).



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE III. Group D inspection.

| Inspection 1/ 2/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 1 3/ | | | | | | |
| Neutron irradiation | 1017 | Neutron exposure $V_{CES}$ = 0V | | | | |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CB}$ = 75 V dc | $I_{CBO1}$ | | 20 | µA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EB}$ = 5 V dc | $I_{EBO1}$ | | 20 | µA dc |
| Breakdown voltage, collector to emitter | 3011 | Bias condition D; $I_C$ = 10 mA dc; pulsed (see 4.5.1) | $V_{(BR)CEO}$ | 40 | | V dc |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CB}$ = 30 V dc | $I_{CBO2}$ | | 500 | nA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EB}$ = 4 V dc | $I_{EBO2}$ | | 200 | nA dc |
| Collector to emitter cutoff current | 3041 | Bias condition A; $V_{CE}$ = 30 V dc, $V_{EB}$ = 2 V dc | $I_{CEX1}$ | | 400 | nA dc |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 10 mA dc | [$h_{FE1}$] 4/ | [17.5] | | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 150 mA dc pulsed (see 4.5.1) | [$h_{FE2}$] 4/ | [20] | | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 500 mA dc pulsed (see 4.5.1) | [$h_{FE3}$] 4/ | [20] | 140 | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1.5 V dc; $I_C$ = 1 A dc pulsed (see 4.5.1) | [$h_{FE4}$] 4/ | [10] | 80 | |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 10 mA dc; $I_B$ = 1 mA dc | $V_{CE(sat)1}$ | | .23 | V dc |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 150 mA dc; $I_B$ = 15 mA dc pulsed (see 4.5.1) | $V_{CE(sat)2}$ | | .35 | V dc |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 5 V dc; $I_C$ = 1.5 A dc pulsed (see 4.5.1) | [$h_{FE5}$] 4/ | [10] | | |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 500 mA dc; $I_B$ = 50 mA dc pulsed (see 4.5.1) | $V_{CE(sat)3}$ | | .58 | V dc |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 1 A dc; $I_B$ = 100 mA dc pulsed (see 4.5.1) | $V_{CE(sat)4}$ | | 1.04 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 10 mA dc; $I_B$ = 1 mA dc | $V_{BE(sat)1}$ | | .92 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 150 mA dc; $I_B$ = 15 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)2}$ | | 1.15 | V dc |

See footnotes at end of table



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE III. Group D inspection - Continued.

| Inspection 1/ 2/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 1 - Continued 3/ | | | | | | |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 500 mA dc; $I_B$ = 50 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)3}$ | | 1.38 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 1 A dc; $I_B$ = 100 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)4}$ | .9 | 1.61 | V dc |
| Subgroup 2 3/ | | | | | | |
| Steady-state total dose irradiation | 1019 | Gamma exposure, Condition A, $V_{CES}$ = 32 V | | | | |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CB}$ = 75 V dc | $I_{CBO1}$ | | 20 | µA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EB}$ = 5 V dc | $I_{EBO1}$ | | 20 | µA dc |
| Breakdown voltage, collector to emitter | 3011 | Bias condition D; $I_C$ = 10 mA dc; pulsed (see 4.5.1) | $V_{(BR)CEO}$ | 40 | | V dc |
| Collector to base cutoff current | 3036 | Bias condition D; $V_{CB}$ = 30 V dc | $I_{CBO2}$ | | 500 | nA dc |
| Emitter to base cutoff current | 3061 | Bias condition D; $V_{EB}$ = 4 V dc | $I_{EBO2}$ | | 200 | nA dc |
| Collector to emitter cutoff current | 3041 | Bias condition A; $V_{CE}$ = 30 V dc, $V_{EB}$ = 2 V dc | $I_{CEX1}$ | | 400 | nA dc |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 10 mA dc | [$h_{FE1}$] 4/ | [17.5] | | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 150 mA dc pulsed (see 4.5.1) | [$h_{FE2}$] 4/ | [20] | | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1 V dc; $I_C$ = 500 mA dc pulsed (see 4.5.1) | [$h_{FE3}$] 4/ | [20] | 140 | |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 1.5 V dc; $I_C$ = 1 A dc pulsed (see 4.5.1) | [$h_{FE4}$] 4/ | [10] | 80 | |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 10 mA dc; $I_B$ = 1 mA dc | $V_{CE(sat)1}$ | | .23 | V dc |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 150 mA dc; $I_B$ = 15 mA dc pulsed (see 4.5.1) | $V_{CE(sat)2}$ | | .35 | V dc |
| Forward-current transfer ratio | 3076 | $V_{CE}$ = 5 V dc; $I_C$ = 1.5 A dc pulsed (see 4.5.1) | [$h_{FE5}$] 4/ | [10] | | |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 500 mA dc; $I_B$ = 50 mA dc plused (see 4.5.1) | $V_{CE(sat)3}$ | | .58 | V dc |

See footnotes at end of table



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

TABLE III. Group D inspection - Continued.

| Inspection 1/ 2/ | MIL-STD-750 | | Symbol | Limit | Limit | Unit |
|---|---|---|---|---|---|---|
| | Method | Conditions | | Min | Max | |
| Subgroup 2 - Continued 3/ | | | | | | |
| Collector-emitter saturation voltage | 3071 | $I_C$ = 1 A dc; $I_B$ = 100 mA dc; pulsed (see 4.5.1) | $V_{CE(sat)4}$ | | 1.04 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 10 mA dc; $I_B$ = 1 mA dc | $V_{BE(sat)1}$ | | .92 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 10 mA dc; $I_B$ = 1 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)2}$ | | 1.15 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 500 mA dc; $I_B$ = 50 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)3}$ | | 1.38 | V dc |
| Base-emitter saturation voltage | 3066 | Test condition A; $I_C$ = 1 A dc; $I_B$ = 100 mA dc; pulsed (see 4.5.1) | $V_{BE(sat)4}$ | .9 | 1.61 | V dc |

1/ Tests to be performed on all devices receiving radiation exposure.
2/ For sampling plan, see MIL-PRF-19500.
3/ See 6.2.e herein.
4/ See method 1019 of MIL-STD-750 for how to determine [$h_{FE}$] by first calculating the delta ($1/h_{FE}$) from the Pre and Post-radiation $h_{FE}$. Notice the [$h_{FE}$] is not the same as $h_{FE}$ and cannot be measured directly. The [$h_{FE}$] value can never exceed the pre-radiation minimum $h_{FE}$ that it is based upon.




Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

* TABLE IV. Group E inspection (all quality levels) - for qualification or re-qualificatrion only.

| Inspection | MIL-STD-750 | | Sample plan |
|---|---|---|---|
| | Method | Conditions | |
| Subgroup 1 | | | 45 devices c = 0 |
| Temperature cycling (air to air) | 1051 | Test condition C, 500 cycles | |
| Hermetic seal<br>Fine leak<br>Gross leak | 1071 | | |
| Electrical measurements | | See table I, subgroup 2 herein | |
| Subgroup 2 | | | 45 devices c = 0 |
| Intermittent life | 1037 | $V_{CB}$ = 10 V dc, 6,000 cycles. Adjust device current, or power, to achieve a minimum $\Delta T_J$ of +100°C | |
| Electrical measurements | | See table I, subgroup 2 herein | |
| Subgroup 4 | | | |
| Thermal impedance curves | | See MIL-PRF-19500, table E-IX, group E, subgroup 4 | |
| Subgroup 6 | | | 11 devices |
| Electrostatic discharge (ESD) | 1020 | | |
| Subgroup 8 | | | 45 devices c = 0 |
| Reverse stability | 1033 | Condition B | |




Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

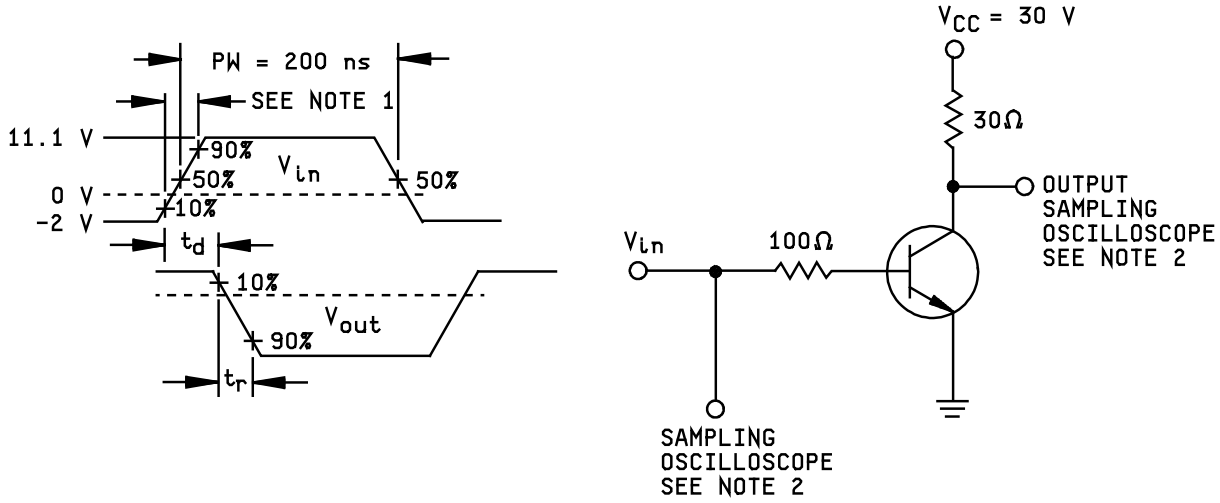


NOTES:
1. The rise time ($t_r$) of the applied pulse shall be ≤ 0.1 ns, duty cycle ≤ 2 percent, and the generator source impedance shall be 50 Ω.
2. Sampling oscilloscope: $Z_{in}$ ≥ 100 kΩ, $C_{in}$ ≤ 12 pF, rise time ≤ 5 ns.

FIGURE 5. Test circuit and waveforms for measuring turn-on.

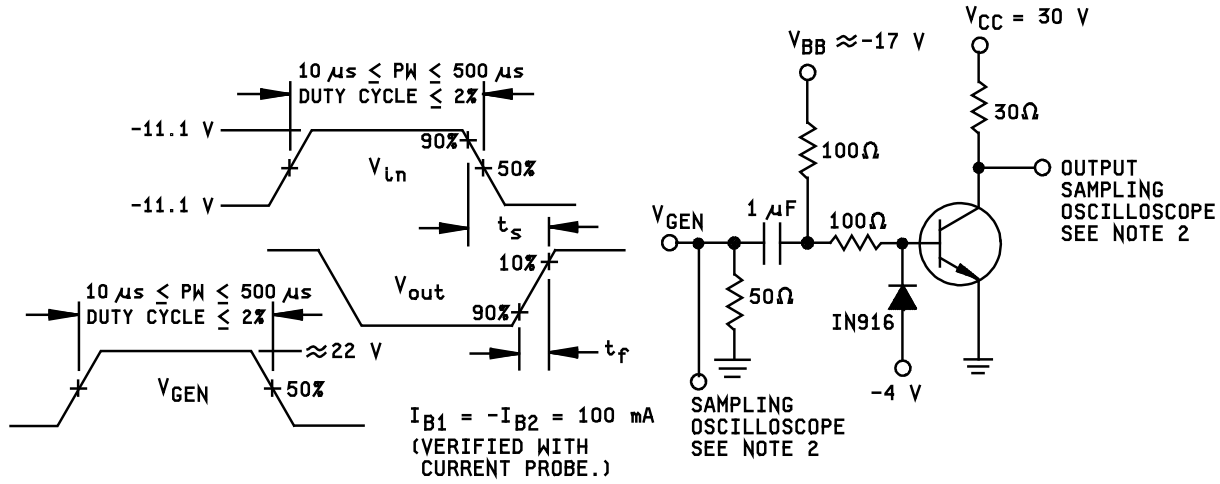


NOTES:
1. The rise time ($t_r$) of the applied pulse shall be ≤ 0.1 ns, duty cycle ≤ 2 percent, and the generator source impedance shall be 50 Ω.
2. Sampling oscilloscope: $Z_{in}$ ≥ 100 kΩ, $C_{in}$ ≤ 12 pF, rise time ≤ 5 ns.

FIGURE 6. Test circuit and waveforms for measuring turn-off.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory. The notes specified in MIL-PRF-19500 are applicable to this specification.)

6.1 Intended use. Semiconductors conforming to this specification are intended for original equipment design applications and logistic support of existing equipment.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead finish (see 3.4.1).

d. The complete PIN, see 1.5.

e. For acquisition of RHA designated devices, table III, subgroup 1 testing of group D herein is optional. If subgroup 1 is desired, it must be specified in the contract.


6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://qpldocs.dla.mil.




Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

6.4 PIN construction example.

6.4.1 Encapsulated devices The PINs for encapsulated devices are constructed using the following form.

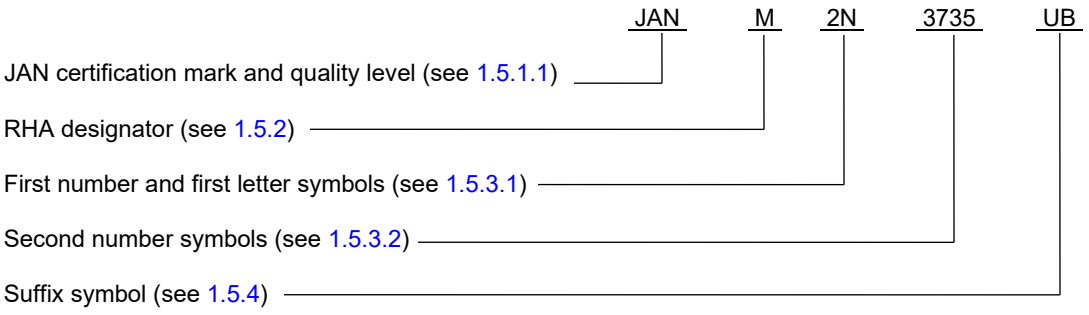


* 6.4.2 Unencapsulated devices The PINs for unencapsulated devices are constructed using the following form.

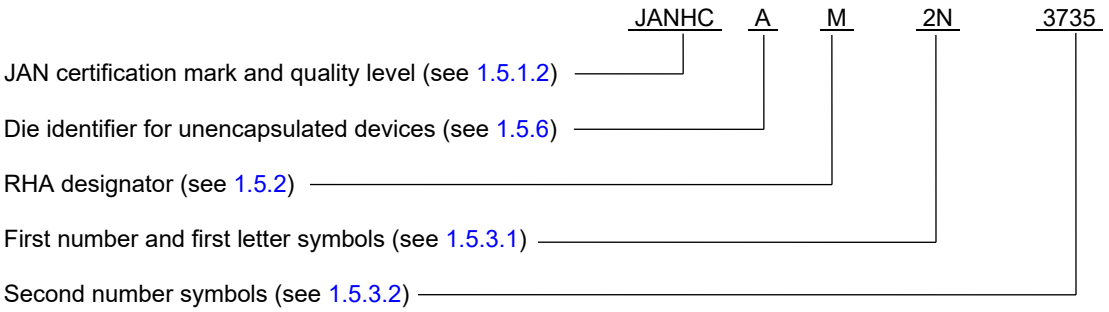


6.5 List of PINs. The following is a list of possible PINs available on this specification sheet.

6.5.1 List of PINs for encapsulated devices. The following is a list of possible PINs for encapsulated devices available on this specification sheet

| PINs for devices of the base quality level | PINs for devices of the "TX" quality level | PINs for devices of the "TXV" quality level | PINs for devices of the "TXV" quality level (1) | PINs for devices of the "S" quality level | PINs for devices of the "S" quality level (1) |
|---|---|---|---|---|---|
| JAN2N3735 | JANTX2N3735 | JANTXV2N3735 | JANTXV#2N3735 | JANS2N3735 | JANS#2N3735 |
| JAN2N3735L | JANTX2N3735L | JANTXV2N3735L | JANTXV#2N3735L | JANS2N3735L | JANS#2N3735L |
| JAN2N3737 | JANTX2N3737 | JANTXV2N3737 | JANTXV#2N3737 | JANS2N3737 | JANS#2N3737 |
| JAN2N3735UB | JANTX2N3735UB | JANTXV2N3735UB | JANTXV#2N3735UB | JANS2N3735UB | JANS#2N3735UB |
| JAN2N3737UB | JANTX2N3737UB | JANTXV2N3737UB | JANTXV#2N3737UB | JANS2N3737UB | JANS#2N3737UB |

(1) The number sign (#) represents one of eight RHA designators available for the JANS quality level (M, D, P, L, R, F, G, or H), and one of two RHA designators available for the JANTXV quality level (R or F).



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.

6.5.2 PINs for unencapsulated devices (die). The following is a list of possible PINs for unencapsulated devices available on this specification sheet.

| Quality level HC | Quality level KC |
|---|---|
| JANHCA#2N3735 | JANKCA#2N3735 |
| JANHCA#2N3737 | JANKCA#2N3737 |

(1) The number sign (#) represents one of eight RHA designators available (M, D, P, L, R, F, G, or H). The PIN is also available without a RHA designator.

* 6.5.3 Suppliers of JANHC and JANKC die. The qualified JANHC and JANKC suppliers with the applicable letter version (example JANHCA2N3735) will be identified on the QML.

| Die ordering information (1) | |
|---|---|
| PIN | Manufacturer |
| | 34156 |
| 2N3735 | JANHCA2N3735 |
| 2N3737 | JANHCA2N3737 |

(1) For JANKC level, replace JANHC with JANKC.

6.6 Amendment notations. The margins of this specification are marked with asterisks to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:
Army - CR
* Navy - SH
Air Force - 85
NASA - NA
DLA - CC

Review activities:
Army - AR, MI, SM
Navy - AS, MC
Air Force - 19, 71

Preparing activity:
DLA - CC

(Project 5961-2023-047)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.



Source: https://assist.dla.mil -- Downloaded: 2026-10-18T16:27Z
Check the source to verify that this is the current version before use.