INCH-POUND

MIL-DTL-2874F
05 MAR 2025
SUPERSEDING
MIL-G-2874E
01 JUL 1987

DETAIL SPECIFICATION

GLOVES, ANTI-FLASH, FLAME RESISTANT

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This military specification covers the requirements for flame resistant anti-flash gloves, of one type and size only.

1.2 Classification. The flame resistant anti-flash gloves are available in one type and one size.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 or 4 of this military specification. This section does not include documents cited in other sections of this military specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 or 4 of this military specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents will be those listed in the solicitation or contract.

Comments, suggestions, or questions on this document should be emailed to trpsptctstandardiz@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 8415

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

FEDERAL SPECIFICATIONS

JJ-W-155	- Webbing, Textile (Cotton, Elastic)

COMMERICAL ITEM DESCRIPTIONS

A-A-50199	- Thread, Polyester Core, Cotton or Polyester-Covered
A-A-52094	- Thread, Cotton

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-DTL-32075	- Label: For Clothing Equipage, and Tentage, (General Use)

(Copies are available online at https://quicksearch.dla.mil/.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

AMERICAN ASSOCIATION OF TEXTILE CHEMISTS AND COLORISTS (AATCC)

AATCC TM20A	- Test Method for Fiber Analysis: Quantitative
AATCC TM81	- Test Method for pH of the Water-Extract from Wet Processed Textiles
AATCC TM96	- Test Method for Dimensional Changes in Commercial Laundering of Woven and Knitted Fabrics Except Wool

(Copies are available online at https://www.aatcc.org.)

AMERICAN SOCIETY FOR QUALITY (ASQ)

ASQ/ANSI Z1.4	- Sampling Procedures and Tables for Inspection by Attributes

(Copies are available online at https://www.asq.org.)

ASTM INTERNATIONAL (ASSTM)

ASTM D737	- Standard Test Method for Air Permeability of Textile Fabrics
ASTM D1424	- Standard Test Method for Tearing Strength of Fabrics by Falling-Pendulum (Elmendorf-Type) Apparatus
ASTM D1776/D1776M	- Standard Practice for Conditioning and Testing Textiles
ASTM D3775	- Standard Test Method for End (Warp) and Pick (Filling) Count of Woven Fabrics
ASTM D3776/D3776M	- Standard Test Methods for Mass Per Unit Area (Weight) of Fabric
ASTM D5034	- Standard Test Method for Breaking Strength and Elongation of

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

	Textile Fabrics (Grab Test)
ASTM D6193	- Standard Practice for Stitches and Seams
ASTM D6413/D6413M	- Standard Test Method for Flame Resistance of Textiles (Vertical Test)

(Copies are available online at https://www.astm.org.)

PARACHUTE INDUSTRY ASSOCIATION (PIA)

PIA-TM-5202	- Stiffness Of Cloth, Directional; Cantilever Bending Method

(Copies are available online at: https://www.pia.com)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample of the flame resistant anti-flash gloves shall be subjected to first article inspection in accordance with 4.2.

3.2 Material.

3.2.1 Basic material. The basic material used for the gloves shall be flame retardant treated cotton flannel cloth.

3.2.1.1 Yarn. The yarn shall be made from cotton which has been carded, drawn, and spun into singles yarn for both the warp and the filling, when tested as specified in 4.4.1.

3.2.1.2 Weave. The weave shall be a 3 or 4 harness twill, when tested as specified in 4.4.1.

3.2.1.3 Color. The cloth shall be unbleached or bleached white.

3.2.1.4 Physical requirements. The finished cloth shall conform to the physical requirements shown in Table I when tested as specified in 4.3.1.2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE I. Basic material physical requirements

Characteristic	Minimum	Maximum
Weight, oz/yd^2	9.00	10.25
Tear Strength, lbs.:		
Warp	4.0	-
Filling	4.0	-
Stiffness, in-lbs.:		
Warp	-	0.006
Filling	-	0.004
Air permeability, ft^3/min/ft^2	10	-
Yarns per inch:		
Warp	62	-
Filling	38	-
Breaking strength, lbs.:		
Warp	65	-
Filling	40	-
Flame resistance:		
Initially and after 25 launderings:		
After flame time, seconds	-	2.0
After glow time, seconds	-	5.0
Char length, inches	-	5.0

3.2.1.5 Finish. The cloth shall be napped on the back side, scoured, desized, and given a flame retardant treatment.

3.2.1.6 Nonfibrous material. Prior to the application of the flame retardant treatment, the cloth shall contain no more than 3.0 percent starch and protein content including chloroform-soluble and water-soluble material, when tested as specified in 4.4.1.

3.2.1.7 Dimensional stability. The finished cloth shall not shrink nor elongate more than 3.0 percent in either the warp or filling direction when tested as specified in 4.4.1. The preshrinking process used shall not be identified by name or by trademark, either on the cloth, ticket, or package.

3.2.1.8 pH. The pH value of the water extract of the finished cloth shall be no less than 5.0 nor more than 8.5 when tested as specified in 4.4.1.

3.2.2 Webbing, elastic. The elastic webbing used for the wrist and elbow take-up on the gauntlet portion of the gloves shall be cotton, conforming to Type II, Class 2 (unbleached or bleached white) of JJ-W-155.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

3.2.3 Thread. The thread for seaming and stitching the gloves shall be Type I of A-A-50199, 2 ply cotton-covered polyester-core, Tex size 36-45 (needle and bobbin) and 31-35 (looper) and shall approximate the color of the basic cloth. As an alternate, the thread may be Type I of A-A- 52094, 3 ply cotton Tex size 60 (needle and bobbin) and Tex size 40 (looper) approximating the color of the basic cloth.

3.2.4 Label. Each glove shall be marked with a combination identification and instruction label, conforming to Type III or IV, Class 15 of MIL-DTL-32075. The markings shall show fastness to accelerated laundering only. The label shall bear the following inscription:

GLOVES, ANTI-FLASH, FLAME RESISTANT
CONTRACT NO. SPE1C1-00-X-0000 (Example)
STOCK NO: 8415-00-000-0000 (Example)
FIBER CONTENT: 100% COTTON (Flame retardant treated)
NAME OF CONTRACTOR:

LAUNDERING INSTRUCTIONS
Machine wash warm
No starch, No bleach
Tumble dry, medium heat

or

FOLLOW NAVEDTRA MANUAL 414-01-4S-81
FORMULA II

3.2.5 Barcode label/tag. Each pair of gloves shall be individually bar coded with a label/tag in accordance with Type VIII, Class 17 of MIL-DTL-32075. The label/tag shall be located so that it is completely visible on the item when it is folded and/or packaged as specified and shall cause no damage to the item.

3.3 Design. The gloves shall be a five finger clute-cut pattern, with an attached one-piece elbow- length gauntlet gathered at the wrist and elbow by an elastic webbing to provide proper fit (see Figure 1).

3.3.1 Figure 1. Figure l is furnished for information purpose only. To the extent of any inconsistencies between the written specification and the figure, the written specification shall govern.

3.4 Patterns. Standard patterns, providing a seam allowance of 3/8” for the gauntlet seams and 3/16” for all other seams, will be furnished by the Government to the contractor for use in cutting working patterns (see 6.3). The working patterns shall be identical to the Government patterns. The use of Government pattern parts is optional; however, the finished dimensions of the gloves shall conform to the requirements specified in 3.7. Minor modifications are permitted to the contractor’s working patterns where necessary when using automatic

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

equipment or production processes. These modifications shall not alter the appearance, serviceability or dimensional requirements cited in this document.

3.4.1 Pattern parts. The component parts of the gloves shall be cut from the basic material specified in 3.2.l, and in accordance with the pattern parts listed in Table II.

TABLE II. Pattern parts

Nomenclature of pattern parts	CAD piece name	Cut parts per pair
No. 2 finger	2874-SECONDFINGER	2
No. 3 finger	2874-THIRDFINGER	2
No. 4 finger	2874-FOURTHFINGER	2
Thumb	2874-THUMB	2
Palm	2874-PALM	2
Gauntlet	2874-GAUNTLET	2

3.5 Construction.

3.5.1 Stitches, seams, and stitchings. Stitches, seams, and stitchings shall be consistent, exhibit a uniform appearance, and conform to the types specified in Table III in accordance with ASTM D6193. The seam allowances annotated on the Government patterns shall be maintained during all sewing operations. Seams shall be formed in a manner that prevents the occurrence of puckering, pleating, irregularity, waviness, or other defects. Whenever two or more methods for seam or stitch types are given for the same part of the operation, any one may be used. Where stitch type 401 is used, the looper (underthread) shall be on the inside of the glove.

3.5.2 Thread breaks and ends of seams. Ends of all seams and stitchings, when not caught in other seams or stitchings, shall be backtacked not less than 3/8 inch. The ends of a continuous line of stitching shall be overlapped not less than 1/2 inch. Thread breaks (all stitch types) shall be secured by stitching back of the break not less than 1/2 inch. Skipped stitches or thread breaks on 401 stitch type may be repaired by using 301 stitch type. The chain extension of 401 stitch type, shall be trimmed to 1/2 to 3/4 inch when not caught in other seams or stitchings.

3.5.3 Stitches per inch. All stitching shall be 10 stitches per inch minimum, 14 stitches per inch maximum.

3.6 Manufacturing operation requirements. The gloves shall be manufactured in accordance with operation requirements specified in Table III. The contractor is not required to follow the exact sequence of operations, provided that the finished gloves are identical to those produced by following the exact sequence of operations as listed in Table III.

THIS SPACE INTENTIONALLY LEFT BLANK

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE III. Construction of gloves

Number	Operation	Stitch Type	Seam Type
1	**Cutting**		
	a. Lay the basic material so that the lay is even and the plies are not stretched or full.		
	b. The component parts of the gloves shall be cut in strict accordance with patterns furnished when applicable (see 3.4), which show shape, directional lines for cutting, placement of component parts, and notches for proper assembly of all component parts.		
	c. The face side of the cotton flannel material shall be the unnapped side.		
	d. Cut the elastic webbing specified in 3.2.2 to a length of 8 (± 1/4) inches for the wrist and 11 (± 1/4) inches for the elbow take up of gauntlet. 1/		
2	**Replacement of defective components**		
	During the spreading, cutting, and manufacturing process, components having material defects or damages that are classified as defects in Section 4, shall be removed from production and replaced with non-defective and properly matched components.		
3	**Marking**		
	Mark, ticket, or bundle all component cut parts to insure proper assembly of the gloves.		
4	**Assemble hand portion of gloves**		
	a. Stitch the thumb piece to thumb section of palm face to face along the periphery of thumb, according to notches on pattern, 3/16 (± 1/16) inch from the raw edge.	301 or 401	SSa-1
	b. Stitch the No. 2 finger portion to the No. 3 finger portion face to face from the wrist edge to the finger crotch, according to notches on pattern, 3/16 (± 1/16) inch from the raw edge.	301 or 401	SSa-1
	c. Stitch the No. 3 finger portion to the No. 4 finger portion face to face from the wrist edge to the finger crotch, according to notches on pattern, 3/16 (± 1/16) inch from the raw edge.	301 or 401	SSa-1

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE III. Construction of gloves (continued)

Number	Operation	Stitch Type	Seam Type
4	**Assemble hand portion of gloves (continued)**		
	d. Stitch the No. 2 finger portion to the first (index) finger portion of palm face to face from the wrist edge to the finger crotch, according to notches on pattern, 3/16 (± 1/16) inch from the raw edge.	301 or 401	SSa-1
5 (Option 1)	**Attach gauntlet and elastic webbings**		
	a. Join gauntlet piece to hand portion of glove at wrist edge face to face, matching notches, and stitch 3/8 (± 1/16) inch from the raw edge.	515, 516 or 602	SSa-2
	b. Position fully extended elastic webbing across the wrist to correspond with marks indicated on gauntlet pattern. Stitch through all plies. Fullness of the glove shall be distributed evenly under the relaxed elastic webbing.	301 or 401	similar to SSaa-1
	c. Turn under the raw edge of gauntlet and insert the elastic webbing for the elbow take-up. Position and fully extend elastic webbing and stitch approximately 1/2 inch from the top finished edge of glove catching the elastic webbing securely along the bottom edge. The cotton flannel material shall be held taut while stitching to distribute the webbing evenly along the seam.	301 or 401	EFf-1
	d. The hem shall finish 3/4 (± 1/8) inch in width.		
OR			
5 (Option 2)	**Attach gauntlet and elastic webbings**		
	e. Join gauntlet piece to hand portion of glove at wrist edge face to face, with the elastic webbing fully extended and superimposed on the gauntlet and stitch through all plies 3/8 (± 1/16) inch from the raw edge. The while stitching to distribute the webbing evenly along the seam.	515, 516 or 602	SSab-2
	f. Turn under the raw edge of gauntlet and insert the elastic webbing for the elbow take-up. Position and fully extend elastic webbing and stitch approximately 1/2 inch from the top finished edge of glove catching the elastic webbing securely along the bottom edge. The cotton flannel material shall be held taut while stitching to distribute the webbing evenly along the seam.	301 or 401	EFf-1
	g. The hem shall finish 3/4 (± 1/8) inch in width .		

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE III. Construction of gloves (continued)

Number	Operation	Stitch Type	Seam Type
6	**Closing**		
	Close the gloves according to notches on pattern by stitching face to face 3/16 (± 1/16) inch from the raw edge, from the top edge of the first index finger along the periphery of the fingers and side of glove, gradually increasing the seam between the notch on the No. 4 finger and the wrist seam to 3/8 (± 1/16) inch and continue stitching to top folded edge of gauntlet. The ends of the wrist and elbow elastic webbings shall be securely caught in the seam.	301 or 401	SSa-1
7	**Finishing**		
	Turn glove to its finished position, napped side of the cotton flannel material on the inside.		
8	**Labeling**		
	Each glove shall have the identification and instruction marking (see 3.2.4) applied on the palm side, bottom portion, of the gauntlet. This shall be centered and positioned so that the distance between the last line of the marking and the stitch line of the hem is approximately 1 inch.		
9	**Trimming and cleaning**		
	a. Trim thread ends (except the 1/2-to-3/4-inch chain extension required on type 401 stitching) and remove all loose threads.		
	b. Remove all spots and stains.		
10	**Pairing**		
	The finished gloves shall be paired and tacked together in accordance with the best commercial practice which will permit the gloves to be separated without damaging the fabric. A pair consists of one left glove and one right glove.		

1/ The elastic webbing does not need to be cut if applied in roll form, but the gloves must meet measurements specified in Table IV.

3.7 Finished measurements. The measurements of the finished gloves shall conform to the dimensions specified in Table IV. All measurements and tolerances are expressed in inches. A visual guide for the location of the measurements is provided in Figure 1. The letters A, B, C, D,

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

and E indicate the location of each measurement in Figure 1. Verification of finished measurements shall be in accordance with 4.4.2.2.

TABLE IV. Finished measurements

Measurement	Dimension	Tolerance
Overall Length (A)	19	± 1/2
Hand Length (B)	8	± 1/4
Width (C)	5	± 1/4
Wrist (D)	3-3/4	± 1/4
Elbow (E)	5-1/4	± 1/4

3.8 Workmanship. Each pair of finished gloves shall conform to the quality established by this specification.

4. VERIFICATION

4.1 Classification of inspection. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.2)
b. Conformance inspection (see 4.3)

4.2 First article inspection. When required, the first article submitted in accordance with 3.1 shall be inspected for compliance with design, construction, workmanship, and dimensional requirements as specified in 4.4.2.1 and 4.4.2.2.

4.2.1 First article sample. The sample unit shall be one pair of gloves and the lot size shall be expressed in units of one glove each.

4.3 Conformance inspection. Conformance inspection shall consist of all examinations and tests specified in Section 4.

4.3.1 Conformance sampling. Unless otherwise specified, sampling for inspection shall be performed in accordance with the provisions of ASQ/ANSI Z1.4. The sample unit for end item inspection shall be one pair of gloves and the lot size shall be expressed in units of one glove each.

4.3.1.1 In-process examination. Visual and dimensional examinations shall be made at any point or during any phase of the manufacturing process to determine whether construction details which cannot be examined in the finished product are in accordance with requirements specified in Section 3. Materials and components which can be classified as having a defect in accordance with Table VI, shall be removed from production.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

4.3.1.2 Inspection conditions. Unless otherwise specified in this specification, all inspections shall be performed in accordance with the test conditions specified in Section 4 of this document.

4.4.1 Component and material testing. The components for the gloves shall be tested in accordance with the test methods specified in Table V. Unless otherwise specified in the applicable test method, all tests shall be performed under conditions in accordance with ASTM D1776/D1776M.

TABLE V. Component verification

Characteristic	Requirement Paragraph	Verification
Basic material:		
Cotton identification	3.2.1.1	AATCC TM20A
Yarn ply	3.2.1.1	visual 1/
Weave	3.2.1.2	visual 1/
Color	3.2.1.3	visual 1/
Weight	3.2.1.4	ASTM D3776/D3776M Option C
Tear strength	3.2.1.4	ASTM D1424
Stiffness	3.2.1.4	PIA-TM-5202
Air permeability	3.2.1.4	ASTM D737
Yarns per inch	3.2.1.4	ASTM D3775
Breaking strength	3.2.1.4	ASTM D5034
Flame resistance: Initially After 25 launderings	 3.2.1.4 3.2.1.4	 ASTM D6413/D6413M AATCC TM96 VIc, ASTM D6413/D6413M
Finish, napped	3.2.1.5	visual 1/
Nonfibrous material	3.2.1.6	AATCC TM20A
Dimensional stability	3.2.1.7	AATCC TM96 VIc
pH	3.2.1.8	AATCC TM81
Elastic webbing	3.2.2	All tests in accordance with Type II, Class 2 of JJ-W-155
Thread	3.2.3	All tests in accordance with Type I of A-A-50199 or Type I of A-A-52094
Label	3.2.4	All tests in accordance with Type III or IV, Class 15 of MIL-DTL-32075, except that for colorfastness, only the colorfastness to laundering test shall be required.
Barcode label/tag	3.2.5	All tests in accordance with Type VIII, Class 17 of MIL-DTL-32075

1/ One determination shall be made on each sample unit and the result reported as “pass” or “fail”.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

4.4.2 Examination of the end item. Examination of the end item shall be in accordance with 4.4.2.1 through 4.4.2.2.

4.4.2.1 End item visual examination. The gloves shall be subjected to visual examination. All defects shall be scored in accordance with Table VI.

TABLE VI. Visual examination defects

Examination	Defect	Classification	
		Major	Minor
Material Defects and Damages	Any hole, cut, tear, smash, mend, needle chew, burn, drill hole	101	
	Any visible mend, float, loose yarn, snag, knot, large slub, misweave, missing yarn, broken yarn, thin place, or woven in waste		201
	Ruptured fibers in line of stitching (caused by a blunt or broken needle)	102	
Cleanness	Any spots or stains on outside		202
	Thread ends not trimmed to 1/2 inch or less on inside (except the 1/2-to-3/4-inch chain extension required on 401 stitching), or thread ends not trimmed to 1/4 inch or less on outside		203
	Loose threads not removed throughout major portion of glove		204
Components and Assembly	Any component not as specified	103	
	Any operation not as specified (unless otherwise classified herein)		205
	Any component part or required operation omitted (unless otherwise classified herein)	104	
	Any component part tight, twisted, distorted, pleated, full, misshaped, puckered or not securely affixed (unless otherwise specified herein)		206

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE VI. Visual examination defects (continued)

Examination	Defect	Classification	
		Major	Minor
Cutting	Any component part not cut in accordance with directional lines indicated on patterns or not in accordance with specification requirements	105	
Seams and Stitching	Accuracy of seaming:		
	Seam puckered, pleated, irregular, wavy, or edges not fully worked out		207
	Part of glove caught in any unrelated operation or stitching	106	
	Needle perforations visible on outside more than one inch		208
	End of seam or stitching when not caught in another seam or stitching not securely backtacked or backstitched less than 3/8 inch		209
	Looper thread of 401 stitch type on outside		210
	Gage of stitching and seam allowance:		
	Stitching irregular, not within range specified or varies more than 1/16 inch when no range is specified (score only when condition exists on more than one half of the length of the seam)		211
	Width of seam allowance varies more than 1/16 inch from allowance specified (score only when condition exists on more than on half of the length of the seam)		212
	Open seam: 1/		
	Any open seam not repaired, except on gauntlet hem	107	
	Open seam repaired, but not repaired as specified		213
	Open stitching on gauntlet hem		214
	Runoff, skipped, or broken stitches: 1/		
	On joining seam - when resulting in an open seam is "open seam" classification		215

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE VI. Visual examination defects (continued)

Examination	Defect	Classification	
		Major	Minor
Seams and Stitching (continued)	Seam and stitch type:		
	Not specified seam or stitch type	108	
	Any line of stitching omitted or insecure		216
	Any line of stitching not beginning or ending where specified (unless otherwise classified herein)		217
	Stitch tension:		
	Loose tension resulting in an open seam:		
	More than one inch	109	
	Up to 1 inch inclusive		218
	Loose tension resulting in loose or tangled loops of lower or top thread		219
	Tight tension (stitches break when normal strain is applied in the direction of the seam or stitching)	110	
	Stitches per inch, on major portion of seam or stitching: 2/		
	More than the maximum specified:		
	Damaging assembly	111	
	Not damaging assembly		220
	Less than the minimum specified:		
	By one or two stitches per inch		221
	By three or more stitches per inch	112	
	Back tacking:		
	Missing insecure, misplaced, not serving intended purpose		222
	Loose stitch tension		223

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

TABLE VI. Visual examination defects (continued)

Examination	Defect	Classification	
		Major	Minor
Gauntlet	Elastic webbing for the wrist or elbow take-up not securely caught in closing of the gloves	113	
Bottom Hem	Finished hem less than 5/8 inch or more than 7/8 inch in width	114	
	Irregular in width by more than 1/8 inch		224
	Twisted, puckered, or pleated		225
Label	Missing, incorrect or illegible:		
	On one glove		226
	On both gloves	115	
	Misplaced		227
Pairing	Mispaired, i.e., two left or two right hand gloves submitted as a pair	116	
	Pair not tacked together		228
	Tacking too tight, i.e., not permitting the gloves to be pulled apart without tearing the fabric	117	
Bar Code Label/Tag	Barcode omitted or not readable by the scanner		229
	Human Readable Interpretation (HRI) omitted or illegible		230
	Not visible on folded, packaged item		231
	Causes damage to the item	118	

1/ One or more broken stitches or two or more continuous skipped or run off stitches constitutes an open seam.
2/ “Major portion” is defined as occurring on more than one half of the length of the seam or stitching.

THIS SPACE INTENTIONALLY LEFT BLANK

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

4.4.2.2 End item dimensional examination. The gloves shall be examined for dimensional defects in accordance with Table VII. Figure 1 is provided as a visual guide. The letters A, B, C, D, and E indicate the location of each measurement in the Figure 1. Any dimension that is not within the specified tolerance (see Section 3) shall be classified as a defect.

TABLE VII. Glove methods of measurement

Measurement Name	Measurement Description
Overall length (A)	Measurement taken from tip of second finger to edge of gauntlet opening.
Hand length (B)	Measurement taken from tip of second finger to gauntlet wrist seam.
Hand width (C)	Measurement taken on palm side from thumb crotch seam to folded edge.
Wrist width (D)	Measurement taken at gathered wrist from folded edge to folded edge, with elastic in relaxed state.
Elbow width (E)	Measurement taken at gauntlet bottom from folded edge to folded edge, with elastic in relaxed state.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful but is not mandatory.)

6.1 Intended use. The gloves covered by this specification are intended to be worn by Naval personnel to protect the hands and forearms exposed to transient elevated temperatures and flash from weapons, and will be used with Hood, Anti-Flash, Flame Resistant (MIL-H-24936).

THIS SPACE INTENTIONALLY LEFT BLANK

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

6.2 Acquisition requirements. Acquisition documents should specify the following: Title, number, and date of this military specification:

a. Quantity (see 1.2) National stock number
b. When first article is required (see 3.1)
c. Number of first article inspection samples (see 4.2)
d. Name and address of the first inspection facility; and the name and address of the Government activity responsible for conducting the first article inspection program.
e. Packaging required (see 5.1)
f. Specific issue of individual documents referenced (see 2.2)
g. Inspection conditions
h. Conformance inspection and acceptable quality limits

6.3 Information requests. For access to information such as patterns, drawings, standard shade samples of cloth etc. go to the DLA Troop Support website for their Specification/Pattern/Drawing Request form, https://www.dla.mil/TroopSupport/ClothingandTextiles/SpecRequest.aspx. Complete the request form and then submit. Requests to use equivalent materials and/or components or to make changes to the pattern should be sent to the contracting officer for approval by the military service.

6.4 Subject term (key word) listing.

Cotton
Flannel
Treated
Gauntlet
Clute-cut

6.5 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes

Custodians:

Army – GL
Navy – NU
Air Force – 11

Preparing Activity:

DLA – CT

Project No.: 8415-2023-067

Review:

Navy – MC

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil/.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.

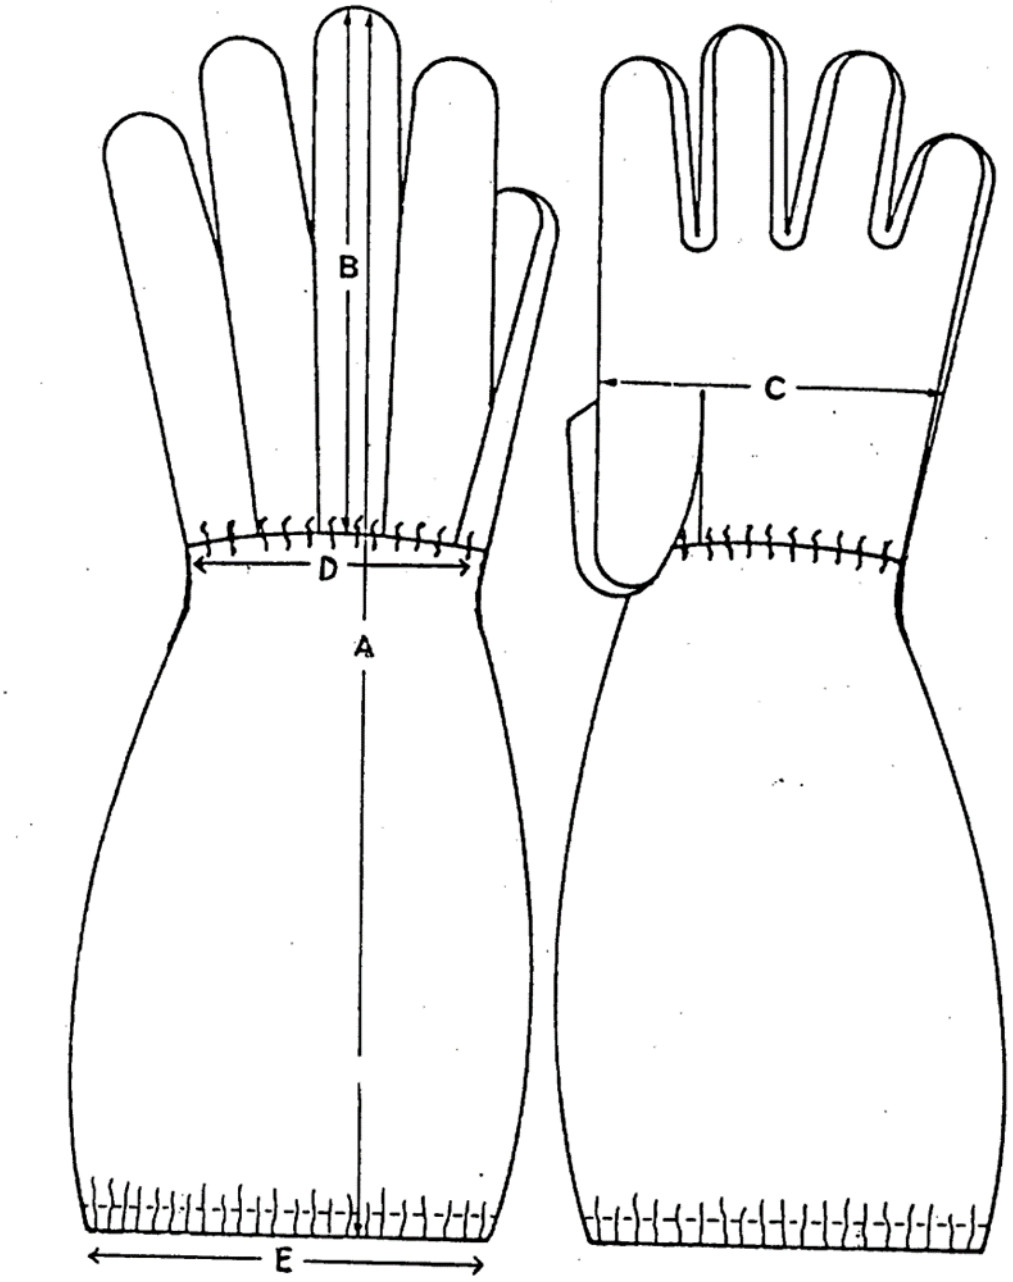


FIGURE 1. Gloves, anti-flash, flame resistant

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T15:50Z
Check the source to verify that this is the current version before use.