MILITARY SPECIFICATION

DIAPER, INFANT'S, PLEATED, DISPOSABLE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers two sizes of absorbent disposable diapers, of pleated construction, suitable for use in military hospitals.

1.2 Classification. The disposable diapers covered by this specification shall be of the following sizes, as specified.

Size 1 Diaper, Infant's, Pleated, Disposable, 13 inches long by 9-3/8 inches wide.

Size 2 Diaper, Infant's, Pleated, Disposable, 16 inches long by 11-7/8 inches wide.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

SPECIFICATIONS

Federal

PPP-B-636 Box, Shipping, Fiberboard

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the currentversion before use.

STANDARDS

Military

MIL-STD-105	Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	Marking for Shipment and Storage

(Copies of specifications, standards, drawings and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Material.

3.1.1 Nonwoven fabric facing. The nonwoven fabric facing shall be a porous hydrophobic facing sheet made of 1.5 to 3.0 denier rayon, and containing 20 to 35 percent acrylic binder. The facing sheet shall have a minimum weight of 15 grams per square yard.

3.1.2 Polyethylene film. The polyethylene film shall be made of virgin materials, embossed, of low density polyethylene, and shall be not less than 0.8 mils thick on embossed material at any point. The thickness shall be tested as specified in 4.5.1. Film may be blue, white or colorless. If colored, the pigment shall be mixed with the polyethylene resin, before the latter is made into film. The resulting film shall not run or bleed when tested in boiling water as specified in 4.5.2.

3.1.3 Absorbent wadding. The absorbent wadding shall be made from fully bleached chemical pulp, soft white (no color or dye added), substantially free of stock spots, slime spots, oil and dirt.

3.1.4 Tissue. Two sheets of tissue, made . om chemical pulp, shall be supplied for each diaper. The tissue shall be ubstantially free of stock spots, slime spots, oil and dirt. One of the sheets shall contain a wet strength resin. The sheets, as a minimum, shall be as large as the rectangle of wadding.


3.1.5 Fastening tapes. Each diaper shall be provided with two fastening tapes. The tapes shall be paper-back with a natural rubber-base adhesive. Overall dimensions shall be 1-3/4 ± 1/8 inches by 3/4 ± 1/8 inch for size 1, and 2-1/8 ± 1/8 inches by 1 ± 1/8 inch for size 2.

Source: https://assist.dla.mil -- Downloaded: 202640-21T09:59Z
Check the source to verify that this is the currentversion before use.

3.1.6 Release tapes. Each diaper shall be provided with two release tapes. The release tapes shall be polypropylene based tape with a natural rubber-based adhesive. Dimensions shall be 1-3/8 ± 1/8 inches by 3/4 ± 1/8 inch for size 1, and 1-5/8 ± 1/8 inches by 1 ± 1/8 inch for size 2.


3.2 Construction. The diaper shall consist of five layers; a non-woven fabric facing, a wet strength tissue, an absorbent pad, a tissue backing for absorbent pad, and a polyethylene backing. All layers except the polyethylene backing shall be of the same width. The non-woven fabric facing shall be a minimum two inches longer than the absorbent pad. The wet strength tissue shall be approximately two inches longer than the absorbent pad. The wet strength tissue shall be folded back on itself approximately one inch at the top and the bottom and placed next to the non-woven fabric facing. The non-woven fabric facing shall be wrapped around the top and bottom of the wet-strength tissue, the absorbent pad, and the tissue backing, forming a sandwich arrangement, and secured by means of adhesive to the bottom face of the tissue facing along the top and bottom edges of the assembly. The adhesive used shall be a plasticized hot melt adhesive. The polyethylene backing shall be larger in width and length, by approximately three inches, than the absorbent pad assembly. The polyethylene backing sheet shall be folded over the long sides of the absorbent pad assembly, approximately one inch on each side, and secured to the non-woven fabric facing by means of plasticized hot melt adhesive along the full length of the absorbent pad assembly. The adhesive seal shall continue to the ends of the polyethylene sheet at all four corners. The embossed side of the polyethylene backing sheet shall be on the outside. The diaper shall be provided with fastening tapes at one end, near the edge of the absorbent pad, perpendicular to the lengthwise centerline of the diaper. The fastening tape end of the diaper shall be reinforced by securing the absorbent pad assembly to the polyethylene backing by two lines of adhesive, extending a minimum of three inches from the edge of the opened polyethylene toward the lengthwise center line of the diaper assembly, along the edge of the absorbent pad assembly. Construction shall be as shown in Figures 1, 2 and 3. After assembly the diaper shall be folded as indicated in Figures 4 and 5. Spots of adhesive shall be placed where indicated in Figure 4 prior to folding so that after folding, the inner narrow sections shall be secured to the side sections along a line at right angles to the length of the diaper. The locations of the spots of adhesive should be 4-1/2 to 6 inches from the untaped end for size 1, and 5-3/4 to 7-3/4 inches for size 2 diaper.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

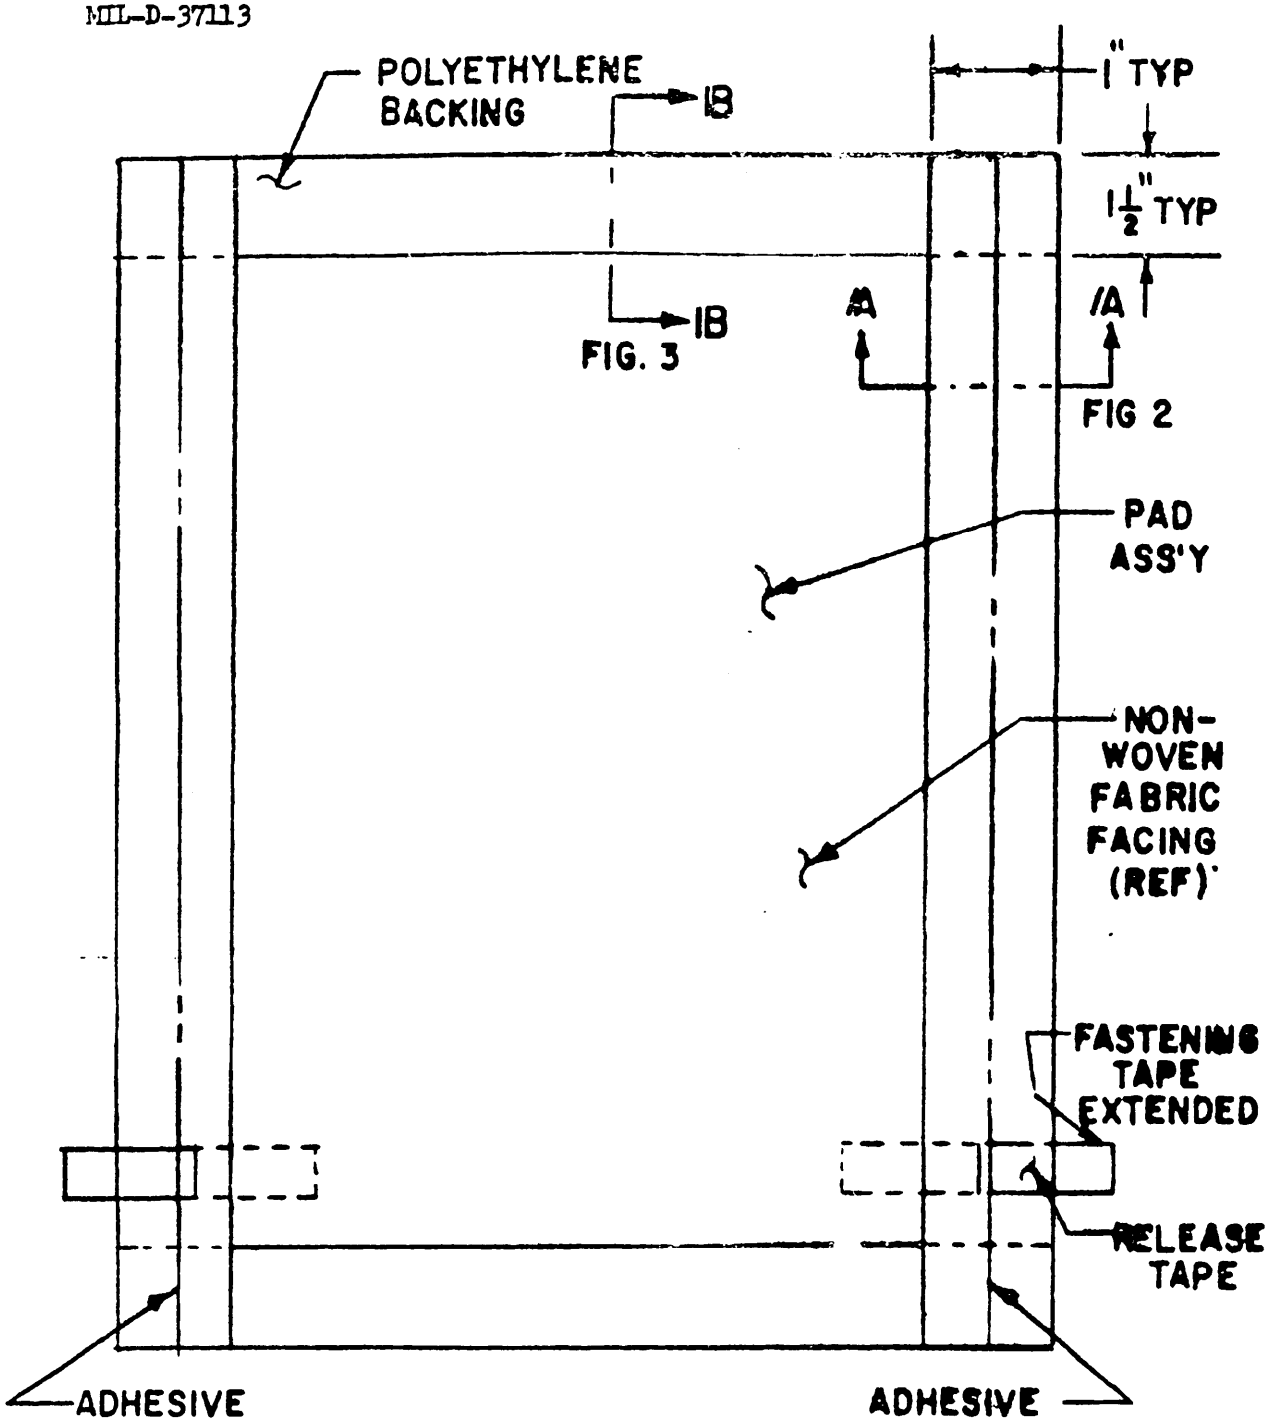

DIAPER ASSEMBLY
FIGURE 1


Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

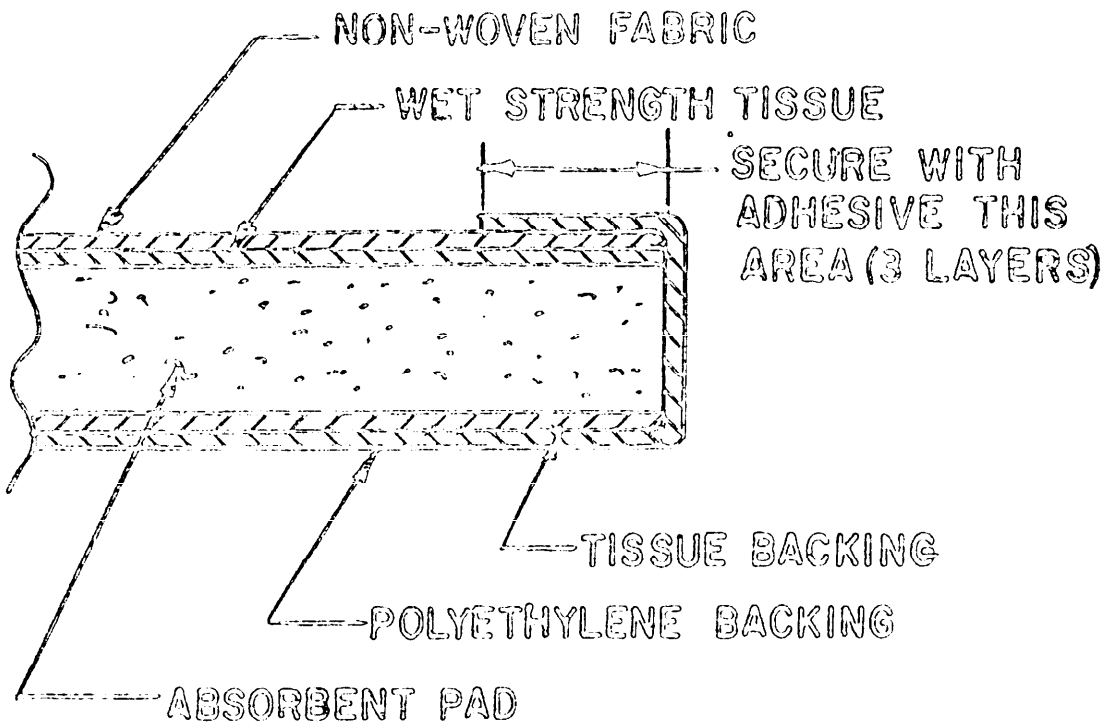

SECTION A-A

FIGURE 2


Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

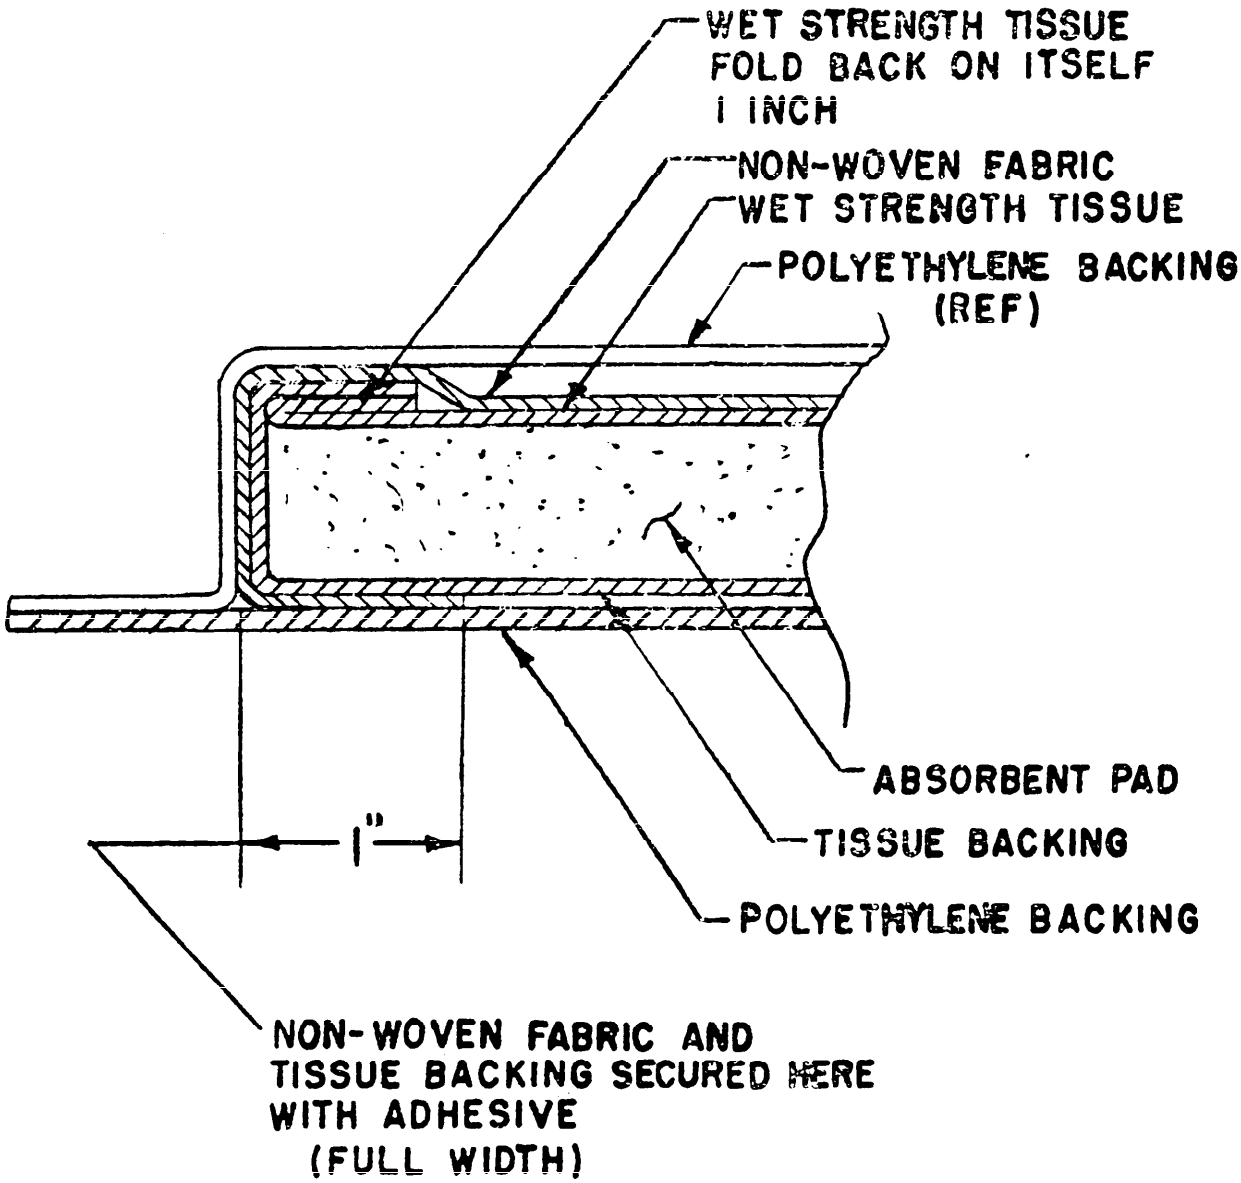

SECTION B-B

FIGURE 3


Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

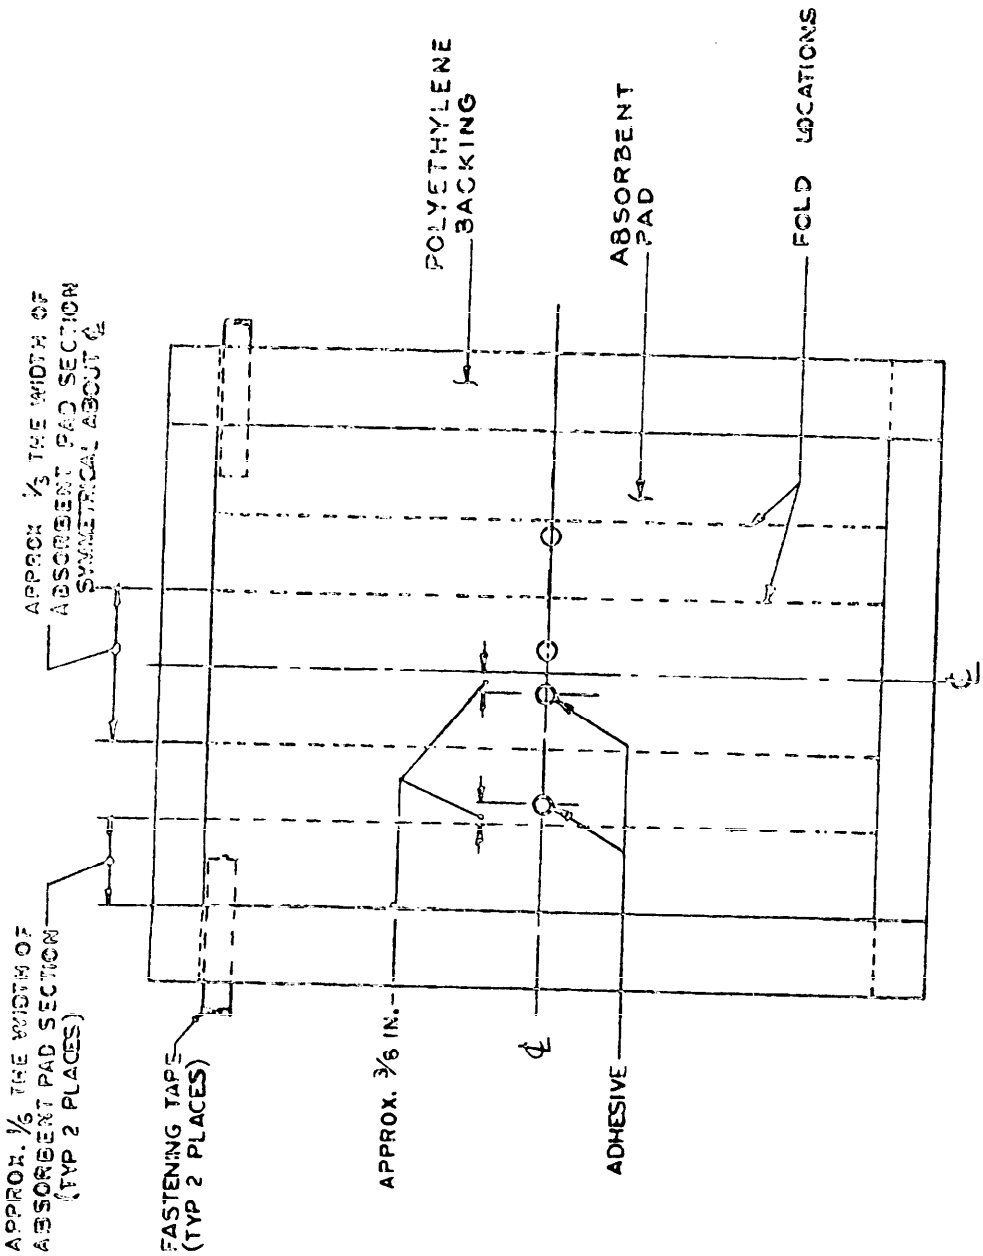

DIAPER PLEATS

FIGURE 4

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

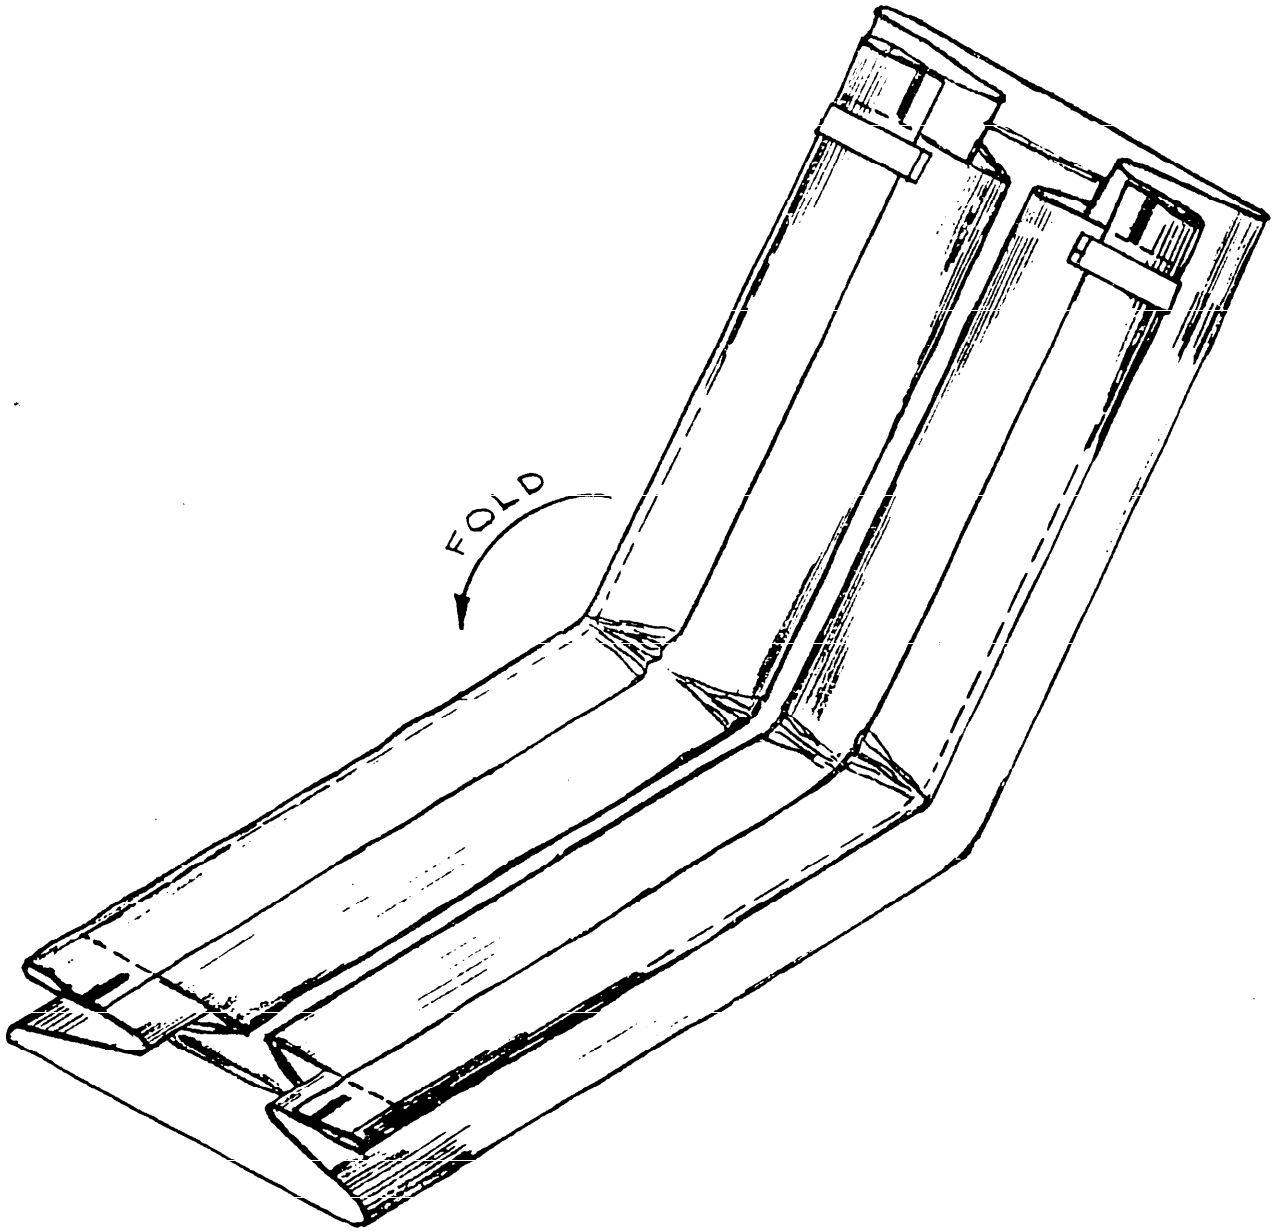

PLEATED DIAPER

FIGURE 5

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

3.3 Finished diapers.

3.3.1 Size 1 diapers. Size 1 diapers shall measure 13 ± 1/4 inches long by 9-3/8 ± 3/16 inches wide. Dimensions shall be measured on the absorbent pad assembly.

3.3.2 Size 2 diapers. Size 2 diapers shall measure 16 ± 1/4 inches long by 11-7/8 ± 3/16 inches wide. Dimensions shall be measured on the absorbent pad assembly.

3.4 Absorbency.

3.4.1 Absorbency rate. The absorbency rate is the length of time water will remain on the hydrophobic non-woven top fabric before it is absorbed into the very absorbent underlying layer. When tested as specified in 4.5.6 the maximum time for absorption shall be 8 to 10 seconds.

3.4.2 Absorptive capacity. Absorptive capacity determines how much water is absorbed by a sample of absorbent material. When tested as specified in 4.5.7, those values shall be as follows.

Absorptive capacity at 1.0 psi = 5.5 grams of water per gram of absorbing material (minimum).

Absorptive capacity at 0.0 psi = 11.0 grams of water per gram of absorbing material (minimum).

3.5 Instructions. Instructions for use shall be printed on each carton.

3.6 Odor. The diaper may be slightly scented.

3.7 Workmanship. Workmanship shall be first class throughout. The finished diapers shall conform to the quality of product established by this specification. The occurrence of defects shall not exceed the limits set by the applicable quality levels. The finished diapers shall be free from cuts, tears, pinholes and other defects which detract from their appearance or may impair their serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

4.1.1 Inspection. Inspection, as used in this specification, is defined as both examination (such as visual or auditory investigation without the use of special laboratory appliances or procedures) and testing (determination by technical means of physical and chemical properties) of the item.

4.1.2 Maintenance of records. Records of examinations and tests performed by or for the contractor shall be maintained by the contractor and made available to the Government, upon the Government's request, at any time, or from time to time, during the performance of the contract and for a period of 3 years after delivery of the supplies to which such records relate.

4.1.3 Certificates of quality. Certificates of quality, supplied by the manufacturer of the nonwoven fabric facing, polyethylene film, and absorbent cellulose wadding, may be furnished in lieu of actual performance of such testing by the contractor, provided lot identity has been maintained and can be demonstrated to the Government. The Certificate shall include the name of the contractor, the contract number, the name of the manufacturer or supplier, the NSN, the item identification, the name of the component/material, the lot number, the lot size, the sample size, the date of testing, the test method, individual test results, and the specification requirements.

4.2 Sampling.

4.2.1 For examination. Sampling for examination shall be conducted in accordance with MIL-STD-105. The inspection levels and acceptable quality levels shall be as indicated in Table I. The unit of product for examination purposes shall be 1 diaper.

Table I. Sampling for Examination

Type defect	Inspection level	AQL percent defective
Major	S-2	4.0
Minor	S-2	10.0

4.2.2 For tests. Sampling for tests shall be conducted in accordance with MIL-STD-105 and Table II, except that the acceptance number shall be zero for all sample sizes. The unit of product for test purposes shall be 1 diaper.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the currentversion before use.

Table II. Sampling for Tests

Component or End Item	Characteristic	Requirement	Test Procedure	Inspection Level	AQL
Nonwoven Material	Denier of rayon	3.1.1	4.5.3	1/	5/
	Percent acrylic	3.1.1	4.5.5	1/	5/
	Weight per square yard	3.1.1	4.5.4	3/	5/
Polyethylene film	Thickness	3.1.2	4.5.1	4/	5/
Diaper	Bleeding	3.1.2	4.5.2	1/	5/
	Absorbency Rate	3.4.1	4.5.6	2/	5/
	Capacity	3.4.2	4.5.7	2/	5/

1/ Run once per lot
2/ Run 5 times per lot
3/ Run 10 times per lot
4/ Run 15 times per lot
5/ Acceptance number shall be zero for all sample sizes

4.3 Examination.

4.3.1 Examination of diaper. The diaper shall be examined to determine compliance with specification requirements. Examination shall be conducted in accordance with MIL-STD-105 and Table III. Examination shall include, but shall not be limited to those listed.

Table III. Classification of defects

Categories	Defects
Major	
101	Diaper not complete with all component parts
102	Components not properly assembled
103	Bonds defective. a. Both center bonds must be present b. Bonds must be strong enough that they do not come loose when the ends of pad are fanned out for inspection.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

Table III. Classification of Defects (Cont'd)

Categories	Defects
Major (Cont'd)	
104	Poor Z-fold. Gross malformation (pad so narrow that pad fold is not covered by polyethylene at all) of the pad materially affecting appearance and/or performance.
105	Weak or no adhesive. The polyethylene sheet shall be attached the entire length of the absorbent pad to within 1 inch of the ends of the absorbent pad, and shall not come off easily when shaken while holding the polyethylene.
106	Dirty, not clean appearance. a. Fabric dirt. Foreign material actually made in the fabric and visible to the casual observer when viewed under reflected light. b. Glue drips/blobs. Large or off color adhesive drip/blobs. c. Dirt. Foreign material actually made in the raw material and visible to the casual observer when viewed under reflected light. d. Converting dirt. Foreign material from the converter on or between the layers of the product and visible to the casual observer when viewed under reflected light.
Minor	
201	Dimensions not in accordance with requirements.
202	Components not properly aligned.
203	Short end flaps. End flaps must extend 1/8 inch or more beyond the pad.
204	Polyethylene folds. The distance between the edge of the absorbent pad and the side crease of the polyethylene must be less than 3/8 inch within the 5 inch center section of the pad and less than 5/8 inch at the end of the pad.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

Table III. Classification of Defects (Cont'd)

Categories	Defects
Minor (Cont'd)	
205	Polyethylene roll. Polyethylene flaps must not be doubled over in any manner such that less than 3/4 inch of polyethylene is inwardly turned when measured from the side polyethylene crease.
206	Misplaced center bond. The center bond shall be 4-1/2 to 6 inches from the untaped end for size 1 and 5-3/4 to 7-3/4 inches for size 2.
207	End fold out. Fabric must be turned over the absorbent pad the entire width of the pad at the ends.
208	Final fold. The ends of the folded pad must be no more than 1-1/2 inches apart.
209	Stumbles. Any corner folded over that protrudes 1/4 inch or more inwardly past the edge of the polyethylene side flap.
210	Absorbent pad not free of stock spots; slime spots, oil, and dirt. Any of these foreign materials having a size greater than 0.002 square inch and found at a frequency of more than one per 144 square inches. This inspection is to be made under reflected light.
211	Torn fabric. No holes, tears, or slits are permitted on the top surface of the fabric topsheet.
212	Polyethylene holes. No holes of any size are permitted within the 5 inch center section of the polyethylene across the width and extending out into the polyethylene side flaps 1/2 inch from the pad. Portions of the polyethylene not specifically mentioned above may not contain holes or tears more than 1/16 inch in length and/or diameter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

4.3.2 Examination of preparation for delivery. An examination shall be made to determine whether the packaging, packing, and marking comply with the requirements of Section 5. Defects shall be scored as specified in Table IV. Sampling shall be in accordance with MIL-STD-105. The sample unit shall be one container fully prepared for delivery. The lot shall be the number of containers offered for inspection at one time. The inspection level shall be S-2 and the acceptable quality level shall be 4.0 defects per hundred units.

Table IV. Examinaton of preparation for delivery

Examination	Defect
Containers	Not as specified.
Quantity	Quantity in interior packages and shipping containers not as specified.
Packaging & packing materials	Any component missing or damaged.
Workmanship	Inadequate application of components, such as incomplete closure of container flaps, tape improperly applied, or containers distorted.
Markings	Omitted, incorrect, illegible, improper size, location, sequence, or method of application.

4.4 Component materials. Sufficient samples of the component materials shall be selected from each lot of material used in the manufacture of the diapers to perform tests as required by the applicable subsidiary specifications and by tests specified herein. When sample size for component materials covered by the subsidiary specifications is not specified, the sample size for each test shall be as indicated in 4.2.2. The unit of product for testing shall be the quantity of material necessary to perform all required tests one time each, taking into consideration the fact that, where possible, the same material may be used for the determination of two or more test characteristics. Where practical the term "lot" may be interpreted to encompass the total production run under a contract.

4.5 Tests. Tests shall be conducted to determine compliance with specification requirements. Where possible, the same sample unit may be used for the determination of two or more tests.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T09:59Z
Check the source to verify that this is the current version before use.

4.5.1 Minimum polyethylene film thickness. The test specimen shall be from an unembossed sheet of polyethylene film of a size commensurate with the lot of diapers. A total of fifteen measurements shall be made on one specimen. The measurements shall be equally spaced throughout the specimen. All measurements shall be a minimum of 1/4 inch from the edge of the specimen. The measurements shall be made by placing the specimen on the anvil of the micrometer and the presser foot lowered gently until it contacts the surface of the specimen. The presser foot shall be adjusted to exert a steady pressure of 7.0 to 9.0 pounds per square inch gage (psig) on the surface of the specimen. The flat anvil shall have a minimum diameter of 0.25 inch and the flat presser foot shall be 0.56 to 0.65 inch in diameter. The thickness of the specimen shall be read from the indicator dial to the nearest 0.001 inch. The surface of the anvil and the presser foot shall be parallel within 0.0001 inch. The minimum thickness shall conform to 3.1.2.

4.5.2 Non-bleeding test. If the polyethylene film is pigmented, a two inch square piece of film shall be boiled in water for five minutes. The boiled film shall meet the requirements of paragraph 3.1.2. One sample shall be tested from each lot.

4.5.3 Denier of non-woven fabric facing. Denier (yarn number) shall be determined in accordance with ASTM D-1577 Method A (Vibroscope Method) - Linear Density of Textile Fibers.

4.5.4 Minimum weight per square yard of fabric facing. Minimum weight of non-woven fabric facing shall be determined in accordance with ASTM Method D646, Basis Weight of Paper and Paperboard, except results shall be reported in grams per square yard. The samples from each lot shall be tested for basis weight.

4.5.5 Acrylic binder, nonwoven fabric. Percent acrylic binder in nonwoven fabric shall be determined as follows:

4.5.5.1 Solutions: Sodium Bicarbonate, 2 percent made with Sodium Bicarbonate, analytical reagent. Solution shall be stabilized at 40°F (4.4°C) before use. Sulfuric acid 72.1 percent, made with analytical reagent grade sulfuric acid. Water-Distilled, room temperature.

4.5.5.2 Procedure. Using an analytical balance, weigh 1 ± 0.05 grams of sample. Cut the sample into approximately 1/16 inch squares, and drop then into a 250 ml. beaker. Using a graduated cylinder, add 100 ml of 72.1 percent H_2SO_4 solution to the beaker. Heat the contents of the beaker on a hot plate to 38 ± 3° C. for 15 minutes, and stir the contents frequently. Transfer the contents of the 250 ml. beaker into a 600 ml. beaker containing 250 ml. of distilled water. Rinse the 250 ml. beaker 3 to 4 times with distilled water and transfer the rinsings to the 600 ml. beaker. Using a filtering flask and water aspirator, filter the contents of the 600 ml. beaker through a dry tared fritted glass crucible. Using a filled 100 ml.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

graduated cylinder, wash the residue in the crucible with portions of refrigerated distilled water. Reduce the vacuum on the flask and allow at least 5 minutes to rinse the contents of the crucible with 100 ml. of refrigerated 2 percent sodium bicarbonate. Using a filled 100 ml. graduated cylinder, again wash the contents of the crucible with portions of refrigerated distilled water. Dry the crucible and residue in a 103 + 2° C. oven to constant weight (or if convenient, overnight in the oven). Cool in a desiccator and weigh on an analytical balance.

4.5.5.3 Calculations: Percent Binder =

$$\frac{\text{Weight of crucible and residue - Weight of crucible}}{\text{sample weight (as is)}} \times 100$$

4.5.6 Absorbency rate test.

4.5.6.1 Preparation. Open diaper and lay it flat on a table with the top sheet facing upward. Cut a 4 in. x 4 in. sample pad. Make sure that this pad is cut above the center glue line and approximately equidistant from the sides of the diaper.

Cut four more test samples from four more diapers.

Set up a ring stand for the separatory funnel so that the tip of the funnel will be about one inch above the base of the ring stand. Set up a burette so that the tip of the burette will be inside the separatory funnel.

Remove the burette and over a sink fill the burette including the tip with distilled water. Drain the burette to the zero mark and replace it so that the tip will be inside the separatory funnel.

4.5.6.2 Procedure. Slide one of the test pads under the funnel making sure that the tip of the funnel is a distance of one inch above the center of the test pad.

With the stopcock of the separatory funnel closed, drain 5 ml. of distilled water from the burette into the separatory funnel.

Open the stopcock of the funnel fully open and simultaneously start the timer.

The distilled water will form a "flat ball" that will remain on the surface of the non-woven fabric for a few seconds. This "flat ball" of water will be absorbed into the test pad. Stop the timer the instant the "flat ball" of water disappears. This will be noticeable because there will no longer be any convex tendency of the water droplet remaining.

Strike through time for this test is the time in seconds from the release of the water from the separatory funnel to the disappearance of the "flat ball" of water from the surface of the non-woven fabric area.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

Record the strike through time to the nearest 0.1 second. Repeat the procedure with the four remaining test pads.

4.5.6.3 Calculations. Strike through time = Average of 5 readings.

Report to the nearest 0.1 second.

4.5.7 Absorptive capacity test.

4.5.7.1 Preparation. Open a diaper and lay it on a table with the fabric topsheet facing upward. Using an Alfa cutter, cut a 3 in. x 4 in. pad with the 3 in. measurement cut parallel with the length of the diaper. Make sure that this pad is cut above the center glue line and approximately equidistant from the side edges. Remove the fabric topsheet and polyethylene layer from the pad. The top tissue and bottom tissue stay on the pad.

Place the sample on a torsion balance and weigh to the nearest 0.01 g. Record weight of sample to the nearest 0.01 g. as weight 1.


Weigh sample and polyurethane pad holder together and record weight to the nearest 0.01 g. as weight 2.

Place the polyurethane pad holder on the pegs of the inclined plane of the absorptive capacity tester (see Fig. 6). Place the sample on the polyurethane pad holder of the tester so that the three inch measurement runs from the top and to the bottom of the inclined plane. Turn on the flow of water and saturate the pad for 60 seconds, at a controlled rate of 500 $\pm$ 25 ml/min.

4.5.7.2 Procedure. Turn on the tester and allow the base plate to come to rest on the saturated sample for 45 seconds with a pressure of 1 lb./sq. in. The rate of descent of the base plate should be regulated at 1.0 $\pm$ 0.1 inch/second. Remove the excess water from the polyurethane pad holder with several pieces of discarded wadding without touching the airfelt sample. Place on a 4 inches long piece of wadding horizontally across the front of the polyurethane pad holder, keeping it out of the slots of the holder and changing it as it becomes saturated by the water draining from the test sample. This is important: Do not actually touch the wet sample. If the mopping material gets against the sample, it will remove water from the sample and thus reduce the absorbency reading.

After the 45 seconds has elasped, raise the base plate to its original position, and carefully remove the polyurethane pad holder and sample from the inclined plane. Holding the sample and pad holder horizontally, place it on a piece of absorbent material to remove the water adhering to the bottom of the pad holder. Carefully place the sample and pad of the torsion balance and weigh to the nearest 0.01 g. Record weight 3. Do not tip the sample and pad holder at any time because this may allow additional moisture to run off the sample. Replace the polyurethane pad

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the currentversion before use.

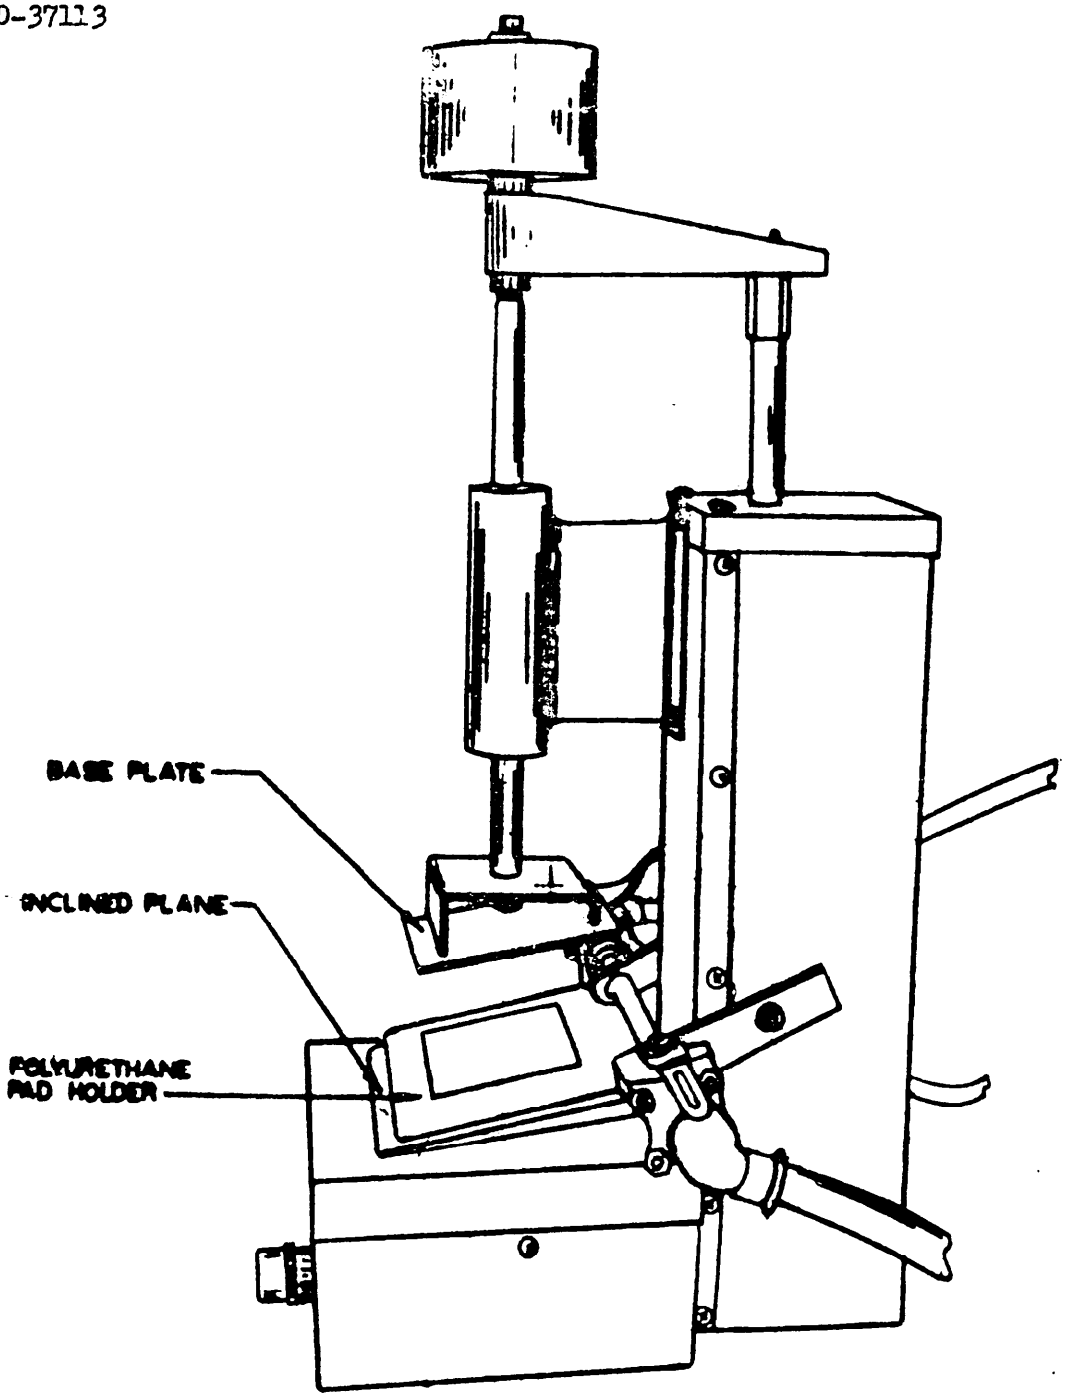

ABSORPTIVE CAPACITY TESTER

FIGURE 6

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

holder with the sample on the inclined plane. Again saturate the pad with water for 60 seconds at a controlled rate of 500 ml ± 25 ml. Allow the saturated pad to remain on the inclined polyurethane pad holder for an additional 45 seconds after the water has been turned off. During this time, remove the excess water as before, place it on absorbent material and again weigh the polyurethane pad holder and saturated sample. Record weight to the nearest 0.01 g. as weight 4.

4.5.7.3 Calculations.

$$\text{Absorption (1.0 psi)} = \frac{\text{Weight 3 (g)} - \text{Weight 2 (g)}}{\text{Weight 1 (g)}}$$

$$\text{Absorption (0.0 psi)} = \frac{\text{Weight 4 (g)} - \text{Weight 2 (g)}}{\text{Weight 1 (g)}}$$

Calculate results to the nearest 0.01 g and report results to the nearest 0.1 g. Result is the grams of water absorbed per gram of absorbing sample.

Check water flow before starting test by running water into a graduated cylinder for exactly 60 seconds. If water volume is not 500 ± 25 ml, adjust the flow and repeat procedure.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C as specified (see 6.1).

5.1.1 Unit of issue. One package containing 180 size 1 or 216 size 2 diapers, as specified, constitutes one unit of issue.

5.1.2 Level A.

5.1.2.1 Individual box. Thirty size 1 or twelve size 2 diapers shall be packaged in a paperboard box of appropriate size and design. Closure shall be adequate to prevent spilling of contents under normal handling.

5.1.3 Level C. Units shall be packaged in standard commercial containers of the size and kind commonly used, which will afford the degree of protection required for shipment and use of the product for its intended purpose.

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

5.2 Packing. Packing shall be level A, B or C as specified (see 6.1).

5.2.1 Level A. Six individual boxes containing thirty diapers each of size 1 diapers or eighteen individual boxes containing twelve diapers each of size 2 diapers shall be packed in an exterior container designed for a type 2 load and constructed in accordance with PPP-B-636, class weather-resistant. Closure, waterproofing and strapping shall be as specified in the appendix of PPP-B-636.

5.2.2 Level B. Diapers shall be packed as specified in 5.2.1 except that the exterior container shall conform to PPP-B-636, type CF, class domestic and method II closure as specified in the appendix of PPP-B-636 shall be utilized.

5.2.3 Level C. The subject commodity shall be packed in substantial commercial containers of the type, size, and kind commonly used for the purpose, so constructed as to insure acceptance and safe delivery by common or other carriers, at the lowest rate, to point of delivery called for in the contract or purchase order.

5.3 Marking.

5.3.1 Individual box. Each individual box shall be commercially marked.

5.3.2 Exterior container. Exterior container shall be marked in accordance with MIL-STD-129. In addition, marking shall include the contract or purchase order number and name and address of the manufacturer.

6. NOTES

6.1 Ordering data. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Sizes required (see 1.2).
(c) Selection of applicable levels of packaging and packing (see 5.1 and 5.2).
(d) National Stock Number (NSN).

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

6.2 This specification is intended to cover the following items listed in the Federal Supply Catalog:

National Stock Number	Item Identification
6532-00-493-3766	Diaper, Infant's, Pleated, Disposable, 13 inches long, by 9-3/8 inches wide, 180s
6532-00-493-3767	Diaper, Infant's, Pleated, Disposable, 16 inches long, by 11-7/8 inches wide, 216s

Custodians:
Army - MD
Navy - MS
Air Force - 03

Preparing activity:
Defense Supply Agency - DM

Project No. 6532-1088
cs

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

MIL-D-37113 DIAPER, INFANT'S, PLEATED, DISPOSABLE

NAME OF ORGANIZATION AND ADDRESS	CONTRACT NUMBER MATERIAL PROCURED UNDER A ☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO *(If "Yes", in what way?)*

4. REMARKS

SUBMITTED BY *(Printed or typed name and address - Optional)*	TELEPHONE NO DATE

DD FORM 1 JAN 72 1426 REPLACES EDITION OF 1 JAN 00 WHICH MAY BE USED

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.

FOLD

DEFENSE PERSONNEL SUPPORT CENTER
2800 South 20th Street
Philadelphia, PA. 19101

POSTAGE AND FEES PAID
DEFENSE SUPPLY AGENCY
DoD - 304

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

HEADQUARTERS, DEFENSE PERSONNEL SUPPORT CENTER
ATTN: DIRECTORATE OF MEDICAL MATERIEL, CODE ATT
2800 SOUTH 20TH STREET
PHILADELPHIA, PA 19101

FOLD

Source: https://assist.dla.mil -- Downloaded: 202610-21T09:59Z
Check the source to verify that this is the current version before use.