
FED SUP CLASS
5310

CONFIGURATION OF NUT OPTIONAL WITHIN THE LIMITATIONS IMPOSED BY DIM.'S AND REQUIREMENTS AS SPECIFIED HEREIN.

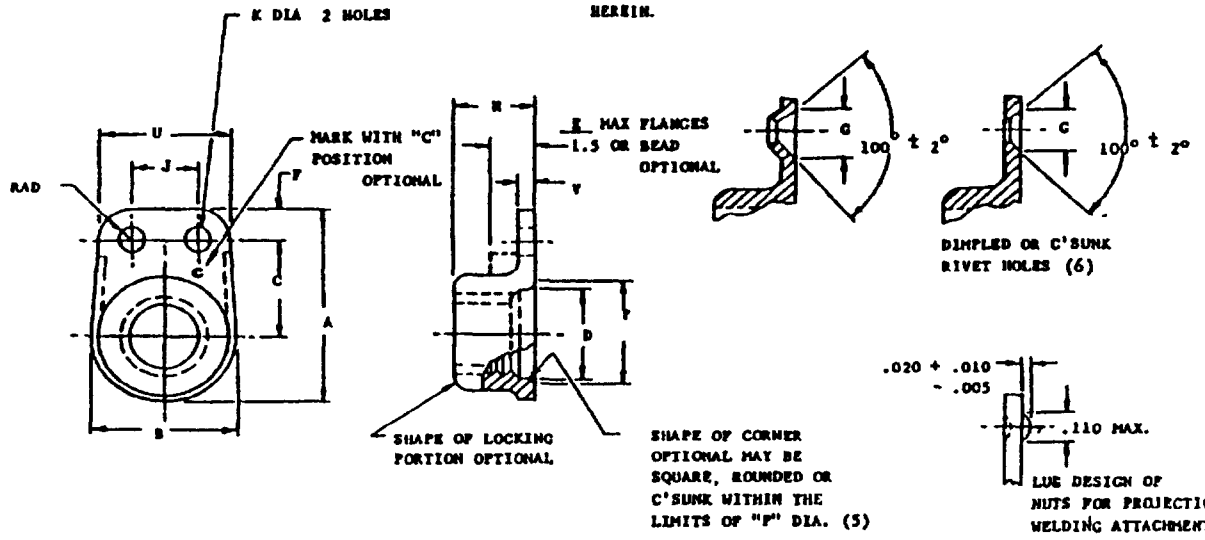

(1) (2) THREAD SIZE	A MAX.	B MAX	B MIN	(4) C ± .005	D MIN	(3) H MAX	F MIN	G DIA ± .010	U MAX	J ± .002	K(6) DIA + .005 -.000	P DIA MAX	V MAX	AXIAL STRENGTH LBS MIN	WEIGHT LBS/100
8-32 UNC-3B	.486	.297	.235	.234	.168	250	.100	.200	.437	.219	.098	.248	.047	1720	23
10-32 UNF-3B	.521	.328	.298	.250	.194	.250	.100	.200	.437	.219	.098	.274	.047	2460	28
1/4-28 UNF-3B	.591	.414	.380	.281	.254	.281	100	.200	.437	.219	.098	344	.055	4580	45
5/16-24UNF-3B	.747	.505	.475	.359	.317	.328	.125	.230	.537	.269	.130	.417	.065	7390	78
3/8-24UNF-3B	.856	.614	.580	.414	.379	.344	.125	.230	.537	.269	.130	.505	.075	11430	1 05

(1) THREADS IN ACCORDANCE WITH MIL-S-8879 BEFORE LUBRICATION
(2) THREADS IN ACCORDANCE WITH MIL-S-7742 ARE ACCEPTABLE UNTIL 31 DECEMBER 1969.
(3) MINIMUM "H" NOT SPECIFIED, LIMITED ONLY BY STRENGTH REQUIREMENT OF SPECIFICATION
(4) CENTER OF TAPPED HOLE SHALL NOT DEVIATE IN ANY DIRECTION FROM THE CENTER OF THE PLATE NUT AS DETERMINED BY THE RIVET HOLES BY MORE THAN .005.
(5) ON SIZE NO. 8 AND LARGER COUNTERBORE THREAD "D" DIA. X.062 DEEP MIN. THREAD RELIEF ON SIZE NO 6 AND SMALLER C'SINK TO "P" DIA. WITHIN THE LIMITS OF P AND D.
(6) DIMPLED RIVET HOLE TOLERANCE FOR "K" IS +.015 -.000.

(B) MATERIAL: CORROSION RESISTANT STEEL, (A286) AMS5735 OR AMS5737 OR AMS 5525.

HARDNESS: ROCKWELL C49 MAX

PLATING. 800°F NUTS. SILVER PLATE IN ACCORDANCE WITH AMS2410. PLATE THICKNESS, MEASURED ON ANY EXTERNAL SURFACE OF THE NUT, SHALL NOT BE LESS THAN 0.0002 IN. THREADS SHALL SHOW COMPLETE COVERAGE BUT THICKNESS REQUIREMENT ON THREAD IS WAIVED NO SILVER PLATE ON WELD NIBS.

LUBRICANT 450° NUTS, DRY FILM LUBRICANT IN ACCORDANCE WITH MIL-M-25027 ~~FOR USAF APPLICATIONS NUTS TREATED WITH DRY FILM LUBRICANTS SHALL NOT BE USED IN INTERNAL FUEL SYSTEMS. (NO SILVER PLATE.)~~

(B) MAGNETIC PERMEABILITY: SHALL BE LESS THAN 2.0 (AIR=1.0) FOR A FIELD STRENGTH H=200 OERSTEDS USING A MAGNETIC PERMEABILITY INDICATOR PER MIL-I-17214

DIMENSIONS IN INCHES UNLESS OTHERWISE SPECIFIED.

DESIGN AND USAGE LIMITATIONS: (B) THESE NUTS ARE DESIGNED TO DEVELOP THE TENSILE STRENGTH OF BOLTS AND SCREWS WITH AN ULTIMATE TENSILE STRENGTH OF 125 KSI BASED ON THE CROSS SECTION AREA AT THE BASIC ROOT DIAMETER OF THE THREADS. THESE NUTS ARE DESIGNED TO BE USED ON 3A EXTERNAL THREADS THESE NUTS SHALL BE USED IN ACCORDANCE WITH THE LIMITATIONS OF MS33588.

PERFORMANCE. SEE PROCUREMENT SPECIFICATION, EXCEPT 450°F DRY FILM LUBRICATED NUTS LIMITED TO FIVE REUSE CYCLES

SURFACE ROUGHNESS IN ACCORDANCE WITH ANSI/ASME B46.1, UNLESS OTHERWISE SPECIFIED, THE SURFACE ROUGHNESS SHALL NOT EXCEED 125 MICRO INCHES.

INTERCHANGEABILITY RELATIONSHIP: MS21087 NUTS CAN UNIVERSALLY REPLACE NAS1067 NUTS OF LIKE MATERIAL, THREAD SIZE, LUBRICANT (SILVER PLATE OR DRY FILM LUBRICANT), AND FASTENING METHOD (PLAIN RIVET HOLES; DIMPLED OR C'SUNK RIVET HOLES; OR PROJECTION WELDING). (B) BUT THESE NAS1067 NUTS CANNOT UNIVERSALLY REPLACE MS21087 NUTS.

(B) DENOTES CHANGES

APPROVED 5 April 65 REVISED (A) 15 FEBRUARY 1979 (B) 25 FEB 91

REVIEWER SYMBOLS: OLA - 15 USAF-99
USER SYMBOLS:
AMSC N/A
DISTRIBUTION STATEMENT A. APPR. FOR PUBLIC RELEASE, DISTRIBUTION IS UNLIMITED

P.A. NAVY - AS Other Cust USAF - 11 ARMY - AV	TITLE NUT, SELF-LOCKING, PLATE, SIDE BY SIDE REDUCED RIVET SPACING, LOW HEIGHT, CRES, 125 KSI FTU, 450° & 800° F.	MILITARY STANDARD MS21087
PROCUREMENT SPECIFICATION MIL-N-25027	SUPERSEDES IN PART NAS1067 (STATUS NOTE)	SHEET 1 OF 2

PROJECT NO 5310-1742

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T14:27Z
Check the source to verify that this is the current version before use.

FED SUP CLASS
5310

(8) BIDS SHALL BE SOLICITED ONLY FROM THE MANUFACTURERS LISTED ON QPL-25027.
(8) IN THE EVENT OF A CONFLICT BETWEEN THE TEXT OF THIS STANDARD AND THE REFERENCES CITED HEREIN, THE TEXT OF THIS STANDARD SHALL TAKE PRECEDENCE.
(8) REFERENCED GOVERNMENT (OR NON-GOVERNMENT) DOCUMENTS OF THE ISSUE LISTED IN THAT ISSUE OF THE DEPARTMENT OF DEFENSE INDEX OF SPECIFICATIONS AND STANDARDS (DoDISS) SPECIFIED IN THE SOLICITATION FORM A PART OF THIS STANDARD TO THE EXTENT SPECIFIED HEREIN.

THREAD SIZE	DASH NUMBERS					
	450°F			800°F		
	PLAIN HOLES	COUNTER SUNK OR DIMPLED HOLES	WELDING PROJECTION	PLAIN HOLES	COUNTER SUNK OR DIMPLED HOLES	WELDING PROJECTION
8-32UNC-3B	L08	L08K	L08W	-08	-08K	-08W
10-32UNF-3B	L3	L3K	L3W	-3	-3K	-3W
1/4-28UNF-3B	L4	L4K	L4W	-4	-4K	-4W
5/16-24UNF-3B	L5	L5K	L5W	-5	-5K	-5W
3/8-24UNF-3B	L6		L6W	-6	—	-6W

EXAMPLE OF PART NUMBERS

MS 21087 L4W

1/4-28UNF-3B NUT SELF LOCKING, ALL METAL DRY FILM LUBRICANT, C'SUNK OR DIMPLED RIVET HOLES, 450°F.

L4W — NUT DASH NUMBER

MS 21087 — STANDARD DESIGNATION NUMBER

APPROVED 5 April 65 REVISED (8) FOR CHANGES SEE SHEETS 1 AND 2

DLA - IS
USAF-99

DISTRIBUTION STATEMENT A. APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED

AMSC N/A

P A
NAVY - AS
Other Cust
USAF - 11
ARMY - AV

PROCUREMENT SPECIFICATION
MIL-N-25027

TITLE
NUT, SELF-LOCKING, PLATE, SIDE BY SIDE REDUCED RIVET SPACING, LOW HEIGHT, CRES, 125 KSI FTU, 450° & 800° F.

SUPERSEDES IN PART
MAS1063 (STATUS NOTE)

MILITARY STANDARD
MS21087
SHEET 2 OF 2

PROJECT NO 5310-1742

Source: https://assist.dla.mil - Downloaded: 2026-10-23T14:27Z
Check the source to verify that this is the current version before use.