INCH-POUND

MIL-C-24938A
10 August 1993

SUPERSEDING
MIL-C-24938
30 September 1988

MILITARY SPECIFICATION

COAT, FIREMEN'S, STRUCTURAL/ALUMINIZED PROXIMITY

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for a flame resistant structural fire fighters coat with a waterproof moisture barrier lining and a para-aramid/PBI blend outershell. In addition, the coat has a removable aluminized para-aramid cover for proximity use.

1.2 Classification. The coat covered by this specification shall be of the following types and sizes (see 6.2):

Type I - Coat, Firemen's, Structural

Type II - Coat Cover, Firemen's, Aluminized Proximity

Sizes.

Small (34-36)	Large (42-44)
Medium (38-40)	Extra Large (46-48)

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Defense Personnel Support Center, Clothing and Textile Directorate, Attn: DPSC-FSSD, 2800 South 20th Street, Philadelphia, PA. 19101-8419 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8415

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202640-20T03:08Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

A-A-50083	- Bag, Plastic, Folded Garment
A-A-50195	- Thread, Aramid
FF-R-556	- Rivets,Solid,Small; Rivets,Split,Small; Rivets, Tubular, Small; and Caps, Rivets, General Purpose
FF-W-92	- Washers, Metal, Flat (Plain)
QQ-N-290	- Plating, Nickel (Electrodeposited)
QQ-P-416	- Plating, Cadmium (Electrodeposited)
DDD-L-20	- Label; For Clothing, Equipage, and Tentage (General Use)
PPP-B-636	- Boxes, Shipping, Fiberboard

MILITARY

MIL-C-3735	- Cuffs, Knit, Wrist and Ankle, and Cloth Knitted
MIL-E-20652	- Eyelet, Metallic, Rolled Flange Type, and Eyelet Washer
MIL-F-21840	- Fastener Tapes, Hook and Loop, Synthetic
MIL-C-24929	- Cloth, Laminated, Aluminized (Para-Aramid Base)
MIL-C-24939	- Cloth, Ripstop, Para-aramid/PBI, Water Repellent
MIL-C-43774	- Cloth, Plain or Pajama Check Weave, Aramid
MIL-T-44100	- Thread, Para-Aramid, Spun, Intermediate Modulus

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-751	- Stitches, Seams, and Stitchings

Source: https://assist.dla.mil -- Downloaded: 20261O-20T03:08Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage
MIL-STD-147	- Palletized Unit Loads
MIL-STD-1666	- Classification of Defects for Evaluating Quality of Aluminized Firemen's Clothing
MIL-STD-2073-1	- DOD Materials Procedure for Development and Application of Packaging Materials
MIL-STD-2073-2	- Packaging Requirement Codes
MS-27980	- Fastener, Snap, Style 2

(Unless otherwise indicated, copies of federal specifications, standards, and other handbooks are available from the Standardization Documents Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.2 Non-government publications. The following document(s) form a part of this specification to the extent specified herein. Unless otherwise specified, the issue of documents which are DOD adopted shall be those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the document cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS

ASTM D 3951 - Standard Practice for Commercial Packaging

(Applications for copies should be addressed to American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA, 19103)

NATIONAL FIRE PROTECTION ASSOCIATION

NFPA 1971 Standard on Protective Clothing for Structural Fire Fighting 1991 Edition

NFPA 1976 Standard on Protective Clothing for Proximity Fire Fighting 1992 Edition

(Application for copies should be addressed to National Fire Protection Association, Batterymarch Park, Quincy, MA, 02269-9990).

WARNING

THE TYPE I STRUCTURAL COAT AND/OR TYPE II PROXIMITY COAT COVER WERE DESIGNED TO MEET NFPA STANDARDS, AND MUST MEET THIRD PARTY CERTIFICATION TO ASSURE CONSTRUCTION, COMPOSITE MATERIALS, AND PERFORMANCE REQUIREMENTS MEET SPECIFIED REQUIREMENTS. THE CONTRACTOR SHOULD OBTAIN A COPY OF THE APPLICABLE NFPA STANDARD FOR CERTIFICATION PROCEDURES.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

JOINT COMMITTEE ON PRINTING (JCP) PUBLICATIONS

Government Paper Specification Standards

(Applications for copies should be addressed to the Superintendent of Documents, U. S. Government Printing Office, Washington, DC, 20402.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence. Nothing in this document, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Guide sample. Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this specification may appear in the sample in which case this specification shall govern.

3.2 First article. When specified, the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3 and 6.2).

3.3 Materials.

3.3.1 Basic material, type I (structural coat). The basic material for the structural coat shall be a water repellent para-aramid/PBI ripstop fabric conforming to MIL-C-24939.

3.3.2 Basic material, type II (proximity coat cover). The basic material for the aluminized proximity coat cover shall be of a highly reflective aluminum surface laminated to a knitted para-aramid base fabric conforming to type II of MIL-C-24929.

3.3.3 Moisture Barrier. The moisture barrier material used for lining the structural coat and binding the facing on the structural coat, shall be undyed pajama check aramid fabric conforming to MIL-C-43774 except that anti-static finish is not required and shall be coated on one side only with a white chloroprene coating. The finished coated fabric shall conform to the physical requirements shown in Table I when tested as specified in 4.4.1 (see 6.5).

Source: https://assist.dla.mil -- Downloaded: 202640-20T03:08Z
Check the source to verify that this is the current version before use.

Table I Physical Requirements

Characteristic	Requirement Minimum	Maximum
Weight (oz/yd^2)	9.0	13.0
Breaking Strength (lbs)		
Warp	90.0	-
Filling	75.0	-
Tearing Strength (lbs)		
Warp	6.0	-
Filling	5.0	-
Hydrostatic Resistance (lbs/in^2)	25.0	-
Flame Resistance		
After Flame (sec)	-	2.0
Char Length (inches)	-	4.0

3.3.4 Cloth, abrasion resistant. The fabric used for the protective shoulder, sleeve tabs, reinforcing the snap hooks, for binding the sleeve edges, for pocket opening reinforcements on the proximity coat cover, and for button hole reinforcement on the proximity coat cover shall be constructed of a 100% para-aramid yarn, 2/1 right hand warp face twill, with a polymer blend coating on both sides of the fabric to finish with 12 ounces per square yard on the face side (grey shade) and 1.8 ounces per square yard on the back side. The finished coated fabric shall conform to the physical requirements specified in table II when tested as specified in 4.4.1 (see 6.6).

Table II - Physical Requirements

Characteristic	Requirement Minimum	Maximum
Weight (oz/yd^2)	18.0	23.0
Thickness (inches)	0.020	0.030
Breaking Strength (lbs)		
Warp	400.0	-
Filling	325.0	-
Tearing Strength (lbs)		
Warp	45.0	-
Filling	45.0	-
Flame Resistance, Vertical		
After Flame (sec)	-	2.0
Char Length (inches)	-	4.0
Abrasion Resistance, 2000 cycles		1/

1/ There shall be no visual exposure of the base fabric.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.5 Wrist cuffs. The material for the wrist cuffs shall be made of aramid conforming to type IV, class 2, of MIL-C-3735, except for the following requirements.

The aramid yarn is not required to be autoclaved prior to knitting and covering.

The elastic yarn shall be of a 140 denier spandex core covered with a texturized 70 denier nylon filament yarn.

The aramid wrist cuffs shall be constructed seamless in one size on a circular knit machine using a 1 X 1 rib stitch and with one end of the elastic yarn specified above laid in every sixth course throughout the cuff. The ends of the cuffs shall be tapered with a tuck or expanding stitch.

The Weight per dozen, ounces shall be 12.0

The finished measurement for Type IV, Class 2, Measurement B shall be 4-1/2 inches.

The finished measurement for Type IV, Class 2, Measurement D shall be 2 and 2-1/2 inches respectively.

3.3.6 Thread. The thread for assembling the coat shall be a 60 Tex aramid, natural shade, conforming to A-A-50195. As an alternate, a para-aramid thread conforming to size T-50 of MIL-T-44100, natural in color may be used.

3.3.7 Heat sealing tape. The 7/8 inch wide clear tape used for heat sealing the seams on the moisture barrier material shall be Electro Seal Corp Style #ST182 or equal (see 6.7 and 6.10).

3.3.8 Reflective tape. The reflective tape shall be in accordance with 3M style 8487 fluorescent lime/yellow, 3 inch wide or equal (see 6.8 and 6.10).

3.3.9 Hook and loop fastener tape. The hook and loop fastener tapes shall conform to type II, class 1 of MIL-F-21840. The tape shall be of either 5/8 inch, 1 inch, or 2 inch widths as specified in Tables III and IV. The color shall be natural, white or black.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.10 Hardware.

3.3.10.1 Fasteners, snap. The snap fasteners for attaching the snap-in liner shall consist of a button and socket (female half) and a stud and eyelet (male half). The fasteners shall be style 2, 24-line (size 1), nickel plate or bright chrome finish conforming to MS-27980 and the following part numbers:

Button - 1N or 1C	Socket - 6N or 6C
Stud - 7N or 7C	Eyelet - 8N or 8C

3.3.10.2 Eyelets and washers. The eyelets and washers for the pocket drain holes shall conform to rolled flange type, M20652/1-BBE114 and M20652/1-BBW101 of MIL-E-20652.

3.3.10.3 Snap hooks and D-rings. The snap hooks and D-rings for fastening the front closure of the coat shall be cast malleable iron, brass, aluminum, or zinc conforming to the style and measurement requirements specified in Figure. 3 (see 4.4.1). The finish for the malleable iron shall be cadmium plate conforming to type I, class 3, of QQ-P-416. The finish for the brass shall be nickel plate conforming to class 2, 0.0005 inch minimum thickness of QQ-N-290 (see 6.9).

3.3.10.4 Rivets, tubular with caps or washers. The rivets for attaching snaps and D-rings shall conform to type XII, class 3, grade B or F of FF-R-556, except that they shall be drilled to the head or partially drilled to the head and the inside of the rivet shank shall be chamfered. As an alternate, split rivets conforming to type XI, class 1, grade E of FF-R-556 may be used. The rivets shall be 9/64 inch nominal diameter and their length shall be sufficient to assure proper clinching. The caps shall conform to type II of FF-R-556. The finish for the brass or steel rivets and caps shall be nickel plate conforming to class 2 of QQ-N-290, except that the minimum thickness shall be 0.0005 inch. An aluminum washer conforming to type A, grade I, class C, No. 20 of FF-W-92 may be used in lieu of caps for securing the tubular rivets. The diameter of the aluminum washer shall be 0.170 to 0.180 inch for the inside and 0.470 to 0.500 inch for the outside.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.11 Labels.

3.3.11.1 Label, structural coat. Each structural coat shall have a combination size, instruction and identification label conforming to type VI, class 14 of DDD-L-20, except that the colorfastness requirements shall not apply. The label shall bear the following inscription:

COAT, FIREMEN'S, STRUCTURAL, (TYPE I)
FIBER CONTENT:
Outershell - 60% Para-aramid/40% PBI
Moisture Barrier - Aramid Chloroprene Coated
CONTRACT NO: DLA-100-00-0-0000 (EXAMPLE)
STOCK NO: 8415-00-000-0000 (EXAMPLE)
SIZE: MEDIUM (38-40) (EXAMPLE)
NAME OF CONTRACTOR:
NAME OF MANUFACTURER: (If other than contractor)

LAUNDERING INSTRUCTIONS
HAND WASH IN LUKE WARM WATER
DO NOT BLEACH
HANG TO DRY
DO NOT MACHINE WASH OR DRY CLEAN

WARNING

STRUCTURAL COAT MUST BE WORN WITH LINER INTACT AND ALL CLOSURES FASTENED WHEN IN USE. DO NOT KEEP IN DIRECT CONTACT WITH FLAME. DO NOT STORE THIS GARMENT IN DIRECT SUNLIGHT. KEEP GARMENT CLEAN AS SOILING WILL REDUCE PROTECTIVE QUALITIES. FAILURE TO COMPLY WITH THESE INSTRUCTIONS MAY RESULT IN SERIOUS INJURY OR DEATH.

DO NOT REMOVE THIS LABEL

3.3.11.2 Warning label, structural coat. Each structural coat shall have a warning label conforming to type IV, class 9 of DDD-L-20 applied to the inside back moisture barrier. The label marking shall be applied to the moisture barrier by a red marking medium. The label shall be printed with block sansserif type with letters 3/4 to 1 inch in height. The label shall contain the following inscription:

WARNING
MUST BE WORN WITH
LINER IN PLACE

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.11.2.1 NFPA approval label, structural coat. Each structural coat shall have a NFPA approved label conforming to type VI, class 3, of DDD-L-20. The label shall contain the following inscription:

THIS STRUCTURAL PROTECTIVE GARMENT, MEETS THE REQUIREMENTS OF NFPA 1971 STANDARD ON PROTECTIVE CLOTHING FOR STRUCTURAL FIREFIGHTING, 1991 EDITION.

WARNING

FOR STRUCTURAL FIREFIGHTING OPERATIONS, BOTH THE STRUCTURAL COAT AND TROUSERS MUST BE WORN OVER THEIR APPLICABLE AND DETACHABLE LINERS FOR LIMB/TORSO PROTECTION. OUTER SHELL, MOISTURE BARRIER, AND THERMAL BARRIER MEETING ALL REQUIREMENTS OF NFPA 1971 MUST BE UTILIZED AND ALL GARMENT CLOSURES MUST BE FASTENED WHEN IN USE. DO NOT KEEP THIS GARMENT IN DIRECT CONTACT WITH FLAMES. THIS GARMENT ALONE MAY NOT PROVIDE PROTECTION FOR FIRE ENTRY APPLICATIONS OR FOR PROTECTION FROM CHEMICAL, BIOLOGICAL, OR RADIOLOGICAL AGENTS. OTHER PROTECTIVE EQUIPMENT (HEAD PROTECTION, SCBA, GLOVES, FOOTWEAR, PASS) IS REQUIRED FOR PROTECTION. KEEP THIS GARMENT CLEAN AS SOILING WILL REDUCE PROTECTIVE QUALITIES.

DO NOT USE CHLORINE BLEACH

CHLORINE BLEACH WILL SIGNIFICANTLY COMPROMISE THE PROTECTION AFFORDED BY THE TEXTILE MATERIALS UTILIZED IN THE CONSTRUCTION OF THE GARMENT. USERS MUST CLEAN, MAINTAIN, AND ALTER ONLY IN ACCORDANCE WITH MANUFACTURER'S INSTRUCTIONS. DO NOT STORE IN DIRECT SUNLIGHT. NO PROTECTIVE CLOTHING CAN PROVIDE COMPLETE PROTECTION FROM ALL CONDITIONS. USE EXTREME CARE FOR ALL EMERGENCY OPERATIONS. FAILURE TO COMPLY WITH THESE WARNINGS MAY RESULT IN SERIOUS INJURY OR DEATH.

DO NOT REMOVE THIS LABEL

THIS STRUCTURAL COAT WHEN WORN WITH A LINER COMPLYING WITH MIL-L-24943 AND UNDER THE REFLECTIVE COAT COVER COMPLYING WITH MIL-C-24938, MEETS NFPA 1976 STANDARD ON PROTECTIVE CLOTHING FOR PROXIMITY FIREFIGHTING - 1992 EDITION.

Classified by Underwriters Laboratories Inc. in accordance with the National Fire Protection Association Standard for Structural Fire Fighting NFPA 1971-1991.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.11.3 Label, proximity coat cover. Each proximity coat cover shall have a combination size, instruction and identification label conforming to Type VI, Class 14 of DDD-L-20 except that the colorfastness requirements shall not apply. The label shall bear the following inscription:

COAT COVER, FIREMEN'S, ALUMINIZED PROXIMITY, (TYPE II)
FIBER CONTENT - 100% Para-Aramid
CONTRACT NO: DLA-100-00-0-0000 (EXAMPLE)
STOCK NO: 8415-00-000-0000 (EXAMPLE)
SIZE: MEDIUM (38-40) (EXAMPLE)
NAME OF CONTRACTOR:
NAME OF MANUFACTURER: (If other than contractor)

INSTRUCTIONS

1. CAUTION: MUST BE USED ONLY AS A COVER WITH STRUCTURAL COAT.
2. Hang to dry and store properly to prevent damage to aluminized surfaces.
3. Clean by gently rubbing surface with cloth using mild soap, PERCHLOROETHYLENE or ISOPROPANOL. When cleaning with perchloroethylene and isopropanol, ensure that you have adequate ventilation and that you use proper gloves and eye protection.
4. To maintain reflective properties and to extend service life, use proximity coat cover for intended purpose only.
5. Do not use aluminized paint to repair worn out surface as it will not provide protection.

NOTE: Aluminized coating is damaged by contact with fire extinguishing agent Potassium Bicarbonate Powder (PKP). Before storing garment with PKP residue present, the following is recommended.

1. Dry powder should be removed with dry brush or blower.
2. Wet powder should be removed by thoroughly flushing with water and wiping the surface down with a clean soft cloth. Damp or wet garments should be hung to dry.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.11.4 NFPA approval label, proximity coat cover. Each coat cover shall have a NFPA label conforming to type VI, class 3, of DDD-L-20. The label shall contain the following inscription:

THIS PROXIMITY PROTECTIVE GARMENT MEETS THE REQUIREMENTS OF NFPA 1976 STANDARD ON PROTECTIVE CLOTHING FOR PROXIMITY FIRE FIGHTING, 1992 EDITION.

WARNING

FOR PROXIMITY FIREFIGHTING OPERATIONS, THIS REFLECTIVE COAT COVER MUST BE WORN OVER THE STRUCTURAL COAT COMPLYING WITH MIL-C-24938 AND LINER COMPLYING WITH MIL-L-24943. BOTH THE STRUCTURAL COAT AND TROUSERS MUST BE WORN OVER THEIR APPLICABLE AND DETACHABLE LINERS FOR LIMB/TORSO PROTECTION. OUTER SHELL, MOISTURE BARRIER AND THERMAL BARRIER MEETING ALL REQUIREMENTS OF NFPA 1976 MUST BE UTILIZED AND ALL GARMENT CLOSURES MUST BE FASTENED WHEN IN USE. DO NOT KEEP THIS GARMENT IN DIRECT CONTACT WITH FLAMES. THIS GARMENT ALONE MAY NOT PROVIDE PROTECTION FOR FIRE ENTRY APPLICATIONS OR FOR PROTECTION FROM CHEMICAL, BIOLOGICAL, OR RADIOLOGICAL AGENTS. OTHER PROTECTIVE EQUIPMENT (HEAD PROTECTION, SCBA, GLOVES, FOOTWEAR, PASS) IS REQUIRED FOR PROTECTION. KEEP THIS GARMENT CLEAN AS SOILING WILL REDUCE PROTECTIVE QUALITIES.

DO NOT USE CHLORINE BLEACH

CHLORINE BLEACH WILL SIGNIFICANTLY COMPROMISE THE PROTECTION AFFORDED BY THE TEXTILE MATERIALS UTILIZED IN THE CONSTRUCTION OF THE GARMENT. USERS MUST CLEAN, MAINTAIN, AND ALTER ONLY IN ACCORDANCE WITH MANUFACTURER'S INSTRUCTIONS. DO NOT STORE IN DIRECT SUNLIGHT. NO PROTECTIVE CLOTHING CAN PROVIDE COMPLETE PROTECTION FROM ALL CONDITIONS. USE EXTREME CARE FOR ALL EMERGENCY OPERATIONS. FAILURE TO COMPLY WITH THESE WARNINGS MAY RESULT IN SERIOUS INJURY OR DEATH.

DO NOT REMOVE THIS LABEL

Classified by Underwriters Laboratories Inc. in accordance with the National Fire Protection Association Standard For Proximity Fire Fighting NFPA 1976-1992.

3.3.12 Repair of aluminum film. The aluminum film used for patches for repairing uncoated or cracked areas on the finished proximity coat cover shall be the same as specified for coating the base cloth. The area to be repaired shall not exceed 1 inch in the longest direction. The patch shall be completely bonded onto the aluminum film of the proximity coat cover and shall be so placed that it extends not less than 1/2 inch beyond all edges of the uncoated or cracked area. No outer shell shall contain more than 3 patches. The unsupported aluminum film and self-curing adhesive used for repairing shall be obtained from the basic material supplier (see 3.3.2). The size of the patch shall not exceed 2 inches in any direction.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.3.13 Instruction manual. An instruction manual shall be furnished by the contractor with each structural coat and proximity coat cover. For the structural coat, the manual shall be inserted into the right patch pocket (see 5.1.1.1). For the proximity coat cover, the manual shall be inserted into the polyethylene bag during packaging, and positioned so that it is visible (see 5.1.1.2). The printing, collation, folding and stitching of the manual shall be in accordance with the standard sample (see 6.3). The cover shall be antique white book paper conforming to Joint Committee Printing-A-100, 140 pound basis weight 25 x 38 inches per 1000 sheets. The text paper shall be white offset book paper conforming to JCP-A-60, 120 pound basis weight 25 X 38 inches per 1000 sheets. A sample of the manual plus four glossy pictures used in the printing of the instruction manual shall be obtained from the contracting officer.

3.4. Design. The coat shall be of a two piece design, consisting of an inner structural coat and a detachable outer proximity coat cover. The structural coat shall be fabricated from a para-aramid/PBI fabric for the outer shell and lined with a chloroprene coated aramid fabric for the moisture barrier. The detachable outer proximity coat cover shall be fabricated from a highly reflective aluminized para-aramid knit fabric. The structural coat shall have an aluminized undercollar, throat strap with the face side aluminized, sleeves with bound edges fabricated from abrasion resistant coated fabric, and side bellow pockets with flaps. The front closure shall consist of protective flaps secured by means of three snap hooks and D-rings. Securing panels on both sides of the front opening are for attachment of the outer shell. The proximity coat cover is designed to fit over the structural coat with openings and flaps made for the pockets. Attachment is made by hook and loop fastener tape and securing panels on both sides of the front opening. There are 4 additional sets of elbow patches included with each proximity coat cover (see Figures 1 and 2).

3.4.1 Figures. Figures are furnished for informational purposes only. When inconsistencies exist between the written specification and the figures, the written specification shall govern.

3.5 Patterns. Standard patterns to be used to cut working patterns will be furnished by the Government (see 6.3). The working patterns shall be identical to the Government patterns. Neither the Government patterns nor the working patterns shall be altered in any way, except that additional notches for use during construction are permitted on the working patterns. Also, minor modifications are permitted where necessary when using automatic equipment. These modifications shall not alter the dimensional, serviceability, or appearance requirements cited in the specification. The patterns allow a 1/2 inch seam allowance for major joining seams, except as otherwise indicated in Tables III and IV.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.5.1 Pattern parts. The component parts of the coat shall be cut from the materials specified and in accordance with the number of parts required for the manufacturing process as follows:

MATERIAL	NOMENCLATURE OF PATTERN PARTS	CUT PARTS
	STRUCTURAL COAT (TYPE I)	
Base fabric	Front left	1
	Front right	1
	Back	1
	Sleeve	2
	Facing left	1
	Facing right	1
	Topcollar	1
	Patch pocket	2
	Patch pocket flap	2
	Radio pocket	1
	Radio pocket flap	1
	Elbow patch	2
	Under throat strap	1
	Bottom closure flap	2
Aluminized	Left securing panel	1
	Right securing panel	1
	Undercollar	1
	Top throat strap	1
Moisture barrier	Front left	1
	Front right	1
	Back	1
	Sleeve	2
	Sleeve moisture barrier extension	2
	Wristlet stand	2
	Facing left	1
	Facing right	1
	Undercollar moisture barrier	2
	Throat strap moisture barrier	2
	Patch pocket reinforcement	2
	Patch pocket flap reinforcement	2
	Radio pocket reinforcement	1
	Radio pocket flap reinforcement	1
Abrasion resistant cloth	Protective shoulder	2
Templates	Marker left side - snap - hook-loop location	
	Marker right side - D-ring - hook location	
	Marker right side - hook location	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

MATERIAL	NOMENCLATURE OF PATTERN PARTS	CUT PARTS
	PROXIMITY COAT COVER (TYPE II)	
Aluminized	Front left	1
	Front right	1
	Back	1
	Sleeve	2
	Radio pocket flap	1
	Radio pocket facing	2
	Pocket flap	2
	Pocket facing	4
	Neck facing	2
	Elbow patch	10 1/
	Elbow patch holder	2
Abrasion resistant cloth	Buttonhole reinforcement	3
Template	Marker for buttonhole reinforcement	-

1/ Elbow patches must be cut as 5 left and 5 right.

3.6 Construction.

3.6.1 Stitches, seams and stitchings. Stitch, seam and stitching types specified in Tables III and IV shall conform to FED-STD-751. Whenever two or more methods for seam or stitch types are given for the same part of the operation any one may be used. Seam allowance shall be maintained with seams sewn so that no raw edges, runoffs, twists, pleats, puckers or open seams result. All seams shall start and finish evenly. Thread tension shall be maintained so that there is no tight or loose stitching. Where stitch type 401 is used, the looper (underthread) shall be on the inside of the garment. Topstitching, edgestitching, and staystitching shall be 1/16 to 3/16 inch from the edge, hook and loop fastener tape and reflective tape stitching shall be 1/16 to 3/16 inch from the tape edge. All double needle stitching shall be 1/4 inch gauge, with the row of stitching next to the folded edge not more than 1/16 inch from the edge. The bight of the overedge stitching shall be 3/16 to 5/16 inch. A knife shall be used on the overedge machine with the guide set so that only the ravelled edges are trimmed. In order to minimize the size of the needle hole in the aluminized fabric, the needle used in the seaming operations shall be the smallest size which will accommodate the specified size thread.

3.6.2 Thread breaks and end of seams. End of all seams and stitching when not caught in other seams or stitching shall be backtacked not less than 3/8 inch. The ends of a continuous line of stitching (except label) shall be overlapped not less than 1/2 inch. The ends of the label stitching shall be overlapped not less than 3 stitches. Thread breaks (all stitch types) shall be repaired by stitching back of the break not less than 1/2 inch. Skipped stitches or thread breaks on 401 stitch type may be repaired by using 301 stitch type. When ends of overedge stitching are not caught in other seams or stitching, the ends shall be tacked. When stitch type 401 is permitted as an option, it shall not be used unless the ends are caught in other seams of stitching.

Source: https://assist.dla.mil -- Downloaded: 20260-20T03:08Z
Check the source to verify that this is the current version before use.

3.6.3 Stitches per inch. The minimum and maximum number of stitches per inch shall be as specified in Tables III and IV.

3.7 Manufacturing operations requirements. The coat shall be manufactured in accordance with the operation requirements specified in Tables III and IV. The supplier is not required to follow the exact sequence of operations listed provided that the finish coats are identical to those produced by following the sequence of operations as listed in Tables III and IV.

3.7.1 Size marking. The component parts of the coat shall be bundled, marked or ticketed to assure proper size assembly. The use of metal fastening devices or sewn-on tickets for marking is prohibited. Adhesive tickets, when used, shall not discolor the material and the adhesive mass shall not adhere to the material upon removal of the tickets.

NOTE: The use of ink pad numbering machines, rubber stamp or pencil is allowed, provided the numbering does not show on the outside of the coat and wherever possible, is covered by the seam allowance.

3.7.2 Abbreviations in table of operations. The abbreviations used in tables III and IV are as follows:

Stch - Stitch
In - Inch
Ndl - Needle
Bob - Bobbin
Lpr - Looper
Brtk - Bartack

Source: https://assist.dla.mil -- Downloaded: 202610-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL BOB, LPR
1.	Cutting.				
	a. Cut the structural coat in strict accordance with patterns which show directional lines, marks and notches for proper assembly. Directional lines shall not appear on the fabrics. Drill holes are not permitted except to aid in the attachment of hardware				
	b. The component parts of the base fabric may be cut from ends and when so cut shall approximate the color of the major cut parts.				
	c. The component parts of the moisture barrier may be cut from ends.				
	d. Cut the sleeve tabs from the abrasion resistant cloth, to finish 1 inch wide by 4-1/2 to 5 inches in length (see 3.3.4).				
	e. Cut the wristlets to finish 4 (± 1/4) inch long on the finished coat.				
	f. Cut the strips for binding the edges of sleeve openings from the abrasion resistant cloth, to finish 2 inches in width (see 3.3.4).				
	g. The face side of the materials to be assembled shall be considered as follows: Outershell - as marked Moisture barrier - uncoated side Abrasion resistant cloth - grey coated side				
	NOTE: During the manufacturing of this garment, the water repellent coated side of the lining shall face away from the wearer in the finished structural coat.				

Source: https://assist.dla.mil -- Downloaded: 20261O-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
2.	Replacement of defective components. During the spreading, cutting and manufacturing operations, components having material defects or damages that are classified as damages in MIL-STD-1666 and section 4 shall be removed and replaced with nondefective and properly matched components.					
3.	Seam direction. The direction of the joining seams shall be lapped as follows: 1. Fronts over backs at sides and shoulders. 2. Front and back body over sleeves at armholes. 3. Front portion of sleeve over back portion of sleeve at underarm.					
4.	Assemble securing panels. a. Fold the left securing panel in half, back to back with the long side edges meeting. Turn top, bottom and side raw edges in 1/4 inch and edgestitch all edges.	301	SSc-1	6-8	B	B
	b. Center a strip of loop fastener tape down the length of the left securing panel and stitch along all edges.	301	LSbj-1	6-8	B	B
	c. Fold right securing panel in half, back to back, with the long edges meeting. Turn top, bottom and side edges in 1/4 inch and edgestitch all edges.	301	SSc-1	6-8	B	B
	d. Fold right securing panel in half again with the long edges meeting, stitch the length of the panel 1/8 (± 1/16) inch from the folded edge.	301	OSf-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 202640-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
4.	Assemble securing panels. (cont'd)					
	e. Open up right securing panel and position four, 1-1/2 inch by 2 inch hook fastener tape pieces on the left side in accordance with the marker right side - D-ring - hook location. Stitch along all edges of the fastener tape.	301	LSbj-1	6-8	B	B
	f. Position three D-rings to the underside of the right securing panel in accordance with the marker right side - D-ring - hook location. Securely rivet the three D-rings to the panel.					
	g. Position a strip of 1 inch wide loop fastener tape down the length of the right side of the opened right securing panel with outside edge of the tape 3/8 (± 1/16) inch from the folded edge, stitch along all edges of the fastener tape.	301	LSbj-1	6-8	B	B
5.	Attach elbow patches and reflective tape to sleeve.					
	a. Turn top, bottom, and front edges of elbow patch in 1/2 inch and double stitch 1/4 to 5/16 inch gauge to sleeve, as indicated by notches on sleeve, with the outer row of stitching 1/8 to 1/4 inch from the folded edge. Top and bottom edges of the elbow patch shall be parallel to the bottom edge of the sleeve.	301	LSd-2	6-8	B	B
	b. Position two (2) strips of reflective tape on each sleeve in accordance with marks on patterns. Stitch each side of the reflective tape to the sleeve.	301	LSbj-1	6-8	B	B
	NOTE: The reflective tape must go over the elbow patch.					
6.	Join shoulders.					
	a. Join the fronts and back at shoulder with a double lapped and double stitched seam.	301 or 401	LSc-2	8-10	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
7.	Attach reflective tape.					
	a. Position reflective tape on fronts in accordance with marks on patterns. The lower tape shall match reflective tape on patch pocket. Topstitch each side of the reflective tape to the fronts.	301	LSbj-1	6-8	B	B
	b. Position reflective tape on back of coat in accordance with marks on patterns. Topstitch each side of the reflective tape to the back.	301	LSbj-1	6-8	B	B
8.	Assemble and attach patch pockets.					
	a. Position reflective tape on the patch pockets as indicated by pattern marks and topstitch each side and both ends of the tape to the pocket.	301	LSbj-1	6-8	B	B
	b. Position two 1-1/2 inch by 3 inch pieces of hook fastener tape on the patch pocket as indicated by the marks on the patterns. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	c. Position patch pocket reinforcement behind the patch pocket. The two plies may be staystitched around the outer edges.	301 or 401	SSa-1	6-8	B	B
	d. Position three metal eyelets on each patch pocket in accordance with marks on pattern and attach with the center of each eyelet 7/8 (±1/8) inch from the finished bottom edge of pocket.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
8.	Assemble and attach patch pockets. (cont'd)					
	e. Turn under the top raw edge of patch pocket 1/2 inch and fold as indicated by pattern marks forming a 2-3/4 inch hem and stitch 1/8 inch from folded hem edge.	301	EFt-1	6-8	B	B
	f. Fold edge of patch pocket on pleat fold line closest to the raw edge, face to face and stitch 1/8 to 3/16 inch from folded edge.	301	OSf-1	6-8	B	B
	g. Fold edge of patch pocket on second pleat fold line, back to back and stitch 1/8 to 3/16 inch from folded edge.	301	OSf-1	6-8	B	B
	h. Turn raw pleated front side edge of patch pocket under 3/8 inch. Lay patch pocket flat with pleats closed. Turn bottom raw edge under 1/2 inch and position on coat front as indicated by pattern marks, with back raw edge of patch pocket and side seam of front even. Double stitch front side and bottom edge of pocket to coat front, 1/4 to 5/16 inch gauge with outside stitching 1/8 (± 1/16) inch from front side and bottom folded edge of patch pocket.	301	LSba-2	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
8.	Assemble and attach patch pockets (cont'd).					
	i. Finished patch pocket for all sizes shall measure 10-1/2 (± 3/8) inches long at center of pocket. The width of the pocket shall be 8-3/4 (± 3/8) inches when measured across top edge of pocket from turned edge of pleats to folded edge of side seam.					
	NOTE: Care shall be exercised so as not to catch the outer pleated edge of patch pocket in the stitching of the pocket front side edge.					
9.	Assemble and attach patch pocket flaps.					
	a. Position two 1-1/2 inch by 3 inch pieces of loop tape on the underside of the patch pocket flap as indicated by marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	b. Position the patch pocket flap reinforcement on the inside of the top layer of the patch pocket flap. The two plies may be staystitched along both side edges.	301	SSa-1	6-8	B	B
	c. Fold patch pocket flap in half face to face, as indicated by marks on pattern and stitch 3/8 inch from the raw side edges.	301	SSe-2(a)	6-8	B	B
	d. Trim points, turn patch pocket flap to finished position and completely force out corners. Topstitch the turned in sides and bottom folded edges 1/8 to 1/4 inch from folded edge.	301	SSe-2(b)	6-8	B	B
	e. Overedge raw edges together.	504	EFd-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 202610-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
9.	Assemble and attach patch pocket flaps. (cont'd)					
	f. Turn under overedged top of patch pocket flap 3/8 inch and position on front as indicated by marks on pattern. Double stitch 1/4 to 5/16 inch gauge, with outer row of stitching 1/8 (± 1/16) inch from folded edge of patch pocket flap.	301 or 401	LSba-2	6-8	B	B
	or					
	g. As an alternate, position the patch pocket flap face down on coat front, with overedged edges facing towards the bottom of the coat and 3/8 inch below the marks on pattern. Stitch 1/4 to inch from overedged edge. Turn patch pocket flap down to finished position and double stitch 1/4 to 5/16 inch gauge with outer row of stitching 1/8 (± 1/16) inch from folded edge of patch pocket flap.	301 or 401	LSbl-3	6-8	B	B
	NOTE: Back edge of the flap shall be free of side seams.					
	h. The finished patch pocket flaps for all sizes shall measure 8-1/2 (± 1/4) inches wide and 3-1/2 (±1/4) inches long.					
	i. Stitch a 5/8 inch vertical bartack at the top corners of the patch pockets, a 5/8 inch horizontal bartack at the bottom front corner of the patch pocket and a 5/8 inch horizontal bartack at each top corner of the patch pocket flap. The bartacks shall be superimposed on the previous inner line of stitching.	Brtk		42 per Brtk	B	B
10.	Attach sleeves and close side seams.					
	a. Join the sleeves to armholes with a double lapped and double stitched seam and matching notches.	301 or 401	LSc-2	8-10	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
10.	Attach sleeves and close side seams. (cont'd)					
	b. Join the side of coat and underarm seam with a double lapped and double stitched seam, simultaneously catching the back edge of the patch pocket and ends of the reflective tape in one continuous operation. Note: The reflective tape shall match under arms and at sides.	301 or 401	LSc-2	8-10	B	B
11.	Attach protective shoulder piece					
	a. Position the protective shoulder piece on the shoulder matching the line with the shoulder seam as indicated on the pattern. The armhole edge of the protective shoulder piece shall finish even with the folded edge. Double stitch the protective shoulder piece to the coat, 1/4 to 5/16 inch gauge, with the outer row of stitching 1/8 to 1/4 inch from the raw edge.	301	LSbj-2	6-8	B	B
12.	Assemble and attach radio pocket.					
	a. Center a 1-1/2 inch by 3 inch piece of hook fastener tape to the pocket front as indicated by pattern marks and stitch tape along all edges.	301	LSbj-1	6-8	B	B
	b. Position radio pocket reinforcement behind the radio pocket. The two plies may be staystitched around the outer edge.	301 or 401	SSa-1	6-8	B	B
	c. Turn under the top raw edge of radio pocket 1/4 inch and fold top again as indicated by pattern marks forming a 1-1/4 (± 1/8) inch hem and stitch 1/8 inch from folded hem edge.	301	EFt-1	6-8	B	B
	d. Position and attach two metal eyelets on the bottom end of the radio pocket as indicated by pattern marks and attach with the center of each eyelet 3/4 (± 1/8) inch from finished bottom edge of pocket.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
12.	Assemble and attach radio pocket. (cont'd)					
	e. Stitch radio pocket corners face to face 1/2 inch from raw edge, trimming corners and working out points.	301	SSa-1	6-8	B	B
	f. Fold radio pocket according to fold lines, back to back and stitch 1/8 to 3/16 inch from folded edge.	301	OSf-1	6-8	B	B
	g. Turn raw edges under 3/8 inch and position on right front as indicated by pattern marks. Double stitch 1/4 to 5/16 inch gauge with outside stitching 1/8 (± 1/16) inch from folded edge.	301	EFt-2	6-8	B	B
	h. Finished radio pocket for all sizes shall measure 8-1/2 (± 1/4) inches long and 4 (± 1/4) inches wide.					
13.	Assemble and attach radio pocket flap. a. Center a 1-1/2 inch by 3 inch piece of loop fastener tape on the underside of the finished end of the radio pocket flap in accordance with marks on pattern and stitch tape along all edges.	301	LSbj-1	6-8	B	B
	b. Position the radio pocket flap reinforcement on the top layer of the radio pocket flap outershell and staystitch all edges.	301	SSa-1	6-8	B	B
	c. Fold radio pocket flap face to face, in accordance with marks on pattern, and stitch 3/8 (± 1/16) inch from side raw edges.	301	SSe-2(a)	6-8	B	B
	d. Trim points, turn radio pocket flap to finished position and completely force out corners. Topstitch the turned sides and bottom folded edge 1/8 to 1/4 inch from folded edge.	301	SSe-2(b)	6-8	B	B
	e. Overedge raw edges together.	504	Efd-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
13.	Assemble and attach radio pocket flap. (cont'd)					
	f. Turn under overedged top of radio pocket flap 3/8 inch and position on right front as indicated by marks on pattern. Double stitch 1/4 to 5/16 inch gauge with outer row of stitching 1/8 (± 1/16) inch from folded edge of radio pocket flap.	301 or 401	LSba-2	6-8	B	B
	or					
	g. As an alternate, position the radio pocket flap face down on right coat front, with overedged edges facing towards the bottom of the coat and 3/8 inch below the marks on the patterns. Stitch 1/4 inch from the overedged edge. Turn radio pocket flap down to finished position and double stitch 1/4 to 5/16 inch gauge with outer row of stitching 1/8 (± 1/16) inch from folded edge of radio pocket flap.	301 or 401	LSbl-3	6-8	B	B
	h. Stitch a 5/8 inch vertical bartack at the top corners of the radio pocket and a 5/8 inch horizontal bartack at the top corners of the radio pocket flap. The bartacks shall be superimposed on the previous inner line of stitching.	Brtk		42 per Brtk	B	B
	i. Finished radio pocket flap for all sizes shall measure 4-1/2 (±1/4) inches long and 4 (± 1/4) inches wide.					
14.	Assemble facings.					
	a. Position and center a combination label (see 3.3.11.1) on the right front facing, to finish between the 2nd and 3rd hook fastener tape pattern marks. Topstitch around all sides of label	301	LSbj-1	6-8	B	B
	b. Position and center the NFPA approval label (see 3.3.11.2.1) on the right front facing, to finish between the 3rd and 4th hook fastener tape pattern marks. Topstitch around all sides of label.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
14.	Assemble facings. (cont'd)					
	c. Superimpose the moisture barrier facings on the structural coat facings and topstitch along all raw edges.	301	SSa-1	6-8	B	B
	d. Position facing assemblies face to face at center back, and stitch 3/8 (± 1/16) from raw edge. Spread seam open and flat.	301	SSa-1	6-8	B	B
	e. Bind inside edge of joined facings with a 1-1/8 (± 1/16) inch wide strip of moisture barrier material. The raw edges of the facing shall extend within and to the fold line of the binding.	301	BSa-1	6-8	B	B
	f. Position and attach 13 snap fastener socket and eyelet combinations to finished facing as indicated by marks on patterns. Socket shall face away from the wearer.					
15.	Assemble throat strap and collar.					
	a. The assembled collar shall consist of a base fabric topcollar, two plies of moisture barrier material positioned coated side to coated side, and an aluminized undercollar.					
	b. Position a 1-1/2 inch by 3 inch piece of hook fastener tape to the under throat strap (base fabric) as indicated by marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	c. Assemble the top throat strap (aluminized) and under throat strap (base fabric) face to face with two plies of throat strap moisture barrier positioned coated side to coated side, and sandwiched between in the finished position. Stitch 3/8 (±1/16) inch on three sides leaving the narrow end open for turning. Turn throat strap assembly to finished position, trimming and working out corners, and topstitch.	301	SSe-2	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
15.	Assemble collar. (cont'd)					
	d. Position throat strap assembly (aluminized side) to left side of undercollar, centering within fastener tape marks on pattern and the square end of the strap facing towards the back of the collar. Stitch 1/4 to 5/16 inch from the raw edge.	301	SSa-1	6-8	B	B
	e. Position a 1-1/2 by 3 inch piece of loop fastener tape to each end of undercollar as indicated by marks on pattern. Stitch tape along all edges. The narrow end of the throat strap assembly specified in operation 15d shall be caught in the stitching.	301	LSbj-1	6-8	B	B
	f. Superimpose the undercollar moisture barriers on the undercollar and staystitch along all raw edges.	301 or 401	SSa-1	6-8	B	B
	g. Join face to face, 5/16 to 3/8 inch, the undercollar assembly and the topcollar along the outer edges.	301 or 401	SSe-2(a)	6-8	B	B
	h. Trim corners and turn collar assembly to finished position, working out edges. Topstitch outer edges 1/4 to 5/16 inch from folded edge.	301	SSe-2(b)	6-8	B	B
	i. The hanger loop shall be made from a 2 inch wide 5 inch long strip of the type I basic material and shall finish 1/2 inch wide.					
	j. Fold in the raw edges of the strip so that they abut each other at the center back of the finished loop. Fold the strip in half again, closing raw edges within the fold.					
	k. Double stitch through all layers, 1/4 inch stitch gauge.	301 or 401	EFs-2	8-10	B	B
	l. The hanger loop shall finish flat without distortions or raw edges, with stitching of uniform gauge.					
	Note: A folder can be used to perform this operation.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
15.	Assemble collar. (cont'd)					
	m. The 5 inch length hanger loop shall be prestitched to the bottom raw edge of the neck portion of collar.	301 or 401	SSab-1	6-8	B	B
	n. When attached to the finished collar, the hanger loop shall be centered between the ends of the collar and its opening shall measure 3 (± 1/4) inches long between attached ends.					
16.	Prepare moisture barrier assembly.					
	a. Join 1/2 inch from raw edge the shoulders, armholes, sides, and sleeve inseams. The side seam and sleeve inseam shall be joined in one continuous operation.	301 or 401	LSq-2(a)	6-8	B	B
	b. Turn one ply back over seam allowance and topstitch 1/8 inch from folded edge.	301 or 401	LSq-2(b)	6-8	B	B
	c. As an alternate, operation 16a and 16b may be performed in one operation by joining with a double lapped and double stitched seam, 1/4 inch gauge.	301 or 401	LSc-2	6-8	B	B
	d. Each of the moisture barrier seams on the coated side of the fabric shall be heat sealed with the 7/8 inch wide tape specified in 3.3.7.					
	e. Apply warning label, (see 3.3.11.2), horizontally across back of moisture barrier so that the top edge of label will finish 6 to 8 inches below collar seam on the finished coat.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
16.	Prepare moisture barrier assembly. (cont'd).					
	f. Position ends of wristlet stand face to face and stitch 1/4 inch from raw edge.	301 or 401	SSa-1	6-8	B	B
	g. Fold wristlet stand back to back in accordance with the fold line on the pattern and staystitch the periphery together 1/4 inch from the raw edge.	301 or 401	SSa-1	6-8	B	B
	h. Position ends of sleeve moisture barrier extension face to face and overedge stitch 1/4 inch from raw edge.	515 or 516 or 519	EFd-1	6-8	B	B
	i. Position wristlet stand inside the knit wristlet with raw edges of knit wristlet and raw edge of wristlet stand even. Stitch 1/8 to 1/4 inch from edge. The knit wristlet shall be stretched so that the wristlet stand is flat and smooth.	301	SSa-1	6-8	B	B
	j. Position sleeve moisture barrier extension outside of the wristlet assembly with top raw edge of sleeve moisture barrier extension even with the raw edges of wristlet assembly, face to face. Stitch 1/4 inch from edges with the knit wristlet stretched so that the sleeve moisture barrier extension is flat and smooth. The joining seams of operations 16f and 16h shall match up.	301	SSa-1	6-8	B	B
	k. Position turned edge of wristlet stand face to face with bottom of sleeve moisture barrier and stitch 1/4 inch from raw edges, simultaneously inserting and catching the abrasion resistant cloth sleeve tabs, with one at the underarm seam and the other directly opposite at notch on sleeve pattern, and with the face side of the abrasion resistant cloth facing the sleeve. For ease in assembly, abrasion resistant cloth sleeve tabs may be prestitched to bottom of sleeve moisture barrier before attachment of wristlet stand.	301	SSa-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
17.	Join prepared coat assemblies.					
	a. Position preassembled facing (moisture barrier side) on face side of assembled moisture barrier with fronts and neckline edges even.					
	b. Position assembled collar (structural side) on the neckline of the facing assembly (structural side) according to notches, face to face.					
	c. Staystitch through all plies 1/4 (± 1/16) inch from the raw edge, simultaneously catching the hanger loop. Continue staystitching up front edge, across neckline, and down opposite front edge.	301	SSa-1	6-8	B	B
	d. Position and stitch moisture barrier assembly to structural coat assembly face to face according to notches. Stitch 1/4 inch from raw edges. Continue stitching up front edge, across neckline, and down opposite front edge.	301	SSe-2(a)	6-8	B	B
	e. Trim corners, turn coat to finished position and work out corners and front edges.					
	f. Topstitch 1/4 inch from folded edge of the fronts from neckline seam to hem.	301	SSe-2(b)	6-8	B	B
	g. Topstitch thru all plies the entire length of facing 2 (± 1/4) inches from folded edge of binding. Stitching shall terminate at the collar seam.	301 or 401	SSa-1	6-8	B	B
	h. Staystitch sleeve moisture barrier extension to structural sleeve with raw edges even.	301	SSa-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
18.	Hem bottom Turn under entire bottom edge of coat 1/2 inch and fold again to form a 5/8 (± 1/8) inch hem, as indicated by notches on pattern. Ends of hem may be folded square or diagonally. Stitch top edge of hem and diagonally folded ends 1/8 to 1/4 inch from folded edge. Square folded ends shall be stitched 1/4 to 3/8 inch from folded edge. Note: Moisture barrier must extend to fold of hem or beyond and should be caught when stitching finished hem.	301	EFb-1	6-8	B	B
19.	Attach securing panels. a. Stitch a line as a guide for placement of right securing panel, lined up with the front edge of the collar and parallel to finished front edge.	301	OSa-1	6-8	B	B
	b. Position the right securing panel to the right front of structural coat on guideline stitched in operation 19a, with the D-rings against the face of the structural coat. The opening of the securing panel should face toward the right armhole. The folded front edge of the right securing panel shall be parallel with the front edge of the structural coat. Stitch right securing panel to coat 1/8 inch from the back edge of the panel.	301	LSbj-1	6-8	B	B
	c. Position the folded edge of the left securing panel to the left front edge of the structural coat with the loop fastener tape positioned against the face of the structural coat. Stitch left securing panel to coat 3/16 inch from the front edge.	301	SSaa-1	6-8	B	B
20.	Assemble and attach bottom closure flap. a. Attach a strip of reflective tape superimposed on top ply of bottom closure flap in accordance with marks on pattern.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
20.	Assemble and attach bottom closure flap. (cont'd)					
	b. Attach a 1-1/2 by 3 inch piece of hook and loop fastener tape on bottom ply of bottom closure flap. The hook tape shall be centered 1/4 inch from the finished outer edge so as to engage the loop tape on the left front of the coat. The loop tape shall be centered 3/4 inch from opposite end of flap.	301	LSbj-1	6-8	B	B
	c. Assemble the top and bottom plies of bottom closure flap face to face. Turn bottom closure flap to its finished position and edgestitch along its sides 1/16 to 1/8 inch from the edge.	401	LSbj-1	6-8	B	B
	d. Position bottom closure flap to reflective tape on right coat front face to face, so that when folded back in its finished position the reflective tape shall match and engage evenly with the left front loop tape. Stitch across width of flap 3/8 inch from the raw edge.	301	LSq-3(a)	6-8	B	B
	e. Turn flap to finished position and double stitch 1/4 inch gauge across width of flap.	301	LSq-3(b)	6-8	B	B
	f. Center and stitch a 1-1/2 by 3 inch loop fastener tape to bottom reflective tape on left front of finished coat, approximately 2-1/4 inches from the outer edge. Stitch around all four sides making sure facing is not caught in stitching. This tape shall match bottom closure flap in it's finished position and not interfere with function of left securing panel.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
21.	Bind sleeve bottom					
	Fold abrasion resistant cloth strip in half lengthwise. Stitch each sleeve opening with a double row of stitching 1/8 to 1/4 inch from raw edges of abrasion resistant cloth strip, through all plies of material, overlapping ends of strip approximately 1 to 1-1/2 inches near the underarm seam. The gauge of stitching shall be 1/4 inch. The ends of the sleeves shall extend within and to the folded edge of the abrasion resistant cloth strips.	301	BSa-2	6-8	B	B
	Note: Folder can be used perform this operation.					
22.	Finish off coats.					
	a. Position four 1 by 2 inch pieces of hook fastener tape on the right front of the structural coat as indicated by marker right side - hook location. Stitch tape along all edges.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
22.	Finish off coats. (cont'd)					
	b. Position four 1 inch by 2 inch pieces of hook fastener tape on the left front of the structural coat as indicated by pattern marker. Also, position four 1 inch by 2 inch pieces of loop fastener tape on the inside of the left front directly behind the previously positioned hook tape. Stitch along all edges of fastener tape, catching both pieces of tape in the stitching.	301	LSbj-1	6-8	B	B
	or					
	c. As an alternate to option to operation 22b, the fastener tapes may be stitched to each side individually.	301	LSbj-1	6-8	B	B
	d. Rivet three snap hooks on the left front in accordance with the pattern marker. Rivets shall not catch the facing and shall be reinforced with an abrasion resistant cloth patch on the inside.					
	e. Center a 1 inch by 2 inch loop fastener tape across each shoulder seam, with its longest dimension 3/8 inch from the collar joining seam. Stitch tape along all edges.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 202610-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE III - CONSTRUCTION OF STRUCTURAL COAT

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL BOB, LPR
22.	Finish off coats. (cont'd)				
	f. Attach four snap fastener socket and eyelet combinations to the ends of the abrasion resistant cloth sleeve tabs. The center of the socket shall be 1/2 inch from the end of the abrasion resistant cloth sleeve tab. The sockets shall face towards the wrist as worn. This operation may be done prior to the attachment of the tabs to the end of the sleeve opening.				
23.	Clean coat.				
	a. Trim all thread ends.				
	b. Remove all loose threads.				
	c. Remove all spots and stains.				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL BOB, LPR
1.	Cutting.				
	a. Cut the proximity coat cover in strict accordance with patterns which show directional lines, marks and notches for proper assembly. Directional lines shall not appear on the fabrics. Drill holes are not permitted.				
	b. The component parts of the aluminized fabric may be cut from ends and when so cut shall finish with the aluminized side face up.				
	NOTE: Elbow patches must be cut face to face, forming left and right patches.				
	c. Cut triangular abrasion resistant cloth pocket opening reinforcements to finish 2 inches on each side (see 3.3.4).				
	d. Cut the strips for binding the edges of the sleeve opening from the abrasion resistant cloth, to finish 2 inches in width (see 3.3.4).				
	e. The face side of the proximity coat cover material is the aluminized side.				
2.	Replacement of defective components.				
	During the spreading, cutting and manufacturing operations, components having material defects or damages that are classified as damages in MIL-STD-1666 shall be removed and replaced with nondefective and properly matched components.				
3.	Seam direction.				
	The direction of joining seams shall be lapped as follows:				
	1. Fronts over back at sides and shoulders. 2. Front and back body over sleeves at armhole. 3. Front portion of sleeve over back portion of sleeve at underarm.				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
4.	Bind patch pockets openings.					
	a. Slash patch pocket openings as indicated by marks on patterns. Slash shall extend into the side seam and the front. Edge of the slash shall be tongue notched 1/4 inch.					
	b. Fold pocket facings, back to back, as indicated by marks on pattern and stitch 3/8 inch from the folded edges.	301	OSf-1	6-8	B	B
	c. Position pocket facings with folded edges abutted and ends even and tack together across each end, 1/8 inch from raw edges.	301	SSa-1	6-8	B	B
	d. Fold raw edges of patch pocket opening under 1/4 inch. Position the folded edges of the patch pocket facings under the top and bottom of the patch pocket openings, with approximately 3/8 inch of the facings showing. Stitch the width of the patch pocket opening 1/16 inch from the folded edge of the top and bottom of the patch pocket openings and across the front edge end through all plies.	301	Similar to LSbz(c)-1	6-8	B	B
	e. Position two 1 inch by 3 inch pieces of loop tape on the inside of the lower edge of the patch pocket opening in accordance with marks on patterns. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	f. Position two 1 inch by 3 inch pieces of hook tape on the outside of the lower patch pocket opening as indicated by marks on patterns. Stitch tape along all edges.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
4.	Bind patch pockets openings. (cont'd)					
	g. As an alternate, operations 4e and 4f may be done at the same time.	301	LSbj-1	6-8	B	B
5.	Assemble and attach pocket flaps.					
	a. Position two 1-1/2 inch by 3 inch pieces of loop tape on the underside of the pocket flap as indicated by marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	b. Fold pocket flap in half face to face, as indicated by marks on pattern and stitch 3/8 inch from the raw side edges.	301	SSe-2(a)	6-8	B	B
	c. Turn pocket flap to finished position and completely force out corners. Topstitch the turned in side and bottom folded edges 1/8 to 1/4 inch from folded edge.	301	SSe-2(b)	6-8	B	B
	d. Turn under raw edge of pocket flap 1/4 inch and position on front as indicated by marks on pattern. Double stitch 1/4 to 5/16 inch gauge with outer row of stitching 1/8 (± 1/16) from folded edge of pocket flap.	301 or 401	LSba-2	6-8	B	B
	or					
	e. As an alternate, position the pocket flap face down on coat front, with raw edges facing towards the bottom of the coat and 3/8 inch below the marks on pattern. Stitch 1/4 inch from raw edge. Turn pocket flap down to finished position and double stitch 1/4 to 5/16 inch gauge with outer row of stitching 1/8 (± 1/16) from folded edge of pocket flap.	301 or 401	LSbl-3	6-8	B	B
	NOTE: Back edge of the pocket flap shall be free of side seams.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
5.	Assemble and attach pocket flaps. (cont'd)					
	f. Finished pocket flap for all sizes shall measure 8-1/4 (± 1/4) inches wide and 3-1/4 (±1/4) inches long.					
	g. Position a triangular shaped abrasion resistant cloth reinforcement piece on inside of proximity coat cover across both ends of the patch pocket opening, with the base of the triangle perpendicular to the pocket opening. Stitch 1/16 to 1/8 inch from all raw edges of the triangle.	301	LSbj-1	6-8	B	B
6.	Bind radio pocket opening.					
	a. Slash radio pocket opening as indicated by marks on patterns. Ends of slash shall be tongue notched 1/4 inch.					
	b. Fold radio pocket facings, back to back as indicated by marks on patterns and stitch 3/8 inch from the folded edges.	301	SSa-1	6-8	B	B
	c. Position radio pocket facings with folded edges abutted and ends even and tack together across each end, 1/8 inch from raw edges.	301	SSa-1	6-8	B	B
	d. Fold raw edges of radio pocket opening under 1/4 inch. Position the folded edges of the radio pocket facings under the top and bottom of the radio pocket openings, with approximately 3/8 inch of the facing showing. Stitch the width of the radio pocket opening 1/16 inch from the folded edge of the top and bottom of the radio pocket openings and across the ends through all plies.	301	Similar to LSbz(c)-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
6.	Bind radio pocket opening. (cont'd)					
	e. Center a 1-1/2 inch by 3 inch piece of loop tape on the inside of the lower radio pocket opening in accordance with marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	f. Position a 1-1/2 inch by 3 inch piece of hook tape on the outside of the lower radio pocket opening as indicated by marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	g. As an alternate, operations 6e and 6f may be done simultaneously.	301	LSbj-1	6-8	B	B
7.	Assemble and attach radio pocket flap.					
	a. Position a 1-1/2 inch by 3 inch piece of loop fastener tape on the underside of the radio pocket flap as indicated by marks on pattern. Stitch tape along all edges.	301	LSbj-1	6-8	B	B
	b. Fold radio pocket flap in half face to face, as indicated by marks on pattern and stitch 3/8 (± 1/16) inch from the side raw edges.	301	SSe-2(a)	6-8	B	B
	c. Turn radio pocket flap to finished position and completely force out corners. Topstitch the turned sides and bottom folded edges 1/8 to 1/4 inch from folded edge.	301	SSe-2(b)	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
7.	Assemble and attach radio pocket flap. (cont'd)					
	d. Turn under the raw edge of the radio pocket flap 1/4 inch , and position on right front as indicated by marks on pattern. Double stitch 1/4 to 5/16 inch gauge with outside stitching 1/8 (± 1/16) inch from folded edge of radio pocket flap.	301 or 401	LSba-2	6-8	B	B
	or					
	e. As an alternate, position the radio pocket flap face down on right coat front, with raw edges facing towards the bottom of the coat 3/8 inch below the marks on the pattern. Stitch 1/4 inch from raw edge. Turn radio pocket flap down to finished position and double stitch 1/4 to 5/16 inch gauge, with outer row of stitching 1/8 (± 1/16) inch from folded edge of radio pocket flap.	301 or 401	LSbl-3	6-8	B	B
	f. Finished radio pocket flaps for all sizes shall measure 4-3/4 (± 1/4) inches wide and 3 (± 1/4) inches long.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
8.	Assemble elbow patch and elbow patch holder.					
	a. Fold over top edge of elbow patch as indicated on pattern face to face 1/2 inch, and position a 5/8 inch strip of loop fastener tape on face side across the width of the elbow patch, simultaneously folding each side of elbow patch face to face 1/2 inch. The edge of the fastener tape shall be even with the folded edge of the elbow patch. Stitch around edge of loop fastener tape.	301	LSbj-1	6-8	B	B
	b. Form pleats in both sides of elbow patch as indicated by notches. The fold of the pleat must face towards the bottom of the elbow patch. Depth of pleat shall be 3/8 inch.					
	c. Fold over side edges of elbow patch with pleats face to face 1/2 inch, and position a strip of 5/8 inch loop fastener tape on face side from the top to bottom edge of elbow patch, simultaneously folding bottom of elbow patch 1/2 inch back to back on each side. The edge of each fastener tape shall be even with the folded edge of the elbow patch. Stitch around edge of loop fastener tape.	301	LSbj-1	6-8	B	B
	d. Position a strip of 5/8 inch loop fastener tape on face side to back side of elbow patch across bottom. The edge of the fastener tape shall be even with the folded edge of the elbow patch. Stitch around edge of the loop fastener tape.	301	LSbj-1	6-8	B	B
	e. Clip inside corners, fold under the inside edges of elbow patch holder 1/2 inch, and position a strip of 5/8 inch hook fastener tape on face side to back side of elbow patch holder. Bottom edges of elbow patch holder shall be turned under 1/2 inch. The edge of the fastener tape shall be even with the folded inner edges of elbow patch holder. Stitch around edges of hook fastener tape.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
8.	Assemble elbow patch and elbow patch holder (cont'd).					
	f. Cut and attach a strip of 5/8 inch hook fastener tape to back of sleeve in accordance with marks on pattern. Stitch around edges of hook fastener tape.	301	LSbj-1	6-8	B	B
	Note: Designation of left and right elbow patches shall be stamped on the back side of the patch with block sansserif type with letters 3/4 to 1 inch in height. The stamp shall be centered above the pleat and shall finish at least 1-1/2 inches from finished top of elbow patch.					
9.	Attach elbow patch holder to sleeve.					
	a. Position elbow patch holder to back of sleeve in accordance with notches on pattern, with angled edge aligned evenly with underarm seam. Turn under 1/2 inch top and straight side edges of elbow patch holder, and stitch assembly to sleeve 1/8 inch from folded edge.	301	LSb-1	6-8	B	B
	NOTE: The side of the elbow patch holder may be staystitched to the underarm 1/8 inch from raw edge.					
	b. Insert the elbow patch within the elbow patch holder.					
10.	Assemble proximity coat cover.					
	a. Join fronts and back at shoulder with a double lapped and double stitched seam.	301 or 401	LSc-2	8-10	B	B
	b. Join the sleeves to the armhole with a double lapped and double stitched seam.	301 or 401	LSc-2	8-10	B	B
	c. Join side seam and underarm seam with a double lapped and double stitched seam, simultaneously catching the raw edge of the elbow patch holder.	301 or 401	LSc-2	8-10	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
10.	Assemble proximity coat cover. (cont'd) or					
	d. As an alternate, join, face to face, 1/2 inch from raw edge, the fronts and back at shoulder. Turn seam allowances to front and topstitch 1/16 to 1/8 inch from folded edge.	301	LSq-2	6-8	B	B
	e. Join face to face 1/2 inch from the raw edge, the sleeves to the armhole, matching notches. Turn back seam allowances toward body of proximity coat cover and topstitch 1/16 to 1/8 inch from folded edge.	301	LSq-2	6-8	B	B
	f. Join face to face 1/2 inch from the raw edge, side seam and underarm seam, simultaneously catching the raw edge of the elbow patch holder, in one continuous operation. Turn seam allowances toward front and topstitch 1/16 to 1/8 inch from folded edge.	301	LSq-2	6-8	B	B
	g. Position a triangular shaped abrasion resistant cloth reinforcement piece on inside of proximity coat cover across both ends of the radio pocket opening, with the base of the triangle perpendicular to the radio pocket opening. Stitch 1/16 to 1/8 inch from all raw edges of the triangle. Note: The point and stitching of the triangular shaped reinforcement piece may extend into the seam allowance of the armhole but may not extend past the armhole seam line.	301	LSbj-1	6-8	B	B
	h. Position neck facings face to face at center back notch with back raw edges even and stitch 1/4 inch from the raw edges.	301	SSa-1	6-8	B	B
	i. Turn in raw edges of fronts as indicated by the outside fold line on the patterns, back to back. Fold front edge face to face along the inside fold line indicated on the pattern.					

Source: https://assist.dla.mil -- Downloaded: 202640-20T03:08Z
Check the source to verify that this is the currentversion before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
10.	Assemble aluminized cover. (cont'd)					
	j. Position neck facing on the proximity coat cover face to face, matching center back notch with joining seam of neck facing and stitch 1/4 inch from the raw edges.	301	SSa-1	6-8	B	B
	k. Trim end of left neck facing and turn neck edge and fronts to finished position and topstitch 1/4 (± 1/16) inch. Stitch again 1/4 (± 1/16) inch from cut edge of neck facing. Topstitch 1 (± 1/16) inch from the left front edge and 1-5/16 (± 1/16) inch from the right front edge.	301	SSae-3(b)	6-8	B	B
	l. Position three abrasion resistant cloth buttonhole reinforcements on the inside left front of cover, 1/16 inch from the front folded edge and in accordance with marker for buttonhole reinforcement. Double stitch the edges and the point of the buttonhole reinforcement 1/8 to 3/16 inch gauge with the outside row of stitching 1/16 inch from the raw edge.	301	LSbj-2	6-8	B	B
	m. Slash abrasion resistant cloth buttonhole reinforcements and proximity coat cover front opening as indicated on the buttonhole reinforcement pattern. Boxstitch slashed opening 1/8 inch all around, starting and stopping at the front folded edge of the coat.	301	LSbj-1	6-8	B	B
	n. Turn under entire bottom edge of coat 1/2 inch. Turn under again and form a 3/4 (± 1/8) inch wide hem, as indicated by notches on pattern. Ends of hem may be folded square or diagonally. Stitch top edge of hem and diagonally folded ends 1/8 to 1/4 inch from folded edge. Square folded ends shall be stitched 1/4 to 3/8 inch from the folded front edge.	301	EFb-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
10.	Assemble proximity coat cover. (cont'd)					
	o. Position a strip of 1 inch wide hook fastener tape down the outside right and left fronts with the edge 1/8 to 3/16 inch from the folded front edges and the ends finishing 1/4 inch from the folded top and 1 inch from the folded bottom edges. Stitch along all edges of the tape.	301	LSbj-1	6-8	B	B
	p. Fold abrasion resistant cloth strip in half lengthwise. Stitch each sleeve opening with a double row of stitching 1/8 to 1/4 inch from raw edges of abrasion resistant cloth strip, through all plies of material, overlapping ends of strip 1 to 1-1/2 inches near the underarm seam. The gauge of stitching shall be 1/4 inch. The ends of the sleeves shall extend within and to the folded edge of the abrasion resistant cloth strips. Note: Folder can be used to perform this operation.	301	BSa-2	6-8	B	B
	q. Center and stitch a 1 inch by 2 inch hook fastener tape to each shoulder seam on inside of proximity coat cover and facing the wearer, with its longest dimension 1/8 inch from finished edge of neck opening. Stitch tape along all edges.	301	LSbj-1	6-8	B	B

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE IV - CONSTRUCTION OF PROXIMITY COAT COVER

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	NDL	BOB, LPR
11.	Labels.					
	a. Position and topstitch the combination label, (see 3.3.11.3) to inside center back of proximity coat cover 1-1/2 to 2 inches below raw edge of neck facing.	301	LSbj-1	6-8	B	B
	b. Position and topstitch the NFPA approval label (see 3.3.11.4) approximately 2 to 3 inches below the bottom edge of combination label.	301	LSbj-1	6-8	B	B
12.	Clean proximity coat covers.					
	a. Trim all thread ends.					
	b. Remove all loose threads.					
	c. Remove all spots and stains.					
	NOTE: Care shall be taken in the use of solvents for cleaning to assure that the aluminized coating is not damaged.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

3.8 Sizes and measurements. Sizes and measurements of the finished structural coat and the proximity coat cover shall be as shown in Tables V and VI (see Figures 1 and 2). All measurements and tolerances are expressed in inches.

TABLE V - STRUCTURAL COAT

SIZE	(A) CHEST	(B) BOTTOM	(C) BACK LENGTH	(D) SLEEVE LENGTH
Small (34-36)	47-1/2	48-1/2	31-1/4	23
Medium (38-40)	51-1/2	52-1/2	32	23-1/2
Large (42-44)	55-1/2	56-1/2	32-3/4	24
X-Large (46-48)	59-1/2	60-1/2	33-1/2	24-1/2
Tolerance	±1	±1	±1/2	±1/2

NOTE: The structural coat shall be laid flat and smooth with the front D-rings and snaps closed.

(A) Chest - Twice the measurement taken across front from folded edge to folded edge at base of armhole.

(B) Bottom - Twice the measurement taken along bottom edge of structural coat from folded edge to folded edge.

(C) Back Length - Measure from collar joining seam to bottom of structural coat along center of back.

(D) Sleeve Length - measure along underarm seam from base of armhole to bottom edge of sleeve.

TABLE VI - ALUMINIZED PROXIMITY COVER

SIZE	(A) CHEST	(B) BOTTOM	(C) BACK LENGTH	(D) SLEEVE LENGTH
Small (34-36)	49	51-1/2	31-1/2	24-1/2
Medium (38-40)	53	55-1/2	32-1/4	25
Large (42-44)	57	59-1/2	33	25-1/2
X-Large (46-48)	61	63-1/2	33-3/4	26
Tolerance	±1	±1	±1/2	±1/2

NOTE: The proximity coat cover shall be laid flat and smooth with front edges placed together.

(A) Chest - Twice the measurement taken across front from folded edge to folded edge at base of armhole.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

(B) Bottom - Twice the measurement taken along bottom edge of proximity coat cover from folded edge to folded edge.

(C) Back Length - Measure from neckline to bottom of proximity coat cover along center of back.

(D) Sleeve Length - Measure along underarm seam from base of armhole to bottom edge of sleeve.

3.9 Workmanship. The finished structural coat and proximity coat cover shall conform to the quality established by this specification. The occurrence of defects shall not exceed the acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated of actual, nor does it commit the government to acceptance of defective material.

4.1.2 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classifier as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

4.3 First article inspection. When required, the first article submitted in accordance with 3.2, shall be inspected as specified in 4.4.2 for compliance with design, construction, workmanship, appearance and dimensional requirements.

4.4 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.4.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable procurement documents. A certificate of compliance shall be furnished for paragraphs 3.3.3 - moisture barrier, 3.3.4 - cloth, abrasion resistant requirements and 3.3.10.3 - identification of metal fasteners. In addition, testing shall be performed on the components and characteristics listed in Table VII. The methods of testing specified in FED-STD-191, wherever applicable, and as listed in Table VII shall be followed. The physical and chemical values specified in Section 3, except where otherwise specified, apply to the average of the determinations made on the sample unit for test purposes as specified in the applicable test methods. All test reports shall contain the individual values utilized in expressing the final results. The lot shall be unacceptable if one or more sample units fail to meet any of the test requirements specified. The sample size shall be in accordance with the following:

LOT SIZE	SAMPLE SIZE
800 or less	2
801 thru 22,000	3
22,001 and over	5

The basis for lot size and sample units for testing shall be as follows:

COMPONENT	LOT SIZE EXPRESSION	SAMPLE UNIT
Moisture barrier	yards	2 yards full width
Cloth,abrasion resistant	yards	2 yards full width
Snaps and D-rings	gross	1 each

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

TABLE VII - TESTING OF COMPONENTS

COMPONENT	CHARACTERISTIC	REQUIREMENT PARAGRAPH	TEST METHOD/ PARAGRAPH
Moisture barrier	Coating compound	3.3.3	1/
	Weight	3.3.3	5041
	Breaking strength	3.3.3	5100
	Tear strength	3.3.3	5134
	Hydrostatic resistance	3.3.3	5512 2/
	Flame resistance	3.3.3	5903.1
Cloth,abrasion resistant	Base fabric	3.3.4	1/
	Type of weave	3.3.4	1/
	Coating compound	3.3.4	1/
	Weight	3.3.4	5041
	Thickness	3.3.4	5030
	Breaking strength	3.3.4	5100
	Tear strength	3.3.4	5134
	Flame resistance	3.3.4	5903.1
	Abrasion resistance	3.3.4	5306 3/
Snaps hooks and D-rings	Metal identification	3.3.11.3	1/
	Style	3.3.11.3	Visual
	Dimensions	3.3.11.3	Visual

1/ A certificate of compliance shall be acceptable for this requirement.

2/ The water pressure shall be applied to the coated side of the material.

3/ Using the H18 abrasion wheel, 500 gram load on each abrasion arm for 2000 cycles.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

4.4.2 Examination of the end item structural coat and proximity coat cover. Examination of the end item shall be in accordance with MIL-STD-1666 for Material Defects and Damages (Sec. I), Components and Assembly (Sec. II), Cutting (Sec. III), Cleanness (Sec.IV), Seams and Stitchings (Sec. V), Metal Components (Sec. VII), Dimensional examination specified in paragraph 4.3, Inspection levels and acceptable quality levels specified in paragraph 4.4, also Examination of packaging requirements specified in 4.4.3 and in accordance with 4.4.2.1 of this specification. Defects listed in paragraph 4.4.2.1 shall take precedence over defects listed for similar examinations in MIL-STD-1666.

4.4.2.1 Visual examination. The structural coat and proximity coat cover shall be examined for defects in construction, design and workmanship as follows:

NOTE: when an asterisk (*) appears, the defect shall be classified as follows:

MAJOR - when seriously affecting serviceability or appearance.
MINOR - When affecting serviceability or appearance, but not seriously.

CLASSIFICATION OF DEFECTS

CLASSIFICATION DEFECT	MAJOR	MINOR
FRONT CLOSURE		
a. Uneven in length at bottom by 1 inch or more when fastened		X
b. Snaps and D-rings out of alignment causing a noticeable gap or pull on front closure when fastened	*	
c. D-rings not positioned on securing panel as specified		X
SECURING PANEL		
a. Puckered or pleated noticeably, affecting serviceability		X
b. Panels reversed, i.e. right panel on left side or left panel on right side	X	
c. Folded edge of right panel not parallel with front edge by more than 1/2 inch when measured from top to bottom		X
COLLAR		
a. Topcollar tight or twisted	*	
b. Topcollar excessively full		X
c. Excessive fullness or twist on collar stand		X
d. Collar edge uneven or not properly forced out		X
e Collar points uneven by more than 1/4 inch		X
f. Collar off center by more than 1/2 inch		X
g. Finished collar less than 4-1/8 or more than 4-3/8 inches wide at center back		X

Source: https://assist.dla.mil -- Downloaded: 20260-20T03:08Z
Check the source to verify that this is the current version before use.

CLASSIFICATION OF DEFECTS (cont'd)

DEFECT	CLASSIFICATION MAJOR	MINOR
POCKET AND FLAP		
a. Pocket and/or flap out of vertical alignment with front edge by more than 3/4 inch		X
b. Pocket and/or flaps out of horizontal alignment by more than 3/4 inch		X
c. Pocket and/or flap poorly shaped, or not of uniform shape		X
d. Pocket and/or flap set on crookedly, affecting appearance		X
e. Pocket and/or flap measurements outside of specified tolerances		X
f. Excessive fullness or twist on outside of flap		X
g. Bellows top edge of pocket caught during pocket attachment to front		X
SLEEVES		
a. Reversed, i.e., left sleeve in right armhole or right sleeve in left armhole	X	
b. Tight at armhole, causing puckers and pleats on front and back	*	
c. Sleeve tabs on inside not positioned as specified		X
d. Snap fastener sockets missing from sleeve tabs	X	
e. Snap fastener sockets facing away from wrist as worn		X
f. Wristlets finish less then 3-3/4 inches or more than 4-1/4 inches		X
g. Bottom of sleeve not abrasion resistant cloth bound		X
h. Abrasion resistant cloth binding on sleeve bottom overlapped less than 1 inch or more than 1-1/2 inch		X
i. Elbow patch missing	X	
j. Elbow patch misplaced or not positioned as specified		X
MOISTURE BARRIER BINDING		
a. Binding not securely caught, pulls away from facing easily		X
b. Binding noticeably puckered or pleated		X
c. Binding tight, will not lie flat		X
ELBOW PATCHES (proximity coat cover only)		
a. Elbow patch missing	X	
b. Aluminized elbow patch misplaced or not as specified.		X
c. Aluminized elbow patch holder missing	X	
d. Aluminized elbow patch holder misplaced or not as specified		X
e. Elbow patches not cut in pairs (5) (5 left and 5 right).	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

CLASSIFICATION OF DEFECTS (cont'd)

DEFECT	CLASSIFICATION MAJOR	MINOR
HANGER LOOP		
a. Omitted or insecurely attached		X
b. Not centered between ends of collar by more than 3/4 inch		X
c. Length of opening less than 2-3/4 or more than 3-1/4 inches		X
BOTTOM HEM		
a. Outside of coat puckered or twisted by stitching forming hem		X
b. Width less than 1/2 or more than 3/4 inches	X	
c. Irregular in width by more than 1/4 inch		X
REFLECTIVE TAPE		
a. One section missing		X
b. More than one section missing	X	
c. Edge of tape not parallel with bottom edge of coat by more than 1/2 inch		X
FASTENER TAPE		
a. Any section missing	*	
b. Any section incorrect component, i.e. hook portion instead of loop portion or loop portion instead of hook portion	*	
c. Not edge stitched along all edges when specified		X
CLOTH, ABRASION RESISTANT REINFORCEMENT		
a. Protective shoulder piece missing	X	
b. Protective shoulder piece misplaced or not attached as specified		X
c. Buttonhole reinforcement missing	X	
d. Buttonhole reinforcement not attached as specified		X
e. Buttonhole reinforcement piece not slit		X
f. Triangular pocket reinforcement piece missing		X
g. Sleeve tab missing		X
h. Sleeve tab less than 1 inch wide		X
i. Sleeve tab less than 5-1/2 or more than 5 inches		X
j. Sleeve tab not attached as specified		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

CLASSIFICATION OF DEFECTS (cont'd)

DEFECT	CLASSIFICATION MAJOR	MINOR
LABEL		
a. Omitted, one or more		X
b. Not attached as specified		X
c. Inscription or instruction omitted, incomplete, illegible or incorrect		X
d. Position not as specified		X
INSTRUCTION MANUAL		
a. Omitted or not positioned as specified		X

4.4.3 Examination for packaging requirements. An examination shall be made to determine that packaging, packing, and marking comply with section 5 requirements of this specification. Defects shall be scored in accordance with the list shown below. The sample unit shall be one shipping container fully prepared for delivery. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be on the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the acceptance quality level (AQL) shall be 2.5, expressed in terms of defects per hundred units.

Examine	Defects
Marking (exterior and interior)	Omitted, incorrect, illegible, or improper size, location, sequence, or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Inadequate application of components, such as: incomplete closure of container flaps, loose strapping, improper taping, inadequate stapling, bulged or distorted container.
Content	Number of items per shipping container is more or less than required. Size shown on one or more items not as specified on shipping container. 1/

1/ For this defect, one item from each shipping container in sample shall be examined.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

4.4.4 Palletization examination. An examination shall be made to determine that palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the end item inspection lot. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5.

Examine	Defect
Finished dimension	Length, width, or height exceeds specified maximum requirements.
Palletization	Pallet pattern not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted; incorrect; illegible; of improper size, location, sequence, or method of application.

5. PACKAGING

5.1 Preservation. Preservation shall be level A or Commercial as specified (see 6.2).

5.1.1 Level A

5.1.1.1 Structural coat. Each structural coat shall be folded as follows:

1. Insert instruction manual into right patch pocket.
2. Fasten snaps and D-rings.
3. Place structural coat flat, front down.
4. Fold each side and sleeve towards center back of structural coat.
5. Each sleeve shall than be placed parallel to the folded sides of the structural coat.
6. Fold structural coat in half by bringing the bottom up toward the collar.

The folded structural coat shall measure approximately 23 inches by 15 inches. Each folded structural coat shall be banded with a commercially acceptable paper strip across the middle, with the ends secured with gummed paper tape.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

5.1.1.2 Proximity coat cover. Each proximity coat cover shall be folded as follows:

1. Place proximity coat cover flat face up.
2. Fold each sleeve over front and down so that top edge of sleeve is parallel to front opening.
3. Fold proximity coat cover in half by placing right side over left side.
4. Fold proximity coat cover in half again by bringing the bottom up towards the top.

The folded proximity coat cover shall measure approximately 23 inches by 15 inches. Each folded proximity coat cover shall include an instruction manual positioned so that it is visible, and sets of spare elbow patches individually packaged in their own snug fitting, clear polyethylene film bag conforming to A-A-50083. Each set of spare elbow patches shall be packed within the proximity coat cover unit pack.

5.1.2 Commercial. Structural coat and proximity coat cover shall be preserved in accordance with ASTM D 3951.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

5.2 Packing. Packing shall be level A, B or Commercial as specified (see 6.2).

5.2.1 Level A.

5.2.1.1 Structural coat. Five structural coats, of one size only, preserved as specified in 5.1, shall be packed in a shipping container conforming to style RSC-L, grade V2s, of PPP-B-636. The inside dimensions of the box shall be approximately 23-1/2 inches in length, 15-1/2 inches in width, and 15-1/2 inches in depth. Each box shall be closed, waterproofed, and reinforced in accordance with the appendix of PPP-B-636.

5.2.1.2 Proximity coat covers. Five proximity coat cover unit packs of one size only, with spare elbow patches included, preserved as specified in 5.1, shall be packed in a shipping container conforming to style RSC-L, grade V2s, of PPP-B-636. The inside dimensions of the box shall be approximately 23-1/2 inches in length, 15-1/2 inches in width, and 15-1/2 inches in depth. Each box shall be closed, waterproofed, and reinforced in accordance with the appendix of PPP-B-636.

5.2.2 Level B.

5.2.2.1 Structural coat. Five structural coats, of one size only, preserved as specified in 5.1, shall be packed in a shipping container conforming to style RSC-L, type CF (variety SW) or SF, class domestic, grade 275 of PPP-B-636. The inside dimensions of the box shall be approximately 23-1/2 inches in length, 15-1/2 inches in width, and 15-1/2 inches in depth. Each box shall be closed in accordance with method II as specified in the appendix of PPP-B-636.

5.2.2.2 Proximity coat cover. Five proximity coat cover unit packs of one size only, with spare elbow patches included, preserved as specified in 5.1, shall be packed in a shipping container conforming to style RSC-L, type CF (variety SW) or SF, class domestic, grade 275 of PPP-B-636. The inside dimensions of the box shall be approximately 23-1/2 inches in length, 15-1/2 inches in width, and 15-1/2 inches in depth. Each box shall be closed in accordance with method II as specified in the appendix of PPP-B-636.

5.2.3 Commercial packing. Structural coat and proximity coat cover with spare elbow patches included, preserved as specified in 5.1, shall be packed in accordance with ASTM D 3951.

5.3 Palletization. When specified (see 6.2), structural coat and proximity coat cover, packed as specified in 5.2.2 and 5.2.3, shall be palletized on a 4-way entry pallet in accordance with load type Ia of MIL-STD-147. Pallet type shall be type I (4-way entry), type IV or type V in accordance with MIL-STD-147. Each prepared load shall be bonded with straps in accordance with bonding means C and D or film bonding means F or G. Pallet pattern shall be 3 in accordance with the appendix of MIL-STD-147.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

5.4 Marking. In addition to any special marking required by the contract or purchase order, unit packs, shipping containers and unit loads shall be marked in accordance with MIL-STD-129 OR ASTM D 3951, as applicable.

5.4.1 Polyethylene bagged packages. Polyethylene bagged packages shall have the required identification information legibly printed or stamped in black directly on the bag across the center face or on a white paper label inserted within the bag so as to permit ready identification. The bag or label shall only indicate the following information:

STOCK NUMBER
NOMENCLATURE
SIZE
QUANTITY

5.5 MIL-STD-2073. When specified (see 6.2), Preservation and Packing shall be is accordance with MIL-STD-2073-1 and MIL-STD-2073-2.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The coats are intended for wear by DOD personnel engaged in fire fighting. The structural coat is for use by firefighters engaged in structural type fires. The structural coat with the proximity coat cover attached is for use by firefighters engaged in proximity type fire fighting.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title and date of this specification.
b. Types and sizes required (see 1.2)
c. Issue of the DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1 and 2.2).
d. When first article inspection is required (see 3.2), the item will be tested and should be a first article sample. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examination, quantity, testing, and approval of the first article.
e. Levels of preservation and packing required (see 5.1 and 5.2).
f. When palletization is required (see 5.3).
g. When all packaging data is to be found in MIL-STD-2073-1 and MIL-STD-2073-2 (see 5.5)

6.3 Samples and patterns. For access to samples and patterns, address the procuring activity issuing the invitation for bids (see 3.1, 3.3.13, and 3.5).

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

6.4 Recycled materials. It is encouraged that recycled materials be used when practical as long as it meets the requirements of this specification.

6.5 A suggested source of supply for moisture barrier material specified in 3.3.3 is Aldan Rubber Co., Tioga and Salmon Streets, Philadelphia, PA, 19134.

6.6 A suggested source of supply for the cloth, abrasion resistant material specified in 3.3.4 is Aldan Rubber Co., Tioga and Salmon Streets, Philadelphia, PA 19134 or Southern Mills, 6501 Mall Boulevard, P. O. Box 289, Union City, GA, 30291.

6.7 A suggested source of supply for the heat sealing tape specified in 3.3.7 is Electro Seal Corp., 55 West Anaque Ave., Pompton, NJ, 07442.

6.8 A suggested source of supply for the reflective tape specified in 3.3.8 is 3M Safety and Security Systems Division, St. Paul, MN, 55144.

6.9 A suggested source of supply for the plated zinc snap hooks and D-rings specified in 3.3.10.3 is Custom Metal Crafters Inc., Newington, CT 06111.

6.10 Equal item. Prior to the use of an "or equal" item, the contractor shall submit the item with supporting data to the contracting officer for subsequent approval or disapproval by the responsible Military Agency.

6.11 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

6.12 Subject term (key word) listing.

Cloth, para-aramid/PBI
Clothing, protective
Trousers, firefighters
Liner, quilted
Suit, firefighters, combination


Custodians:
Navy - NU
Air Force - 99

Preparing activity:
DLA-CT
Project No. 8415-0928


Review activities:
Navy - MC
Air Force - 82, 50, 45

User activities:
Navy - SH
Coast Guard - CG

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

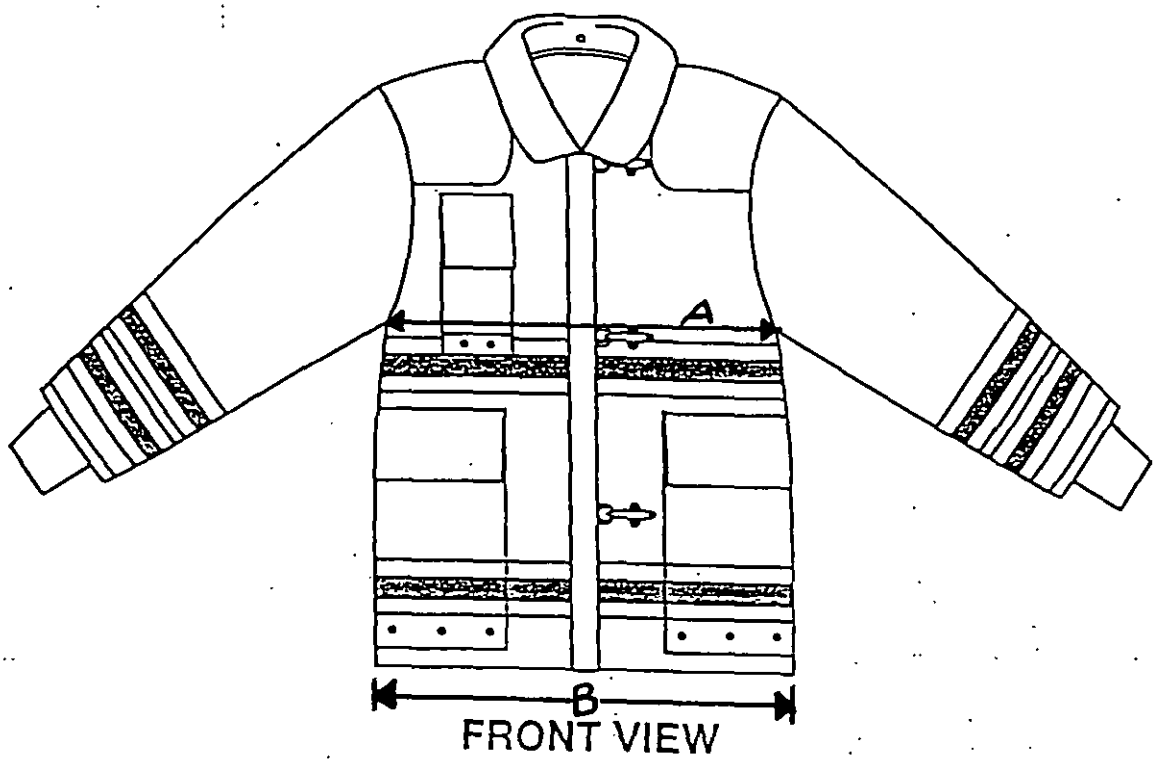


FRONT VIEW

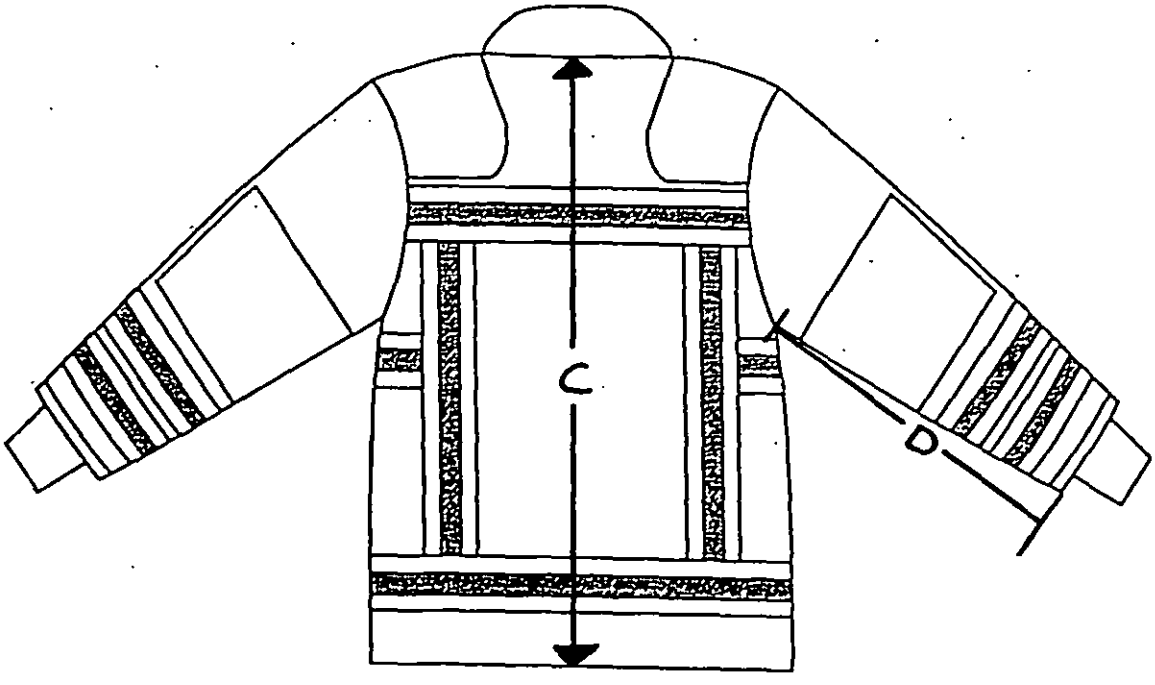


BACK VIEW

FIGURE 1
FIREMEN'S STRUCTUAL COAT

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

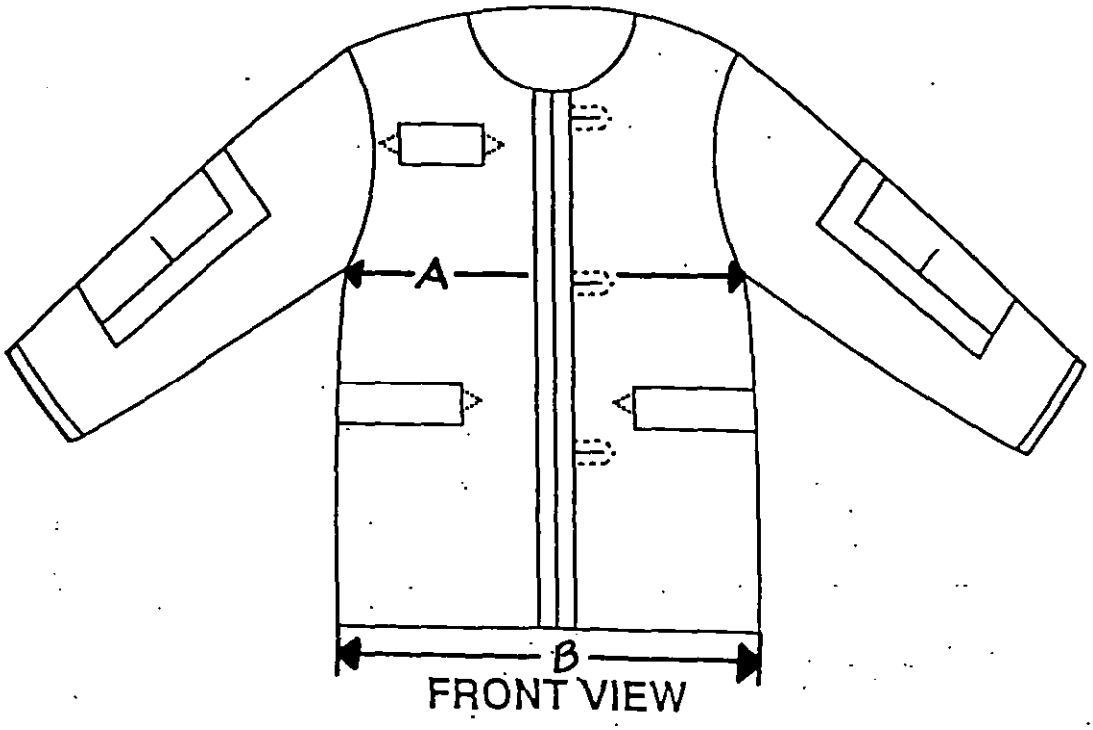

FRONT VIEW

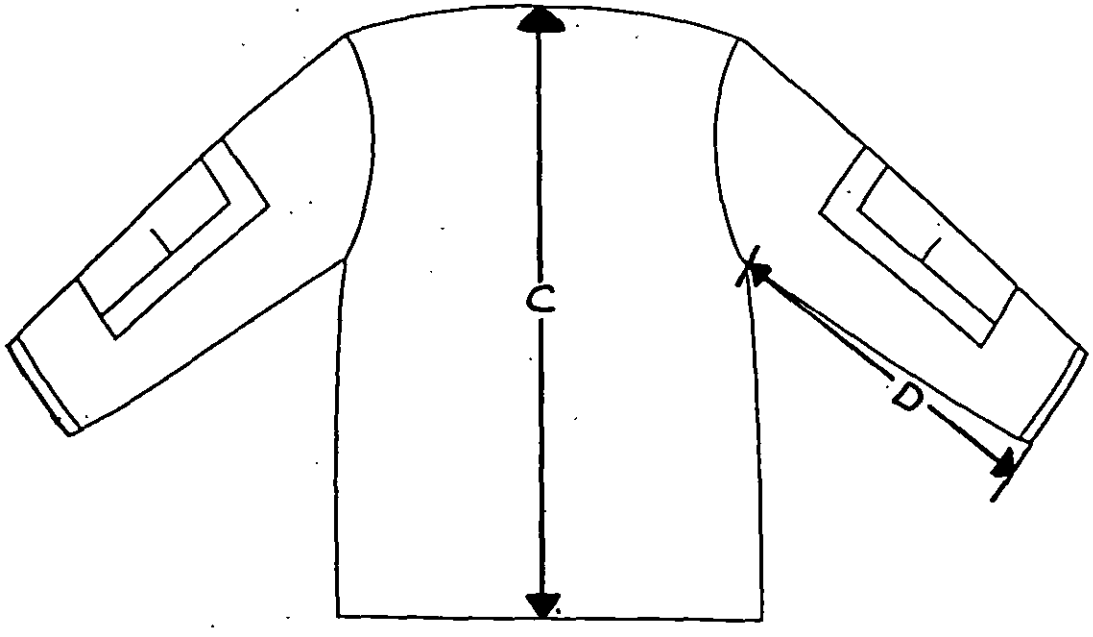

BACK VIEW

FIGURE 2
ALUMINIZED PROXIMITY OUTERSHELL

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

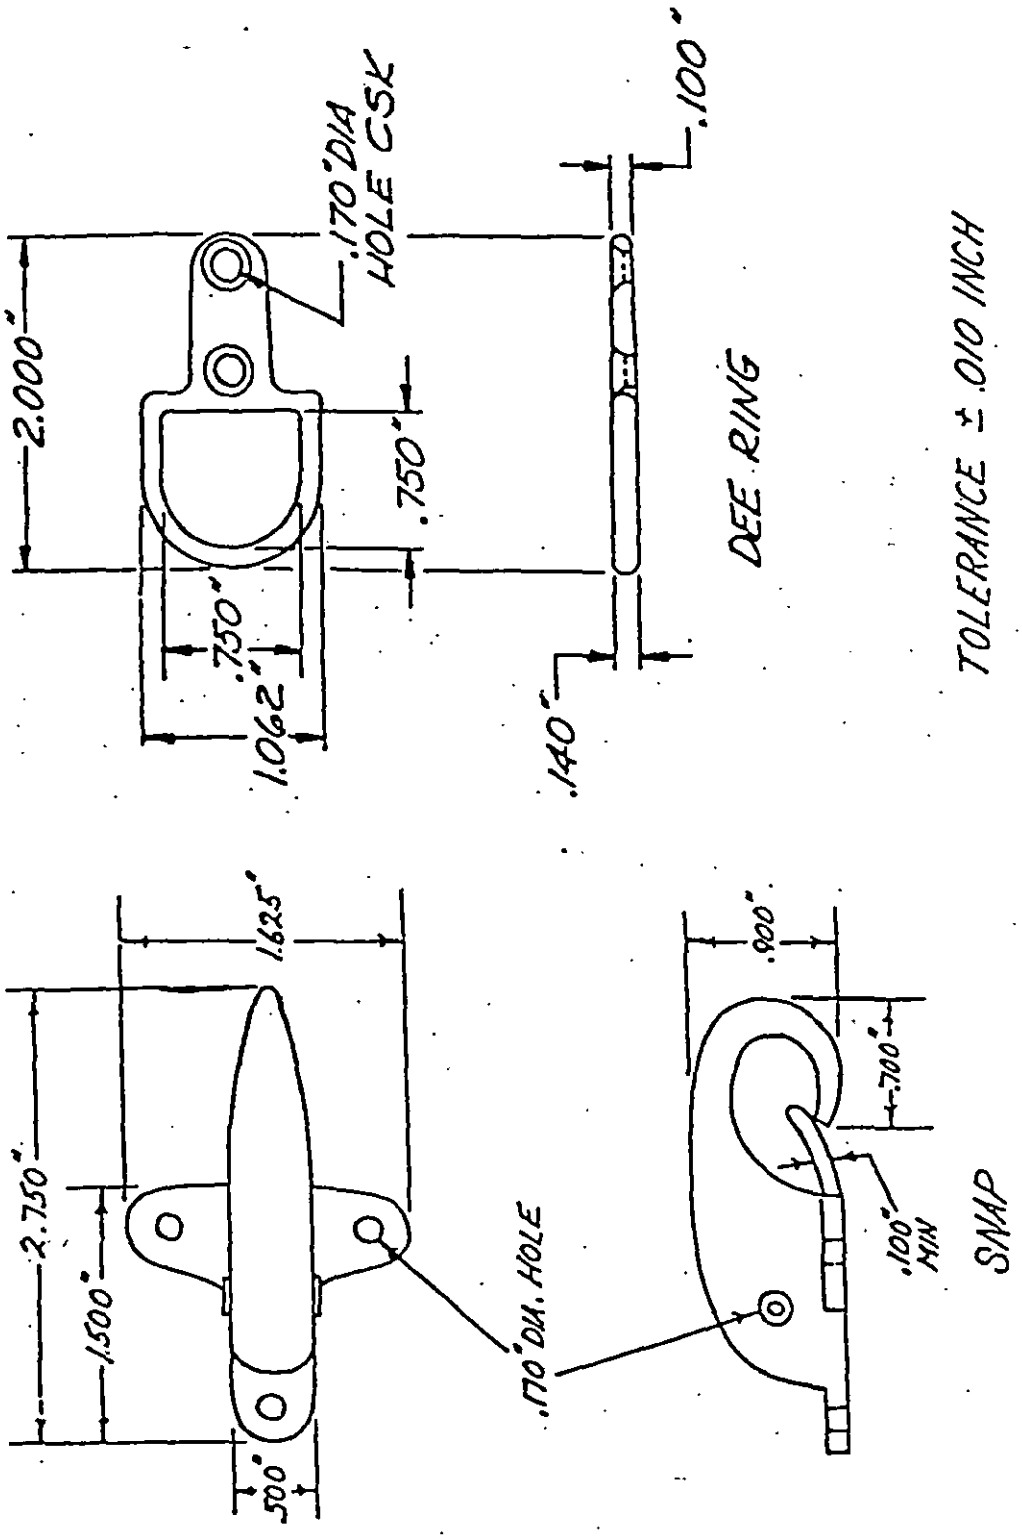


FIGURE 3

SNAP HOOK AND DEE RING

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:08Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER	2. DOCUMENT DATE (YYMMDD)
	MIL-C-24938A	930810

3. DOCUMENT TITLE

COAT, FIREMEN'S, STRUCTURAL/ALUMINIZED PROXIMITY

4. NATURE OF CHANGE (*Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.*)

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (*Last, First, Middle Initial*)	b. ORGANIZATION	
c. ADDRESS (*Include Zip Code*)	d. TELEPHONE (*Include Area Code*) (1) Commercial (2) AUTOVON (*If applicable*)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY

a. NAME Defense Personnel Support Center ATTN: DPSC-FSSD (12-3-D)	b. TELEPHONE (*Include Area Code*) (1) Commercial (2) AUTOVON
c. ADDRESS (*Include Zip Code*) 2800 South 20th Street P. O. Box 8419 Philadelphia, Pennsylvania 19101-8419	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340

Source: https://assist.dla.mil -- Downloaded: 20260120T03:08Z
Check the source to verify that this is the current version before use.