MIL-H-24925
14 September 1987

MILITARY SPECIFICATION

HOOD, FIREMAN'S ALUMINIZED, PROXIMITY, WITH LIFT-UP VISOR

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for a heat protective hood constructed from a para-aramid knit outer fabric having a highly reflective aluminized face with a protective lift-up visor.

1.2 Classification. The hood covered by this specification shall be of one type and size only.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: OFFICER IN CHARGE, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick, MA 01760-2490 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8415

DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

FEDERAL

L-P-377	- Plastic Sheet and Strip, Polyester
L-P-378	- Plastic Sheet and Strip, Thin Gauge, Polyolefin
FF-W-92	- Washer, Flat
NN-P-71	- Pallet, Material Handling, Wood, Stringer Construction, 2 Way and 4 Way (Partial)
RR-P-00560	- Post, Ledger and Binder, Screw Type
CCC-C-440	- Cloth, Cheesecloth, Cotton, Bleached and Unbleached
DDD-L-20	- Label; For Clothing, Equipage, and Tentage (General Use)
GGG-H-142	- Helmet; Construction Worker's
PPP-B-26	- Bag, Plastic (General Purpose)
PPP-B-636	- Box, Shipping Fiberboard
PPP-T-45	- Tape, Gummed, Paper, Reinforced and Plain for Sealing and Securing

MILITARY

MIL-W-530	- Webbing, Textile, Cotton, General Purpose, Natural or in Colors
MIL-W-5664	- Webbing, Textile, Elastic Cotton
MIL-F-10884	- Fasteners, Snap
MIL-P-15011	- Pallet, Material Handling, Wood Post Construction, 4-Way Entry
MIL-C-19699	- Cloth, Coated (Nylon Taffeta)
MIL-F-21840	- Fastener Tapes, Hook and Pile, Synthetic
MIL-C-24929	- Cloth, Laminated, Aluminized
MIL-T-43548	- Thread, Polyester, Cotton Covered and Rayon Covered
MIL-T-43636	- Thread, Aramid
MIL-C-43774	- Cloth, Plain or Pajama Check Weave, Aramid
MIL-T-44100	- Thread, Para-Aramid, Spun, Intermediate Modulus
MIL-A-46106	- Adhesive-Sealants, Silicone, RTV, General-Purpose (For Eletrical and Mechanical Sealing)
MIL-P-46144	- Plastic Sheet, Polycarbonate
MIL-B-87002	- Batting, Synthetic Fibers, Quilted Aramid

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
FED-STD-191	- Textile Test Methods
FED-STD-751	- Stitches, Seams, and Stitchings

MILITARY

MIL-STD-129	- Marking for Shipment and Storage
MIL-STD-147	- Palletized Unit Loads
MIL-STD-1666	- Classification of Defects for Evaluation of Quality of Aluminized Firemen's Clothing
MS 9358	- Nut, Castellated, Hexagon-A 286, MIL-S-8879
MS-24679	- Nut, Plain Cap, Low Crown Unc-2b, and Unf-2b
MS-27980	- Fasteners, Snap, Style 2 (Regular Wire Spring Clamp Type)
MS 35207	- Screw, Machine-pan Head, Cross Recessed, Carbon Steel, Cadimum Plated, Unf-2a
MS-51957	- Screw Machine Pan Head, Cross Recessed Corrosion Resisting Steel, Passivated, Unc-2a

DRAWINGS

NAVY CLOTHING AND TEXTILE RESEARCH FACILITY

16-1-836	- Hood Firefighters with Lift Up Visor
16-1-837	- Frame, Outer
16-1-838	- Frame, Inner
16-1-839	- Visor
16-1-840	- Frame, Side Visor Left
16-1-841	- Frame, Side Visor Right
16-1-842	- Face Shield Gold Coated Mylar
16-1-843	- Block, Helmet
16-1-844	- Block, Pivot Visor
16-1-845	- Strike
16-1-846	- Latch Assembly
16-1-847	- Chin Strap Assembly

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

LAWS AND REGULATIONS

U.S. POSTAL SERVICE MANUAL

(Copies of the manual may be obtained from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DODISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS shall be the issue of the nongovernment documents which is current on the date of the solicitation.

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Association, ATTN: Traffic Department, 1616 P Street, N.W., Washington, DC 20036).

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606).

JOINT COMMITTEE ON PRINTING (JCP) PUBLICATIONS
Government Paper Specification Standards

(Application for copies should be addressed to the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

AMERICAN SOCIETY FOR TESTING MATERIALS
ASTM-D-1003-61 - Haze and Luminous Transmittance
of Transparent Plastic, Test for

(Application for copies should be addressed to the American Society for Testing Materials, 1916 Race Street, Philadelphia, PA 19103.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

CODES FOR COMMERCIAL AND GOVERNMENT ENTITIES (CAGE)
Cataloging Handbook H4-1 (Name to Code) and H4-2 (Code to Name)

(Application for copies should be addressed to Defense Logistics Service Center, Federal Center, Battle Creek, MI 49017)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence. Nothing in this specification however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Guide sample. Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this specification may appear in the sample in which case this specification shall govern.

3.2 First article. When specified, the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3 and 6.2).

3.3 Material.

3.3.1 Basic material. The material for the outer shell of the hood shall be a knit para-aramid fabric laminated with a vacuum deposited aluminium on a .25 mil. polyester film on the face conforming to MIL-C-24929.

3.3.2 Quilted lining. The material for the quilted lining shall be aramid quilted batting conforming to type I of MIL-B-87002 except the use of recycled material (batting) is prohibited. The outer covering cloth shall conform to MIL-C-43774, except it shall have 69 filling yarns and the dimensional stability for warp and filling shall be 3 percent maximum.

3.3.3 Thread. The thread for assembling the outershell and for joining the outershell to the linings shall be a thread conforming to size T-50 of MIL-T-44100, natural in color. As an alternate non-melting nylon (Aramid), natural shade, conforming to Size B and E of MIL-T-43636 may be used.

3.3.4 Interlining. The material for interlining the quilted lining of the hood shall be coated nylon taffeta conforming to type II of MIL-C-19699 except the colorfastness to crocking shall be not less than "fair".

3.3.5 Elastic take-up strap . The material for the back take-up strap shall be elastic cotton webbing natural or dyed black conforming to class 1, of MIL-W-5664, 3/4 inch wide, except that the colorfastness requirements shall not apply.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.6 Snap fasteners. The snap fasteners for attaching the hood front cover flap to the visor, the bib to the hood front cover flap, and to adjust the bib shall consist of Button and Socket (female half), Stud and Eyelet (male half) and a combination Stud/Socket. The fasteners shall be style 2, 24-line (size 1) nickel plate or bright chrome finish conforming to MIL-F-10884, MS 27980 and the following part numbers:

Button - 1N or 1C	Socket - 6N or 6C
Stud - 7N or 7C	Eyelet - 8N or 8C.

3.3.7 Chin (take-up) adjustment strap assembly. The chin strap assembly shall be as shown in drawing 16-1-847 and shall consist of cotton webbing with a hook and pile fastener closure.

3.3.7.1 Hook and pile fastener tape. The hook and pile fastener tapes shall conform to type II, class 1 of MIL-F-21840. The tape shall be 5/8 inch wide for the chin strap, 1 and 2 inch wide for the frame cover assembly. The color shall be natural or black.

3.3.7.1.1 Webbing. The webbing shall be cotton, natural, bleached or dyed shade black conforming to type IIa, classes 1, 2, or 3, 3/4 inch wide conforming to MIL-W-530, except that the colorfastness requirements shall not apply.

3.3.7.1.2 Thread. The thread for assembling the chin strap shall be a thread conforming to ticket No. 50, 2 or 3 ply of MIL-T-43548. The color shall be natural or black.

3.3.8 Hood facepiece assembly.

3.3.8.1 Visor. The visor shall be polycarbonate sheeting conforming to MIL-P-46144, type I, grade A, clear, 0.125 (± 0.015) inch thick or equal. All dimensions shall be in accordance with drawing 16-1-839. The visor shall be coated with anti-fog coating "Izonex" by Exxene Corp. (see 6.4) or equal (see 4.4.1). Stud/Eyelet snap fasteners, and screws and posts shall be positioned according to drawing 16-1-839 with the studs on the outside of the visor.

3.3.8.2 Gold coated face shield. The material for the gold coated face shield shall be polyester type plastic film conforming to type III of L-P-377, except that the thickness shall be 0.007 (± 0.001) inch and the maximum haze factor shall be 9.2 percent. The gold coated face shield shall be gold coated on one surface and then overcoated with an abrasion resistant coating (see 4.4.1) by vacuum deposition or other suitable techniques. The gold coated side shall be identified with the word "outside" printed in black indelible ink letters of not less than 1/4 inch high along the edge of the sheet. The gold coated face shield shall be in accordance with drawing 16-1-842. It shall be positioned over the visor so that the "outside" surface is away from the visor as shown in Figure 1.

3.3.8.3 Performance. The performance of the gold coated face shield and visor shall be as indicated below when tested as specified in 4.4.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.8.3.1 Vertex power and prismatic power. The vertex power of the visor, excluding the area 3/4 inch from the outer edge, shall not exceed the inherent power to the required curvature and thickness by more than ± 0.06 diopters in any horizontal meridian when tested as specified in 4.4.1.1. The inherent power of the visor shall be calculated by use of the following equation:

$$F = (F_1 + F_2) \frac{-t}{n} F_1 X F_2)$$

$$F_1 = \frac{n-1}{r_1}, \quad F_2 = \frac{1-n}{r_2}$$

or

$$F = \frac{-t}{r_2 (r_2 + t)} 1 - \frac{1}{n}$$

F = Inherent power of the visor in diopters.

F_1 = Power of the front surface of the visor in diopters.

F_2 = Power of the back surface of the visor in diopters.

n = Index of refraction of the visor material.

t = Thickness of visor in meters.

r_1 = Radius of the front surface of the visor in meters.

r_2 = Radius of the back surface of the visor in meters.

The vertical prismatic components at any two points on any given horizontal meridian of the visor excluding the area 3/4 inch from the outer edge shall not differ algebraically by more than 0.125 prism diopter and the absolute vertical prismatic deviation measured from any point in any horizontal meridian shall not exceed 0.125 prism diopter when tested as specified in 4.4.1.1.

3.3.8.3.2 Optical distortion. The gold coated face shield and the visor shall be free from any visible distortion or optical defects when tested as specified in 4.4.1.2.

3.3.8.3.3 Luminous transmittance. The luminous transmittance of the visor shall be not less than 20 percent (illuminant C) when tested as specified in 4.4.1.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.8.3.4 Adhesion of coatings. The coatings on the gold coated face shield shall not be removed when subjected to the adhesion test specified in 4.4.1.4.1. If there is visual evidence that some of the coatings were removed, the tested area of the gold coated face shield shall be tested again for optical distortion, hardness of coatings, and infrared radiant heat resistance. The gold coated face shield shall be acceptable if it meets the requirements of the above tests after the adhesion test.

3.3.8.3.5 Hardness of coatings. The coatings on the gold coated face shield shall not be removed or show visible evidence of marring or abrasion when tested as specified in 4.4.1.4.2. If there is visual evidence that some marring or coating removal has occurred, the tested area of the gold coated face shield shall be tested again for optical distortion, luminous transmittance, and infrared radiant heat resistance. The gold coated face shield shall be acceptable if it meets the requirements of the above tests after the hardness test.

3.3.8.3.5.1 Cloth cheesecloth. The cheesecloth used in testing the hardness of coating for the gold coated face shield shall conform to type I, class 2 of CCC-C-440 (see 4.4.1.4.2).

3.3.8.3.6 Infrared transmittance. The infrared transmittance of the gold coated face shield shall be no greater than 10.0 percent between 1.0 and 7.5 microns when tested as specified in 4.4.1.5.

3.3.8.3.7 Infrared radiant heat resistance. The gold coated film shall show no holes or visual evidence of cloudiness or dullness when tested as specified in 4.4.1.6.

3.3.8.3.8 Frames, side visor. The visor side frames left and right shall be made of Aluminium 5052-H32, 0.092 inch thick stock in accordance with drawings 16-1-840 and 16-1-841 respectively. (see 4.4.1)

3.3.9 Hood support assembly.

3.3.9.1 Inner frame. The inner frame shall be made of Aluminum 6061-T3 or 6061-T4, 0.062 inch thick and shall conform to the dimensions shown in drawing 16-1-838. (see 4.4.1)

3.3.9.2 Outer frame The outer frame shall be made of Aluminum 6061-T3 or 6061-T4, 0.062 inch thick and shall conform to the dimensions shown in drawing 16-1-837. (see 4.4.1)

3.3.9.3 Seal. A P-configuration oven extruded rubber seal equivalent to North American Reiss Co. Part #1750 shall be positioned around the face opening of the outer frame in accordance with drawing 16-1-836. (see 4.4.1, 6.5 and 6.7)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.9.4 Silicone adhesive. RTV 108 Silicone Adhesive in accordance with MIL-A-46106, Type I (translucent) shall be used to attach the rubber seal to the outer frame. Care should be exercised when attaching the seal to assure proper adhesion is obtained (See Oper. 2 of Table I).

3.3.9.5 Machine screw. Pan head, cross recessed machine screws , corrosion resisting steel in accordance with MS-51957-29, CAGE No. 96906 shall be used around the face opening to attach the inner and outer frame to the hood as shown in drawing 16-1-836.

3.3.9.6 Nut, plain cap, low crown. A nut with plain cap and low crown in accordance with MS-24679-1, CAGE No. 96906 shall be used to secure the screws cited in 3.3.9.5. The nuts shall be used as indicated in drawing 16-1-836.

3.3.9.7 Machine screws. Pan head cross recessed machine screws, carbon steel cadium plated in accordance with MS 35207-265 CAGE No. 96906 and MS 35207-263, CAGE No.96906 shall be used to attach the visor assembly to frame, frame to helmet and to attach the latch assembly respectively as illustrated in drawing 16-1-836.

3.3.9.8 Nut, castellated, hexagon. Nuts, castellated, hexagon in accordance with MS-9358-09, CAGE 96906 shall be used to secure tne screws that attach the visor assembly to frame and the frame to the helmet. Positions shall be as indicated in drawing 16-1-836.

3.3.9.9 Latch assembly. A latch assembly in accordance with drawing 16-1-846 and Rexnord Part # 51L138-1X1BB or equal shall be used on both sides of the hood to secure the visor in a down position (see 4.4.1 and 6.6).

3.3.9.10 Strike. A stainless steel, Type 302, Finish 2B, 0.125 inch thick (8 GA) strike in accordance with drawing 16-1-845 shall be attached to each side frame to be used in conjunction with latch assembly to lock the visor in a down position (see 4.4.1 and 6.6).

3.3.9.11 Rivet. Solid rivets in accordance with CAGE 53551, RN AF085D-4 shall be used to attach the strike to the visor, side frames. Rivets shall be positioned as illustrated in drawings 16-1-847, 16-1-840 and 16-1-841.

3.3.9.12 Screw, post. Screw post assemblies with 8/32 Post and 8/32 x 1/4" screw in accordance with RR-P-00560 are used to secure the side frames to the gold coated face shield and visor. Placement of the screw post assembly is as illustrated in drawings 16-1-840 and 16-1-841.

3.3.9.13 Block, pivot. A pivot block made of Aluminum 6061-T3 or 6061-T4, (see 4.4.1) 0.186 inch thick as shown in drawing 16-1-844 shall be positioned on the outside of the hood to allow mobility of the visor.

3.3.9.14 Washer. A washer constructed from a fiber reinforced Chloroprene rubber 0.5 OD x 0.156 ID and 3/32" thick shall be positioned in between the side frame and pivot block as shown in drawing 16-1-836. The washer shall be suitable to hold the visor in an up position. (see 4.4.1)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.9.15 Helmet. The helmet shall conform to type II of GGG-H-142 and shall be adjustable from sizes 6-3/4 to 7-3/4 inclusive. Insulation resistance and chin straps are not required.

3.3.9.16 Helmet Block. The helmet block made of Aluminum 2024-T351 (see 4.4.1), 0.05 inch thick, shall be in accordance with drawing 16-1-843 and positioned between the helmet and inner frame.

3.3.9.17 Washer. An aluminum washer in accordance with FF-W-92 and the proper size shall be used to reinforce the screws holding the helmet block and chin strap assembly. Position shall be in accordance with drawing 16-1-836.

3.3.10 Instruction Manual. An instruction manual shall be furnished by the contractor with each hood. The manual shall be placed in the plastic bag with the repair kit and inserted behind the label. The printing, collation, folding and stitching of the manual shall be in accordance with the standard sample (see 6.3). The cover shall be antique white book paper conforming to Joint Committee Printing-A-100, 140 pound basis weight 25 X 38 inches per 1000 sheets. The text paper shall be white offset book paper conforming to JCP-A-60, 120 pound basis weight 25 X 38 inches per 1000 sheets. A sample of the manual plus a 5 x 4 inch glossy of the picture for the front cover shall be obtained from the contracting officer.

3.3.11 Repair Kit. The contents of the repair kit shall be as follows:

- Two each of the screws and nuts specified in 3.3.9.5 and 3.3.9.6 respectively
- Two each of the screws and nuts specified in 3.3.9.7 and 3.3.9.8 respectively
- Instruction manual as specified in 3.3.10

All components listed above shall be placed in a bag as specified in 3.3.12.

3.3.12 Bag, Plastic. The bags used to package the Instruction Manual and loose items of the repair kit shall conform to type I, style 3 of PPP-B-26. The bags shall be made of polyethylene film conforming to type I, class I, grade A, finish 1, of L-P-378. The size of the bags shall be suitable for the items and quantity intended.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.3.13 Identification and instruction label. Each hood shall have a combination identification and instruction label conforming to type VI, class 15, of DDD-L-20, except that the colorfastness requirements shall not apply. The label shall be large enough to insert the repair kit behind it. The label shall bear the following inscription:

HOOD, FIREMAN'S ALUMINIZED, PROXIMITY, WITH LIFT-UP VISOR
BASIC FABRIC: ARAMID (100%)
CONTRACT NO.: DLA-100-00-0-0000 (EXAMPLE)
STOCK NO.: 8415-00-000-0000 (EXAMPLE)
NAME OF CONTRACTOR:

USE AND CARE INSTRUCTIONS

PURPOSE

The gold-coated face shield and aluminized materials are reflective heat shields. The face shield is NOT a sun shield. Both items must be kept in good condition to reflect the heat radiation efficiently. In particular, when the face shield's gold surface becomes worn, scratched or marred, it should be immediately replaced, because 90% of the heat protection may be lost.

CARE

Gold Coated Face Shield

1. Keep the protective aluminized bib snapped in place over the visor when carrying or storing the hood to minimize damage to gold-coated surface. Unsnap the bib from the visor when using hood; the bib may be re-snapped below the visor, or it may remain completely unsnapped.

2. For adequate protection, replace worn out gold-coated face shield. Make sure the gold surface is on OUTSIDE as marked on the face shield.

3. Avoid touching or wiping the gold surface as much as possible.

4. After each use, clean the face shield, without removing it from the hood, using a clean, soft cloth with mild soapy water, rinse, and pat dry.

Aluminum Material

1. Hang or store hood properly to prevent damage to aluminized surface. Clean by gently rubbing aluminized surface with a soft cloth using either a mild soapy water, ISOPROPANOL or PERCHLORETHYLENE.

2. Do not use aluminized paint to repair worn surface as it will not provide protection.

NOTE: Aluminized coating is damaged by contact with Potassium Bicarbonate Powder (PKP). Before storing garment with PKP residue present, the following is recommended:

1. Dry powder should be removed with a clean soft brush or blower.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

2. Wet powder should be removed by thoroughly flushing with water and wiping the surface down with a clean soft cloth. Damp or wet hoods should be hung to dry.

REPLACEABLE STOCK HOOD COMPONENTS

1. Face Shield, Firemen's Hood (Gold Coated); NSN 8415-00-0-0000 (EXAMPLE)
2. Visor (Clear Plastic); NSN 8415-00-0-0000 (EXAMPLE)
3. Aluminum Fabric Hood,Component; NSN 8415-00-0-0000 (EXAMPLE)
4. Repair Kit; NSN 8415-00-0-0000 (EXAMPLE)

SOURCE - Defense Logistics Agency, 2800 South 20th Street, Philadelphia, PA 19101

3.3.14 Repairing aluminized surface. The unsupported aluminum film used for repairing exposed or cracked areas on the finished hood shall be the same as specified for laminating the para-aramid base cloth. The area to be repaired shall not exceed 1 inch in the longest direction. The repair patch shall be bonded onto the aluminum film and shall be so placed that it extends not less than 1/2 inch beyond all edges of the area to be repaired. No hood shall contain more than 6 patches. The unsupported aluminum film and self-curing adhesive used for repairing shall be obtained from the basic material supplier (see 3.3.1). The size of the patch shall not exceed 2 inches in any direction.

3.4 Design. The hood is made up of a fabric assembly constructed around a size-adjustable helmet with a chinstrap and supported by an aluminum framework. The hood has a polycarbonate lift-up visor with separate gold-coated polyester sheeting faceshield. The visor latches shut on each side over a sealing gasket around the face opening. The fabric assembly is a layered construction. The outer layer is aluminized fabric. The inner layer is aramid batting quilted between rayon and aramid woven fabrics. The rayon side of the quilted lining is next to the wearer. An attached bib snaps up over the faceshield to protect it when not in use. An elasticized take-up strap is positioned at center back. A carrying/hanging handle is provided at the bottom underside of the hood center back.

3.4.1 Figures. Miniature copies of Drawings 16-1-836 thru 16-1-847 and parts lists are attached for information purposes only. Figure 1 is considered part of this specification. When inconsistencies exist between the written specification and the figures, the specification shall govern.

3.5 Patterns. Standard patterns to be used to cut working patterns will be furnished by the Government (see 6.3). The patterns allow a 3/8 inch seam (aluminized outer shell assembly) and 1/2 inch seam (quilted lining-interlining inner shell assembly), except as otherwise indicated in Table I. The working patterns shall be identical to the Government patterns. Neither the Government patterns nor the working patterns shall be altered in any way.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

Pattern parts. The component parts for the hoods shall be cut from the materials specified in accordance with the following pattern parts:

Material	Nomenclature of Pattern Parts	Cut Parts
Cloth, laminated, knitted (outer shell)	Hood	1
	Bib	2
	Facing 1/	1
	Hood Front Cover Flap	2
	Take-Up Strap	1
	Hanger Loop	1
	Hood Front Cover	1
	Frame Cover	1
Cloth, coated, nylon taffeta (interlining)	Hood Interlining	1
Quilted assembly (lining)	Hood Lining	1

1/ Pattern may be cut as two pieces with a 3/8 inch seam allowance added for each piece.

3.6 Construction.

3.6.1 Stitch, seam and stitching types. Stitch, seam, and stitching types specified in Table I shall conform to FED-STD-751. Wherever two or more methods for seam or stitch types are given for the same part of the operation, any one may be used. Where stitch type 401 is used, the ends of stitching shall be caught in other seams or row(s) of stitching and the looper (underthread) shall be on the inside of the hood. Topstitching and edgestitching shall be 1/8 to 3/16 inch from the turned edge, except edgestitching of dome seam which shall be 3/16 to 1/4 inch from the turned edge. In order to minimize the size of needle hole in aluminized fabric, the needle used in the seaming operation shall be of the smallest size which will accommodate the specified size of thread. Wherever LSq-2 stitch type is specified, the top ply shall not be turned back sharply over the first row of stitching but turned in such a manner that a loose welt is formed. The bight of the serge stitching shall be 3/16 to 1/4 inch.

3.6.2 Thread breaks and ends of seams. Ends of all seams and stitchings when not caught in other seams or stitchings shall be backstitched not less than 3/8 inch. The ends of a continuous line of stitching shall be overlapped not less than 1/2 inch. Thread breaks (301 or 401 stitch types) may be repaired by 301 stitch type with the stitching anchoring both ends of the break.

3.6.3 Stitches per inch. The minimum and maximum number of stitches per inch shall be as specified in Table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.7 Manufacturing operations requirements. The hoods shall be manufactured in accordance with the operation requirements specified in Table I. The contractor is not required to follow the exact sequence of operations listed provided that the finished hoods are identical to those produced by following the sequence of operations as listed in Table I.

3.7.1 Abbreviations in table of operations. The abbreviations used in Table I are as follows:

Stch	-	Stitch
in	-	inch
Ndl	-	Needle
Bob	-	Bobbin
Lpr	-	Looper
Mchne	-	Machine
Brtck	-	Bartack
Comrcl	-	Commercial
smlr	-	similar
Btnhl	-	Buttonhole
incl	-	including
dbl	-	double

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL BOB/ LPR
1.	Make hardwear. All hardwear components shall be manufactured in accordance with drawings 16-1-837 thru 16-1-847.				
2.	Apply rubber seal. Position rubber seal on outer frame in accordance with drawing 16-1-836 and apply adhesive specified in 3.3.9.4 as follows: 1. Do not exceed the shelf life of the silicone adhesive. 2. Clean seal and frame surfaces with methyl ethyl ketone (MEK). 3. Pass seal along the feather of a gas flame. 4. Apply an even coat of silicone adhesive to the seal and set onto the frame, applying even pressure until set. 5. Allow adhesive to cure undisturbed for 24 hrs.				
3.	Cutting a. The hood shall be cut in strict accordance with patterns furnished which show placement of component parts, directional lines for cutting, and notches for proper assembly of all parts. A maximum swing of 2-1/2 inches from the directional line is permitted. Measurements shall be taken at the top and bottom of the directional line on the pattern to the selvage edge of the fabric on the even side of the lay. The difference between the two measurements shall not exceed 2-1/2 inches. Drill holes are permitted for positioning provided they are covered in the finished hood. Positioning of drill holes for hardware, before assembly shall be in accordance with the frames. NOTE: Patterns allow the quilted batting to be cut in any direction. b. The component parts of the para-aramid cloth may be cut from ends and when so cut shall finish with the aluminized side face up. A single splice on the side and bottom facings is permitted.				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. The quilted lining shall be cut in such a manner so that the aramid cloth side is against the uncoated side of the nylon taffeta interlining.					
	d. The coated nylon taffeta interlining shall be cut in such a manner so that the coated side of the material is against the uncoated side of the outer shell.					
	e. Cut elastic webbing for back take-up strap not less than 13-1/2 inches in length.					
	f. The face side of the materials to be assembled shall be considered as follows:					
	1. Outershell - aluminized side 2. Quilted batting - black rayon side 3. Interlining - coated side					
4.	Replacement of defective components During the spreading, cutting, and manufacturing process, components having material defects or damages that are classified as defects in MIL-STD-1666 shall be removed from production and replaced with nondefective and properly matched components.					
5.	Prepare Face Openings.					
	a. Cut out hood outershell on the cut lines at face opening. Notch each corner as indicated on the patterns. The shape of the face opening shall be as shown by fold lines on patterns.					
	Note: The uncoated side of the nylon taffeta interlining shall be against the aramid cloth side of the quilted lining.					
	b. Join the quilted lining and coated interlining together by stitching 3/16 to 1/4 inch from the raw edge or by overedge stitching all raw edges of assembly.	301 or 401 or 502 or 503 or 504	SSa-1	6-8 6-10	B or E B or E	B or E B or E

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. Cut out each ply of quilted lining and coated interlining material on the cut lines at face opening.					
	d. Stitch raw edges together around face cut-out 3/16 to 1/4 inch from raw edges.	301 or 401	SSa-1	6-8	B or E	B or E
6.	Make and attach bib.					
	a. Position bibs face to face and stitch 3/8 (+ 1/16) inch from raw edges of one end and sides.	301 or 401	SSe-2(a)	6-8	B or E	B or E
	b. Turn bib to finished position, work out edges and corners and topstitch sides and bottom.	301 or 401	SSe-2(b)	6-8	B or E	B or E
	c. Position bib on outershell hood front in the down position, according to marks on patterns and stitch 3/16 to 1/4 inch from raw edges. Turn bib up covering front opening and double stitch 1/8 to 3/16 inch from folded edge with a 1/4 inch gauge stitching.	301 or 401	LSd-2	6-8	B or E	B or E
	d. Attach two button/socket snap fasteners to the corners of the free edge of the bib as indicated by marks on patterns. Buttons shall finish on the outside when bib is in an up position.					
	e. Attach two studs/eyelet combination snaps to the corners of the attached end of the bib as indicated by marks on patterns. Studs shall finish on the inside when bib is in an up position. NOTE: All snap fasteners shall be positioned properly to mate with the corresponding part.					
7.	Join aluminized and innershell lining assemblies.					
	a. Position the inner shell assembly on top of the outershell so that the coated side of the interlining is against the uncoated side of the outershell.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	b. Turn in facepiece edges of the hood outershell to the underside over the quilted lining. Turn under raw edges 1/8 to 1/4 inch and topstitch 5/8 inch from the turned edges along all four sides through all plies of material.	301	Smlr LSn-1	6-8	B or E	B or E
8.	Attach fastener tape to hood.					
	a. Cut two 4-1/2 - 5 inch long and one 8-1/2 - 9 inch long by 1 inch wide pile fastener tapes. Join to quilted side of hood as indicated by pattern marks, stitching thru all plies all four sides, 1/8 inch from the edge.	301	LSbj-1	8-12	B	B
	b. Cut two 2-1/4 - 2-1/2 inch long by 2 inch wide pile fastener tapes. Join to quilted side of hood as indicated by pattern marks, stitching thru all plies all four sides, 1/8 inch from the edge.	301	LSbj-1	8-12	B	B
	NOTE: Drill holes shall go thru the pile tape (Oper. 8b) also to allow the hardware to be assembled.					
9.	Make frame cover.					
	a. Punch holes thru frame cover in accordance with the frames and as shown on the patterns.					
	b. Cut two 4-1/2 - 5 inch long and one 9 - 9-1/2 inch long by 1 inch wide hook fastener tapes. Join to back side of frame cover as indicated by pattern marks, stitching all four sides, 1/8 inch from the edge.	301	LSbj-1	8-12	B	B
	c. Cut two 2-1/4 - 2-1/2 inch long by 2 inch wide hook fastener tapes. Join to back side of frame cover as indicated by pattern marks, stitching all four sides, 1/8 inch from the edge.	301	LSbj-1	8-12	B	B
	d. Notch the corners of the face opening as indicated on the patterns.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
10.	Prepare aluminized outer shell assembly Dome seam joining the left and right sections of the hood shall be uniformly stitched and carefully sewn to avoid twisting or pleating and finish evenly. NOTE: Slitting and spreading of lapped seam for a distance of approximately 1 inch shall be permitted at the dome and dome dart seam junction.					
	a. Join face to face, 3/8 (+ 1/16 inch) from the raw edge, the dome seam of the right and left sections of the hood outershell. Turn joining seam face side up to form a loose welt and stitch 3/16 to 1/4 inch from the turned edge. An adjustable hinged raising foot may be used in forming the loose welt seam. The left section shall overlap the right section. NOTE: The dome darts shall be carefully tapered to avoid unsightly bulging, with ends securely tacked	301	LSq-2	6-8	B or E	B or E
	b. Join face to face, 1/2 (+ 1/16) inch from the raw edge, the horizontal dome darts of the right and left sections of the hood outershell in one continuous operation as indicated by notches on pattern. Turn joining seam and edgestitch 1/8 to 3/16 inch from the turned edge with the fold towards the face opening.	301	LSq-2	6-8	B or E	B or E
	c. Join face to face, 1/2 (+ 1/16) inch from the raw edge, the horizontal dome darts of the right and left section of the hood inner shell assembly as indicated by notches on pattern in one continuous operation.	301 or 401	SSa-1	6-8	B or E	B or E
11.	Make and attach hood front cover and hood front cover flap. a. Position one button/socket snap combination on the center of the inside Hood Front Cover Flap as indicated by pattern marks with the socket finishing on the outside.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	b. Position Hood Front Cover Flaps face to face and stitch 3/8 (+ 1/16) inch from sides and one long end.	301 or 401	SSe-2(a)	6-8	B or E	B or E
	c. Turn flap to finished position working out edges and corners and topstitch folded edges.	301 or 401	SSe-2(b)	6-8	B or E	B or E
	d. Position Hood Front Cover Flap on the Hood Front Cover face to face according to the notches on the cover. Stitch 1/4 inch from raw edges.	301 or 401	LSq-2(a)	6-8	B or E	B or E
	e. Turn in all edges of Hood Front Cover and Hood Front Cover Flap 3/8 inch and topstitch 1/16 inch from folded edges.	301 or 401	Efa-1 LSq-2(b)	6-8	B or E	B or E
	f. Position two combination socket/stud Snaps on the Hood Front Cover Flap, according to marks on patterns, with the sockets finishing on the inside.					
12.	Attach facing and label.					
	a. Join face to face, 3/8 (+ 1/16) inch from the raw edge, the ends of the aluminized facing pieces. Spread seam and stitch 1/8 to 3/16 inch from each side of the joining seam. (Omit this operation if cut from one piece)	301 or 401	SSz-3	6-8	B or E	B or E
	b. Position the bottom of aluminized facing pieces, as applicable, on the rayon side of the quilted assembly, raw edges together and stitch together along outside raw edges 1/8 to 3/16 inch from edge.	301 or 401	SSa-1	6-8	B or E	B or E
	NOTE: Spliced facing shall be prestitched (see oper. 12a).					
	c. Turn under 3/8 to 1/2 inch the inner edge of aluminized facings and topstitch 1/8 to 3/16 inch from the folded edge to the inner shell lining assembly.	301 or 401	LSd-1	6-8	B or E	B or E

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	d. Attach label by simultaneously catching the bottom edge of label while performing topstitching in operation 12c. The label shall be positioned at back of hood on either the right or left section approximately 1/2 to 1 inch from the dome seam. Stitch 1/16 to 1/8 inch from the edge the two sides of label, leaving the top of the label open to insert the Repair Kit. (See Para. 3.3.11)	301	LSbj-1	6-8	B or E	B or E
	e. Join, face to face, 1/2 (± 1/16) inch from the raw edge, the dome seam of the right and left sections of the inner shell, catching the free end of aluminized facing between the plies.	301 or 401	SSa-1	6-8	B or E	B or E
	f. Stitch 1/16 inch from bottom raw edge of facing catching the innershell in the stitching.	301 or 401	SSa-1	6-8	B or E	B or E
	g. Fold bottom edge of the outer shell as indicated on patterns against the aluminized facing prejoined to the inner shell lining assembly. Turn in raw edge 3/8 to 1/2 inch and stitch 1/8 to 3/16 inch from the turned edge thru all plies, forming a 3/4 to 7/8 inch hem along the periphery.	301	LSd-1	6-8	B or E	B or E
13.	Attach hood front cover to hood.					
	a. Position Hood Front Cover on hood according to pattern mark and stitch the back edge to the hood through all plies 1/4 inch from raw edge.	301	LSd-1	6-8	B or E	B or E
14.	Make and attach hanger loop					
	a. Fold hanger loop part in accordance with marks on pattern. Turn under top layer 1/4 to 5/16 inch along its length and stitch 1/8 to 3/16 inch from folded edge down center of loop.	301	Smlr to EFj-1	6-8	B or E	B or E

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	b. Position and center the formed hanger loop horizontally across the center back seam of facing according to facing pattern marks with bottom edge of loop 1-1/2 to 1-3/4 inches from folded bottom edge of hood. Turn under ends as indicated by marks on pattern and stitch to hood through all plies with a 5/8 (+ 1/16) inch cross boxstitch.	301	Box-criss-cross	6-8	B or E	B or E
	c. The finished hanger loop shall measure 5 (+ 1/4) inches long and 3/4 to 7/8 inch wide.					
15.	Make and attach rear tape-up strap					
	a. Position a single piece of elastic webbing on the uncoated side of the rear take-up strap 1/4 inch below center fold and on the underply side (as formed). Stretch full length and position ends 2-1/4 inches from the finished ends of the aluminized strap. Stitch both ends of elastic to the underply of the strap. Fold rear take-up strap in half lengthwise with the aluminized face side in. Stitch the ends 1/2 (+ 1/16) inch from the raw edge.	301	SSa-1	6-8	B or E	B or E
	b. Trim corners and turn to finished position working out corners. Turn in bottom raw edges 1/2 inch and stitch 1/8 to 3/16 inch from both long edges and ends. The elastic webbing shall not be caught in the seaming.	301	SSc-1	6-8	B or E	B or E
	c. Stitch the rear take-up strap to hood as indicated by marks on hood pattern, forming a 1-7/16 (+ 1/16) inch wide by 2-3/4 (+ 1/4) inches long cross boxstitch.	301	Box-criss-cross stitch	6-8	B or E	B or E

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
16.	Make chin strap.					
	a. The finished lengths shall be in accordance with drawing 16-1-847.					
	- Straps shall be measured from outer folded edge of hem to point of attachment at inner side of helmet					
	b. Attachment of pile fasterner tape shall be in accordance with drawing 16-1-847.	301	LSbj-1	6-8	50	50
	c. Attachment of hook fasterner tape shall be in accordance with drawing 16-1-847.	301	LSbj-1	6-8	50	50
	d. Assembly of the unfinished ends for both straps shall be in accordance with drawing 16-1-847.	301	EFb-1	6-8	50	50
	e. Chin strap shall be attached to the helmet on the left side with the pile facing the chin; on the right side with the hook facing away from the chin.					
17.	Clean hoods					
	a. Trim all ends of thread and remove all loose thread.					
	b. Remove all spots and stains.					
	NOTE: Care shall be taken in the use of the solvents for cleaning to assure that the coating on the aluminized material is not damaged.					
18.	Insert Repair Kit.					
	a. Place one repair kit behind the label.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

TABLE 1 - CONSTRUCTION OF HOODS

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL BOB/ LPR
19.	Assembly of Hood				
	a. Position the Aluminum Fabric Hood Component and Frame Cover between the inner and outer frames and attach hardwear and visor as illustrated in drawing 16-1-836.				
	b. Tighten all screws with the appropriately sized hand tools. Adjust latches by turning to lenghten or shorten latching mechanism so that the seal is closed around the face opening when visor is latched shut.				
	c. Drill holes for assembly of hardwear shall be in accordance with the frames. All holes in the fabric component shall line up with holes in the frame and there shall be no twisting, pulling or distortion of the fabric in the finished hood. The adhesive specified in para. 3.3.9.4 may be used to hold the Frame Cover in place.				
	d. The visor shall be latched shut and the bib shall be snapped over the visor in the final assembly				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

3.8 Workmanship. The finished hoods shall conform to the quality established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

4.3 First article inspection. The first article submitted in accordance with 3.2 shall be inspected for compliance with design, construction, workmanship, appearance, and dimensional requirements.

4.4 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-1666 and the following, except where otherwise indicated.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

DEFECTS	CLASSIFICATION MAJOR	MINOR A	MINOR B
HOOD SUPPORT ASSEMBLY			
1. Frame not conforming to specified dimensions.	X		
2. Hardwear not assembled as specified, will not serve intended purpose.	X		
3. Rubber seal on frame not securely attached:			
a. Gaps in application of adhesive or unadhered portions of seal.	X		
b. Adhesive or seal peeling from aluminum frame.	X		
CHIN STRAP.			
1. Finished length of straps not as specified		X	
2. Pile fastener tape finishes not facing the chin.			X
3. Hook fastener tape finishes facing the chin.			X
4. Not attached properly to frame assembly.	X		
FINISHED HOOD ASSEMBLY			
1. Frame Cover does not cover inner frame on sides and bottom.		X	
2. Visor not sealed around face opening when hood is latched:			
a. Latches improperly adjusted		X	
b. Seal cannot be effected			X
3. Bib does not attach properly to Hood Cover			X
4. Instruction Manual and repair kit not positioned properly			X
5. Contents of repair kit not as specified			X
6. Latch and Strike do not engage/disengage properly		X	
7. Location of snaps on bib, visor and hood cover not as specified. i.e. difficulty in mating		X	
8. Screws not tightened:			
a. No force required to unscrew any screw		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

DEFECTS	CLASSIFICATION MAJOR	MINOR A	MINOR B
b. Minimal force required to unscrew:			
1. Fewer than 3 screws			X
2. 3 screws or more but fewer than half		X	
3. More than half	X		
9. Visor when attached to frame will not swivel	X		
10. Visor when attached to frame cannot be held firmly at the desired angle when tilted upward	X		

4.4.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable procurement documents. A certificate of compliance shall be furnished for the following requirements: Rubber seal in 3.3.9.3, Latch in 3.3.9.9, Strike in 3.3.9.10, Aluminum requirements in 3.3.8.3.8, 3.3.9.1, 3.3.9.2, 3.3.9.13, and 3.3.9.16, Stainless steel requirements in 3.3.9.10, fiber reinforced chloroprene rubber in 3.3.9.14, and coatings of 3.3.8.2. In addition, testing shall be performed on the components listed for the characteristics noted in Table II. The methods of testing specified in FED-STD-191, wherever applicable and as listed in Table II shall be followed. The physical and chemical values specified in Section 3, except where otherwise specified, apply to the average of the determinations made on the sample unit for test purposes as specified in the applicable test methods. All test reports shall contain the individual values utilized in expressing the final results. The lot shall be unacceptable if one or more sample units or lots average fail to meet any of the test requirements specified. The sample size shall be in accordance with the following:

Lot size	Sample size
2	800 or less
3	801 thru 22,000
5	22,001 and over

The lot size expression and sample units for testing shall be as follows:

Component	Lot Size Expression	Sample Unit
Visor	Each	2 visors
Gold Coated Face Shield	Each	10 faceshields

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

Table II - Testing of components

Component	Characteristic	Requirement	Test Method Paragraph
Visor	Vertex and prismatic power	3.3.8.3.1	4.4.1.1
	Optical distortion	3.3.8.3.2	4.4.1.2
Gold Coated face shield	Optical distortion	3.3.8.3.2	4.4.1.2
	Luminous transmittance	3.3.8.3.3	4.4.1.3
	Adhesion of coating	3.3.8.3.4	4.4.1.4.1
	Hardness of coating	3.3.8.3.5	4.4.1.4.2
	Infrared transmittance	3.3.8.3.6	4.4.1.5
	Infrared radiant heat resistance	3.3.8.3.7	4.4.1.6

4.4.1.1 Vertex and prismatic power. The visor shall be tested for vertex and prismatic power with a telescope lensometer, projection lantern, or any other suitable instrument, to determine conformance to 3.3.8.3.1.

4.4.1.2 Optical distortion. The visor, excluding the area 3/4 inch from the outer edge, shall be viewed from the wearer's position with the unaided eye for visible distortion and optical defects to determine conformance to 3.3.8.3.2. The definition of "unaided eye" shall be a person who possesses 20/20 or better visual acuity without spectacles.

4.4.1.3 Luminous transmittance. The gold coated face shield, excluding the area 3/4 inch from the outer edge, shall be tested in accordance with ASTM-D-1003-61 to determine conformance to 3.3.8.3.3.

4.4.1.4 Durability of coatings. Before and after subjecting the gold coated face shield to any durability of coating test, the gold coated face shield shall be thoroughly and carefully cleaned to remove dirt, film, fingermarks, and grease using mild soapy water followed by a thorough rinsing and drying with a soft, lintless, facial tissue pad.

4.4.1.4.1 Adhesion of coating. A strip of cellophane tape shall be firmly pressed to the center of the coated surface parallel to the 8.8 inch side starting at one edge and allowing 1-3/4 inches of the tape to extend over the other edge. The cellophane tape shall be 1 inch in width by 10 inches in length and shall possess a minimum adhesion value of not less than 40 ounces per inch of width. The free end of the tape shall be double backed at 180 degrees and pulled parallel to the facepiece surface. The tape shall be removed quickly with a snap action which exerts the greatest possible stripping effect on the coatings. The tested face shield area shall be visually examined for conformance to 3.3.8.3.4. Examination of the cellophane tape surface will aid in determining whether any of the coating has been removed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

4.4.1.4.2 Hardness of coatings. A pad of bleached cheesecloth (previously laundered), one inch in diameter, 1/2 inch in thickness, shall be rubbed for 25 cycles lengthwise across the gold coated surface of a 3-1/2 by 8 inch specimen. The 8 inch side shall be considered the lengthwise direction for this test. Either a stationary or dynamic force of two pounds shall be applied. If a stationary pressure is chosen, then the gold coated surface of the specimen shall be cycled in its lengthwise direction under the stationary abradant (cheesecloth pad) for 25 cycles at one second per cycle. If a dynamic pressure is chosen, the abradant (cheesecloth pad) shall be rubbed lengthwise across the gold coated surface of the specimen for 25 cycles at one second per cycle. A cycle shall consist of a rubbing motion extending from one edge to the extreme opposite edge and back. The area shall be examined for conformance to 3.3.8.3.5.

4.4.1.5 Infrared transmittance. The gold coated face shield shall be tested for infrared transmittance with a double beam infrared spectrophotometer capable of providing a continous reading of 1 - 7.5 microns, or as an option, from 1 - 3 microns, the readings shall be taken at 0.1 micron intervals and for 3 - 7.5 microns, the readings shall be taken at 0.5 micron intervals to determine conformance to 3.3.8.3.6. A 2 by 8 inch strip is cut from each face shield. From the latter, four 2 by 2 inch squares are cut. Two of the squares are treated with aqual regia to remove gold coating. The plastic substrate is immediately washed with distilled water and dried. In cases where a plastic overcoat is present, more time will be required before the gold is dissolved and the overcoat will begin to separate. The plastic substrates must be carefully handled because they will be employed in the adjustment of the instrument for compensation. Positioning the clear plastic substrate in the instrument (one in each channel) the wavelength is set at a particular value of interest. All instrumental settings are made for optimum response between zero and 100%. The gold-coated sample is then inserted in place of the substrate in the sample beam and its transmittance recorded for the particular wavelength setting. In all measurements, the substrate in the reference beam is never removed.

4.4.1.6 Infrared radiant heat resistance. The apparatus for conducting the heat resistance tests shall be in accordance with Figure 1 of MIL-C-24929. The heat source shall consist of a bank of five, 500 W, infrared, tubular, translucent quartz lamps having a 5 inch lighted length and a mean overall length of 8-13/16 inches. The lamps shall be mounted so that the lamp's surfaces are approximately 0.015 inch apart. The bank or array shall be mounted and centered behind a 2-1/4 by 5-1/2 inch cutout on 1/2 inch transite board. A specimen holder plate with a 2-1/2 by 6 inch center cutout shall be positioned so that the distance from the nearest lamp surfaces to the test specimen is exactly one inch. The quartz lamp shall be heated electrically and the power input controlled by means of a variac having a capacity of at least 25 amps. A voltmeter, accurate to $\pm$ 1 volt shall be installed on the load circuit to indicate operating or load voltage to the lamps. The quartz lamp shall be operated at 82 operating volts and the temperature indication of the array shall be $2730^{\circ}F \pm 10^{\circ}F$ ($1499 \pm 5.6^{\circ}C$). The individual lamps in the array shall not vary more than $\pm 25^{\circ}F$ ($\pm 13.9^{\circ}C$) from the average temperature. Adjustment may be made in the variac setting to produce the required temperature. Temperature indications shall be made at the center of the lamps using an optical type pyrometer.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

Test procedure. The test specimen shall be approximately 3-1/2 by 8 inches. Before positioning specimen holder in front of the heat source, apply current to the lamps and adjust variac to obtain 82 operating volts as indicated by the voltmeter. The individual lamp temperature shall be determined by a properly scaled optical type pyrometer. The temperature indications shall be taken along the center line of the individual lamps, not between the lamps. The average temperature of the array shall be 2730° + 10°F (1499 + 5.6°C) and the individual lamps shall not vary more than ± 25°F (± 13.9°C) from the average temperature. Adjustments may be made in the variac setting to obtain the specified temperature. The variac setting shall be undisturbed and current to the lamps shall be shut off. The side of the gold coated face shield marked "outside" shall be considered the face for test purposes. The specimens shall be placed on the back of the face plate of the specimen holder so that the face of the test specimen completely covers the window of the holder plate and faces the heat source when positioned in front of the quartz lamp array. The test specimen shall be held securely to the holder plate by taping all four sides with a pressure sensitive tape. The tape should not overlap the window or be exposed directly to radiation. The distance from the specimen to the nearest edges of the lamp surface shall be exactly one inch. Current shall be applied to the lamps and the specimen shall be exposed for 300 seconds. Timing shall start when the current is applied to the lamps and terminate when the current is shut off. The specimen holder shall be removed from the apparatus and the test area visually examined for conformance to 3.3.8.3.7.
Report. Five specimens shall be tested from each unit of product. Failure of any one specimen shall constitute failure of the unit of product.

4.4.2 Examination of the end item. The end item examination provisions for the finished hoods shall be as specified in MIL-STD-1666.

4.4.3 Examination of packaging requirements. The examination of packaging requirements shall be as specified in MIL-STD-1666.

4.5 Palletization examination. An examination shall be made to determine that the palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the end item inspection lot. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5 as specified in MIL-STD-105.

Examine	Defect
Finished dimensions	Length, width, or height exceeds specified maximum requirements.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits
Marking	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Preservation-packaging. Preservation-packaging shall be level A or C as specified (see 6.2).

5.1.1 Level A. Each hood, with the bottom neatly folded inside the dome of the hood, shall be individually packaged in a snug-fitting clear polyethylene film bag having a film thickness of not less than 0.003 inch. All seams and closures shall be formed by heat sealing. A 1/4 inch diameter hole shall be made at one corner of each bag to allow excess air to escape. As an alternate, the polyethylene bag may be of the tuck-in or reverse flap type, in which a heat seal closure and corner hole are not required. The open end of the bag shall be of sufficient length so that it can be folded over. The bag may be fabricated from polyethylene film tubing or sheeting. Each hood shall then be placed in a snug-fitting fiberboard box conforming to style RSC, type CF, class domestic, variety SW, grade 200 of PPP-B-636. The top and bottom flaps of the box shall be securely sealed with gummed paper tape, 3 inches in width conforming to type III, grade B of PPP-T-45.

5.1.2 Level C . Hoods shall be packaged to afford adequate protection against physical damage during shipment from the contractor to the first receiving activity. The package and the quantity per package shall be the same as that normally used by the contractor for retail distribution.

5.2 Packing. Packing shall be level A, B, or C, as specified (see 6.2).

5.2.1 Level A. Six (6) hoods, of one type only, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container, as follows: Place the packages flat, three along the length, one across the width and two in depth, with the length of the packages parallel to the end panels of the container. The shipping container shall conform to style RSC, type CF, variety DW, class weather-resistant, grade V15c of PPP-B-636. The shipping container shall be closed, waterproofed and reinforced in accordance with method V requirements of the appendix of the container specification.

5.2.2 Level B. Six (6) hoods, of one type only, packaged as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container, as follows: Place the packages flat, three along the length, one across the width, and two in depth, with the length of the packages parallel to the end panels of the container. The shipping container shall conform to style RSC, type CF, class domestic, variety DW, grade 275 of PPP-B-636. The shipping container shall be closed in accordance with method II as specified in the appendix of the container specification.

5.2.3 Level C . Hoods, Face Shields, Visors and Aluminum Fabric Hood Component packaged as specified in 5.1.2, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. The quantity per shipping container shall be the same as that normally used by the contractor for retail distribution. Containers shall comply with the U.S. Postal Service Manual, Uniform Freight Classification Rules or National Motor Freight Classification Rules, as applicable.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

5.3 Palletization. When specified (see 6.2), hoods packaged as specified in 5.2, shall be palletized on a 4-way entry pallet in accordance with load type Ia of MIL-STD-147. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means C, K, and L or O or P. Pallet pattern shall be in accordance with the appendix of MIL-STD-147.

The pallet shall be a 4-way , Type IV, V or VIII, Class 1, Style A, Size 2, wood group I, II, III or IV, Grade A of NN-P-71, or 4-way, Style 1, Size A, Type I, Class 1 of wood group I, II, III or IV, Grade A of MIL-P-15011. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the patterns specified in MIL-STD-147, the pallet pattern used shall be approved by the contracting officer.

5.4 Marking. In addition to any special marking required by the contract or order, interior packages and shipping containers shall be marked in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use. The hood is intended to be worn as follows:

The hood is to be used with Coat, Trousers, and Gloves, Aluminized, Proximity as part of an ensemble for personnel rescue and fighting aircraft fires on air fields.

The hood is also used with the Coveralls and Gloves, Aluminized, Proximity as part of an ensemble for personnel rescue and fighting aircraft fires aboard aircraft carriers.

The two ensembles rely on the simultaneous use of water and foam and any other firefighting or damage control equipment to provide maximum protection while the wearer approches and operates close to the fire.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number, and date of this specification
b. When first article is required (see 3.2), the item will be tested and should be a first article sample. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examination, quantity and testing and approval of the first article.
c. When faceshield, visor, alumunium fabric hood or repair kit (see 3.3.13) is required.
d. Selection of applicable levels of packaging and packing (see 5.1 and 5.2)
e. When palletization is required (see 5.3)

6.3 Samples and patterns. For access to samples and patterns, address the procuring activity issuing the invitation for bids.

6.4 Anti-Fog Coating. A suggested source of supply for the anti-fog coating is Exxene Corp., Addison, IL 60101.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

6.5 Rubber Seal. A suggested source of supply for the rubber seal is North American Reiss Co., Homestead Road, Belle Mead, NJ 08502

6.6 Latch and Strike Assembly. A suggested source of supply for the latch and strike assembly is Rexnord Specialty Fastener Division, 601 Route 46 West, Hasbrouke Heights, NJ 07604.

6.7 Equal item. Prior to the use of an "or equal" item, the contractor shall submit the item with supporting data to the contracting officer for subsequent approval or disapproval by the responsible Military Agency.

Custodian:
Navy - NU
Army - GL
Air Force - 99

Review Activities:
Navy - MC
Army - MD
Air Force - 82
DLA - CT

User Activities:
Navy - AS, SH, CG
Air Force - 45

Preparing Activity:
Navy - NU

Project No. 8415-0557

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.


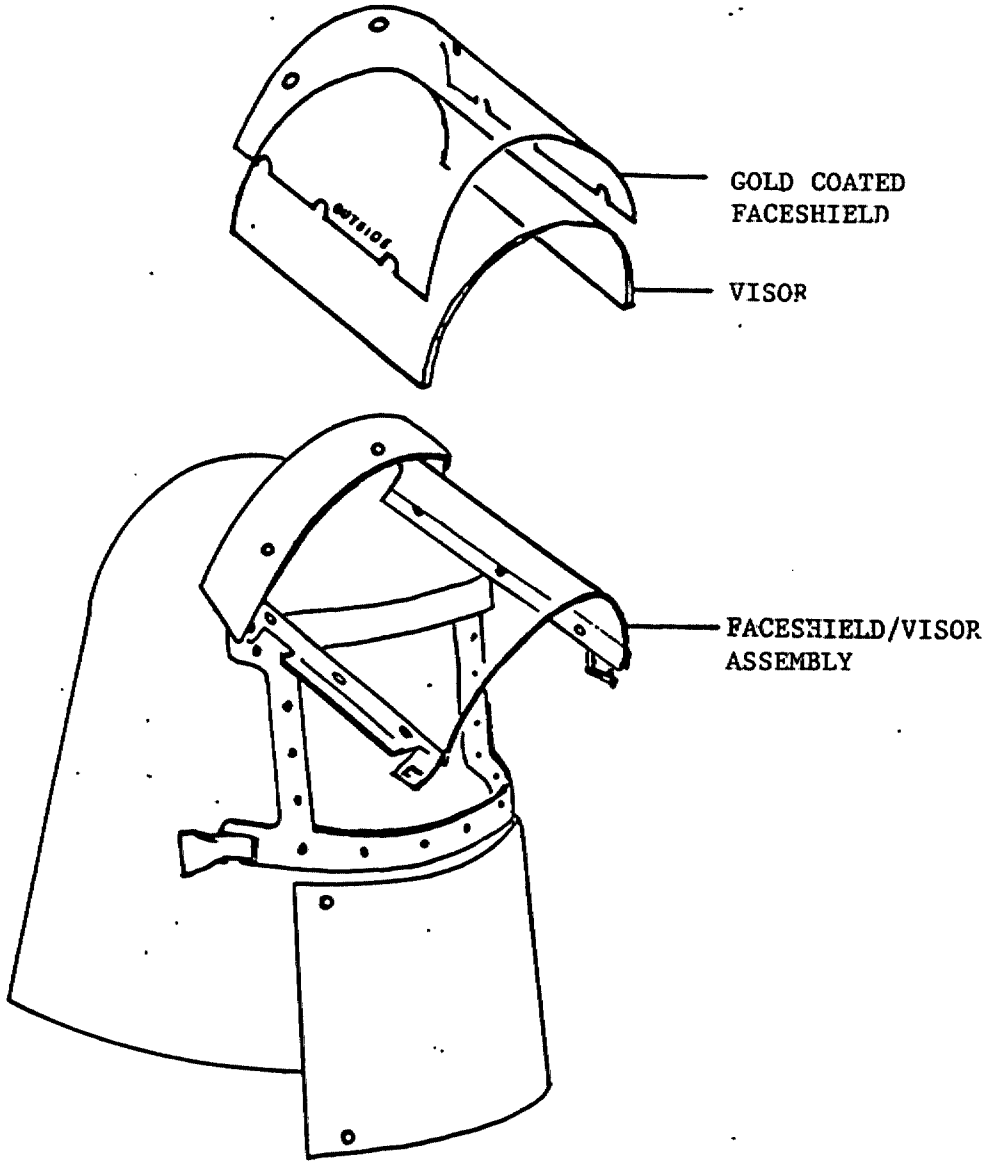


FIGURE 1

HOOD, FIREMAN'S, ALUMINIZED, PROXIMITY, WITH LIFT-UP VISOR

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

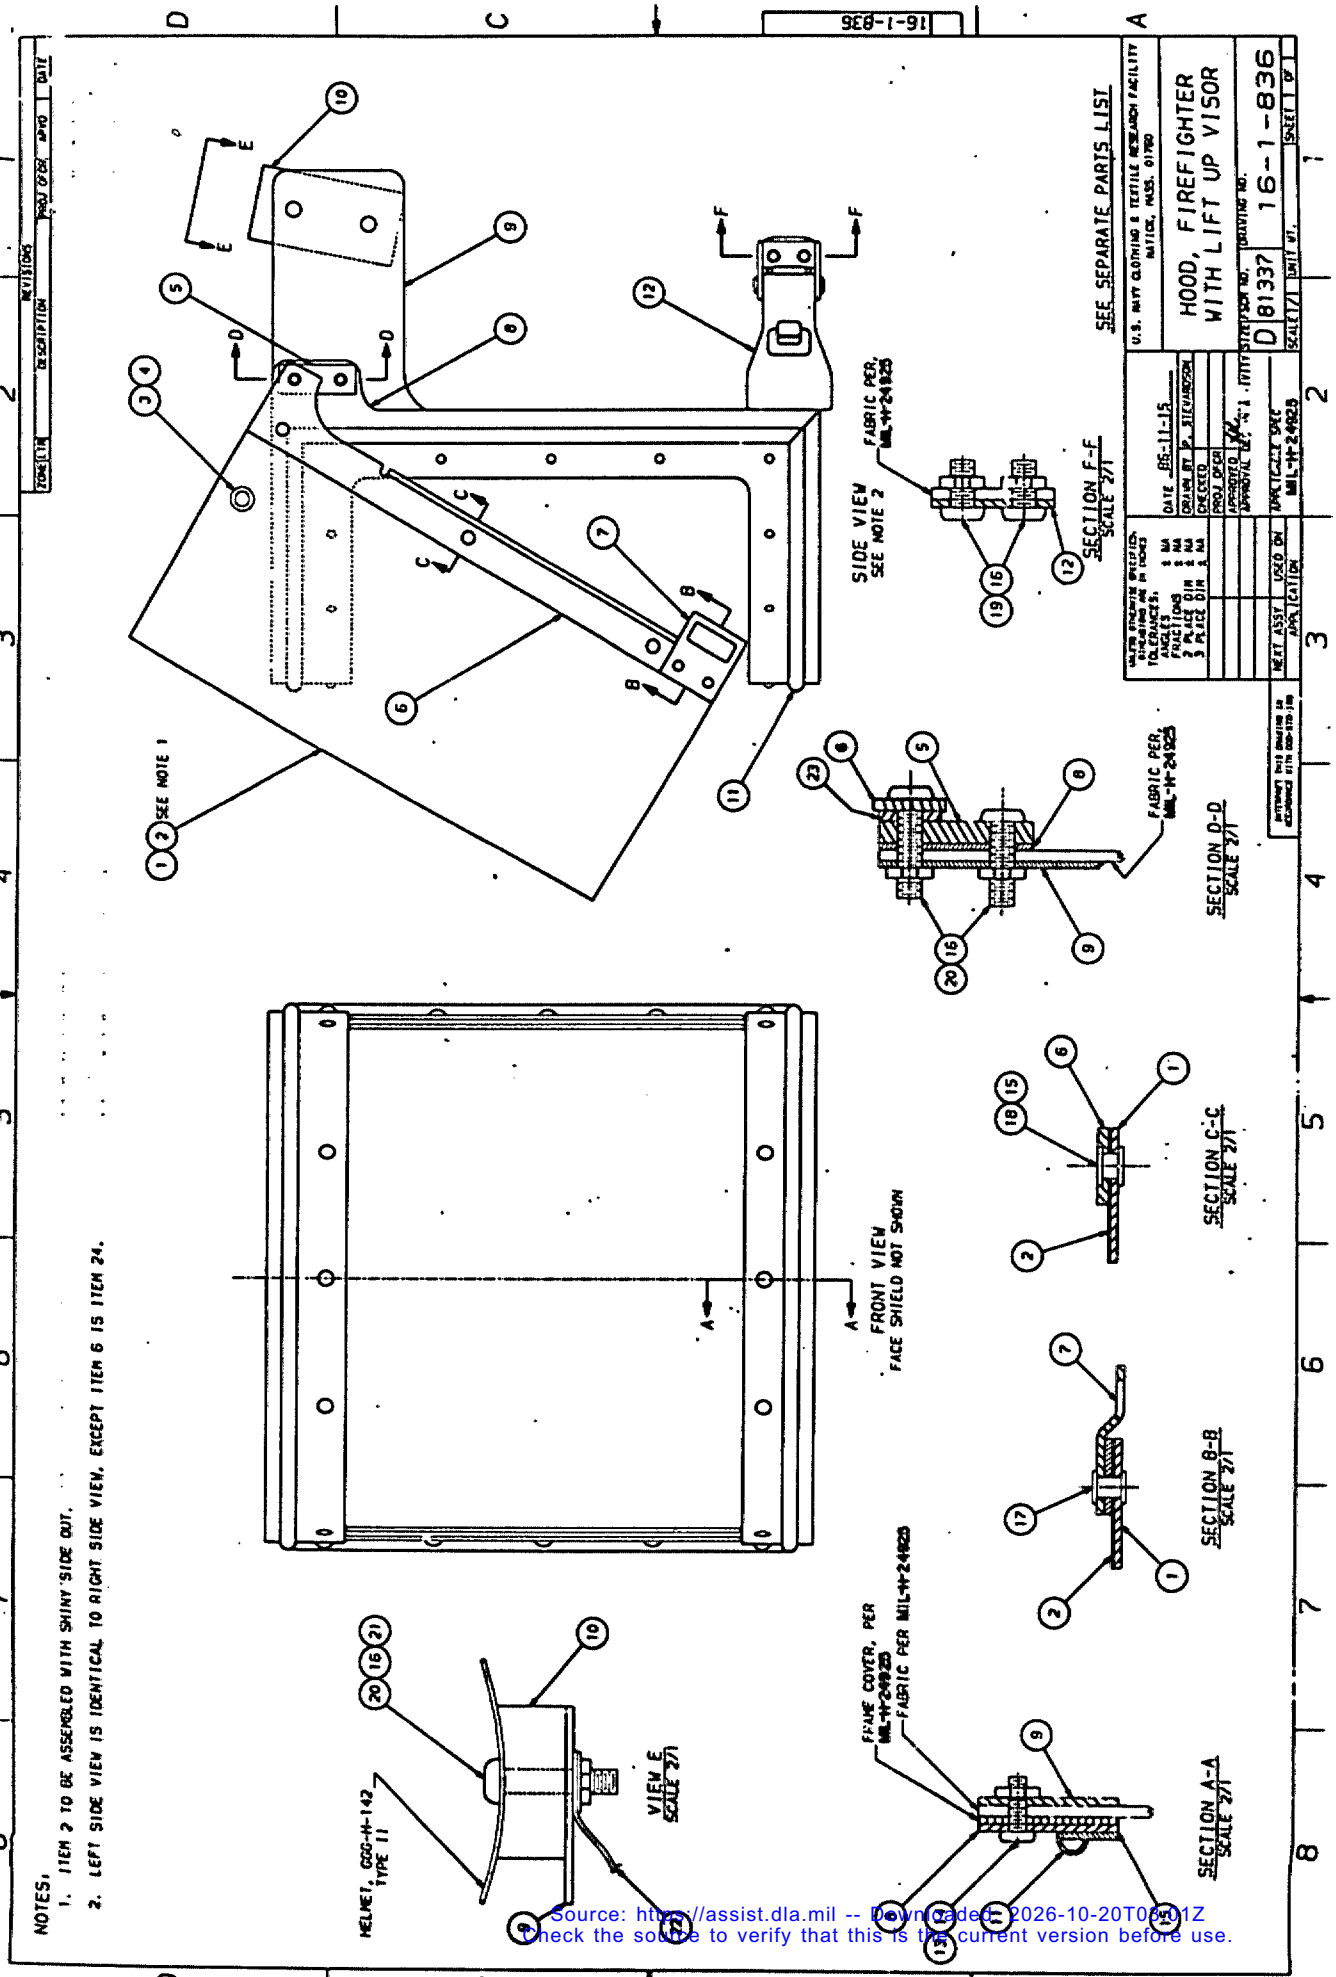


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T06:01Z
Check the source to verify that this is the current version before use.

PARTS LIST	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASSACHUSETTS 01760	FSCM 81337	PL 16-1-836	REVISION LTR —— DATE 86-11-15
LIST TITLE HOOD, FIREFIGHTER WITH LIFT UP VISOR			APPROVED	REV AUTH NO. —— SHEET 1 OF 1 SHEETS

FIND NO.	QTY RQD	QTY RQD	QTY RQD	CAGE	DRAWING OR DOCUMENT NUMBER	DWG SIZE	PART OR IDENTIFYING NUMBER	NOMENCLATURE OR DESCRIPTION
1			1		16-1-839	D	16-1-838	VISOR
2			1		16-1-842	C	16-1-842	FACESHIELD, GOLD COATED MYLAR
3			3		MS 27980		MS 27980-8N OR 8C	SNAP FASTENER, EYELET STYLE 2, 24 LINE, SIZE 1
4			3		MS 27980		MS 27980-7N OR 7C	SNAP FASTENER, STUD STYLE 2, 24 LINE, SIZE 1
5			2		16-1-844	B	16-1-844	BLOCK, PIVOT
6			1		16-1-841	C	16-1-841	FRAME, SIDE VISOR RIGHT
7			1		16-1-845	B	16-1-845	STRIKE
8			1		16-1-837	D	16-1-837	FRAME, OUTER
9			1		16-1-838	D	16-1-838	FRAME, INNER
10			2		16-1-843	B	16-1-843	BLOCK,HELMET
11			AR				1750	SEAL, SILICONE EXTRUDED OVEN OHO AMERICAN REISS CO)
12			2		16-1-846	B	16-1-846	LATCH ASSEMBLY
13			20	96906	MS51957		MS51597-29	SCREW, MACHINE
14			20	96906	MS24679		MS24679-1	NUT, PLAIN CAP, LOW CROWN
15			AR		MIL-A-46106		MIL-A-46106, TYPE I	RTV 108 SILICONE ADHESIVE
16			12	96906	MS9358		MS9358-09	NUT, CASTELLATED, HEXAGON
17			2	53551			RN AF08SD4-4	RIVET, SOLID
18					RR-P-00560		RR-P-00560	SCREW POST UNIT
19			4	96906	MS35207		MS35207-263	SCREW, MACHINE
20			8	96906	MS35207		MS35207-265	SCREW, MACHINE
21			2		FF-W-92		FF-W-92	ALUMINUM WASHER
22			1		16-1-837	C	16-1-837	CHIN STRAP ASSEMBLY
23			2		MIL-H-24926		MIL-H-24926	FIBER REINF CHLOROPRENE RUBBER WASHER .50 OD X .156 ID X .09 THK
24			1		16-1-840	C	16-1-840	FRAME, SIDE VISOR LEFT

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

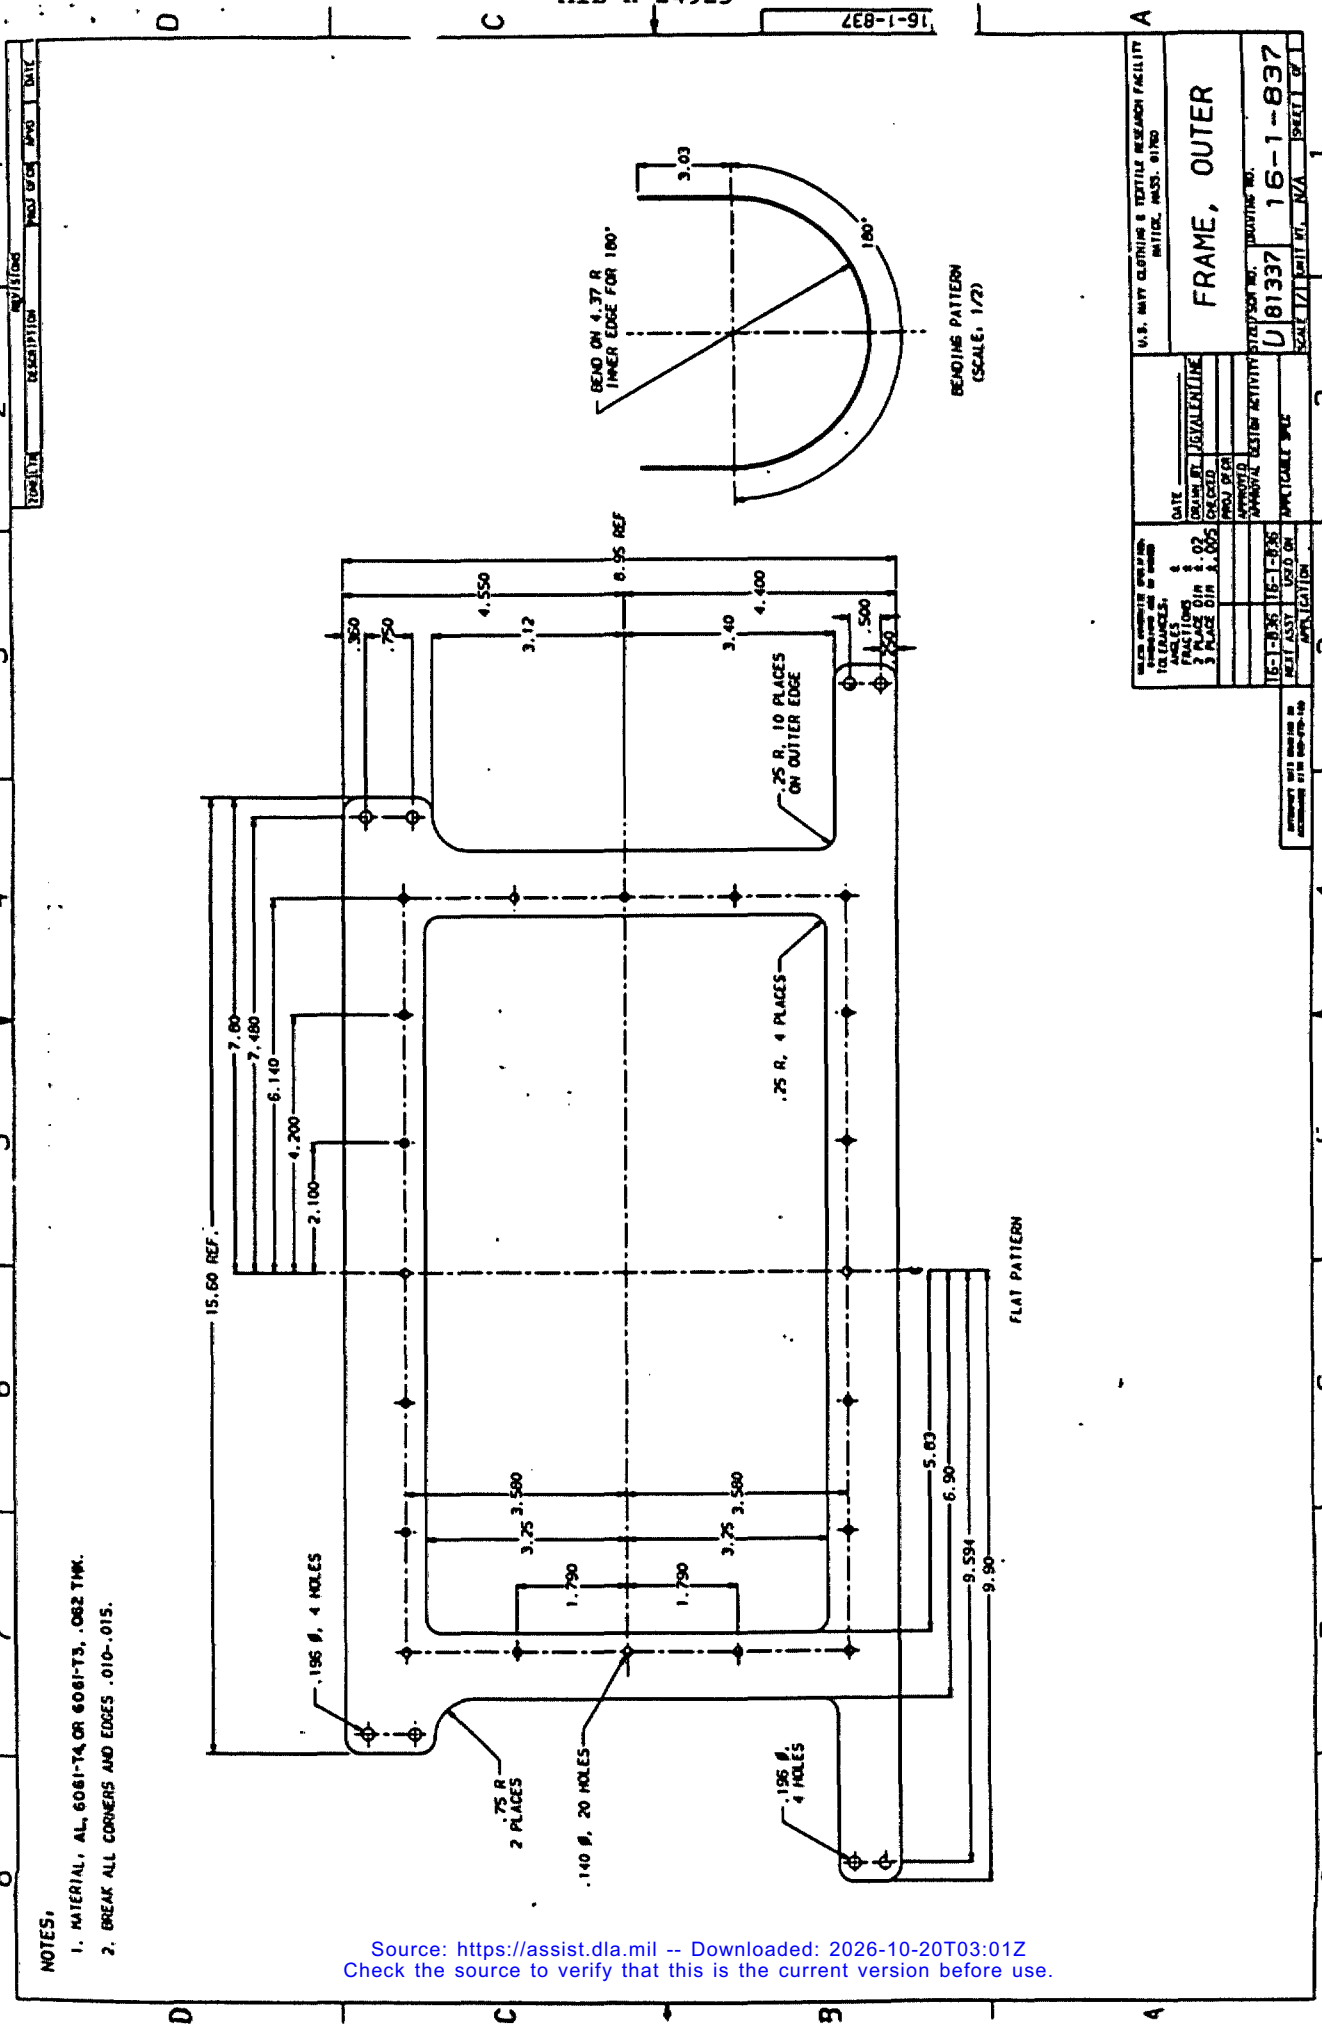


NOTES:

1. MATERIAL, AL, 6061-T4 OR 6061-T3, .062 THK.
2. BREAK ALL CORNERS AND EDGES .010-.015.


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

NOTES.

1. MATERIAL: AL, 6061-T4, OR 6061-T6, .0062 THK.
2. BREAK ALL CORNERS AND EDGES .010-.0015.

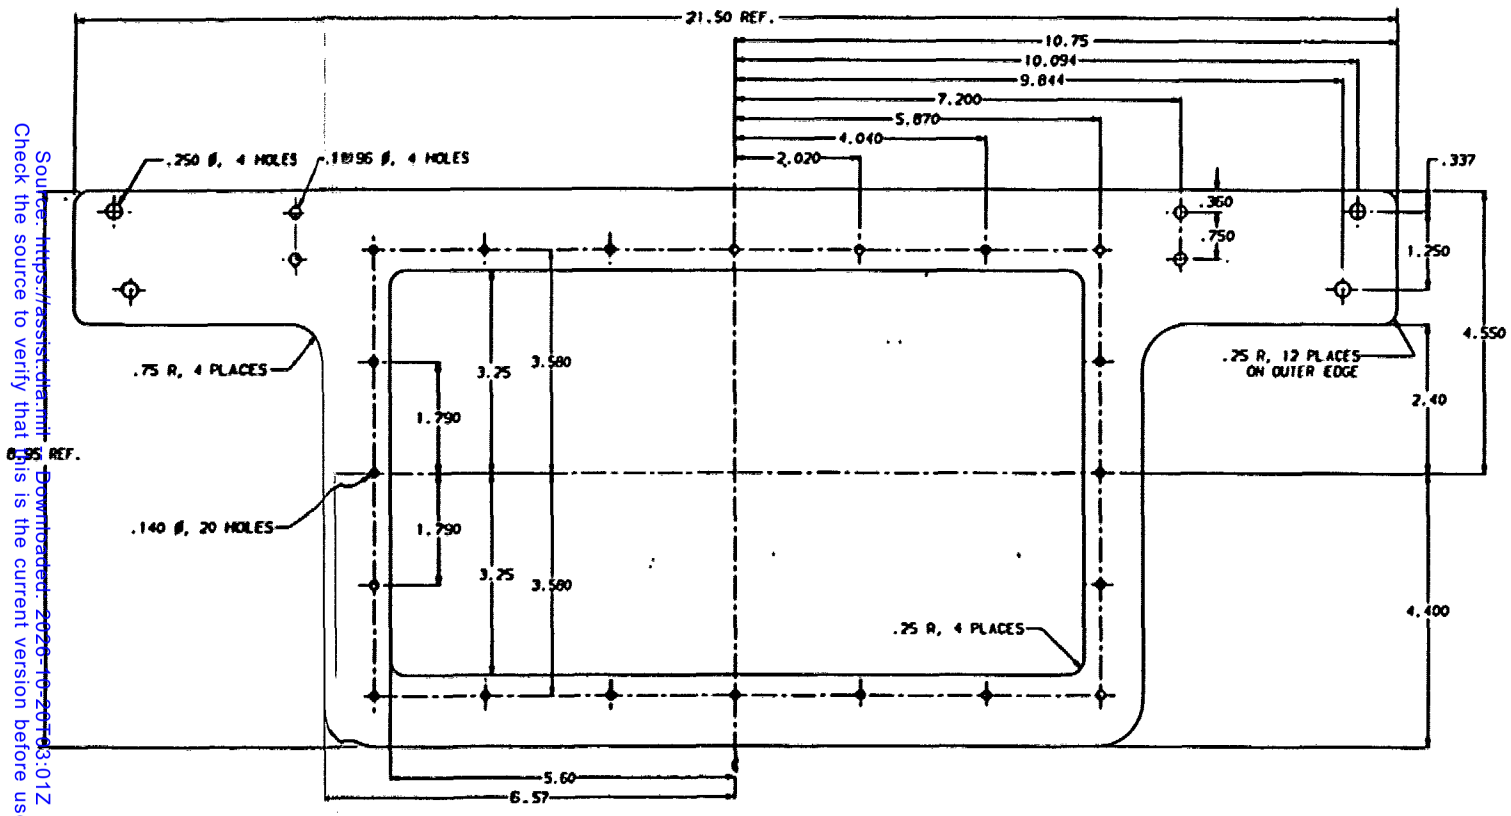

FLAT PATTERN

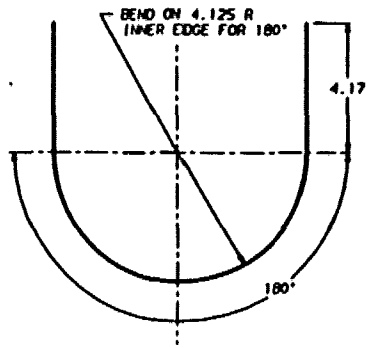

BENDING PATTERN
(SCALE. 1/2)

MIL-H-24925

838-.11

REVISIONS				
ZONE	LTR	DESCRIPTION	PROJ OFCR	APPD	DATE

TOLERANCES.
ANGLES ±
FRACTIONS ±
2 PLACE DIM ± .02
3 PLACE DIM ± .005

DATE
DRAWN BY JGVALENTINE
CHECKED
PROJ OFCR
APPROVED
APPROVAL DESIGN ACTIVITY
APPLICABLE SPEC

16-1-836 | 16-1-836
NEXT ASSY | USED ON
APPLICATION

U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY
NATICK, MASS. 01760


FRAME, INNER


SIZE D | FSCM NO. 81337 | DRAWING NO. 16-1-838
SCALE 1/1 | UNIT WT. N/A | SHEET 1 OF 1


Source: https://assistdocs.com - Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

NOTES,

1. MATERIAL, G.E. LEXAN, POLYCARBONATE, CLEAR, .125 THK.
2. FINISH, TREAT WITH "IZONEX" ANTI-FOG COATING BY EXXENE CORP. PER MIL-H-24028
3. FORMING TEMP 320° ± 5°, TIME 5 MIN ± 30 SECONDS.
4. AFTER FORMING VISOR, ALLOW TO STABILIZE A MINIMUM OF 24 HOURS, BEFORE CUTTING AND DRILLING TO THE FINAL CONFIGURATION.

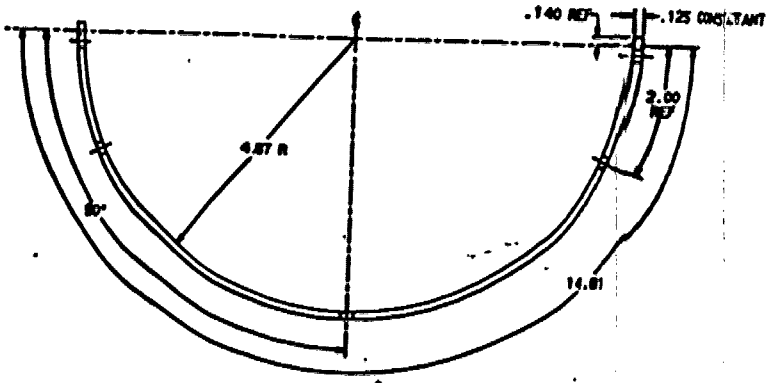

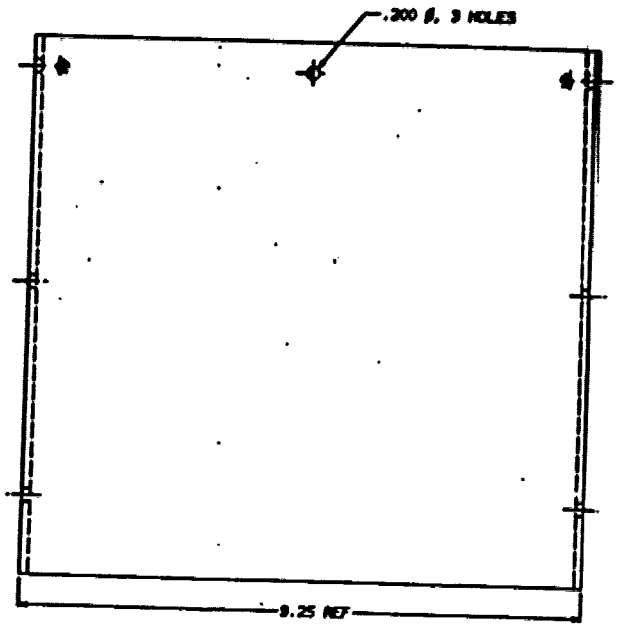

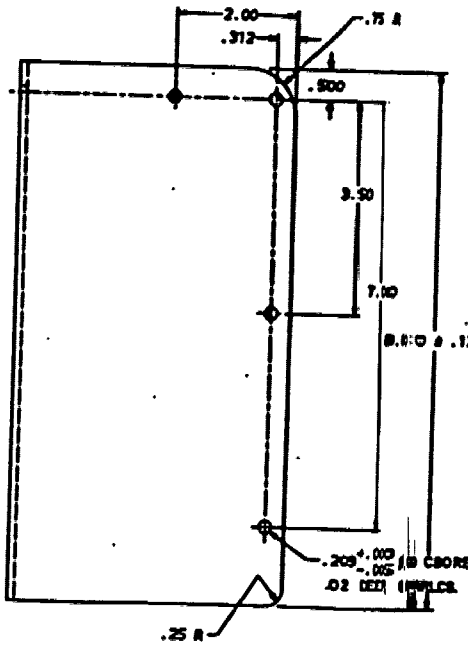

	DATE 86-11-10	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS. 01760	
	DRAWN BY DEVALERIE LINE	VISOR	
	CHECKED		
	PROJ ENGR		
	APPROVED VDK		
	MATERIAL DEFINITION ACTIVITY	SIZE / IDENTIFICATION NO. D 81337	COUNTER NO. 16-1-839
	APPLICATION	SCALE 1/1 UNIT WT. N/A	SHEET 1 OF 1


MIL-H-24925


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.


NOTES:

1. MATERIAL: AL, 5052-H32, .092 THK.
2. BREAK ALL EDGES AND CORNERS .010-.015.


REVISIONS				
ZONE	LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

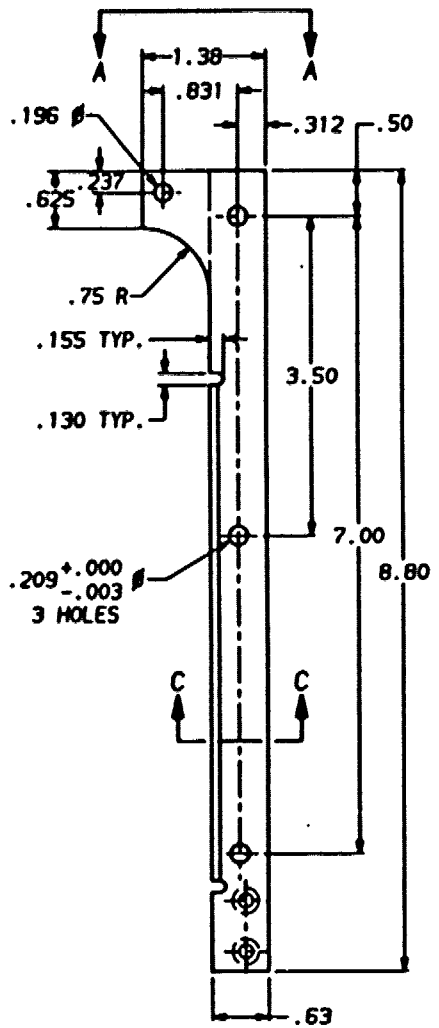

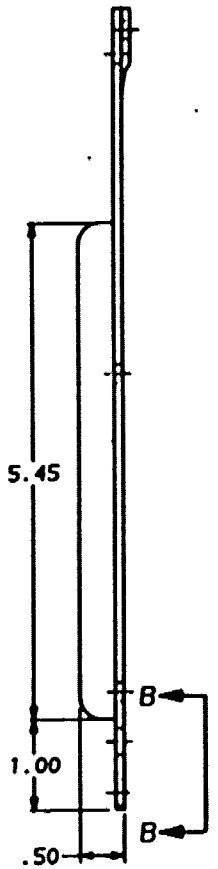




VIEW A-A

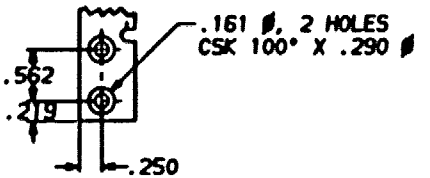

VIEW B-B



SECTION C-C

UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES: ANGLES ± FRACTIONS ± 2 PLACE DIM ±.02 3 PLACE DIM ±.005		DATE	
		DRAWN BY	JGVALENTINE
		CHECKED	
		PROJ OFCR	
		APPROVED	
		APPROVAL DESIGN ACTIVITY	
16-1-846	16-1-846	APPLICABLE SPEC	
NEXT ASSY	USED ON		
APPLICATION			

INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100

U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY
NATICK, MASS. 01760

FRAME, SIDE
VISOR LEFT

SIZE	FSCM NO.	DRAWING NO.
C	81337	16-1-840

SCALE 1/1 | UNIT WT. N/A | SHEET 1 OF 1

MIL-H-24925


16-1-840

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

NOTES:


1. MATERIAL: AL., 5052-H32, .092 THK.
2. BREAK ALL EDGES AND CORNERS .010-.015.

REVISIONS				
ZONE	LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

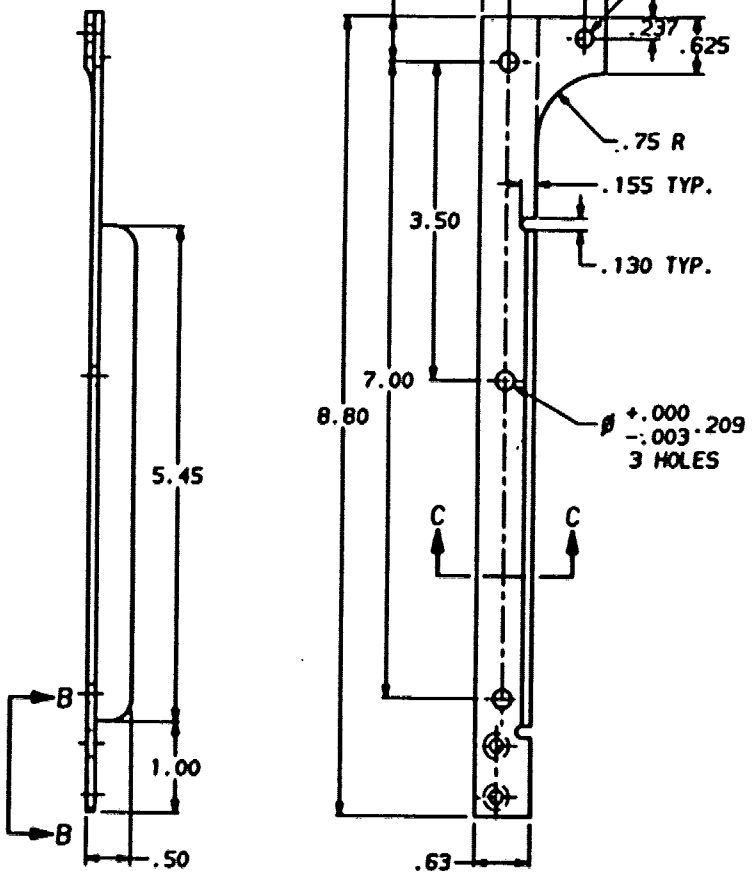




VIEW A-A

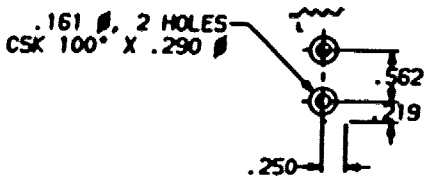

B-B VIEW



SECTION C-C


UNLESS OTHERWISE SPECIFIED, DIMENSIONS ARE IN INCHES. TOLERANCES: ANGLES ±, FRACTIONS ±, 2 PLACE DIM ±.02, 3 PLACE DIM ±.005		DATE	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS. 01760
		DRAWN BY JGVALENTINE	FRAME, SIDE VISOR RIGHT
		CHECKED	
		PROJ OFCR	
		APPROVED	
		APPROVAL DESIGN ACTIVITY	SIZE C / FSCM NO. 81337 / DRAWING NO. 16-1-841
16-1-836	16-1-836	APPLICABLE SPEC	
NEXT ASSY	USED ON		SCALE 1/1 / UNIT WT. N/A / SHEET 1 OF 1
APPLICATION			

INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100.

MIL-R-24925

16-1-841

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

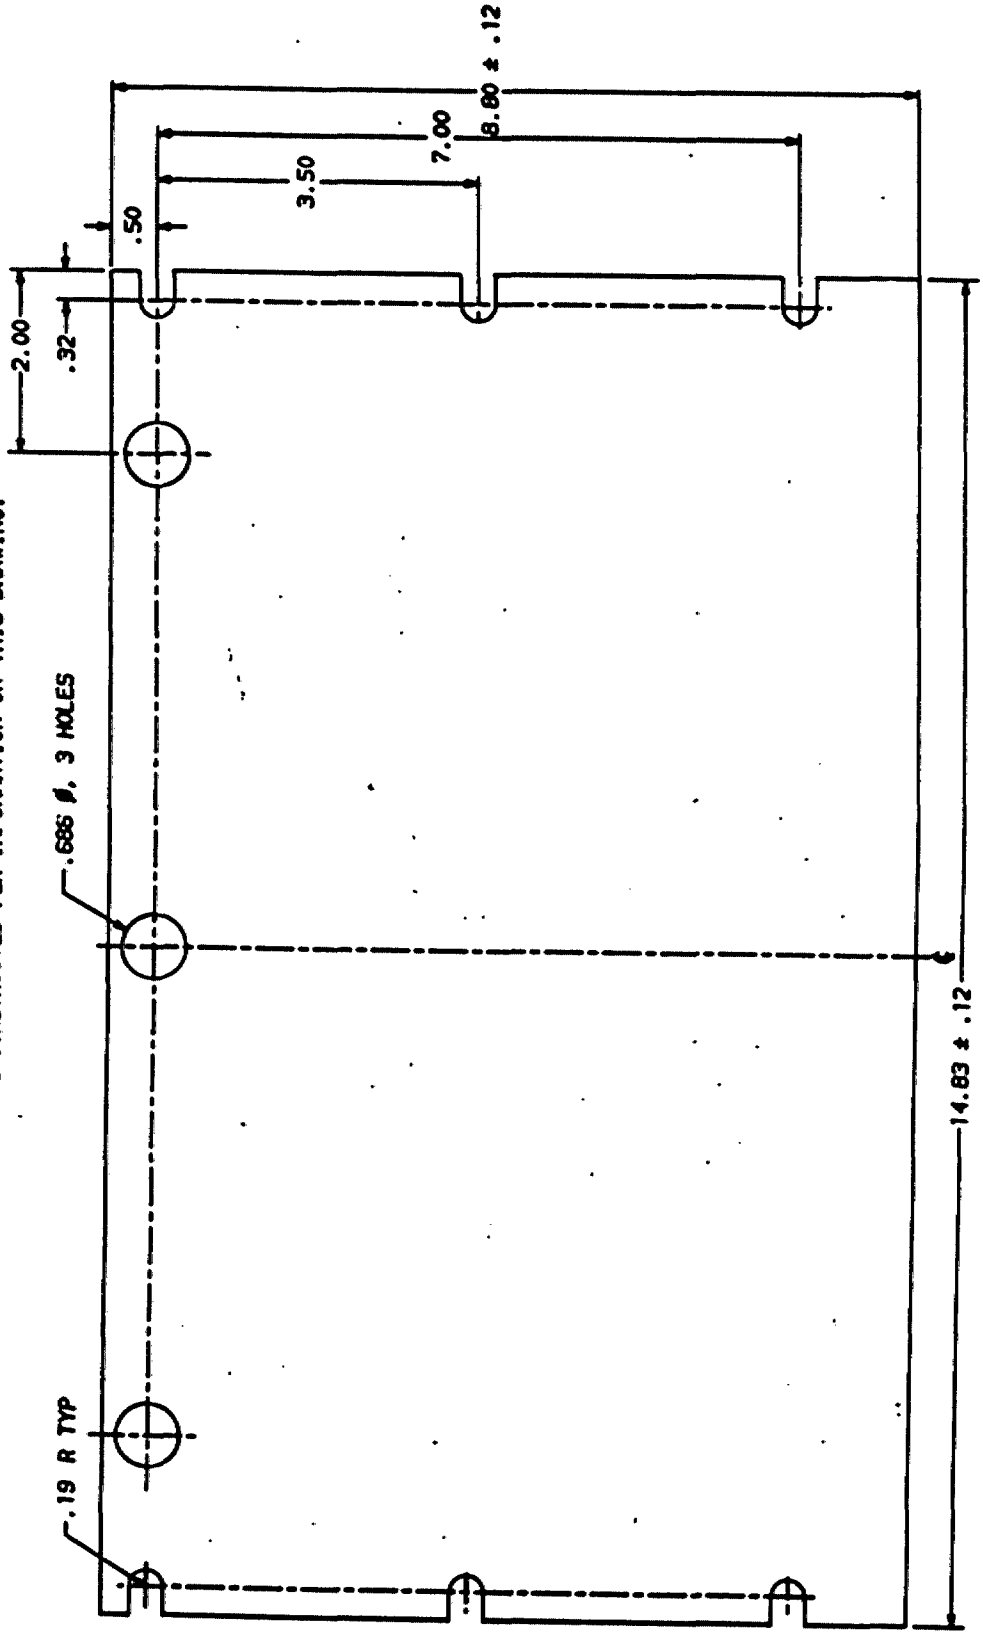

NOTES:

1. MATERIAL, MYLAR, LP-377 FILM, TYPE III, .007 THK. FINISH, GOLD FILM PER MIL-H-24925.
2. TEMPLATE FOR HOLE AND CUT OUT LOCATIONS TO BE CONSTRUCTED PER INFORMATION ON THIS DRAWING.

U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY
NATICK, MASS. 01760

FACESHIELD, GOLD COATED MYLAR

SIZE | FSCM NO. 81337 | DRAWING NO. 16-1-842

SCALE 1=1 | UNIT WT. N/A | SHEET 1 OF 1

DATE 86-11-10
DRAWN BY J.GVALENTINE
CHECKED
PROJ OFCR
APPROVED
APPROVAL DESIGN ACTIVITY

APPLICABLE SPEC

16-1-836 | 16-1-842
NEXT ASSY | USED ON
APPLICATION

UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES
TOLERANCES,
ANGLES ±
FRACTIONS ±
2 PLACE DIM ±.01
3 PLACE DIM ±.005

INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.


16-1-843


REVISIONS				
LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

NOTES:

1. MATERIAL: AL., 2024-T351, .500 THK.
2. BREAK ALL CORNERS AND SHARP EDGES .010 - .015.

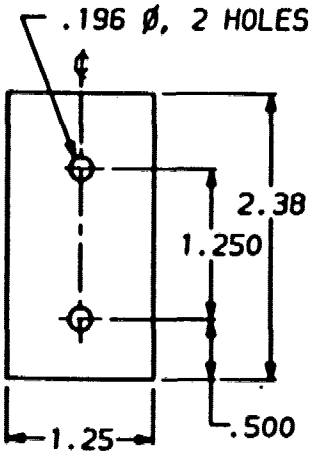

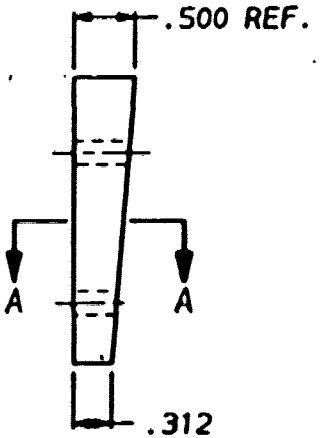

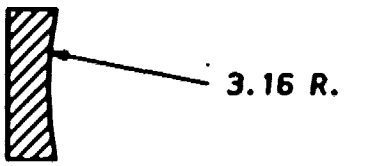

SECTION A-A

		UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES: ANGLES ± FRACTIONS ± 2 PLACE DIM ±.02 3 PLACE DIM ±.005	DATE	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS 01760
			DSGN BY JGVALENTINE	BLOCK, HELMET
			CHKD	
			PROJ OFCR	
			APVD	
16-1-836	16-1-836	INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100	APPL DESIGN ACTIVITY	SIZE A / FSCM NO. 81337 / DRAWING NO. 16-1-843
NEXT ASSY	USED ON		APPLICABLE SPEC	SCALE 1=1 / UNIT WT. N/A / SHEET 1 OF 1
APPLICATION				

MIL-H-24925


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

16-1-844

REVISIONS				
LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

NOTES:

1. MATERIAL: AL., 6061-T3, OR 6061-T4, .186 THK.
2. BREAK ALL CORNERS AND SHARP EDGES .010-.015.

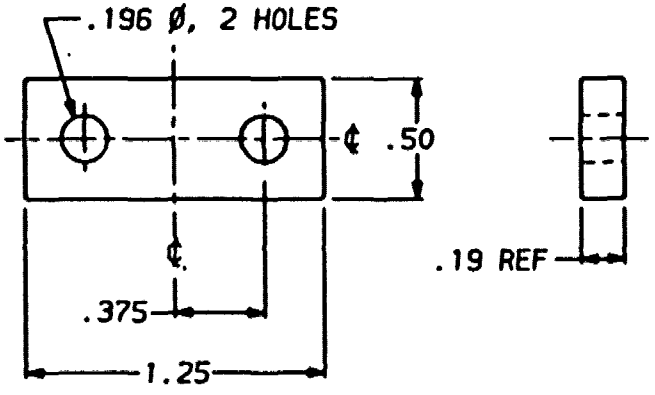

MIL-H-24925

		UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES. ANGLES ± FRACTIONS ± 2 PLACE DIM ±.02 3 PLACE DIM ±.005	DATE	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS 01760	
			DWN BY JGVALENTINE		
			CHKR	BLOCK, PIVOT VISOR	
			PROJ OFCR		
			APVD		
16-1-836	16-1-836	INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100	APVL DESIGN ACTIVITY	SIZE B FSCM NO. 81337	DRAWING NO. 16-1-844
NEXT ASSY	USED ON		APPLICABLE SPEC	SCALE 2=1 UNIT WT. N/A	SHEET 1 OF 1
APPLICATION					


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:07Z
Check the source to verify that this is the current version before use.


16-1-845

REVISIONS				
LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

NOTES:

1. MATERIAL: STEEL, STAINLESS, TYPE 302, FINISH 2B, .125 THK. (8 GA).
2. BREAK ALL EDGES .010-.015.

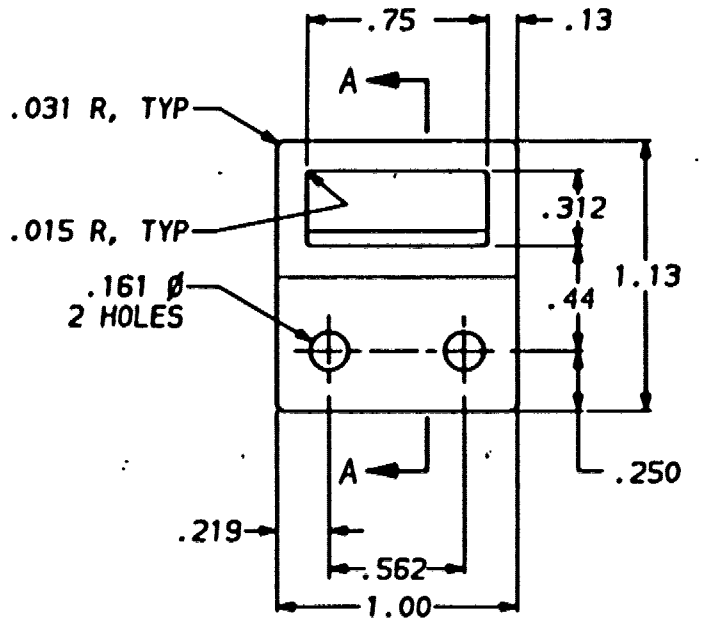

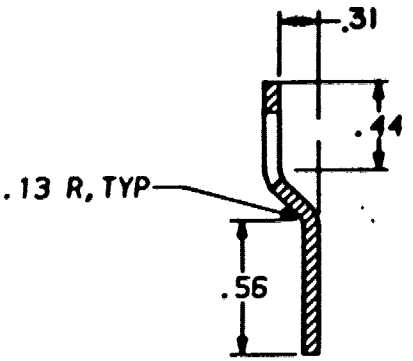

SECTION A-A

MIL-H-24925

		UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES. ANGLES ± 3° FRACTIONS ± 2 PLACE DIM ± .01 3 PLACE DIM ± .005	DATE	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS 01760
			DRAWN JGVALENTINE	
			CHKR	STRIKE
			PROJ OFCR	
			APVD	
16-1-836	16-1-836	INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100	APPR. DESIGN ACTIVITY	SIZE 8 FSCM NO. 81337 DRAWING NO. 16-1-845
NEXT ASSY	USED ON		APPLICABLE SPEC	SCALE 2/1 UNIT WT. N/A SHEET 1 OF 1
APPLICATION				


Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

16-1-846

REVISIONS				
LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

NOTES

1. IDENTIFICATION OF THE "SUGGESTED SOURCES OF SUPPLY" HEREON IS NOT TO BE CONSTRUED AS A GUARANTEE OF PRESENT OR CONTINUED AVAILABILITY AS A SOURCE OF SUPPLY FOR THE ITEM(S).

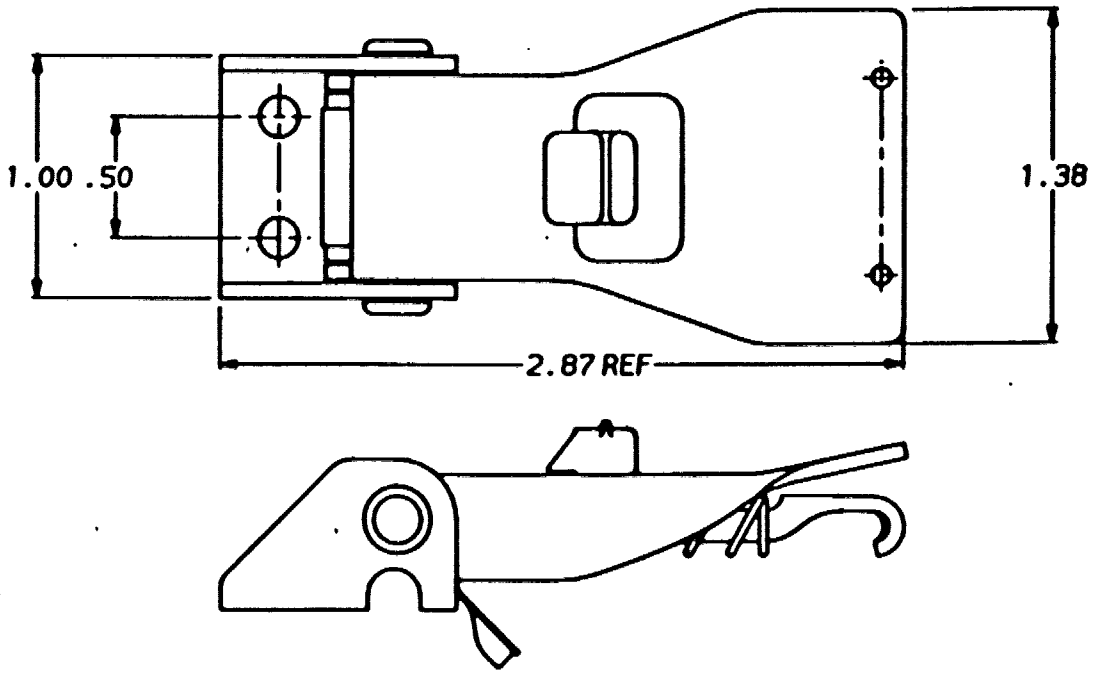

SUGGESTED SOURCES OF SUPPLY		
SUPPLIER DATA		
FSCM	PART NO.	NAME AND ADDRESS
71286	81L130-0088	REXNORD INC HASBROUCK HEIGHTS NJ

SPECIFICATION CONTROL DRAWING

		UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES. ANGLES ± FRACTIONS ± 2 PLACE DIN ± 3 PLACE DIN ±	DATE	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS 01760
			DSGN BY JGVALENTINE	LATCH, ASSEMBLY
			CHKD	
			APPLY QFCR	
			APVD	
16-1-836	16-1-836	INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100	APPL DESIGN ACTIVITY	SIZE B FSCM NO. 81337 DRAWING NO. 16-1-846
NEXT ASSY	USED ON		APPLICABLE SPEC	SCALE 2/1 UNIT WT. N/A SHEET 1 OF 1
APPLICATION				

MIL-H-24925


Source: http://assist.daps.dla.mil - Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

NOTES:


1. MATERIAL IS WEBBING, PER MIL-W-530, TYPE IIa, CLASS 1.
2. TOLERANCES SHALL BE AS FOLLOWS:

LESS THAN 1/8	± 1/16
MORE THAN 1/8 BUT LESS THAN 2	± 1/8
MORE THAN 2 BUT LESS THAN 10	± 1/4
GREATER THAN 10	± 3/8

REVISIONS					
ZONE	LTR	DESCRIPTION	PROJ OFCR	APVD	DATE

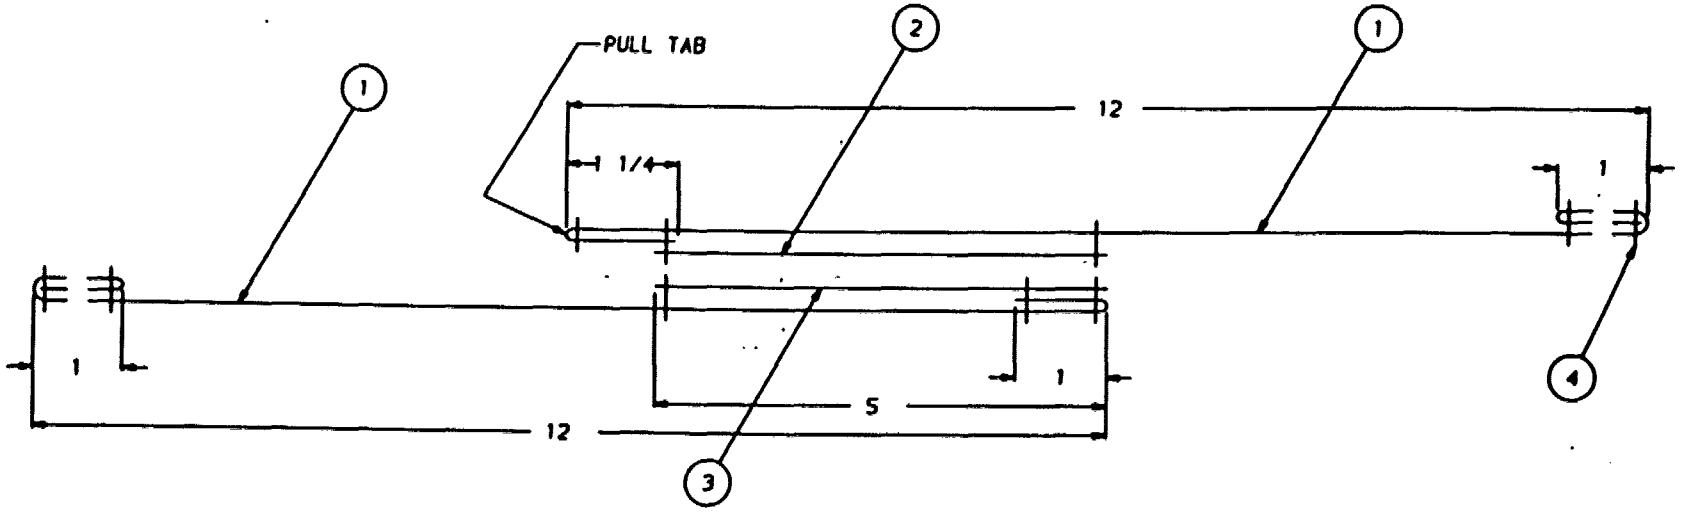

SECTION A-A

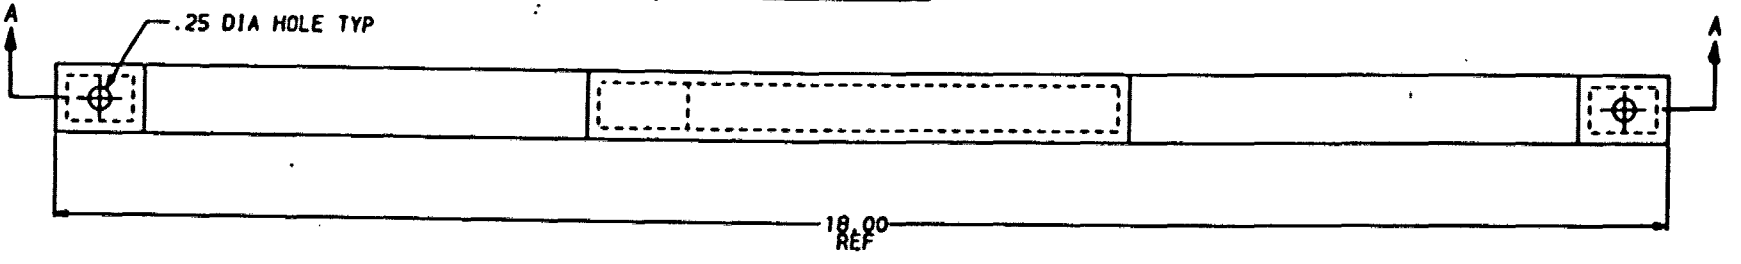

SEE SEPARATE PARTS LIST

UNLESS OTHERWISE SPECIFIED, DIMENSIONS ARE IN INCHES TOLERANCES: ANGLES ± FRACTIONS ± 2 PLACE DIM ± 3 PLACE DIM ±		DATE 86-11-10	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASS. 01760
		DRAWN BY P STEWARDSON	CHIN STRAP ASSEMBLY
		CHECKED	
		PROJ OFCR	
		APPROVED	SIZE: C; FSCM NO.: 81337; DRAWING NO.: 16-1-847
16-1-836	16-1-836	APPROVAL DESIGN ACTIVITY	
NEXT ASSY	USED ON	APPLICABLE SPEC	SCALE NONE; UNIT WT.; SHEET 1 OF 1
APPLICATION			

INTERPRET THIS DRAWING IN ACCORDANCE WITH DOD-STD-100

MIL-H-24925

16-1-847

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.

PARTS LIST	U.S. NAVY CLOTHING & TEXTILE RESEARCH FACILITY NATICK, MASSACHUSETTS 01760	FSCM 81337	PL 16-1-847	REVISION LTR —— DATE
LIST TITLE CHIN STRAP ASSEMBLY			APPROVED	REV AUTH NO. ——

SHEET 1 OF 1 SHEETS

FIND NO.	QTY RQD	QTY RQD	QTY RQD	CAGE	DRAWING OR DOCUMENT NUMBER	DWG SIZE	PART OR IDENTIFYING NUMBER	NOMENCLATURE OR DESCRIPTION
1			AR		MIL-W-530		MIL-W-530, TYPE IIa, CLASS 1, 2, OR 3, 3/4 WIDE	WEBBING, TEXTILE, COTTON, GEN'L PURPOSE
2			AR		MIL-F-21840		MIL-F-21840, TYPE II, CL 1, 5/8 WIDE	TAPE, FASTENER PILE 5 LONG
3			AR		MIL-F-21840		MIL-F-21840, TYPE II, CL 1, 5/8 WIDE	TAPE, FASTENER HOOK 5 LONG
4			AR		MIL-T-43548		MIL-T-43548 TICKET #50, 2 OR 3 PLY	THREAD, POLYESTER, COTTON COVERED AND RAYON COVERED

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T03:01Z
Check the source to verify that this is the current version before use.