The documentation and process conversion measures necessary to comply with this document shall be completed by 24 February 2020.

INCH-POUND

MIL-PRF-19500/631C
26 October 2019
SUPERSEDING
MIL-PRF-19500/631B
9 March 2004

PERFORMANCE SPECIFICATION SHEET

TRANSISTOR, FIELD EFFECT, N-CHANNEL SILICON,
RADIATION HARDENED (TOTAL DOSE AND SINGLE EVENT EFFECTS),
TYPES 2N7395, 2N7396, 2N7397, AND 2N7398,
QUALITY LEVELS JANSD AND JANSR

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-PRF-19500.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for a N-channel, enhancement-mode, MOSFET, radiation hardened (total dose and single event characterization only), power transistors. One level of product assurance (JANS) is provided for each device type as specified in MIL-PRF-19500.

1.2 Package outline. The device package outline is a modified TO-205AG package in accordance with figure 1.

1.3 Maximum ratings. Unless otherwise specified, T_A = +25°C.

Type	P_T (1) T_C =+25°C	P_T T_A =+25°C	V_{DS}	V_{DG}	V_{GS}	I_{D1} (2) (3) T_C =+25°C	I_{D2} (2) (3) T_C = +100°C	I_S	I_{DM}	V_{ISO} 70,000 ft. altitude	T_J and T_{STG}
	W	W	V dc	V dc	V dc	A dc	A dc	A dc	A (pk)	V dc	°C
2N7395	25	10	100	100	±20	8.0	5.0	8.0	24	N/A	−55
2N7396	25	10	200	200	±20	5.0	3.0	5.0	15	N/A	to
2N7397	25	10	250	250	±20	4.0	2.0	4.0	12	250	+150
2N7398	25	10	500	500	±20	2.0	1.0	2.0	6	500	

(1) Derate linearly 0.2 W/°C for T_C > +25°C;
(2) The following formula derives the maximum theoretical I_D limit. I_D is limited by package and internal wires and may be limited by pin diameter:

$$I_D = \sqrt{\frac{T_{JM} - T_C}{(R_{\theta JC}) \text{ X } (r_{DS(on)}) \text{ at } T_{JM}}}$$

(3) See figure 2, maximum drain current graphs.
(4) I_{DM} = 4 X I_{D1}; I_{D1} as calculated by footnote (3).

Comments, suggestions, or questions on this document should be addressed to DLA Land and Maritime, VAC, P.O. Box 3990, Columbus, OH 43218-3990, or emailed to Semiconductor@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A

FSC 5961

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics. Unless otherwise specified, at T_C = +25°C.

Type	Min $V_{(BR)DSS}$ V_{GSS} = 0 I_D = 1.0 mA dc	$V_{GS(TH)1}$ $V_{DS} > V_{GS}$ I_D = 1.0 mA dc		Max I_{DSS1} V_{GS} = 0 V_{GS} = 80% of rated V_{DS}	Max $r_{DS(on)}$ (1) V_{GS} = 12V		$R_{\theta JC}$ Max	I_{AS} = I_{DM}
					T_J = +25°C at I_{D2}	T_J = +125°C at I_{D2}		
	V dc	V dc Min	Max	µA dc	Ω	Ω	°C/W	A (pk)
2N7395	100	1.5	4.0	25	0.23	0.36	5.00	24
2N7396	200				0.46	0.81		15
2N7397	250				0.61	1.11		12
2N7398	500				2.50	4.80		6

(1) Pulsed (see 4.5.1).

1.5 Part or Identifying Number (PIN). The PIN is in accordance with MIL-PRF-19500, and as specified herein. See 6.4 for PIN construction example and 6.5 for a list of available PINs.

1.5.1 JAN brand and quality level designators for encapsulated devices. The only quality level designator for encapsulated devices that are applicable for this specification sheet is "JANS".

1.5.2 Radiation hardness assurance (RHA) designator. The RHA levels that are applicable for this specification sheet are "D" and "R".

1.5.3 Device type. The designation system for the device types of transistors covered by this specification sheet are as follows.


1.5.3.1 First number and first letter symbols. The transistors of this specification sheet are identified by the first number and letter symbols "2N".

1.5.3.2 Second number symbols. The second number symbols for the transistor covered by this specification sheet are as follows: "7395", "7396", "7397" and "7398".

1.5.4 Lead finish. The lead finishes applicable to this specification sheet are listed on QML-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

Symbol	Dimensions				Notes
	Inches		Millimeters		
	Min	Max	Min	Max	
CD	.315	.335	8.00	9.02	4
CH	.160	.180	4.06	4.57	
HD	.350	.370	8.64	9.40	4
LC	.200 BSC		5.08 BSC		5
LD	.016	.021	0.41	0.53	6, 7
LL	.500	.750	12.70	19.05	6, 7, 8
LU	.016	.019	0.41	0.48	6, 7
L1		.050		1.27	6, 7
L2	.250		6.35		6, 7
P	.070		1.78		
Q		.050		1.27	4
r		.010		0.25	9
TL	.029	.045	0.74	1.14	10
TW	.028	.034	0.71	0.86	11
α	45° BSC		45° BSC		5

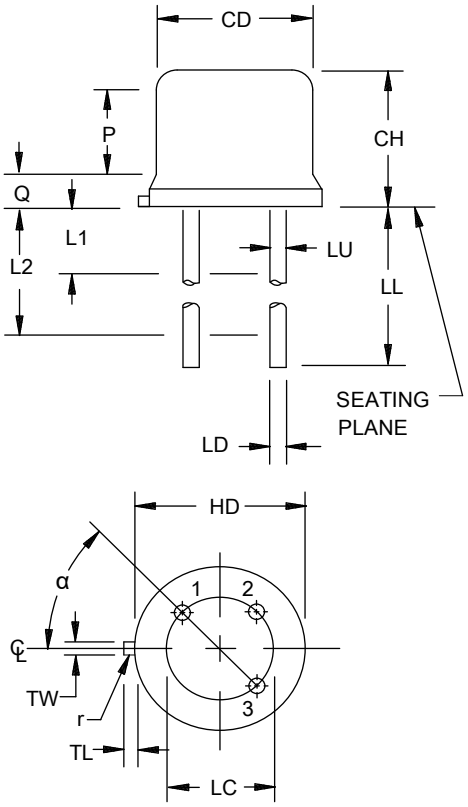

NOTES:

1. Dimension are in inches. Millimeters are given for general information only.
2. Terminal 1 = source, terminal 2 = gate, and terminal 3 is drain. Terminal 3 is butt welded to stem base.
3. Terminal 4 is omitted from this outline.
4. Body contour optional within zone defined by dimensions CD, HD, and Q.
5. Leads at gauge plane .054 +.001 −.000 inch (1.37 +0.03 −0.00 mm) below seating plane shall be within .007 inch (0.18 mm) radius of true position (TP) at maximum material condition (MMC) relative to tab at MMC. The device may be measured by direct methods.
6. Dimension LU applies between dimensions L1 and L2. Dimension LD applies between dimensions L2 and LL minimum. Diameter is uncontrolled in dimension L1 and beyond dimension LL minimum.
7. All three leads.
8. For "L" suffix devices, dimension LL = 1.5 inches (38.10 mm) minimum and 1.75 inches (44.45 mm) maximum.
9. Dimension r (radius) applies to both inside corners of tab.
10. Dimension TL measured from maximum HD.
11. Beyond r (radius) maximum, dimension TW shall be held for a minimum length of .011 inch (0.28 mm).
12. In accordance with ASME Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 1. Physical dimensions for modified TO-205AG.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Copies of these documents are available online at https://quicksearch.dla.mil.)

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 General. The individual item requirements shall be as specified in MIL-PRF-19500 and as modified herein.

3.2 Qualification. Devices furnished under this specification shall be products that are manufactured by a manufacturer authorized by the qualifying activity for listing on the applicable qualified manufacturers list before contract award (see 4.2 and 6.3).

3.3 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500 and as follows.

nC	nano Coulomb.
I_{AS}	Rated avalanche current, non-repetitive.

3.4 Interface and physical dimensions. Interface and physical dimensions shall be as specified in MIL-PRF-19500 and on figure 1.

3.4.1 Lead finish. Lead finish shall be solderable in accordance with MIL-PRF-19500, MIL-STD-750, and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition document (see 6.2 and 6.6).

3.4.2 Internal construction. Multiple die construction is not permitted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

3.5 Marking. Marking shall be in accordance with MIL-PRF-19500. At the option of the manufacturer, marking of the country of origin may be omitted from the body of the transistor but shall be retained on the initial container.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be as specified in table I.

3.8 Electrostatic discharge sensitive (ESDS). The devices covered by this specification sheet have been classified as ESDS. The devices shall be handled in accordance with the ESD program established to comply with the requirements of MIL-PRF-19500 to avoid damage due to the accumulation of static charge. The following handling practices shall be followed:

a. Devices shall be handled on benches with conductive handling devices.

b. Ground test equipment, tools and personnel handling devices.

c. Do not handle devices by the leads.

d. Store devices in conductive foam or carriers.

e. Avoid use of plastic, rubber or silk in MOS areas.

f. Maintain relative humidity above 50 percent if practical.

g. Care should be exercised during test and troubleshooting to apply not more than maximum rated voltage to any lead.

h. Gate shall be terminated to source, R ≤ or 100 kΩ, whenever bias voltage is applied drain to source.

3.9 Workmanship. Semiconductor devices shall be processed in such a manner as to be uniform in quality and shall be free from other defects that will affect life, serviceability, or appearance.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3).

c. Conformance inspection (see 4.4 and tables I, II, and III).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500 and as specified herein.

4.2.1 Group E qualification. Group E inspection shall be performed for qualification or re-qualification only. In case qualification was awarded to a prior revision of the specification sheet that did not request the performance of table III tests, the tests specified in table III herein that were not performed in the prior revision shall be performed on the first inspection lot of this revision to maintain qualification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANS only). Screening shall be in accordance with table E-IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (1) (2)	Measurement
	JANS
(3)	Gate stress test (see 4.3.1).
(3)	Method 3470 of MIL-STD-750, (see 4.3.2).
(3) 3c	Method 3161 of MIL-STD-750, (see 4.3.3).
9	I_{GSSF1}, I_{GSSR1}, I_{DSS1}, subgroup 2 of table I herein.
10	Method 1042 of MIL-STD-750, test condition B .
11	I_{GSSF1}, I_{GSSR1}, I_{DSS1}, $r_{DS(ON)}$, $V_{GS(TH)}$; Subgroup 2 of table I herein; ΔI_{GSSF1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{GSSR1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{DSS1} = ±25 µA dc or ±100 percent of initial value, whichever is greater.
12	Method 1042 of MIL-STD-750, test condition A.
13	Subgroups 2 and 3 of table I herein; ΔI_{GSSF1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{GSSR1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{DSS1} = ±25 µA dc or ±100 percent of initial value, whichever is greater. $\Delta r_{DS(ON)1}$ = ±20 percent of initial value. $\Delta V_{GS(TH)1}$ = ±20 percent of initial value.

(1) At the end of the test program, I_{GSSF1}, I_{GSSR1}, and I_{DSS1}, are measured.
(2) An out-of-family program to characterize I_{GSSF1}, I_{GSSR1}, I_{DSS1}, and $V_{GS(th)1}$ shall be invoked.
(3) Shall be performed anytime before screen 9.

4.3.1 Gate stress test. Apply V_{GS} = 30 V minimum for t = 250 µs minimum.

4.3.2 Single pulse avalanche energy. The test for single pulse avalanche energy shall be performed in accordance with method 3470 of MIL-STD-750. The following details shall apply:

a. Peak current (I_{AS}) ..... $I_{AS} = I_{DM}$.

b. Peak gate voltage (V_{GS}) ..... 20 V, up to maximum rated V_{GS}.

c. Gate to source resistor (R_{GS}) ..... $25 \leq R_{GS} \leq 50\ \Omega$.

d. Initial junction temperature (T_J) ..... 25°C, −5°C, +10°C.

e. Inductance (L) ..... 0.1 mH.

f. Supply voltage (V_{DD}) ..... 50 V to 150 V dc.

g. Number of pulses to be applied ..... 1 pulse minimum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

4.3.3 Thermal impedance (ΔV_{SD} measurement). The ΔV_{SD} measurement shall be performed in accordance with method 3161 of MIL-STD-750. The ΔV_{SD} measurement conditions (I_H and V_H) and maximum limit shall be derived by each vendor from the thermal response curves (see figure 3) and shall be specified in the certificate of conformance prior to qualification. The following parameter measurements shall apply:

a. Measuring current (I_M).....10 mA.

b. Heating time (t_H).....10 ms.

c. Measurement time delay (t_{MD}).....30 to 60 µs.

d. Sample window time (t_{SW}).....10 µs maximum.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with table E-V of MIL-PRF-19500 and table I herein.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VIA (JANS) of MIL-PRF-19500 and as follows. End-point electrical measurements shall be in accordance with the applicable steps of table IV herein.

Subgroup	Method	Condition
B3	1051	Temperature cycling, test condition G, 100 cycles.
B3	2077	SEM.
B4	1042	Intermittent operation life, condition D, 2,000 cycles. No heat sink nor or forced-air cooling on the device shall be permitted during the on cycle. t_{ON} = 30 seconds minimum.
B5	1042	Accelerated steady-state reverse bias, condition A, V_{DS} = rated; T_A = +175°C; t = 120 hours, minimum.
B5	1042	Accelerated steady-state gate bias, condition B, V_{GS} = rated; T_A = +175°C; t = 24 hours.
B5	2037	Bond strength; test condition A.
B6	3161	Thermal resistance, see 4.5.2.

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-VII of MIL-PRF-19500 and as follows. Electrical measurements (end-points) and delta requirements shall be in accordance with the applicable steps of table IV herein.

Subgroup	Method	Condition
C2	2036	Terminal strength, test condition E, weight = 8 oz. (226.8 g), 3 arcs.
C5	3161	See 4.5.2.
C6	1042	Intermittent operation life, test condition D, 6,000 cycles; 1 cycle = 30 seconds minimum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

4.4.4 Group D inspection. Group D inspection shall be conducted in accordance with table E-VIII of MIL-PRF-19500 and table II herein.

4.4.4.1 Design parameters. Not tested on a per lot basis. Design shall be such that the devices shall be capable of meeting the requirements herein.

4.4.5 Group E inspection. Group E inspection shall be conducted in accordance with the conditions specified for subgroup testing in table E-IX of MIL-PRF-19500 and as specified in table III herein. Electrical measurements (end-points) and delta requirement shall be in accordance with the applicable steps of table IV herein.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurement shall be as specified in section 4 of MIL-STD-750.

4.5.2 Thermal resistance. Thermal resistance measurements shall be performed in accordance with method 3161 of MIL-STD-750. The maximum limit of $R_{\theta JC}$ = 5.0 °C/W. The following parameters shall apply:

a. Measuring current (I_M)..... 10 mA.

b. Drain heating current (I_H) ..... 1 A (minimum).

c. Heating time (t_H)..... Steady-state.

d. Drain-source heating voltage (V_H)..... 25 V.

e. Measurement time delay (t_{MD})..... 30 to 60 µs.

f. Sample window time (t_{SW})..... 10 µs maximum.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Condition		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Thermal impedance 2/	3161	See 4.3.3	ΔV_{SD}			
Breakdown voltage drain to source	3407	Bias condition C, V_{GS} = 0 V dc, I_D = 1 mA dc	$V_{(BR)DSS}$			
2N7395				100		V dc
2N7396				200		V dc
2N7397				250		V dc
2N7398				500		V dc
Gate to source voltage (threshold)	3403	$V_{DS} > V_{GS}$, I_D = 1 mA dc	$V_{GS(th)}$	1.5	4.0	V dc
Gate current	3411	Bias condition C, V_{GS} = +20 V dc, V_{DS} = 0 V dc	I_{GSSF1}		+100	nA dc
Gate current	3411	Bias condition C, V_{GS} = −20 V dc, V_{DS} = 0 V dc	I_{GSSR1}		−100	nA dc
Drain current	3413	Bias condition C, V_{GS} = 0 V dc, V_{DS} = 80 percent of rated V_{DS}	I_{DSS1}		25	µA dc
Static drain to source on-state resistance	3421	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D2}	$r_{DS(on)1}$			
2N7395					0.23	Ω
2N7396					0.46	Ω
2N7397					0.61	Ω
2N7398					2.50	Ω
Static drain to source on-state voltage	3405	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D1}	$V_{DS(on)}$			
2N7395					1.93	V dc
2N7396					2.42	V dc
2N7397					2.56	V dc
2N7398					5.25	V dc
Forward voltage	4011	Condition A, V_{GS} = 0 V dc, pulsed (see 4.5.1), I_D = I_{D1}	V_{SD}		1.8	V dc
Subgroup 3						
High temperature operation		T_C = T_J = +125°C				
Gate current	3411	Bias condition C, V_{GS} = +20 V dc and −20 V dc, V_{DS} = 0 V dc	I_{GSS2}		±200	nA dc

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Condition		Min	Max	
Subgroup 3 – continued						
Drain current	3413	Bias condition C, V_{GS} = 0 V dc, V_{DS} = 80 percent of rated V_{DS}	I_{DSS2}		0.25	mA dc
Static drain to source on-state resistance	3421	Bias condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D2}	$r_{DS(on)2}$			
2N7395					0.36	Ω
2N7396					0.81	Ω
2N7397					1.11	Ω
2N7398					4.80	Ω
Gate to source voltage (threshold)	3403	$V_{DS} \geq V_{GS}$, I_D = 1 mA dc	$V_{GS(th)2}$	0.5		V dc
Low temperature operation		$T_C = T_J$ = −55°C				
Gate to source voltage (threshold)	3403	$V_{DS} \geq V_{GS}$, I_D = 1 mA dc	$V_{GS(th)3}$		5.0	V dc
Subgroup 4						
Switching time test	3472	$I_D = I_{D1}$, V_{GS} = 12 V dc, R_G = 7.5 Ω, V_{DD} = 50 percent of rated V_{DS}				
Turn-on delay time			$t_{D(on)}$			
2N7395					70	ns
2N7396					65	ns
2N7397					60	ns
2N7398					80	ns
Rise time			t_R			
2N7395					220	ns
2N7396					150	ns
2N7397					140	ns
2N7398					100	ns
Turn-off delay time			$t_{D(off)}$			
2N7395					100	ns
2N7396					120	ns
2N7397					120	ns
2N7398					150	ns
Fall time			t_f			
2N7395					90	ns
2N7396					85	ns
2N7397					95	ns
2N7398					140	ns

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection - Continued.

Inspection 1/	MIL-STD-750		Symbol	Limits		Unit
	Method	Condition		Min	Max	
Subgroup 5						
Safe operating area test (high voltage)	3474	See figure 4, tp = 10 ms minimum V_{DS} = 80 percent of maximum rated V_{DS} (V_{DS} < 200 V)				
Electrical measurements		See table IV, steps 1, 2, 3, 4, 5, 6, and 7.				
Subgroup 6						
Not applicable						
Subgroup 7						
Gate charge	3471	Condition B				
On-state gate charge			$Q_{g(on)}$			
2N7395					43	nC
2N7396					38	nC
2N7397					40	nC
2N7398					35	nC
Gate to source charge			Q_{gs}			
2N7395					8.7	nC
2N7396					8.4	nC
2N7397					8.4	nC
2N7398					6.7	nC
Gate to drain charge			Q_{gd}			
2N7395					22	nC
2N7396					20	nC
2N7397					20	nC
2N7398					16	nC
Reverse recovery time	3473	Condition A, di/dt = 100 A/µs, V_{DD} ≤ 30 V, I_D = I_{D1}	t_{rr}			
2N7395					330	ns
2N7396					360	ns
2N7397					400	ns
2N7398					390	ns

1/ For sampling plan, see MIL-PRF-19500.
2/ For end-point measurements, this test is required for the following subgroups:
Group B, subgroups 3, 4 and 5.
Group C, subgroups 2 and 6.
Group E, subgroup 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE II. Group D inspection.

Inspection 1/ 2/ 3/ 4/	MIL-STD-750		Symbol	Pre-irradiation limits		Post irradiation limits		Units
	Method	Conditions		Min	Max	Min	Max	
Subgroup 1								
Not applicable								
Subgroup 2		T_C = +25°C						
Steady state total dose irradiation (V_{GS} bias) 4/	1019	V_{GS} = 12 V, V_{DS} = 0 V						
Steady state total dose irradiation (V_{DS} bias)	1019	V_{GS} = 0 V, V_{DS} = 80 percent of rated V_{DS}						
Breakdown voltage drain to source	3407	Bias condition C, V_{GS} = 0 V, I_D = 1 mA dc,	$V_{(BR)DSS}$					
2N7395				100		100		V dc
2N7396				200		200		V dc
2N7397				250		250		V dc
2N7398				500		500		V dc
Gate to source voltage (threshold)	3403	V_{DS} > V_{GS}, I_D = 1 mA dc	$V_{GS(TH)1}$	1.5	4.0	1.5	4.0	V dc
Gate current	3411	Bias condition C, V_{GS} = +20 V dc and −20 V dc, V_{DS} = 0 V	I_{GSS1}		+100		+100	nA dc
Drain current	3413	Bias condition C, V_{GS} = 0 V, V_{DS} = 80 percent of rated V_{DS}	I_{DSS1}		25		25	µA dc
Static drain to source on-state resistance	3421	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D2}	$r_{DS(ON)1}$					
2N7395					0.23		0.23	Ω
2N7396					0.46		0.46	Ω
2N7397					0.61		0.61	Ω
2N7398					2.50		2.50	Ω
Static drain to source on-state voltage	3405	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D1}	$V_{DS(ON)}$					
2N7395					1.93		1.93	V dc
2N7396					2.42		2.42	V dc
2N7397					2.56		2.56	V dc
2N7398					5.25		5.25	V dc

1/ For sampling plan see MIL-PRF-19500.
2/ Electrical specifications are for 'D' and 'R' rad levels.
3/ Group D qualification may be performed prior to lot formation. Wafers qualified to these group D QCI requirements may be used for any other specification utilizing the same die design.
4/ At the manufacturers option, group D samples need not be subjected to all the screening tests, but shall be assembled in its qualified package or in any qualified package that the manufacturer has data to correlate the performance to the designated package.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE III. Group E inspection (all quality levels) for qualification or requalification only.

Inspection 1/ 2/ 3/ 4/ 5/	MIL-STD-750		Sample plan
	Method	Conditions	
Subgroup 1			12 devices, c = 0
Temperature cycle	1051	Condition G, 500 cycles	
Hermetic seal	1071	Fine and gross leak	
Electrical measurements		See table IV, steps 1, 2, 3, 4, 5, 6, and 7	
Subgroup 2 1/			12 devices, c = 0
Steady-state gate bias	1042	Condition B, 1,000 hours	
Electrical measurements		See table IV, steps 1, 2, 3, 4, 5, 6, and 7	
Steady-state reverse bias	1042	Condition A, 1,000 hours	
Electrical measurements		See table IV, steps 1, 2, 3, 4, 5, 6, and 7	
Subgroup 3			3 devices, c = 0
DPA	2102		
Subgroup 4			Sample size N/A
Thermal impedance curves		See MIL-PRF-19500	
Subgroup 5			5 devices, c = 0
Barometric pressure test 2N7397 2N7398	1001	Condition C. Not required for $V_{BR(DSS)}$ < 200 V V_{DS} = 250 V; $I_{(ISO)}$ < 0.25 mA V_{DS} = 500 V; $I_{(ISO)}$ < 0.25 mA	
Subgroup 6			
ESD	1020		
Subgroup 9			
Commutating diode for safe operating area test procedure for measuring dv/dt during reverse recovery of power MOSFET transistors	3476		22 devices, c = 0

1/ A separate sample for each test may be pulled.
2/ Group E qualification of single event effect testing may be performed prior to lot formation. Wafers qualified to these group E QCI requirements may be used for any other specification utilizing the same die design.
3/ As a minimum, gate to source leakages and drain to source leakage are to be examined to verify the electrical performance of the DUT prior to and after test. At the manufacturer's option, the remaining static tests in table IV, with the exception of step 8, may be performed.
4/ Devices passing a given combination of drain and gate voltage for an LET of 36 to 40 MeV-cm^2/mg qualify the same conditions for an LET of 26 to 30 MeV-cm^2/mg.
5/ This sampling plan applies to each bias condition defined.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

TABLE IV. Group A, B, C and E electrical and delta measurements.


Step	Inspection 1/ 2/	MIL-STD-750		Symbol	Limits		Units
		Method	Conditions		Min	Max	
1.	Breakdown voltage drain to source	3407	Bias condition C, I_D = 1 mA dc, V_{GS} = 0 V	$V_{(BR)DSS}$			
	2N7395				100		V dc
	2N7396				200		V dc
	2N7397				250		V dc
	2N7398				500		V dc
2.	Gate to source voltage (threshold)	3403	V_{DS} > V_{GS}, I_D = 1 mA dc	$V_{GS(TH)1}$	1.5	4.0	V dc
3.	Gate current	3411	Bias condition C, V_{GS} = +20 V and −20 V dc, V_{DS} = 0 V	I_{GSS1}		+100	nA dc
4.	Drain current	3413	Bias condition C, V_{GS} = 0 V dc, V_{DS} = 80 percent of rated V_{DS}	I_{DSS1}		25	µA dc
5.	Static drain to source on-state resistance	3421	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D2}	$r_{DS(ON)1}$			
	2N7395					0.23	Ω
	2N7396					0.46	Ω
	2N7397					0.61	Ω
	2N7398					2.50	Ω
6.	Static drain to source on-state voltage	3405	Condition A, V_{GS} = 12 V dc, pulsed (see 4.5.1), I_D = I_{D1}	$V_{DS(ON)}$			
	2N7395					1.93	V dc
	2N7396					2.42	V dc
	2N7397					2.56	V dc
	2N7398					5.25	V dc
7.	Forward voltage	4011	Condition A, V_{GS} = 0 V dc, pulsed (see 4.5.1), I_D = I_{D1}	V_{SD}		1.8	V dc
8.	Thermal impedance	3161	See 4.3.3	ΔV_{SD}		125	mV

1/ The electrical measurements for table E-VIA (JANS) of MIL-PRF-19500 are as follows:
   a. Subgroup 3, see table IV herein, steps 1, 2, 3, 4, 5, 6, and 7.
   b. Subgroup 4, see table IV herein, steps 1, 2, 3, 4, 5, 6, 7, and 8.
   c. Subgroup 5, see table IV herein, steps 1, 2, 3, 4, 5, 6, and 7.


2/ The electrical measurements for table E-VII of MIL-PRF-19500 are as follows:
   a. Subgroup 2 and 3, see table IV herein, steps 1, 2, 3, 4, 5, 6, and 7.
   b. Subgroup 6, see table IV herein, steps 1, 2, 3, 4, 5, 6, 7, and 8.

3/ The electrical measurements for table E-IX of MIL-PRF-19500 are as follows:
   a. Subgroups 1 and 2, see table IV herein, steps 1, 2, 3, 4, 5, 6, 7, and 8.
   b. Subgroup 8, see table IV herein, steps 3 and 4.


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

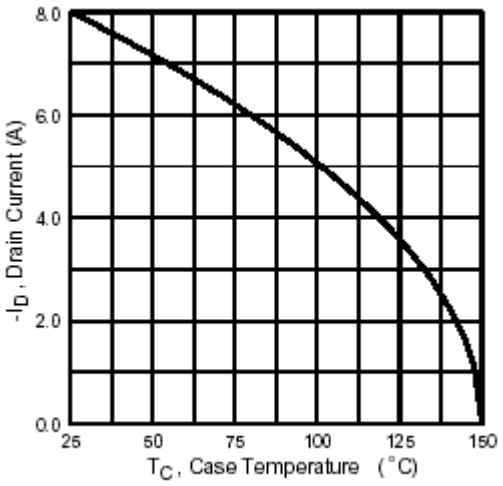


2N7395

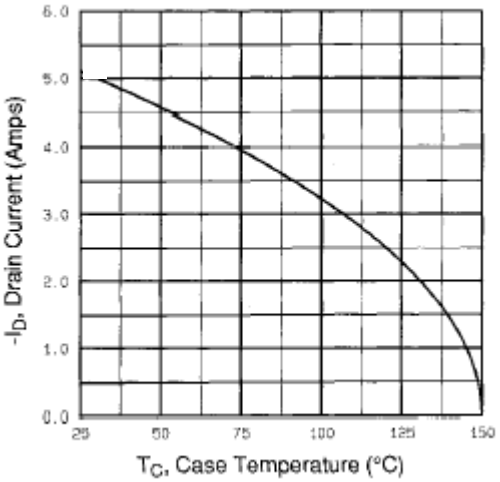

2N7396

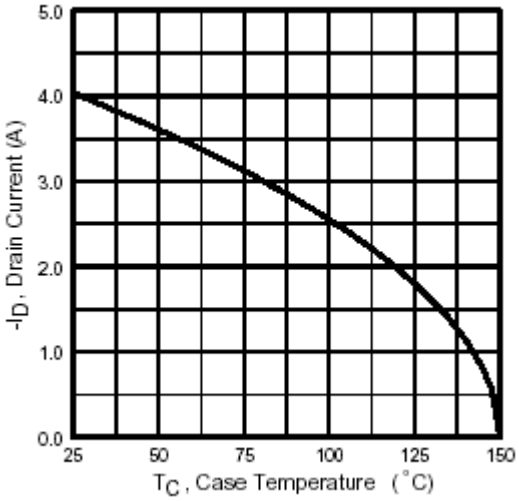

2N7397

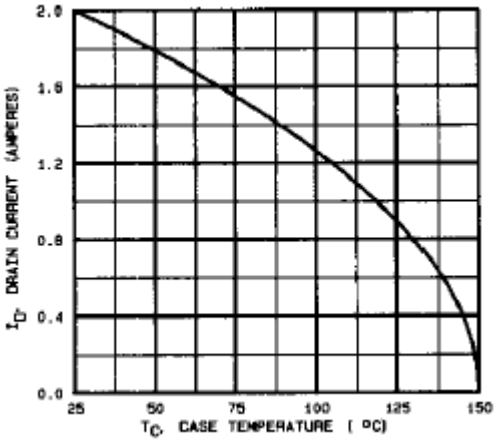

2N7398

FIGURE 2. Maximum drain current vs case temperature graphs.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.


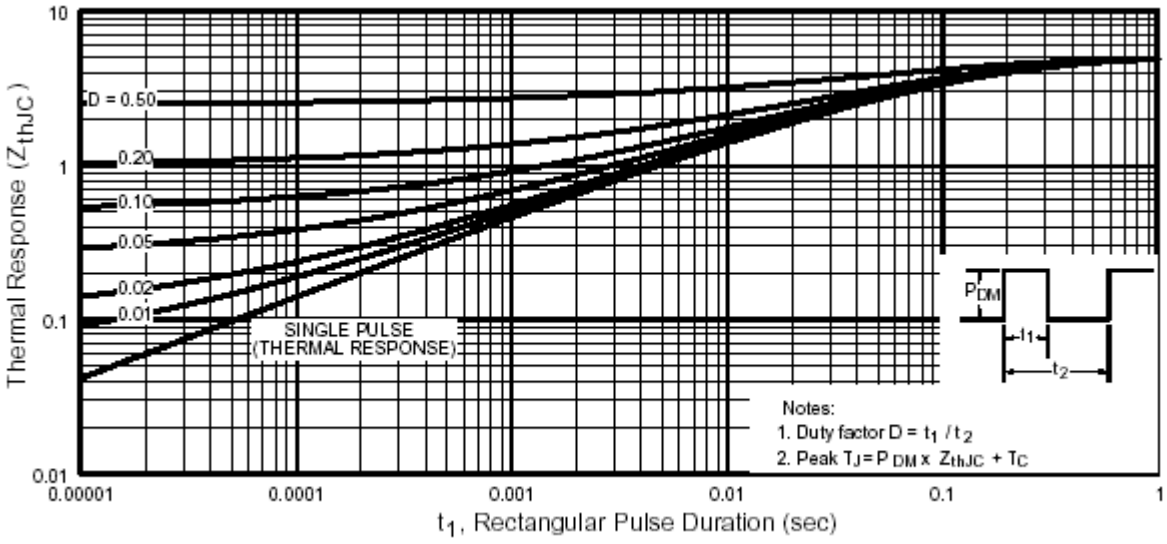


FIGURE 3. Thermal response curves.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

2N7395

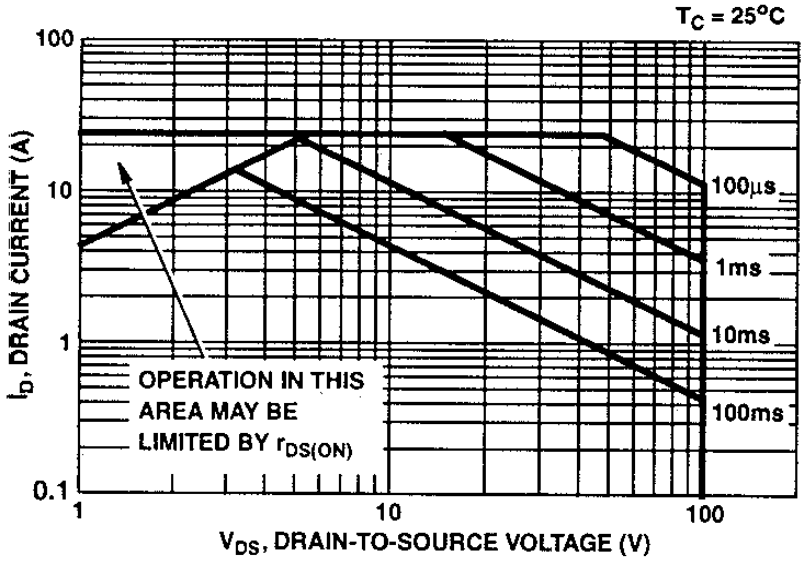

2N7396


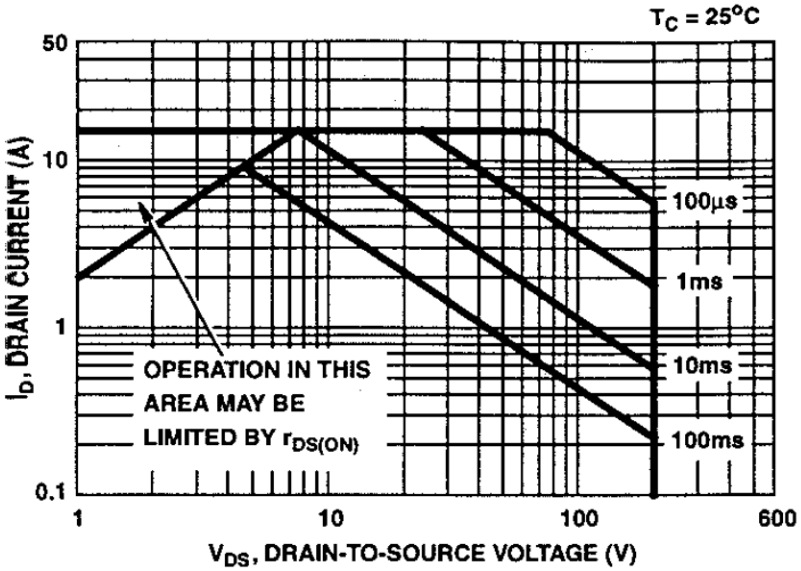


FIGURE 4. Safe operating area graphs.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

2N7397

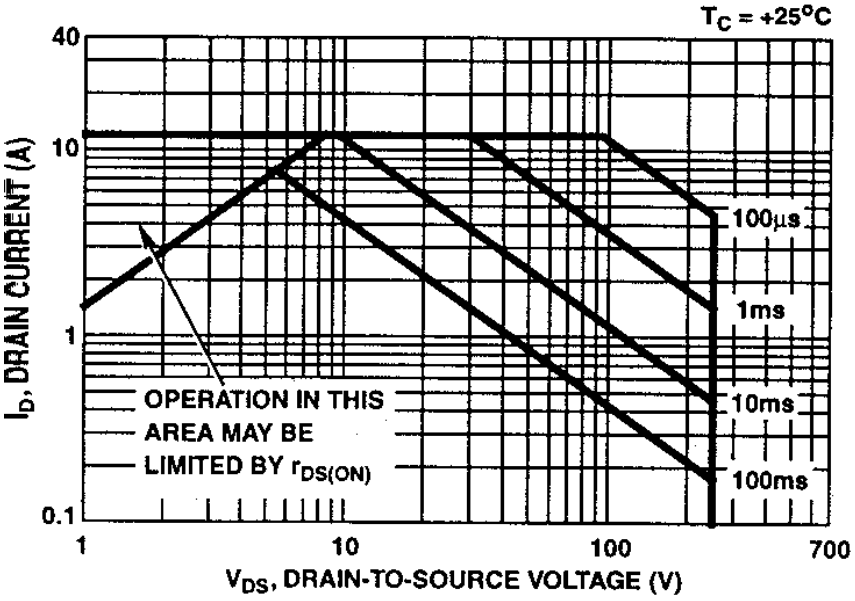

2N7398

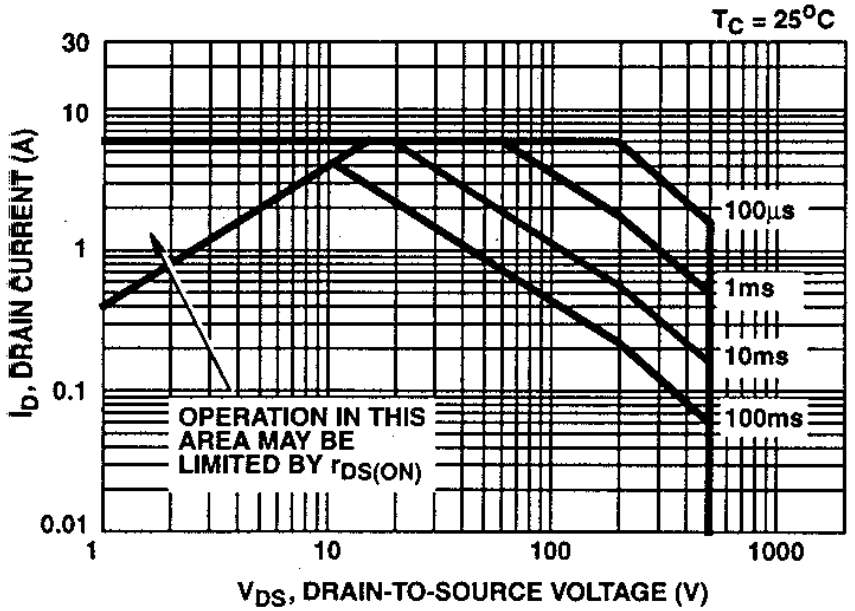


FIGURE 4. Safe operating area graphs - Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification.

b. Packaging requirements (see 5.1).

c. Lead material and finish may be specified (see 3.4.1).

d. The complete PIN, see 1.5 and 6.4.


e. For acquisition of RHA designated devices, table II, subgroup 1 testing of group D herein is optional. If subgroup 1 is desired, it should be specified in the contract.

f. If specific SEE characterization conditions are desired (see section 6.7 and table V), manufacturer's cage code should be specified in the contract or order.

g. If SEE testing data is desired, it should be specified in the contract or order.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List (QML 19500) whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from DLA Land and Maritime, ATTN: VQE, P.O. Box 3990, Columbus, OH 43218-3990 or e-mail vqe.chief@dla.mil . An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://qpldocs.dla.mil.

6.4 PIN construction example. The PINs for encapsulated devices are constructed using the following form.

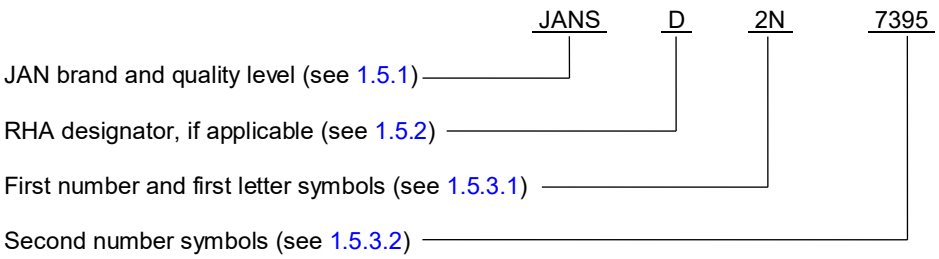

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

6.5 List of PINs. The following is a list of possible PINs available on this specification sheet.

PINs for devices of the "D" RHA level	PINs for devices of the "R" RHA level
JANSD2N7395	JANSR2N7395
JANSD2N7396	JANSR2N7396
JANSD2N7397	JANSR2N7397
JANSD2N7398	JANSR2N7398

6.6 Lead material. The original issue of this specification through MIL−PRF−19500/631B (9 March 2004) specified that the lead material as Kovar or Alloy 52. Because of the performance format of this document, a lead material is no longer specified.

6.7 Manufacturer specific irradiation data. Each manufacturer qualified to this slash sheet has characterized its devices to the requirements of MIL-STD-750 method 1080 and as specified herein. Since each manufacturer's characterization conditions can be different and can vary by the version of method 1080 qualified to, the MIL-STD-750 method 1080 revision version date and conditions used by each manufacturer for characterization have been listed here (see table V) for information only. SEE conditions and figures listed in section 6 are current as of the date of this specification sheet, please contact the manufacturer for the most recent conditions.

TABLE V. Manufacturers characterization conditions.

Manufactures CAGE	Inspection	MIL-STD-750		Sample plan
		Method	Conditions	
Upon qualification, all manufacturers should provide the verification test conditions to be added to this table.				

6.8 Request for new types and configurations. Requests for new device types or configurations for inclusions in this specification sheet should be submitted to: DLA Land and Maritime, ATTN: VAC, Post Office Box 3990, Columbus, OH 43218-3990 or by electronic mail at Semiconductor@dla.mil or by facsimile (614) 693-1642 or DSN 850-6939.

6.9 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.

Custodians:
Army − CR
Navy − EC
Air Force − 85
NASA − NA
DLA – CC

Review activity
Air Force − 19

Preparing activity:
DLA − CC

(Project 5961−2019−086)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:22Z
Check the source to verify that this is the current version before use.