KK-G-476E
April 5, 1976
SUPERSEDING
Fed. Spec. KK-G-476D
August 6, 1969

FEDERAL SPECIFICATION

GLOVES, LEATHER, GAUNTLET, LINEMEN'S

This specification was approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers leather gauntlet work gloves used where contact with live wires is not involved (see 6.1).

1.2 Classification.

1.2.1 Type and sizes. The gloves covered by this specification shall be of one type and furnished in the following sizes as specified (see 6.2):

Small
Medium
Large
Extra large

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

Federal Specifications:

V-T-285	-	Thread, Polyester.
KK-L-162	-	Leather, Cattlehide, Chrome Tanned, for Gloves, Garments, and Equipage.
KK-L-169	-	Leather, Horsehide, Chrome Tanned, for Gloves, Garments, and Equipage.
UU-P-268	-	Paper, Kraft, Wrapping.
CCC-C-419	-	Cloth, Duck, Cotton, Unbleached, Plied-Yarns, Army and Numbered.
DDD-L-20	-	Label; for Clothing, Equipage and Tentage, (General Use).

FSC 8415

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

Federal Standards:

FED-STD-123 - Marking for Shipment (Civil Agencies).
FED-STD-191 - Textile Test Methods.
FED-STD-311 - Leather, Methods of Sampling and Testing.
FED-STD-751 - Stitches, Seams, and Stitchings.

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U. S. Government Printing Office, Washington, DC 20402.

(Single copies of this specification and other Federal Specification required by activities outside the Federal Government for bidding purposes are available without charge from Business Service Centers at the General Services Administration Regional Offices in Boston, New York, Washington, DC, Atlanta, Chicago, Kansas City, MO, Fort Worth, Denver, San Francisco, Los Angeles, and Seattle, WA.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specification:

MIL-B-17757 - Boxes, Shipping, Fiberboard, (Modular Size).

Military Standards:

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.

(Copies of specifications and standards required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply:

National Motor Freight Traffic Association, Inc., Agent

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Associations, Inc., Tariff Order Section, 1616 P Street, N. W., Washington, DC 20036.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

Uniform Classification Committee, Agent

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

3. REQUIREMENTS

3.1 Guide samples. Samples, when furnished, are solely for guidance and information to the supplier (see 6.3). Variations from the specification may appear in the sample, in which case the specification shall govern.

3.2 Material.

3.2.1 Leather. The leather for the back of the hand section of the glove and the leather for the gauntlet shall be split cattlehide conforming to type IV of KK-L-162. The palm, thumb, fingers, and reinforcing pieces shall be full grain horsehide conforming to type II of KK-L-169 or full grain cattlehide conforming to type II of KK-L-162. All grain leather components shall be made of the same kind of leather.

3.2.1.1 Thickness. The thickness of leather glove parts shall be not less than 2-1/2 ounces nor more than 3-1/2 ounces. (Note: An ounce is equivalent in thickness to 1/64 inch). Thickness determinations shall be conducted as specified in 4.2.3.2.

3.2.1.2 Color. The color of all leather components shall be cream or light gray. All leather components used in each pair of gloves shall be of the same color.

3.2.2 Thread. The thread used for stitching and seaming the gloves shall be white thread, polyester, size E, conforming to type I or II, class 1, subclass A of V-T-285.

3.2.3 Gauntlet lining. The gauntlet lining shall be either unbleached cotton duck conforming to the requirements for type I, number 8, hard texture numbered duck described in CCC-C-419, or gauntlet lining fabric composed of two thicknesses of unbleached cotton fabric securely laminated together. The laminated fabric shall be composed of a cotton twill face fabric weighing not less than 3.7 ounces per square yard and plain weave cotton backing fabric weighing not less than 1.7 ounces per square yard. The finished fabric (laminated) shall contain not less than 14 ounces of natural rubber, synthetic rubber, or synthetic resin and weigh not less than 19.4 ounces per square yard.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.2.4 Label. Each glove shall have a combination size and identification label conforming to type III or IV, class 4 of DDD-L-20. The marking medium shall be dark blue or black and shall show fair color fastness to accelereated laundering when tested as specified in DDD-L-20. The label shall include the information required by the applicable products labeling act.

3.3 Stitches, seams, and stitching. All stitching and seaming shall be stitch type 301 and seam types as specified in table II and shall be in conformance with the requirement of FED-STD-751, using not less than 7 nor more than 10 stitches per inch. Unless otherwise indicated, ends of all seams and stitching produced with 301 stitch type, when not caught in other seams or stitching, shall be backstitched not less than 1/2 inch. Thread tension shall be maintained so there will be no loose stitching resulting in a loose bobbin or top thread or no excessively tight stitching resulting in puckering of the materials sewn.

3.3.1 Repairs of type 301 stitching. Repairs of stitching shall be as follows:

a. When thread breaks or bobbin run-outs occur during sewing, the stitching shall be repaired by restarting the stitching a minimum of 1/2 inch back of the end of stitching.

b. Thread breaks, or two or more consecutive skipped stitches or run-offs noted during inspection of the item (in-process or end item) shall be repaired by overstitching. The stitching shall start a minimum of 1/2 inch back of the defective area, continue over the defective area and continue a minimum of 1/2 inch beyond the defective area onto the existing stitching. Loose or tight stitching shall be repaired by removing the defective stitching without damaging the material and restitching in the required manner. 1/

1/ When making the above repairs, the ends of stitching are not required to be backstitched.

3.4 Dies and patterns. The dies or patterns for cutting all parts of the gloves shall be furnished by the supplier and shall be of the proper proportions to provide good fitting gloves conforming to finished measurements in table I.

3.5 Figures. Figure 1 is furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figures, the written specification shall govern.

3.6 Dimensions of gloves. The finished gloves shall conform to the dimensions shown in table I. Measurements shall be taken as shown in figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.7 Dimensions of reinforcements. The flap, reinforcing the front seam joining the palm and bottom of gauntlet, shall be approximately 2 inches wide. The thumb welt shall be approximately 1/2 inch wide; the welt for base of fingers approximately 5/8 inch wide; and the welt for the "Davey tips shall be cut approximately 5/8 inch wide.

TABLE I. Finished dimensions of gloves

Measurements	Sizes				Tolerance plus or minus
	Small	Medium	Large	Extra Large	
	Inches	Inches	Inches	Inches	Inch
A. Top edge of cuff to tip of second finger	12-3/4	13	13-1/2	14	1/2
B. Bottom edge of cuff to tip of second finger	7-3/4	8	8-1/2	8-3/4	1/4
C. Across palm at thumb, crotch, seam to seam	4-1/2	5	5-1/2	5-3/4	1/8
D. Tip of index finger to thumb crotch	4-3/4	5	5-1/2	5-3/4	1/8
E. Thumb crotch to tip of thumb	2-3/4	3	3-1/4	3-1/2	1/8
F. Across bottom edge of cuff	4-3/4	5	5-1/2	6	1/4
G. Across top edge of cuff	6-1/4	6-3/4	7	7-1/2	1/4

3.8 Design. The design of the glove shall be a two-piece, half out-seamed slip-on style, Gunn-cut glove, with a hemmed gauntlet. The continuous thumb shall be inseamed around all edges with a turn-back leather welt inserted in the seam. The seam at the base of the fingers shall include a leather reinforcing welt turned up to protect the stitching. A palm reinforcing flap is attached to the top of the hand and bottom of the gauntlet, on the palm side as shown in figure 1. The fingers shall be outseam and shall have protective turn-back leather welts (Davey tips) caught in the seams of the finger tips.

3.8.1 Gauntlet. The gauntlet shall be made in two pieces, each piece lined with cotton duck or laminated cotton fabric extending to within 3/8 inch of the top edge of the gauntlet to facilitate the hemming of the top edge. The remainder of the glove shall be unlined. The joining of the gauntlet and the closing shall be of outseam construction.

3.9 Manufacturing operations requirements. The gloves shall be made by and with the use of all manufacturing operations listed in table II. The supplier is not required to follow the exact sequence of operations listed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

NO.	MANUFACTURING OPERATIONS REQUIREMENTS TABLE II	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN or LOOPER	COVER
1.	Preparation before cutting. Before cutting, the leather shall be dampened and all the stretch in the lengthwise direction (butt to head direction of skin) shall be pulled out.						
2.	Cutting. Each leather component shall be cut with its length direction (cuff to fingertip direction) parallel to the lengthwise direction of the leather.						
3.	Join palm to fourchette. Lap palm over the fourchette, position welt grain side down on top of grain side of palm and align edge of welt with the edge of the palm. Join welt, palm and fourchette with a double row of stitches 1/16 to 3/32 inch gage. The welt piece shall be positioned so when it is turned back over the seam the portion folded back shall be not less than 1/2 inch wide. The corners of the welt that are against the palm shall be caught in the seaming of the first finger and little finger respectively. The beginning and end of the stitching shall be securely back-stitched with not less than three stitches. Care shall be taken to avoid twisting or distortion of the fingers.	301	LSa-2	7-10	E	E	
4.	Join thumb and palm (inseam construction). Seam the thumb to the palm all around the edge of thumb using 1/16 to 1/8 inch stitch margin. The welt strip shall be caught in the entire seam and shall be so positioned that when it is turned back away from the palm the grain side shall face away from the glove.	301	SSa-1	7-10	E	E	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

NO.	MANUFACTURING OPERATIONS REQUIREMENTS TABLE II	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN or LOOPER	COVER
4.	Join thumb and palm (inseam construction). (cont'd) The beginning and end of the thumb seam and welt shall be caught in the seam joining the gauntlet to the hand section.						
5.	Join fingers (outseam construction). The end of each of the four fingers shall have protective leather welt strips positioned as indicated in figure 1. Seam the back of the fingers to the front of the fingers using 1/16 to 1/8 inch stitch margin catching the welts which have been positioned with their grain sides on top of the grain side of the front of the fingers. When the welt strips are turned back away from the front of the fingers toward the finger tips the grain side of the turned back portion shall face away from the front of the fingers. Care shall be taken to avoid any twisting or distortion of the fingers.	301	SSa-1	7-10	E	E	
6.	Back seam. Lap the front of the glove over the back of the glove and join them with a double row of stitching 1/16 to 1/8 inch gage.	301	LSa-2	7-10	E	E	
7.	Make gauntlet. The two lined gauntlet pieces (see 3.8.1) shall be joined on the thumb side of glove by lapping the palm side section of the gauntlet over the back gauntlet piece and double stitching using a 1/8 to 3/16 inch gage.	301	LSa-2	7-10	E	E	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

NO.	MANUFACTURING OPERATIONS REQUIREMENTS TABLE II	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN or LOOPER	COVER
8.	Hem gauntlet. The top leather edge of gauntlet shall be turned in 1/2 to 5/8 inch and single stitched 1/16 to 1/8 inch from raw edge.	301	EFa-1	7-10	E	E	
9.	Join gauntlet to hand section. The bottom edge of lined gauntlet shall be attached to the top of hand at wrist by lapping the gauntlet 1/2 to 5/8 inch over the hand and stitching with a double row of stitching 1/8 to 3/16 inch gage catching the flap reinforcement piece.	301	LSa-2	7-10	E	E	
10.	Attach flap (reinforcement piece) at wrist. The flap shall be caught in the seam joining the palm side of gauntlet to hand section. The flap shall be turned back over the seam with grain side facing out and stitched to the gauntlet with a double row of stitching around the sides and top edge of flap using a 1/8 to 3/16 inch gage (see figure 1).	301	LSbj-2	7-10	E	E	
11.	Closing. The side seam from tip of fourth finger to hem of gauntlet shall be outseamed single stitched using a 1/16 to 1/8 stitch margin. A second row of stitching 1/16 to 1/8 inch in back of first row shall be stitched on glove section from tip of fourth finger along the side to the seam joining the gauntlet to the hand.	301	SSa-1	7-10	E	E	

STSNL Form 903
27 Jul 73 EDITION OF 16 JUN 72 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

NO.	MANUFACTURING OPERATIONS REQUIREMENTS TABLE II	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN or LOOPER	COVER
12.	Marking. The label (see 3.2.4) shall be applied to the inside of the back of each glove in the center approximately 1/2 inch down from the finished top edge.						
13.	Pairing. The gloves shall be matched, paired and tacked together with thread or non-corrosive soft metal staples. Tacking shall be done with one staple or not more than two stitches using cord thread which will permit the gloves to be pulled apart without tearing the materials. The tack shall be located just below the hem of gauntlet and approximately 1/2 inch from the closing seam.						

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

3.10 Replacement of defective components. During the spreading, cutting and manufacturing process, components having material defects or damages that are classified as defects in 4.2.3.1 and 4.2.3.2 shall be removed from production and replaced with non-defective and properly matched components.

3.11 Workmanship. The finished gloves shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels (AQL's).

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated hereinafter.

4.2.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase documents. In addition, testing shall be performed on components as specified in 4.2.1.1.

4.2.1.1 Fabric testing. The fabric shall be tested for the characteristics in table III. The test methods listed in table III shall be in accordance with FED-STD-191, wherever applicable. Testing for all requirements listed in table III are applicable to the sample unit. The sample unit shall be one linear yard. The sample size shall be as follows:

Lot size (yards)	Sample size
800 or less	2
801 up to, and including 22,000	3
22,001 and over	5

The lot shall be unacceptable if one or more units fail to meet any requirements specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE III. Fabric component tests

Component	Characteristic	Requirement reference	Test method
Face fabric	Material identification	3.2.3	1200 1/
	Weight (oz. per sq. yds)	3.2.3	5041 1/
	Weave	3.2.3	Visual
Backing fabric	Material identification	3.2.3	1200 1/
	Weight (oz. per sq. yd)	3.2.3	5041 1/
	Weave	3.2.3	Visual
Finished fabric	Weight (oz. per sq. yd.)	3.2.3	5041

1/ Unless otherwise specified, a certificate of compliance shall be submitted and will be acceptable for the stated requirement.

4.2.2 In-process inspection. Inspection shall be made at any point or during any phase of the manufacturing process to determine whether operations or assemblies are carried out as specified. The Government reserves the right to exclude from consideration for acceptance any material or service for which in-process inspection has indicated non-conformance.

4.2.3 Examination of the end item. The defects found during examination of the end product shall be classified in accordance with 4.2.3.1 and 4.2.3.2. The applicable inspection levels and AQL's shall be as indicated in 4.2.3.3. The sample unit for this examination shall be one glove. Selection of the sample shall be by pairs. The sample unit for pairing defects shall be one pair. Defects for pairing shall be classified as a single defect. The lot size shall be expressed in terms of one glove each.

4.2.3.1 Visual examination of gloves. The gloves shall be examined for defects in pairing, color, design, construction, material workmanship, and marking as indicated in table IV.

TABLE IV. Classification of defects

Examine	Defect	Classification Major	Minor
Pairing	Not properly mated, e.g., not right and left of same size.	X	
	Not tacked together.		X
	Wide variation in color in the pair.		X
Color	Not as specified.	X	
	Color not uniform or shaded parts affecting appearance.		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (cont'd)

Examine	Defect	Classification Major	Minor
Design	Any characteristic not in accordance with the specified requirements (unless otherwise classified herein).	X	
Leather	Not cattlehide or horsehide (where specified).	X	
	Not full grain (where specified).	X	
	Not split leather (where specified).	X	
	Not soft and pliable.	X	
	Any through hole (except pinhole), cut, tear or rip.	X	
	Three or more pinholes in a glove.		X
	Grain damage or imperfections:		
	-Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
	Deep open scratch.	X	
	Deep wrinkles, seriously affecting serviceability.	X	
	Wrinkles affecting serviceability but not seriously		X
	Any scar or abraded area:		
	- Seriously affecting serviceability.	X	
	- Affecting serviceability, but not seriously.		X
	Bony area or thin spot:		
	-Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
	Flesh side of grain leather or either side of split leather contains excessively loose flesh more than two square inches in total area.		X
	Loose or spongy leather.	X	
	Flanky leather:		
	- Seriously affecting serviceability.	X	
	-Affecting serviceability, but not seriously.		X
Finish (Leather)	Finish applied to grain surface.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (cont'd)

Examine	Defect	Classification Major	Minor
Gauntlet lining	Any hole, cut, or tear.	X	
	Multiple floats, loose ends, smashes, or slubs.		X
	Any broken or missing pick or end.		X
	Any mend in fabric (except re-stitching of seams).		X
Construction and workmanship	Any component or operation omitted.	X	
General (applicable to all components unless other wise indicated herein.)	Any component misplaced or not serving purpose intended.		X
	Any component or assembly damaged.	X	
	Any component not securely affixed, e.g., gauntlet loosely attached to back or palm of glove.	X	
	Any workmanship damage, e.g., scissor or knife cut.	X	
	Any mend in leather, e.g., patch (not applicable to restitched seam repair).	X	
Seams and stitching	Open seam:		
	- In single stitched seam.	X	
	- In both rows of a double stitched seam.	X	
	- In one row of a double stitched seam.		X
	- Repaired, but not repaired as specified.		X
NOTE:	A seam shall be classified as open when one or more stitches joining a seam are broken or when two or more consecutive skipped stitches or run-offs occur.		
	Not specified seam type.	X	
	Not specified stitch type.	X	
	Any row of stitching omitted.	X	
	Loose stitch tension resulting in a loosely secured seam.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (cont'd)

Examine	Defect	Classification Major	Minor
Seams and stitching (cont'd)	Ends of 301 stitching not back-stitched or backstitched less than 1/2 inch when not caught in another row of stitching.		X
	Tight stitch tensions resulting in cutting of leather or breaking of stitches when normal pull is applied in direction of the seam or stitching.	X	
	Gage or margin of stitching irregular or not as specified: -Affecting serviceability seriously.	X	
	-Affecting serviceability but not seriously.		X
	Any part caught in unrelated row of stitching.	X	
	One or two stitches per inch less than specified.		X
	Three or more stitches per inch less than specified.	X	
	More than the specified maximum number of stitches per inch damaging leather.	X	
	More than the specified maximum number of stitches per inch not damaging leather.		X
Assembly detail	Glove not neatly laid off.		X
	Not outseam or inseam construction where specified.	X	
	Finger distorted or twisted affecting comfort of wearer.	X	
	Thread ends not trimmed through-out glove.		X
	Not properly trimmed or finished, e.g., lump or bulk in finger inseam because leather was not properly trimmed.	X	
	Not constructed with specified number of pieces of leather (except welting and rein-forcements).	X	
	Welting reinforcing flap or reinforcements, missing, or not caught by stitching.	X	
	Gauntlet not lined.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

TABLE IV. Classification of defects (cont'd)

Examine	Defect	Classification Major	Minor
Marking	Missing, incomplete, incorrect, not legible, not specified size, not in proper location, or not accomplished in the specified manner.		X

4.2.3.2 Dimensional examination. The gloves shall be examined for dimensional defects including thickness of leather. Any dimension that is not within the established tolerance shall be classified a defect.

NOTE: Each leather part of the glove shall be checked for thickness, i.e., palm, thumb, and body of gloves. Any of these parts that are not within the required thickness range shall constitute a defect. (Thickness shall be determined in accordance with the procedure for "Fabricated-Leather Articles" of method 1011 in FED-STD-311, except that two determinations shall be made on each part. Where glove parts are lined, the lining should be parted from the leather and the thickness of the leather should be taken doubled. This dimension is then divided by two.

4.2.3.3 Inspection levels and AQLs. The inspection levels and AQLs, expressed in defects per 100 units, shall be as follows:

Examination	Inspection level	AQL Major	AQL Total
Par 4.2.3.1	II	2.5	6.5
Par 4.2.3.2	S-3	-	4.0

4.2.4 Examination of preparation for delivery requirements. An examination shall be made to determine that the packaging, packing, and marking comply with the section 5 requirement. Defects shall be scored in accordance with list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be closed. Examination for workmanship defects listed below shall be conducted on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing, damaged or not as specified.
Workmanship	Inadequate application of component such as: Incomplete closure of container flap, loose strapping, improper taping or inadequate stapling. Bulged or distorted container.
Content	Number of bundles per shipping container is more or less than required. Number of pairs of gloves per bundle is more or less than required. 1/

1/ For this defect, two bundles shall be examined from each shipping container in the sample.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Packaging shall be level A or C as specified (see 6.2).


5.1.1 Level A. Four pairs of gloves, of one size only, shall be evenly stacked in a bundle. The gloves shall be alternately reversed, finger-tip to gauntlet, with the small fingers of each pair positioned in each corner of the bundle. Each glove bundle shall be securely tied with cotton tape or twine.

5.1.2 Level C. Gloves shall be packaged to afford adequate protection against physical damage during shipment from the supply source to the first receiving activity. The contractor may use his standard practice when it meets this requirement.


5.2 Packing. Packing shall be level A, B, or C as specified (see 6.2).

5.2.1 Level A. Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled, closed, and reinforced conforming to class weather-resistant, grade V2s, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class weather-resistant, variety DW, grade 15C of MIL-B-17757. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to type I, grade B of UU-P-268. Toward the end of the contract, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same shipping container.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

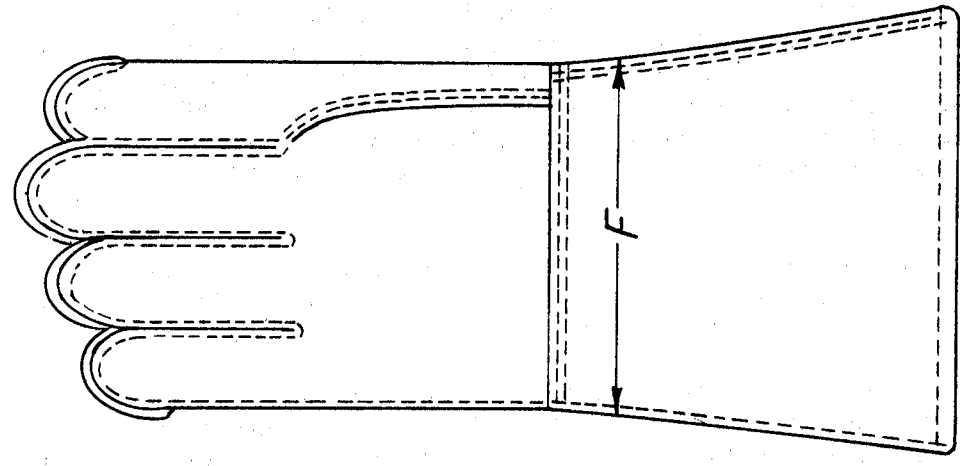

BACK

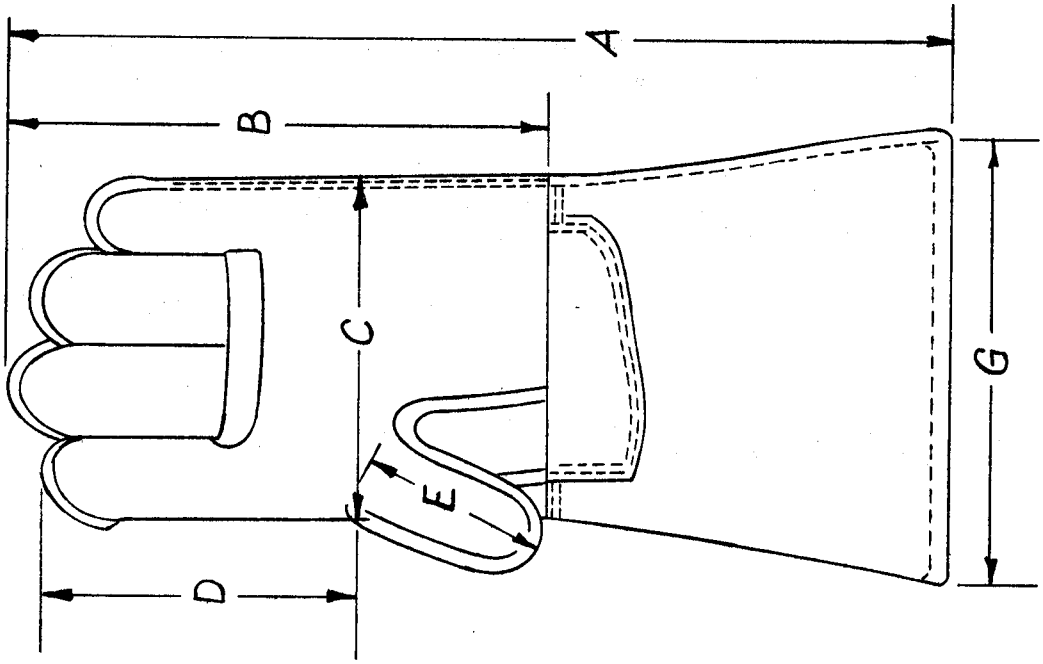

FRONT

FIG 1. GLOVES, LEATHER, GAUNTLET, LINEMEN'S

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

5.2.2 Level B. Eighty pairs of gloves of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled and closed conforming to class domestic, grade 275, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class domestic, variety DW, grade 275 of MIL-B-17757. Level A packages shall be packed flat, four in length, one in width, and five in depth within a shipping container. Each container shall have the contents completely covered on the top and bottom with a sheet of 30-pound minimum basis weight kraft paper conforming to type I, grade B of UU-P-268. Toward the end of the contract, or when there is less than the required amount per container of the same size, mixed sizes may be packed within the same shipping container.

5.2.2.1 When specified (see 6.2), the shipping container shall be a grade V3c, V3s or V4s fiberboard box fabricated in accordance with MIL-B-17757 and closed in accordance with the appendix of the box specification.

5.2.3 Level C. Gloves, pakcaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. Containers shall be in accordance with Uniform Freight Classification or National Motor Freight Classification, as applicable.

5.3 Marking. Marking shall be in accordance with 5.3.1 or 5.3.2 (see 6.2).

5.3.1 Military requirements. In addition to any special marking required by the contract or order, shipping container shall be marked in accordance with MIL-STD-129.

5.3.2 Civil agencies. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with FED-STD-123.

5.3.3 Labels, mixed sizes. Each shipping container, packed with mixed sizes only, shall have securely attached to the end or side, directly under the printing or stencilling, a white paper label 5 by 4 inches with the words "MIXED SIZES" plainly stamped or printed thereon and under these words shall be legibly stamped or printed the correct quantity and sizes contained therein.

6. NOTES

6.1 Intended use. This glove is intended for use by linemen or others where contact with live wires is not involved.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Size required (see 1.2).
(c) Selection of applicable levels of packaging and packing required (see 5.1 and 5.2).
(d) When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.2.2.1).
(e) Marking required (see 5.3).

6.3 Samples. For access to samples, address the procuring activity issuing the invitation for bids.

Custodians:

Army - GL
Navy - SA
Air Force - 82

Review activities:

Army - MD
Navy - YD
DSA - CT

User activities:

Army - SM
Navy - OS, MC

Preparing activity:

Army - GL

Civil Agency Coordinating Activities:

AGR - AMS
COMMERCE - NBS
GSA - FSS
HEW - FDA
INTERIOR - BLM
VA - DMS

Project No. 8415-0817

Orders for this publication are to be placed with General Services Administration, acting as an agent for the Superintendent of Documents. See section 2 of this specification to obtain extra copies and other documents referenced herein. Price 45 cents each.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:57Z
Check the source to verify that this is the current version before use.