INCH-POUND

MIL-R-7885/10(AR)
29 September 1989

MILITARY SPECIFICATION SHEET

RIVET, BLIND, STRUCTURAL, UNIVERSAL PROTRUDING HEAD, MULTI-GRIP, MECHANICALLY LOCKED (TYPE I, STYLE A, CLASS 1)

This specification sheet is approved for use by the U.S. Army Armament Munitions and Chemical Command, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and the issue of the following specification listed in that issue of the Department of Defense Index of Specifications and Standards (DODISS) specified in the solicitation: MIL-R-7885.

Intended Use. The Rivet covered herein is intended for the HMMWV (Hummer) system application and similar type equipment.

Qualified Products List (QPL). A QPL for MIL-R-7885/10(AR) is not required.

DESIGN AND USAGE LIMITATION. Rivets shall be used in compliance with the limitations of MS33522.

INSTALLATION. Rivets shall be capable of being installed by a tool conforming to MIL-R-85188. Lubricant shall not be removed prior to installation.

REQUIREMENTS:

MATERIAL:

Rivets are available in the following material combinations:

Sleeve: 5056 Al Alloy per QQ-A-430 (UNS A95056)
Spindle: 7075 Al Alloy per QQ-A-430 (UNS A97075) or
2014 Al Alloy per QQ-A-225 (UNS A92014)

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T09:27Z
Check the source to verify that this is the current version before use.

Sleeve: Carbon Steel, C1008 thru C1022 (UNS G10080 thru G10220) per ASTM A545.
Spindle: Carbon Steel, C1008 thru C1022 (UNS G10080 thru G10220) per ASTM A545.

Sleeve: Corrosion-Resistant Steel, 304 per ASTM A580 (UNS S30400) or per ASTM A493 (UNS S30430).
Spindle: Corrosion-Resistant Steel, 304 per ASTM A580 (UNS S30400) or 305 per ASTM A580 (UNS S30500).

LUBRICANT: See MIL-R-7885

PROTECTIVE TREATMENT:

Sleeve: 5056 Al Alloy: Chemically treated per MIL-C-5541, color clear.
Spindle: 7075 Al Alloy: Chemically treated per MIL-C-5541, color clear.

Sleeve: Carbon Steel: Zinc Coated per ASTM B633, Type III (clear), Class Fe/Zn 5.
Spindle: Carbon Steel: Zinc Coated per ASTM B633, Type II (Gold), Class Fe/Zn 5.


Sleeve: Corrosion-Resistant Steel: Passivate per QQ-P-35.
Spindle: Corrosion-Resistant Steel: Passivate per QQ-P-35.

SURFACE TEXTURE: Surface texture shall not exceed 125 microinches in accordance with ANSI/ASME B46.1.

TOLERANCES: Unless otherwise specified, decimals $\pm$.010, angles $\pm 2^{\circ}$.

Unless otherwise specified, dimensions are in inches.
Break all sharp edges and remove all burrs and slivers.

Source: https://assist.dla.mil -- Downloaded: 202610-17T09:27Z
Check the source to verify that this is the current version before use.

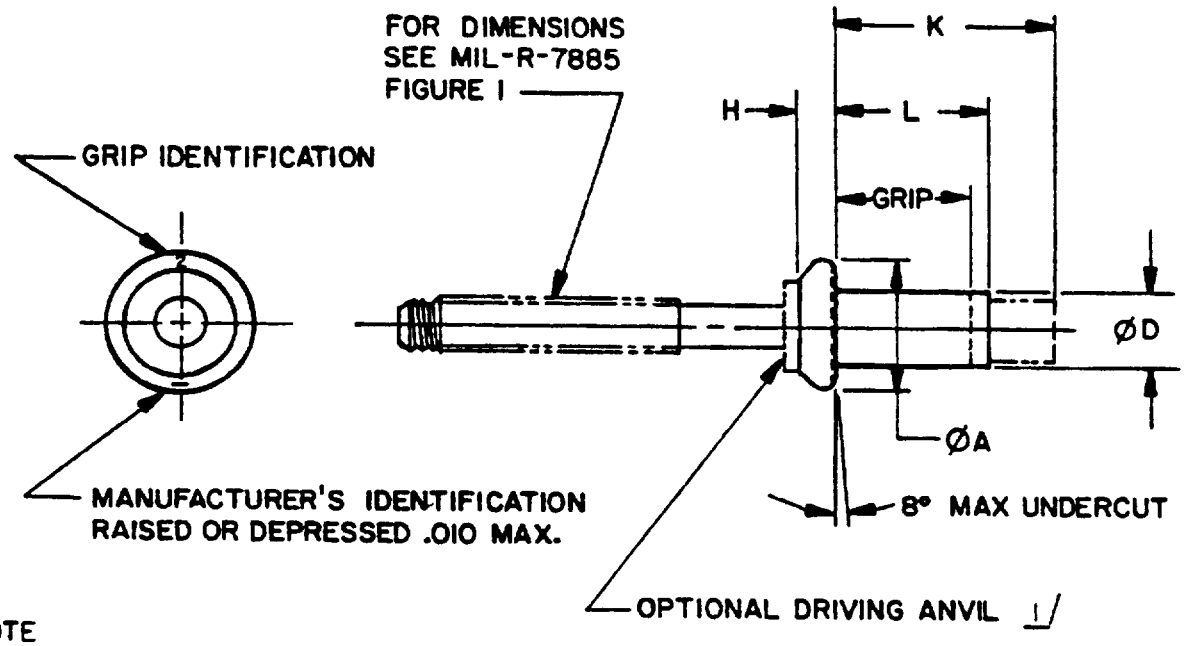

NOTE
1/ THE SUPPLIER HAS THE OPTION OF PROVIDING A DRIVING ANVIL TO INSURE COMPATIBILITY OF THE RIVET WITH MIL-R-85188 AND MIL-R-7885 REQUIREMENTS

FIGURE 1. RIVET, BLIND, STRUCTURAL, UNIVERSAL PROTRUDING HEAD, MUTI-GRIP, MECHANICALLY LOCKED (TYPE I, STYLE A, CLASS 1

TABLE I

NOMINAL SIZE	DIAMETER REFERENCE	ØA		ØD		H		INSTALLATION HOLE LIMITS	
		MAX	MIN	MAX	MIN	MAX	MIN	MAX	MIN
6	0.188	0.400	0.375	0.193	0.184	.085	.067	0.204	0.194

TABLE II

GRIP RANGE	DASH NO.	L MAX	K MAX.
0.062-0.270	1	0.416	0.727
0.214-0.437	2	0.577	0.862

Source: https://assist.dla.mil -- Downloaded: 20261 0-17T09:27Z
Check the source to verify that this is the current version before use.

TABLE III. Single Shear and Tensile Strength Values

NOMINAL SIZE	MATERIAL	SHEAR STRENGTH MIN LBS.	TENSILE STRENGTH MIN LBS.
6	Carbon or corrosion-resistant steel	1400	1100
	Aluminum	600	500

TABLE IV. Spindle Retention Load

NOMINAL SIZE	SPINDLE RETENTION LOAD MIN LBS.	
	Carbon or corrosion-resistant steel	Aluminum
6	100	50

EXAMPLE OF PART IDENTIFYING NUMBER (PIN):

M7885/10 - 6 B - 1

- 1 — Grip Length Dash No. (See Table II)
- B — Material: B - Aluminum; R - Corrosion-Resistant Steel; S - Carbon Steel
- 6 — Nominal Size in 0.0312-Inch (see Table I)
- M7885/10 — Specification Sheet No.

The following requirements specified in MIL-R-7885 are not applicable to MIL-R-7885/10(AR):

a. Qualification.
b. Identification of product.
c. Tensile strength in thin sheet.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T09:27Z
Check the source to verify that this is the current version before use.

Custodian:
Army - AR

Review Activity:
Army - AT

Preparing Activity:
Army - AR

(Project 5320-A010)

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T09:27Z
Check the source to verify that this is the current version before use.