MIL-E-22200/1E
3 October 1973
SUPERSEDING
MIL-E-0022200/1D(SHIPS)
31 January 1967
MIL-E-22200/1C
29 June 1962
(See 6.4)

MILITARY SPECIFICATION

ELECTRODES, WELDING, MINERAL COVERED, IRON-POWDER, LOW-HYDROGEN MEDIUM AND HIGH TENSILE STEEL, AS WELDED OR STRESS-RELIEVED WELD APPLICATION

This specification is approved for use by all Departments and agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers iron-powder, low-hydrogen types of covered electrodes, for the fabrication and repair welding of low and medium carbon, high tensile and higher-strength low-alloy steels for as-welded and stress-relieved applications.

1.2 Classification. Iron-powder low-hydrogen electrodes shall be furnished in the types, classes, and sizes shown in table I, as specified (see 6.2).

Table I - Types, classes, and sizes.

Type 1/ 2/ 3/	Class	Positions of welding	Sizes (diameter)
MIL-7018 MIL-8018-C3 MIL-8018-C3SR	1 2	All Horizontal fillets and flat	3/32, 1/8, 5/32 3/16, 7/32, 1/4
	3	Flat	5/16
MIL-9018-M MIL-10018-M MIL-11018-M	1 2	All Horizontal fillets and flat	3/32, 1/8, 5/32 3/16, 7/32, 1/4

1/ Type classifications of electrodes will be determined according to the capability of the electrode to meet the tests specified herein, when used in the positions of welding specified in table I and in section 4. An electrode shall be approved under ONE type classification; and an electrode shall NOT be approved if it differs in type from that stated in the manufacturer's request for test. The position description indicates the maximum size qualified under the specification. However, reference should be made to the Qualified Products List (QPL) for the selection of electrodes for all positions of welding.

2/ The suffix RC added to the MIL type pertains to restriction of the copper content (see 3.4). All requirements, tests and acceptance criteria remain otherwise unchanged.

3/ Addition of the suffix SR to the basic MIL type designation indicates a special MIL type electrode formulated to meet the long time (50 hours) stress-relieved mechanical properties/ requirements only.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

MILITARY

MIL-W-10430 - Welding Rods and Electrodes; Preparation for Delivery of.
MIL-E-22200 - Electrodes, Welding, Covered; General Specification for.
MIL-S-22698 - Steel Plate, Carbon, Structural, for Ships.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL
FED-STD-151 - Metals Test Methods

MILITARY
MIL-STD-271 - Nondestructive Testing Requirements for Metals.
MIL-STD-418 - Mechanical Tests for Welded Joints.

PUBLICATION

MILITARY
NAVSHIPS 0900-003-9000 - Radiographic Standards for Production and Repair Welds.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following document forms a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

UNIFORM CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606.)

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)
A131-71 - Structural Steel for Ships.

(Application for copies should be addressed to the American Soceity for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.)

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)
Z49.1-67 - Safety in Welding and Cutting.

(Application for copies should be addressed to the American National Standards Institute, Inc., 1430 Broadway, New York, New York 10018.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3 REQUIREMENTS

3.1 Electrodes furnished under this specification shall conform to the requirements of MIL-L-222000 and as specified herein.

3.2 Composition and iron content.

3.2.1 Composition. The chemical composition of the coverings, except as specified in 3.2.2, is optional with the manufacturer. The water content of the coverings shall not exceed the percent-by-weight values specified in table II

Table II - Water content.

Type	Percent by weight maximum
MIL-7018	0.40
MIL-8018-C3	0.40
MIL-8018-C3H8	0.40
MIL-9018-M	0.20
MIL-10018-M	0.20
MIL-11018-M	0.20

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

3.2.2 Total iron content. The total iron content of the covering, including any combined iron in addition to metallic iron powder, shall be not less than 15 percent.

3.3 Groove welds.

3.3.1 Mechanical properties. The weld metal properties for the tensile and impact tests required for qualification inspection, comparison inspection, quality conformance inspection or the procurement document shall be as specified in table III. The applicable stress-relieving treatments shall be as follows:

(a) MIL-7018 and MIL-8018-C3. The coupon shall be heated to 1150° + 25°F, held at this temperature for two hours and furnace cooled at 200°F per hour or slower to below 500°F.

(b) MIL-8018-C3SR. The coupon shall be heated to 1150° + 25°F, held at this temperature for two hours and furnace cooled at 200°F per hour or slower to below 500°F.

(c) MIL-8018-C3SR. The coupon shall be heated to 1150° + 25°F, held at this temperature for 50 hours minimum and furnace cooled at 10°F per hour to 600°F.

(d) MIL-9018-M, MIL-10018-M and MIL-11018-M. The coupon shall be heated to 1025° + 25°F, held at this temperature for one hour and furnace cooled at 200°F per hour or slower to below 500°F.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

Table III - Mechanical properties.

Type	Ultimate tensile strength		Yield strength[1/]		Elongation[2/] percent in 2 inches		Charpy-V notch impact			
	As-welded	Stress-relieved	As-welded[3/]	Stress-relieved	As-welded	Stress relieved	As-welded		Stress-relieved	
	Psi minimum	Psi minimum	Psi	Psi minimum	Minimum	Minimum	Energy ft/lbs min avg	Temperature minus °F	Energy ft/lbs min avg	Temperature minus °F
MIL-7018	70,000	---	58,000 to 70,000	55,000	24	24	20	20	20	20
MIL-8018-C3	80,000	---	68,000 to 80,000	65,000	24	24	20	20	20	20
MIL-8018-C3SR	---	80,000	---	65,000	--	24	--	--	20	20
MIL-9018-M	90,000	---	78,000 to 90,000	75,000	24	24	20	60	20	60
MIL-10018-M	100,000	---	88,000 to 100,000	85,000	20	20	20	60	20	60
MIL-11018-M	110,000	---	98,000 to 110,000	95,000	20	20	20	60	20	60

1/ Yield strength shall be determined by offset method (offset = 0.2 percent).
2/ Percent reduction in area shall be reported for information only.
3/ The upper value of the yield strength may be 5,000 psi higher than the indicated value for the 3/32 inch size electrode.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

3.4 Chemical composition of deposited weld metal. Chemical composition of deposited weld metal shall be as specified in table IV.

Table IV - Chemical composition (percent)[1/] of deposited weld metal.[2/]

Element	MIL-7018	MIL-8018-C3 MIL-8018-C3SR	MIL-9018-M	MIL-10018-M	MIL-11018-M
Carbon	0.12	0.12	0.10	0.10	0.10
Manganese	0.40-1.25	0.40-1.25	0.60-1.25	0.75-1.70	1.30-1.80
Silicon	0.80	0.80	0.80	0.60	0.60
Phosphorus	0.030	0.030	0.030	0.030	0.030
Sulfur	0.030	0.030	0.030	0.030	0.030
Chromium	0.15	0.15	0.15	0.35	0.40
Nickel	0.25	0.80-1.10	1.40-1.80	1.40-2.10	1.25-2.50
Molybdenum	0.35	0.35	0.35	0.25-0.50	0.25-0.50
Vanadium	0.05	0.05	0.05	0.05	0.05

1/ Single values are maximum percentages.
2/ Use of the suffix RC, e.g., MIL-10018-M RC, indicates that the maximum copper content of the deposited weld metal shall be 0.15 percent. The remaining basic compositional requirements remain unchanged for the specific MIL-type.

3.5 Electrode identification. Electrodes shall be identified as specified in 3.5.10 of MIL-E-22200.

3.5.1 Heat and lot identification. When specified (see 6.2), each electrode shall be marked with heat or lot identification as specified in 3.5.10.1 of MIL-E-22200.

3.6 Electrode lengths. The specified lengths of electrodes shall be in accordance with table V, except for type MIL-8018-C3SR which may be qualification tested in longer lengths for the QPL.

Table V - Electrode lengths.

Sizes	Electrode lengths end-grip
Inch	Inches
3/32	9, 12 or 14
1/8, 5/32, 3/16	14
7/32, 1/4, 5/16	18

4. QUALITY ASSURANCE PROVISIONS

4.1 The quality assurance provisions shall be in accordance with MIL-E-22200 and as specified herein.

4.2 Qualification tests. Qualification tests shall be as specified in 4.2 of MIL-E-22200 and table X herein. Types MIL-7018, MIL-8018-C3, MIL-9018-M, MIL-10018-M and MIL-11018-M shall be tested in both the as-welded and stress-relieved conditions. Type MIL-8018-C3SR shall be tested in each of the stress-relieved conditions specified in 3.3.1(b) and (c). MIL-8018-C3SR shall be tested in the longest length intended to be used (see 3.6)

4.3 Comparison inspection. In addition to the examination and tests required in 4.5 of MIL-E-22200, tests specified in table VI shall be conducted as specified in 4.3 of MIL-L-22200, when required by the Naval Ship Engineering Center (NAVSEC).

Table VI - Comparison inspection.

Types	Sizes	Tests	Requirements
All All	All All	4.6.8 (MIL-E-22200) Weld test No. 1 (see table X herein)	3.4 and table IV herein 3.3.1 and table III herein

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection.

4.4.1 Lot.

4.4.1.1 A lot of electrodes shall be as specified in 4.4.4 and 4.4.6 of MIL-E-22200 for inspection level C for types MIL-7018 and MIL-8018-C3.

4.4.1.2 A lot of electrode shall be as specified in 4.4.3 and 4.4.6 of MIL-E-22200 for inspection level B for types MIL-9018-M, MIL-10018-M, MIL-11018-M, and MIL-12018-M.

4.4.2 Sampling for quality conformance inspection. Sampling for quality conformance inspection shall be in accordance with 4.4.7 through 4.4.8.3 of MIL-E-22200 for tests specified in MIL-E-22200 where required and as specified in 4.4.3 for quality conformance weld tests.

4.4.3 Quality conformance inspection.

4.4.3.1 Quality conformance tests shall be conducted on samples as follows:

(a) Types MIL-7018, MIL-8018-C3 and MIL-8018-C3SR. Samples shall be selected as specified in 4.4.2. One sample representing one wet mix of covering mixture in each lot shall be subjected to all the tests required by table VII (i.e., x-ray, mechanical and complete chemical analysis). Samples representing each of the remaining wet mixes of covering mixture in a lot shall be tested as specified in table VIII, to assure equivalency as required by 4.4.4.2 of MIL-E-22200.

(b) Types MIL-9018-M, MIL-10018-M, and MIL-11018-M. Samples shall be selected as specified in 4.4.2 from electrodes produced from each wet mix of covering mixture in each lot as defined in 4.4.3 of MIL-E-22200. One sample shall be subjected to all the tests specified in table VII (i.e., x-ray, mechanical and complete chemical analysis). The samples representing each of the remaining wet mixes of covering mixture in each lot shall be subjected to equivalency tests as specified in table VIII and IX.

Table VII - Quality conformance inspection.

Types	Tests	Procedures
All	Test No. 3 and 8a 1/ 2/ 3/ 4/ 5/	Table X
All	Table XI	Table XI
All	Chemical analysis 1/ 6/	Test No. 3, table X

1/ All type MIL-9018-M, MIL-10018-M, and MIL-11018-M electrodes shall be subjected to one rebaking at 800° ± 25°F for a period of one-half hour to one hour prior to testing. It should be noted that this rebaking is in addition to the initial manufacturing baking of the electrode covering. This rebaking shall be accomplished except where specifically not required by the procurement document.

2/ As-welded impact properties shall be determined only when specifically required by the procurement document for types MIL-7018, MIL-8018-C3, MIL-9018-M, MIL-10018-M and MIL-11018-M.

3/ Stress-relieved mechanical and impact properties shall be determined only when specifically required by the procurement document for types MIL-7018, MIL-8018-C3, MIL-9018-M, MIL-10018-M and MIL-11018-M

4/ Type MIL-8018-C3SR shall be tested in the stress-relieved condition only using treatment specified in 3.3.1(b) or (c) as required (see 6.2)

5/ When specified (see 6.2), types MIL-7018, MIL-9018-M, and MIL-11018-M shall have the SR suffix added to the designation, and quality conformance inspected in the stress-relieved condition only, in accordance with 3.3.1(c)

6/ Add a copper analysis for electrode types with suffix RC,

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

Table VIII - Wet mix equivalency tests.

Types	Tests	Procedures
MIL-7018, MIL-8018-C3, and MIL-8018-C3SR	1/	1/
MIL-9018-M, MIL-10018-M, MIL-11018-M	Test 8a 3/	Table X
MIL-9018-M, MIL-10018-M, MIL-11018-M	Chemical analysis 2/ 3/ 4/ 5/	Table X

1/ See 4.4.4.2 of MIL-E-22200.
2/ Required chemical analysis of the deposited weld metal is for selected elements only as specified in table IX.
3/ Equivalency chemical analysis tests are not required when the lot is as defined in 4.4.3.1(c) of MIL-E-22200.
4/ 4.6.8.1 of MIL-E-22200 may be applied.
5/ Rebaking as specified by footnote 1 to table VII is not required.

Table IX - Wet mix equivalency weld deposit chemical analysis.

	MIL-9018-M	MIL-10018-M	MIL-11018-M
Manganese	X	X	X
Chromium			
Nickel	X	X	X
Molybdenum	X	X	X

4.4.3.2 Unsatisfactory test results. If the results of the first tests are determined to be unsatisfactory, two retests shall be permitted. The results of both retests shall be satisfactory for lot acceptance.

4.5 Test procedures.

4.5.1 Weld tests. Table X summarizes the weld tests required under this specification for qualification testing of electrodes and for the inspection as specified in tables VI, VII, VIII and IX. Medium steel base material in accordance with MIL-S-22698 and ASTM A131-71 may be used for all electrode tests.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

Table X - Summary of required weld tests. 1/ 2/

Weld test No.	Type	Diameter sizes							Weld joint design procedure	Welding position 3/	Tests			Chemical	Requirements
		3/32	1/8	5/32	3/16	7/32	1/4	5/16			X-ray	Tensile 5/	Impact		
3	All	X	X	X	X	X	X	X	Figure 1 and notes	F	4/	X	X	Chemical analysis 6/	3.7.1 of MIL-E-22200 and tables III and IV herein
8a	All	X	X	X	---	---	---	---	Figure 2 and notes	V	X	---	---	---	3.7.1 of MIL-E-22200
		---	---	---	X	X	X	X		F	X 4/	---	---	---	

1/ For qualification testing of the electrodes for the QPL, all electrode types shall be tested using direct current (dc), reverse polarity (rp). In addition, MIL-7018 and MIL-8018-C3 electrode types shall be tested using alternating current (ac). For comparison inspection, when required, and quality conformance inspection, all electrode types shall be tested using dc, rp.

2/ Types MIL-9018-M, MIL-10018-1 and MIL-11018-M electrodes shall be subjected to one rebaking at 800° + 25°F for a period of one-half hour to one hour prior to testing. It should be noted that this rebaking is in addition to the initial manufacturing baking of the electrode covering.

3/ V = vertical, F = flat.

4/ When both tests (3 and 8a) are applicable, radiography of test No. 3 will satisfy the requirements for test No. 8a for class 2 and 3 electrodes. If test No. 3 is radiographed, test No. 8a may be eliminated for class 2 and 3 electrodes.

5/ Included ultimate, yield, elongation, reduction in area.

6/ May be determined from milling sample taken from ruptured ends of tensile specimens or drillings. In event of variances with composition requirements or conflicting results by testing activities, analysis shall be verified by procedures specified in 4.6.8 of MIL-E-22200.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

4.5.2 Other tests. Table XI summarizes tests, in addition to those specified in table X required for qualification testing of the electrodes for the QPL and for quality conformance inspection, as applicable.

Table XI - Summary of other tests.

Tests	Procedures	Requirements
	MIL-E-22200	
Visual and dimensional	4.6.2.3	3.10 (MIL-E-22200 and 3.6 herein)
Concentricity	4.6.2	3.5.2 (MIL-E-22200)
Dielectric strength 1/	4.6.3	3.5.4 (MIL-E-22200)
Flaking and cracking of covering 1/	4.6.4	3.5.5 (MIL-E-22200)
Covering moisture	4.6.9	3.2.1 herein
Total iron content in covering 1/	4.6.10	3.2.2 herein

1/ Required for qualification inspection only.

4.6 Certificate of test. A certificate of quality conformance of the weld tests specified in 4.4.3 (i.e., x-ray, mechanical, and chemical analysis), containing actual quantitative test and inspection results including the range of amperage employed in making the required welds for quality conformance inspection for each accepted lot, heat, and wet mix, as applicable, included in a particular shipment shall be furnished to the consignee with the shipment. The certification shall include test results from the quality conformance test and the wet mix equivalency test as applicable for the shipment and the results of all retests of the material offered for acceptance, together with the reason retest was required, when acceptance is based on any of the following provisions of FED-STD-151.

(a) Replacement of test specimens.
(b) Retest of additional specimens from the lot.
(c) Resubmittal of a rejected lot for test after rework or removal of nonconforming material.

The minimum quality conformance test result data and wet mix equivalence test result data required shall be as shown on figures 3 and 4 and shall be submitted on the forms shown.

4.7 Inspection of preparation for delivery. The packaging, packing, and marking shall be inspected for compliance with section 5 of this document.

5. PREPARATION FOR DELIVERY

(The preparation for delivery requirements specified herein apply only for direct Government procurements.)

5.1 Packaging. Packaging shall be level A or C, as specified (see 6.2).

5.1.1 Level A. All electrodes shall be packaged in class 1 unit containers in accordance with MIL-W-10430, except when specified (see 6.2), 12, 14 and 18-inch electrodes shall be supplied in class lb (50-pound) unit containers.

5.1.1.1 Special instructions. When electrodes are packaged in class is unit containers in accordance with MIL-W-10430, fiberboard or other cushioning material shall be inserted in each end of the unit container to restrict the end-wise movement of the electrodes. The cushioning materials shall be dry and in equilibrium with the electrode covering. Class 1a containers shall be of a snug fittinq design with the container length not to exceed the rod length by approximately l/2-inch.

5.1.2 Level C. Packaging shall afford protection against deterioration and physical damage during shipment from the supply source to the using activity. The packaging applied shall insure conformance to the stabililty requirements specified in 3.5.8 of MIL-E-22200.

5.2 Packing. Packing shall be level A, B, or C, as specified (see 6.2).

5.2.1 Levels A and B. Electrodes, packaged as specified (see 6.2), shall be packed level A or B in accordance with MIL-W-10430. Palletization, when required, shall be in accordance with MIL-W-10430.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

5.2.2 Level C. Electrodes, packaged as specified (see 6.2), shall be packed in containers acceptable to the common carrier and which will insure safe delivery at destination in a satisfactory condition at the lowest applicable rate. Containers, packing or method of shipment shall comply with Uniform Freight Classification Rules and Regulations or other carrier rules as applicable to the mode of transportation.

5.3 Marking. In addition to any special marking required herein or by the contract or order (see 6.2), interior packages and exterior shipping containers and palletized loads shall be marked in accordance with MIL-W-10430.

5.3.1 Special marking.

5.3.1.1 Interior packages and shipping containers. In addition to the lot identification required by 4.4.6 of MIL-E-22200, identification on interior packages shall include MIL type, size, specification number, manufacturer's or distributor's name, date of manufacture (month/year), and manufacturer's or distributor's brand or type designation. In addition, all unit packages shall be marked or labeled with the following precautionary information, as a minimum and prominently displayed:

CAUTION
Welding may produce fumes and gases hazardous to health. Avoid breathing these fumes and gases. Use adequate ventilation. See ANSI Standard Z49.1 "Safety in Welding and Cutting" published by the American Welding Society.

Significant toxic constituents when present in the electrode in greater than trace amounts shall be included in the precautionary information so that normal ventilation can be increased accordingly. These constituents include but are not limited to those itemized in section 8.5 through 8.11 of ANSI Z49.1-67.

5.3.1.2 Class 1b containers. Each class 1b container on the container end adjacent to the electrode grip end shall be marked "OPEN THIS END".

6. NOTES

6.1 Intended use. This specificatoon is intended to cover several low-hydrogen types of arc-welding electrodes of various alloys and strength levels, capable of depositing weld metal, that in the as-welded or stress-relieved conditions meet mechanical-property requirements given herein. It will be noted that, although these electrodes may be used for some applications in the as-welded condition, they are capable of stress relief as required. Properties may be affected by long time stress-reilieving and slow cooling from stress–relieving temperature. Properties should be determined to be satisfactory after a simulated production postweld heat treatment by the user when required by the fabrication document. The designation, low-hydrogen, is applied to electrodes having coverings that are substantially free of any compound that may liberate hydrogen in the arc. Low alloy steel electrodes that produce low-hydrogen in the arc have been found suitable for welding many steels that formerly gave serious difficulty through excessive porosity and underbead cracking, unless welded with high-alloy electrodes.

6.1.1 Type MIL-7018. This type is intended to cover medium steel electrodes used in welding mild, medium or high-tensile steels such as grade HT of MIL-S-16113 and MIL-S-22698.

6.1.2 Type MIL-8018-C3. This type is intended to cover low-alloy electrodes capable of depositing weld metal of higher strength than type MIL-7018.

6.1.3 Type MIL-8018-C3SR. This type is intended to cover a special MIL-type electrode formulated to meet the long time (50-hours) stress-relieved mechanical properties requirements only.

6.1.4 Type MIL-9018-M. This type is intended to cover low-alloy electrodes suitable for welding steels having properties similar to those of the weld, and for welding attachments to HY-90 steel, as may be permitted. This electrode is intended to be used with the dc, rp electrical characteristics only.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

6.1.5 Type MIL-10018-M. This type is intended to cover low-alloy electrodes for welding low-alloy, high-yield, notch-tough steel such as grade HY-80 of MIL-S-16216. This electrode is intended to be used with dc, rp electrical characteristics only.

6.1.6 Type MIL-11018-M. This type is intended to cover low-alloy electrodes for welding groove butt joints in HY-80 and T-1 steels. This electrode is intended to be used with dc, rp electrical characteristics only.

6.1.7 All types with suffix RC. This type is intended to cover electrodes for welding pressure and strength welds which will be subject to irradiation.

6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number and date of this specification.
(b) Type, class and size required (see 1.2).
(c) Whether the copper content is restricted as designated by the suffix RC to the MIL-type (see 3.4).
(d) Whether electrode identification shall include heat or lot identification (see 3.5.1).
(e) For MIL-8018-C3SR, the length required (see 3.6) .
(f) For 3/32-inch size electrode, the length required (see table V).
(g) If rebaking of types MIL-9018-M, MIL-10018-M, and MIL-11018-M is not required for quality conformance inspection (see table VII, footnote 1).
(h) Whether quality conformance impact tests are required (see table VII, footnote 2).
(i) Whether stress-relieved quality conformance inspection are required (see table VII, footnote 3).
(j) For MIL-8018-C3SR, the stress-relieved condition required for quality conformance inspection (see table VII, footnote 4).
(k) Whether types MIL-7018, MIL-9018-M, MIL-10018-M, or MIL-11018-M are to be quality conformance inspected in the stress-relieved condition for the 50-hour holding time (see table VII, footnote 5).
(l) Levels of packaging and packing required (see 5.1 and 5.2).
(m) When 12, 14 and 18-inch electrodes are required in class 1b containers (see 5.1.1).
(n) Special marking required (see 5.3).

6.2.1 Electrodes should be ordered by the pound.


6.3 Inspection after delivery. Post delivery inspection of electrodes to determine conformity to this specification and for acceptance thereof is the responsibility of the consignee.

6.4 THE MARGINS OF THIS SPECIFICATION ARE MARKED "#" TO INDICATE WHERE CHANGES (ADDITIONS, MODIFICTIONS, CORRECTIONS, DELETIONS) FROM THE PREVIOUS ISSUE HAVE BEEN MADE. THIS WAS DONE AS A CONVENIENCE ONLY AND THE GOVERNMENT ASSUMES NO LIABILITY WHATSOEVER FOR ANY INACCURACIES IN THESE NOTATIONS. BIDDERS AND CONTRACTORS ARE CAUTIONED TO EVALUATE THE REQUIREMENTS OF THIS DOCUMENT BASED ON THE ENTIRE CONTENT IRRESPECTIVE OF THE MARGINAL NOTATIONS AND RELATIONSHIP TO THE LAST PREVIOUS ISSUE.

Custodians:
Army - WC
Navy - SH
Air Force - 84
Review activities:
Army - MR, MC, WC
Navy - SH, YD
Air Force - 84
User activities:
Army - AT
Navy - MC, OS


Preparing activity:
Navy - SH
(Project 3439-0213)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

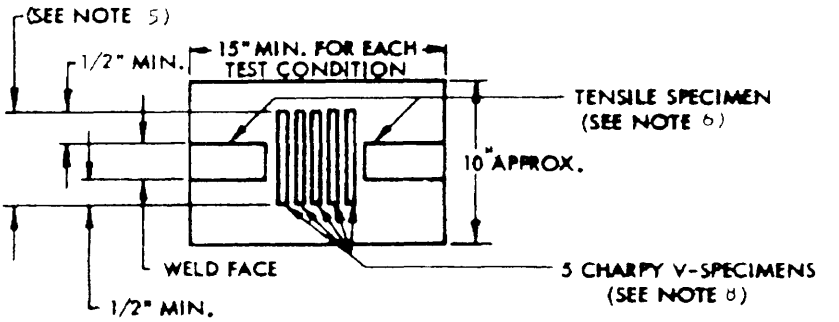

LAYOUT OF TEST PLATE


NOTE: LENGTH MAY BE DECREASED ACCORDINGLY WHERE IMPACTS OR STRESS RELIEVED SAMPLES ARE NOT REQUIRED. WHERE IMPACTS IN THE AS-WELDED AND STRESS-RELIEVED CONDITION BOTH ARE REQUIRED, THE LENGTH MAY BE INCREASED ACCORDINGLY

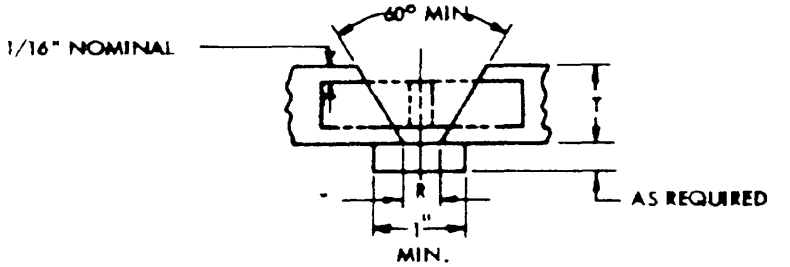

GROOVE PREPARATION OF TEST PLATE

SHOWING ORIENTATION OF CHARPY-V TEST SPECIMEN

SH 8985

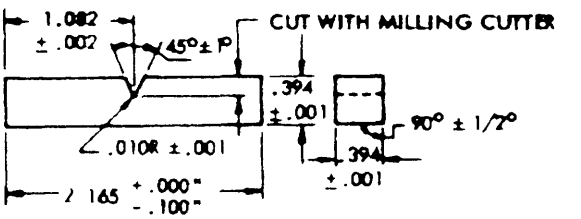

CUT NOTCH WITH MILLING CUTTER. MAKE FOUR CUTS PER NOTCH IN FOLLOWING ORDER a) .040, b) .025, c) .010, d) .004 NO IRREGULARITIES IN CONTOUR OF APEX OF NOTCH. NO. 8 POLISH MICRO-INCH FINISH.

Source: https://assist.dla.mil -- Downloaded: 202640-19T11:21Z
Check the source to verify that this is the current version before use.

Notes to figure 1:


1. Base metal shall be l s specified in 4.5.1.
2. Types MIL-9018-M, MIL-10018-M and MIL-11018-M electrodes shall be qualification tested for the OPL and quality conformance tested after rebaking in accordance with the procedure outlined in footnote 1 to table VII unless specifically exempted by the procurement document.
3. Welds shall be deposited in layers using a 2-1/2 core wire diameter maximum weave build-up sequence. Record and report as specified in table XII. Layers should be approximately l/8-inch thick, and shall be deposited in such a manner that the final layers include a reinforcement of standard proportions (1/32-inch to l/8-inch). Welding currents shall be in accordance with the manufacturer's recommendations and the actual values used shall be recorded and reported. Each layer shall be started at the finishing end of the preceding layer.
4. After the joint has been tacked, the assembly shall be heated to 225° + 25°F prior to welding. After completion of each pass the assembly shall be allowed to cool in still air at room temperature and the subsequent pass shall be started when the temperature of the plate has dropped to 225° + 25°F. If it is necessary to interrupt this procedure, the assembly shall be preheated to 225° + 25°F.
5. The weld shall be cut as shown resulting in two tensile coupons suitable for 0.505-inch diameter specimens (or 0.252-inch diameter specimens when testing 3/32-inch and 1/8-inch size electrodes) and a center coupon of size sufflcient for the required charpy v-notch specimens. No base metal shall be removed within 1/2-inch of the edges of the face of the weld by flame cutting. Only sawing or machining shall be used for specimen finishing.
6. One tensile coupon, where required, shall be stress-relieved in accordance with 3.3.1 herein.
7. Both the stress-relieved and as-welded coupons, when required, shall be machined into 0.505-inch tensile specimens (or 0.252-inch diameter specimens when testing 3/32-inch and 1/8-inch size electrodes). For details sea MIL-STD-418.
8. The center section of the welded joint shall be used for the preparation of charpy v-notch impact specimens. The charpy v-notch specimens shall be machined in accordance with details shown on figure 1. Prior to machining specimens, where required, the coupon shall be stress-relieved in accordance with 3.3.1 herein.
9. Impact properties for the five specimens for each test condition shall be obtained at test temperatures specified in table III herein, plus or minus 3°F. The extreme lowest impact value thus obtained together with the extreme highest value my be disregarded for this test. Two of the three remaining values shall be greater than the specified 20 foot/pound energy level, one of the three may be lower but shall be not less than 15 foot/pounds: the computed averaqe value of these three shall be greater than the specified 20 foot/pound level (see table III herein).

Table XII - Groove weld preparation.

Electrode size	Minimum thickness (T)	Maximum root opening (R)	Number of layers 1/	
			Minimum	Maximum
(Inch)	(Inches)	(Inch)		
3/32	1/2	1/4	1/	1/
1/8	1/2	1/4	1/	1/
5/32	3/4	1/2	7	9
3/16	3/4	1/2	7	9
7/32	3/4	1/2	7	8
1/4	1	1/2	9	11
5/16	1-1/4	1/2	11	12

1/ Pass and layer sequence shall be reported.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

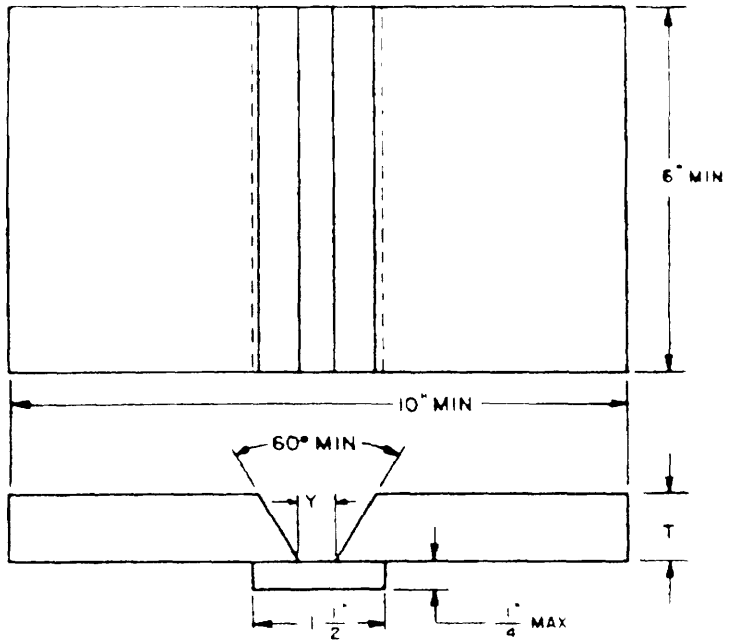

SH 7724A

Electrode size	3/32 (Inch)	1/8 (Inch)	5/32 (Inch)	3/16-5/16 (Inch)
Thickness (T) 1/	1/4	3/8	1 2	1/2
Root opening (Y) 2/	1/4	5/16	3/8	1/2
Weld bead width (max)	3/8	1/2	5/8	3/4

1/ Minimum.
2/ Tolerance ± 1/16-inch.

Figure 2 - Groove weld usability test (test 8a).

Notes to figure 2:

1. Welding shall be accomplished with the test plate in the vertical or flat position as specified in table X. Welding current shall be in accordance with the manufacturer's recommendations and the actual values shall be recorded and reported. Unless otherwise specified by the procurement document, test shall be done with dc only.
2. base metal shall be in accordance with 4.5.1 herein.
3. The edge preparation shall be flame cut and ground to remove slag and surface irregularities.
4. Welds shall be deposited in approximately 1/8-inch thick layers. Weld bead widths shall be as shown above. Each bead shall contain a start in the area to be evaluated.
5. The reinforcement shall be 3/16-inch maximum.
6. Preheat and interpass temperature shall be to 225° ± 25°F.
7. After completion of the weld, the weld reinforcement and backing strips shall be removed flush with the base plate on both surfaces and the assembly shall be x-rayed in accordance with MIL-STD-271.
8. The radiograph shall meet the x-ray standards of [illegible] as specified in 3.7.1 of MIL-E-22200.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

CERTIFICATION OF QUALITY CONFORMANCE TESTS

Manufacturer or Distributor _____ Customer's Name _____

Address _____

Date _____ Customer's Order No. _____

Specification MIL- _____

Type MIL- _____ Core Wire Heat No. _____

Diameter & Legnth _____ Lot Identification MIL-E-22200 Para. _____

Inspection Level _____

Lot No. _____ Wet Batch No. _____ _____

Chemical Analysis (Complete)

Carbon _____

Manganese _____

Silicon _____

Phosphorus _____

Sulfur _____

Chromium _____

Nickel _____

Molybdenum _____

Vanadium _____

Copper _____

Mechanical Tests

	As-welded	Stress-relieved
Yield Strength (0.2% offset method)		
Tensile Strength		
Elongation (%)		
Reduction of Area (%)		
CHARPY IMPACTS		
1.		
2.		
3.		
4.		
5.		

Chemistry was taken from: [ ] Chem Pad [ ] Groove Weld

X-Ray Results _____

Concentricity (%) _____

Covering Moisture _____

Grinding During 8a Test Plate Preparation (see note 3)

Groove Weld Test

Test No.	3	8a	Chem Pad
Amperage			

Operator Error (Layer Nos.) _____

We hereby certify that the above material has been tested in accordance with the listed specification and is in conformance with all requirements.

_____

NOTES:

1. Items not applicable to the type electrode involved or exempted by the procurement document shall be marked N/A.
2. This form is applicable to the quality conformance tests required for each lot. Figure 4 forms shall be employed to report and certify the wet mix equivalency tests where applicable for each wet mix of covering mixture in the lot. One copy of the figure 4 form shall be employed for certifying equivalency of each wet mix in a lot where applicable. One copy of the quality conformance certificate (figure 3) for the lot l mali be forwarded with copies of the batch equivalency certificates for each additional mix from that lot that is included in the shipment.
3. See paragraphs 3.5.7 and 3.9 of MIL-E-22200.
4. Copper content is required for MIL types with suffix

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

CERTIFICATION OF WET MIX EQUIVALENCY TESTS

Manufacturer or Distributor _____ Customer's Name _____

Address _____

Date _____ Customer's Order No. _____

Specification MIL- _____

Type MIL- _____

Diameter Size _____ Core Wire Heat No. _____

Lot No. _____ Wet Batch No. _____

Sampling Chemical Analysis

Manganese _____

Silicon _____

Chromium _____

Nickel _____

Molybdenum _____

Copper _____

X-Ray Results _____

Chemistry was taken from:

☐ Chem Pad ☐ Groove Weld

Test No. _____

Chem Pad 8a

Amperage _____ _____ _____

We hereby certify that the above material has been tested in accordance with the listed specification and in conformance with all requirements.

_____

NOTES:

1. Items not applicable to the type electrode involved or exempted by the procurement document shall be marked N/A.
2. One copy of the figure 4 form shall be employed for certifying equivalency of each wet mix in a lot where applicable. One copy of the quality conformance certificate (Figure 3) for the lot shall be forwarded with copies of the mix equivalency certificates for each additional mix from that lot that is included in the shipment.
3. Copper content is required for MIL-types with R suffix.

Figure 4

Source: https://assist.dla.mil -- Downloaded: 202610-19T11:21Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form submitting comments and suggestions for improvements. All users of military standardization documents are invited suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STA* mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpre too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviat problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled ou acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are considered.

NOTE. This form may not be used to request copies of documents, nor to request waivers, deviations, or clarificati specification requirements on current contracts. Comments submitted on this form do not constitute or imply autho to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commander
Naval Ship Engineering Center
Center Building-Sec 61247
Prince George's Center
Hyattsville, MD 20782

Source: https://assist.dla.mil -- Downloaded: 202610-19T11:21Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions — Reverse Side)

1 DOCUMENT NUMBER	2 DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4 TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)* _____
3b. ADDRESS *(Street, City, State, ZIP Code)*	

5 PROBLEM AREAS

a. Paragraph Number and Wording

b. Recommended Wording

c. Reason/Rationale for Recommendation

6 REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* — Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* — Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* — Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:21Z
Check the source to verify that this is the current version before use.