INCH-POUND
MIL-DTL-22200/8C
w/AMENDMENT 1
19 March 2026
SUPERSEDING
MIL-DTL-22200/8C
14 February 2025

DETAIL SPECIFICATION SHEET

ELECTRODES, WELDING, COVERED, LOW-HYDROGEN, AND IRON-POWDER, LOW-HYDROGEN, CHROMIUM-MOLYBDENUM ALLOY STEEL, AND CORROSION RESISTING STEEL

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The requirements for acquiring the product described herein shall consist of this specification sheet and MIL-DTL-22200.

1. SCOPE

1.1 Scope. This specification covers low-hydrogen and iron-powder low-hydrogen electrodes for welding chromium-molybdenum alloy steels and corrosion resisting steels used for corrosion resistance in certain media, such as petroleum crudes, and for high-temperature strength and resistance to creep.

1.2 Classification. Electrodes are furnished in the types, classes, and sizes shown in table I, as specified (see 6.2).

TABLE I. Types, classes, positions of welding, and sizes. 1/, 2/

Type	Class	Positions of welding	Sizes (diameter, inch)
MIL-7015-B2L MIL-7018-B2L	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-8015-B2 MIL-8016-B2 MIL-8018-B2	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-8015-B3L MIL-8018-B3L	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-9015-B3 MIL-9016-B3 MIL-9018-B3	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4

Comments, suggestions, or questions on this document should be addressed to Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard, DC 20376-5160 or emailed to CommandStandards@navy.mil, with the subject line "Document Comment". Since contact information can change, you may want to verify the currency of this address information using ASSIST at https://assist.dla.mil.

AMSC N/A FSC 3439

Distribution Statement A. Approved for public release: distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

TABLE I. Types, classes, positions of welding, and sizes – Continued. 1/, 2/

Type	Class	Positions of welding	Sizes (diameter, inch)
MIL-410-15 MIL-410-16	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-502-15 MIL-502-16	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-502-15-L MIL-502-16-L	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4
MIL-505-15 MIL-505-16	1	All	3/32, 1/8, 5/32
	2	Horizontal fillets and flat	3/16, 7/32, 1/4

NOTES:

1/ Type classification of electrodes will be determined according to the capability of the electrode to meet the tests specified herein, when used in the positions of welding specified in this table and in section 4. An electrode will be approved under one type of classification; an electrode will not be approved if it differs in type from that stated in the manufacturer's request for test. The position description indicates the maximum size qualified under this specification. However, reference should be made to the qualified products list (QPL) for the selection of electrodes for all positions of welding.

2/ See 6.4.

2. APPLICABLE PUBLICATIONS

2.1 General. The publications listed in this section are specified in sections 3 and 4 of this specification. This section does not include publications cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of publications cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government publications.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these publications are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-DTL-22200 - Electrodes, Welding, Covered: General Specification for

MIL-S-22698 - Steel Plate, Shapes and Bars, Weldable Ordinary Strength and Higher Strength: Structural

(Copies of these publications are available online at https://quicksearch.dla.mil.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

2.3 Non-Government publications. The following publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these publications are those cited in the solicitation or contract.

AMERICAN WELDING SOCIETY (AWS)

AWS A5.5/A5.5M - Specification for Low-Alloy Steel Electrodes for Shielded Metal Arc Welding

(Copies of this publication are available online at www.aws.org.)

ASTM INTERNATIONAL

ASTM A131/A131M - Standard Specification for Structural Steel for Ships

(Copies of this publication are available online at www.astm.org.)

2.4 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. Electrodes furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified products list before contract award (see 4.2 and 6.3).

3.2 Electrodes. Electrodes furnished under this specification shall be in accordance with the requirements of MIL-DTL-22200 and as specified herein.

3.3 Core wire composition. The core wire composition is at the manufacturer's discretion.

3.4 Covering composition. Except as specified in 3.4.1 and 3.4.2, and subject to the requirements of MIL-DTL-22200, the chemical composition of the electrode covering is at the manufacturer's discretion.

3.4.1 Covering moisture. The covering moisture of each electrode covering shall not exceed the percent by weight values specified in table II.

TABLE II. Covering moisture.

Type	Covering moisture, maximum (wt. %)	
	Condition A 1/	Condition B 2/, 3/
MIL-70XX	0.15	0.25
MIL-80XX	0.15	0.25
MIL-90XX	0.15	0.25
MIL-410-XX	0.60	---
MIL-502-XX	0.60	---
MIL-505-XX	0.60	---

NOTES:

1/ Condition A – When removed from the manufacturer's sealed container.

2/ Condition B – After 9 hours (minus 0, plus 30 minutes) of exposure at 80 percent relative humidity and 80 °F as specified in 4.4.2.

3/ For receipt inspection by the contracting activity, the maximum water content shall be not greater than 0.29 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

3.4.2 Total iron content. The total iron content of the covering of MIL-XX18 type electrodes, including any combined iron in addition to metallic iron powder, shall be not less than 15 percent.

3.5 Groove welds.

3.5.1 Mechanical properties of deposited weld metal. The as-welded and stress-relieved mechanical properties of weld metal deposited in groove joints shall be as specified in table III (see table VII, notes 3, 4, 7, and 8).

TABLE III. Mechanical properties of deposited weld metal.

Type	Ultimate tensile strength		Yield strength [1/]		Elongation in 2 inches		CVN impact
	As-welded (psi) (minimum)	Stress-relieved (psi) (minimum)	As-welded (psi) (minimum)	Stress-relieved (psi) (minimum)	As-welded (percent) (minimum)	Stress-relieved (percent) (minimum)	
MIL-7015-B2L	---	75,000	---	57,000	---	19	[2/]
MIL-7018-B2L	80,000	75,000	67,000	57,000	19	19	[2/]
MIL-8015-B2 MIL-8016-B2 MIL-8018-B2	---	80,000	---	67,000	---	19	[2/]
MIL-8015-B3L	---	80,000	---	67,000	---	17	[2/]
MIL-8018-B3L	90,000	80,000	77,000	67,000	17	17	[2/]
MIL-9015-B3 MIL-9016-B3 MIL-9018-B3	---	90,000	---	77,000	---	17	[2/]
MIL-410-15 MIL-410-16 MIL-502-15 MIL-502-16 MIL-505-15 MIL-505-16	---	75,000	---	50,000	---	20	[2/]
MIL-502-15-L MIL-502-16-L	75,000	70,000	50,000	45,000	17	22	[2/]

NOTES:

[1/] The yield strength shall be determined by the offset method (offset = 0.2 percent).

[2/] CVN impact values and test temperatures shall be as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

3.5.2 Chemical composition of deposited weld metal. Chemical composition of deposited weld metal shall be as specified in table IV.

TABLE IV. Chemical composition of deposited weld metal.

Type	Carbon	Manganese	Phosphorous	Sulfur	Silicon	Chromium	Molybdenum
	Percentage (single values are maximum)						
MIL-7015-B2L MIL-7018-B2L	0.05	0.90	0.03	0.03	1.00 0.80	1.00-1.50	0.40-0.65
MIL-8015-B2 MIL-8016-B2 MIL-8018-B2	0.05-0.12	0.90	0.03	0.03	0.60 0.60 0.80	1.00-1.50	0.40-0.65
MIL-8015-B3L MIL-8018-B3L	0.05	0.90	0.03	0.03	1.00 0.80	2.00-2.50	0.90-1.20
MIL-9015-B3 MIL-9016-B3 MIL-9018-B3	0.05-0.12	0.90	0.03	0.03	0.60 0.60 0.80	2.00-2.50	0.90-1.20
MIL-410-15 MIL-410-16	0.10	1.00	0.04	0.03	0.90	11.00-13.50	---
MIL-502-15 MIL-502-16	0.10	1.00	0.04	0.03	0.90	4.00-6.00	0.45-0.65
MIL-502-15-L MIL-502-16-L	0.05	1.00	0.04	0.03	0.90	4.00-6.00	0.45-0.65
MIL-505-15 MIL-505-16	0.10	1.00	0.04	0.03	0.60	8.50-10.50	1.00-1.50

3.6 Electrode lengths. The nominal lengths of electrodes specified (see 6.2) shall be as specified in table V.

TABLE V. Electrode lengths.

Size (inch)	Electrode lengths (inches)
3/32	9, 12, or 14
1/8, 5/32	9 or 14
3/16	14
7/32, 1/4	18

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2 and table VI).

b. Conformance inspection (see 4.3 and table VI).

4.2 Qualification inspection. Qualification inspection shall include the examinations and tests in MIL-DTL-22200 and the additional tests in table VI herein.

TABLE VI. Required additional tests for qualification and conformance inspections. 1/

Tests	Procedures	Requirements	Qualification	Conformance
Covering moisture	MIL-DTL-22200 and 4.4.2 herein	3.4.1 herein	X 2/	X 2/
Total iron content in covering	MIL-DTL-22200	3.4.2 herein	X	---
Alloy identity	MIL-DTL-22200	MIL-DTL-22200	X	X
Groove weld tests	See table VII		X	X

NOTES:

1/ See 4.2 and 4.3 for additional requirements.

2/ Condition B of table II is required for qualification inspection. Condition A of table II is required for conformance inspection.

4.3 Conformance inspection. Conformance inspection shall include the examinations and tests in MIL-DTL-22200 and the additional tests in table VI herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

TABLE VII. Groove weld tests required for qualification and conformance inspections. [1/]

Weld test assembly	Electrode type	Diameter sizes						Welding position	Tests [2/, 3/, 4/]				Test procedures	Requirements
		3/32	1/8	5/32	3/16	7/32	1/4		RT [5/]	Tensile [6/]	Chemical analysis	CVN impact		
3 (Figure 1)	All types [7/]	X	X	X	X	X	X	Flat	X	X	X	[8/]	MIL-DTL-22200	Table III herein for tensile and impact. Table IV herein for chemical.
8a (Figure 2)	All types [7/]	X	X	X	--	--	--	Vertical	X	---	---	---	MIL-DTL-22200	MIL-DTL-22200

NOTES:

1/ For qualification testing of the electrodes for the QPL, all electrode types shall be tested using direct current, electrode positive (DCEP). In addition, MIL-XX16 and MIL-XX18 electrode types shall be tested using alternating current (AC). For conformance inspection, all electrode types shall be tested using DCEP.

2/ See table X for the preheat, interpass, and postheat treatment required for the weld tests.

3/ For types 7018-B2L, 8018-B3L, 502-15-L, and 502-16-L, the as-welded and stress-relieved tensile properties shall be determined for qualification inspection. The stress-relieved tensile properties shall be determined for conformance inspection. The as-welded tensile properties shall be determined for conformance inspection when specified (see 6.2 and table III).

4/ For electrode types not covered in note 3 of this table, the stress-relieved tensile properties shall be determined for qualification and conformance inspection (see table III).


5/ "RT" is Radiographic Testing.

6/ Includes ultimate, yield, elongation, and reduction in area (for information only).


7/ Types MIL-90XX-B3 and MIL-80XX-B3L electrodes shall be subjected to one rebaking at 800±25 °F for a period of 30 to 60 minutes prior to testing. It should be noted that this rebaking is in addition to the initial manufacturing baking of the electrode covering. Unless otherwise specified (see 6.2), this rebaking shall be accomplished.

8/ Impact properties are not required for qualification. CVN impact testing shall be as specified (see 6.2 and table III).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

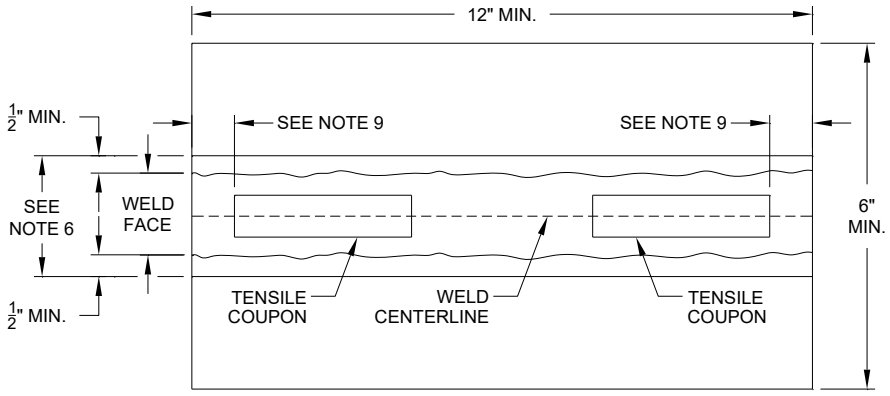

LAYOUT OF TEST PLATE

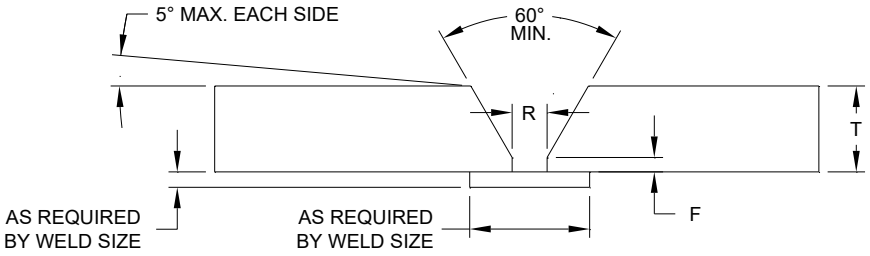

NOTES:

1. Base plate material shall be as specified in 4.4.1. See table VIII for required weld joint dimensions.
2. Welds shall be deposited in the flat position using DCEP and AC in accordance with table VII, note 1. Welding parameters shall be as specified in the manufacturer's weld procedure. The root weld layer may be deposited with ⅛-inch-diameter electrodes when testing 3⁄16-inch-diameter and larger electrodes, provided both electrodes have the same manufacturer's designation. Welds shall be deposited in approximately ⅛-inch-thick layers. The weld bead layers shall be deposited with a maximum weave width (electrode manipulation) of 2½ times the core wire diameter. The final layer shall include a reinforcement of standard proportions (1⁄32 to ⅛ inch). Each layer shall be started at the finishing end of the preceding layer. The pass and layer sequence shall be recorded, as specified in table VIII.
3. After the joint has been tacked, the assembly shall be preheated as specified in table X. After completion of each layer, the assembly shall be allowed to cool in still air at room temperature and the subsequent layer shall be started where the temperature of the plate has dropped to the interpass temperature specified in table X. If it is necessary to interrupt this procedure, the assembly shall be slow cooled and preheated again.
4. Weld pickup (i.e., welding performed prior to formal nondestructive inspection to correct minor visual surface irregularities, such as low areas in the weld reinforcement, weld bead roll, and a start-stop area) and minor repair (e.g., shallow lack of fusion against backing bar) may be accomplished on the weld face (before or after flush grinding or machining) and on the backside after backing bar removal, provided that the same electrode being tested is used in conjunction with the same welding conditions, welding position, and other controls used in the original welding of the test assembly.

FIGURE 1. Test plate layout and weld joint configuration for all-weld metal tension test (see weld test no. 3 of table VII).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

NOTES (continued):

5. The weld reinforcement and the backing shall be removed flush with the base plate surfaces prior to RT. RT of the assembly shall be done after stress relief (when required by table VII, notes 3 and 4) and prior to test coupon removal and shall be in accordance with MIL-DTL-22200. Radiographs shall meet the acceptance standards of MIL-DTL-22200.
6. Stress-relief, when required, shall be done in an electric furnace and as specified in table X and notes thereto.
7. The test weldment shall then be cut as shown for the removal of tensile coupons. No base plate material shall be removed within ½inch of the edge of the face of the weld by flame cutting. Only sawing or machining shall be used within ½inch of the weld.
8. The as-welded and stress-relieved tensile coupons shall be machined into one all-weld metal tensile specimen for each condition specified in table VII (as-welded and stress-relieved). The tensile coupon shall be etched, when necessary, to establish the location of the weld. The 0.500-inch-diameter specimens shall be machined from ¾-inch-thick coupons and 0.350-inch-diameter specimens from ½-inch-thick coupons and in accordance with MIL-DTL-22200. The specimens shall be tested for conformance with table III.
9. Specimen shall not be removed within ¾ inch of the end of the test assembly.

FIGURE 1. Test plate layout and weld joint configuration for all-weld metal tension test number 3 (see table VIII) – Continued.


TABLE VIII. Groove weld preparation (see figure 1).

Electrode size (inch)	Minimum thickness (T) (inch)	Minimum root opening (R) (inch)	Root face (F) (inch)	Number of layers	
				Minimum	Maximum
3/32	½	¼	0 to 1/32	1/	1/
⅛	½	¼	0 to 1/32	1/	1/
5/32	¾	½	0 to 1/32	7	9
3/16	¾	½	0 to 1/32	7	9
7/32	¾	½	0 to 1/32	7	8
¼	¾	½	0 to 1/32	9	11

NOTE:

1/ Number of layers shall be recorded.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

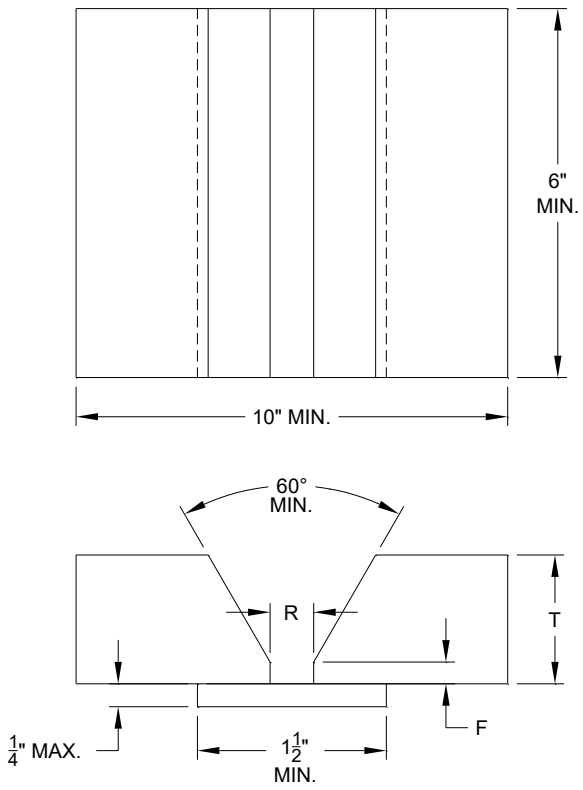

NOTES:

1. Welding shall be accomplished with the test plate in the vertical or flat position as specified in table VII. DCEP and AC shall be used in accordance with table VII, note 1. Welding parameters shall be as specified in the manufacturer's weld procedure.
2. Base metal shall be in accordance with 4.4.1. See table IX for required weld joint dimensions.
3. The edge preparation shall be flame cut and ground to remove slag and surface irregularities.
4. Welds shall be deposited in approximately ⅛-inch-thick layers. Weld bead widths shall be as shown above. Each bead shall contain a start in the area to be evaluated.
5. The reinforcement shall be a maximum of 3⁄16 inch.
6. Preheat and interpass temperature shall be as specified in table X.
7. After completion of the weld, reinforcement and backing strips shall be removed flush with the base plate on both surfaces and the assembly shall be RT inspected in accordance with MIL-DTL-22200.
8. Radiographs shall meet the acceptance criteria of MIL-DTL-22200.

FIGURE 2. Groove weld usability number 8a (see table IX).

TABLE IX. Weld joint dimensions for groove weld usability test number 8a (see figure 2).

Electrode size	3⁄32 (inch)	1⁄8 (inch)	5⁄32 (inch)
Root opening (R)	3⁄16 to 5⁄16	1⁄4 to 3⁄8	5⁄16 to 7⁄16
Thickness (T) (minimum)	3⁄16 to 5⁄16	5⁄16 to 7⁄16	7⁄16 to 9⁄16
Weld bead width (maximum)	5⁄16 to 7⁄16	7⁄16 to 9⁄16	9⁄16 to 11⁄16
Root face (F) (maximum)	1⁄32	1⁄32	1⁄32

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

TABLE X. Required preheat, interpass, and post weld heat treatment for weld tests.

Type	Preheat and interpass temperatures (°F)				Post weld heat treatment temperature (°F) 1/
	¾-inch thickness and under		Over ¾-inch thickness		
	Minimum	Maximum	Minimum	Maximum	
MIL-70XX-B2L MIL-80XX-B2 MIL-80XX-B3L MIL-90XX-B3	325	375	325	375	1275±25
MIL-410-XX MIL-502-XX MIL-502-XX-L MIL-505-XX	400	---	500	---	1375±25

NOTE:

1/ For postweld heat treatment, the holding time at temperature shall be 1 hour per inch of thickness. For thicknesses less than 1 inch, the holding time shall be proportional to the thickness but not less than 30 minutes. The maximum rate of raising or lowering the temperature shall be 200 °F per hour.

4.3.1 Lot. A lot of electrodes shall be in accordance with MIL-DTL-22200 for AWS classification C3.

4.3.2 Certification of conformance. A certificate of conformance shall be in accordance with MIL-DTL-22200.

4.4 Test procedures.

4.4.1 Weld joint base plate material. The weld joint base plate material shall be medium steel conforming to MIL-S-22698 or ASTM A131/A131M, with the fusion faces of the groove and backing strip buttered with a layer of weld metal. The buttering shall be deposited with the type of electrodes being tested. The buttering thickness shall be a minimum of 3/16 inch. The buttered surfaces shall be machined or ground reasonably smooth before assembly of the test plate. When available, base plate materials having the same chemical composition as the deposited weld metal of the electrode being tested can be substituted for the buttered plates.

4.4.2 Temperature and humidity environmental exposure procedures. The electrode sample shall be exposed to elevated temperature and humidity conditions in accordance with exposure procedures specified in AWS A5.5/A5.5M. At the end of the exposure time, the electrodes shall be removed from the chamber and tested for covering moisture content in accordance with MIL-DTL-22200.

4.5 Inspection of packaging and marking. Inspection of packaging and marking shall be in accordance with MIL-DTL-22200.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful but is not mandatory.)

6.1 Intended use. The electrode products herein are several types of low-hydrogen arc welding electrodes of various alloys for elevated temperature service and for corrosion resistance. The designation "low-hydrogen" applies to electrodes having coverings that are substantially free of any compound that may liberate hydrogen in the arc. This specification contains requirements above and beyond those of commercial specifications for use in critical military applications. The intended use of each type is as specified in 6.1.1 through 6.1.7. Current stock of electrode types specified in this specification may be used until depleted; future requisitions for electrode types specified in this specification should refer to the current version of this specification.

6.1.1 MIL-70XX-B2. This type is intended for welding 1¼ percent chromium, ½ percent molybdenum steel in high-temperature service up to 950 °F, but with lower strength than MIL-80XX-B2L (see 6.4).

6.1.2 MIL-80XX-B2. This type is intended for welding 1¼ percent chromium, ½ percent molybdenum steel in high-temperature service up to 950 °F (see 6.4).

6.1.3 MIL-90XX-B3. This type is intended for the welding of 2¼ percent chromium, 1 percent molybdenum steel in high-temperature service up to 1,050 °F involving moderate conditions of corrosion or oxidation (see 6.4).

6.1.4 MIL-410-XX. This type is intended for the welding of 12 percent chromium steel in service up to 1,300 °F where very good resistance to corrosion and oxidation is required. Where strength is a factor, it is seldom used above 1200 °F.

6.1.5 MIL-502-XX. This type is intended for the welding of 5 percent chromium, ½ percent molybdenum steel in high-temperature service up to 1,200 °F involving severe corrosive or oxidizing conditions.

6.1.6 MIL-505-XX. This type is intended for the welding of 9 percent chromium, 1¼ percent molybdenum steel in high-temperature service up to 1,300 °F involving severe corrosive and oxidizing conditions. This alloy has good oxidation resistance up to 1,500 °F.

6.1.7 Low-carbon type. The L type electrode is intended for use in welding materials of the same composition as the respective higher carbon type that is used. L types may be used where preheat and interpass temperature control is impractical, where the base material is 1 inch thick or less. The L types may also be used on heavier than 1-inch base material with preheat and interpass temperature control 100 °F to 200 °F below that required for the respective higher carbon types. The L types may also be used on base material less than 1 inch in thickness when postheat is impractical.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of the specification.
b. Type, class, and size required (see 1.2).
c. Whether CVN impacts are required (see table III, note 2 and table VII, note 8).
d. For 3/32-, 1/8-, and 5/32-inch size electrodes, the length required (see 3.6).
e. Whether as-welded tensile properties are required for conformance inspection (see table VII, note 3).
f. If rebaking is not required for conformance inspection (see table VII, note 7).
g. Packaging requirements (see 5.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Products List QPL No. 22200 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Commander, Naval Sea Systems Command, ATTN: SEA 05S, 1333 Isaac Hull Avenue, SE, Stop 5160, Washington Navy Yard, DC 20376-5160 or emailed to CommandStandards@navy.mil. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

6.4 Changes to electrode type designations for low carbon electrode types. The naming conventions of the low carbon electrode types (i.e., B2L, B3L) in this specification sheet have been changed to match that of AWS specifications as compared to MIL-E-22200/8B. Electrode types formerly listed in MIL-E-22200/8B as MIL-8015-B2L, MIL-8018-B2L, MIL-9015-B3L, and MIL-9018-B3L have been modified to MIL-7015-B2L, MIL-7018-B2L, MIL-8015-B3L, and MIL-8018-B3L, respectively. These electrode types with the modified designations also have modified mechanical properties in table III and chemical compositions in table IV relative to MIL-E-22200/8B.

6.5 Subject term (key word) listing.

Shielded metal arc welding
MIL-410-15
MIL-410-16
MIL-502-15
MIL-502-16
MIL-8015-B2
MIL-8015-B2L
MIL-8016-B2
MIL-8018-B2
MIL-8018-B2L
MIL-9015-B3
MIL-9015-B3L
MIL-9016-B3
MIL-9018-B3
MIL-9018-B3L

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.

6.6 Amendment notations. The margins of this specification are marked with vertical lines to indicate modifications generated by this amendment. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations.

CONCLUDING MATERIAL

Custodians:
Army – AR
Navy – SH
Air Force – 20

Review activities:
Army – AT, EA, MR
Navy – OS, YD
DLA – GS

Preparing activity:
Navy – SH
(Project 3439-2025-005)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using ASSIST at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:23Z
Check the source to verify that this is the current version before use.