MILITARY SPECIFICATION

ELECTRODES, WELDING, MINERAL-COVERED, IRON-POWDER,

LOW-HYDROGEN, 8 NICKEL-CHROMIUM-MOLYBDENUM-VANADIUM ALLOY STEEL FOR

PRODUCING HY-130 WELDMENTS TO BE HEAT-TREATED

This specification is approved for use by the Naval Sea Systems Command and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers low-hydrogen, iron-powder type of covered electrodes, for the fabrication and repair welding of HY-130 steel to be heat-treated.

1.2 Classification. Electrodes covered by this specification are classified on the basis of type, class, welding position, and size as shown in table I, as specified (see 6.2).

Table I - Classification.

Type	Class	Welding position	Size diameter (inch)
MIL-14018-HT	2	Horizontal fillets and flat	3/16

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

MILITARY

MIL-W-10430 - Welding Rods and Electrodes; Preparation for Delivery of.
MIL-E-22200 - Electrodes, Welding, Covered; General Specification for.
MIL-S-24371 - Steel Plate, Alloy, Structural, High Yield Strength (HY-130).

STANDARDS

MILITARY

MIL-STD-271 - Nondestructive Testing Requirements for Metals.
MIL-STD-418 - Mechanical Tests for Welded Joints.
MIL-STD-1601 - Method for 5/8 Inch Dynamic Tear Testing of Metallic Materials.

PUBLICATIONS

MILITARY

NAVSEA 0900-LP-005-5000 - Standard Procedures for Preproduction Testing Materials by the Explosion Bulge Test.
NAVSEA 0900-LP-003-8000 - Surface Inspection Acceptance Standards, Metals.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

UNIFORM CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules.

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION INCORPORATED, AGENT
National Motor Freight Classification Rules.

(Application for copies should be addressed to the National Motor Freight Traffic Association, Inc., 1616 P Street, N.W., Washington, DC 20036.)

AMERICAN NATIONAL STANDARDS INSTITUTE (ANSI)
Z49.1-73 - Safety in Welding and Cutting.

(Application for copies should be addressed to the American National Standards Institute, Inc., 1430 Broadway, New York, NY 10018.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Electrodes furnished under this specification shall conform to the requirements of MIL-E-22200 except as specified herein.

3.2 Covering composition.

3.2.1 Water content. The water content of the coverings shall not exceed the percent-by-weight value specified in table II.

Table II - Water content.

Type	Percent by weight maximum
MIL-14018-HT	0.10

3.2.2 Total iron content. The total iron content of the covering, including any combined iron in addition to metallic iron powder, shall be not less than 15 percent.

3.3 Groove welds.

3.3.1 Mechanical properties. The mechanical properties of groove welds shall be as specified in table III.

Table III - Heat-treated mechanical properties[1/].

Type	Yield strength p.s.i.[2/]	Elongation in 1.4 inches or 2 inches minimum percent	Transverse side bend	5/8 Inch dynamic tear		Explosion bulge
				Energy ft/lbs minimum	Temperature °F	
MIL-14018-HT	135,000 to 150,000	14	3/	475	30	4/

1/ The ultimate tensile strength and percentage reduction of area shall be recorded for information only.

2/ The yield strength shall be the average of duplicate specimens measured at 0.2 percent offset by using a class B extensometer or better. The minimum single value shall be 135,000 p.s.i.

3/ The convex surface of the specimen after bending shall have no visual cracks exceeding 1/8 inch. The corners of the specimen shall have no visual cracks exceeding 3/16 inch. The bend radius shall be 3 times the specimen thickness (3t) and the tests conducted as specified in 4.4.1.

4/ The explosion bulge test shall be conducted as specified in 4.4.2. The criteria of performance shall be in accordance with the following:

(a) Two crack-starter weldments.
(b) Two bulge weldments.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

(1) Crack starter:
a. First shot - Crack-starter bead shall crack.
Percent reduction in thickness obtained for information only.
No piece shall be thrown out of weldments.
No through-thickness cracks shall be present.
No crack shall extend into hold-down area.*
b. Second shot - Percent reduction in thickness obtained for information only.
No piece shall be thrown out of weldment.
Through-thickness cracks are acceptable.
No cracks shall extend into hold-down area.*

(2) Bulge:
a. First shot - Percent reduction in thickness obtained for information only.
No piece shall be thrown out of weldment.
No through-thickness cracks shall be present.
No crack shall extend into hold-down area.*
b. Second shot - Percent reduction in thickness obtained for information, 5 percent reduction is expected.
No piece shall be thrown out of weldment.
No through-thickness cracks shall be present.
No crack shall extend into hold-down area.*
In the event that 7 percent reduction in plate thickness is obtained on both sides of the weld or 7-1/2 percent reduction in plate thickness is obtained on one side of the weld the performance is considered satisfactory and the third shot shall not be made provided the following conditions are met:
No piece shall be thrown out of weldment.
Through-thickness cracks are acceptable.
No cracks shall extend into the hold-down area.*
c. Third shot - Percent reduction in thickness obtained for information, 7 percent reduction is expected.
No piece shall be thrown out of weldment.
Through-thickness cracks are acceptable.
No cracks shall extend into hold-down area.*

*Crack shall remain within 12-1/2 inch radius measured from center of weldment.

3.4 Chemical composition of deposited weld metal. Chemical composition of deposited weld metal shall be as specified in table IV.

Table IV - Chemical composition (weight-percent)[1/] of deposited weld metal.

Type	Element	Weight-percent
MIL-14018-HT	Carbon	0.10
	Manganese	.40 to .80
	Phosphorus	.013
	Sulfur	.010
	Silicon	.50
	Nickel	7.00 to 9.00
	Chromium	.05 to .60
	Molybdenum	.40 to .70
	Vanadium	.04 to .10

[1/] Single values are maximum percentages.

3.5 Electrode length. The electrode length shall be 14 inches.

4. QUALITY ASSURANCE PROVISIONS

4.1 The quality assurance provisions shall be in accordance with MIL-E-22200 except as specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

4.2 Qualification tests. Qualification tests shall be as specified in 4.2 of MIL-E-22200 and table V herein.

Table V - Summary of weld metal tests required for qualification[1/].

Electrode type	Radio-graphic	Ten-sile	Bend	Chemical	Dynamic tear	Explosion bulge	Test procedures	Requirements
MIL-14018-HT	X	--	--	--	--	--	4.4.1, 4.4.3, figures 1 and 2	3.7.1 of MIL-E-22200
	--	X	--	--	--	--	4.4.1 4.4.3, figures 1 and 2	Table III
	--	--	X	--	--	--	4.4.1 and figure 1	Table III
	--	--	--	X	--	--	4.6.8 of MIL-E-22200	Table IV
	--	--	--	--	X	--	4.4.1, 4.4.3, figures 1 and 2	Table III
	--	--	--	--	--	X	4.4.2	Table III

1/ The electrode sample selected in accordance with 4.2.1.2 of MIL-E-22200 shall be large enough to make all welds required by figure 1, figure 2, and the explosion bulge test.

4.3 Quality conformance inspection.

4.3.1 Lot. A lot of electrodes shall be as specified in 4.4.2.1 and 4.4.6.1 of MIL-E-22200 for inspection level A.

4.3.2 Samples for quality conformance inspection. Sampling for quality conformance inspection shall be in accordance with 4.4.7 through 4.4.8.3 of MIL-E-22200.

4.3.3 Quality conformance inspection. The samples selected in accordance with 4.3.2 shall be subjected to the examination and tests specified in table VI and the weld metal tests specified in table VII.

Table VI - Quality conformance inspection.

Examination or test	Test procedures	Requirements
	MIL-E-22200	
Visual and dimensional	4.6.2.3	3.6 and 3.10 of MIL-E-22200 and 3.5 herein
Concentricity	4.6.2	3.5.2 of MIL-E-22200
Covering moisture	4.6.9	3.2.1 herein

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

Table VII - Summary of weld metal tests required for quality conformance inspection.

Electrode type	Radio-graphic	Tensile	Chemical	Dynamic tear	Test procedures	Requirements
MIL-14018-HT	X	---	---	---	4.4.1 and figure 1	3.7.1 of MIL-E-22200
	---	X	---	---	4.4.1 and figure 1	Table III
	---	---	X	---	4.6.8 of MIL-E-22200	Table IV
	---	---	---	X	4.4.1 and figure 1	Table III

4.3.3.1 Unsatisfactory test results. If the results of the first tests except dynamic tear are determined to be unsatisfactory, two retests shall be permitted. The results of both retests shall be satisfactory for lot acceptance. Retesting of the 5/8-inch dynamic tear test specimens shall be in accordance with MIL-STD-1601.

4.4 Test procedures.

4.4.1 One-inch thick weld test groove joint. The dimensions of the test weldment and the location of the tensile and dynamic tear specimens are shown on figure 1. The test weldment, figure 1, shall be extended to provide for two transverse side bend test specimens when qualification testing an electrode. The transverse side bend test specimens shall be taken next to the discard ends. The test assembly shall be welded, heat treated, radiographed, and tested as follows:

(a) The base-plate material shall be HY-130 steel in accordance with MIL-S-24371.
(b) Direct current reverse polarity shall be used.
(c) Welding shall be done in the flat position.
(d) The joint surfaces shall not be clad or buttered.
(e) Upon removal from vendor's unit containers or holding oven, electrodes shall be placed in a holding oven at the job site. The temperature of the holding oven shall be 225°F to 300°F. The welder shall use each electrode immediately upon removal from the holding oven at the job site.
(f) The preheat and interpass temperature range shall be 250°F to 275°F.
(g) The heat input shall be 38,000 to 42,000 joules per inch.
(h) Welding may be continuous except for interpass cooling. Planned interruption of welding shall be followed immediately by one of the following heat soaking treatments without tube weldment cooling below the interpass temperature:
  (1) Partially completed welds 1/2-inch thick or less 250°F +25°F -0°F for 4 hours minimum.
  (2) Partially completed welds over 1/2-inch thick 350°F +25°F -0°F for 12 hours minimum.
(i) The weldment shall be given the following heat treatment without cooling below the interpass temperature range:
  (1) Charge into furnace at 250°F to 500°F.
  (2) Heat to 1700°F ± 25°F, hold at temperature for 1 hour and water quench.
  (3) Reheat to 1500°F ± 25°F, hold at temperature for 1 hour and water quench.
  (4) Reheat to 1100°F ± 25°F, hold at temperature for 1 hour and water quench.

  When it is planned to cool the weldment to room temperature before heat-treating, the weldment shall be given a post weld soaking treatment of 350°F +25°F -0°F for 12 hours minimum without the weldment cooling below the minimum interpass temperature.
(j) The heat-treated weldment shall then have the reinforcement and backing strip removed flush with the base plate on both surfaces.
(k) The flush weld shall be inspected radiographically in accordance with level 2-2T of MIL-STD-271 for compliance with the requirements of 3.7.1 of MIL-E-22200.
(l) The bend test specimens, when required, and the tension test specimens shall be machined and tested in accordance with MIL-STD-418 for compliance with the requirements of table III.
(m) The 5/8-inch dynamic tear test specimens shall be machined and tested in accordance with MIL-STD-1601 for compliance with the requirements of table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

4.4.2 Explosion bulge test. The explosion bulge test shall be conducted in accordance with NAVSEA 0900-LP-005-5000 using the following procedures:

(a) The base-plate material shall be HY-130 steel in accordance with MIL-S-24371.
(b) Direct current reverse polarity shall be used.
(c) Welding shall be done in the flat position.
(d) The joint surfaces shall not be clad or buttered.
(e) Upon removal from vendor's unit containers or holding oven, electrodes shall be placed in a holding oven at the job site. The temperature of the holding oven shall be 225°F to 300°F. The welder shall use each electrode immediately upon removal from the holding oven at the job site.
(f) The preheat and interpass temperature range shall be 250°F to 275°F.
(g) The heat input shall be 38,000 to 42,000 joules per inch.
(h) Welding may be continuous except for interpass cooling. Planned interruption of welding shall be followed immediately by one of the following heat soaking treatments without tube weldment cooling below the interpass temperature:
(1) Partially completed welds 1/2-inch thick or less 250°F +25°F -0°F for 4 hours minimum.
(2) Partially completed welds over 1/2-inch thick 350°F +25°F -0°F for 12 hours minimum.
(i) One hundred percent of the welds, with the weld reinforcement left in place, shall be inspected radiographically in accordance with level 2-2T of MIL-STD-271 for compliance with the requirements of 3.7.1 of MIL-E-22200.
(j) One hundred percent of the welds, with the weld reinforcement left in place, shall be inspected by the magnetic particle test in accordance with MIL-STD-271 to the acceptance criteria of NAVSEA 0900-LP-003-8000, class 1.
(k) The crack starter and explosion bulge weldments shall be tested only after satisfactory completion of the following tests:
(1) Small scale mechanical tests from the two prolongations to the explosion bulge test weldments required by NAVSEA 0900-LP-005-5000.
(2) The radiographic tests required by (i) above.
(3) The magnetic particle test required by (j) above.
(l) The crack starter and explosion bulge weldments, when tested, shall have the weld reinforcement left in place.

4.4.3 Four-inch thick weld test groove joint. The dimensions of the test weldment and the location of the tensile and dynamic tear specimens are shown on figure 2. The test assembly shall be welded, heat-treated, radiographed, and tested as follows:

(a) The base-plate material shall be HY-130 steel in accordance with MIL-S-24371.
(b) Direct current reverse polarity shall be used.
(c) Welding shall be done in the flat position.
(d) The joint surfaces shall not be clad or buttered.
(e) Upon removal from vendor's unit containers or holding oven, electrodes shall be placed in a holding oven at the job site. The temperature of the holding oven shall be 225°F to 300°F. The welder shall use each electrode immediately upon removal from the holding oven at the job site.
(f) The preheat and interpass temperature range shall be 250°F to 275°F.
(g) The heat input shall be 38,000 to 42,000 joules per inch.
(h) Welding may be continuous except for interpass cooling. Planned interruption of welding shall be followed immediately by one of the following heat soaking treatments without tube weldment cooling below the interpass temperature.
(1) Partially completed welds 1/2-inch thick or less 250°F +25°F -0°F for 4 hours minimum.
(2) Partially completed welds over 1/2-inch thick 350°F +25°F -0°F for 12 hours minimum.
(i) The weldment shall be given the following heat treatment without cooling below the interpass temperature range:
(1) Charge into furnace at 250°F to 500°F.
(2) Heat to 1700°F ± 25°F, hold at temperature for 4 hours and water quench.
(3) Reheat to 1500°F ± 25°F, hold at temperature for 4 hours and water quench.
(4) Reheat to 1100°F ± 25°F, hold at temperature for 4 hours and water quench.

When it is planned to cool the weldment to room temperature before heat treating, the weldment shall be given a post weld soaking treatment of 350°F +25°F -0°F for 12 hours minimum without the weldment cooling below the minimum interpass temperature.
(j) The heat treated weldment shall then have the reinforcing removed flush with the base plate.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

(k) The flush weld shall be inspected radiographically in accordance with level 2-2T of MIL-STD-271 for compliance with the requirements of 3.7.1 of MIL-E-22200.

(l) Two 0.505 all weld metal tension specimens shall be machined and tested in accordance with MIL-STD-418 for compliance with the requirements of table III.

(m) Two 5/8-inch dynamic tear test specimens shall be taken near the surface and 2 at the center, machined and tested in accordance with MIL-STD-1601 for compliance with the requirements of table III. Figure 2 also shows the location of extra specimens for retest.

4.5 Certificate of test. A certificate of quality conformance of the weld tests specified in 4.3, containing actual quantitative test and examination results including the range of amperage employed in making the required welds for quality conformance inspection for each accepted lot, included in a particular shipment shall be furnished to the consignee with the shipment. The minimum quality conformance test result data required shall be listed on figure 3 and shall be submitted on the form shown.

4.6 Inspection of preparation for delivery. The packaging, packing, and marking shall be inspected for compliance with section 5 of this document.

5. PREPARATION FOR DELIVERY

(The preparation for delivery requirements specified herein apply only for direct Government procurements.)

5.1 General. Each end of unit containers (metal cans) shall be provided with fiberboard or other cushioning material to restrict the end-wise movement of the electrodes and to provide a snug-fitting nonshifting load. The applied packaging shall meet the stability requirements specified in 3.5.8 of MIL-E-22200 and provide the necessary protection so that the electrode coverings do not exceed the water content of 3.2.1 and table II herein.

5.2 Packaging. Packaging shall be level A or C, as specified (see 6.2).

5.2.1 Level A. Electrodes shall be packaged in class 1 unit containers in accordance with MIL-W-10430.

5.2.2 Level C. Electrodes shall be packaged to afford protection against deterioration and physical damage (see 5.1) during shipment from the supply source to the using activity. The supplier's retail or wholesale packaging procedures may be utilized when such meets the requirements of this level.

5.3 Packing. Packing shall be level A, B, or C, as specified (see 6.2).

5.3.1 Levels A and B. Electrodes, packaged as specified (see 6.2), shall be level A or B in accordance with MIL-W-10430. Palletization when required (see 6.2) shall be in accordance with MIL-W-10430.

5.3.2 Level C Electrodes, packaged as specified (see 6.2) shall be packed in containers acceptable to the common carrier and which will insure safe delivery at destination in a satisfactory condition at the lowest applicable rate. Containers, packing, or method of shipment shall comply with Uniform Freight or National Motor Freight Classification Rules or Regulations or other carrier rules as applicable to the mode of transportation.

5.4 Marking. In addition to any special marking required herein or by the contract or order (see 6.2), interior packaging, exterior shipping containers, and palletized loads shall be marked in accordance with MIL-W-10430.

5.4.1 Special marking.

5.4.1.1 Interior packages and shipping containers. In addition to the lot identification required by 4.4.6 of MIL-E-22200, identification on interior packages shall include MIL type, size, specification number, manufacturer's or distributor's name, date of manufacture (month/year), and manufacturer's or distributor's brand or type designation. In

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

addition, all unit packages shall be marked or labeled with the following precautionary information, as a minimum and prominently displayed:

CAUTION
Welding may produce fumes and gases hazardous to health. *Avoid breathing these fumes and gases.* Use adequate ventilation. See ANSI Standard Z49.1 "Safety in Welding and Cutting" published by the American Welding Society.

5.4.1.2 Class 1b containers. Each class 1b container on the container end adjacent to the electrode grip end shall be marked "OPEN THIS END".

6. NOTES

6.1 Intended use. This specification is intended to cover nickel-chromium-molybdenum-vanadium alloy steel mineral-covered welding electrodes capable of depositing weld metal, that in the heat-treated condition meets the mechanical properties given herein when welded on HY-130 steel with the shielded metal-arc process using direct current reversed polarity and the techniques specified herein. The primary use of these electrodes are for the welding of HY-130 steel for applications in the heat-treated condition.

6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number, and date of this specification.
(b) Type, class, welding position, and size required (see 1.2).
(c) Levels of packaging and packing required (see 5.2 and 5.3).
(d) When palletization is required (see 5.3.1).
(e) Special marking required (see 5.4).


6.2.1 Electrodes should be ordered by the pound.

6.3 Inspection after delivery. Post delivery inspection of electrodes to determine conformity to this specification and for acceptance thereof is the responsibility of the consignee.


6.4 Electrode manufacturers may make arrangements to have 5/8-inch dynamic tear tests conducted by contacting the following: Commander, Mare Island Naval Shipyard (Code 138), Vallejo, CA 94592 or Commander, Portsmouth Naval Shipyard (Code 374), Portsmouth, NH 03801.

Preparing activity:
Navy - SH
(Project 3439-N289)


Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

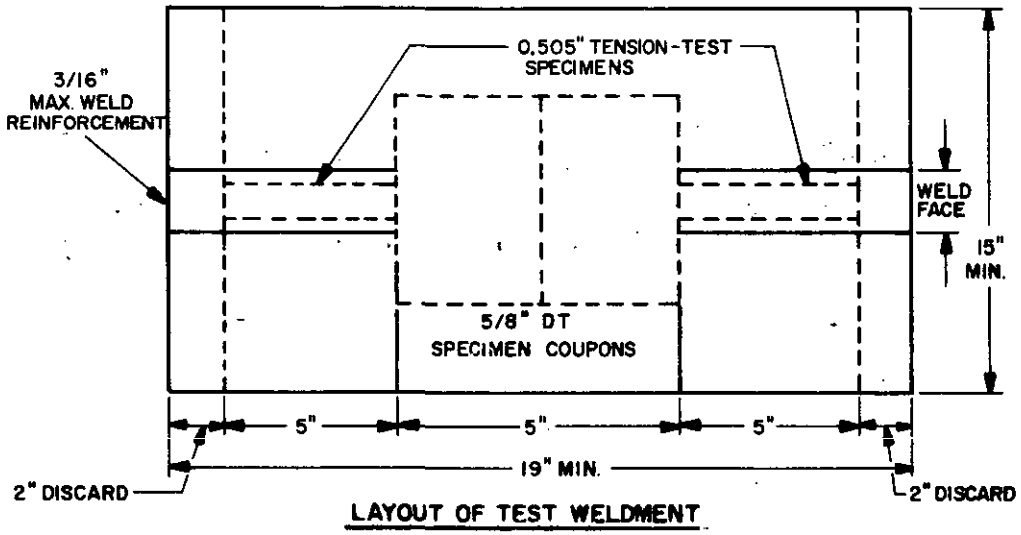

LAYOUT OF TEST WELDMENT

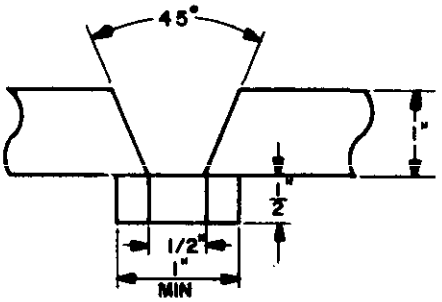

JOINT GEOMETRY

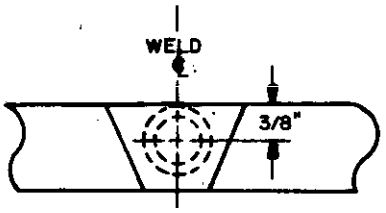

SPECIMEN LOCATION

SH 10866

Figure 1 - One-inch thick weld test groove joint.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

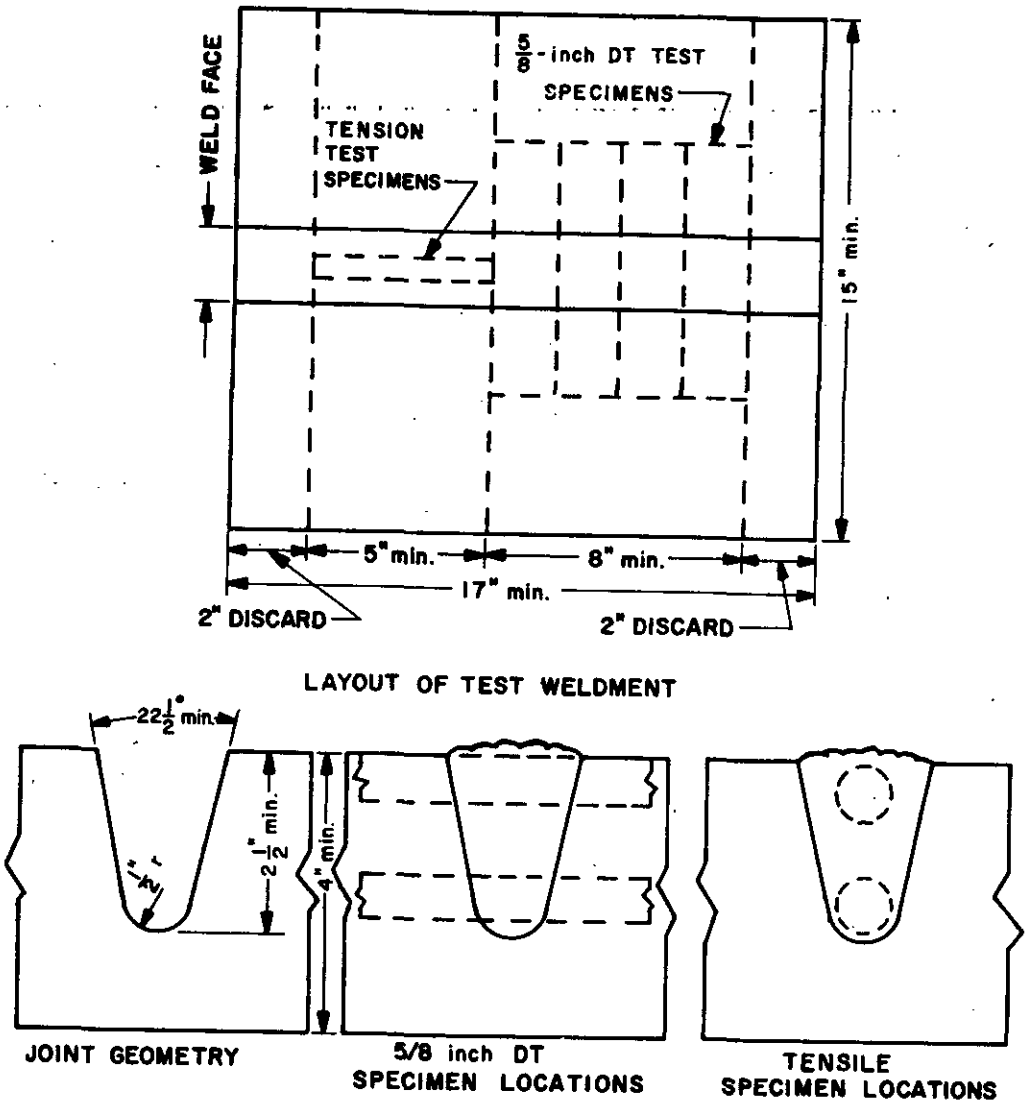


Figure 2 - Four-inch thick weld test groove joint.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

Manufacturer or Distributor _____

Address _____

Date _____

Specification _____

Type _____

Size _____

Wet Batch No. _____

Lot No. _____

Core Wire Heat No. _____

Customer's Name _____

Customer's Order No. _____

Mechanical Test Results

Yield Strength (p.s.i.) _____

% Elongation _____

5/8 DT Test @ 30°F (ft. lbs.) _____

Chemical Analysis

Carbon _____

Manganese _____

Phosphorus _____

Sulfur _____

Silicon _____

Nickel _____

Chromium _____

Molybdenum _____

Vanadium _____

Chemistry Taken From: ☐ Chem Pad ☐ Groove Weld ☐ Tensile Specimen

Interpass, Interlayer or Intraweld Time Delay or Heat Soaking _____

Grinding during test-plate preparation (see note 2) _____

Radiography Results _____

Visual & Dimensional _____

Concentricity _____

Covering Moisture _____

Welding Procedure

Preheat/Interpass Temp _____

Welding Current (Amps) _____

Weld Energy Input _____

We hereby certify that the above material has been tested in accordance with the listed specification and is in conformance with all requirements.

_____

NOTES:

1. This form is applicable to the quality conformance tests required for each lot of electrodes. One copy shall be forwarded for each lot included in the shipment.
2. See 3.5.7 and 3.9 of MIL-E-22200.

Figure 3 - Certification of quality conformance inspection.

_____

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO (If "Yes", in what way?)

4. REMARKS

SUBMITTED BY (Printed or typed name and address - Optional)

TELEPHONE NO.

DATE

DD FORM 1 JAN 72 1426 REPLACES EDITION OF 1 JAN 68 WHICH MAY BE USED

S/N 0102-014-1802

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:25Z
Check the source to verify that this is the current version before use.