MILITARY SPECIFICATION

ELECTRODES, WELDING, MINERAL COVERED, LOW-HYDROGEN OR IRON-POWDER, LOW-HYDROGEN, NICKEL-MANGANESE-CHROMIUM-MOLYBDENUM ALLOY STEEL FOR PRODUCING HY-130 WELDMENTS FOR AS-WELDED APPLICATIONS

1. SCOPE

1.1 Scope. This specification covers low-hydrogen or low-hydrogen iron-powder types of covered electrodes, for the fabrication and repair welding of HY-130 steel for as-welded applications.

1.2 Classification. Iron-powder low-hydrogen electrodes shall be furnished in types, classes, and sizes shown in table I as specified (see 6.2).

Table I - Classification

Type	Class 1/	Positions of welding	Sizes (diameter)
MIL-14018 MIL-14018(NC)	1 2	All Horizontal fillets and flat	1/8, 5/32, 3/16

1/ Type classifications of electrodes will be determined according to the capability of the electrode to meet the tests specified hereinafter, when used in the positions of welding specified in table I and in section 4. An electrode shall be approved under ONE type classification; and an electrode shall NOT be approved if it differs in type from that stated in the exhibitor's request for test. The position description indicates the maximum size qualified under the specification. However, reference should be made to the Qualified Products List (QPL) for the selection of electrodes for all positions of welding.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal, form a part of the specification to the extent specified herein.

SPECIFICATIONS

MILITARY

MIL-W-10430 - Welding Rods and Electrodes; Preparation for Delivery of.
MIL-E-22200 - Electrodes, Welding, Covered; General Specification for.
MIL-S-24371 - Steel Plate, Alloy, Structural, High Yield Strength (HY-130)

STANDARDS

FEDERAL

FED-STD-151 - Metals; Test Methods

MILITARY

MIL-STD-147 - Palletized and Containerized Unit Loads 40"X48" 4-Way (Partial) Pallet Skids, Runners, or Pallet-Type Base
MIL-STD-271 - Nondestructive Testing Requirements for Metals
MIL-STD-418 - Mechanical tests for Welded Joints

PUBLICATIONS

MILITARY

NAVSHIPS 0900-003-9000 - Radiographic Standards for Production and Repair Welds
NAVSHIPS 0900-005-5000 - Standard Procedures for Preproduction Testing Materials by the Explosion Bulge Test.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

AMERICAN WELDING SOCIETY (AWS)
Z49.1 - Safety in Welding and Cutting

(Application for copies should be addressed to the American Welding Society, 345 47th Street, New York, N. Y. 10017.)

UNIFORM CLASSIFICATION COMMITTEE
Uniform Freight Classification Rules

(Application for copies should be addressed to the Uniform Classification Committee, 202 Union Station, 516 West Jackson Boulevard, Chicago, Illinois 60606.)

(Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

3. REQUIREMENTS

3.1 Electrodes furnished under this specification shall conform to the requirements of MIL-E-22200 and as specified hereinafter.

3.2 Composition and iron content.

3.2.1 Composition. The chemical composition of the coverings, except as specified in 3.2.2, is optional with the manufacturer. The water content of the coverings shall not exceed the percent-by-weight values specified in table II.

Table II - Water content.

Type	Percent by weight maximum
MIL-14018	0.10
MIL-14018(NC)	.10

3.2.2 Total iron content. The total iron content of the covering, including any combined iron in addition to metallic iron powder, shall be not less than 15 percent.

3.3 Groove welds.

3.3.1 Mechanical properties. The mechanical properties of groove welds shall be as specified in table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

Table III - As-welded mechanical properties 1/

Type	Yield strength psi 2/	Elongation in 1.4 inches or 2 inches minimum percent	Transverse side bend	Charpy -V notch impact 3/		Explosion bulge
				Energy ft./lbs. min. avg.	Temperature °F	
MIL-14018	135,000 to 145,000	14	4/	50 50	30 Room Temp. (75 min.)	5/
MIL-14018(NC)	135,000 to 145,000	14	4/	40 40	30 Room Temp. (75 min.)	5/

1/ The ultimate tensile strength and percentage reduction of area shall be recorded for information only. Both electrode types shall be tested using direct current reverse polarity.

2/ The yield strength shall be the average of duplicate specimens measured at 0.2 percent offset by using a class B extensometer or better. The minimum single value shall be 135 Ksi.

3/ For each testing temperature, the average values of five tests shall be greater than the minimum average value specified. No two specimens shall have values below the minimum average specified. One specimen can have a value of 10 foot-pounds below the minimum average specified.

The average value obtained at room temperature (75°F. minimum) shall not be more tl 10 foot-pounds higher than the average value obtained at the lower testing temperature.

4/ The convex surface of the specimen after bending shall have no visual cracks exceeding 1/8 inch. The corners of the specimen shall have no visual cracks exceeding 3/16 inch. The bend radius shall be 3t and the tests conducted in accordance with the requirements of MIL-STD-418.

5/ The test results shall comply with the requirements of NAVSHIPS 0900-005-5000 and the following modification: a 10 percent minimum thickness reduction of the explosion bulge specimens with no crack outside the bulge region is required for this test.

3.4 Chemical composition of deposited weld metal. Chemical composition of deposited weld metal shall be as specified in table IV.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

Table IV - Chemical composition (weight-percent 1/) of deposited weld metal.

Type	Element	Weight percent
All	Carbon	0.10
	Manganese	1.50 to 2.25
	Phosphorus	0.010
	Sulfur	.010
	Silicon	.50
	Nickel	2.00 to 2.75
	Chromium	0.50 to 1.00
	Molybdenum	.30 to 0.60
	Vanadium	.05

1/ Single values are maximum percentages.

3.5 Electrode identification. Electrodes shall be identified as specified in 3.5.10 of MIL-E-22200.

3.6 Electrode lengths. The specified lengths of electrodes shall be in accordance with table V.

Table V - Electrode lengths.

Sizes	Electrode lengths end-grip
Inch	Inches
1/8, 5/32, 3/16	14

3.7 Decoated core wire. Any core wire or electrode which is removed from the assembly line area during production of a lot of electrodes shall not be used to fill any order under this specification.

3.8 Soundness. Welds shall be capable of meeting the requirements of NAVSHIPS 0900-003-8000 for magnetic particle inspection. Radiographs of welds deposited with type MIL-14018 electrodes shall meet the requirements for grade I of NAVSHIPS 0900-003-9000 for one thickness lower than the actual plate thickness tested. Radiographs of welds deposited with type MIL-14018(NC) electrodes shall meet the requirements for grade I of NAVSHIPS 0900-003-9000.

4. QUALITY ASSURANCE PROVISIONS

4.1 Qualification test. Qualification test shall consist of conducting the examination and tests specified in table VI herein and 4.6 of MIL-E-22200.

4.1.1 Samples for qualification test. Samples for the qualification test shall be in accordance with 4.2.1.4 of MIL-E-22200.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

Table VI - Summary of weld metal tests required for qualification

Electrode Type	Size			Non-destructive	Tensile	Bend	Impact	Chemical	Explosion Bulge 1/	Test procedure	Requirements
	1/8	5/32	3/16								
All	X	X	-	X	-	-	-	-	-	4.3.2 and figure 2 herein	3.8 herein
	X	X	-	-	X	X	X	-	-	4.3.2 and figure 2 herein	Table III herein
	X	X	-	-	-	-	-	X	-	4.6.8 of MIL-E-22200	Table IV herein
	All			-	-	-	-	-	X	NAVSHIPS 0900-005-5000	NAVSHIPS 0900-005-5000 and table III herein
	-	-	X	X	-	-	-	-	-	4.3.1 and figure 1 herein	3.8 herein
	-	-	X	-	X	X	X	-	-	4.3.1 and figure 1 herein	Table III herein
	-	-	X	-	-	-	-	X	-	4.6.8 of MIL-E-22200	Table IV herein

1/ All types and all sizes of electrodes shall be qualification tested in accordance with NAVSHIPS 0900-005-5000 for compliance with the requirements of table III herein, except as noted below. The test results shall contain charpy v-notch data for minus 60°F, minus 30°F, zero, plus 30°F, and room temperature (75°F minimum). A smaller size electrode of the same class electrode previously qualified shall be evaluated on the bases of an equivalent charpy v-notch impact energy curve for weld metal from the two inch thick weldment and the explosion bulge test shall be omitted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

4.2 Quality conformance inspection.

4.2.1 Lot. A lot of electrode shall be as specified in 4.4.2.1 and 4.4.6.1 of MIL-E-22200 for inspection level A.

4.2.2 Samples for quality conformance inspection. Sampling for quality conformance inspection shall be in accordance with 4.4.7 through 4.4.8.3 of MIL-E-22200.

4.2.3 Quality conformance inspection. The samples selected in accordance with 4.2.2 shall be subjected to the examination and tests specified in table VII and the weld metal tests specified in Table VIII.

Table VII Summary of electrode examination and tests required for quality conformance inspection.

Examination or test	Procedures	Requirements
	MIL-E-22200	
Concentricity	4.6.2	3.5.2 of (MIL-E-22200)
Visual and dimensional	4.6.2.3	3.6 and 3.10 of (MIL-E-22200) and 3.6 herein
Covering moisture	4.6.9	3.2.1 herein

4.2.3.1 Unsatisfactory test results. If the results of the first tests are determined to be unsatisfactory, two retests shall be permitted. The results of both retests shall be satisfactory for lot acceptance.

4.3 Weld metal test procedures.

4.3.1 Flat-groove-weld metal test. The dimensions of the test weldment and the location of the tensile and impact specimens are shown on figure 1. The test weldment, figure 1 shall be extended to provide for two transverse side bend test specimens when qualification testing an electrode. The transverse side bend test specimens shall be taken next to the discard ends. The test assembly shall be welded, machined and tested as outlined below:

(a) The base-plate material shall be HY-130 steel in conformance with MIL-S-24371.
(b) The weldments shall be fabricated with 3/16 inch diameter electrode in the flat position using direct current reverse polarity and tested in the as-welded condition.
(c) The preheat and interpass temperature shall be maintained at 250° ± 25°F.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

Table VIII - Summary of weld metal tests required for quality conformance inspection 1/

Electrode type	Size			Non-destructive	Tensile	Impact	Chemical	Test procedure	Requirements
	1/8	5/32	3/16						
All	X	X	-	X	-	-	-	4.3.2 and figure 2 herein	3.8 herein
	X	X	-	-	X	X	-	4.3.2 and figure 2 herein	Table III herein
	X	X	-	-	-	-	X	4.6.8 of MIL-E-22200	Table IV herein
	-	-	X	X	-	-	-	4.3.1 and figure 1 herein	3.8 herein
	-	-	X	-	X	X	-	4.3.1 and figure 1 herein	Table III herein
	-	-	X	-	-	-	X	4.6.8 of MIL-E-22200	Table IV herein

1/ Electrodes shall be subject to one rebaking at 800° ± 25°F for a minimum period of 1/2 hour followed by storage in a holding oven at 275° ± 25°F. for a minimum period of one week prior to testing. This treatment shall be accomplished except when specifically not required by the procurement document.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

(d) The welding-heat input shall be 30,000 to 40,000 joules per inch.
(e) Peening of weld beads is not permitted.
(f) The test assembly shall be prepared by using welding sequence and techniques recommended by the manufacturer.
(g) The joint surfaces shall not be clad or buttered.
(h) All welding may be continuous except for interpass cooling. No postweld heat treatments shall be employed. All time delay per pass beyond that necessary for interpass cooling shall be reported.
(i) When 48 hours has elapsed after completion of welding, the weldment shall have the reinforcement and backing strip removed flush with the base plate on both surfaces and shall be examined non-destructively.
(j) Both surfaces of the weld shall be magnetic particle inspected in accordance with MIL-STD-271 for compliance with the applicable requirements of 3.8 herein.
(k) The weld shall be inspected radiographically according to level 2-2T of MIL-STD-271 for compliance with the applicable requirements of 3.8 herein.
(l) The bend test specimens when required, tension- and impact test specimens shall be machined and tested according to MIL-STD-418. The bend- and tension test specimens shall be tested at room temperature. Five impact specimens shall be tested at room temperature (75°F minimum) and five at 30°F.

4.3.2 Vertical-groove-weld metal test. The dimensions of the test weldment and the location of the tensile and impact specimens are shown on figure 2. The test weldment, figure 2 shall be extended to provide for two transverse side bend test specimens when qualification testing an electrode. The transverse side bend test specimens shall be taken next to the discard ends. The test assembly shall be welded, machined and tested as outlined below:

(a) The base-plate material shall be HY-130 steel in conformance with MIL-S-24371.
(b) The weldments shall be fabricated with 1/8- and 5/32-inch-diameter electrodes in the vertical-up position, using direct current reversed polarity and tested in the as welded condition.
(c) Bevelled plate edges shall be machined or gas cut and ground to remove surface irregularities.
(d) The preheat and interpass temperature shall be 250° ± 25°F.
(e) The weld metal shall be deposited in 1/8-inch-thick layers by using a maximum bead-width build-up sequence of 3/8 inch and 1/2 inch for the 1/8- and 5/32-inch-diameter electrodes, respectively. Each layer shall contain a start in the center of the weldment.
(f) All welding may be continuous except for interpass cooling, and no postweld heat treatments shall be employed. All time delay per pass beyond that necessary for interpass cooling shall be reported.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

(g) When 48 hours has elapsed after completion of welding, the weldment shall have the reinforcement and backing strip removed flush with the base plate on both surfaces and shall be examined nondestructively.
(h) Both surfaces of the weld shall be magnetic particle inspected in accordance with MIL-STD-271 for compliance with the applicable requirements of 3.8 herein.
(i) The weld shall be inspected radiographically according to level 2-2T of MIL-STD-271 for compliance with the applicable requirements of 3.8 herein.
(j) The bend test specimens when required, tension- and impact-test specimens shall be machined and tested according to MIL-STD-418. The bend- and tension test specimens shall be tested at room temperature. Five impact specimens shall be tested at room temperature (75°F minimum) and five at 30°F.

4.3.3 Restraint-cracking-weld metal test. The dimensions of the test weldment and the location of the tension test and transverse side bend specimens are shown on figure 3. The test assembly shall be welded and tested as outlined below:

(a) The base-plate material shall be HY-130 steel plates in accordance with MIL-S-24371.
(b) One assembly shall be fabricated with each electrode size in the flat position, using direct current reverse polarity and tested in the as welded condition.
(c) Bevelled plate edges shall be machined or gas cut and ground to remove surface irregularities.
(d) The preheat and interpass temperature shall be 250° ± 25°F and the welding heat input shall be 30,000 to 40,000 joules per inch.
(e) On the exposed side of the joint (side no. 1) layers of weld metal shall be deposited until the total thickness is approximately 1/2 inch. The backside of the root shall then be ground to a radius of approximately 1/4 inch, and the backside (side no. 2) shall then be welded until completion.
(f) Welding may be continuous except for interpass cooling and for grinding of the backside of the root. All time delay per pass beyond that necessary for interpass cooling shall be reported.
(g) After welding is completed, the weldment shall be allowed to cool in air to room temperature and no postweld heat treatment shall be employed.
(h) When 48 hours has elapsed after completion of welding, the weldment shall have the reinforcement and backing strip removed flush with the the base plate on both surfaces and shall be examined nondestructively.
(i) Both surfaces of the weld shall be magnetic particle inspected in accordance with MIL-STD-271 for compliance with the applicable requirements of 3.8 herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

(j) The weld shall be inspected radiographically according to level 2-2T of MIL-STD-271 for compliance with the applicable requirements, of 3.8 herein.
(k) After radiography, four 0.505-inch tension-test specimens and four transverse side bend specimens shall be removed as shown on figure 3 and the specimens shall be machined and tested according to MIL-STD-418.
(l) The yield strength (0.2 percent offset), tensile strength, and reduction of area of all four specimens shall be reported and the yield strength (average of four specimens) shall meet the requirements of table III herein. The reduction in area shall not be less than 40 percent.
(m) The test results of the four transverse bend specimens shall meet the requirements of table III herein.

4.4 Certificate of test. A certificate of quality conformance of the weld tests specified in 4.2 (i.e., X-ray, mechanical, and chemical analysis), containing actual quantitative test and examination results including the range of amperage employed in making the required welds for quality conformance inspection for each accepted lot, included in a particular shipment shall be furnished to the consignee with the shipment. The minimum quality conformance test result data required shall be listed on figure 4 and shall be submitted on the form shown.

4.5 Inspection of preparation for delivery. The packaging, packing and marking shall be inspected for compliance with section 5 of this document.

5. PREPARATION FOR DELIVERY

(The preparation for delivery requirements specified herein apply only for direct Government procurements. For the extent of applicability of the preparation for delivery requirements of referenced documents listed in section 2, see 6.4.)

5.1 Packaging.

5.1.1 Level A. All electrodes shall be packaged in class 1 unit containers in accordance with MIL-W-10430.

5.2 Packing (see 6.2).

5.2.1 Levels A and B. Electrodes shall be packed level A or B as specified in accordance with MIL-W-10430, except that for levels A and B packing, palletization for other than cylindrical cans shall be in accordance with MIL-STD-147.

5.2.2 Level C. Packing shall be accomplished in a manner which will insure acceptance by common carrier and will afford protection against physical or mechanical damage during direct shipment from the supply source to the using activity. The shipping containers or method of packing shall conform to the

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

Uniform Freight Classification Rules or other carrier regulations as applicable to the mode of transportation.

5.3 Marking.

5.3.1 Interior packages. Shipment marking information shall be provided on interior packages in accordance with the manufacturer's commercial practice. In addition to the lot identification required by 4.4.6 of MIL-E-22200, the information shall include type, size, specification number, manufacturer's or distributor's name, date of manufacture (month/year), and manufacturer's or distributor's brand or type designation. In addition, all packages, or the smallest integral unit within a shipping container, shall carry the following warning label, as a minimum, prominently displayed in legible type on the package:

CAUTION

Welding may produce fumes and gases hazardous to health.
Avoid breathing these fumes and gases.
Use adequate ventilation.
See USAS Standard Z49.1 "Safety in Welding and Cutting" published by the American Welding Society.

Significant toxic constituents when present in the electrode in greater than trace amounts shall be identified on the warning label so that normal ventilation can be increased accordingly. These constituents include but are not limited to those itemized in section 8.5 through 8.11 of USAS Z49.1.

5.3.2 Exterior shipping containers and palletized unit loads. Shipment marking information shall be provided on exterior shipping containers and palletized unit loads in accordance with the manufacturer's commercial practice. In addition to the information required for interior packages as specified in 5.4.1 except the warning label, the information shall include shipping destination, stock number furnished with contract or order, customer's order number, customer's item number, and customer's name.

6. NOTES

6.1 Intended use. This specification is intended to cover nickel-manganese chromium-molybdenum alloy steel mineral covered welding electrodes capable of depositing weld metal, that in the as-welded condition meets the mechanical properties given herein when welded on HY-130 steel with the shielded metal-arc process using direct current reversed polarity and the techniques specified herein. The primary use of these electrodes are for the welding of HY-130 steel for applications in the as-welded condition.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

6.1.1 Type MIL-14018. Type MIL-14018 electrode meets the minimum Charpy v-notch impact requirements for 30°F minimum service, environment established for weld metal of this strength level. This type electrode is intended for general use.

6.1.2 Type MIL-14018 (NC). Type MIL-14018(NC) electrode is not required to meet the minimum impact referred to above and its use is intended to be limited to noncritical applications.

6.2 Ordering data.

6.2.1 Procurement documents should specify the following:

(a) Title, number and date of this specification.
(b) Type, class and size required (see 1.2).
(c) If rebaking is not required for quality conformance testing (see table VIII, footnote 1).
(d) Level of packing (see 5.2).

6.2.2 Electrodes should be ordered by the pound.

6.3 Inspection after delivery. Post delivery inspection of electrodes to determine conformity to this specification and for acceptance thereof is the responsibility of the consignee.

6.4 Sub-contracted material and parts. The preparation for delivery requirements of referenced documents listed in Section 2 do not apply when material and parts are procured by the supplier for incorporation into the equipment and lose their separate identity when the equipment is shipped.

Preparing activity:
Navy - SH
(Project 3439-N169)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

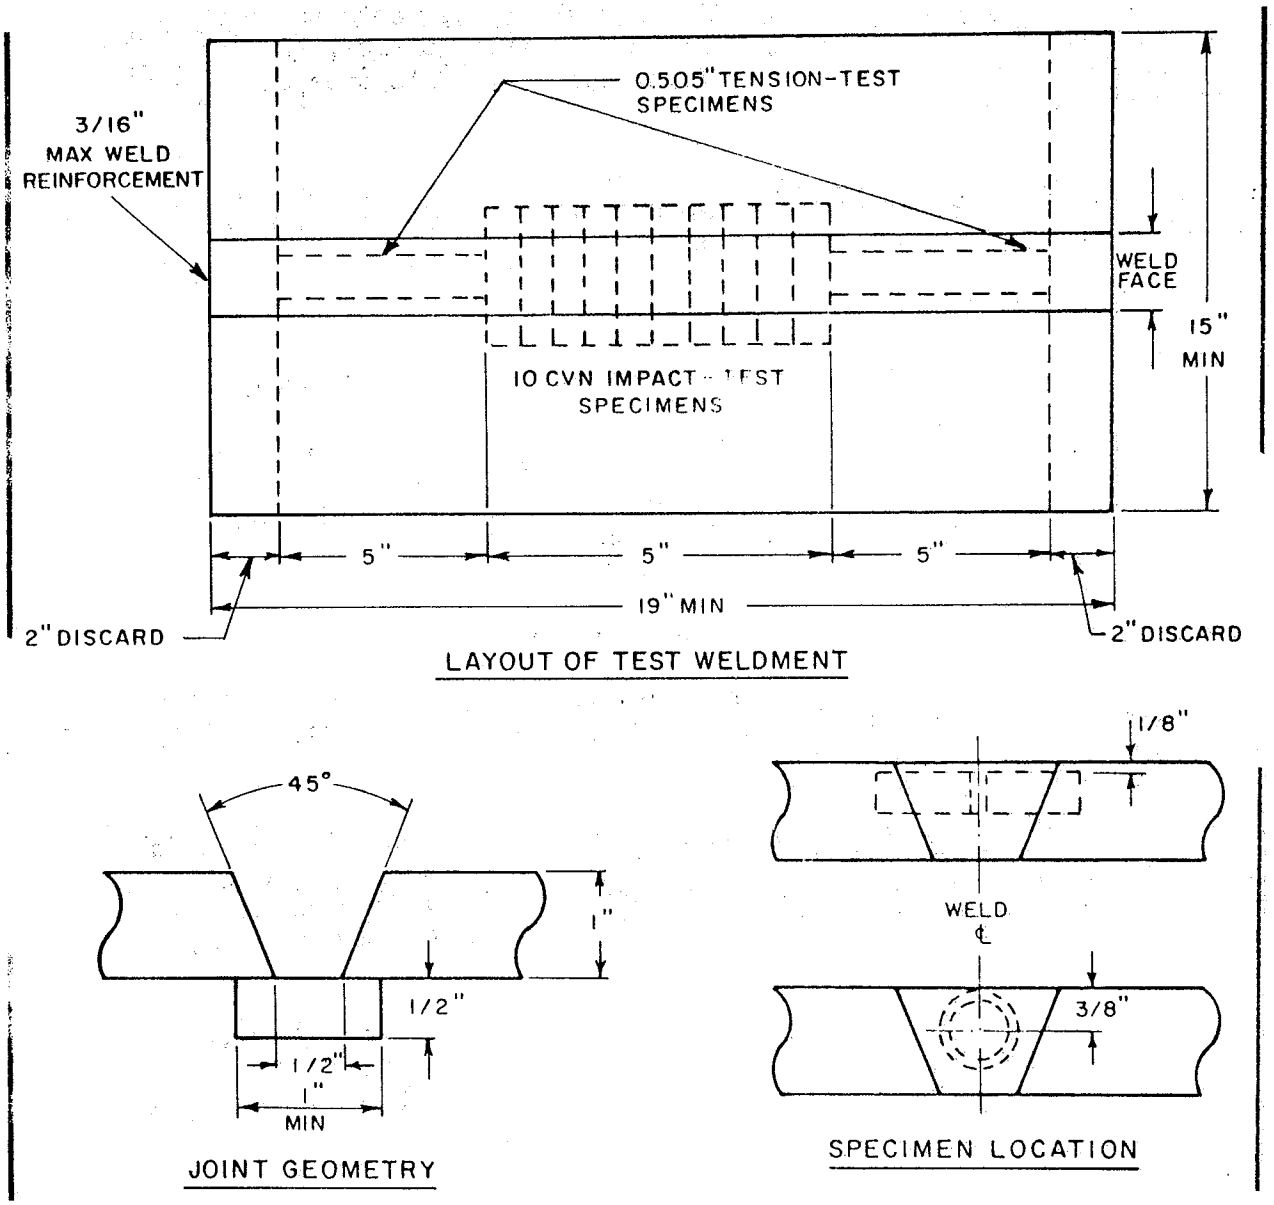


Figure 1 - Flat groove-weld metal test (for 3/16 inch diameter electrodes)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

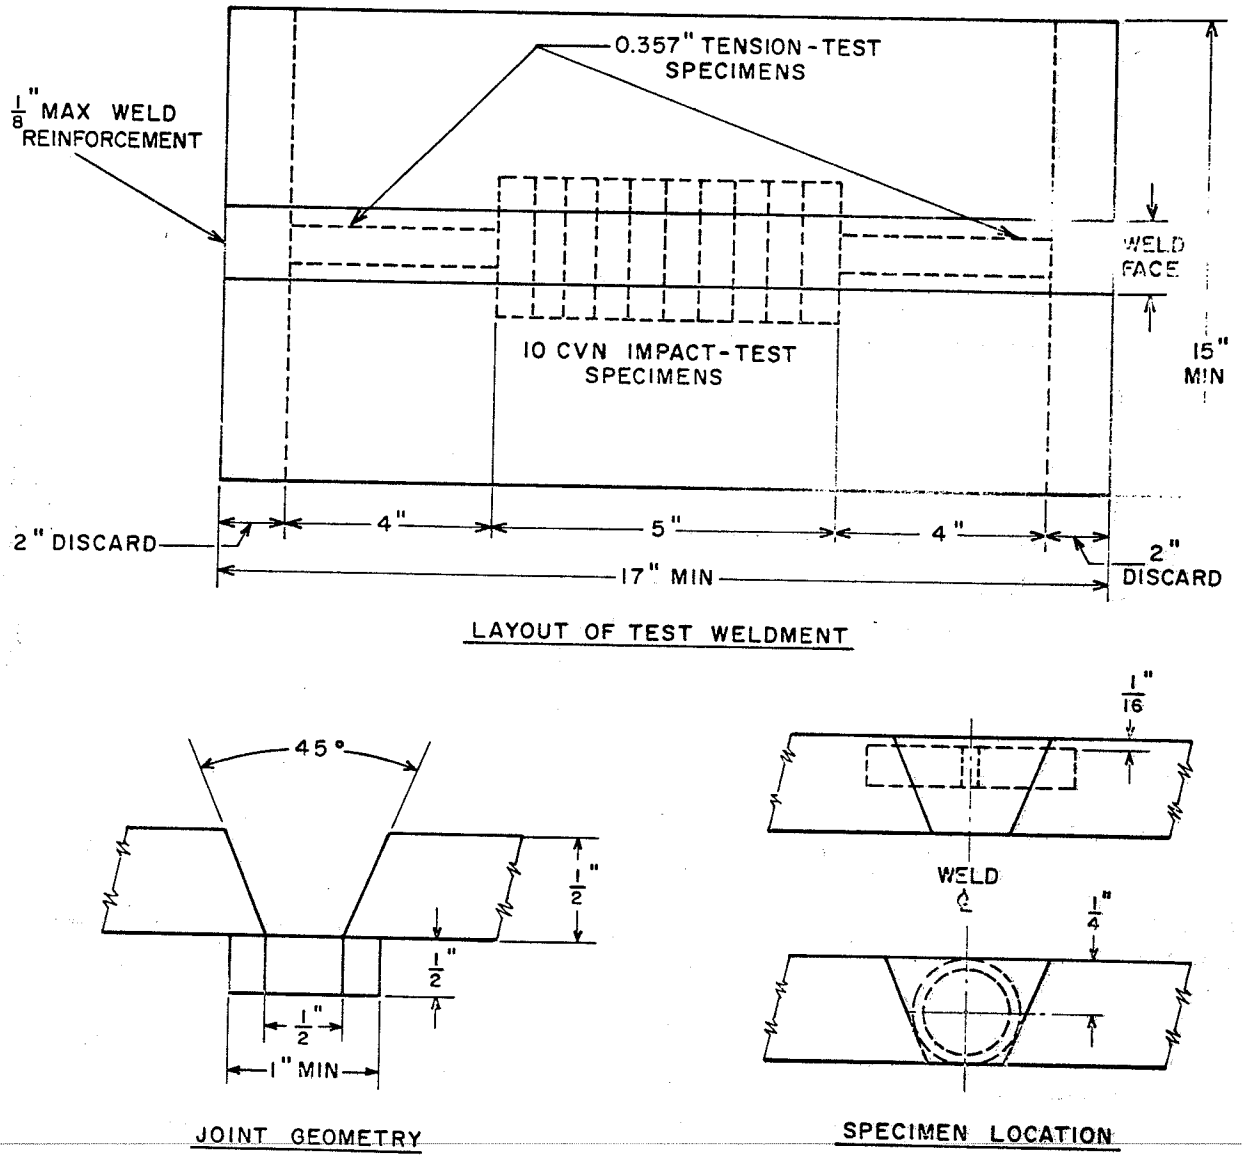


Figure 2 - Vertical groove-weld metal test (for 1/8 inch and 5/32 inch diameter electrodes)

Electrode size	T	Y	Tension Test Specimen
1/8	1/2 1/	1/4	0.357
5/32	3/4	3/8	0.505

1/ Plate thickness shall be increased to 3/4" for qualification testing.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

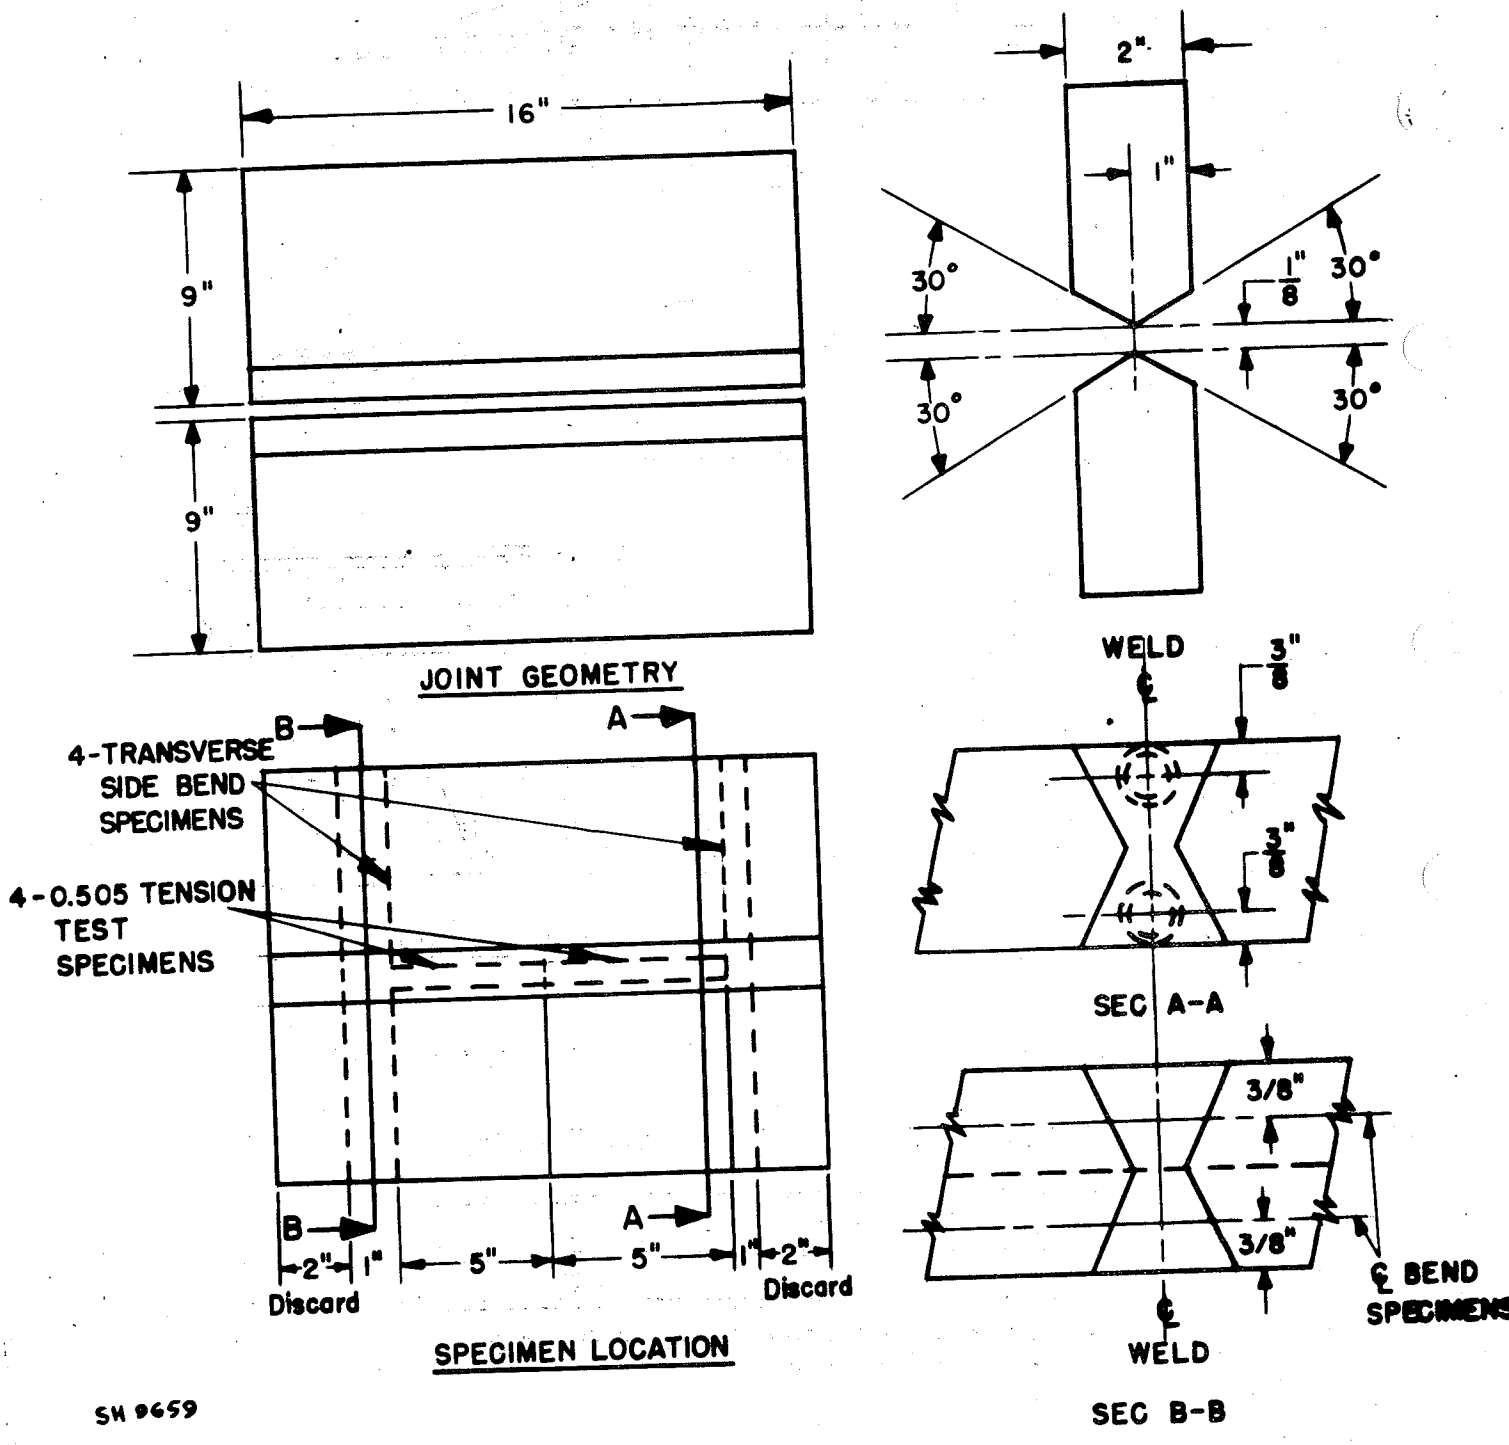


Figure 3 - Restraint-cracking-weld metal test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.

CERTIFICATION OF QUALITY CONFORMANCE TESTS 1/

Manufacturer or Distributor _____

Address _____

Customer's Name _____

Date

Customer's Order No. _____

Specification MIL- _____

Type MIL- _____

Core Wire Heat No. _____

Diameter & Length _____

Lot Identification MIL-E-0022200E Para. _____

Inspection Level _____

Lot No. _____

Wet Batch No. _____

Chemical Analysis (Complete)

Carbon _____

Manganese _____

Phosphorus _____

Sulfur _____

Silicon _____

Nickel _____

Chromium _____

Molybdenum _____

Vanadium _____

Yield Strength (0.2% offset method)

Tensile Strength

Elongation (%)

Reduction of Area (%)

Mechanical Test As-Welded

_____

_____

_____

_____

CHARPY IMPACTS

1. _____		1. _____
2. _____		2. _____
3. _____		3. _____
4. _____		4. _____
5. _____		5. _____

Chemistry was taken from: ☐ Chem Pad ☐ Groove Weld

X-Ray Results _____

Concentricity (%) _____

Covering Moisture _____

Grinding During 8a Test Plate Preparation 2/

Groove Weld Test

Figure No.	1 or 2	3	Chem Pad
Amperage	_____	_____	_____

Operator Error (Layer Nos.) _____

Time delay per pass _____

We hereby certify that the above material has been tested in accordance with the listed specification and is in conformance with all requirements.

_____

1/ This form is applicable to the quality conformance tests required for each lot. One copy of the quality conformance certificate (figure 5) shall be forwarded for each lot that is included in the shipment.

2/ See paragraphs 3.5.7 and 3.9 of MIL-E-22200.

Figure 4

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T11:24Z
Check the source to verify that this is the current version before use.