MILITARY SPECIFICATION

HOSE ASSEMBLY, ELASTOMERIC:

FUEL DISCHARGE, COLLAPSIBLE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers collapsible, elastomeric discharge hose assemblies.

1.2 Classification. The collapsible discharge hose assemblies are of the following sizes and types as specified in 1.2.1:

Size (Inside diameter)	Dash No.
2-inch	-08
4-inch	-11
6-inch	-32


Type A - Cam-locking type couplings
Type B - Single groove, snap lock couplings

1.2.1 Part number. The part number for the hose assemblies is as follows (see 6.2).

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research, Development, and Engineering Center, ATTN: STRBE-TSE, Fort Belvoir, VA 22060-5606 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 4720
DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

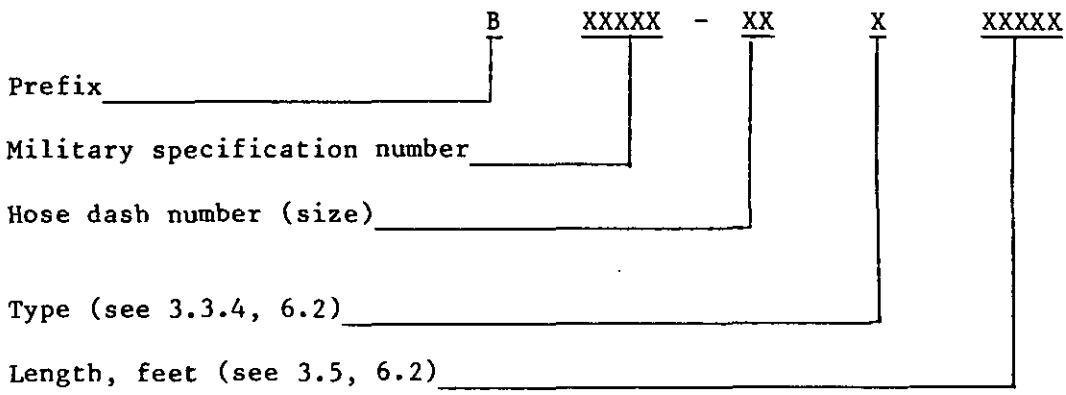

Example: BXXXXX - 08A500

A hose assembly conforming to MIL-H-53073 having a 2-inch inside diameter with cam-locking type couplings and a length of 500 feet.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. The following specifications and standards form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DoDISS) and supplement thereto, cited in the solicitation.

SPECIFICATIONS

FEDERAL

QQ-S-766	- Steel Plates, Sheets, and Strip-Corrosion Resisting.
VV-F-800	- Fuel Oil, Diesel.
VV-G-1690	- Gasoline Automotive, Leaded or Unleaded.
WW-C-440	- Clamps, Hose, (Low-Pressure).

MILITARY

MIL-P-775	- Packaging of Hose, Hose Assemblies; Rubber, Plastic, Fabric, or Metal (Including Tubing); and Fittings, Nozzles and Strainers.
MIL-G-3056	- Gasoline, Automotive, Combat.
MIL-G-5572	- Gasoline, Aviation: Grades 80/87, 100/130, 115/45.
MIL-C-10387	- Couplings, Clamp, Pipe, with Bolts and Synthetic Rubber Gasket, for Pipe and Tube.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:58Z
Check the source to verify that this is the current version before use.

MIL-T-5624 - Turbine Fuel, Aviation, Grades JP-4 and JP-5.
MIL-T-83133 - Turbine Fuel, Aviation, Kerosene Type, Grade JP-8.

STANDARDS

FEDERAL

FED-STD-595 - Colors.

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-889 - Dissimilar Metals.
MIL-STD-1472 - Human Engineering Design Criteria for Military Systems, Equipment, and Facilities.
MS27021 - Coupling Half, Quick Disconnect, Cam-Locking Type, Male, Hose Shank, Type II.
MS27025 - Coupling Half, Quick Disconnect, Cam-Locking Type, Female, Hose Shank, Type VI.

(Copies of specifications and standards required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS shall be the issue of the non-Government documents which is current on the date of the solicitation.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 380 - Rubber Hose Testing.
D 381 - Existent Gum in Fuels by Jet Evaporation.
D 412 - Rubber Properties in Tension.
D 413 - Rubber Property - Adhesion to Flexible Substrate.
D 471 - Rubber Property - Effect of Liquids.
D 518 - Rubber Deterioration - Surface Cracking.
D 1053 - Measuring Rubber Property - Stiffening at Low Temperature Using A Torsional Wire Apparatus.
D 1149 - Rubber Deterioration - Surface Ozone Cracking in a Chamber (Flat Specimens).

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

(Non-Government standards and other publications are normally available from the organizations which prepare or which distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. Unless otherwise specified (see 6.2), a sample shall be subjected to first article inspection (see 4.3 and 6.3). Any changes or deviations of hose assemblies from the approved first article during production will be subject to the approval of the contracting officer. Approval of the first article will not relieve the contractor of his obligation to furnish hose assemblies conforming to this specification.

3.2 Material. Material shall be as specified herein. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification.

3.2.1 Material deterioration prevention and control. The hose assemblies shall be fabricated from compatible materials, inherently corrosion resistant or treated to provide protection against the various forms of corrosion and deterioration that may be encountered in any of the applicable operating and storage environments to which the hose assemblies may be exposed.

3.2.1.1 Dissimilar metals. Dissimilar metals shall not be used in intimate contact with each other unless protected against galvanic corrosion. Dissimilar metals and methods of protection are defined and detailed in MIL-STD-889.

3.2.1.2 Identification of materials and finishes. The contractor shall identify the specific material, material finish or treatment for use with component and subcomponent, and shall make information available upon request to the contracting officer or designated representative.

3.2.1.3 Recovered materials. For the purpose of this requirement, recovered materials are those materials which have been collected from solid waste and reprocessed to become a source of raw materials, as distinguished from virgin raw materials. The components, pieces and parts incorporated in the hose assemblies may be newly fabricated from recovered materials to the maximum extent practicable, provided the hose assemblies produced meets all other requirements of this specification. Used, rebuilt or remanufactured components, pieces and parts shall not be incorporated in the hose assemblies.

3.3 Design and construction. The hose assemblies shall consist of collapsible, reinforced synthetic rubber hose with attached cam-locking type coupling halves.

Source: https://assist.dla.mil -- Downloaded: 202640-22T21:58Z
Check the source to verify that this is the currentversion before use.

3.3.1 Hose. The hose shall be constructed of a compounded inner tube, a synthetic fiber reinforcement, and a compounded cover.

3.3.2 Tube. The tube shall be fabricated from a synthetic compound. The compound shall be resistant to aromatic hydrocarbon fuels, and shall not have any deleterious effects upon all types and grades of fuels conforming to MIL-G-3056 and VV-G-1690 (automotive gasoline), MIL-G-5572 (aviation gasoline), MIL-T-5624 and MIL-T-83133 (jet fuels), and VV-F-800 (diesel fuel). The tube shall be smooth, free from pits, and of uniform thickness. The thickness of the tube shall be not less than 1/16 inch.

3.3.3 Cover. The cover shall be fabricated from a synthetic compound. The cover shall be uniform in thickness and shall be not less than 1/16 inch. The color of the cover shall be sand matte in accordance with FED-STD-595, color chip 30277.

3.3.4 Coupling halves. The coupling halves shall be type A or type B as specified (see 1.2 and 6.2). Coupling halves shall be securely attached to the hose to form a permanent electric bond with the static wires.

3.3.4.1 Type A, cam-locking types. Type A cam-locking type coupling halves with specified gaskets shall be furnished with each size of hose as shown in table I, except that the working pressure rating shall be 150 psi (pounds per square inch).

3.3.4.2 Type B, single grooved, snap lock couplings.

3.3.4.2.1 Hose to grooved adapter. For type B couplings, a one piece aluminum adapter shall be provided with grooved end conforming to MIL-C-10387, figure 2. For each size, the dimensions shown in MIL-C-10387 for the equivalent nominal pipe size shall be used. The nipple shall conform to the dimensions shown on MS27021, for the "C" length only. The appropriate MS27021 dash number for each size of hose shall be as specified in table I.

3.3.4.2.2 Grooved coupling. The grooved couplings shall conform to MIL-C-10387, class A. For each size, the equivalent nominal pipe size from MIL-C-10387 shall be used.

3.3.5 Hose clamps. Each cam-locking type coupling half shall be banded to the hose with clamps conforming to WW-C-440, type H, except the clamp material shall be corrosion-resistant steel conforming to QQ-S-766, class 201, condition A, and the hydraulic test pressure shall be 225 psi. Quantity and size of clamps for each size hose shall be as shown in table I. When installed and locked the clamps shall have no protruding ends.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

TABLE I. Coupling halves and clamps.

Hose dash no.	Hose size nom.	Couplings		Clamps	
		Female	Male	Size width	Qty. per cplg.
08	2	MS27025-11	MS27021-11	5/8	2
11	4	MS27025-17	MS27021-17	3/4	2
32	6	MS27025-21	MS27021-21	3/4	3

3.3.6 Reinforcement. The reinforcement material shall be one or more plies of braided or spiraled synthetic fiber cord or fabric which shall be evenly and firmly fabricated and thoroughly impregnated with synthetic rubber compound which shall cause the plies to adhere firmly to each other and to the tube and cover. The reinforcement material shall be applied by braiding, looming, or spiral winding twist to provide a balanced design. The reinforcement shall be evenly and firmly fabricated, and shall be free from defects, dirt, knots, lumps, and irregularities of twist so that the completed hose shall comply with all the applicable requirements herein.

3.3.7 Static wires. Two helically wound, static electric bonding wires shall be embedded within or between plies to form an angle of not less than 45 degrees to the longitudinal axis of the hose. The wires shall not break when the hose is coiled or subjected to internal or external pressure. The wires may be either braided or stranded and shall have an area equivalent to:

Stranded - 7 strands No. 31B and S gauge (0.0089 inch diameter)

Braided - 48 strands No. 36B and S gauge (0.005 inch diameter)

The static wire shall be continuous to effect an electric bond between both ends of the hose when tested in accordance with 4.5.2.1.

3.4 Physical and chemical properties.

3.4.1 Hydrostatic pressure. When tested as specified in 4.5.2.1, the hose with couplings attached shall not leak nor show any imperfections in either the hose or couplings.

3.4.1.1 Length change and twist. When tested as specified in 4.5.2.8, the length of hose shall not change more than ±3 percent and shall not twist either clockwise or counterclockwise more than 1 degree per foot of length.

3.4.1.2 Minimum burst. When tested as specified in 4.5.2.2, each type of hose shall have a minimum burst pressure as specified in table II.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:58Z
Check the source to verify that this is the current version before use.

TABLE II. Burst and working pressures.

Hose dash no.	Size I.D. (inches nom.)	Burst pressure psi (min.)	Working pressure psi
08	2	400	100
11	4	600	150
32	6	600	150

3.4.2 Tensile strength. When tested as specified in 4.5.2.3.1, the tensile strength of the tube shall be not less than 1,250 pounds force per square inch psi and the tensile strength of the cover shall be not less than 1,000 psi. The tensile strength of the tube and cover after fuel immersion shall be not less than 40 percent or less than 600 psi (whichever is greater) of the tensile strength obtained before immersion when tested as specified in 4.5.2.3.2.

3.4.2.1 Tensile strength after water immersion. When tested as specified in 4.5.2.3.3, the tensile strength of the tube and cover after 14 day water immersion shall be not less than 40 percent or less than 600 psi (whichever is greater) of the tensile strength obtained before immersion. The tensile strength after 42 day water immersion shall be not less than 25 percent or less than 300 psi (whichever is greater) of the tensile strength before immersion.

3.4.3 Ultimate elongation. The ultimate elongation of the tube and cover shall be not less than 200 percent or, when tested as specified in 4.5.2.3.2, shall be not less than 40 percent of the original elongation obtained before fuel immersion.

3.4.3.1 Ultimate elongation after water immersion. The ultimate elongation after 14 day water immersion, when tested as specified in 4.5.2.3.3, shall be not less than 40 percent of the original elongation obtained before immersion. The ultimate elongation after 42 days shall be not less than 25 percent of the original elongation obtained before immersion.

3.4.4 Adhesion.

3.4.4.1 Original. When tested as specified in 4.5.2.3.4, the original adhesion between tube and plies, and between the cover and the plies, and between the cover and end reinforcement, shall be not less than 10 pounds force (lb_f).

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

3.4.4.2 After fill test. When tested as specified in 4.5.2.3.5, the adhesion between the tube and plies, between the plies, and between the cover and the plies and between the cover and end reinforcement, shall be not less than 6 lb_f.

3.4.5 Volume increase. When tested as specified in 4.5.2.4, the volume increase of the tube specimen after immersion in test fluid shall not exceed 40 percent, and the volume increase of the cover specimen shall not exceed 70 percent.

3.4.6 Low temperature flexibility. When tested as specified in 4.5.2.5, the relative torsional modulus for the inner tube and the outer cover shall be not greater than 5 at -32 °C (-25.6 °F).

3.4.7 Existent gum content. When tested as specified in 4.5.2.6, the remainder shall be not more than 20 milligrams per 100 milliliters of test fluid.

3.4.8 Ozone resistance. When tested as specified in 4.5.2.7, the hose cover material shall show no evidence of cracking, checking, or irregularities at the end of the exposure time when viewed under 7 power magnification.

3.5 Quantities, dimensions, and weights. The quantities and lengths of the hose shall be as specified (see 6.2) and shall be the actual hose length exclusive of the couplings. A tolerance in length of ±2 percent will be permitted. This hose shall be furnished in the diameters and weights shown in table III.

TABLE III. Diameters and weights.

Size (ID) inches +1/32 inch)		Outside diameter (inches at ends)	Pounds per foot (maximum)
Dash no.	Size		
08	2	2-9/16, +1/8 or -1/16	1-1/4
11	4	4-3/4, +1/8 or -1/16	1-3/4
32	6	6-3/8, +1/8 or -1/16	2-5/8

3.6 Identification marking. Each length of hose shall be branded with manufacturer's name or trademark, the quarter and year of manufacture, the manufacturer's serial number, the type, the working pressure, and the words "Hose, Liquid Petroleum Fuels, Dispensing, Collapsible". The hoses shall be branded with the manufacturer's standard working pressures for the specific type and size hose supplied, and shall be rated at the working pressures indicated in

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

table II. The letters shall be molded, either recessed or in relief, shall be of a contrasting color to the hose color, and shall be not less than 1/4-inch high. Letter characteristics shall be in accordance with MIL-STD-1472. Hoses shall be branded at 10-foot intervals or by continuous-impression branding, provided that the pattern will be repeated every 5 feet or less.

3.7 Workmanship. The hose assemblies shall conform to the quality requirements specified herein with no cuts, nicks, bruised, blisters, sharp edges, or lumps, and shall be clean and smooth. Each hose assembly shall be free from any other workmanship deficiencies that could impair the function or serviceability of the hose or endfitting in its intended use.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).

4.3 First article inspection.

4.3.1 Examination. The first article hose assembly shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

4.3.2 Tests. The first article hose assembly shall be tested as specified in 4.5.2.1 through 4.5.2.9, inclusive. Failure of any test shall be cause for rejection of the hose assembly.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection.

4.4.1 Lot. Each lot shall consist of all units of hose assemblies of the same size manufactured under the same conditions and at the same time, and offered to the Government at one time.

4.4.2 Sampling. Sampling of hose and hose assemblies for examination and tests shall be in accordance with MIL-STD-105, inspection level S-2.

4.4.3 Examination. Samples selected in accordance with 4.4.2 shall be examined as specified in 4.5.1. Acceptable quality level (AQL) shall be 1.0 percent defective.

4.4.4 Tests.

4.4.4.1 Individual. Each hose assembly shall be tested as specified in 4.6.2.1. Failure of the test shall be cause for rejection.

4.4.4.2 Samples. Samples selected in accordance with 4.4.2 shall be tested as specified in 4.5.2.1 through 4.5.2.7, inclusive. AQL shall be 1.0 percent defective.

4.5 Inspection procedure.

4.5.1 Examination. The hose assembly shall be examined as specified herein for the following major defects:

101. Materials not as specified.
102. Materials not resistant to corrosion and deterioration, or treated to be resistant to corrosion and deterioration for the applicable storage and operating environments.
103. Dissimilar metals as defined in MIL-STD-889 are not effectively insulated from each other.
104. Contractor does not have documentation available for identification of material, material finishes, or treatment.
105. Used, rebuilt or remanufactured components, pieces, or parts incorporated in the hose assemblies.
106. Diameters and weights not as specified.
107. Couplings not as specified.
108. Hose clamp not as specified.
109. Length of hose not as specified.
110. Design and construction not as specified.
111. Identification marking missing, illegible, or not as specified.
112. Workmanship not as specified.
113. Color not as specified.

4.5.2 Tests.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the currentversion before use.

4.5.2.1 Hydrostatic. Each length of hose, with fittings such as couplings and adapters attached, shall be subjected to hydrostatic pressure test in accordance with ASTM D 380 and as specified in table IV. The electric bond shall be determined while full test pressure is applied. Nonconformance to 3.3.7 and 3.4.1 shall constitute failure of this test.

TABLE IV. Hoses sizes and hydrostatic test pressures.

Dash no.	Size nom.	Hydrostatic test psi
08	2	225
11	4	225
32	6	225

4.5.2.2 Minimum burst. A sample of not less than 3 feet nor more than 6 feet shall be cut from the one length selected from each 100 lengths for burst and physical tests. The hose shall be subjected to a hydrostatic test pressure in accordance with ASTM D 380 and as specified in table II. The pressure shall be supplied at a uniform rate sufficient to develop the test pressure in 10 seconds, ±2 seconds. Nonconformance to 3.4.1.2 shall constitute failure of this test. The remaining section of hose from which the test sample has been taken shall be accepted as a full length, provided the sample meets all the requirements of the specification.

4.5.2.3 Tensile strength, elongation, and adhesion.

4.5.2.3.1 Tensile and elongation specimens. Tensile and elongation specimens shall be tested in accordance with ASTM D 412 method A. The immersion fuel test shall be performed in accordance with ASTM D 471, utilizing test fluid consisting of 60 percent of medium no. 4 (low swelling), 25 percent of medium no. 8 (toluene), and 15 percent of medium no. 9 (xylene). Die "C" shall be used for cutting test specimens. The tube specimens shall be buffed to not less than 0.050-inch thickness. Nonconformance to 3.4.2 and 3.4.3 shall constitute failure of this test.

4.5.2.3.2 Tensile strength and ultimate elongation after fuel immersion. Tensile strength and ultimate elongation after fuel immersion shall be determined in accordance with ASTM D 471. The immersion test fluid medium shall be as specified in 4.5.2.3.1 at 23 °C for 46 hours. Nonconformance to 3.4.2 and 3.4.3 shall constitute failure of this test.

4.5.2.3.3 Tensile strength and ultimate elongation after water immersion. Tensile strength and ultimate elongation after water immersion shall be determined in accordance with ASTM D 471. The immersion test shall be performed in accordance with ASTM D 471, utilizing water as a test fluid. One specimen shall be subjected to water immersion test for 14 days at 23 °C. One specimen shall be subjected to water immersion for 42 days at 23 °C. Nonconformance to 3.4.2.1 and 3.4.3.1 shall constitute failure of this test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-22T21:58Z
Check the source to verify that this is the current version before use.

4.5.2.3.4 Original adhesion test. A dry specimen of hose material shall be tested in accordance with ASTM D 413 machine method. Nonconformance to 3.4.4.1 shall constitute failure of this test.

4.5.2.3.5 Adhesion after filling. A 12-inch length of the hose shall be stoppered and filled with the test fluid specified in 4.5.2.3.1. The section of hose with the test fluid shall be maintained at a temperature of +23 ±3 °C (+73 ±5 °F) for not less than 48 hours. Ring specimens shall be cut from the 12-inch length of hose and tested in accordance with ASTM D 413 machine method within 15 minutes after the removal of the test fluid. Nonconformance to 3.4.4.2 shall constitute failure of this test.

4.5.2.4 Volume increase. Volume increase test shall be determined in accordance with ASTM D 471 with the test fluid specified in 4.5.2.3.1 at 23 °C for 46 hours. Nonconformance to 3.4.5 shall constitute failure of this test.

4.5.2.5 Low temperature flexibility. The test for low temperature flexibility shall be made in accordance with ASTM D 1053. The low temperature test shall be determined after the samples have been conditioned 7 at days -32 °C (-25.6 °F). Nonconformance to 3.4.6 shall constitute failure of this test.

4.5.2.6 Existent gum. A test sample of hose, not less than 14 inches long, shall be selected and the bottom plugged with a clean corrosion-resisting steel cylinder 2 inches long secured in place with a clamp. The sample shall be filled to within 2 inches of the top with test fluid specified in 4.5.2.3.1. The top end of the hose shall be plugged in a manner similar to the bottom. The sample shall then be stored in a vertical position for 7 days at an ambient temperature of +38 ±1 °C (100 ±2 °F). At the end of each 24 hours, the fuel in the sample shall be agitated for 5 minutes by moving the hose back and forth from a vertical to a horizontal position at a rate of 2 cycles per minute. At the end of the 7-day storage period, the fuel shall again be agitated in the sample for 5 minutes and immediately removed from the hose. The removed fuel shall be tested for existent gum in accordance with the air-jet solvent wash method of ASTM D 381. A blank shall be run on the test fluid at the same time and by the same method. The existent gum of the blank fluid shall be subtracted from the existent gum obtained from the test fluid removed from the hose. Nonconformance to 3.4.7 shall constitute failure of the test.

4.5.2.7 Ozone resistance. Specimens of the cover, prepared as described in ASTM D 518 procedure A, shall be mounted in a 20-percent elongated position and tested in accordance with ASTM D 1149. After conditioning for 24 hours in an ozone-free atmosphere, the mounted specimens shall be exposed for 336 hours at 40 ±1 °C (104 ±1 °F), to an atmosphere containing 50 parts, ±10 parts, per hundred million (pphm) of ozone. Upon completion of the test, the specimens shall be examined. Nonconformance to 3.4.8 shall constitute failure of this test.

4.5.2.8 Length change and twist. A measurement of the original length of each length of hose shall be made, with the hose laid out in a straight horizontal position, after a pressure of 10 psi is applied and maintained. With a crayon or soft pencil, make a mark on the top surface of the hose at each end

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

adjacent to the coupling. These marks are used as a means of measuring the amount of twist during the test. The pressure shall then be increased to 100 psi and held for not less than 30 seconds. With the pressure still maintained, the final length measurement and the final twist measurement shall be taken. The percent change in length shall be calculated as plus for increase and minus for decrease in length. Nonconformance to 3.4.1.1 shall constitute failure of this test.

4.5.2.9 Hydrostatic pressure with kerosene. A sample of hose, not less than 3 feet and not greater than 6 feet with fittings such as couplings and adapters attached, shall be subjected to a hydrostatic pressure test in accordance with ASTM D 380 and as specified in table IV, except that kerosene shall be used as the test fluid. Nonconformance to 3.4.1 shall constitute failure of this test.

4.6 Inspection of packaging. The packaging shall be examined to determine compliance with the quality assurance provisions of MIL-P-775 and with the requirements of section 5 herein.

4.7 Component and material inspection. Components and materials used in the manufacturing, testing, and packaging of the hose assemblies shall be inspected in accordance with the applicable referenced documents. Nonconformance to the applicable referenced documents shall be cause for rejection.

5. PACKAGING

5.1 Preservation. Preservatives shall not be used for hoses covered by this specification. Preservation shall be level A or level C as specified (see 6.2), and shall be in accordance with the applicable preservation-packing requirements of MIL-P-775.

5.2 Packing. Packing shall be level A, level B or level C as specified (see 6.2) and shall be in accordance with the applicable packing requirements of MIL-P-775.

5.3 Marking. Marking shall be in accordance with all the marking requirements of MIL-P-775.

6. NOTES

6.1 Intended use. The hose assemblies covered by this specification are intended for transferring automotive and aviation gasoline, JP-4 or JP-5 jet fuel, or diesel fuels.

6.2 Ordering data. Procurement requirements should specify the following:

a. Title, number, and date of this specification.
b. Size required (see 1.2).
c. Type of coupling (see 1.2 and 3.3.4).
d. Specification part number required (see 1.2.1).

Source: https://assist.dla.mil -- Downloaded: 202640-22T21:58Z
Check the source to verify that this is the current version before use.

e. When first article is required for inspection and approval (see 3.1, 4.3, and 6.3).
f. Quantity and length of hose assembly (see 3.5).
g. Level of packaging and packing required (see 5.1 and 5.2).

6.3 First article. When a first article inspection is required, the items should be a preproduction model. The first article should consist of one hose assembly. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, tests, and approval of the first article test results and disposition of the first article.

6.4 Subject term (key term) listing.

Collapsible
Discharge
Fuel
Hose

Custodians:
Army - ME
Navy - YD
Air Force - 99

Preparing activity:
Army - ME

Project 4720-0758

Review activities:
Navy - SH
Air Force - 82
DLA - CS

User activity:
Navy - MC

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the currentversion before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Belvoir RDE Center
ATTN: STRBE-TSE
Fort Belvoir, VA 22060-5606

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-H-53073	Hose Assembly, Elastomeric: Fuel Discharge, Collapsible

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 202610-22T21:58Z
Check the source to verify that this is the current version before use.