MILITARY SPECIFICATION

TAPE, TEXTILE, NYLON, LANDBASED
ARRESTING GEAR, 7 INCH

This amendment forms a part of Military Specification MIL-T-81521A(AS), dated 24 April 1969.

PAGE 1

* 2.1, delete in its entirety and substitute the following:

"2.1 The following documents of the issue in effect on date of invitation for bids or request for proposal form a part of the specification to the extent specified herein.

SPECIFICATIONS

Military

MIL-B-131	-Barrier Material, Watervaporproof, Flexible, Heat Sealable

STANDARDS

Federal

FED-STD-191	-Textile Test Methods

Military

MIL-STD-105	-Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	-Marking for Shipment and Storage
MIL-STD-1480	-Color Codes for Webbing, Textile; Manufacturers' Identification

FSC 8315

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

DRAWINGS

Naval Air Engineering Center

8506730	-Tape Reel Assembly, Tape Installation Method (7 Inch Tape)
508306	-Reel, Tape Assembly

(When requesting specifications, standards, and publications, refer to both title and number. Copies of this specification and applicable documents may be obtained upon application to the Commanding Officer, Naval Publications and Forms Center, 5801 Tabor Avenue, Philadelphia, Pennsylvania 19120. All other documents should be obtained from the procuring activity or as directed by the contracting officer.)"

PAGE 2

2.2 Delete the following: "U.S. Air Force Specification Bulletin No. 90 Color Codes Manufacturers' Identification, Nylon Webbing

(Application for copies should be addressed to the procuring activity or as directed by the contracting officer.)"

PAGE 3

TABLE I: Under "REQUIREMENT" column and after "70,000" insert "1/."

At bottom of table insert the following: "1/ A failure at or above 70,000 pounds tension or a jaw break at or above 70,000 pounds will be considered acceptable. A failure below 70,000 pounds tension or a jaw break below 70,000 pounds will be considered unacceptable."

PAGE 5

3.5, line 2: Delete entire line and insert "contain either 1375 plus or minus 5 foot or 1500 plus or minus 5 foot lengths as speci-"

3.5, line 4: Delete "25" and insert "10."

3.6.1, delete in its entirety and substitute the following:

"3.6.1 The tape shall be impregnated with polyvinyl butyral plasticized with butyl ricinoleate (see 6.5). The resin shall contain carbon black in a ratio of 3 parts carbon black to 100 parts resin. The resin shall be applied from a water dispersion, dried and cured so as to form a firmly adherent and evenly distributed deposit or coating on the yarns of the tape (see 6.6)."

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

3.6.3, delete in its entirety.

3.7.1, delete in its entirety and substitute the following:

"3.7.1 Manufacturer's identification. Each manufacturer shall incorporate as part of the binder warp at the center of the tape two ends dyed to match the shade assigned to the manufacturer in accordance with MIL-STD-1480. A producer not listed in MIL-STD-1480 shall apply to the Commander, US Army Natick Research and Development Command, Natick, Massachusetts 01760, for assignment of color coding. The colorfastness of this yarn shall be rated as "Fair" or "Good" when tested as specified in Table II."

PAGE 6

4.1, delete and substitute:

"4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements."

PAGE 7

4.4.4.1, delete (a) and (b) and substitute:

"(a) Yard-by-yard. Prior to the addition of resin as specified in 3.6, a one yard unit of each production tape length shall be inspected as specified in 4.5.4.1 and 4,5.4.1.1 at intervals of approximately 40 feet.

(b) Overall. Each production tape length shall be examined for the defects specified in 4.5.4.2."

4.5.1, line 1: Delete "CCC-T-191" and substitute "FED-STD-191".

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

TABLE II, delete in its entirety and substitute the following:

* TABLE II. Tests and test methods

SAMPLING PLAN	TEST	METHOD	
		FED-STD-191 METHOD NO.	OTHER
A	Width	5020	
A	Thickness	5030 1/	
A	Weight	5040	
A	Length	5010	
A	Breaking strength		4.5.2
A	Extractable matter		4.5.3
A	Resin	5/	4.6
B	Ends in warp		
	Ground		Visual
	Binder		Visual
	Stuffer		Visual
B	Filling, yarn per in.	5050	
B	Yarn ply		
	Ground		Visual
	Binder		Visual
	Stuffer		Visual
	Filling		Visual
B	Twist, turn per in.		
	Ground	4054 4/	
	Binder	4054 4/	

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

TABLE II. Tests and test methods -(Continued)

SAMPLING PLAN	TEST	METHOD	
		FED-STD-191 METHOD NO.	OTHER
	Stuffer	4054 4/	
	Filling	4054 4/	
B	Weave		Figure 1
C	Colorfastness to laundering	5614 2/ 3/	
C	Melting point	1534 5/	4.6
C	Denier	4021 5/	4.6
C	Filament count	5/	Visual
	Yard-by-yard		4.5.4.1
	Overall		4.5.4.2

1/ Except that a six ounce total load shall be applied and the presser foot diameter shall be 3/8 inch.
2/ Applicable only to manufacturer's identification yarns.
3/ Except that nylon color transfer cloth shall be used.
4/ One test on each 5 yarns.
5/ Unless otherwise specified, a supplier's certificate of compliance is required and will be accepted for the requirement (See 4.6).

4.5.2.1, line 5: Delete "3 feet 6 inches" and insert "18 inches."

4.5.2.2, Delete entire paragraph and insert the following:

"4.5.2.2 Ultimate strength test. A test specimen 10 feet long shall be cut from each tape as noted in 4.5.2.3. The specimen shall be load tested."

Source: https://assist.dla.mil -- Downloaded: 202610-23T05:38Z
Check the source to verify that this is the current version before use.

4.5.2.3, delete the entire paragraph and substitute the following:

"4.5.2.3. Method of sampling for breaking strength test. The contract or order shall specify either 1375 or 1500 foot lengths, or both. The first section of tape leaving a loom run shall have a 10 foot sample removed from the lead end. After this every 1375 foot or 1500 foot section shall have 10 feet removed immediately following every production tape. The rolls of tape shall be marked consecutively as they leave the loom, with the 10 foot specimens marked identically with the rolls of tape to which they apply. Test the first 10 foot specimen leaving the loom run and every 10 foot specimen thereafter. Then, the tests shall result in one of the following four possibilities: (see FIGURE 2.)

4.4.2.3.1 Test Result I

If the three specimens pass the strength test, the two production tapes in between are satisfactory.

4.5.2.3.2. Test Result II

If the first specimen leaving the loom run fails the strength test and the other two specimens pass the strength test, the second production tape is satisfactory but a 10 foot specimen must then be cut from the lead end of the first production tape and tested in order to determine if the first tape is satisfactory. If the specimen should fail, the first production tape is unsatisfactory. If the specimen should pass, the first production tape is satisfactory.

4.5.2.3.3 Test Result III

If the second specimen fails and the first and third pass the strength test, a 10 foot specimen must be taken from the trailing end of the first production tape and the leading end of the second tape. If these two specimens pass, both production tapes are satisfactory. If one or both of the specimens fail the strength test, the production tape containing the failed sample is unsatisfactory.

4.5.2.3.4 Test Result IV

If all specimens fail, proceed with additional tests as outlined above to prove the strength of individual tapes. (Any deviation from the above described procedures shall only be made upon approval by the Commanding Officer, Naval Air Engineering Center, Attn: Code 913, Lakehurst, NJ 08733.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

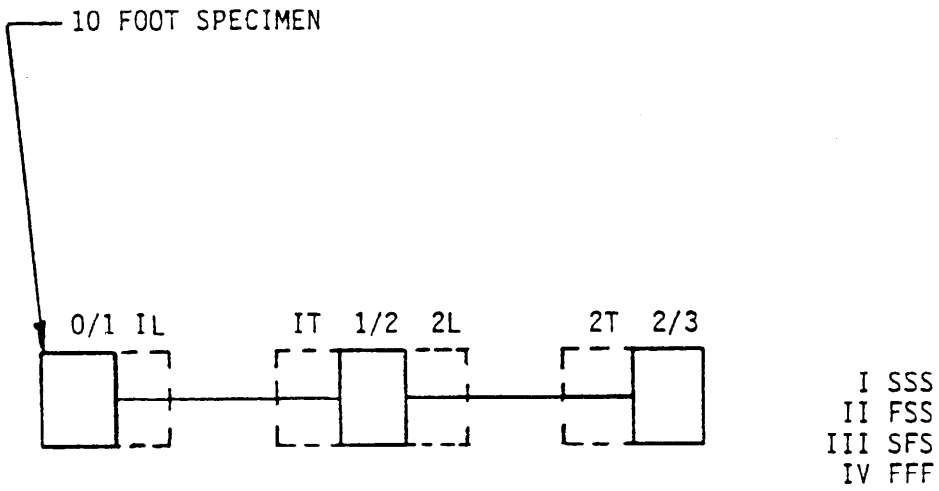


FIGURE 2. 2-Tape loom run

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

PAGE 11

TABLE III, line 8: Delete "of" and insert "or."

PAGE 13

TABLE III, under "Defects" column, delete the defects along with the entire notation as follows:

"Mispick, Double Pick
Identification Threads"

TABLE III, under "Defects" column, add the following defects:

DEFECTS	DESCRIPTION	CRITICAL	MAJOR	MINOR
Double pick	Two or more across the full width	X		
Mispick	Single across the full width			X
Identification thread				
	Misplaced			X
	Missing		X	

PAGE 14

4.6, delete the entire paragraph and substitute:

* "4.6 Type of nylon, melting point, resin, denier and filament count. A certificate of compliance shall be submitted from the yarn manufacturer and will be accepted as proof that requirements for type of nylon, melting point, resin, denier, filament count, and bright, high tenacity, light and heat resistant nylon yarn are met. The certificate shall contain verifiable actual test data. If the approximate melting point of the specimens is not known before testing, it shall be determined by a trial run."

* 5.2, lines 4 and 5: Delete "MIL-B-81374 or MIL-B-13239, Type B-2, Class 1, Grade A" and substitute "MIL-B-131, class 1."

* 5.2, line 8: Delete "(see Figure 2)" and substitute "(see FIGURE 3)".

5.3 Add the following:

"CAUTION - Store inside only"

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T05:38Z
Check the source to verify that this is the current version before use.

PAGE 15

At the bottom of the page, delete "Figure 2" and substitute "FIGURE 3".

PAGE 16

6.3, last line: Delete "ATTN: NE-7, Philadelphia, Pennsylvania 19112" and substitute "ATTN: Code 913, Lakehurst, NJ 08733."

Add the following:

"6.5 Resin TR-5418 has proven to be equivalent or even superior to the material specified in 3.6.1. Resin TR-5418, a proprietary material which should not be construed as a sole endorsement, may be obtained from the Spraylat Corporation, 1 Park Avenue, New York, N.Y. 10016 (see 3.6.1).

6.6 Curing of the resin impregnated tape has been accomplished in the temperature range of 115.6 to 182.2°C (240° to 360°F) (see 3.6.1)."

NOTE: The margins of this amendment are marked with an asterisk to indicate where changes from the previous amendment were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous amendment.

Preparing Activity:
Navy - AS
(Project No. 8315-N266)

☆ U.S. GOVERNMENT PRINTING OFFICE: 1977 — 703-122/569

Source: https://assist.dla.mil -- Downloaded: 202610-23T05:38Z
Check the source to verify that this is the current version before use.