MIL-G-12803B(MR)
20 October 1976
SUPERSEDING
MIL-G-12803A(Ord)
24 May 1960

MILITARY SPECIFICATION

GASKET MATERIAL, NON-METALLIC

This specification is approved for use by the Army Materials and Mechanics Research Center, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers gasket stock made from non-metallic materials and suitable for general automotive, aeronautical and other mechanical applications. This specification does not cover molded gaskets, rubber or plastic sheet gaskets, which are covered by other specifications.

1.2 Classification. Gasket stocks shall be of the following types, dependent upon the nature of the principal fibrous or particulate reinforcing material:

Type 1 - Asbestos or other inorganic materials
Type 2 - Cork or cork-elastomeric materials
Type 3 - Cellulose or other organic materials


1.2.1 Identification number for mechanical and physical properties. The mechanical and physical properties for the types of gasket materials covered by this specification shall be specified by a six digit number prefixed by the letter "F" (for example, F125400). (Note: The identification number may also be referred to as a line "call-out" number.) In addition to the six digits, identification numbers shall include suffix letters A through Z, when applicable, to specify the gasket characteristics for sealability, creep relaxation, adhesion, corrosion, tensile strength, volume weight and thickness changes in ASTM oils and other physical and mechanical properties required (for example, F125400B2M4). Identification numbers for types 1, 2 and 3 gasket materials shall be determined in accordance with tables I and II of ASTM F 104, as specified (see 6.2 and 6.4).

FSC 5330

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Army Materials and Mechanics Research Center, Watertown, MA 02172 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Example: F125400B2E33M4

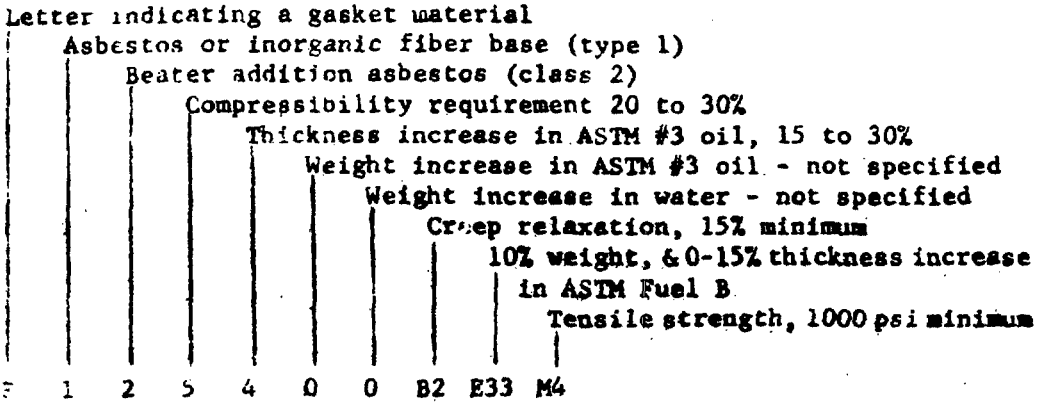

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on date of invitation for bids, or request for proposal, form a part of this specification to the extent specified herein.

SPECIFICATIONS

FEDERAL
- PPP-B-585 - Boxes, Wood, Wirebound
- PPP-B-591 - Boxes, Shipping, Fiberboard, Wood Cleated
- PPP-B-601 - Boxes, Wood Cleated Plywood
- PPP-B-621 - Boxes, Wood, Nailed and Lock Corner
- PPP-B-636 - Boxes, Shipping, Fiberboard
- PPP-B-1055 - Barrier Material, Waterproofed, Flexible
- PPP-T-76 - Tape, Pressure-Sensitive Adhesive, Paper (for Carton Sealing)

MILITARY
- MIL-L-10547 - Liners, Case, and Sheet, Overwrap; Water-Vaporproof, or Waterproof Flexible
- MIL-B-13239 - Barrier Materials, Waterproofed, Flexible, All Temperature, Heat Sealable

STANDARDS

FEDERAL
- Fed. Std. No. 356 - Commercial Packaging of Supplies and Equipment

MILITARY
- MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes
- MIL-STD-129 - Marking for Shipment and Storage
- MIL-STD-147 - Palletized and Containerized Unit Loads for 40" x 48" Pallets, Skids, Runners or Pallet Type Base
- MIL-STD-177 - Rubber Products, Terms for Visible Defects of

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM) STANDARDS

F 36 - Compressibility and Recovery of Gasket Materials
F 37 - Sealability of Gasket Materials
F 38 - Creep Relaxation of a Gasket Material
F 39 - Testing Compressed Asbestos Sheet Packing
F 64 - Corrosive and Adhesive Effects of Gasket Materials on Metal Surfaces
F 104 - Classification System for Nonmetallic Gasket Materials
F 146 - Fluid Resistance of Gasket Material
F 147 - Flexibility of Cork-Containing Gasket Materials
F 152 - Tension Testing of Non-Metallic Gasket Materials
G 21 - Resistance of Synthetic Polymeric Materials to Fungi

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

Technical society and technical association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), the contractor shall furnish a sample unit for first article inspection and approval (see 4.2.1 and 6.3).

3.2 Material. Materials used in the manufacture of the gasket material shall be those necessary to produce gasket compositions conforming to the requirement of this specification.

3.3 Physical and mechanical properties. The physical and mechanical properties, such as flexibility, tensile strength, compressibility, etc. for types 1, 2, and 3 gasket materials shall be specified in accordance with 1.2.1 and the additional requirements specified herein and designated by suffix letters in the identification number.

3.3.1 Sealability. When specified (see 6.2), gasket material shall be subjected to the sealability test specified in 4.5. The rate of leakage, the test pressure and time required to perform the test shall be specified by the contracing officer. Identification numbers shall indicate sealability requirement by the suffix letter "A9".

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

3.3.2 Volume change in fluids. When specified (see 6.2, 6.3 and table VI), gasket material shall be subjected to one or all of the following liquids to determine the volume change: ASTM No. 1 oil, ASTM No. 3 oil, ASTM Fuel A and ASTM Reference Fuel B. The test shall be performed in accordance with 4.5. Identification numbers shall indicate volume change in fluids by the suffix letter "S9".

3.3.3 Ignition loss. When specified (see 6.2), type 1 gasket material shall be subjected to the ignition loss test specified in 4.5.1. The weight loss shall be no greater than 20 percent. Identification numbers shall indicate ignition loss requirement by suffix letter "Z".

3.3.4 Fungus resistance. Unless otherwise specified (see 6.2), all gasket material covered by this specification shall show no signs of fungi growth after being subjected to the test specified in 4.5.

3.4 Dimensional requirements. Gasket material shall be furnished in sheets (flat cuts) or in rolls as specified (see 6.2). All cut sheets and rolls shall be trimmed square on four sides. The edges of the gaskets shall be smooth.

3.4.1 Length and width. The length and width of cut sheets and roll gaskets shall be as specified (see 6.2).

3.4.1.1 Tolerances. Unless otherwise specified (see 6.2), tolerances for width and length of cut sheets and rolls shall be as follows:

Dimension in inches	Tolerance in inches
Cut sheets:	
36 by 36	Plus or minus 1/4
Over 36 by 36	Minus 1/4 plus 1/2
Rolls:	
Width under 18	Plus or minus 1/8
Width over 18	Plus or minus 1/4
Length as specified	Minus 0, plus 5 percent of length specified
Millimeter equivalents:	
36" = 914.4mm	1/8" = 3.18mm
18" = 457.2mm	1/4" = 6.35mm
	1/2" = 12.7mm

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

3.5 Identification marking. Unless otherwise specified (see 6.2), sheets and rolls shall be legibly marked with a fuel-oil resistant lacquer, ink or dye to show the following: Manufacturer's identification, F-identification number, this specification number and date of manufacture. Fabricated gaskets and gasket material less than 0.010 inch in thickness do not require identification marking.

3.6 Workmanship. Gaskets covered by this specification shall be uniform in construction and appearance. The finished stock shall be free from porous areas, weak sections, bubbles, separation, foreign matter, cracks extending through the body, voids extending into the body, sponginess or porosity, delamination, trapped air on critical surfaces, and other defects affecting serviceability.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.2 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.2.1).
b. Quality conformance inspection (see 4.2.2)

4.2.1 First article inspection. First article inspection shall be performed on one unit when a first article sample is required (see 3.1). This inspection shall include the examination of 4.4 and the tests of 4.5. Failure of the first article to pass the examination or any of the tests shall be cause for rejection.

4.2.2 Quality conformance inspection. Quality conformance inspection shall be performed on the sample units selected in accordance with 4.3.3 and 4.3.4. The inspection shall include the examination of 4.4 and the tests of 4.5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

4.3 Sampling.

4.3.1 Lot. Unless otherwise specified (see 6.2), all gasket material of the same type and identification number, manufactured in the same identifiable production period, by the same process under the same operating conditions, and submitted to the Government at one time, shall be considered a lot for the purpose of acceptance.

4.3.2 Unit of product.

4.3.2.1 Sheet material. A unit of product shall be one sheet of gasket material of the size and thickness specified (see 6.2).

4.3.2.2 Roll material. A unit of product shall be approximately one yard (one metre) of gasket material of the width specified for visual and dimensional examination.

4.3.3 Sampling for examination. A random sample of gaskets shall be selected from each lot offered to the Government in accordance with MIL-STD-105 at inspection level II. In terms of defects per 100 units, the acceptable quality level shall be 2.5 for major defects.

4.3.4 Sampling for tests. A random sample of gasket sheets or rolls shall be selected from each lot offered to the Government in accordance with MIL-STD-105 at inspection level S-4. From each roll selected, two product units shall be taken from different locations.

4.4 Examination. Each unit, selected in accordance with 4.3.3 shall be examined to verify compliance with this specification. Examination shall be conducted as specified in table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table I. Classification of defects 1/

Categories	Defects	Requirement paragraph	Method of inspection
Major			
101	Gasket material not as specified	1.2, 1.2.1, 3.2	Visual
102	Length and width not as specified	3.4.1	Scale
103	Thickness not as specified	3.4.3	Dial micrometer
104	Crack extending through body	3.6	Visual
105	Void extending into body	3.6	Visual
106	Blister extending through body	3.6	Visual
107	Sponginess or porosity	3.6	Visual
108	Trapped air on critical surface	3.6	Visual
109	Delamination	3.6	Visual
Minor			
201	Poor dispersion	3.6	Visual
202	Flow mark	3.6	Visual
203	Wrong marking	3.5	Visual

1/ Visual defects specified shall be as defined in MIL-STD-177.

4.5 Tests. Each sample unit, selected in accordance with 4.3.4 shall be subjected to the applicable tests specified in table II as dictated by the identification number specified (see 1.2.1, 3.3, and 6.2). Gasket material not meeting the applicable tests specified shall be cause for rejecting the lot.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table II. Physical and mechanical characteristics

Physical and mechanical characteristics	ASTM test method
Sample conditioning	F 104
Compressibility	F 36
Tensile strength	F 152 & F 104
Resistance to exposure in ASTM No. 3 oil	F 146
Volume change - 70 hrs at 212°F (100°C)	
Weight increase - 22 hrs at 70-85°F (21.1-29.4°C)	
5 hrs at 302°F (150°C)	
Thickness change - 5 hrs at 302°F (150°C)	
Resistance to exposure in ASTM Fuel B	F 146
Weight increase - 22 hrs at 70-85°F (21.1-29.4°C)	
5 hrs at 70-85°F (21.1-29.4°C)	
Thickness change - 22 hrs at 70-85°F (21.1-29.4°C)	
5 hrs at 70-85°F (21.1-29.4°C)	
Resistance to exposure in ASTM No. 1 oil	F 146
Volume change - 70 hrs at 70-85°F (21.1-29.4°C)	
Resistance to exposure in ASTM Fuel A	F 146
Volume change - 22 hrs at 70-85°F (21.1-29.4°C)	
Resistance to exposure in distilled water	F 146
Weight increase - 22 hrs at 70-85°F (21.1-29.4°C)	
Thickness change - 22 hrs at 70-85°F (21.1-29.4°C)	
Sealability	F 37
Creep relaxation	F 38
Adhesion and corrosion	F 64
Flotation	F 104
Fungus resistance	G 21

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

4.5.1 Loss on ignition. Loss on ignation of type 1 gasket materials shall be determined as follows: A specimen weighing from 5 to 10 grams shall be pulverized, conditioned at 70 to 80°F (21.4 to 26.7°C) in a desiccator containing anhydrous calcium chloride, and weighed. It shall be ignited in a crucible at 1500 ± 20°F (815 ± 7°C) for not less than 1 hour, cooled in a desiccator, and reweighed. The loss on ignition shall be calculated as a percentage of the original weight. Three or more specimens shall be tested from each sample submitted for test. The average of the test results shall constitute the loss ignition.

$$\text{Loss on ignition, percent} = \frac{(\text{original weight} - \text{ignited weight}) \times 100}{\text{original weight}}$$

5. PACKAGING

Application. The requirements of section 5 apply only to purchase by or direct shipment to the Government.

5.1 Preservation - packaging. Preservation - packaging shall be level A, or commercial, as specified (see 6.2).

5.1.1 Level A unit packaging. The gasket material shall be properly segregated as to identification number (call-out numbers) when packaged for shipment. Whenever applicable the gasket material shall be interleaved or otherwise protected with suitable material to prevent adherence. Material in rolls, or sheets in stacks shall be wrapped in waterproof barrier material conforming to MIL-B-13239 or PPP-B-1055 and sealed with tape conforming to PPP-T-76.

5.1.2 Commercial. Gasket material shall be packaged in accordance with Fed. Std. No. 356.

5.2 Packing. Packing shall be level A, B, or commercial as specified (see 6.2).

5.2.1 Level A. The gasket material shall be packed in overseas type boxes conforming to any of the following specifications: PPP-B-585 (style 2 or 3, class 3), PPP-B-591, PPP-B-601, PPP-B-621 (style 4, class 2), or PPP-B-636 (WWVR). Gross weight of wood and wood cleated boxes shall not exceed 91.72 Kg (200 lbs), fiberboard boxes shall not exceed the weight limitation of the box specification. Cushioning shall be applied as required to protect the gasket material. Box closures and strapping shall conform to the box specification and appendix thereto. When specified, containers shall be lined with sealed case liners conforming to MIL-L-10547.

5.2.2 Level B. Gasket material shall be packed as specified in 5.2.1 except that the boxes shall be domestic type and case liners will not be required. Fiber boxes conforming to PPP-B-636 shall be weather resistant.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

5.2.3 Level C (Commercial). Packing shall be in accordance with Fed. Std. No. 356.

5.3 Marking.

5.3.1 Material identification. Each package and each container shall be clearly marked with the applicable material identification call-out number.

5.3.2 Marking for shipment. In addition to any special marking required in the contract, shipping containers shall be marked in accordance with MIL-STD-129.

5.4 Palletization. When specified in the contract or purchase order, shipping containers shall be palletized in accordance with MIL-STD-147.

6. NOTES

6.1 Intended use. Suggested applications for the types of gaskets covered by this specification are described in MIL-HDBK-212.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number and date of this specification.
b. Identification call-out number required, including suffix letter codes for sealability, volume change in fluids, ignition loss as applicable (see 1.2.1, 3.3. thru 3.3.3).
c. If fungus resistance is not required (see 3.3.4).
d. Length, width, and thickness required (see 3.4.1 and 3.4.3).
e. If different tolerances are required (see 3.4.1.1 and 3.4.3.1).
f. If different identification marking is required (see 3.5).
g. Level of packaging and packing required (see 5.1 and 5.2).
h. If special marking is required (see 5.3.2).
i. If shipping containers shall be palletized (see 5.4).

6.3. First article inspection. When first article inspection is required, appropriate provisions should be included in the contract to allow the contracting officer to waive completely or in part the first article inspection and reduce the bid price accordingly if the successful bidder has previously performed any or all of the first article tests in recent procurement. When contract allows for the waiver of first article inspection, the contract should require that successful bidder seeking such waiver submit satisfactory evidence, including test and inspection reports that the inspection has been performed, and additional information such as contract identification, the procuring activity, the date, and other pertinent data deemed necessary by the contracting officer.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

6.4 Cross-reference. The following tables III, IV, and V, show the conversion of the P-identification numbers covered by MIL-G-12803A and the applicable F-identification numbers covered by this specification and ASTM F 104. The F-identification numbers in tables III, IV, and V are representative of the gasket material commercially available. However, the tables do not include all gasket materials currently available.

Custodian:
Army - MR

Review activities:
Army - MI, GL, SM, AT

User activities:
Army - ME

Preparing activity:
Army - MR

Project No. 5330-A069

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table III. F-Identification numbers for type 1 gasket material

P-number of MIL-G-12803	Former "G" number	Substitute F-numbers in accordance with ASTM 104												
									1/					2/
P 1141A	1122-1	F	1	1	2	1	0	0	E	3	3	M	6	
P 1151A	1123-1	F	1	1	2	4	0	0	E	4	5	M	6	
P 1161A	1111-1	F	1	1	2	6	0	0	E	5	6	M	6	
P 1161B	-	F	1	1	2	7	0	0	E	6	7	M	6	
P 1162A	1111-2	F	1	1	4	6	0	0	E	5	6	M	5	
P 1241A	-	F	1	2	3	2	0	0	E	4	3	M	4	
P 1241B	-	F	1	2	4	2	0	0	E	4	2	M	4	
P 1242A	-	F	1	2	6	2	0	0	E	5	2	M	5	
P 1242C	-	F	1	2	6	2	0	0	E	6	3	M	4	
P 1242D	-	F	1	2	5	2	0	0	E	5	3	M	6	
P 1243A	1422-2	F	1	2	7	2	0	0	E	6	1	M	3	
P 1251A	1423-1	F	1	2	3	2	0	0	E	4	3	M	6	
P 1252A	1423-2	F	1	2	5	5	0	0	E	6	4	M	4	
P 1253A	1423-3	F	1	2	7	1	0	0	E	6	3	M	4	
P 1261A	-	F	1	2	4	3	0	0	E	6	2	M	4	
P 1262B	-	F	1	2	6	5	0	0	E	7	3	M	4	
P 1301A	4131	F	1	3	2	0	0	0	E	0	0	M	1	Z
P 1302A	4111	F	1	3	4	0	0	0	E	0	0	M	1	Z

Notes: The following requirements shall be specified in contract or purchase order:

1/ See table VII for definition and interpretation of E suffix numbers.

2/ Weight loss after ignition shall be no greater than 20 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table IV. F-Identification numbers for type 2 gasket material

P-number of MIL-G-12803A	Former "G" number	Substitute F-numbers in accordance with ASTM F 104									1/	
P 2116A	2114	F	2	1	3	0	0	0	M	2	R	
P 2117A	2113	F	2	1	4	0	0	0	M	2	R	
P 2117B	2112	F	2	1	5	0	0	0	M	1	R	
P 2118A	2111	F	2	1	7	0	0	0	M	1	R	
P 2126A	2214	F	2	1	3	0	0	0	M	2	R	
P 2127A	2213	F	2	1	4	0	0	0	M	1	R	
P 2127B	2212	F	2	1	5	0	0	0	M	1	R	
P 2128A	2211	F	2	1	7	0	0	0	M	1	R	
											2/	
P 2236A	1221-3	F	2	2	6	0	0	0	M	2	S	9
P 2243A	1222-2	F	2	2	4	0	0	0	M	2	S	9
P 2245A	1222-3	F	2	2	6	0	0	0	M	2	S	9
P 2245B	-	F	2	2	8	0	0	0	M	2	S	9
P 2246A	1222-4	F	2	2	7	0	0	0	M	2	S	9
P 2254A	1223-2	F	2	2	4	0	0	0	M	2	S	9
P 2255A	1223-3	F	2	2	6	0	0	0	M	2	S	9
P 2255B	-	F	2	2	8	0	0	0	M	1	S	9
P 2256A	1223-4	F	2	2	7	0	0	0	M	2	S	9
P 2265A	1211-3	F	2	2	6	0	0	0	M	1	S	9
P 2268A	1211-5	F	2	2	8	0	0	0	M	1	S	9

1/ Gasket stock shall show no disintegration when subjected to the following conditions:

a. Three hours in boiling water.
b. One-half hour in boiling hydrochloric acid (35% concentration).
c. Two hours in ASTM Oil No. 1 at 100°C (212°F).

2/ For volume change requirement (see table VI).

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table V. F-Identification number for type 3 gasket material

P-number of MIL-G-12803A	Former "G" number	Substitute F-numbers in accordance with ASTMF 104								
P 3002A	3111	F	3	1	3	0	0	0	M	5
P 3102A	3141	F	3	1	5	0	0	0	M	3
P 3200A	3261 & 3262	F	3	1	1	0	0	0	M	9
P 3301A	3151	F	3	1	2	0	0	0	M	7
P 3302C	3122	F	3	1	4	0	0	0	M	5
P 3312B	3212	F	3	2	6	1	2	8	M	6
P 3341A	-	F	3	3	2	1	2	8	M	8
P 3341D	-	F	3	3	2	1	5	5	M	7
P 3342C	-	F	3	3	4	1	3	4	M	7
P 3342F	-	F	3	3	4	4	7	7	M	5
P 3342G	3232-3	F	3	3	5	1	6	7	M	5
P 3345A	3232-6	F	3	3	8	1	7	6	M	3
P 3353A	-	F	3	3	7	5	7	7	M	5
P 3353B	-	F	3	3	7	5	7	6	M	6
P 3354A	3233-5A	F	3	3	5	1	7	6	M	3
P 3365A	3234-6B	F	3	3	8	1	9	7	M	3
P 3413A	3221	F	3	2	6	1	2	7	M	5
P 3415A	3222	F	3	2	8	1	4	8	M	4
P 3421A	3223	F	3	9	3	1	4	4	M	5
P 3423A	-	F	3	9	6	1	4	3	M	4
P 3441A	-	F	3	3	2	2	4	4	M	6
P 3442A	-	F	3	3	3	1	4	6	M	7
P 3443B	3242-2	F	3	3	6	1	6	4	M	4
P 3443C	-	F	3	3	6	1	7	6	M	4
P 3444A	3242-3	F	3	3	7	1	7	6	M	3
P 3464A	3243-3	F	3	3	7	4	9	7	M	3
P 3553A	3233-3	F	No replacement[1/]							
P 3561A	3234-2	F	No replacement[1/]							
P 3562A	3234-3	F	No replacement[1/]							

1/ Item no longer manufactured.

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table VI. Volume change requirements for type 2 gaskets after oil immersion

Type 2 gaskets	Volume change after aging 70 hrs at 100°C (212°F) in ASTM #1 Oil	Volume change after aging 70 hrs at 100°C (212°F) in ASTM #3 Oil	Volume change after aging 22 hrs at 21.1 to 29.4°C (70 to 85°F) in ASTM fuel B
P 2236A	-5 to +5	0 to +10	-5 to +5
P 2243A	-5 to +10	-2 to +15	-2 to +10
P 2245A	-5 to +10	-2 to +15	-2 to +10
P 2246A	-5 to +10	-2 to +15	-2 to +10
P 2254A	-2 to +20	+15 to +50	0 to +15
P 2255A	-2 to +20	+15 to +50	0 to +15
P 2256A	-2 to +20	+15 to +50	0 to +15

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

Table VII. Weight and thickness increase requirements for type 1 gaskets after immersion in ASTM Fuel B (5 hours at 70-85°F)[1/]

Suffix symbol	First numeral	% weight increase maximum	Second numerical digit	% thickness increase
E	1	10	1	0-5
E	2	15	2	0-10
E	3	20	3	0-15
E	4	30	4	5-20
E	5	40	5	10-25
E	6	60	6	15-35
E	7	80	7	25-45
E	8	100	8	30-60
E	9	As specified	9	As specified

[1/] The maximum weight and thickness increase of type 1 gasket material, after immersion in ASTM Fuel B for 5 hours at 70-85°F, shall be indicated in the identification number by the suffix E followed by a two digit number. The first numeral of the two-digit number denotes the maximum weight increase and the second numerical digit the thickness increase range (Example E15 indicates a 10% maximum weight increase and a thickness increase of 10-25%).

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

Source: https://assist.dla.mil -- Downloaded: 2026-10-17T23:22Z
Check the source to verify that this is the current version before use.