MIL-S-51421(EA)
8 March 1976
(See section 6)

MILITARY SPECIFICATION

SCREENING, CHEMICAL-BIOLOGICAL FILTER

This specification is approved for use by all
Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for one type of screening made of plastic coated or impregnated fibrous glass yarn (see 6.6).

1.2 Classification.

1.2.1 Mesh sizes. The screening shall be of the following mesh sizes, as specified (see 6.2):

Mesh size 18 by 14 per inch
Mesh size 20 by 20 per inch

2. APPLICABLE DOCUMENTS

2.1 The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

EE-M-101 - Match, Safety, and Match, Nonsafety (Strike-Anywhere).
CCC-D-950 - Dyeing and Aftertreating Processes for Cotton Cloths.

STANDARDS

FEDERAL

Fed. Std. No. 123 - Marking for Shipment (Civil Agencies).
Fed. Std. No. 141 - Paint, Varnish, Lacquer, and Related Materials; Methods of Inspection, Sampling, and Testing.
Fed. Std. No. 191 - Textile Test Methods.
Fed. Std. No. 595 - Colors.

FSC 4240

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.

(Copies of specifications, standards, drawings, and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

3. REQUIREMENTS

3.1 Material. The material used to coat or impregnate fibrous glass screening yarns shall be a compound of polymerized or copolymerized vinyl chloride resin, plasticized with phosphate or phthalate ester plasticizers exclusively, pigmented and stabilized to meet the requirements herein.

3.1.1 Plasticizers (optional). At the supplier's option, plasticizers other than phosphate or phthalate may be used, provided the coating compound is treated with inhibitor (e) (solubilized copper 8-quinolinolate) of CCC-D-950 and the color is not affected. The amount of fungicide shall be based on the nonvolatile content of the coating. The coating compound shall be chemically analyzed for copper 8-quinolinolate content in accordance with CCC-D-950.

3.2 Yarns. When inspected as specified in 4.2.2.1 the diameter of the yarns (see 3.1) used in fabrication of the screening, shall be as specified in table I. The yarn used in fabrication of the screening shall be obtained from PPG Industries, Incorporated (see 6.7).

TABLE I. Diameter of the yarns.

| Mesh size of screening | Yarn diameter (inch) |
|---|---|
| 18 by 14 | 0.0130 ± 0.0010 |
| 20 by 20 | 0.0130 ± 0.0010 |

3.2.1 Elongation of yarns. The elongation of the yarns shall be 3 percent maximum, when inspected as specified in 4.2.2.1.

3.2.2 Splices. Splices shall be permitted at any point of an individual yarn provided they show no tails, and do not exceed 1 inch in length. The number of splices shall not exceed one in any one square foot nor fifteen in any roll. Knots shall not be permitted.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

3.3 Construction.

3.3.1 Screening. The finished screening shall be fabricated from the yarns specified in 3.1, and have a woven or mock selvage of at least 6 ends in each edge. Except for one half inch from each side, the yarns shall be uniformly spaced on both the warp and filling directions. When tested as specified in 4.3, the mesh shall be within plus or minus 0.5 mesh per inch of the mesh specified.

3.4 Physical properties. The physical properties of the finished screening shall be as specified in table II, when tested as specified in 4.3.

3.5 Color. The color of the screening shall be aluminum and shall be integrally incorporated in the plastic coating. The color shall fall between No. 36492 and No. 36173 of FED-STD-595.

TABLE II. Physical properties of screening

| Mesh size | Average bursting strength, pounds per square inch (minimum): Initial | After accelerated weathering | After water immersion (24 hours) | After water immersion (24 hours) and air-drying (48 hours) |
|---|---|---|---|---|
| 18 by 14 | 130 | 98 | 74 | 98 |
| 20 by 20 | 190 | 146 | 113 | 146 |

3.6 Width. The screening shall be supplied in widths from 24 to 48 inches, inclusive, in 2-inch increments, as specified (see 6.2), and the width specified shall be the minimum acceptable width.

3.7 Length. Unless otherwise specified, the screening shall be furnished in rolls containing not less than 100 linear feet (see 6.2) and shall contain not more than three pieces per roll with no piece less than 10 linear feet in length. Each roll of screening shall weigh not more than 20 pounds.

3.8 Blocking. When tested as specified in 4.3, the screening shall show no blocking in excess of scale No. 1.

3.9 Colorfastness. The screening shall show fair colorfastness to accelerated weathering, when tested as specified in 4.3.

3.10 Yarn slippage resistance. When tested as specified in 4.3, the tension required for complete slippage of the yarn shall be not less than 5.0 pounds.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:06Z
Check the source to verify that this is the currentversion before use.

3.11 Heat resistance. When tested as specified in 4.3, the yarns of the screening shall remain unaffected after being in contact with the lighted end of a cigarette for 10.0 seconds.

3.12 Flame resistance. When tested as specified in 4.3, the screening shall not burn for longer than 10 seconds after removal of a match flame.

3.13 Workmanship. The screening shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels (AQLs) established herein for any examinations and tests of materials, components, and end items, as applicable.

3.14 Mildew resistance. When tested as specified in 4.4.13, the screening shall show no evidence of fungus growth.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection.

4.1.1 Suppliers responsibility. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.1.2 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Quality conformance inspection.

4.2.1 Sampling. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated hereinafter.

4.2.2 Inspection procedure.

4.2.2.1 Component and material inspection. Components and materials shall be inspected and tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable purchase documents. Inspection shall be performed on components



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

and materials listed in table III for the characteristics shown. The sample unit for sampling purposes shall be one cone, spool, or roll. (The sample unit for test purposes shall be 13 feet of yarn). Each test unit shall be taken from a different cone, spool, or roll of yarn. The sample size shall be as listed below. The lot size for purposes of sampling shall be expressed in units of cones, spools, or rolls of yarns. All requirements are applicable to the lot average. There shall be no evidence of failure to meet the specified requirements.

| Lot size | Sample size |
|---|---|
| 800 or less | 2 |
| 801 up to and including 22,000 | 3 |
| 22,001 and over | 5 |

TABLE III. Instructions for testing

| Component | Characteristic | Specification reference: Requirement | Specification reference: Test method | Number determinations per sample unit | Results reported: as numerically to nearest |
|---|---|---|---|---|---|
| Plastic material | Composition | 3.1 | Fed Std No. 191: 1410 & 1540 1/ | 2 (composite) | |
| Yarn | Diameter | 3.2 | 4.4.3 | 3 | 0.001 inch |
| | Ultimate elongation | 3.2.1 | 4.4.5 | 5 | 0.1 percent |

1/ A certificate of compliance may be furnished in lieu of testing.

4.2.2.2 Inspection of the end item. The end item shall be inspected for defects in accordance with classifications in 4.2.2.2.1, and 4.2.2.2.2.

4.2.2.2.1 Foot-by-foot examination. The required footage of each roll shall be examined and the visual defects classified as listed below. All defects found shall be counted regardless of their proximity one to another, except where two or more defects represent a single local condition of the screening, in which case only the more serious defect shall be counted as one defect for each warpwise foot or fraction thereof in which it occurs. The sample unit for this examination shall be one linear foot. The sample size shall be in accordance with inspection level II of MIL-STD-105. The AQL shall be 4.0 defects per 100 units (feet). The lot size shall be expressed in units of one foot each. An approximately equal number of feet shall be examined from each roll selected. The number of rolls from which the sample is to be selected shall be in accordance with table IV.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

Classification of defects.

Broken or missing end or pick.
Crease - wrinkle - hard, embedded.
Any curled, doubled, rolled, or folded selvage.
Any cut, hole, or tear.
Damaged selvage extending into body of screening.
Floats - Any multiple floats.
Single float more than 1/4 inch in length in warp or filling direction.
Hitch-back, open place or slippage.
Jerked-in filling, slough-off, or thick place more than twice the thickness of the normal yarn.
Double picks, more than one in a shed.
Scalloped selvage - any indentation in excess of 1/4 inch.
Any mesh opening larger than specified regardless of the cause.
Selvage, slack or tight - causing pronounced waviness or slackness in selvage.
Width - Less than specified.
Smash - any.
Mottled or cloudy.*
Spot, stain, or streak clearly visible.*
Off shade.*
Tight end or pick - causing waviness or ridge in screening.
Not clean.
Bias or bowed filling - distortion at any point 1/2 inch or more from horizontal.
Uneven weaving (heavy or light bars).
Weak spots - any.
Uncoated or unimpregnated yarns - any.**
Any knot.
More than one splice in a square foot area.
Any splice more than 1 inch in length.
Any splice not well made and showing tails.
Wrong draw - any.

*At normal inspection distance (approximately 3 feet).

**Single ends or picks unevenly coated and giving the appearance of a streak or light colored but coated yarn shall not be scored as a defect when examined at normal inspection distance (approximately 3 feet).



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

TABLE IV. Sample size and acceptance number

| Lot size in feet | Sample size in rolls | Acceptance number |
|---|---|---|
| Up to 1200 inclusive 1/ | 3 | 0 |
| 1201 up to and including 3200 | 5 | 0 |
| 3201 up to and including 10,000 | 8 | 0 |
| 10,001 up to and including 35,000 | 13 | 0 |
| 35,001 up to and including 150,000 | 20 | 1 |
| 150,001 and over | 32 | 2 |

1/ If lot contains fewer than 3 rolls, each piece in the lot shall be examined.

4.2.2.2.2 Length examination.

4.2.2.2.2.1 Examination for length of individual rolls. The required rolls shall be examined for defects classified as listed below. The sample unit for this examination shall be one roll. The sample size and acceptance number shall be as shown in table IV. The number of rolls from which the sample is selected shall be in accordance with table IV.

Classification of defects.

Gross length less than specified minimum length.
Any piece less than 10 feet.
Any roll containing more than 3 pieces.

4.2.2.2.2.2 Examination for total footage in samples. The lot shall be unacceptable if the total of the actual gross lengths of rolls in the sample is less than the total of the gross lengths marked on the roll tickets.

4.2.3 Examination of preparation for delivery requirements. An examination shall be made to determine whether the packaging, packing, and marking complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 of MIL-STD-105 and the AQL shall be 2.5 defects per 100 units.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

| Examine | Defect |
|---|---|
| Marking (exterior and interior) | Omitted; incorrect, illegible, of improper size, location, sequence, or method of application. |
| Materials | Any component missing.<br>Any component damaged, affecting serviceability. |
| Workmanship | Inadequate application of components such as incomplete closure of container flaps, improper taping, loose strapping, or inadequate stapling.<br>Bulged or distorted container. |
| Weight | Gross weight exceeds requirements. |
| Content | Number of interior packages per container is more or less than required. |

4.3 Testing of the end item. The methods of testing specified in Fed. Std. No. 191 and Fed. Std. No. 141, wherever applicable, and as listed in table V, shall be followed. The physical and chemical values specified in Section 3 apply to the average of the determinations made on a sample unit for test purposes as specified in the applicable test method. The lot size shall be expressed in units of 1 linear foot. The sample unit for test purposes shall be 9 linear feet, full width of the finished screening. The sample size shall be as listed below. The lot shall be unacceptable if any unit fails to meet any requirement specified.

| Lot size (feet) | Sample size |
|---|---|
| 800 or less | 2 |
| 801 up to and including 22,000 | 3 |
| 22,001 and over | 5 |

TABLE V. Test methods

| Characteristics | Specification reference: Requirements | Specification reference: Test method | Number determinations per sample unit | Results reported as |
|---|---|---|---|---|
| Mesh (1/2 inch from each side) warp and filling directions 1/ | Table II | 4.4.4 | 3 (each direction | Average of 3 determinations (each direction) to nearest 0.10 meshes |



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

TABLE V. Test methods (continued)

| Characteristics | Specification reference: Requirements | Specification reference: Test method | Number determinations per sample unit | Results reported as |
|---|---|---|---|---|
| Blocking | 3.8 | 4.4.7 | 1 | Scale reading |
| Colorfastness to accelerated weathering | 3.9 | 4.4.9 | 1 | Good, fair or poor 2/ |
| Bursting strength: Initial | Table II | 4.4.6 | 3 | Average of 3 determinations to nearest 1.0 pound |
| Bursting strength immediately after 24 hours immersion in distilled water | Table II | 4.4.6 and 4.4.8 | 3 | Average of 3 determinations to nearest 1.0 pound |
| Bursting strength after 24 hours immersed in distilled water and 48 hours of air drying | Table II | 4.4.6 and 4.4.8 | 3 | Average of 3 determinations to nearest 1.0 pound |
| Bursting strength after 240 hours of accelerated weathering | Table II | 4.4.6 and 4.4.9 | 3 | Average of 3 determinations to nearest 1.0 pound |
| Yarn slippage (complete) | 3.10 | 4.4.10 | 3 | Average of 10 determinations of nearest 1.0 pound |
| Heat resistance | 3.11 | 4.4.11 | 3 | Pass or fail |
| Flame resistance | 3.12 | 4.4.12 | 3 | Average of 3 determinations to nearest 0.1 second |



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

TABLE V. Test methods(continued).

| Characteristic | Specification reference: Requirement | Specification reference: Test method | Number determinations per sample unit | Results reported as: |
|---|---|---|---|---|
| Mildew resistance | 3.14 | 4.4.13 | 1 | Growth or no growth |

1/ The mesh size of screening is defined as the number of meshes per linear inch in each direction of the screening (warp and filling). Each mesh is numerically counted by the distance from one yarn to the next adjacent yarn.

2/ Good: No appreciable change in color.
Fair: Appreciable but not objectionable change in color.
Poor: Objectionable change in color.

4.4 Tests.

4.4.1 Laboratory atmospheric conditions. Laboratory atmosperic conditions for testing shall be 73.5° ± 2.0° F and 50 ± 4 percent relative humidity, except where otherwise indicated herein.

4.4.2 Conditioning of test specimens. Unless otherwise specified herein, test specimens shall be conditioned for 24 hours at laboratory atmospheric conditions prior to testing.

4.4.3 Diameter of yarn. The diameter of the yarn shall be determined with a dial micrometer having an accuracy of 0.0005 inch (see 6.4). Determinations shall be made instantaneously. The average of ten determinations shall be reported.

4.4.4 Mesh. The mesh shall be determined by counting the yarns for 1 foot length and dividing by 12. The average of 3 determinations in both warp and filling directions shall be reported.

4.4.5 Elongation properties of yarns. The elongation of individual yarns taken from samples shall be determined with a tensile testing machine specified in Method 5100 of Fed. Std. No. 191. The distance between the jaws shall be 10 inches. The tensile strength and elongation shall be calculated from measured values of the jaw separation at rupture. The rate of jaw separation shall be 2 inches per minute. Five yarns shall be tested and the results averaged.

4.4.6 Bursting strength. The bursting strength shall be determined in accordance with Method 5122 of Fed. Std. No. 191 except that the test specimens shall be 4 by 4 inches and the clamping surfaces shall be suitably padded to prevent cutting of the glass fibers.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

4.4.7 Blocking. Blocking shall be determined as specified in Method 5872 of Fed. Std. No. 191 except that the specimen shall be folded in a "Z" fold and placed in an oven for 6 hours at 165° F. with a 3 pound weight compressing the sample.

4.4.8 Bursting strength after water immersion. Six specimens, 4 by 4 inches shall be immersed in distilled water at 73.5° ± 2.0°F for 24 hours. The samples shall then be removed from the water and the bursting strength shall be determined as specified in 4.4.6 on three specimens while they are wet. The remaining three specimens shall be air dried for 48 hours at laboratory atmospheric conditions and then tested as specified in 4.4.6. The average of each of three determinations shall be reported.

4.4.9 Accelerated weathering. Test specimens, 4 by 4 inches, shall be air dried and then subjected to 240 hours of accelerated weathering in accordance with Fed. Std. No. 141, Method 6151. The test specimen shall then be compared for solar colorfastness with the unexposed part of the screening. Immediately after the accelerated weathering period, the specimen shall be tested as specified in 4.4.6.

4.4.10 Yarn slippage resistance. Two sets of five specimens, 2 inches in width by 5 inches in length, shall be tested. One set shall have the filling parallel to the width of the specimen, and the other shall have the filling parallel to the length of the specimen. Each specimen shall be cut at A and B as shown on figure 1. The yarn slippage resistance shall be determined as specified in Fed. Std. No. 191, Method 5100. Complete slippage is defined as the separation of the specimen into two sections caused by slippage of the yarns out of the woven pattern.

4.4.11 Heat resistance. The heat resistance shall be determined by subjecting the center of a 2 by 5 inch test specimen to the lighted end of a cigarette for 10 seconds. After the 10-second period, the cigarette shall be removed and the specimen examined for conformance to 3.11. The results of three determinations shall be reported.

4.4.12 Flame resistance. The flame resistance shall be determined by subjecting a 2 by 10 inch test specimen to the flame of a match for 10 seconds. The match shall conform to type III, class 1 of EE-M-101. During this test, the specimen shall be held hin a vertical position. The stem of the match shall be held horizontally and its entire length shall touch or be as close as possible to the bottom of the screen during the burning operation. After the 10-second period, the flame source shall be removed and the time the specimen continues to burn shall be noted.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:06Z
Check the source to verify that this is the currentversion before use.

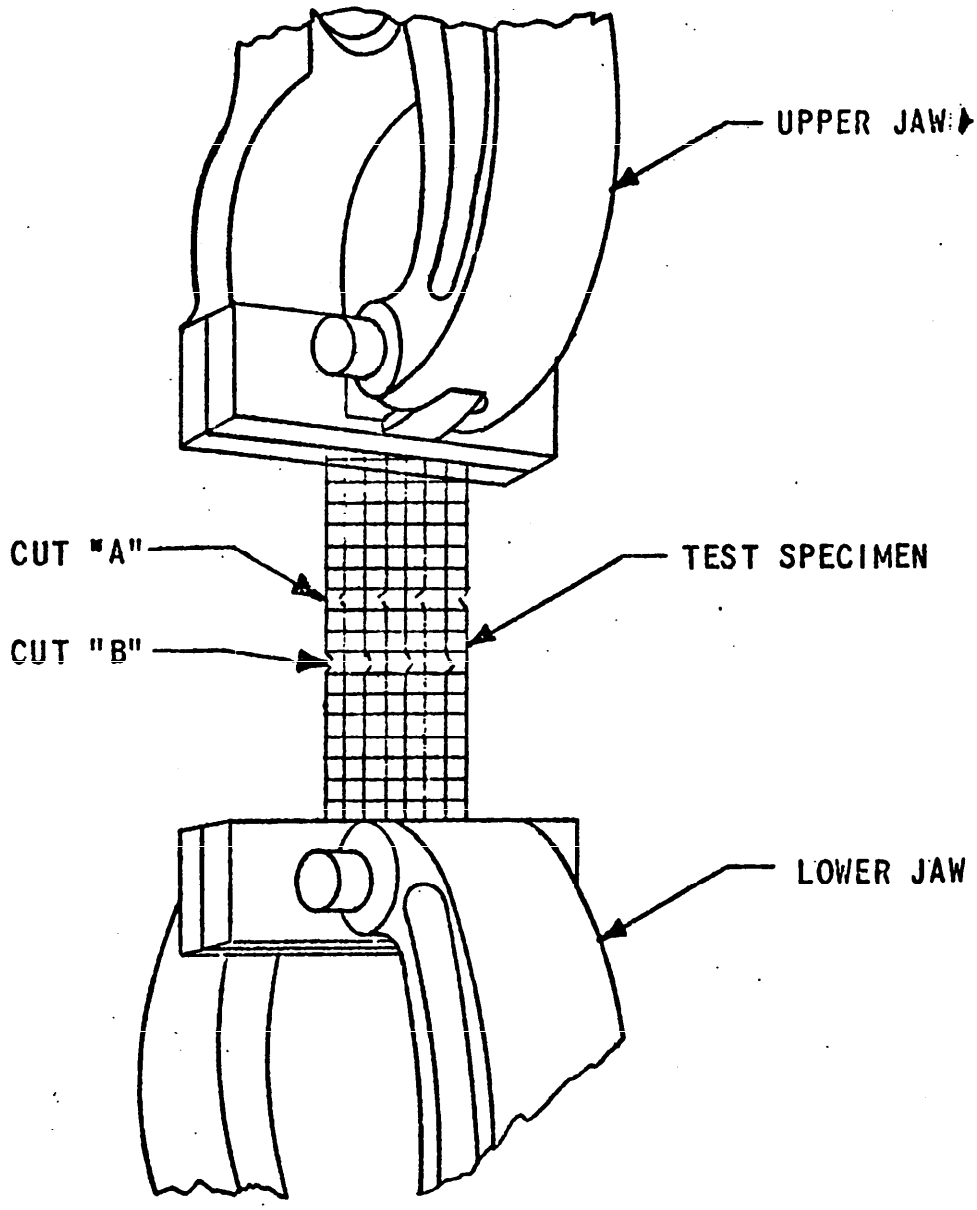



Figure 1-SCREENING, CHEMICAL-BIOLOGICAL FILTER
CUT PATTERN OF SPECIMEN



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

4.4.13 Mildew resistance. Determination of the mildew resistance shall be made by the following biological test method.

(a) Test organisms. Screening material processed in accordance with this specification shall be tested using the following fungi (see 6.5):

| Test Organism | ATCC No. | QM No. |
|---|---|---|
| Aspergillus flavus | 11655 | 4m |
| Aspergillus niger | 6275 | 458 |
| Penicillium funiculosum | 11797 | 474 |
| Penicillium piscarium | 12109 | 471 |
| Trichoderma sp. | 9645 | 365 |

(b) Maintaining stock cultures. Cultures of these fungi shall be maintained separately on a potato-dextrose agar medium. The stock culture may be kept for not more than four months in a refrigerator at approximately 3° to 10° C. (37.4° to 50° F). Subcultures incubated at 23° to 30° C (82.4° to 86° F) for 7 to 20 days shall be used in preparing the inoculum.

(c) Inoculum. The inoculum shall be prepared by pouring into one subculture of each of the five fungi in a ripe fruiting condition, approximately 10 ml of sterile distilled water containing about 0.05 percent of a nontoxic wetting agent. Force the spores into suspension. The five spore suspensions shall be combined, thoroughly mixed, and then diluted to 200 ml with sterile distilled water.

(d) Procedure and evaluation of results.

(1) Test agar medium. The medium shall have the following composition:

| | |
|---|---|
| Distilled water | 1000 ml |
| $NH_4NO_3$ | 3.0 g |
| $KH_2PO_4$ | 1.0 g |
| $MgSO_4 7H_2O$ | 0.5 g |
| KCl | 0.25g |
| Agar | 15.0 g |

The pH shall be 5.5 to 6.5; if otherwise, adjust to the range with HCl or NaOH. After mixing, the above ingredients shall be sterilized by autoclaving for 15 minutes at 15 pounds per square inch (121°C). The medium shall be poured into 10-cm Petri dishes, about 30 ml per dish and allowed to harden.



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

(2) Test specimens. Three specimens, 1-1/2 inch square, taken at random shall be cut from the sample, completely immersed in slowly running water for 24 hours, and subsequently dried. The leaching tank shall be large enough to hold an amount of water weighing not less than 50 times the weight of the specimens, the water shall not fall directly on the specimens, and shall flow at a rate of 5 to 10 liters per hour. The pH of the water shall be in the range of 6.0 to 8.0.

(3) Inoculation. The test specimen shall be fully immersed in the composite inoculum for 3 to 5 seconds, and then placed firmly on the surface of the solidified agar medium in the Petri dishes.

(4) Incubation. The period of incubation shall be 14 days at a temperature of 29° to 32° C (84.2° to 89.6° F) and 85 to 90 percent relative humidity.

(5) Controls. Three samples of untreated filter paper shall be tested along with the test specimens to check the viability of the inoculum. At the end of the incubation period, the controls shall be well-covered with the mildew growth.

(6) Results. Upon completion of the incubation period, the test specimens shall be examined visually. The treated screening material shall be considered to have failed the requirements of this specification when any of the specimens show evidence of mildew growth.

5. PREPARATION FOR DELIVERY

5.1 Packaging and packing, interplant shipment (see 6.3). Screening shall be packaged and packed to prevent damage in shipment from the supply source to the first receiving activity for immediate use. Shipping containers shall be in compliance with the rules and regulations applicable to the mode of transportation.

5.2 Marking. In conjunction with the information provided in the contract or order, marking shall be in accordance with Fed. Std. No. 123 and shall include the contract or purchase order number.

6. NOTES

6.1 Intended use. Screening covered by this specification is designed and woven primarily for use in the manufacture of chemical-biological filters.



Source: https://assist.dla.mil -- Downloaded: 202610-26T04:06Z
Check the source to verify that this is the currentversion before use.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Mesh size required (see 1.2.1).
(c) Widths required (see 3.6).
(d) Length, if other than specified (see 3.7).

6.3 Interplant shipment. Packaging and packing for interplant shipment is for supplies and materials that do not directly enter the military supply system. Typical interplant shipments are shipments from a vendor to contractor or from a supplier to a military arsenal.

6.4 The Starret Dial Micrometer, Model No. 170, manufactured by the L. S. Starret Company, Athol, Massachusetts, is suitable for measuring yarn diameter.

6.5 Pure cultures of the organisms required for the mildew resistanct test may be obtained upon request from American Type Culture Collection (ATCC), 12301 Parklawn Drive, Rockville, Maryland 20852; or Mycology Group, PRL, U. S. Army Natick Laboratories, Natick, Massachusetts.

6.6 The screening covered by this specification conforms to type II, class 2, mesh size 18 by 14 or 20 by 20, color aluminum, L-S-125B except that the following requirements have been added:

a. The yarn shall be obtained from PPG Industries, Inc.

b. The screening shall pass a mildew resistance test; the test method has been extracted from L-S-125(2).

6.7 PPG Industries, Incorporated. The Fiber Glass Division of PPG Industries is located at 1 Gateway Center, Pittsburgh, PA 15222.

6.8 Supersession data. This specification supersedes Edgewood Arsenal Purchase Description EA-S-1121, dated 24 August 1973.

Custodian:

Army - EA

Preparing activity:

Army - EA

Project No. 4240-A670



Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 20261O-26T04:06Z
Check the source to verify that this is the currentversion before use.

upper number of splices shall not exceed one in any one square foot nor li

# STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?
   A. GIVE PARAGRAPH NUMBER AND WORDING.

   B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

   ☐ YES ☐ NO *(If "Yes", in what way?)*

4. REMARKS

SUBMITTED BY *(Printed or typed name and address - Optional)*

TELEPHONE NO.

DATE

**DD FORM 1 JAN 72 1426** REPLACES EDITION OF 1 JAN 66 WHICH MAY BE USED

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.

FOLD

POSTAGE AND FEES PAID
DEPARTMENT OF THE ARMY
DOD – 314

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

Commander
Edgewood Arsenal
Attn: SAREA-TS-S
Aberdeen Proving Ground, MD 21010

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T04:06Z
Check the source to verify that this is the current version before use.