INCH-POUND

MIL-R-24919A

15 Nov 88

SUPERSEDING
MIL-R-24919
31 Jan 85

MILITARY SPECIFICATION

RAINCOAT, WOMEN'S, W/REMOVABLE LINER(CG)

This specification is approved for use by the United States Coast Guard, Department of Transportation, and is available for use by all Departments and Agencies.

1. Scope

1.1 Scope. This specification covers the requirements for a Coast Guard women's raincoat made of water repellent treated polyester/cotton poplin.

1.2 Classification. The raincoat shall be of one type in the following sizes and lengths (see 6.2).

1.2.1 Sizes. 6, 8, 10, 12, 14, 16, 18, 20, 22

1.2.2 Lengths. Short, Regular, Long

2. APPLICABLE DOCUMENTS

2.1 Government documents.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Officer in Charge, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick, MA 01760-2490 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8410

DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

* 2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATIONS

FEDERAL

DDD-L-20	- Label: For Clothing, Equipage, and Tentage (General Use)
V-F-106	- Fasteners, Slide, Interlocking
V-T-276	- Thread, Cotton
V-T-280	- Thread, Gimp, Cotton, Buttonhole
V-B-871	- Button, Sewing Hole, and Button, Staple, (Plastic)
* NN-P-71	- Pallet, Material Handling, Wood, Stringer Construction, 2-way and 4-way (Partial)

MILITARY

MIL-B-371	- Braid, Textile, Tubular
* MIL-P-15011	- Pallet, Material Handling, Wood, Post Construction, 4-way Entry
MIL-C-21852	- Cloth, Taffeta, Nylon
MIL-C-29363	- Cloth, Poplin, Polyester and Cotton (Water Repellant)
MIL-C-43251	- Cloth, Pile, Acrylic Fiber Pile
MIL-C-43479	- Cloth, Broadcloth, Polyester and Cotton
MIL-C-43525	- Cloth, Satin, Acetate or Rayon Face and Rayon or Cotton Back
MIL-T-43548	- Thread, Polyester Core: Cotton-, Rayon-, or Polyester-covered
MIL-C-43836	- Cloth, Interlining, Non-Woven

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-751	- Stitches, Seams and Stitching

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage
* MIL-STD-147	- Palletized Unit Loads

(Unless otherwise indicated, copies of federal and military specifications, standards, and handbooks are available from the Naval Publications and Forms

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

* 2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

U.S. POSTAL SERVICE MANUAL

(Copies of the manual may be obtained from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20242-0001).

* 2.2 Non-Government publications. The following document(s) form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Association, ATTN: Traffic Department, 1616 P Street, N.W., Washington, DC 20036-1404).

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, Illinois 60606-5808).

THE COLOR ASSOCIATION OF THE UNITED STATES

Department of Defense Standard Shades for Sewing Thread

(Application for copies may be obtained from the Color Association of the United States, 343 Lexington Avenue, New York, NY 10016).

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

* 2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Guide sample. Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this specification may appear in the sample in which case this specification shall govern.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

3.2 First article. When specified, the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3 and 6.2).

3.3 Material.

* 3.3.1 Basic material. The basic material shall be a water repellant treated polyester/cotton poplin, conforming to MIL-C-29363. The color shall match Blue 3376. Piece number for the standard sample is 85017.

3.3.2 Lining. The lining material for the raincoat shall be a polyester/cotton broadcloth conforming to Type I, Class 3, of MIL-C-43479, except that colorfastness for wet dry cleaning shall be tested in accordance with FED-STD-191 TM. 5622. The color shall match Blue 3377.

3.3.3 Fusible materials.

3.3.3.1 Interlining fusible (non-woven). The top collar, pocket welts, facing, long sleeve strap, epaulets, and belt shall be fused with an non-woven web, made of mechanically entangled fibers thermally bonded together and shall be binder free. The fusible cloth may be composed of 100 % polyester fibers or a combination of polyester with nylon or rayon fibers with not less than 50% polyester fibers. The fusible adhesive shall be applied to one side of the web in a uniform dot pattern in accordance with good commercial practice. The color shall be black, dark grey or approximate the shade of the base fabric. The finished weight of the fusible material shall be a minimum of 1.5 ounces per square yard.

The fused sample, consisting of fusible interlining and base fabric, shall conform to the requirements stated below when tested as specified in Table IV.

Component Testing Requirements

Appearance of fused samples 1/
Initial 2/ - No evidence of bubbling, delamination, change of color or strike through

After 5 dry cleanings 2/- No evidence of bubbling, delamination, change of color or strike through

Bond Strength (ounces per inch of width) 3/
Initial 22 ounces(or splits)
After 5 dry cleanings 17 ounces (or splits)

Shrinkage
After 1 dry cleaning 2% max.

1/ Applies to quality conformance and in-process tests
2/ After evaluation for appearance and shrinkage, samples may be used for the remainder of tests.
3/ The item will be accepted if the fusible either splits from itself rather than separates from the outershell material or if it begins to separate from the outershell material higher than the minimum bond strength and then splits from itself.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

3.3.3.2 Fusible interlining (woven). The fusible interlining for the collar stand shall be a 100% cotton, plain weave cloth. The color shall be black, dark grey or natural. The fusible adhesive shall be applied to one side of the fabric in a uniform dot pattern in accordance with good commercial practice. The finished fusible shall conform to the following requirements:

Weight, ounces per square yard(min)	5.5 - 6.5
Yarns per inch (min)	
Warp	48
Filling	48

The interlining when fused to the base fabric, shall conform to the following requirements when tested as specified in Table IV.

Component Testing Requirements

Appearance of fused samples 1/
Initial 2/ - No evidence of bubbling, delamination, change of color or strike through
After 5 dry cleanings 2/- No evidence of bubbling, delamination, change of color or strike through

1/ applies to quality conformance and in-process tests
2/ after evaluation for appearance and shrinkage, samples may be used for the remainder of tests.

Bond Strength (ounces per inch of width)	
Initial	22 ounces
After 5 dry cleanings	17 ounces
Shrinkage	
After 1 dry cleaning	2% max.

3.3.3.3 Seam Web. The tape for topstitched seams as specified in Table II, shall be a polyamide fusible web, 3/8 ± 1/16 inch in width and weigh 1.0 ± 0.2 ounces per square yard. The color shall be natural (see Table IV).

* 3.3.3.4 Colorfastness. All dyed, finished, fusible interlining materials shall show fastness to dry cleaning (3 cycles), equal to or better than the standard sample. As a limit of acceptability, or when no standard sample is available the finished, dyed fusibles shall show "fair" fastness after 3 dry cleanings (see Table IV).

3.3.3.5 Fusing conditions. The interlinings shall be fused to the base fabrics on a fusing press. For optimum results with the applicable fusible material and press used, specific information should be obtained from the fusible supplier.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

3.3.4 Sleeve hem interlining. The non-woven interlining for the sleeve (cuff) hem shall conform to Type I or II, class 1 of MIL-C-43836. The color shall be natural, black or grey.

* 3.3.5 Removable liner and outer shell binding. The fabric for binding the removable liner and the outer shell shall be a nylon taffeta conforming to Type III or IV of MIL-C-21852, except that the finish shall be natural with no added starches or resins and that testing for colorfastness to Wet dry cleaning shall be in accordance with FED-STD 191, TM. 5622. The color shall match Blue shade 3376. The piece number is 85018.

* 3.3.6 Removable pile liner material. The fabric for the removable liner shall be a pile material with 100% acrylic face and 100% polyester back, back treated with an acrylic binder and brushed finished to pile, color blue shade 3376, piece number 85019, conforming to the requirements of MIL-C-43251, class 2, except for the following:

Weight	15 oz/sq yd
Sheered Pile Weight	5.5 - 6 oz/sq yd

All requirements listed above shall be tested in accordance with MIL-C-43251, class 2.

* 3.3.7 Satin fabric. The satin fabric for the removable liner shall be in accordance with MIL-C-43525, Type II. The color shall match shade Blue 3376, piece number 85020.

3.3.8 Thread.

* 3.3.8.1 Polyester covered thread. The thread used for seaming and stitching the raincoat shall be a polyester core thread conforming to MIL-T-43548. The polyester-covered, polyester-core thread is not allowed. The color of the thread shall be shade Blue AB, CA 66044 of the Department of Defense Standard Shade for Threads and in the following sizes:

Use	Ticket No.	Ply
Seaming, stitching, buttonholes buttons, and bartacks	50	2 or 3
Overedge stitching	70	2 or 3
Tacking		
Hand	70	2 or 3
Machine	30	2 or 3

* 3.3.8.2 Thread cotton. As an alternate to the polyester-core thread, a cotton thread conforming to V-T-276, Type I, may be used. The color shall be the same as specified in 3.3.8.1 and in the following types and sizes:

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

Use	Type	Ticket No.	Ply
Seaming, stitching	IC2	0	3
		00	3
Buttonholes,buttons, and bartacks	IC2	A	3
Overedge stitching	IA3	70	2
Tacking			
Machine	IA3	70	3
Hand	IB3	16	4

* 3.3.8.3 Colorfastness. The dyed thread shall show colorfastness to wet-dry cleaning and light equal to or better than the standard sample when tested as specified in V-T-276 or MIL-T-43548. As a limit of acceptability, or when no standard sample is available, the thread shall show a minimum of "good" colorfastness to wet-dry cleaning and light when tested as specified in V-T-276 or MIL-T-43548.

3.3.9 Gimp. The gimp for reinforcing buttonholes shall be cotton, Blue AB C.A.66044, conforming to size No. 8, type I or II of V-T-280.

* 3.3.9.1 Colorfastness. The gimp shall show fastness to dry cleaning equal to or better than the standard sample. As a limit of acceptability, or when no standard sample is available, the colored gimp shall show a minimum of "good" colorfastness to dry cleaning when tested as specified in V-T-280.

3.3.10 Buttons. The buttons shall be State Button style No. 1010 or equal, 24 and 30 line, Dk Navy # 81. The reinforcement buttons shall be 1/2 inch, Type II, style 15, shade black of V-B-871 or equal (see 6.5).

* 3.3.11 Buckles. The belt and sleeve strap buckles shall be State Button style "English" or equal, color Dk Navy, in the following sizes: Belt - 1 3/4 inch # 9003 and Sleeve Strap - 1 inch # 9910 (see 6.5).

3.3.12 Slide fastener. The slide fastener for the raincoat and removable liner shall be type IV, style 1, size L, short tab pull and aluminum chain, conforming to V-F-106. The tape shall approximate shade Blue 3376 and may be 7/16 or 9/16 inch wide.

3.3.13 Stay Straps. The stay straps shall be of rayon braid, black, 3/16 to 1/4 inches wide, in accordance with MIL-B-371, Type X, Class 1.

* 3.3.14 Combination identification personal and instruction label. Each raincoat and liner shall have a combination identification personal and instruction label that conforms to type VI, class 15, of DDD-L-20. The printing shall show fastness to dry cleaning and shall bear the following inscription:

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

NAME:
SERVICE NO:
RAINCOAT, WOMEN'S, (w/REMOVABLE LINER)(CG)
CONTRACT NO: DLA 100-00-0-0000(Example)
NAME OF CONTRACTOR:
NAME OF MANUFACTURER: (If other than contractor)
CLEANING INSTRUCTIONS: For Best results,
DRY CLEAN ONLY

3.3.14.1 Size label. Each raincoat and liner shall have a size label conforming to type VI, class 2 of DDD-L-20. The printing shall show fastness to dry cleaning and bear the following inscription:

Size: 12R (Example)
Stock No: 8410-00-000-0000 (Example)

NOTE: Abbreviations to be used for the applicable lengths shall be "S" for Short, "R" for Regular, and "L" for Long.

3.4 Design. The raincoat shall be made from polyester/cotton poplin material. It shall be full length, double breasted, princess seam lines, fully lined with an all-around belt with buckle and a lined yoke on the back. It shall have a two piece raglan sleeves with sleeve straps positioned on front and back sleeve seams and secured with a buckle. The collar shall be convertible type, notched with pointed ends and overlapping lapels. Epaulets are threaded thru a loop and secured with a button on each shoulder. The raincoat shall also have a removable zippered liner (see Figures 1 and 2).

3.4.1 Figures. Figures are furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figures, the written specification shall govern.

* 3.5 Patterns. Standard patterns to be used to cut working patterns will be furnished by the Government (see 6.3). The working patterns shall be identical to the Government patterns. Neither the Government patterns nor the working patterns shall be altered in any way, except that additional notches for use during construction are permitted on the working patterns. Standard patterns shall show size, directional lines, placement mark, and notches for assembly. Unless otherwise indicated in Table II, the seam allowances shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 202640-20T02:57Z
Check the source to verify that this is the currentversion before use.

1/2 inch
outer shell joining seams
1/4 inch
lining joining seams
pile liner joining seams.
welt joining seams
joining collar to collarstand
joining collarstand to coat
joining facing to coat front
assembling belt
assembling epaulets
assembling sleeve straps
assembling collar
assembling collarstand
assembling welts
assembling belt anchor

3.5.1 List of pattern parts. The component parts of the raincoat shall be cut from materials specified in accordance with the number of parts indicated in Table I.

Table I. List of pattern parts

Material	Pattern Nomenclature	Cut Parts
Basic Material:		
Polyester/Cotton Poplin	Back	1
	Front	2
	Side Front	2
	Front Facing	2
	Back Sleeve	2
	Front Sleeve	2
	Collar	2
	Collar Stand	2
	Pocket Welt	2
	Top Pocket	2
	Under Pocket	2
	Back Yoke	1
	Epaulet	4
	Sleeve Strap (long)	2
	Sleeve Strap (short)	2
	Belt	1
	Belt Anchor	1
Lining:		
Polyester/Cotton Broadcloth Lining	Front	2
	Back	1
	Back Sleeve	2
	Front Sleeve	2
	Back Yoke Lining	1

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

Table I. List of pattern parts (cont'd)

Material	Pattern Nomenclature	Cut Parts
Interlining Material :		
Fusible Interlining(Woven)	Collar Stand	1
Fusible Interlining(Non-Woven)	Front Facing	2
	Top Collar	1
	Pocket Welt	2
	Epaulet	2
	Sleeve Strap (long)	2
	Belt	1
Interlining Material:		
Interlining(Non-Woven)	Bottom Sleeve	2
Removable Liner:		
Pile Fabric	Back	1
	Front	2
Satin Fabric	Back Sleeve	2
	Front Sleeve	2
Templates	Buttons and buttonholes	-
	Lapel Shaper	-
	Collar Shaper	-

3.6 Construction.

* 3.6.1 Stitches, seams, and stitching. Stitch, seam, and stitching types specified in Table II shall conform to FED-STD-751. Wherever two or more methods for seam or stitch types are given for the same part of the operation, any one may be used. Where stitch type 401 is used, the looper, (underthread) shall be on the inside of the raincoat or the raincoat side of the liner. Seam allowances shall be maintained with seams sewn so that no raw edges, runoffs, twists, pleats or open seams result. All seams shall start and finish evenly. Thread tension shall be maintained so that there is no tight or loose stitching. Unless otherwise specified, topstitching or edgestitching shall be 1/4 to 5/16 inch from the edge. The gauge of stitching for safety stitch construction shall be 1/4 inch. The guides and knives of the safety stitch machines shall be set to trim only the ravelled ends of the fabric. The fusing tape shall not be exposed in the seam construction. All bartacks shall be 3/8 inch (± 1/16) inch long and the width shall be 1/8 (±1/32) inch wide unless otherwise specified in Table II.

Source: https://assist.dla.mil -- Downloaded: 20261O-20T02:57Z
Check the source to verify that this is the current version before use.

* 3.6.2 Thread breaks and ends of seams. Ends of all seams and stitchings with stitch type 301 when not caught in other seams or stitching shall be backtacked not less than 1/2 inch. The ends of a continuous line of stitching (except label) shall be overlapped not less than 1/2 inch. Thread breaks (all stitch types) shall be secured by stitching back of the break not less than 1/2 inch. Skipped stitches or thread breaks (401 stitch type) shall be repaired using 301 stitch type.

3.6.3 Stitches per inch. The minimum and maximum number of stitches per inch shall be as specified in Table II.

3.7 Manufacturing operations requirements. The raincoat shall be manufactured in accordance with operation requirements specified in Table II. The contractor is not required to follow the exact sequence of operations provided the finished coat is identical to that produced by following the sequence as listed in Table II. Any additional basting or holding stitching used to facilitate manufacturing is permissible provided that the thread is removed or does not show on the finished raincoat.

3.7.1 Shade and size marking. The component parts of the coat shall be marked to insure a uniform shade and size throughout the garment. Any method may be used except:

(1) Metal fastening devices
(2) Sew-on shade tickets
(3) Adhesive type tickets which discolor or adhere to the material upon removal of tickets.

3.7.2 Pressing. All pressing as required in Table II shall be performed with a heated pressing iron or steam pressing machine except the fusible pressing which shall be pressed as recommended by the fusible manufacturer.

3.7.3 All fusing of the fusible to the basic material shall be on a single ply basis (no stacking allowed).

3.7.4 The statement "press fusible to various parts in accordance with the directions of the fusing manufacturer" refers to time, temperature and pressure.

3.8 Abbreviations in table of operations. The abbreviations used in Table II are as follows:

Stch	-	Stitch
in	-	inch
Ndl	-	Needle
Bob	-	Bobbin
Lpr	-	Looper
Mchne	-	Machine
Brtck	-	Bartack
Comrcl	-	Commercial
smlr	-	similar
Btnhl	-	Buttonhole
incl	-	including
dbl	-	double

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL BOB/ LPR
1.	Cutting.				
	a. Cut the raincoat in strict accordance with patterns furnished, which shall show size, shape, placement of pockets, directional lines for cutting and notches for proper assembly of all component parts.				
	b. Cut all component parts of the basic material from one piece of material except front facings, collarstand, undercollar, top epaulets, pockets, and front and back sleeve reinforcment, shoulder keeper loops, belt anchor and hanger loop which may be cut from ends and when so cut shall approximate the shade of the main assembly.				
	c. Cut all component parts of the lining material from one piece of material. Cut fronts and back parts of pile liner from one piece of material, and in a manner so that on the finished liner, the back and front pile pieces fall in the same direction, with the nap running down from top to bottom. Sleeves for removable pile lining may be cut from ends. When pair of sleeve is cut from ends, each sleeve shall be shade marked and shall match each other.				
	d. Cut all interlining fabrics in accordance with pattern furnished.				
	e. Cut the binding material for both the raincoat and liner on the bias, 1-1/4 to 1-3/8 inches wide.				
	f. Cut stripping for shoulder keeper loops from basic material of sufficient width to finish 3/8 (± 1/8) inch wide and 2-1/2 (± 1/8) inches in length between bartacks (see operations 4 and 29).				
	g. Cut stripping for belt loops from basic material of sufficient width to finish 3/8 (± 1/8) inch wide and 2 1/4 (± 1/16) inches in length between bartack and finished end when positioned on coat. (see operation 30).				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	h. Cut stripping for hanger loop from basic material of sufficient width to finish 3/8 (+ 1/8) inch wide and 2 (+ 1/8) inches in length between bartacks (see operation 6f).					
	i. Seams employing fusible tape shall be pressed in accordance with the directions supplied by the manufacturer of the fusing material.					
	j. Fusing of the fusible to the basic material shall not be performed prior to cutting of cut parts.					
2.	Replacement of defective components. During the spreading, cutting and manufacturing process, components having material defects as specified in Table V shall be removed from production and replaced with non-defective and properly matched components.					
3.	Size and shade marking. a. All component parts of the basic material, liner material, and linings including sleeve linings whether cut from ends or in the main lay shall be marked or ticketed to assure a uniform shade throughout the raincoat. Other parts cut from ends need not be shade marked.					
	b. The use of ink pad numbering machine, rubber stamp, or pencil is acceptable provided the numbers are legible and do not show through on the outside of the raincoat; wherever possible, numbers shall be on the seam allowance.					
4.	Make shoulder keeper loops and sliding belt keeper loop. a. Fold a strip of self fabric in half lengthwise; turn raw edges to the inside, and stitch 1/16 inch from each edge see operations 1f and 1g).	301	EFp-2	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	OR					
	b. Abut raw edges of a self fabric strip and double stitch not less than 3/16 inch gauge, using a covering stitch on the under side.	406	EFh-1	8-10	50	50
5.	Make collar.					
	a. Position fusible interlining to top collar and press. Stitch under collar to top collar around the side and top edges.	301 or 401	SSe-2(a)	8-10	50	50
	b. Trim, turn, force out edges and points and stitch 1/4 to 5/16 inch from edges.	301	SSe-2(b)	8-10	50	50
	c. Stitch raw edges of the collar, simultaneousley turning collar to allow the collar to roll properly.	301	SSa-1	8-10	50	50
6.	Make collar stand and attach collar.					
	a. Position fusible to top collar stand and press. Position collar between top and undercollar stands matching center back marks on the pattern, and with raw edges even stitch top edge of collar stand.	301 or 401	SSe-2(a)	8-10	50 50	50 7
	NOTE: The collar stand fusible interlining shall extend into the collar stand seam allowance.					
	b. Turn collar stand to finished position, turn in raw edges at sides and edgestitch sides and top of collar stand through all plies with the stitching 1/16 to 3/32 inch from turned edges.	301	SSe-2(b)	8-10	50	50
	c. Stitch along bottom raw edge of collarstand.	301	SSa-1	8-10	50	50
	d. Collar shall measure 2 1/2 $\pm$ 1/4 inches wide at center back.					

Source: https://assist.dla.mil -- Downloaded: 20261O-20T02:57Z
Check the source to verify that this is the currentversion before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	e. Hanger loop shall be made of basic material. Loop shall be double stitched using a cover stitch on underside, or with edges folded under (see operation 1i).	406 or 301	EFh-1 / EFp-2	8-10 / 8-10	50 / 50	50 / 50
	f. Turn under each end of hanger loop, center it on collar stand, and backstitch or bartack the folded edges through all plies.	Brtck		28 per brtck	50	50
7.	Make pocket welts.					
	a. Position fusible interlining to top underside of the open welt piece and press. Fold welt in half lengthwise face to face and stitch side edges.	301 or 401	SSe-2(a)	8-10	50 / 50	50 / 70
	b. Trim upper and lower corners of welt, turn and force out edges and points and topstitch 1/4 to 5/16 inch from folded edges.	301	SSe-2(b) and OSf-1	8-10	50	50
	c. The welt when stitched to raincoat front shall finish 1-7/8 (± 1/16) inches wide and 6-7/8 (± 1/8) inches long.					
8.	Make and set pockets.					
	Finished appearance. The pockets and welts shall be uniform in appearance and placement and shall lie flat and smooth, without twisitng, pleating, or puckering. The stitching shall be uniform in width.					
	a. Position face side of welt against coat front and simultaneously stitch under pocket piece and welt to front 1/4 inch from slash mark indicated on patterns. The stitching shall not extend beyond the pocket line.	301	SSaw-2(a)	8-10	50	50
	b. Position top pocket piece, adjacent and parallel to welt joining seam and stitch 1/4 inch from raw edge.	301	SSa-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. Cut the front between the two parallel lines of stitching, cutting a triangular tongue at each end in the front. Care shall be taken so that the ends of the tongue notch in the fronts will not be deeper than the ends of the two rows of stitching.					
	d. Turn the welt against the under pocket piece and the welt joining seam allowance against the front. Raise stitch the welt joining seam 1/16 inch from folded edge.	301	similar SSaw-2(b)	8-10	50	50
	e. Turn under pocket and top pocket pieces through opening and stitch 1/4 inch from the edge of top pocket ply, closing pocket.	301	SSa-1	8-10	50	50
	f. Smooth closed pocket towards front of coat and stitch outer edge of pocket piece to front edge of coat, 1/4 inch from raw edges.	301 or 401	LSa-1	8-10	50 50	50 70
	g. Stitch across each end of welt 1/16 inch from folded edge thru all plies. This stitch shall continue diagonally from top edge of welt to meet the previously stitched row of 1/4 to 5/16 inch top stitching, where it will continue superimposed on stitchline to bottom of welt.	301	SSa-1	8-10	50	
9.	Make sleeve straps.					
	a. Position fusible interlining to underside of open long sleeve strap piece and press. Fold long and short sleeve straps in half lenghthwise and stitch raw edge of short sleeve strap, and raw edge and point of long sleeve strap.	301 or 401	SSe-2(a)	8-10	50 50	50 70
	b. Trim corners, turn and topstitch along folded edges and point of long sleeve strap and folded edges of short sleeve strap. The underside of the sleeve straps along the edges shall not be exposed from the top side. Press.	301	SSe-2(b) and OSf-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. The finished sleeve straps shall measure 1 (± 1/8) inch wide.					
	d. Thread buckle thru the short strap, fold strap in half lengthwise and stitch the raw edges together. NOTE: The raised side of the buckle shall finish away from the wearer.	301	SSa-1	8-10	50	50
10.	Make belt anchor.					
	a. Fold belt anchor piece in half lengthwise and stitch 3/8 inch from raw edge and one end.	301	SSe-2(a)	8-10	50	50
	b. Trim, turn and topstitch along folded edges and finished end.	301	SSe-2(b) and OSf-1	8-10	50	50
	c. Mark location of buttonhole to correspond with the mark on the belt closest to the pointed end of the belt. The buttonhole shall be cut-first, eyelet-end taper bar type with worked over gimp with ends of the gimp pulled through to the underside. The buttonholes shall be 3/4 inch in length and 1/2 to 3/4 inch from the point with purling on the topside of loop (see operation 11c).	Btnhl		52 per btnhl not including brtck	50	50
11.	Make belt.					
	a. Position fusible interlining to underside of belt and press. Position unfinished end of belt anchor to finish on the belt mark closest to the buckle end of the belt, with a 1/4 inch turn up. Stitch across the width of the belt anchor.	301	LSd-2	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	b. Stitch one reinforcement button onto back ply of belt according to mark on belt pattern closest to pointed end of belt.	101		14-16 per button	50	50
		or 301		14-16 per button	50	50
	c. Fold belt in half lenghthwise face to face and seam edges and point together 1/4 inch from raw edges.	301 or 401	SSe-2(a)	8-10	50	50
					50	70
	d. Trim corners, turn, force out edges and topstitch along folded edges and point. The underside of the belt along the edges shall not be exposed from the topside. Press.	301	SSe-2(b) and OSf-1	8-10	50	50
	e. Fold unfinished end of belt over buckle bar 2 (± 1/4) inches.					
	NOTE: Raised side of the belt buckle shall finish away from the wearer.					
	f. Turn raw edge of unfinished end 1/4 inch and stitch to belt 1/16 to 1/8 inch from fold at end.	301	ESd-1	8-10	50	50
	g. The finished belt shall measure 1-3/4 (± 1/4) inches wide.					
12.	Make belt loops.					
	a. Fold a strip of self fabric in half lengthwise; turn raw edges to the inside, and stitch 1/16 inch from each edge.	301	EFp-2	8-10	50	50
	OR					
	b. Abut raw edges of a self fabric strip and double stitch not less than 3/16 inch gauge, using a covering stitch on the under side.	406	EFh-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
13.	Make back yoke.					
	a. Position back yoke and back yoke lining, face to face and stitch 1/4 inch from raw edge along bottom edge.	301	SSe-2(a)	8-10	50	50
	b. Turn, work out edge, and topstitch along turned edge.	301	SSe-2(b)	8-10	50	50
14.	Make epaulets.					
	a. Position fusible interlining to bottom ply of epaulet and press. Place top and bottom ply epaulet pieces face to face and stitch length sides and point 1/4 inch from raw edges.	301	SSe-2(a)	8-10	50	50
	b. Trim corners and turn to finished position, working out edges and point. Topstitch length sides and point.	301	SSe-2(b)	8-10	50	50
	c. Buttonhole in each shoulder epaulet shall be cut-first, eyelet-end taper bar type with worked over gimp with ends of the gimp pulled through to the underside. The inside edge of eyelet shall be 3/4 (± 1/8) inches from the pointed end of epaulet. The buttonholes shall not be off center by more than 1/8 inch. Buttonholes shall be 7/8 inch in length with purling on the underside of loop.	Btnhl		50-54 per btnhl	50	50
	d. Bartack ends of buttonhole stitching and gimp by machine.	Brtck		21 per brtck	50	50
15.	Make facing and attach label.					
	a. Position fusible interlining to front facings and press.					
	b. Bind back raw edge of facing. Binding shall finish 3/16 to 1/4 inch wide. (See 3.3.5)	301	BSc-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. Superimpose the right facing on the left facing at center neck as indicated by marks on pattern and stitch along outer edge thru all plies.	301	SSa-1	8-10	50	50
	d. Stitch combination label on all four sides to the left facing, centered and the bottom edge of the label positioned approximately 10 inches from the finished bottom edge of facing.	301	LSbj-1	8-10	50	50
16.	Make lining.					
	a. Overedge all raw edges of lining except coat and sleeve bottoms.	502 or 503 or 504	EFd-1	8-10	50	50
	b. Position fronts to back at side seams, matching marks on patterns and stitch 3/8 inch from raw edges.	301	SSa-1	8-10	50	50
	c. Position sleeve reinforcement pieces on the wrong side of back and front sleeve lining pieces, tack along neck edge seam.					
	d. Stitch underarm seam on sleeve forming pleat on back sleeve lining as indicated by marks on the pattern.	301	SSa-1	8-10	50	50
	e. Stitch sleeve to front and back lining, according to marks on pattern, 1/4 inch from raw edge.	301	SSa-1	8-10	50	50
*	f. Stitch top edges of front and back sleeve seam according to marks on pattern 3/8 inches from raw edges.	301	SSa-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	OR					
	As an alternate the above operations may be stitched and overedged in one operation.	515 516 or 519	SSa-1	8-10	50	50
	g. Turn bottom raw edge under 3/8 inch and form a 1 (+ 1/8) inch wide hem. Stitch hem 1/16 inch from the folded edge, catching the stay straps in the hem at side seams.	301	EFb-1	8-10	50	50
17.	Join front to side front.					
	a. Position front to side front, face to face with raw edges even. Position seam webbing along seam allowance of front and join front and side front by simultaneousley stitching, overedging, and catching the webbing in the stitching.	515 or 516 or 519	LSbm-3(a)	8-10	50	50
	b. Press seam toward front fusing the seam web. Topstitch 5/16 inch from folded edge.	301	LSbm-3(b)	8-10	50	50
18.	Join back to side fronts.					
	a. Position back to side front, face to face, according to marks on patterns, with raw edges even. Position seam webbing along seam allowance of back and join back and side front by simultaneousley stitching, overedging, and catching the webbing in the stitching.	515 or 516 or 519	LSbm-3(a)	8-10	50	50
	b. Press seam toward back fusing the seam web. Topstitch 5/16 inch from folded edge.	301	LSbm-3(b)	8-10	50	50
19.	Attach yoke					
	a. Superimpose yoke on raincoat , matching step on side front and yoke, and stitch 1/4 inch from sides and neck edge.	301	SSa-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
20.	Make sleeve					
	a. Stitch dart on sleeve back as indicated by marks on patterns.	301	OSf	8-10	50	50
	b. Join the top edges of front and back sleeves, face to face and stitch 1/2 inch from raw edge, simultaneousley catching the fusible tape to the back edge of back sleeve and catching the short sleeve strap in the seam according to marks on patterns.	301 or 401	SSa-1	8-10	50 50	50 70
	c. Press seam towards back fusing the seam web. Topstitch 5/16 inch from the folded edge.	301 or 401	LSq-2(b)	8-10	50 50	50 70
	d. Stitch non-woven sleeve interlining across bottom width of sleeve 1/4 inch from raw edges.	301	SSa-1	8-10	50	50
	e. Stitch underarm seam catching the long sleeve strap in the stitching according to marks on patterns. The dart shall be folded towards the shoulder.	301	SSa-1	8-10	50	50
21.	Join sleeves to body.					
	a. Align sleeve and raincoat according to marks and stitch armhole 1/2 inch from raw edge, simultaneousley catching fusible tape in stitching at raglan seams front and back.	301	LSq-2(a)	8-10	50	50
	b. Notch fused seam allowace, turn to finished position and topstitch raglan seams on front and back 5/16 inch from folded edges to step as marked on pattern. At step, turn and stitch to joining seamline. Press seams.	301	LSq-2(b)	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
22.	Attach collarstand to raincoat.					
*	a. Center raw edge of epaulet on shoulder joining seam in the neck area with the top side of epaulet facing the sleeve and stitch 1/4 inch from raw edge.	301	SSa-1	8-10	50	50
	b. Position bottom edge of collarstand to neckline of shell in accordance with notches on patterns, and stitch 1/4 inch from raw edges, catching the epaulets and size label centered at back neck edge, in the stitching. Slash front neckline seam allowance, as necessary.	301 or 401	SSa-1	8-10	50 50	50 70
23.	Attach lining to facing.					
	a. Mark facing 1-1/4 inches from bound back edge for positioning of lining.					
	b. Position raw edge of lining to mark on facing and stitch lining to facing forming a 1/2 inch pleat at center back. The right facing shall lap the left facing and the pleat shall be folded toward right side.	310	LSa-1	8-10	50	50
24.	Attach facing assembly to shell.					
	a. Turn raincoat bottom under 1/2 inch and form a 1 inch hem against raincoat face side. Position facing onto fronts and neckline with the raw edges even and stitch across neckline through raincoat. Continue stitching across lapel and down fronts, positioning hem area as indicated above. Turn facing to finished position and force out edges. The lapels shall be uniform in size and shape.	301	SSe-2(a)	8-10	50	50
	b. Overedge stitch the bottom raw edge of sleeve lining.	516	SSa-1	8-10	50	50
	c. Position bottom edge of sleeve lining even with bottom raw edge of sleeve and stitch.	301	SSa-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	d. Turn up bottom of sleeve at hem mark. Align underarm seams of lining and shell and stitch lining seam allowance to back underarm seam allowance of shell for a distance of 3-1/2 to 4 inches beginning 5 (± 1/2) inches from the folded edge.	301	SSa-1	8-10	50	50
25.	Hem raincoat bottom a. Turn up raincoat bottom 1/2 inch and fold hem to finished position inserting facing and stitch along top folded edge, catching 1/4 to 1/2 inches of stay straps in hem at side seams. Finished hem shall measure 1 (± 1/8) inch wide.	301	EFb-1	8-10	50	50
26.	Finish raincoat fronts. a. Edge stitch fronts 5/16 inch from edge across top of lapels and down fronts.	301	SSe-2(b)	8-10	50	50
27.	Buttonholes. a. Buttonholes for right and left fronts shall be cut-first, eyelet-end square bar type with worked over gimp with ends of the gimp pulled through to the underside. Buttonholes shall be clean and correctly positioned. The ends of the buttonholes shall be bartacked in a seperate operation from buttonhole making, securely catching the ends of the gimp and covering the width of the bar. Buttonholes shall be measured from the center of the eyelet and placed as follows:					
	b. Mark location and stitch as indicated by template, five 7/8 to 1 inch horizontal buttonholes on right front and one on left front. The purling of the front buttonholes shall finish on the outside of the front.	Btnhl		50-54 per btnhl	50	50

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the currentversion before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	c. Bartack ends of buttonhole stitching and gimp by machine.	Brtck		21 per brtck	50	50
28.	Sew on buttons. a. Sew buttons according to marks on patterns. The ends of hand shank wrapped buttons shall be tacked off with not less than two stitches.					
	b. Mark location and sew ten 30 line buttons with reinforcement buttons, five on each front. Buttons shall be shank wrapped by hand or machine and sewn through the facing except the bottom button on each side which shall be sewn with the reinforcement button through the raincoat front only.	101 or 301 or hand		14-16 btn	70	70
	c. Mark location and sew one 30 line button, on inside of right facing approximately 1/2 inch below center reinforcement button thru facing only. The button shall correspond to the buttonhole on left front.	101 or 301 or hand		14-16 btn	70	70
	d. Mark location and sew one 30 line button, through all plies of the epaulet to correspond with buttonhole in each epaulet. The center of the epaulet when buttoned, shall be horizontal to the shoulder seam.	101 or 301 or hand		14-16 btn	70	70
	e. Mark location and sew one reinforcement button on sleeve underarm seam sewn through the lining only, to correspond with loop on bottom of removable liner sleeve.	101 or 301 or hand		14-16 btn	70	70
	f. Two 30 line buttons on inside of left facing below the combination label, sewn in a vertical line through the facing only.	101 or 301 or hand		14-16 btn	70	70

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
29.	Attach shoulder keepers.					
	a. With ends of shoulder keepers turned under, position keeper on shoulder centered on sleeve outseam according to marks on patterns, bartack each end.(see operation 1f)	Brtck		28 per brtck	50	50
30.	Attach belt loops to raincoat.					
	a. There shall be two belt loops on the raincoat, one on each of the side back to back seams.					
	b. Fold belt loop in half lengthwise, positioned on raincoat as indicated by patterns, and stitch lower end of loop 1/8 inch from raw edges.	301	SSa-1	8-10	50	50
	c. Position top folded end of belt loop, according to marks on pattern and bartack. (see oper. 1g).	Brtck		28 per brtck	50	50
	d. Insert belt through double belt loops and thread the belt anchor around the inside beltloop and button to the backside of the belt.					
31.	Set slide fastener on raincoat.					
	a. Position the slide fastener on the raincoat facings so that the ends of the fastener are equidistant from the bottom edge of the raincoat and the front edge of the chain is 1/8 to 3/16 inchs from the bound edge. The separating pin of the slide fastener shall be on the right facing.					
	b. Turn in the end of the tape 1/2 to 3/4 inch if end of tape is not finished and stitch the length of the tape 3/16 to 5/16 inch from back edge of the chain.	301	SSa-1	8-10	50	50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
32.	Close liner sleeve.					
	a. Position front and back liner sleeves face to face, simultaneously stitch and overedge top and underarm seams.	515 or 516 or 519	LSbm-3(a)	8-10	50	50
33.	Assemble pile liner.					
	a. Position fronts to back face to face, and simultaneousley stitch and overedge side seams in one operation.	515 or 516 or 519	LSbm-3(a)	8-10	50	50
	b. Stitch liner identification label on center back 2-1/2 (± 1/2) inches below neck edge.	301	SSa-1	8-10	50	50
34.	Set liner sleeve.					
	a. Set sleeve into pile liner according to marks and stitch around armhole.	515 or 516 or 519	LSbm-3(a)	8-10	50	50
35.	Bind edges of liner and attach size label. Finished appearance. The binding shall be uniformly stitched with no raw edges showing. The fabric shall be caught in the stitching. The binding shall finish 1/4 ± 1/16 inch wide.					
	a. Bind edges of bottom, fronts and neck of liner in one operation. The binding shall start and finish other than at fronts and the end shall be turned in and caught in the stitching. The ends of the binding shall overlap not less than 1/2 inch with the end of the binding turned over on itself and securely stitched or bartacked. Liner size label shall be centered at neck and caught in stitching while attaching the binding.	301 or 401 Brtck	BSc-1 BSc-1	8-10 8-10 28 per brtck	50 50 50	50 50 50

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL	THREAD BOB/ LPR
	b. Bind sleeve bottoms with binding starting and finishing at under arm seam. The end of the binding shall form into a loop to accommodate reinforcement button on raincoat lining. The end of binding shall be bartacked or securely stitched.	301 or 401 Brtck	BSc-1 BSc-1	8-10 8-10 28 per brtck	50 50 50	50 50 50
36.	Set slide fastener and attach combination label on liner. a. Position the slide fastener on the underside of liner with the back edge of the chain immediately adjacent to bound edge of liner, and ends equdistant from bottom of liner.					
	b. Turn in the raw edge of the slide fastener tape 1/2 to 3/4 inch, if end of tape is not finished, and stitch the length of the tape with the stitching superimposed on the binding stitching.	301	LSa-1	8-10	50	50
	c. The slider shall be positioned on right side of liner.					
*	d. Position combination label on center back 2 (± 1/2) inches below neck edge and stitch label on all 4 sides.	301	SSa-1	8-10	50	50
36.	Clean raincoats. a. Trim thread ends and remove loose threads.					
	b. Remove spots, stains and markings.					
	c. Remove shade tickets.					
	NOTE: Care shall be taken when trimming thread ends that damage to the fabric does not result.					
37.	Press raincoat. Press collar, fronts, backs, sleeves and hems with steam pressing machine or hand pressing iron.					

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE II - Construction of Raincoat

NO.	OPERATION	STCH TYPE	SEAM/ STCH TYPE	STCH IN	THREAD NDL BOB/ LPR
38.	Attach liner to raincoat. Attach liner to raincoat by means of the slide fasteners and buttons on inside of coat sleeve and loop on liner, checking the finished operation to insure free and easy manipulation of the slider. There shall be no bulging or distortion of the raincoat or the liner when fastener is engaged. The liner shall match the raincoat in size.				
39.	Button and belt raincoat. Button five front buttons on right front and one anchor button on left front. Buckle belt loosely around raincoat and position buckle on center front.				

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

3.9 Table of Measurement. Finished measurements shall be as shown in Table III. All measurements and tolerances are expressed in inches.

Table III - Sizes and measurements

Size	(A) Chest	(B) Sleeve Inseam	(C) Center Back Length	(D) Liner Back Length
		Short		
6	40	16	41-1/2	30-1/2
8	41	16	42	31
10	42	16	42-1/2	31-1/2
12	43-1/2	16	43	32
14	45	16	43-1/2	32-1/2
16	46-1/2	16	44	33
18	48	16	44-1/2	33-1/2
20	50	16	45	34
22	52	16	45-1/2	34-1/2
		Regular		
6	40	17	44-1/2	33-1/2
8	41	17	45	34
10	42	17	45-1/2	34-1/2
12	43-1/2	17	46	35
14	45	17	46-1/2	35-1/2
16	46-1/2	17	47	36
18	48	17	47-1/2	36-1/2
20	50	17	48	37
22	52	17	48-1/2	37-1/2
		Long		
6	40	18	48-1/2	37-1/2
8	41	18	48-3/4	37-3/4
10	42	18	49	38
12	43-1/2	18	49-1/4	38-1/4
14	45	18	49-1/2	38-1/2
16	46-1/2	18	49-3/4	38-3/4
18	48	18	50	39
20	50	18	50-1/4	39-1/4
22	52	18	50-1/2	39-1/2
TOLERANCE	(±3/4)	(±1/2)	(±1/2)	(±1/2)

NOTE: Refer to Figure 1 for A, B, and C measurements. All measurements shall be taken with coat fully buttoned, placed smooth and flat.

(A) Chest - Twice the measurement taken across front at the base of armholes from folded edge to folded edge.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

(B) Sleeve Inseam - Measurement shall be taken along sleeve inseam from base of armhole to bottom of sleeve.

(C) Center back length - Measurement shall be taken from the neckline seam to bottom edge of raincoat.

(D) Liner Back Length - Measurement shall be taken from the top edge of neckline to bottom edge of liner.

3.10 Workmanship. The finished raincoats and liners shall conform to the quality of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable point value or selected defect limit.

4. QUALITY ASSURANCE PROVISIONS

* 4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) as specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

* 4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

4.3 First article inspection. When required, the first article submitted in accordance with 3.2 shall be inspected for compliance with design, construction, workmanship, appearance, and dimensional requirements.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the currentversion before use.

4.4 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.4.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable procurement documents. In addition, testing shall be performed on components listed in Table IV and in accordance with characteristics noted. The methods of testing specified in FED-STD-191, wherever applicable and as listed in Table IV shall be followed. All requirements are applicable to the sample unit. All test reports shall contain the individual values used in expressing the final result. The lot shall be unacceptable of one or more sample units fail to meet any of the test requirements specified. The lot size and sample size shall be in accordance with the following:

Component	Lot expressed as	Sample unit for testing
Tape, non-woven polyamid web for seams	Yards	two 24 inch long specimens 1/
Fusible interlining Woven	Yards	two 24 by 24 inch specimens 1/
Fusible interlining Non- Woven	Yards	two 24 by 24 inch specimen 1/

1/ Prepared by the contractor during the same period and under the same conditions as for the fusing of the end item.

Table IV - Component testing

Component	Characteristic	Requirement paragraph	Test method
Polyamide fusible web for seams	Width	3.3.3.3	5020
	Weight	3.3.3.3	5041
Woven interlining fused to basic cloth	Construction	3.3.3.2	1/
	Appearance	3.3.3.2	Visual
	Weight	3.3.3.2	5041
	Yarns per inch		
	-Warp	3.3.3.2	5050
	-Filling	3.3.3.2	5050
	Bond strength		
	-initial	3.3.3.2	5951
	-after 5 dry cleanings	3.3.3.2	5580 2/ and 5951
	Shrinkage		
	-after 1 dry cleaning	3.3.3.2	5580
Non-Woven interlining fused to basic cloth	Construction	3.3.3.1	1/
	Appearance	3.3.3.1	Visual
	Weight	3.3.3.1	5041

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

Component	Characteristic	Requirement paragraph	Test Method
	Bond strength		
	-initial	3.3.3.1	5951
	-after 5 dry cleanings	3.3.3.1	5580 2/ and 5951
	Shrinkage		
	-after 1 dry cleaning	3.3.3.1	5580
All dyed fusible interlinings	Colorfastness to: after 3 dry cleanings	3.3.3.4	5622

1/ A certificate of compliance will be acceptable for this requirement.
2/ Pressing and shrinkage requirements shall not apply.

4.4.1.1 Test for shearable pile weight. The original (total) weight of the specimen shall be determined by FED-STD-191, TM 5041, using a specimen size not less than 4 inches square. The weight specimen shall then be placed on a flat surface with the pile side up, and the pile sheared off with an electric clipper (see 6.4). Shearing shall be done in the direction of the wales, and in the direction of the courses, with the base of the cutting head parallel to the plane of the specimen. Following the shearing, the specimen shall be shaken to remove the shearing, and shall be weighed. This procedure shall be repeated until the sheared backing attains a constant weight with 0.05 gram tolerance. The sheared backing shall be examined for damage to the backing yarns. If damage is found, the results shall be discarded, and the entire procedure repeated. The weight of the shearable pile shall be determined by subtracting the weight of the sheared backing from the original weight. Reporting shall be in accordance with TM 5041. (See 6.4).

4.4.2 In-process inspection.

4.4.2.1 Sample size. The size of the fused check sample shall correspond to the total area covered by the facings, top collar, pocket welts, long sleeve straps, epaulets, belt and collar stand which are fused at one time on the press.

4.4.2.2 Number of check samples. One check sample shall be prepared following fusing of every 100 facings, top collars, pocket welts, long sleeve straps, epaulets, belt and collar stands, or once every 4 hours, whichever occurs first.

4.4.2.3 Appearance of the fused check sample. Each check sample shall be visually inspected for color change, bleed through, bubbling, and delamination. If there is any evidence of these conditions present, the previously fused pieces represented by the sample shall be inspected for the above conditions. Any fused part exhibiting one of the above conditions shall be removed from the lot. (see 3.3.3.1 and 3.3.3.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

4.4.2.4 Bond strength. The method of testing shall be as specified in 4.4.2.4.1. If the check sample fails the bond strength requirements of 22 oz or splits, the previously fused pieces and check samples shall be re-fused after the fault has been corrected. If the check sample fails a second time, all fused pieces represented by the sample shall be rejected. (see 3.3.3.1 and 3.3.3.2).

4.4.2.4.1 Apparatus and procedures for in-process bond strength testing. The apparatus to be used for this test shall be a commercial type spring scale accurate to 0.5 oz. The procedure to be followed in performimng the test shall be as follows:

(1) Three 1 x 8 inch wide strips parallel to the warp direction shall be cut from right, middle and left side of the check sample for peel strength testing.

(2) Seperate the fusible from the basic fabric at the end of the 1 inch wide strips for a distance of 2 inches.

(3) Secure the end of the basic fabric to a lightweight clamp like holder. 1 inch or more in width and approximately 1.0 ounce in weight. Hang the clamp to the end of the spring scale.

(4) Position the fusible in another clamp 1 inch or more in width and approximately 1.0 ounce in weight and pull the fusible downwards in a vertical direction with a steady continuous motion (motion to be exerted by hand) until complete seperation of the fusible from the samples. Minimum bond strength readings shall be taken visually from the spring scale. Failure of any individual strip shall indicate failure of the check sample.

NOTE: Care shall be taken not to jerk the fabric during testing.

4.4.3 Examination of the end item. Examination of the end item shall be in accordance with 4.4.3.1 and 4.4.3.2. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 4.4.3.3. The sample unit shall be one finished coat. The lot size shall be expressed in units of coats.

* 4.4.3.1 Visual examination. As a final step in the contractor's production control plan before formation of a lot:

(a) Each raincoat shall be buttoned on a model form or hanger and examined for selected defects.
(b) A raincoat containing a selected defect shall not be included in the end item lot.

Selected defects are those defects in Table V which are identified by an asterisk (*) in the Classification column. The selected asterisk defects are listed individually in Table VI.

The raincoats shall be examined for defects in shade, design, material, construction and workmanship and the defects classified in accordance with Tables V and VI.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects 1/

Defects	Classification Major	Minor A	Minor B
I. MATERIAL DEFECTS AND WORKMANSHIP DAMAGE			
a. Hole, cut, tear, smash, mend, burn, scorched area, needle chew:			
1. On outside	X		
2. On inside (longest dimension in any direction)			
(a) Up to 1/4 inch, inclusive			X
(b) More than 1/4 inch		X	
* b. Misweave, area of no dye penetration, dye streak, missing yarn, broken yarn, visible mend, thin place, shade bar:			
1. On outside and facing (longest dimension in any direction):			
(a) Up to 1/2 inch, inclusive		X	
(b) More than 1/2 inch	X		
2. On inside		X	
3. On liner or lining		X	
c. Loose yarn, snagged thread, coarse yarn, or woven in waste; more than 1 inch, on the outside		X	
* d. Permanent fold, pleat, or crease in cloth, (caused by seaming or stitching.			
1. On outside and facing	X		
2. On liner and lining		X	
e. Needle chew:			
1. Up to 1/4 inch inclusive		X	
2. More than 1/4 ianch	X		
* f. Knot or slub (exceeding the limits specified in the basic cloth specification)		X	

1/ Defects I through IX are general defects.
Defects X through XVIII should be inspected with the raincoat on a model form, completely buttoned and buckled.
Defects XIX through XXXII should be inspected with the raincoat spread out on the table.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
II. SHADED PART			
a. On outside:			
1. Any part shaded from the other parts (except parts which may be cut from ends)	X		
2. Variation in shade within a part	X		
3. Parts cut from ends badly shaded			X
b. On inside:			
1. Lining - badly shaded except sleeve lining.		X	
2. Sleeve lining - not matching or badly shaded			X
3. Liner - badly shaded		X	
III. PRESSING			
a. Pressing omitted for any specified operation (unless otherwise specified herein)	X		
* b. Sleeve not roll pressed			X
* c. Edge of collar or front not pressed solid, smooth, and flat			X
d. Wrinkles, creases or pressing impressions not removed			X
IV. CLEANNESS			
a. Spot or stain on outside:			
1. Up to 1/4 inch inclusive in longest direction		X	
2. More than 1/4 inch in longest direction	X		
b. Any marking exposed or visible on outside	X		
* c. Thread ends or floats:			
1. Three or more on outside of raincoat not trimmed to 1/4 inch or less	X		
2. Five or more inside the raincoat and liner not trimmed to 1/2 inch or more			X
d. Two or more shade or size tickets not removed			X
e. Basting thread (including monofilament thread or fragments of monofilament thread) not completely removed from outside			X
f. Fusible resin visible on outside:			
1. Up to 1/4 inch inclusive in longest direction		X	
2. More than 1/4 inch in longest direction	X		
g. Fusible resin visible on inside:			
1. Up to 1/4 inch inclusive in longest direction			X
2. More than 1/4 inch in longest direction		X	

Source: https://assist.dla.mil -- Downloaded: 202640-20T02:57Z
Check the source to verify that this is the currentversion before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
V. COMPONENT AND ASSEMBLY			
a. Any component part or operation omitted (unless otherwise classified herein)	X		
b. Any component not as specified	X		
c. Any component part tight, twisted, distorted, pleated or full (unless otherwise classified herein)		X	
d. Any operation not as specified (unless otherwise classified herein)		X	
* e. The edge of any component part required to be forced out having folds of more than 1/8 inch (unless otherwise classified herein)		X	
VI. CUTTING			
a. Any component part not cut in accordance with specified pattern, directional lines on patterns, or not in accordance with specification requirements	X		
VII. SEAMS AND STITCHING			
a. Accuracy of seaming:			
* 1. Seam noticeably puckered (score only when on major portion of seam)		X	
2. Seam irregular, pleated, or wavy (unless otherwise classified herein)		X	
3. Any part of coat or liner caught in an unrelated operation or stitching	X		
* 4. End of stitching when not caught in other seams or stitching not backstitched as specified (except attaching labels and automatic stitching)			X
5. Thread break secured by stitching back of the break less than 1/2 inch			X
6. Ends of a continuous line of stitching overlapped less than 1/2 inch			X
* 7. Not specified color thread used on outside	X		
8. Stitching attaching labels or automatic stitching not finished as specified			X
9. Needle penetrations visible on outside		X	
*10. Broken, missing or skipped stitches on edge, top or raised stitches (when seam is seamed, turned and stitched):			
(a) - 1/4 inch up to 1/2 inch inclusive			X
(b) - more than 1/2 inch		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
b. Gage of stitching and seam allowance:			
1. Edge, top or raised stitching seam too close to edge resulting in damage to cloth	X		
2. Seam allowance not as specified by 1/8 inch or more. (Score only when condition exists on more than 1/2 the length of the seam)		X	
3. Irregular or not within range specified or varies more than 1/16 inch when no range is specified. (Score only when condition exists on more than 1/2 the length of the seam)		X	
c. Open seam			
1. Outside (including undercollar)			
(a) - up to 1/4 inch inclusive			X
(b) - more than 1/4 inch up to 3/4 inch inclusive		X	
(c) - more than 3/4 inch	X		
2. On inside and liner			
(a) - up to 3/4 inches inclusive			X
(b) - more than 3/4 inches		X	
* d. Runoff, skipped or broken stitch on joining seam - use open seam classification			
e. Raw edge: 2/			
1. On outside:			
(a) - up to 3/4 inch inclusive		X	
(b) - more than 3/4 inch	X		
2. On inside and liner			
(a) - 1/4 inch up to 2 inches			X
(b) - More than 2 inches		X	
f. Seam and stitch type:			
1. Not specified seam or stitch type	X		
2. Looper thread of 401 or 406 stitch type on outside	X		
3. Any line of stitching omitted or insecure	X		
4. Any line of stitching not beginning or ending where specified (unless otherwise classified herein)			X
5. Direction of seam not as specified			X

2/ Raw edge resulting from missing, incomplete, or loose serging shall be scored as a raw edge on inside.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
g. Stitch tension:			
1. Loose tension resulting in a loose seam	X		
2. Loose tension on raised or edge stitching resulting in exposed loops of lower or top thread		X	
3. Thread tension (stitches break when normal strain is applied in the direction of the seam or stitching)	X		
h. Stitches per inch (score only when condition exists on more than 1/2 the length of seam):			
1. More than the maximum specified			X
2. Less than the minimum specified:			
(a) - by one or two stitches			X
(b) - by three or more stitches		X	
i. Bartack, backtack, tack or tacking (except buttonhole bartack):			
1. Missing, insecure, misplaced, not serving intended purpose or not specified size or type		X	
* 2. Loose stitch tension			X
* 3. Needle perforations more than 1 inch in length			X
VIII. BUTTONHOLE			
a. Omitted, added, not specified type or not finished as specified	X		
b. Misplaced or not positioned as specified; out of alignment resulting in bulge or twist when buttoned	X		
c. Gimp omitted, uncut buttonhole, incomplete stitching or stitching not securely caught in fabric		X	
d. Ragged edge, broken stitch or two or more skipped stitches		X	
e. Buttonhole stitching extending beyond tack			X
f. Purling not finished on the side specified		X	
g. Buttonhole stitching not uniform and even			X
h. Bartack missing, loose or misplaced (not serving intended purpose)		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
i. Stitches per buttonhole or tack less than specified minimum number by:			
1. One to three stitches			X
2. Four or more stitches		X	
* j. Two or more buttonholes out of vertical alignment by:			
1. 1/8 inchs to 1/ inch inclusive			X
2. More than 1/4 inch		X	
* k. Spacing between two or more buttonholes unequal by 1/4 inch or more		X	
* l. Ragged inside edges, i.e., yarns or thread ends not trimmed to less than 1/4 inch or basic fabric not caught by buttonhole stitching:			
1. Less than 4			X
2. More than 4		X	
IX BUTTON (including reinforcement button)			
a. Omitted, broken or defective		X	
b. Out of horizontal or vertical alignment (except top and lapel buttonhole) by:			
1. 3/16 inch to 3/8 inch			X
2. More than 3/8 inch		X	
c. Misplaced, loose, not attached as specified, or insecurely sewn		X	
d. Tacking stitches omitted or insecure (hand sewn)			X
e. Shank wrapping (when required) omitted, loose or insecurely wrapped		X	
f. Stitching on button not locked at end of cycle (tug at loose end of the thread when accesible to determine whether it will ravel)			X
* g. Any part of raincoat puckered or pleated by button sewing			X
X. COLLAR OR LAPEL			
a. Not uniform in size or shape - any point varying:			
* 1. More than 1/4 inch with corresponding point on matching part	*		
* 2. More than 1/8 inch up to 1/4 inch inclusive with corresponding point on matching part.	X		

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the currentversion before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
* 3. More than 1/16 up to 1/8 inch inclusive with corresponding point on matching part		X	
b. Twisted, not smooth and flat, short or tight causing collar or lapel to turn out	X		
* c. Collar:			
1. Collar off center by 1/4 inch or more 1/		X	
2. Finished width of collar or collar stand at center back not as specified		X	
3. Collar or collar stand too loose or tight causing puckers or pleats on collar, collar stand or neckline		X	
4. Edge of collar not properly forced out, i.e., having a fold of more than 1/8 inch in depth		X	
5. Fusible collar stand interlining not extended into seam joining the collar stand and collar		X	
6. Finished width of collar not as specified			X
7. Under collar exposed along collar edge for a length of 1/2 inch or more			X
8. Collar edge crooked, irregular or wavy		X	
d. Lapel:			
1. Left and right lapel varying in length by:			
(a) - more than 1/4 inch up to 1/2 inch inclusive		X	
(b) - more than 1/2 inch	X		

1/ Center of collar is determined by aligning the two shoulder seams at junction of collar.

XI FRONT AND FRONT FACING			
a. Front facing excessively full, tight, or twisted:			
1. At lapel	X		
2. Below lapel		X	
b. Front facing short, tight, or twisted causing fullness or twist on front or causing lapel end to curl up	X		
c. Front facing too long causing bottom corner of front to curl up	X		
d. Front tight or short, button out of alignment with buttonhole, or front facing tight or twisted causing noticeable bulge or twist		X	
e. Fronts uneven in length at bottom or top by:			
1. More than 1/4 inch up to 1/2 inch inclusive			X
2. More than 1/2 inch		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
* f. Front edge not folded straight with warp line	X		
g. Front edge irregular, stretched uneven			X
* h. Front facing exposed beyond edge of front for a length of 1 inch or more		X	
* i. Front of coat pleated or puckered at corner of pocket welt	X		
j. Front part exposed along lapel edge.			X
XII. POCKET			
a. Pockets out of alignment (in any direction) or misplaced by:			
* 1. More than 1/2 inch	*		
* 2. More than 3/8 inch up to 1/2 inch inclusive	X		
* 3. 1/4 inch up to 3/8 inch inclusive		X	
b. Pocket notch exposed on outside		X	
c. Pocket welt:			
1. Not uniform in size and shape - any point varying			
(a) - More than 3/8 inch with corresponding point	X		
(b) - 1/4 inch up to 3/8 inch with corresponding point		X	
2. Twisted or full (not finished smooth, flat and even)		X	
3. Inner pocket welt exposed along top or bottom edge of pocket welt			X
4. Length or width not as specified by:			
(a) - 1/8 inch up to 1/4 inch inclusive			x
(b) - More than 1/4 inch up to 3/8 inch inclusive		X	
(c) - More than 3/8 inch	X		
5. Welt stitching not as specified		X	
* 6. Back edge of welt short causing pleat or puckers on front or too loose causing welt to gap	X		
* 7. Interlining omitted	X		
d. Pocket opening:			
1. Not smooth and flat		X	
2. End not caught in welt stitching		X	
* e. Front of hanging pocket not stitched under facing		X	
XIII. SHOULDER CONSTRUCTION			
a. Improperly joined or set causing front or back of shoulder to twist	X		
b. Any component tight, twisted, pleated, creased, full, or puckered		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
XIV. EPAULET			
a. Not uniform in size or shape - any point varying:			
1. More than 3/8 inch with corresponding point on matching part	X		
2. 1/4 inch up to 3/8 inch (inclusive) with corresponding point on matching part		X	
b. Epaulet tight, loose, or badly distorted when buttoned		X	
c. Interlining short, tight, or twisted affecting appearance of loop		X	
* d. Not positioned as specified or attached crookedly		X	
e. Buttonhole not centered or positioned from finished end of loop as specified			X
* f. Shoulder loop keeper(s) less than 2 or more than 2-1/2 inches long between bartacks.			X
g. Shoulder loop keeper not attached or not positioned properly			X
* h. Epaulet reversed, seam on upper side	X		
XV. SLEEVE			
a. Sleeve lining twisted, tight, or short causing fullness or twist on outside of sleeve	X		
b. Sleeve tight in lower front armhole causing a bulge, break, or twist in sleeve	X		
c. Sleeve fullness at armholes misplaced, affecting appearance		X	
d. Sleeve tight at armholes, causing ridges, puckers, or pleat on outside		X	
e. Underarm seam of sleeve staggered more than 3/8 inch with side seam at armhole			X
f. Interlining twisted, tight, or pleated causing puckering on outside of sleeve clearly noticeable			X
* g. Sleeves reversed i.e., right sleeve set in left armhole	X		
XVI. SLEEVE STRAPS			
a. Edge of sleeve strap not parallel to bottom edge of sleeve by more than 1/4 inch		X	
* b. Width of strap not as specified		X	
c. Not attached or not positioned as specified			X
* d. Out of alignment by:			
1. More than 1/4 inch with each other		X	
2. More than 1/2 inch with each other	X		

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
XVII. DART OR PLEAT			
a. Omitted or not specified type	X		
b. Not positioned as specified		X	
c. Depth of pleat at top end of back lining not as specified			X
XVIII. LINING			
a. Twisted, tight, or short causing bulge or twist on front	X		
b. Too long causing lining to sag at bottom		X	
c. Any required tack or backtack on sleeve lining omitted, unsecured, or not positioned as specified		X	
d. Bottom edge or hem not finished as specified			X
e. Tacking of facing to pocket omitted, insecure or not positioned as specified			X
f. Stitches tacking lining to outer shell caught through outside causing impression marks			X
XIX. BINDING			
a. Omitted	X		
b. Twisted			X
c. Not securely caught, causing binding to pull away from fabric	X		
d. Binding short or tight, causing edge of seam to curl and not lie flat		X	
e. Stretched causing edge to be wavy in appearance		X	
f. End not overlapped as specified			X
g. Not starting or finishing as specified or incomplete			X
XX. BELT			
a. Buckle defective	X		
b. Buckle stitching insecure		X	
c. Irregular in width by more than 1/8 inch			X
* d. Belt in reversed position		X	
e. End poorly shaped			X
* f. Twisted or puckered		X	
g. Width not as specified			X

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
XXI. BELT LOOP			
* a. Omitted	X		
b. Finished length or width not as specified			X
* c. Not positioned as specified by more than 1/2 inch		X	
* d. Loop not attached as specified or opening not as specified		X	
* e. Belt loop set at an angle, more than 1/4 inch off the perpendicular		X	
XXII. BELT ANCHOR			
a. Finished length or width not as specified			X
b. Misplaced, i.e., stitched to belt so that belt buckle cannot be positioned at front center when fronts are buttoned		X	
c. Button stitching exposed on outside of belt			X
d. Not positioned through belt loop, i.e., not serving intended purpose			X
e. Belt safety strap extends below bottom edge of belt			X
XXIII. HANGER LOOP			
a. Finished width or length not as specified			X
b. Not positioned as specified, by more than 1/4 inch			X
c. Not attached as specified			X
d. Insecure			X
XXIV. FUSIBLE TAPE AND FUSIBLE INTERLINING			
a. Omitted	X		
b. Twisted causing puckers, pleats, or twists on the outside of raincoat	X		
c. Any evidence of bleed through, bubbling, delamination, or color change	X		
d. Not positioned or stitched as specified		X	
e. Exposed		X	
XXV. HEM			
a. Twisted or pleated		X	
b. Puckers			X
c. Width of hem not as specified			X

Source: https://assist.dla.mil -- Downloaded: 20260-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
XXVI. LABEL			
a. Missing, incorrect, or illegible:			
1. Size label, instruction or combination label	X		
2. Identification label			X
b. Not attached as specified, misplaced, or stitching through the printing			X
XXVII. LINER			
a. Size shown on liner not same as raincoat			X
b. Liner tight or short causing puckering of raincoat	X		
c. Ends of binding not caught in bartack or stitching			X
d. Fabric not securely caught in binding		X	
e. Fronts uneven in length by more than 3/4 inch		X	
f. Finished width of binding not as specified			X
g. Ends of binding overlapped less than 1/2 inch			X
h. End of binding on sleeve bottom not finishing at underarm seam or not formed into a loop to accommodate a reinforcement button		X	
XXVIII. SLIDE FASTENER			
a. Slide fastener not type, style, size, type of pull, or finish required	X		
b. Slide fastener does not function properly - pull detaches, slider binds or sticks, or chain unmeshes	X		
* c. Slider positioned on left side of liner (as worn)	X		
d. Slide fastener not positioned as specified		X	
e. Ends of slide fastener unequal in distance from bottom edge of liner by more than 1 inch		X	
f. Slide fastener pull tab not on outside (pile side) of liner			
* g. Slide fastener tape stitched too close to metal chain not permitting slider to move freely	X		
h. Slide fastener tapes wavy or puckered (too tight or too full)		X	
i. Slide fastener separating pin not on right facing of raincoat			X
j. Slide fastener retainer not on right side of liner (as worn)			X
k. Raincoat or liner twisted or distorted when slide fastener is engaged	X		

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

TABLE V - Classification of defects (cont'd)

Defects	Classification Major	Minor A	Minor B
XXIX. ARMHOLE			
a. Stretched causing excessive fullness on back between shoulders and underarm		X	
b. Crooked or puckered seam		X	
c. Any component part on or around armhole that is tight, twisted, pleated, creased, full, or puckered		X	
XXX. COLLAR CLOSURE (POSITION OF LAPEL BUTTON)			
* a. Misplaced on left front causing a noticeable bulge or twist on fronts when buttoned		X	
b. Misplaced on left front causing collar ends to overlap when buttoned		X	

* TABLE VI - Selected defects

COLLAR OR LAPEL
Not uniform in size or shape - any point varying more than 1/4 inch with corresponding point on matching part.
POCKETS
Out of alighment (in any direction) or misplaced by more than 1/2 inch.

4.4.3.2 Dimensional examination. The coats shall be examined for defects in dimensions in accordance with the following:

a. Any measurement deviating from nominal dimensions and tolerances specified in Table III shall be scored as a measurement defect.

b. Sleeve lengths unequal in length by 1/2 inch or more shall be scored as a size measurement defect.

4.4.3.3 Inspection levels and acceptable quality levels. The inspection levels and acceptable quality levels (AQL's) expressed in defects per 100 units, for visual and dimensional examination shall be as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

	AQL's	Inspection level
For visual examination in 4.4.3.1		
Major	1.0	III
Major, Minor A (combined)	6.5	III
Total (Major, Minor A, Minor B combined)	15.0	III
For dimensional examinations in 4.4.3.2		
One class	4.0	S-3

4.4.3 Examination of packaging requirements. An examination shall be made to determine that packaging, packing, and marking comply with Section 5 requirements of this specification. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be on the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the acceptable quality level (AQL) shall be 2.5 defects per hundred units in accordance with MIL-STD-105.

Examine	Defect
Marking (exterior and interior	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Inadequate application of components, such as: incomplete closure of container flaps, loose strapping, improper taping, inadequate stapling, bulged or distorted container.
Content	Number of items per shipping container is more or less than required. Size shown on one or more items not as specified on shipping container. 1/ Open and non-continuous heat sealed seams and closure of polyethylene bag. 1/ Alternate closure of polyethylene bag not provided with tuck or reverse flap. 1/ Omission of vent hole in polyethylene bag. 1/

1/ For this defect, one intermediate package from each shipping container in sample shall be examined.

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

* 4.4.4 Palletization examination. An examination shall be made to determine that the palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the end item inspected lot. The inspection level shall be S-1 and the acceptable quality level (AQL), expressed in terms of defects per hundred units, shall be 6.5 in accordance with MIL-STD-105.

Examine	Defect
Finished dimensions	Length, width,or height exceeds specified maximum requirements.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted, incorrect, illegible, of improper size, location, sequence, or method of application.

5. PACKAGING

5.1 Preservation. Preservation shall be level A or C as specified (see 6.2).

5.1.1 Level A. The raincoats shall be hung with fronts lapping, buttoned, and belted on hanger. The hanger shall be made of high impact polypropylene. The hook of the hanger shall be square and made of 8 gauge wire. The hanger shall be able to withstand a garment weighing a minimum of 5 lbs. The hanger shall measure 17 inches across the width for all sizes. Each coat shall then be enclosed in a open-bottom polyethylene bag of 0.0006 inch (± 20%) thickness which shall extend beyond the bottom of the coat. The top of the bag shall be sealed to fit over the shoulders and shall have a small opening centered at the top to accommodate the hanger hook. Suggested dimensions for the bag are 21 inches wide by 50 inches long with a 4 inch gusset at each side.

5.1.2 Level C. Each raincoat shall be preserved to afford adequate protection against deterioration and physical damage during shipment to the first recovering activity. The package and quantity per package shall be the same as that normally used by the contractor for retail distribution.

5.2 Packing. Packing shall be level A or C as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

* 5.2.1 Level A packing. Fifteen (15) raincoats of one size and length only, packaged as specified in 5.1.1 shall be packed in a front loading style fiberboard wardrobe container. The container shall be a regular slotted container, made of double wall corrugated fiberboard, 350 T. The front panel shall have a diagonal score or horizontal cut. The dimensions of the container shall be 21 inches X 22 inches X 54 inches. The hanger bar of the container shall be 21 inches long, made of galvanized steel, have end brackets to fit securely onto the side panels of the container, and shall accept square hook hangers. The container shall be fabricated according to good commercial practice. Three inch wide (minimum) fiberglass reinforced plastic adhesive tape shall be used to first seal completely the overlapped top flaps of the container, and then the butted top flaps. The tape shall be centered over the butted edges of the flaps. A third taping operation shall completely seal the edges of the flaps. The fourth taping operation shall close the front panel along the length of the side opening, and across the bottom cut edge, as applicable. Reinforcement tape shall be placed in two locations across the side closure, spaced equidistantly from the top and bottom of the panel. When the quantity per size and length is ten (10) coats or less, a 14 inch X 22 inch X 54 inch container may be used.

* 5.2.2 Level C. Raincoats of one size and length only, preserved as specified in 5.1, shall be packed in a manner to ensure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. The quanitity per shipping container shall be the same as that normally used by the contractor for retail distribution. Containers shall comply with the U.S. Postal Service Manual, Uniform Freight Classification Rules or National Motor Freight Classification Rules, as applicable.

5.3 Marking. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with MIL-STD-129. When wardrobe containers are used, the container shall have marked on each side in bold, clear, red or blue lettering not less than two inches high "DO NOT DROP" and "THIS SIDE UP" with arrows pointing to the top of the container.

* 5.4 Palletization. When specified (see 6.2) item packed as specified shall be palletized on a 4-way entry pallet in accordance with load type 1A of MIL-STD-147. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means C, K, and L or O or P. Pallet pattern shall be in accordance with the appendix of MIL-STD-147.

The pallet shall be 4-way, Type IV; Type V, Class 1, Size 2; or Type VIII, fabricated from wood group I, II, III or IV, Grade A of NN-P-71, or 4-way, Style 1, Size A, Type I, Class 1 fabricated from wood groups specified in MIL-P-15011. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the patterns specified in MIL-STD-147, the pallet pattern used shall be approved by the contracting officer.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

6.1 Intended use. The coats are intended for wear by female personnel of the U.S. Coast Guard.

* 6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification
b. Sizes and lengths required (see 1.2)
c. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1 and 2.2).
d. When first article sample is required (see 3.2). The item will be tested and should be a first article sample. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examination, quantity, testing and approval of the first article.
e. Levels of packaging and packing required (see 5.1 and 5.2)
f. When palletization is required (see 5.4)

* 6.3 Samples and patterns. For access to samples and patterns, address the procuring activity issuing the invitation for bids (see 3.1 and 3.5).

* 6.4 Clipper. An Oster Model (or equal) No. 111 carrying a NO. 50, size 000 cutting head is recommended. Local barber supply agencies may be sources for the clipper described. A source is Oster Mfg. Co., 5055 N. Lydell Street, Milwaukee, WI.

6.5 Buckles and buttons. A suggested source of supply for the buckles and buttons is the State Button Co., 45 West 18th St., New York, NY 10011.

* 6.6 Box. A suggested source of supply for the boxes (see 5.2.1) is CLOPAX, 44 Norfolk Avenue, Easton, MA 02375.

6.7 Equal item Prior to the use of an "or equal" item, the supplier shall submit the item with supporting data to the contracting officer for subsequent approval or disapproval by the responsible Military Agency.

* 6.8 Recycled materials. It is encouraged that recycled materials be used when practical as long as it meets the requirements of this specification.

* 6.9 Changes from previous issue. The margins of this specification are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

* 6.10 Subject term (key word) listing.

- Coat, water repellant treated polyester/cotton poplin
- Raincoat, removable fleece lining
- Raincoat with lining

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

Custodian:
Navy - NU

Review Activity:
DLA - CT
Navy - CG

Preparing Activity:
Navy - NU

Project No. 8410-N685

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

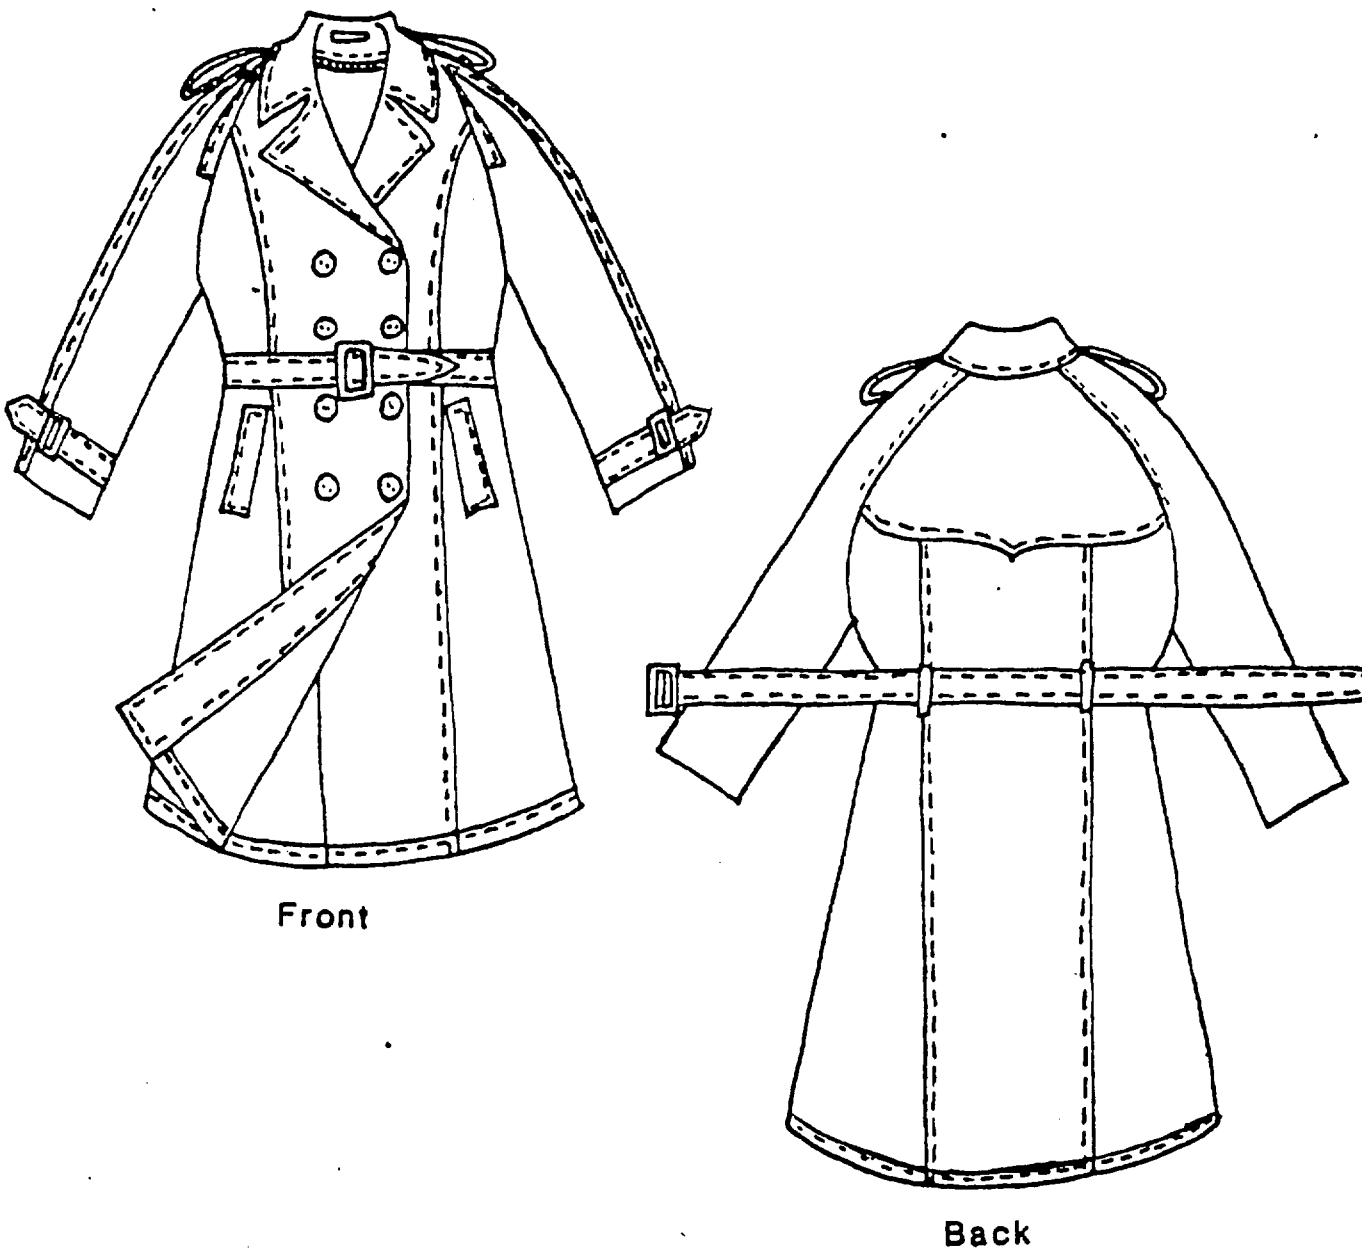


Figure 1- Raincoat Women's (w/Removable Liner)CG

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

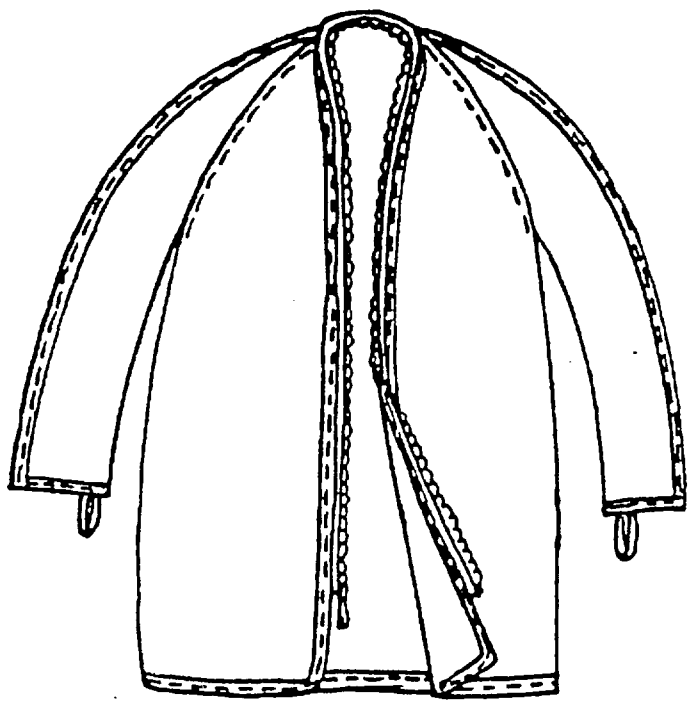


Figure 2 - Raincoat, Women's (w/Removable Liner)CG

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:57Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-R-24919A	RAINCOAT, WOMEN'S, W/REMOVABLE LINER (CG)

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to prov suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Navy Clothing and Textile Research Facility
21 Strathmore Road, Natick, Mass. 01760

Source: https://assist.dla.mil -- Downloaded: 202610-20T02:57Z
Check the source to verify that this is the current version before use.