MILITARY SPECIFICATION

SOCKS, MEN'S, ACRYLIC/NYLON, RIBBED, STRETCH TYPE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for men's over-the-calf length, stretch acrylic/nylon dress socks with an elastic top.

1.2 Classification. The socks shall be of one type in the following sizes (see 6.2):

Schedule of sizes:

Sock size	
Small	9- 11
Medium	10- 13
Large	13- 16

2. APPLICABLE DOCUMENTS

2.1 Government documents.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Officer in Charge, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick MA 01760-2490 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

FSC 8440

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

2.1.1 Specifications, standards, and handbooks. Unless otherwise specified, the following specifications, standards and handbooks of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation form a part of this specification to the extent specified.

SPECIFICATIONS

FEDERAL

DDD-L-20	Label; for Clothing, Equipage, and Tentage (general use)
PPP-B-636	- Boxes, Shipping, Fiberboard

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-751	- Stitches, Seams, and Stitchings

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage
MIL-STD-147	- Palletized Unit Load

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

LAWS AND REGULATIONS

U.S. POSTAL SERVICE MANUAL

(Copies of the manual may be obtained from the Superintendent of Documents, U.S.Goverment Printing Office, Washington, DC 20402)

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. The issues of documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and supplement thereto, if applicable.

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

Source: https://assist.dla.mil - Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

(Applications for copies should be addressed to the American Trucking Association, ATTN: Traffic Department, 1616 P Street, N.W., Washington, DC 20036).

CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106 222 South Riverside Plaza, Chicago, IL 60606).

2.3 Order of precedence. In the event of conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Guide sample. Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this specification may appear in the sample in which case this specification shall govern.

3.1.1 Standard samples. The sock shall match the standard sample for shade and shall be equal to or better than the standard sample with respect to all characteristics for which the standard sample is referenced (see 6.3).

3.2 First article. When specified, the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3 and 6.2).

3.3 Material.

3.3.1 Knitting yarn. The knitting yarn shall be one end of acrylic (specified in 3.3.1.2) with 12 to 16 turns per inch, plaited over one end of two ply 70 denier stretch nylon yarn specified in 3.3.1.1.1.

3.3.1.1 Nylon yarn.

3.3.1.1.1 Nylon yarn (body). The yarn shall be two ply consisting of two ends of 70 denier (± 5 percent) stretch type nylon when tested as specified in 4.4.1.

3.3.1.1.2 Nylon yarn (heel and toe). The yarn shall be one end of 70 denier (± 5 percent) stretch type nylon when tested as specified in 4.4.1. The yarn shall be inserted 14 courses above the heel and run thru heel area and repeat at toe area.

3.3.1.2 Acrylic yarn The worsted yarn shall be 22 singles relaxed acrylic, when tested as specified in 4.4.1.

3.3.2 Elastic yarn. The yarn shall be 210 denier spandex having a 70 denier stretch type nylon inner and outer cover when tested as specified in 4.4.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

3.3.3 Thread. The thread shall be nylon, commercial size 4, one or two ply and shall have 96,000 (± 5 percent) yards per pound, with a minimum breaking strength of 0.35 pounds and a minimum elongation of 35 percent when tested as specified in 4.4.1. The color shall approximate the shade of the sock.

3.3.3.1 Looping yarn. The yarn for looping shall be 1/70 denier texturized nylon,when tested as specified in 4.4.1. The color shall approximate the shade of the sock.

3.4 Color. The color of the socks shall be Blue shade no. 3346 . The use of sulfur dyes and dyes containing elementary sulfur or compounds capable of oxidation to sulfuric acid are prohibited. The dyestuff shall be chosen and applied so that the dyed and finished socks shall contain no more labile sulfur than shown by the standard sample when tested as specified in 4.4.3. When a standard sample is not available, the dyed and finished socks shall show no more than a slight trace of labile sulfur when tested as specified in 4.4.3.

3.4.1 Matching. The color of the finished socks shall match the standard sample under artificial daylight having a color temperature of 7000 ± 500 Kelvin and shall be a good approximation to the standard sample under incandescent lamplight at 2850 (± 100) Kelvin.

3.4.2 Colorfastness. When no standard sample is available, the socks shall show "good" fastness to laundering (after 3 cycles) and perspiration when tested as specified in 4.4.3. When a standard sample is available, the socks shall show fastness to laundering (after 3 cyles) and perspiration equal to or better than the standard sample when tested as specified in 4.4.3.

3.5 Design. The socks shall be seamless, over-the-calf length, stretch type with a 6 inch (French top) ribbed elastic top (see Figure 1).

3.6 Figures. The figures are furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figures, the written specification shall govern.

3.7 Construction.

3.7.1 Knitting. The socks shall be knit seamless in one integral unit on a 132 needle circular machine having a cylinder diameter of 4 inches.

3.7.1.1 Leg and top of foot. The leg and top of foot as far as the ring toe shall be a 2 by 1 ribbed knit using one end of the knitting yarn specified in 3.3.1.

3.7.1.2 Sole, heel, toe and ring toe. The sole, heel, toe and one-inch ring toe shall be plain knit using one end of the knitting yarn specified in 3.3.1. A minimim of 14 gore needles shall be used in knitting the heel. A minimum of 14 gore needles shall be used in knitting the toe.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

3.7.1.3 French elastic top. The elastic top shall be a true 1 by 1 ribbed knit using one end of the knitting yarn specified in 3.3.1 with one end of the elastic yarn specified in 3.3.2 laid in every other course through out the six inches. The top edge shall be finished with a turnover, well defined, non-raveling welt, free from loose ends.

3.7.2 Toe closure. The toes shall be closed by looping as specified in 3.7.2.1 or by seaming as specified in 3.7.2.2.

3.7.2.1 Looped toe closure. The toes shall be closed with a looper using not less than two ends of the yarn specified in 3.3.1.1. The looping line shall be as elastic as the knit fabric and shall be smooth and free from lumps, laps and cuts.

3.7.2.2 Seamed toe closure. The toes shall be closed by turning the socks inside out, superimposing the two edges of the opening, and stitching using stitch type 521 and seam type SSa-1 conforming to FED-STD-751. The thread specified in 3.3.3.1 shall be used for the needles and looper. The stitches per inch shall be 50 to 56 in the relaxed state. A 1/4 to 1 inch stitched thread chain shall be left at each end of the row of stitching. The socks shall then be turned right side out and the seam pulled flat so that the edges of the toe opening are butted as in seam type FSa-1 of FED-STD-751. The seamed closure shall be as elastic as the knit fabric, shall lie flat and shall be free from lumps, laps, and cuts.

3.7.3 Yarn ends. All loose ends of yarn on the inside of the finished socks shall be trimmed to not less than 3/8 inch nor more than 1 inch long. Floated ends, which at one extremity are firmly attached as a part of the knitted fabric with the other end loosely caught in the stitch shall be regarded as loose ends.

3.7.4 Finishing. The socks shall be scoured and boarded on drying forms to their proper minimum size and length.

3.7.5 Pairing. The socks shall be matched and paired so that there will be not more than 1/4 inch difference in foot length, and not more than 1/2 inch difference in leg length. The use of thread, twine or staple to secure the pair of socks is not permitted.

3.8 Physical requirements.

3.8.1 Sizes, measurements, number of courses and weight. Sizes and measurements of the finished socks shall be as shown in Table I. The number of courses and the weight per dozen of the finished socks shall conform to the requirements shown in Table I when tested as specified in 4.4.3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

Table I - Sizes, measurements, number of courses and weight of finished socks

		S	M	L	TOLERANCE
Leg					
(A)	Number of courses 1/	134	194	240	Minimum
(B)	Length (inches)	15 1/2	18	20 1/2	± 1/2
Foot					
(C)	Number of courses 2/	122	156	184	Minimum
(D)	Length (inches)	8 1/2	10	11 1/2	± 1/4
French top (inches)		6	6	6	± 1/4
(E)	Number of courses	124	124	124	Minimun
(F)	width (inches)	2 3/8	2 3/8	2 3/8	Minimun
(G)	Ring toe width (inches)	1	1	1	Minimum
Weight(ounces per dozen pairs)		16	17	18	Minimum

1/ Leg courses shall be counted from first short butt heel gore needle to bottom edge of elastic ribbed top.

2/ Foot courses shall be counted from bottom edge of welt to joining line of leg fabric.

NOTE: A, B, C, D, E, F, and G refer to Figure 1. All measurements shall be taken with the socks laid flat and smooth and without tension.

3.8.2 Stretch. The finished sock shall conform to the requirement specified in Table II when tested as specified in 4.4.3.

Table II - Minimum stretch requirements for finished socks

	S	M	L
Crosswise stretch (inches)			
Leg 1/	8	8	8
Foot 2/	8	8	8
Lengthwise stretch (inches)			
Foot	13	15	17

Source: https://assist.dla.mil Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

1/ Measure across a point midway between bottom of heel and top of sock.

2/ Measure across a point midway between heel and toe.

3.8.3 Bursting strength. The leg fabric of the finished socks shall have a minimum bursting strength of 85 pounds when tested as specified in 4.4.3.

3.8.4 Nonfibrous materials. The starch and protein content including chloroform-soluble and water-soluble material of the finished sock shall not exceed 2.0 percent when tested as specified in 4.4.3.

3.8.5 pH. The pH values of the water extracts of the finished socks shall not be less than 5.5 nor more than 8.5 when tested as specified in 4.4.3.

3.9 Workmanship. The finished socks shall conform to the quality and grade of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels.

3.10 Label. Each sock shall have a size marking applied just below the rib knit and centered between the ankle and toe. The size marking shall conform to type III, class 9 of DDD-L-20. The color of the marking medium shall be white.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

4.3 First article inspection. The first article submitted in accordance with 3.2 shall be inspected as specified in 4.4.2 for compliance with design, construction, workmanship and dimensional requirements.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

4.4 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.4.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable procurement documents. In addition, components and materials listed in Table IV shall be tested for the characteristics specified and in accordance with the referenced test methods of FED-STD-191 unless otherwise specified herein. The sample unit for the yarns and thread shall be one spool, cone or tube and the lot size shall be expressed in units of one spool, cone, or tube. The lot shall be unacceptable if one or more units fail to meet any requirement specified. All test reports shall contain the individual values utilized in expressing the final result. The sample size shall be as follows:

Table III - sample size

Lot size	Sample size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

Table IV - Component tests

Component	Characteristic	Reference requirement	Test method
Knitting yarn:	Ply	3.3.1	Visual 1/
	Twist	3.3.1	4054 2/
Nylon yarn:			
Body	Material identification	3.3.1.1	3/
	Ply	3.3.1.1	Visual 1/
	Denier	3.3.1.1	3/
Heel and toe	Material identification	3.3.1.1	3/
	Ply	3.3.1.1	Visual 1/
	Denier	3.3.1.1	3/
Acrylic yarn:	Material identification	3.3.1.2	3/
	Ply	3.3.1.2	Visual 1/
	Count	3.3.1.2	3/

Source: https://assist.dla.mil - Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

Table IV - Component tests - (continued)

Component	Characteristic	Reference requirement	Test method
Elastic yarn:			
Core:	Material identification	3.3.2	3/
	Denier	3.3.2	3/
Cover yarn:	Material identification	3.3.2	3/
	Denier	3.3.2	3/
Thread	Material identificaton	3.3.3	3/
	Ply	3.3.3	Visual 1/
	Size	3.3.3	3/
	Yards per pound	3.3.3	4010
	Breaking strength	3.3.3	4100
	Elongation	3.3.3	4100
Looper yarn:	Material identification	3.3.3.1	3/
	Denier	3.3.3.1	3/

1/ One determination shall be made from each sample unit and the results reported as "pass" or "fail".

2/ Determination of twist contraction is not applicable.

3/ A certificate of compliance shall be submitted for this characteristic.

4.4.2 Examination of the end item. Examination of the end item shall be in accordance with 4.4.2.1 and 4.4.2.2. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 4.4.2.3. The sample unit shall be one sock and the selection shall be by pairs. The lot size shall be expressed in units of one sock.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

4.4.2.1 Visual examination. The finished socks shall be visually examined for defects in accordance with the list below:

Defect	Classification Major	Minor
Any hole, run, or dropped stitch, including any hole in looping	X	
Thin area or mend	X	
Welt omitted, cut, frayed or raveled	X	
Welt uneven or not clearly defined		X
Poor looping or fashioning of heel and toe gores resulting in tight tension, lumps, and dog ears; will not level out.	X	
Looped with less than two yarns	X	
Loose or floated ends:		
a. Not trimmed or trimmed less than 3/8 inch or more than 1-1/2 inches long		X
b. Any floated ends on outside of sock	X	
Pattern of knit not as specified	X	
Sock not knitted as integral unit	X	
Ring toe omitted	X	
Elastic yarn omitted or improperly inserted	X	
End out for more than one course	X	
Nonuniform in overall appearance; not well shaped		X
Slubby yarn		X
Streaks, stains, spots or shadebars clearly noticeable 1/		X
Not color specified (off shade or mismatch of shade)		X
Rancid or bad odor		X
Wrong size board used	X	
Stretch lacking (tight) or loosely knit (slack or sleazy)	X	
Burn or scorch in fabric	X	
Label missing, incorrect or illegible		X
Seamed toes:		
a. Wrong seam or stitch type	X	
b. Sewing thread chain less than 1/4 inch or more than 1 inch		X
c. Any hole at either end of the seamed toe	X	
d. Skipped stitches, run-offs, broken thread resulting in any open seam	X	
e. Edges of toe opening do not abut or are overlapped		X
f. Seam not flat or smooth		X
g. Stitches per inch more or less than specified		X
h. Label missing ,incorrect ,or illegible		X

1/ At normal inspection distance (approximately 3 feet).

4.4.2.2 Dimensional examination. The finished sock shall be examined for defects in dimensions in accordance with the following:

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

a. Any measurement deviating from dimensions and tolerances specified shall be scored as a measurement defect.
b. A defect shall be scored if a pair of socks is mismated so that there is a difference of more than 1/4 inch in foot length or more than 1/2 inch in leg length.

4.4.2.3 Inspection levels and acceptable quality levels. The inspection and acceptable quality levels (AQL's) expressed as defects per 100 units (DHU) for visual and dimensional examinations shall be as follows:

	AQL's	Inspection level
For examination in 4.4.2.1:		
Major	1.5	II
Total (Major and Minor combined)	4.0	II
For examinination in 4.4.2.2:		
One class	4.0	S-3

4.4.3 Testing of the end item. The methods of testing specified in FED-STD-191, wherever applicable, and as listed in Table V shall be followed. The physical and chemical values specified in Section 3 apply to the average of the determinations made on a unit of product for test purposes as specified in the applicable test method. All test reports shall contain the individual values utilized in expressing the final result. The lot size shall be expressed in units of one sock. The sample unit shall be twelve pairs of socks. The sample size shall be in accordance with Table III and the lot shall be unacceptable if one or more units fail to meet any requirement specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

Table V - End item tests

Characteristics	Requirement reference	Test method
Labile sulfur	3.4	2020
Colorfastness to: 2/		
Perspiration	3.4.2	5680
Laundering (after 3 cycles)	3.4.2	5610 1/
Weight per dozen pairs (oz.)	3.8.1	4.4.3.1
Number of courses:		
Leg	3.8.1	5070 3/
Foot	3.8.1	5070 3/
Elastic top	3.8.1	5070 3/
Stretch-crosswise (inches):		
Leg	3.8.2	4.4.3.2
Foot	3.8.2	4.4.3.2
Elastic top	3.8.2	4.4.3.2
Stretch-lengthwise (inches):		
Foot	3.8.2	7560 4/
Bursting strength (lbs)	3.8.3	5120
Nonfibrous materials (percent)	3.8.4	2611
PH	3.8.5	2811

1/ The specimen must be dried after each of the 3 laundering cyles.

2/ The specimen only shall be rated.

3/ Courses per inch is not applicable.

4/ Determination of relaxation shrinkage and shrinkage after laundering is not applicable. The measured stretched "foot length" shall be read to the nearest 0.1 inch and shall be reported as the "lengthwise stretch."

4.4.3.1 Determination of weight per dozen socks. The weight per dozen pairs of socks shall be determined using a scale calibrated in ounces and capable of being read to the nearest 0.25 ounce. The socks shall be weighed in a conditioned state as indicated in Section 4 of FED-STD-191. Twelve pairs of socks shall be placed on the scale at one time. Results shall be reported to the nearest 0.25 ounce.

Source: https://assist.dla.mil Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

4.4.3.2 Determination of crosswise stretch. The crosswise stretch of the sock shall be determined using as Houchin modification of a Schieffer machine consisting of a metal separating form which shall be fixed in front of an upright arm having a scale graduated in divisions of 0.1 inch with a freely rotating pulley at the top. An indicator consisting of a pointer pin which is inserted through the sock and the hole in the form shall be provided. The indicator shall be attached by means of a cord which passes over the pulley to a weight (see Figure 2). Testing shall be performed by positioning a 2-inch portion of the body of the sock over the top and bottom of the separating form, inserting the pointer pin and applying a 10-pound weight. The weight shall be applied slowly to insure a uniform load. The sock shall be evaluated after the weight has hung freely for 30 seconds, and shall be expressed in inches to the nearest 0.1 inch as the distance between the upper and lower edge of the separated form. Right socks of each pair in the lot shall be tested.

4.4.4 Examination of packaging requirement. An examination shall be made to determine that packaging, packing, and marking comply with Section 5 requirements of this specification. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery except that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per 100 units.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, sequence or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Inadequate application of components, such as incomplete closure of container flaps, improper taping, loose strapping, or inadequate stapling; bulging or distortion of container.
Content	Number of bundles per container is more or less than specified. Number per bundle is more or less than specified. 1/

1/ For this defect, one bundle shall be examined from each shipping container in the sample.

4.4.5 Palletization examination. An examination shall be made to determine that the palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the end item inspection lot. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

Examine	Defect
Finished dimensions	Length, width, or height exceeds specified maximum requirements.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted; incorrect; illegible; of imroper size, location, sequence, or method of application.

5. PACKAGING

5.1 Packaging. Packaging shall be level A.

5.1.1 Level A. Each banded pair of socks shall be neatly folded at the heels in accordance with industry's practices. Twelve (12) pairs of socks of one type only shall be evenly stacked in a bundle, with every other pair or every six pairs reversed, and securely tied at each end with cotton tape or twine.

5.2 Packing. Packing shall be level B.

5.2.1 Level B. One hundred twenty (120) pairs of socks of one type only, packaged as specified in 5.1 shall be packed in a snug fitting fiberboard shipping container conforming to style RSC-L, Type CF, (variety SW), or SF, class domestic, grade 200 of PPP-B-636. The inside of each shipping container shall be fitted with a liner conforming to Type CF, class domestic, variety SW or DW, grade 200 of PPP-B-636. Level A bundle shall be packed within a shipping container in two layers of five bundles each layer. The inside of each shipping container shall approximate 16-1/2 inches in length, 11-1/2 inches in width, and 8-1/2 inches in depth. Approximate dimensions are furnished as a guide only. Each shipping container shall have the contents completely covered on top and bottom with a sheet of commercial grade kraft paper. Each shipping container shall be closed in accordance with method II as specified in appendix of box specification.

5.3 Palletization. When specified (see 6.2), socks, packed as specified in 5.2, shall be palletized in accordance with load type Ia of MIL-STD-147. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means K and L or film bonding means O or P. Pallet patterns shall be in accordance with the appendix of MIL-STD-147. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the pallet patterns specified in MIL-STD-147, the pallet pattern used shall first be approved by the Contracting Officer.

5.4 Marking. In addition to any special marking required by the contract or order, shipping containers and palletized unit loads shall be marked in accordance with MIL-STD-129.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

5.4.1 Labels ,mixed sizes. Each shipping container packed with mixed sizes, shall have securely attached to the end and side, directly under the printing or stenciling, a white paper label 5 by 4 inches with the words "MIXED NSN'S" plainly stamped or printed thereon and under these words shall be legibily stamped or printed the correct quantity and nsn's contained therein.

6. NOTES

6.1 Intended use. The socks are intended for use by male personnel as a component of the dress and work uniforms.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number and date of the specification.
b. Size required (see 1.2).
c. When first article sample is required (see 3.2). The item will be tested and should be a first article sample. The Contracting Officer should include specific instructions in acquisition documents regarding arrangements for examinations, quantity, and testing and approval of the first article.
d. Selection of applicable levels of preservation and packing (see 5.1 and 5.2).
e. When palletization is required (see 5.3).

6.3 Samples. For access to samples, address the procuring activity issuing the invitation for bids.

Custodian:
Navy - NU
Air Force -11

Preparing activity:
Navy - NU

Review:
Air Force - 82, 99

Project Number:
8440 -0165

User:
Air Force -45

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

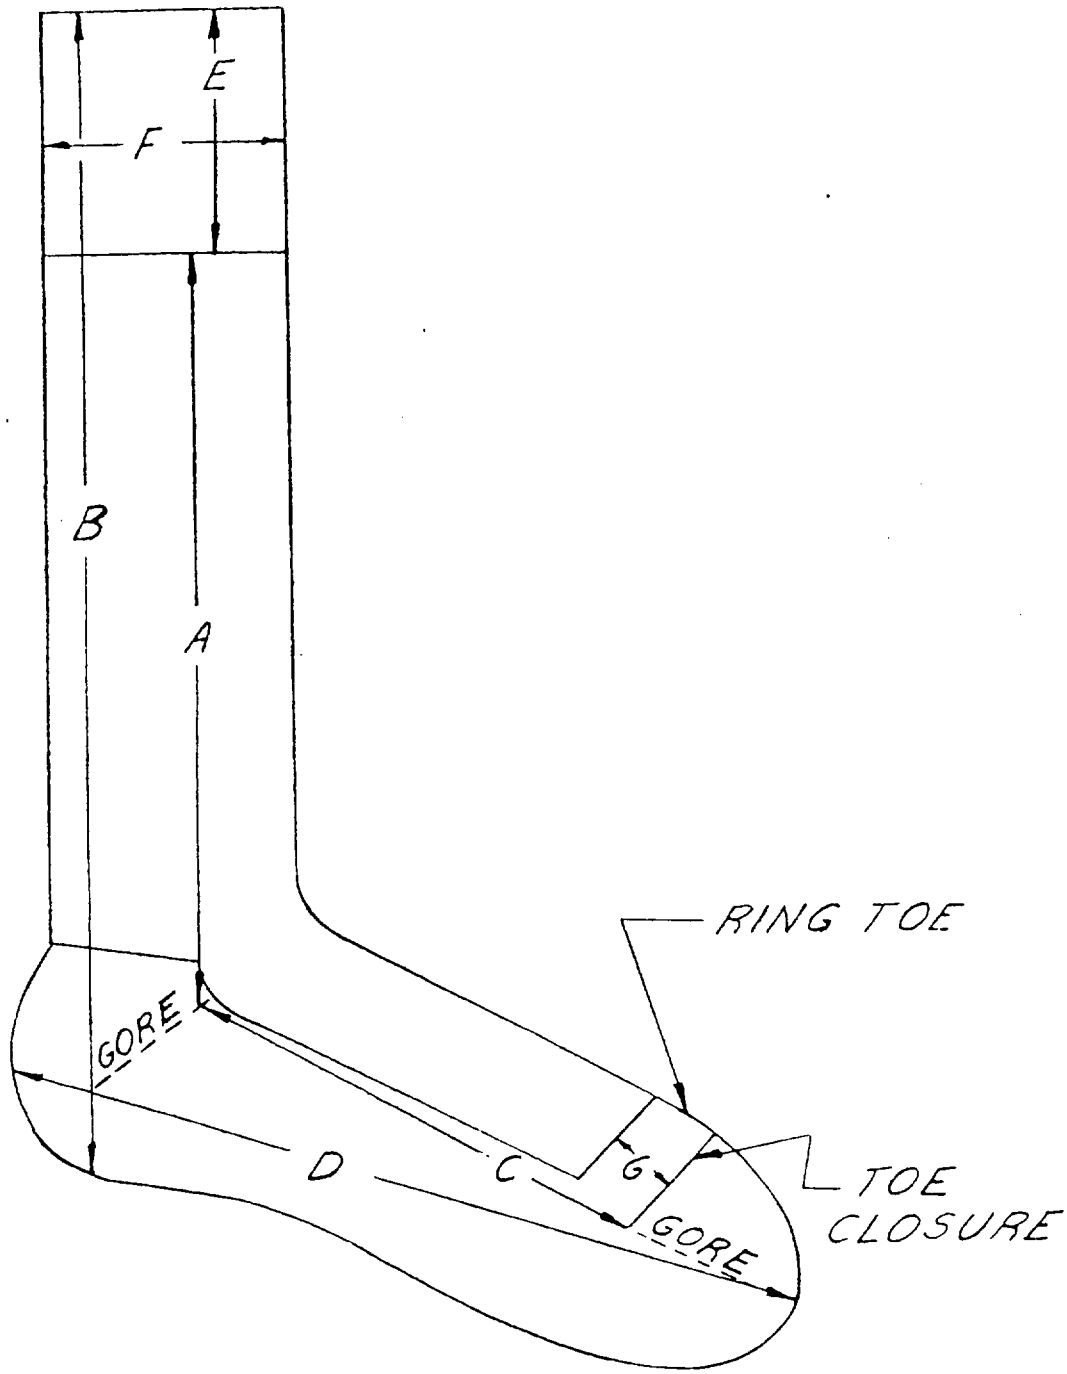


Fig. 1 Socks, Men's, Acrylic/Nylon, Ribbed, Stretch Type

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

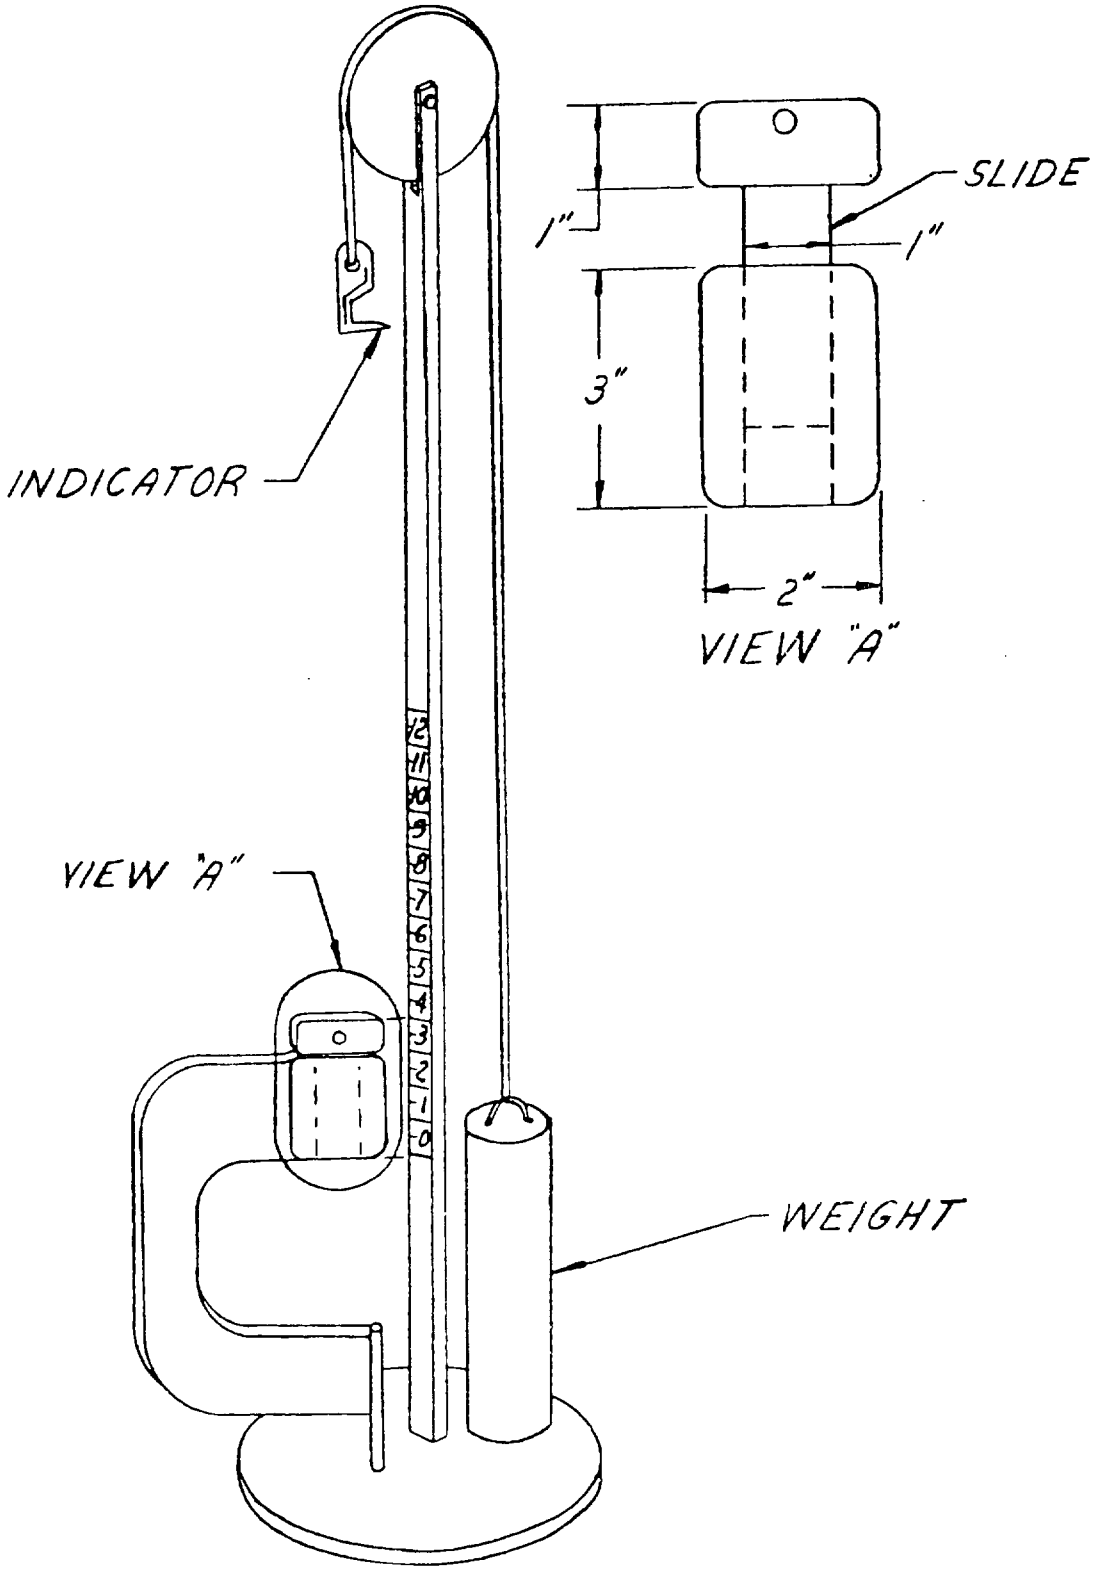


FIGURE 2 HOUCHIN MODIFICATION OF SCHIEFFER MACHINE

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Officer in Charge
Navy Clothing & Textile Research Facility
Code 50
21 Strathmore Road
Natick, MA 01760

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-S-24917	SOCKS, MEN'S, ACRYLIC/NYLON, RIBBED, STRETCH TYPE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

Source: https://assist.dla.mil -- Downloaded: 2026-10-20T02:56Z
Check the source to verify that this is the current version before use.