MIL-M-82272B(SA)
24 November 1975
SUPERSEDING
MIL-M-82272A(SA)
3 November 1970

MILITARY SPECIFICATION

MITTEN, WET SUIT (CHLOROPRENE FOAM)

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope.- This specification covers the requirements for a Mitten, Wet Suit, fabricated from closed cell chloroprene foam.

1.2 Classification.- The mitten shall be of one type only and of the following sizes (see 6.2).

Schedule of Sizes

Small/Medium
Large/Extra Large

2. APPLICABLE DOCUMENTS

2.1 The following documents of the issue in effect on the date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

SPECIFICATIONS

FEDERAL

V-T-285	- Thread, Polyester
DDD-L-20	- Labels, For Clothing, Equipage and Tentage (General Use)
PPP-B-566	- Boxes, Folding, Paperboard
PPP-B-601	- Boxes, Wood, Cleated-Plywood
PPP-B-636	- Box, Fiberboard
PPP-T-76	- Tape, Pressure-Sensitive Adhesive, Paper, (For Carton Sealing)

FSC 4220

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-356	- Commercial Packaging of Supplies and Equipment
FED-STD-751	- Stitches, Seams, and Stitchings

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage

(Copies of specifications, standards, drawings and publications required by suppliers in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer).

2.2 Other publications.- The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply:

American Society for Testing and Materials

D-1056 - Test for Sponge and Expanded Cellular Rubber Products

(Copies of ASTM Publications may be obtained from the American Society for Testing Material, 1916 Race Street, Philadelphia, PA 19103).

3. REQUIREMENTS

3.1 Guide sample.- Samples when furnished are solely for guidance to the supplier (see 6.3). Variations from this specification may appear in the sample in which case this specification shall govern.

3.2 First article approval.- The requirement for First Article will be as specified by the procuring activity (see 6.2).

3.3 Materials.-

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

3.3.1 Chloroprene foam.- The chloroprene foam for the mittens shall be of expanded chlorinated cellular rubber, pigmented Black, 3/16 (± 1/32) inch (4.8 ± .8mm) thick, having a closed cell structure conforming to ASTM designation SCE 41, and other requirements set forth herein when tested as specified in 4.3.1.1. It shall have a minimum density of 10 and a maximum density of 20 pounds per cubic foot (minimum density of 157.5 and maximum density of 315 grams per cubic centimeters), with a natural skin surface on one or two sides.

3.3.2 Knitted stretch cloth.- The stretch cloth shall be circular knit from 100% continuous filament stretch type nylon yarn and shall conform to the physical requirements specified in table I when tested as specified in 4.3.1.1.

Table I - Knitted stretch cloth

Knitted stitch	Yarn per inch (min) Wales	Courses	(Yarn per cm. (min) Wales	Courses	Weight oz per sq. yd	(gr per sq m.)	Elongation % Wales	Courses	Color
Jersey	20	30	(7.9)	(11.8)	3.0 ± 0.25	(100.8 ± 7)	140 min. 200 max.	200 min. 280 max.	Black

3.3.2.1 Colorfastness.- The knitted cloth shall show fastness to laundering, crocking and perspiration equal to or better than the standard sample. When no standard sample is available, the finished material shall show a minimum of "good" fastness to laundering, perspiration, and a Munsell value for crocking not lower than 8.5. Testing shall be as specified in 4.3.1.1.

3.3.3 Lamination.- The stretch cloth shall be laminated to one side of the 3/16 inch (4.8mm) chloroprene foam by means of a suitable adhesive, or other process capable of meeting the physical requirements of the laminated foam material. If the foam has no side with a cut surface, the stretch cloth shall be laminated on any side. When foam has a cut surface on one side the stretch cloth shall be laminated to the cut side. The adhesive used shall be non-toxic, non-irritant and free from objectionable odor. The fabric backed (laminated) side shall be smooth and free of wrinkles or puckers, and show no signs of blocking, tackiness or ahdesive strike-through.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

3.3.3.1 Laminated foam.- The finished laminated foam material shall conform to table II when tested as specified in 4.3.1.1.

Table II - Laminated foam

Compression Set % Max.	Compression deflection PSI (g/cm^2)	Accelerated aging shrinkage % Max. in each direction	Water Absorption % Max.	Laundering resistance	Adhesion original lbs. (kg) min. per two inches (50.8 mm)	Adhesion after launderings lbs. (kg) min. per two inches (50.8 mm)	Adhesion after aging lbs (kg) min. per two inches (50.8mm)	Blocking
35	2.0(139) Min. 7.0(486.5) Max.	5.0	15.0	No delamination	6.0 (2.7)	6.0 (2.7)	6.0 (2.7)	No blocking

3.3.4 Thread, Polyester.- The thread used for sewing the side seams shall conform to type II, Class 1, 4 ply, letter size F of V-T-285. The color of the thread shall be black AA, Cable No. 66043.

3.3.4.1 Colorfastness.- The dyed thread shall show fastness to laundering, perspiration and light equal to or better than the standard sample when tested as specified in V-T-285. When no standard sample is available, the dyed thread shall show a minimum of "good" fastness to laundering, perspiration and light when tested as specified in V-T-285.

3.3.5 Adhesive cement.- The cement used to seal the seams shall be a chloroprene compound and shall conform to the requirements specified herein when inspected as specified in 4.3.1.1.

3.3.6 Marking.- The marking shall be applied on each mitten with a yellow marking medium conforming to Type IV, Class 1 of DDD-L-20. Marking shall be applied to the inside of mitten centered on left side one inch (25.4mm) from the top edge of the mitten. The marking shall be permanent and shall not run, bleed or rub off when tested as specified in paragraph 4.3.1.1. The inscription shall read as follows:

Name of Item: Mitten, Wet Suit (Chloroprene Foam)
Contract No: DSA-100-00-0-000 (Example)
Stock No. 4220-00-000-0000 (Example)
Size: Small/Medium (Example)
Name of Supplier:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

3.3.6.1 Special marking.- A white paper label printed or stamped with black block letters 1/8 inch (3.2mm) high for capital letters and 1/16 inch (1.6mm) for lower case letters bearing the following information shall be placed inside one mitten of each pair.

"To prolong the life of the mitten, observe the following instructions for care and handling:

1. Do not pull and tug mitten on or off since the foam may tear or split at the seams. If required, dust inside of mitten with talc to facilitate donning.
2. To remove, turn mitten inside out.
3. After each use, wash with fresh water.
4. Allow to dry before storing.
5. Do not crease or fold in storage."

3.4 Design.- The mitten shall be ambidextrous, trigger finger design and made of laminated closed cell chloroprene foam material. All seams shall be cemented and the seams at the top opening shall also be reinforced with stitching (see figure 1).

3.4.1 Figure.- Figure 1 is furnished for information purposes only. To the extent of any inconsistencies between the written specification and the figure, the written specification shall govern.

3.5 Patterns.- Standard patterns will be furnished by the Government. The standard patterns shall not be altered in any way and are to be used for cutting the suppliers working patterns. The working patterns shall be identical to the standard patterns.

3.5.1 Pattern parts.- The component parts of the mitten shall be cut from the material specified in accordance with the following pattern parts.

Material	Nomenclature of Pattern Parts	Cut Parts
Laminated foam	Top of hand	1
	Bottom of hand	1

3.6 Construction.-

3.6.1 Stitch, seam and stitching types.- Stitch, seam, and stitching types specified in Table III shall conform to FED-STD-751.

3.6.2 Thread breaks and ends of seams.- The ends of the side seam stitching shall be securely tacked or backstitched not less than 3/8 inch (9.5mm).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

3.6.3 Stitches per inch.- The minimum and maximum number of stitches per inch shall be as specified in Table III.

3.6.4 Cemented seams.- The cemented seams shall have a minimum breaking strength of 28 pounds per two inches (12.6kg per 50.8mm) when tested as specified in 4.3.1.1.

3.7 Manufacturing requirements.- The mitten shall be manufactured in accordance with the operation requirements specified in Table III. The supplier is not required to follow the exact sequence of operations listed provided that the finished mittens are identical to that produced by following the sequence of operations as listed in Table III. The smooth natural skin side of the foam rubber shall be used as the face of the material and shall be on the outside.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Table III - Construction of mittens

No.	Description of Operation	Stitch Type	Seam and Stitching Type	Stitches Per Inch	Thread	
					Needle	Bobbin or Looper
1.	Cutting of laminated foam material The mitten shall be cut in accordance with patterns furnished which shall show size, shape and markings for proper assembly of all component parts.					
2.	Replacement of damaged components During the spreading, cutting and manufacturing process components having material defects or damages that are classified as defects in Section 4, shall be removed from production and replaced with non-defective and properly matched components.					
3.	Part markings a. All parts of the basic material shall be marked or ticketed to insure proper assembly and size. b. The use of metal fastening devices or sew-on tickets is prohibited. c. The use of ink pad numbering machine, rubber stamp or pencil is allowed providing the numbering does not show on the outside of the mittens.					
4.	Preparing components for assembly a. Apply two coats of chloroprene cement to all areas to be abutted; 24 hours prior to assembly. b. Apply two additional coats of chloroprene cement to all area to be abutted, after the 24 hour period. (No solvent is required on seams).					

NCTR Form 1, 15 Sep 1967

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Table III - Construction of mittens (cont'd)

No.	Description of Operation	Stitch Type	Seam and Stitching Type	Stitches Per Inch	Thread	
					Needle	Bobbin or Looper
4.	Preparing components for assembly (cont'd) c. The abutted seams shall be overcoated 1/4 (± 1/16) inch (6.4 ± 1.6mm) beyond seams on the outside and on the inside of the mitten.					
5.	Assembly instruction a. Insure that all seams to be cemented are cleaned of foreign matter, and are tacky prior to joining. b. Allow more time for curing on critical curves prior to the next step of joining.					
6.	Assembly of mitten a. Place two parts of the mitten side by side. b. Abut the two parts; commence at the top and cement around the periphery of mitten.					
	c. Stitch the top of cemented seams extending 1 1/2 (± 1/8) inches (38 ± 3.2mm) from the top opening. The needle bite across the abutted edges shall be not less than 5/16 inch (7.9mm) with the abutted edge centered between the stitches.	304	FSa-1	4-5	F	F
7.	Markings Mark each mitten as specified in 3.3.6.					
8.	Cleaning a. Trim all thread ends. b. Remove all loose threads. c. Remove all spots, stains and excessive cement without injury to the material.					

NCTR Form 1, 15 Sep 1967

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

3.8 Sizes and measurements.- The sizes and measurements of the finished mittens shall conform to the measurements shown in Table IV. All measurements and tolerances are expressed in inches and millimeters. The measurements shall be taken as indicated below (see figure 1).

Table IV

Size	Length A	Width palm B	Top opening C
Small/Medium	11 3/8 (289)	4 1/4 (108)	3 3/4 (95)
Large/Extra Large	11 1/2 (292)	4 1/2 (114)	4 (102)
Tolerances	± 1/8 (3.2)	± 1/8 (3.2)	± 1/8 (3.2)

NOTE: The measurements shall be taken with the mitten laid flat and in a relaxed condition.

Length A - Length shall be measured from top opening of mitten in a line perpendicular to the top opening to tip of index finger.

Width Palm B - Width measured with a line parallel to top opening from base of index finger where thumb is attached to side of mitten.

Top opening C- Width of top opening shall be measured from side to side.

3.9 Workmanship.- The finished mittens shall conform to the quality of product established by this specification. The occurrence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISION

4.1 Responsibility for inspection.- Unless otherwise specified in the contract or order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order the supplier may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to the prescribed requirements.

4.1.1 Certificates of compliance.- Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

4.2 First article inspection.- When required, the first article submitted in accordance with 3.2 shall be inspected as specified in 4.3.2, for compliance with design, construction, workmanship, appearance, and dimensional requirements.

4.3 Inspection.- Inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.3.1 Component and material inspection.- In accordance with 4.1 above, components and materials shall be inspected and tested in accordance with all the requirements of reference specifications, drawings, and standards unless otherwise excluded, amended, modified or qualified in the specification of applicable purchase document.

4.3.1.1 Testing of components.- In addition to the quality assurance provisions of the referenced specifications, components listed in table VI shall be tested for the characteristic shown therein. The tests shall be performed on specially prepared cemented seams, similar to those on the end item. The methods of testing specified in FED-STD-191 wherever applicable and as specified herein shall be followed. All test reports shall contain the individual values utilized in expressing the final result. The sample size shall be in accordance with Table V and the lot shall be unacceptable if one or more units fail to meet any requirements specified. The basis for lot size for the laminated and unlaminated chloroprene foam shall be one sheet and one yard full width for the knitted stretch fabric. The sample unit for testing shall be as follows:

Unlaminated foam	- one square yard (.8 square meter)
Laminated foam	- one sheet
Knitted stretch fabric	- one yard (.9 meter) full width

Table V - Sample size

Lot Size	Sample Size
800 or less	2
801 up to and including 22,000	3
22,001 and over	5

Table VI - Testing of Components

Component	Characteristic	Requirement Paragraph	Test Method
Chloroprene Foam	Material identification	3.3.1	1/
	Color	3.3.1	Visual 2/
	Thickness	3.3.1	ASTM D 1056 3/
	Density	3.3.1	4.3.1.1.1

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Table VI Testing of Components (cont'd)

Component	Characteristic	Requirement Paragraph	Test Method
Knitted Stretch Cloth	Material identification	3.3.2	1/
	Filament	3.3.2	1/
	Weight	3.3.2	5040
	Wales and Courses/ inch (cm.)	3.3.2	5070
	Elongation	3.3.2	4.3.1.1.2
	Color	3.3.2	Visual 2/
	Colorfastness:		
	Laundering	3.3.2.1	5614
	Crocking	3.3.2.1	5651
	Perspiration	3.3.2.1	5680
Laminated foam	Compression set	3.3.3.1	ASTM D 1056 4/
	Compression deflection	3.3.3.1	ASTM D 1056
	Shrinkage after accelerated aging	3.3.3.1	4.3.1.1.3
	Water absorption	3.3.3.1	4.3.1.1.4
	Laundering resistance	3.3.3.1	5556 6/
	Adhesion		
	Initial	3.3.3.1	5950 5/
	After 3 launderings	3.3.3.1	5556 and 5950 5/ 6/
	After aging	3.3.3.1	4.3.1.1.3 and 5950 5/
	Blocking	3.3.3.1	5872 7/
Markings	Permanency	3.3.6	4.3.1.1.5
Adhesive Cement	Material identification	3.3.5	1/
Cemented seam	Breaking strength	3.6.4	5100 8/

1/ A certificate of compliance will be accepted as evidence of conformance with the requirement.
2/ One determination shall be taken.
3/ Thickness: Except that 5 determinations shall be made.
4/ Compression set - Test shall be run at room temperature for 22 hours with a recovery time of 24 hours.
5/ Adhesion - Except that the distance between the clamps shall be one inch at the start of the test. The use of a suitable solvent (e.g. MEK) to help separate the fabric from the foam sufficiently to fit the clamps is permissible. The adhesion shall be tested in the fabric's length (wale) direction only.
6/ Laundering - Except that five 8 by 8 inch (203 by 203mm) specimens shall be tested and three cotton laundering cycles performed.
7/ Blocking - Except specimens 4 by 4 inches (102 by 102mm) shall be placed together fabric side to fabric side.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

8/ Cemented seam strength - The cemented seams shall be centered equidistant from the clamps. All breaks shall be made with the seam at right angles to load direction. The clamps shall be one inch (25.4mm) apart at the start of the test and the face of each jaw shall be not less than 1 by 2 inches (25.4 by 50.8mm). The cemented seam test specimen shall be rectangular, 2 inches (50.8mm) wide by not less than 6 inches (152.4mm) long.

4.3.1.1.1 Density.- Five specimens each 2 inches (50.8mm) square shall be weighed separately to the nearest 0.001 gram on an analytical balance. The thickness of each specimen shall be determined in accordance with ASTM method D1056 and the following formula shall be used to determine density.

$$D = \frac{0.95 \times W}{T}$$

Where D = density in lbs/ft^3 (grams per cm^3)
W = the sum of the weights of the 5 specimens (grams)
T = the sum of the thickness of the 5 specimens (inches)

4.3.1.1.2 Elongation.- An incline plane type of machine (i.e., I-P-4 or similar type) with a suitable autographic recording device shall be used. Specimens of the fabric shall be cut 4 by 6 inches (102 by 152mm) with the long direction parallel to the direction to be tested. The specimen shall be evenly aligned without tension or slack in the 1 by 3 inch (25.4 by 76.2mm) clamps set two inches (50.8mm) apart. The machine shall run through two complete cycles, proceeding to its maximum depression so as to exert a five pound (2.25kg) tension. Five specimens, each containing different wales and courses shall be tested, using individual recorded elongation graphs. The average stretch of five specimens for each direction shall be measured at the peak of the last recorded cycles, in a line perpendicular to the horizontal zero axis and reported to the nearest percent.

4.3.1.1.3 Accelerated aging.- Three square specimens each with a minimum dimension of 8 by 8 inches (203.2 by 203.2mm) shall be measured to the nearest 1/32 inch (.8mm) in both length and width direction by means of a steel rule. The specimens shall be suspended vertically in an air-oven at 158°F (± 2°F) (70°C ± 1°C) for seven days. At the conclusion of the aging interval, the specimens shall be cooled at room temperature on a flat surface and allowed to rest at least 4 hours before determination of shrinkage. The average shrinkage in each direction shall be calculated as follows and reported to the nearest 0.1 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

$$\text{Percent shrinage} = \frac{O-A}{O} \times 100$$

Where:

O = Original length or width (inches) (mm)
A = Length or width after aging (inches) (mm)

4.3.1.1.4 Water absorption.- Three specimens each 4 x 6 inches (101.6 by 152.4mm) shall be weighed separately on an analytical balance to the nearest 0.1 gram. The specimens shall be placed in a tumble jar apparatus (as described in TM 5500 of FED-STD-191) containing two liters of distilled water and rotated for 20 minutes. At the end of the rotating period the specimens shall be immediately removed from the water, without pressure blotted dry of surface water with filter paper or other absorbent material and weighed. The average percent water absoprtion shall be calculated as follows and reported to the nearest 0.1 percent.

$$\text{Water absorption, percent} = \frac{W2 - W1}{W1} \times 100$$

Where:

W1 is weight of specimen before immersion
W2 is weight of specimen after immersion

4.3.1.1.5 Marking test.- The marking shall be tested by rubbing a wet white cotton print cloth across markings six times using normal pressure. There shall be no staining of the cotton cloth. The markings shall be complete in all details as specified in regard to correctness, completeness, legibility, and location. Any of the above attributes that are not as specified shall be classified as a defect.

4.3.2 Examination of the end item.- Examination of the end item shall be in accordance with 4.3.2.1 and 4.3.2.2. The applicable inspection levels and acceptable quality levels (AQL's) shall be as indicated in 4.3.2.3. The sample unit shall be one finished pair of mittens. The lot size shall be expressed in units of one mitten.

4.3.2.1 Visual examination.- The mittens shall be examined for defects in color, design, material, workmanship and marking and the defects classified in accordance with the list below:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Defect	Classification Major	Minor
MATERIAL DEFECTS AND WORKMANSHIP DAMAGES		
a. Any hole	X	
b. Any weakening defect such as deep creases or fold lines	X	
c. Needle chew	X	
d. Cut, tear or mend	X	
e. Unsightly cement mass		X
BASIC MATERIAL		
a. Any evidence of delamination	X	
b. Any brittle area which cracks when bent	X	
c. Area of excess cement, e.g., solid runs, ridges or lumps		X
d. Chloroprene foam or cement tacky	X	
e. Any imbedded foreign material easily removed resulting in damage of basic material	X	
f. Any imbedded foreign matter not easily removed, but if removable does not damage base material		X
g. Any blister or pin hole	X	
h. Mottled, cloudy or streaky finish		X
i. Any objectionable odor		X
CLEANNESS		
a. One or more spots or stains of an obvious permanent nature (excessive cement on outside surface of foam)		X
b. Thread ends not trimmed or loose thread ends not removed from mitten		X
COMPONENT AND ASSEMBLY		
Any component part omitted or any required operation omitted or improperly performed (unless otherwise classified herein)	X	
CUTTING		
Any component part not cut in accordance with marks indicated on pattern or not in accordance with specification requirements	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Defect	Classification Major	Minor
SEAMS AND STITCHING		
a. Stitching omitted	X	
b. Not specified seam or stitch type		X
c. Less than or more than the required stitches per inch		X
d. Thread breaks not secured or stitching back of the break less than 1/2 inch (12.7mm)		X
e. Ends of stitching not securely tacked or back-stitched less than 3/8 inch (9.5mm)		X
f. Stitching less than 1 3/8 inches (34.9mm) or more than 1 5/8 inches (41.3mm)from top opening		X
g. Open seam	X	
CEMENTED SEAMS		
a. Any open seam	X	
b. Uneven seam		X
c. Twisted or puckered seam	X	
d. Seam not properly joined		X
MARKING AND SPECIAL MARKING		
a. Omitted, incorrect or illegible	X	
b. Color not as specified		X
c. Marking not permanent		X

4.3.2.2 Dimensional examination.- The mittens shall be examined for defects in dimensions in accordance with the following:

Any measurement deviating from nominal dimensions and tolerances specified shall be scored as a measurement defect.

4.3.2.3 Inspection levels and acceptable quality levels.- The inspection levels and acceptable quality levels (AQL's) expressed as defects per 100 units, for visual and dimensional examinations shall be as follows:

For examination in 4.3.2.1:

	AQL's	Inspection level
Major	2.5	II
Total (Major and Minor combined)	6.5	II
For examination in 4.3.2.2: One class	6.5	S-3

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

4.3.3 Examination of preparation for delivery.- An examination shall be made to determine that packaging, packing, and marking complies with the Section 5 requirements of this specification. Defects shall be scored in accordance with the list below. The sample unit shall be one shipping container fully prepared for delivery except that it need not be sealed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per 100 units.

Examine	Defect
Marking (exterior and interior)	Omitted, incorrect, illegible, of improper size, location, or method of application.
Materials	Any component missing, damaged or not as specified.
Workmanship	Inadequate application of components such as incomplete closure of container flaps or paperboard boxes, improper taping, loose strapping or inadequate stapling, bulging or distortion of container.
Content	Number of mittens per shipping container is more or less than required. 1/ Size shown on one or more mittens not as specified on packages or outer containers. 1/

1/ For this defect, two shipping containers in the sample shall be examined.

5. PREPARATION FOR DELIVERY

5.1 Packaging.- Packaging shall be level A or commercial as specified (see 6.2).

5.1.1 Level A.- Each pair of mittens shall be packaged in a folding paperboard box conforming to variety 2, style III, type F or G, class h or i of PPP-B-566. The mittens shall be placed in the box reversed end to end. The inside dimensions of each paperboard box shall be 11 1/2 inches (292mm) in length, 7 5/8 inches (194mm) in width, and 1 3/4 inches (50.8mm) in depth. Box closure shall be secured with 2 inch (50.8mm) minimum width gummed paper tape conforming to PPP-T-76, applied at the center of the length opening and extending over the top and along the bottom at least 1 inch (25.4mm).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

5.1.2 Commercial.- Mittens shall be packaged in accordance with FED-STD-356, provided the package and the quantity per package is the same as that normally used by the supplier for retail distribution.

5.2 Packing - Packing shall be level A, B, or commercial as specified (see 6.2).

5.2.1 Level A.- Twenty-eight pair of mittens of one size only as specified in 5.1, shall be packed in a close fitting box conforming to PPP-B-601, overseas type, Grade B, style optional. Strapping shall be zinc coated.

5.2.2 Level B.- Twenty-eight pair of mittens, of one size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container conforming to class weather resistant style RSC, grade V2s of PPP-B-636. Level A packages shall be packed flat, two in length, two in width and seven in depth within a shipping container. Inside dimensions of each shipping container shall approximate 23 1/8 inches (587mm) in length, 15 1/4 inches (387mm) in width and 12 3/8 inches (314mm) in depth. Approximate dimensions are furnished as a guide only. Each shipping container shall be closed, waterproofed, and reinforced in accordance with the appendix of PPP-B-636.

5.2.3 Commercial.- Mittens, packaged as specified in 5.1, shall be packed in accordance with FED-STD-356, provided the quantity packed per shipping container is the same as that normally used by the supplier for retail distribution.

5.3 Marking.-

5.3.1 Military (Levels A and B).- In addition to any special marking required by the contract or order, intermediate packages and shipping containers shall be marked in accordance with MIL-STD-129.

5.3.2 Commercial.- In addition to any special marking required by the contract or order, intermediate packages and shipping containers shall be marked in accordance with FED-STD-356.

6. NOTES

6.1 Intended use.- The foam mitten is intended to be worn with the jacket, trouser, hood and bootee components of a wet-suit which is designed to protect personnel against the effect of cold water immersion.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

6.2 Ordering data.- Procurement documents should specify the following:

a. Title, number and date of this specification
b. Sizes required (see 1.2)
c. Whether first article sample is required (see 3.2)
d. Selection of applicable levels of packaging and packing (see 5.1 and 5.2)

6.3 Samples and patterns.- For access to samples and patterns address the procuring activity issuing the invitation for bids.

Custodian:
Navy - SA

Review activities:
Navy -MS
DSA -CS

User activity:
Navy - AS, OS

Preparing activity:
Navy - SA

Project No. 8415-0874

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

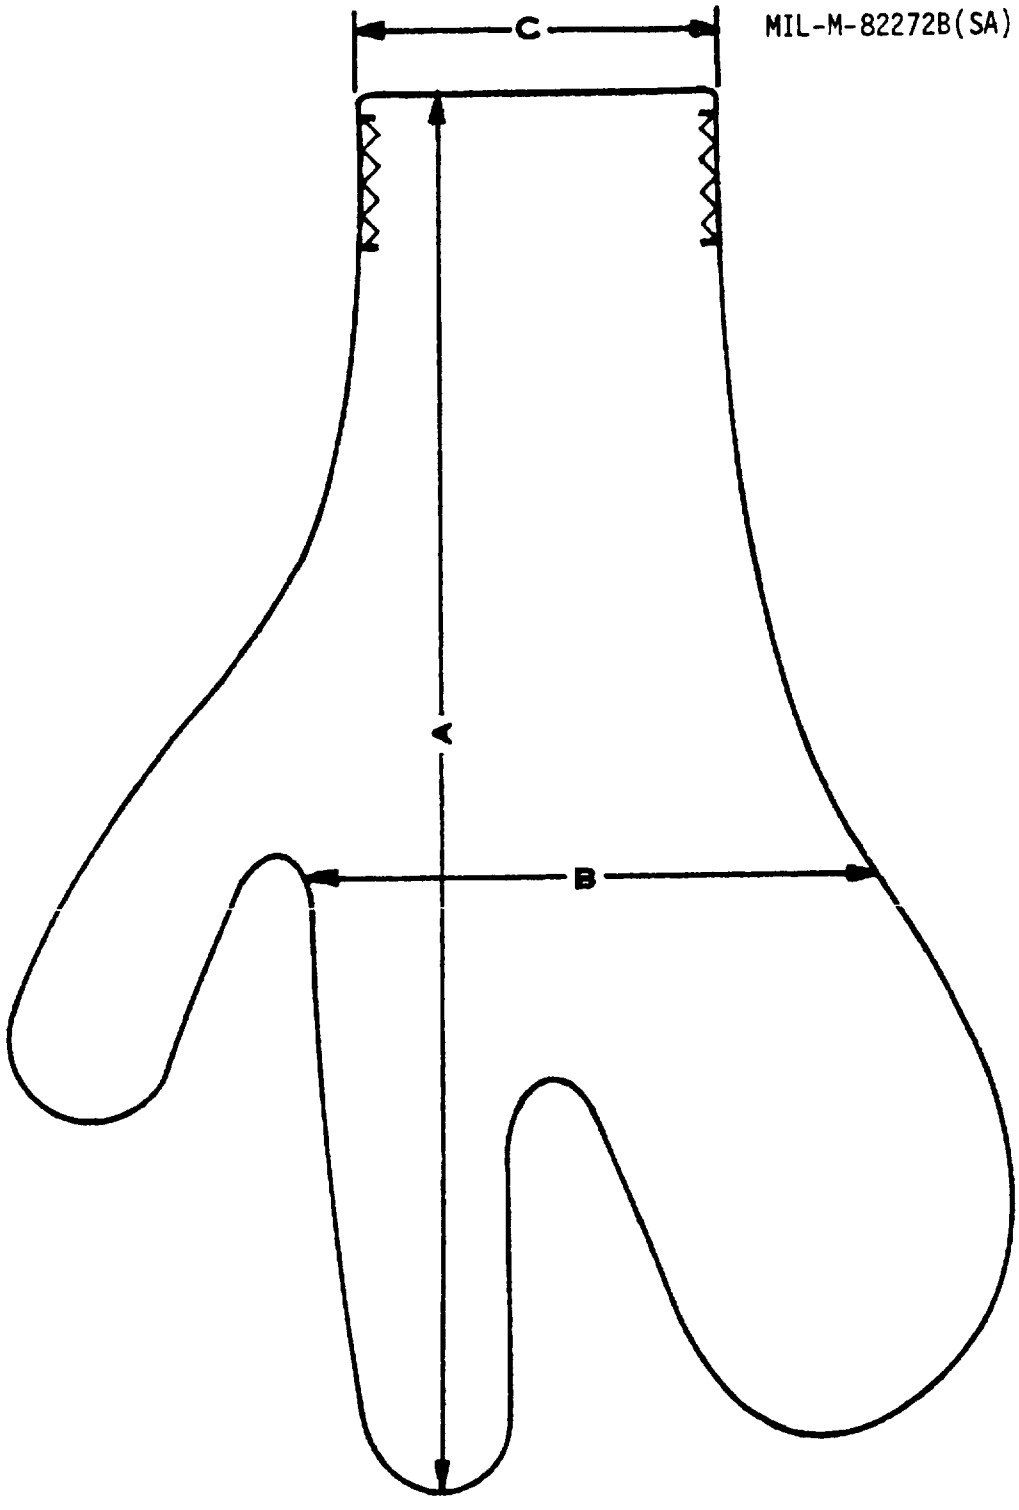


FIGURE 1 **MITTEN, WET-SUIT** (CHLOROPRENE FOAM)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

FOLD

OFFICER IN CHARGE
NAVY CLOTHING & TEXTILE RESEARCH UNIT
21 STRATHMORE ROAD
NATICK, MA 01760

POSTAGE AND FEES PAID
DoD 316

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

OFFICER IN CHARGE
NAVY CLOTHING & TEXTILE RESEARCH UNIT
21 STRATHMORE ROAD
NATICK, MA 01760

FOLD

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

OMB Approval
No. 22-R255

INSTRUCTIONS: The purpose of this form is to solicit beneficial comments which will help achieve procurement of suitable products at reasonable cost and minimum delay, or will otherwise enhance use of the document. DoD contractors, government activities, or manufacturers/ vendors who are prospective suppliers of the product are invited to submit comments to the government. Fold on lines on reverse side, staple in corner, and send to preparing activity. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements. Attach any pertinent data which may be of use in improving this document. If there are additional papers, attach to form and place both in an envelope addressed to preparing activity.

DOCUMENT IDENTIFIER AND TITLE

MIL-M-82272B(SA) MITTEN, WET SUIT (CHLOROPRENE FOAM)

NAME OF ORGANIZATION AND ADDRESS

CONTRACT NUMBER

MATERIAL PROCURED UNDER A

☐ DIRECT GOVERNMENT CONTRACT ☐ SUBCONTRACT

1. HAS ANY PART OF THE DOCUMENT CREATED PROBLEMS OR REQUIRED INTERPRETATION IN PROCUREMENT USE?

A. GIVE PARAGRAPH NUMBER AND WORDING.

B. RECOMMENDATIONS FOR CORRECTING THE DEFICIENCIES

2. COMMENTS ON ANY DOCUMENT REQUIREMENT CONSIDERED TOO RIGID

3. IS THE DOCUMENT RESTRICTIVE?

☐ YES ☐ NO *(If "Yes", in what way?)*

4. REMARKS

SUBMITTED BY *(Printed or typed name and address - Optional)*

TELEPHONE NO.

DATE

DD FORM 1 JAN 72 1426

REPLACES EDITION OF 1 JAN 66 WHICH MAY BE USED

S/N 0102-014-1802

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T06:58Z
Check the source to verify that this is the current version before use.