The documentation and process conversion measures necessary to comply with this revision shall be completed by 21 September 1999.

INCH-POUND

MIL-PRF-19500/604A
21 June 1999
SUPERSEDING
MIL-S-19500/604
10 November 1992

PERFORMANCE SPECIFICATION SHEET

SEMICONDUCTOR DEVICE, FIELD EFFECT RADIATION HARDENED (TOTAL DOSE CHARACTERIZATION ONLY)
TRANSISTORS,
N-CHANNEL, SILICON TYPES 2N7272, 2N7275, 2N7278, AND 2N7281
JANTXVM, D, R, AND JANSM, D AND R

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the performance requirements for an N-channel, enhancement-mode, MOSFET, radiation hardened (total dose characterization only), power transistor. Two levels of product assurance are provided for each device type specified in MIL-PRF-19500.

1.2 Physical dimensions. See figure 1, similar to TO-205AF.

1.3 Maximum ratings. T_A = +25°C unless otherwise specified.

Type	P_T 1/ T_C = +25°C	V_{DS}	V_{DG}	V_{GS}	I_{D1} 2/ T_C = +25°C	I_{D2} T_C = +100°C	I_S 2/	I_{DM}	T_J and T_{STG}	V_{ISO} 70,000 feet altitude
	W	V dc	V dc	V dc	A dc	A dc	A dc	A (pk)	°C	V dc
2N7272	25	100	100	±20	8.0	5.0	8.0	24	-55	
2N7275	25	200	200	±20	5.0	3.0	5.0	15	to	
2N7278	25	250	250	±20	4.0	2.0	4.0	12	+150	250
2N7281	25	500	500	±20	2.0	1.0	2.0	6		500

1/ Derate linearly 1.2°C/W for T_C > +25°C; $P_T = \frac{T_{JM} - T_C}{R_{\theta JC}}$

2/ $I_D = \sqrt{\frac{T_{JM} - T_C}{(R_{\theta JC}) x (R_{DS}(on) \text{ at } T_{JM})}}$ 1

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Defense Supply Center Columbus, ATTN: DSCC-VAT, 3990 East Broad St., Columbus, OH 43216-5000, by using the addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 5961

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

1.4 Primary electrical characteristics at T_C = +25°C.

Type	Min $V_{(BR)DSS}$ V_{GS} = 0 I_D = 1.0 mA dc	$V_{GS(th)1}$ V_{DS} = V_{GS} I_D = 1.0 mA dc		Max I_{DSS1} V_{GS} = 0 V_{DS} = 80 percent of rated V_{DS}	Max $r_{DS(on)}$ 1/ V_{GS} = 10 V dc		$R_{\theta JC}$ max	I_{AS} = I_{DM}	E_{AS} at I_{AS}
					T_J = +25°C at I_{D2}	T_J = +125°C at I_{D2}			
		V dc							
	V dc	Min	Max	µA dc	ohm	ohm	°C/W	A(pk)	mJ
2N7272	100	2.0	4.0	25	0.18	0.36	5.00	24	29
2N7275	200	2.0	4.0	25	0.50	1.10	5.00	15	11
2N7278	250	2.0	4.0	25	0.70	1.68	5.00	12	7
2N7281	500	2.0	4.0	25	2.50	6.50	5.00	6	2

1/ Pulsed (see 4.5.1).

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3 and 4 of this specification, whether or not they are listed.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

SPECIFICATION

DEPARTMENT OF DEFENSE

MIL-PRF-19500 - Semiconductor Devices, General Specification for.

STANDARD

MILITARY

MIL-STD-750 - Test Methods for Semiconductor Devices.

(Unless otherwise indicated, copies of the above specifications, standards, and handbooks are available from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein (except for related associated specifications or specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.


3. REQUIREMENTS

3.1 Associated specification. The individual item requirements shall be in accordance with MIL-PRF-19500, and as specified herein.

3.2 Abbreviations, symbols, and definitions. Abbreviations, symbols, and definitions used herein shall be as specified in MIL-PRF-19500.

E_{AS} ..... Single pulse avalanche energy capability.
I_{AS} ..... Rated avalanche current, non-repetitive.
$V_{(ISO)}$ ..... Source pin to case isolation voltage.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

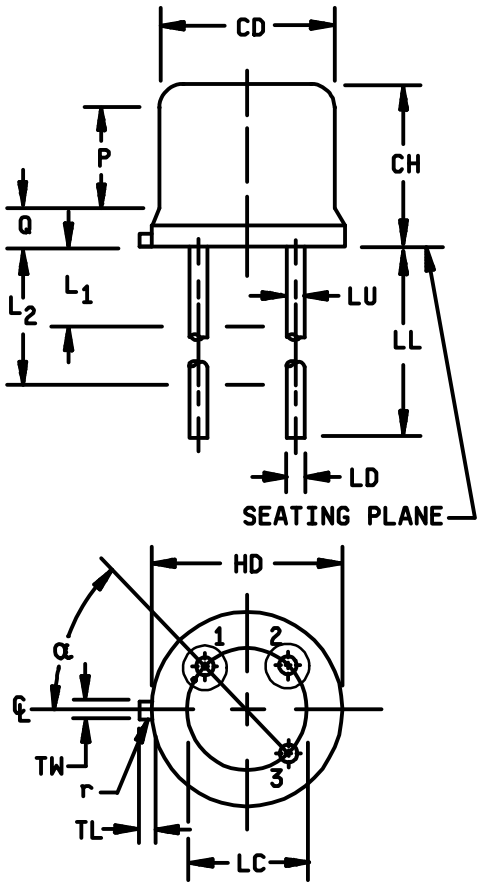

Ltr	Dimensions			
	Inches		Millimeters	
	Min	Max	Min	Max
CD	.315	.335	8.01	8.50
CH	.160	.180	4.07	4.57
HD	.350	.370	8.89	9.39
LC	.190	.210	4.83	5.33
LD	.016	.023	0.41	0.58
LL	.500	.560	12.7	14.22
LU	.016	.021	0.41	0.53
L1		.050		1.27
L2		.250		6.35
P		.100		2.54
Q		.040		1.02
r		.010		0.018
TL	.029	.045	0.74	1.14
TW	.028	.034	0.72	0.86
α	45° TP		45° TP	
Term 1	Source			
Term 2	Gate			
Term 3	Drain			

NOTES:
1. Dimensions are in inches.
2. Equivalents are given for general information only.
3. Terminals 1 and 2 are isolated from case, terminal 3 is butt welded to stem base.
4. The preferred measurements used herein are the metric units. However, this transistor was designed using inch-pound units of measurement. In case of conflicts between the metric and inch-pound units, the inch-pound units shall be the rule.
5. In accordance with ANSI Y14.5M, diameters are equivalent to ϕx symbology.

FIGURE 1. Dimensions and configuration (similar to T0-205).

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

3.3 Interface requirements and physical dimensions. The Interface requirements and physical dimensions shall be as specified in MIL-PRF-19500, MIL-HDBK-6100, and herein.

3.3.1 Lead material and finish. Lead material shall be Kovar or Alloy 52; a copper core or plated core is permitted. Lead finish shall be solderable in accordance with MIL-PRF-19500 and herein. Where a choice of lead finish is desired, it shall be specified in the acquisition requirement (see 6.2).

3.3.2 Internal construction. Multiple chip construction is not permitted to meet the requirements of this specification.

3.4 Marking. Marking shall be in accordance with MIL-PRF-19500. At the option of the manufacturer, marking of the country of origin may be omitted from the body of the transistor, but shall be retained on the initial container.

3.5 Electrostatic discharge protection. The devices covered by this specification require electrostatic discharge protection.

3.5.1 Handling. MOS devices must be handled with certain precautions to avoid damage due to the accumulation of static charge. However, the following handling practices are recommended (see 3.5).

a. Devices should be handled on benches with conductive handling devices.

b. Ground test equipment, tools, and personnel handling devices.

c. Do not handle devices by the leads.

d. Store devices in conductive foam or carriers.

e. Avoid use of plastic, rubber, or silk in MOS areas.

f. Maintain relative humidity above 50 percent if practical.

g. Care should be exercised during test and troubleshooting to apply not more than maximum rated voltage to any lead.

h. Gate must be terminated to source, $R \leq 100$ k, whenever bias voltage is to be applied drain to source.

3.6 Electrical performance characteristics. Unless otherwise specified herein, the electrical performance characteristics are as specified in 1.3, 1.4, and table I.

3.7 Electrical test requirements. The electrical test requirements shall be the subgroups specified in 4.4.2, 4.4.3, and table I.

3.8 Qualification. Devices furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified manufacturers list before contract award (see 4.2 and 6.2).

4. VERIFICATION

4.1 Classification of Inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).

b. Screening (see 4.3)

c. Conformance inspection (see 4.4).

4.2 Qualification inspection. Qualification inspection shall be in accordance with MIL-PRF-19500, and as specified herein. Alternate flow is allowed for qualification inspection in accordance with MIL-PRF-19500.

4.2.1 Group E inspection. Group E inspection shall be conducted in accordance with MIL-PRF-19500, and table III herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

4.3 Screening (JANTX, JANTXV, and JANS levels only). Screening shall be in accordance with table IV of MIL-PRF-19500, and as specified herein. The following measurements shall be made in accordance with table I herein. Devices that exceed the limits of table I herein shall not be acceptable.

Screen (see table IV of MIL-PRF-19500)	Measurement	
	JANS level	JANTX and JANTXV levels
1/	Method 3161 (see 4.5.3)	Method 3161 (see 4.5.3)
1/	Gate stress test (see 4.5.5)	Gate stress test (see 4.5.5)
1/	Method 3470, E_{AS} test (see 4.5.4)	Method 3470, E_{AS} test (see 4.5.4)
2/	Subgroup 2 of table I herein	Subgroup 2 of table I herein
9	I_{GSS}, I_{DSS1}	Not applicable
10	MIL-STD-750, method 1042 test condition B	MIL-STD-750, method 1042 test condition B
11	I_{GSSF1}, I_{GSSR1}, I_{DSS1}, $R_{DS(on)}$, $V_{GS(TH)}$ Subgroup 2 of table I herein; ΔI_{GSSF1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{GSSR1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{DSS1} = ±25 µA dc or ±100 percent of initial value, whichever is greater.	I_{GSSF1}, I_{GSSR1}, I_{DSS1}, $R_{DS(on)}$, $V_{GS(th)}$ Subgroup 2 of table I herein
12	MIL-STD-750, method 1042, test condition A	MIL-STD-750, method 1042, condition A or T_A = +175°C and t = 48 hours min 3/
13	Subgroups 2 and 3 of table I herein; ΔI_{GSSF1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{GSSR1} = ±20 nA dc or ±100 percent of initial value, whichever is greater. ΔI_{DSS1} = ±25 µA dc or ±100 percent of initial value, whichever is greater. $\Delta R_{DS(on)1}$ = ±20 percent of initial value. $\Delta V_{GS(th)1}$ = ±20 percent of initial value.	Subgroups 2 and 3 of table I herein. ΔI_{GSSF1} = ±20 nA dc or 100 percent of initial value, whichever is greater. ΔI_{GSSR1} = ±20 nA dc or 100 percent of initial value, whichever is greater. ΔI_{DSS1} = ±25 µA dc or 100 percent of initial value, whichever is greater. $\Delta R_{DS(on)1}$ = ±20 percent of initial value. $\Delta V_{GS(th)1}$ = ±20 percent of initial value.

1/ Shall be performed any time after screen 10.
2/ Shall be performed after E_{AS} test, method 3161, and gate stress test.
3/ Use of this accelerated screening option requires a 1,000 hour life test in accordance with the applicable group E, subgroup 2 life test, and end-points specified herein to be provided to the qualifying activity for review and acceptance.

4.4 Conformance inspection. Conformance inspection shall be in accordance with MIL-PRF-19500, and as specified herein. Alternate flow is allowed for quality conformance inspection in accordance with MIL-PRF-19500.

4.4.1 Group A inspection. Group A inspection shall be conducted in accordance with MIL-PRF-19500 and table I herein. (End point electrical measurements shall be in accordance with table I, group A, subgroup 2 herein.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

4.4.2 Group B inspection. Group B inspection shall be conducted in accordance with the conditions specified for subgroup testing in tables VIa (JANS) and VIb (JAN, JANTX, and JANTXV) of MIL-PRF-19500 and paragraphs 4.4.2.1 and 4.4.2.2 herein. Electrical measurements (end-points) shall be in accordance with the applicable inspections of table I, group A, subgroup 2 herein.

4.4.2.1 Group B inspection, table VIa (JANS) of MIL-PRF-19500.

Subgroup	Method	Condition
3	1051	Condition G, 100 cycles.
3	2037	Test condition A, all internal wires for each device shall be pulled separately.
4	1042	Condition D, 2,000 cycles. No heat sink or forced air cooling on the device shall be permitted during the on cycle. t_{on} = 30 seconds minimum.
4		Electrical measurements: in addition to table I, group A, subgroup 2, ΔV_{SD} shall be measured per 4.5.3.
5	1042	Condition A; V_{DS} = 100 percent of rated; T_A = +175°C, t = 120 hours, or T_A = +150°C, t = 120 hours minimum.
5	1042	Condition B; V_{GS} = 100 percent of rated; T_A = +175°C; t = 24 hours minimum.
5	2037	Bond strength (Al-Au die interconnects only), test condition A.
6	3161	See 4.5.2

4.4.2.2 Group B inspection, table VIb (JANTX and JANTXV) of MIL-PRF-19500.

Subgroup	Method	Condition
2	1051	Test condition G, 25 cycles.
3	1042	The heating cycle shall be 30 seconds minimum.
5	----	Not applicable
6	----	Not applicable

4.4.3 Group C inspection. Group C inspection shall be conducted in accordance with the conditions specified for subgroup testing in table VII of MIL-PRF-19500, and as follows. Electrical measurements (end points) shall be in accordance with table I, group A, subgroup 2 herein.

Subgroup	Method	Condition
2	2036	Terminal strength, test condition E, weight = 8 oz., 3 arcs.
6	1042	Test condition D, 6,000 cycles; heating cycle = 30 sec. min.

4.4.4 Group D Inspection. Group D inspection shall be conducted in accordance with MIL-PRF-19500 and table II herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection .

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 1						
Visual and mechanical examination	2071					
Subgroup 2						
Breakdown voltage, drain to source	3407	V_{GS} = 0 V; I_D = 1 mA dc, bias condition C	$V_{(BR)DSS}$			
2N7272				100		V dc
2N7275				200		V dc
2N7278				250		V dc
2N7281				500		V dc
Gate to source voltage (threshold)	3403	V_{DS} = V_{GS}, I_D = 1 mA dc	$V_{GS(th)1}$	2.0	4.0	V dc
Gate current	3411	V_{GS} = +20 and -20 V dc, bias condition C, V_{DS} = 0	I_{GSS1}		±100	nA dc
Drain current	3413	V_{GS} = 0 V dc, bias condition C; V_{DS} = 80 percent of rated V_{DS}	I_{DSS1}		25	µa DC
Static drain to source "ON" state resistance	3421	V_{GS} = 10 V dc, condition A, pulsed (see 4.5.1), Id = Id2	$r_{DS(on)1}$			
2N7272					0.18	Ω
2N7275					0.50	Ω
2N7278					0.70	Ω
2N7281					2.50	Ω
Static drain to source "ON" state resistance	3421	V_{GS} = 10 V dc, condition A, pulsed (see 4.5.1), Id = Id1	$r_{DS(on)2}$			
2N7272					0.189	Ω
2N7275					0.525	Ω
2N7278					0.735	Ω
2N7281					2.630	Ω
Forward voltage	4011	Pulsed (see 4.5.1), Id = Id1; V_{GS} = 0 V dc	V_{SD}		1.8	V DC
Subgroup 3						
High temperature operation		T_C = T_J = +125°C				
Reverse gate current	3411	V_{GS} = +20 and -20 V dc, bias condition C, V_{DS} = 0	I_{GSS2}		±200	nA dc
Drain current	3413	V_{GS} = 0 V dc, bias condition C; V_{DS} = 100 percent of rated V_{DS}	I_{DSS2}		1.0	mA dc
Drain current		V_{DS} = 80 percent of rated V_{DS}	I_{DSS3}		0.25	mA dc

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection .

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 3 - Continued.						
Static drain to source "ON" state resistance	3421	V_{GS} = 10 V dc, pulsed (see 4.5.1), Id = Id2	$r_{DS(on)3}$			
2N7272					0.36	Ω
2N7275					1.10	Ω
2N7278					1.68	Ω
2N7281					6.50	Ω
Gate to source voltage (threshold)	3403	$V_{DS} = V_{GS}$, I_D = 1 mA dc	$V_{GS(th)2}$	1.0		V dc
Low temperature operation		$T_C = T_J$ = -55°C				
Gate to source voltage (threshold)	3403	$V_{DS} = V_{GS}$, I_D = 1 mA dc	$V_{GS(th)3}$		5.0	V dc
Subgroup 4						
Switching time test	3472	$I_D = I_{D1}$, V_{GS} = 10 V dc, R_G = 25Ω, V_{DD} = 50 percent of rated V_{DS}				
Turn-on delay time			$t_{d(on)}$			
2N7272					35	ns
2N7275					35	ns
2N7278					35	ns
2N7281					46	ns
Rise time			t_r			
2N7272					210	ns
2N7275					140	ns
2N7278					85	ns
2N7281					58	ns
Turn-off delay time			$t_{d(off)}$			
2N7272					200	ns
2N7275					172	ns
2N7278					195	ns
2N7281					208	ns
Fall time			t_f			
2N7272					145	ns
2N7275					80	ns
2N7278					75	ns
2N7281					54	ns
Subgroup 5						
Safe operating area test	3474	See figure 3; t_p = 10 ms minimum V_{DS} = 80 percent of max rated V_{DS} ($V_{DS} \leq 200$)				
Electrical measurements		See table I, group A, subgroup 2 herein.				
Subgroup 6						
Not applicable						

See footnote at end of table.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

TABLE I. Group A inspection .

Inspection 1/	MIL-STD-750		Symbol	Limit		Unit
	Method	Conditions		Min	Max	
Subgroup 7						
Gate charge	3471	Condition B				
On-state gate charge		V_{DD} = 0.5 BV_{DSS}; I_D = I_{D1}; $V_{GS} \leq 20V$; I_{GS1} = I_{GS2}	$Q_{g(on)}$			
2N7272					76	nC
2N7275					60	nC
2N7278					62	nC
2N7281					64	nC
Gate to source charge			Q_{gs}			
2N7272					13	nC
2N7275					12	nC
2N7278					12	nC
2N7281					12	nC
Gate to drain charge			Q_{gd}			
2N7272					38	nC
2N7275					29	nC
2N7278					30	nC
2N7281					32	nC
Reverse recovery time	3473	di/dt = 100 A/µs, $V_{DD} \leq 30$ V, Id = Id1	t_{rr}			
2N7272					450	ns
2N7275					600	ns
2N7278					800	ns
2N7281					900	ns

1/ For sampling plan, see MIL-PRF-19500.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

TABLE II Group D inspection

Inspection 1/ 2/ 3/	MIL-STD-750		Symbol	Pre-irradiation limits		Post-irradiation limits		Unit
				M, D, and R		M, D, and R		
	Method	Conditions		Min	Max	Min	Max	
Subgroup 1								
Not Applicable								
Subgroup 2		T_C = + 25°C						
Steady-state total dose irradiation	1019	2/, 3/						
End-point electricals								
Breakdown voltage, drain to source	3407	V_{GS} = 0 V; I_D = 1 mA; Bias condition C	$V_{(BR)DSS}$					
2N7272				100		100		V dc
2N7275				200		200		
2N7278				250		250		V dc
2N7281				500		500		V dc
Gate to source voltage (threshold)	3403	V_{DS} = V_{GS}; I_D = 1 mA	$V_{GS(th)1}$	2	4	2	4	V dc
Gate current	3411	V_{GS} = 20 V; V_{DS} = 0 V Bias condition C	I_{GSSF1}		100		100	nA dc
Gate Current	3411	V_{GS} = 20 V; V_{DS} = 0 V Bias condition C	I_{GSSR1}		-100		-100	nA dc
Drain current	3413	V_{GS} = 0 V; V_{DS} = 80% of rated VDS (preirradiation) Bias condition C	I_{DSS1}		25		25	µA dc
Static drain to source on-state resistance	3421	V_{GS} = 10 V Cond. A pulsed see 4.5.1; I_D = I_{D2}	$R_{DS(on)1}$					
2N7272					0.180		0.180	Ω
2N7275					0.500		0.500	Ω
2N7278					0.700		0.700	Ω
2N7281					2.50		2.50	Ω
Drain to source on-state voltage	3405	V_{GS} = 10 V, cond. A, pulsed see 4.5.1; I_D = I_{D1}	$V_{DS(on)}$					
2N7272					1.51		1.51	V dc
2N7275					2.63		2.63	V dc
2N7278					2.94		2.94	V dc
2N7281					5.25		5.25	V dc

1/ For sampling plan see MIL-PRF-19500.

2/ Inspection requires all subgroup 2 (group D) measurements after exposure to both of the following insitu bias conditions:

V_{GS} = 10 V; V_{DS} = 0

V_{GS} = 0 V; V_{DS} = 80 percent of rated V_{DS}

3/ Each bias condition requires a separate total dose sample.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

TABLE III. Group E inspection (all quality levels) for qualification only.

Inspection	MIL-STD-750		Qualification and large lot quality conformance inspection
	Method	Conditions	
Subgroup 1			12 devices c = 0
Temperature cycling (air to air)	1051	-55°C to +150°C, 500 cycles	
Hermetic seal	1071		
Fine leak Gross leak			
Electrical measurements		Table I, group A, subgroup 2 herein.	
Subgroup 2 1/			12 devices c = 0
Steady-state reverse bias	1042	Condition A: 1,000 hours	
Electrical measurements		Table I, group A, subgroup 2 herein.	
Steady-state gate bias	1042	Condition B: 1,000 hours	
Electrical measurements		Table I, group A, subgroup 2 herein.	
Subgroup 3			
Not applicable			
Subgroup 4			
Thermal resistance	3161	$R_{\theta JC}$ = 5.0°C/W maximum. See 4.5.2	12 devices c = 0

1/ A separate sample for each test shall be pulled.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

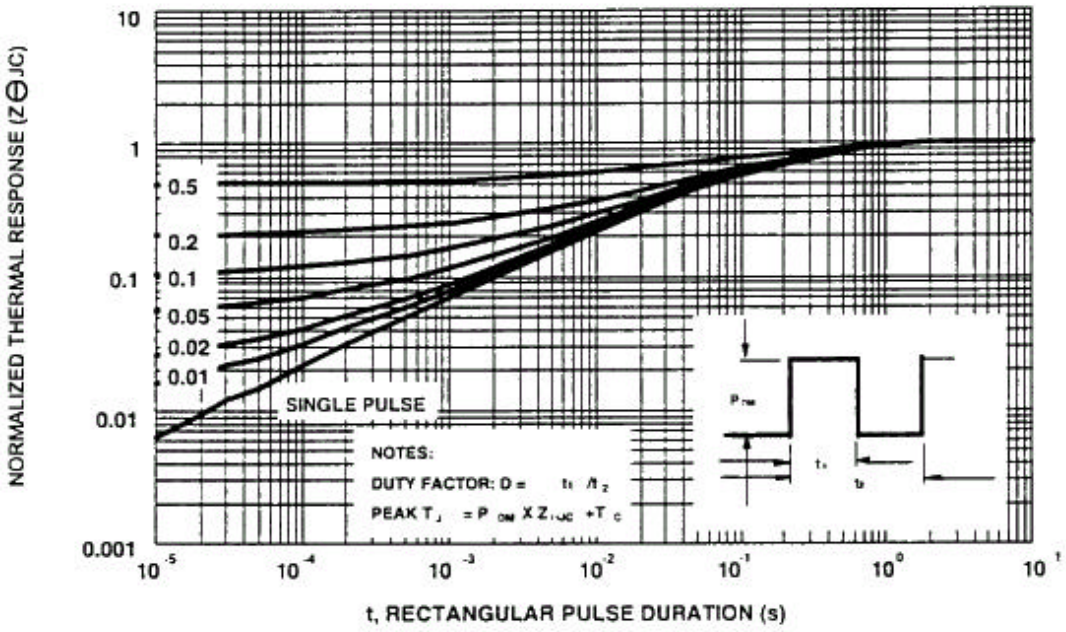


FIGURE 2. Thermal response curves.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

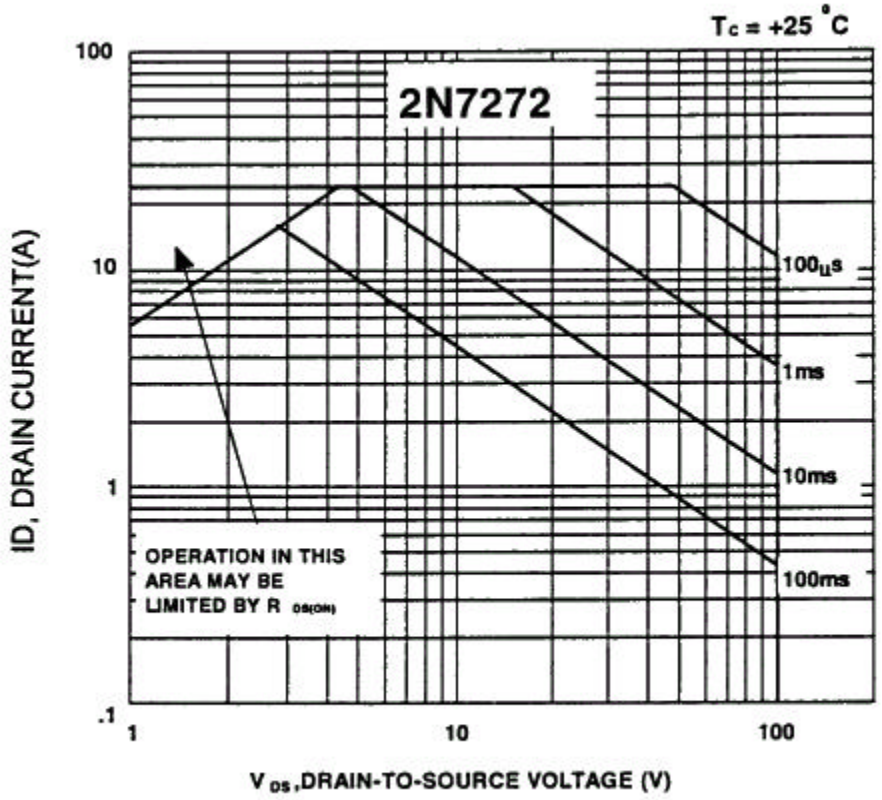


FIGURE 3. Safe operating area graphs.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

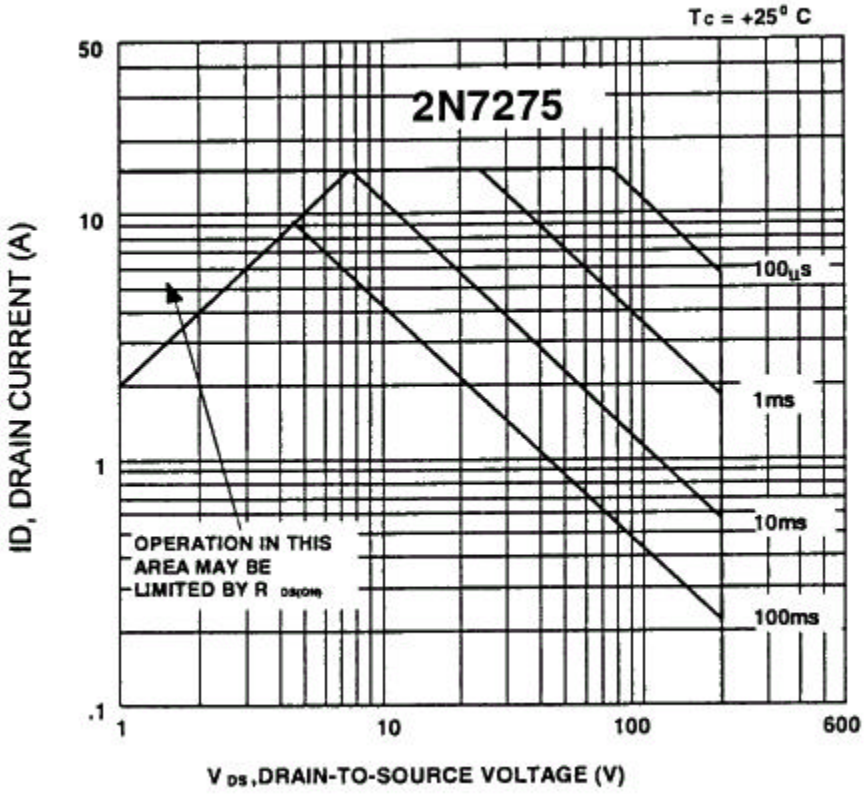


FIGURE 3. Safe operating area graphs - Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

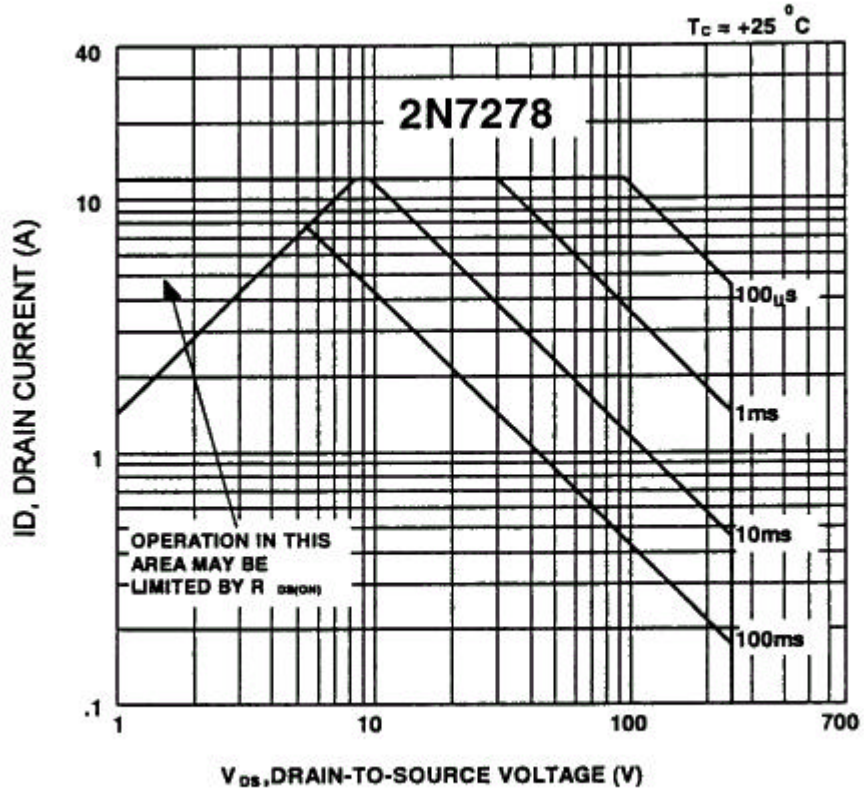


FIGURE 3. Safe operating area graphs - Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

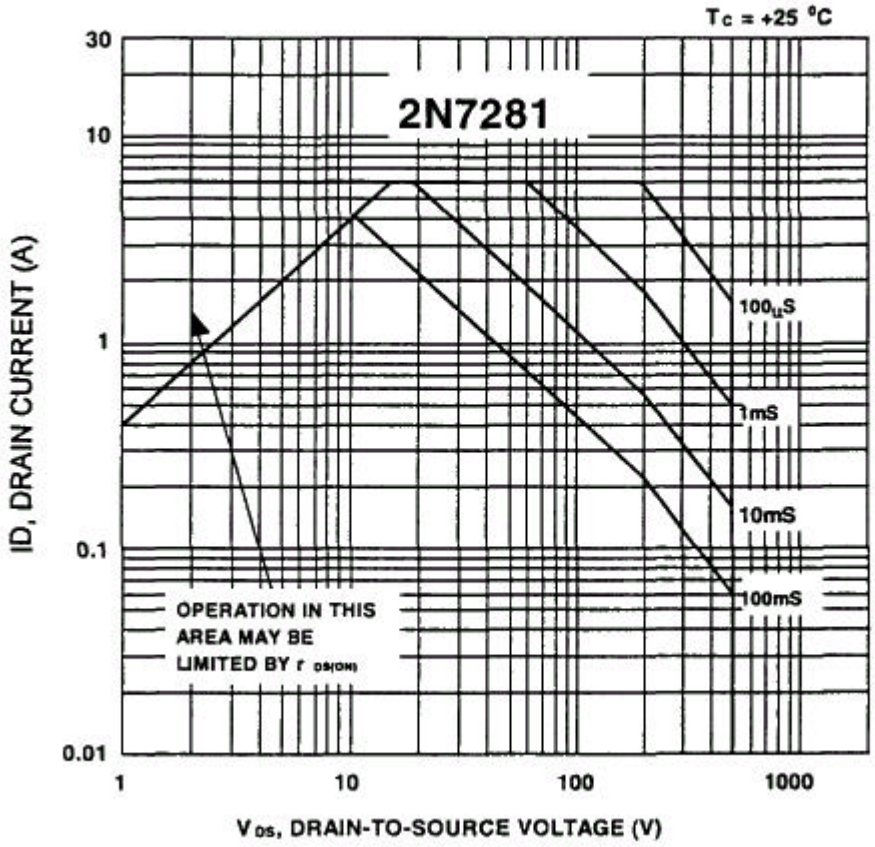


FIGURE 3. Safe operating area graphs - Continued.

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

4.5 Methods of inspection. Methods of inspection shall be as specified in the appropriate tables and as follows.

4.5.1 Pulse measurements. Conditions for pulse measurements shall be as specified in section 4 of MIL-STD-750.

4.5.2 Thermal resistance. Thermal resistance measurements shall be performed in accordance with method 3161 of MIL-STD-750. The maximum limit of $R_{\theta JC(max)}$ = 5.00°C/W. The following parameter measurements shall apply:

a. Measuring current (I_M) ..... 10 mA

b. Drain heating current (I_H) ..... 1 A

c. Heating time (t_H) ..... Steady-state (see MIL-STD-750, method 3161 for definition)

d. Drain-source heating voltage (V_H) ..... 25 V

e. Measurement time delay (t_{MD}) ..... 30 to 60 µs

f. Sample window time (t_{SW}) ..... 10 µs maximum

4.5.3 Thermal response (ΔV_{SD} measurement). The delta V_{SD} measurement shall be performed in accordance with method 3161 of MIL-STD-750. The delta V_{SD} conditions (I_H and V_H) and maximum limit shall be derived by each vendor from the thermal response curves (see figure 2). The following parameter measurements shall apply:

a. Measuring current (I_M) ..... 10 mA

b. Drain heating current (I_H) ..... 1 A minimum

c. Heating time (t_H) ..... 10 ms

d. Drain-source heating voltage (V_H) ..... 25 V

e. Measurement time delay (t_{MD}) ..... 30 to 60 µs

f. Sample window time (t_{SW}) ..... 10 µs maximum

4.5.4 Single pulse avalanche energy (E_{AS}).

a. $I_{AS} = I_{DM}$

b. L = .1 mH

c. $E_{AS} = 1/2\ LI_{AS}^2$

d. Initial junction temperature = +25°C,+10°C, -5°C

4.5.5 Gate stress test.

a. V_{GS} = 30 V minimum

b. t = 250 µs minimum

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of material is to be performed by DoD personnel, these personnel need to contact the responsible packaging activity to ascertain requisite packaging requirements. Packaging requirements are maintained by the Inventory Control Points' packaging activity within the Military Department or Defense Agency, or within the Military Departments' System Command. Packaging data retrieval is available from the managing Military Departments' or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

5.2 Marking. Unless otherwise specified (see 6.2), marking shall be in accordance with MIL-STD-129.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Notes. The notes specified in MIL-PRF-19500 are applicable to this specification.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of the specification.

b. Issue of DODISS to be cited in the solicitation and, if required, the specific issue of individual documents referenced (see 2.1).

c. Lead finish as specified (see 3.3.1).

d. Type designation and product assurance level.

6.3 Substitution information. Devices covered by this specification are substitutable for the manufacturer's and user's Part or Identifying Number (PIN). This information in no way implies that manufacturer's PIN's are suitable for the military PIN.

Preferred types	Commercial types
2N7272	FRL130 1/
2N7275	FRL230 1/
2N7278	FRL234 1/
2N7281	FRL430 1/

1/ FRLxxxM, FRLxxxD FRLxxxR, 3 k, 10 k, 100 k RAD(Si)

6.4 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extent of the changes.

6.5 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time of award of contract, qualified for inclusion in Qualified Manufacturers List QML-19500 whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or purchase orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from Defense Supply Center Columbus, DSCC-VQE, Columbus, OH 43216.

CONCLUDING MATERIAL

Custodians:
Army - CR
Navy - EC
Air Force - 11
NASA - NA
DLA - CC

Review activities:
Navy - TD
Air Force - 19, 70, 80

Preparing activity:
DLA - CC

(Project 5961-1930)RP

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.

2. The submitter of this form must complete blocks 4, 5, 6, and 7.

3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	**1. DOCUMENT NUMBER** MIL-PRF-19500/604A	**2. DOCUMENT DATE** 99/06/21

3. DOCUMENT TITLE SEMICONDUCTOR DEVICE, FIELD EFFECT RADIATION HARDENED (TOTAL DOSE CHARACTERIZATION ONLY) TRANSISTORS, N-CHANNEL, SILICON TYPES 2N7272, 2N7275, 2N7278, AND 2N7281 JANTXVM, D, R, AND JANSM, D AND R

4. NATURE OF CHANGE (Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)

5. REASON FOR RECOMMENDATION

6. SUBMITTER		
a. NAME (Last, First, Middle initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) Commercial DSN FAX EMAIL	7. DATE SUBMITTED

8. PREPARING ACTIVITY				
a. Point of Contact Alan Barone	b. TELEPHONE Commercial 614-692-0510	DSN 850-0510	FAX 614-692-6939	EMAIL alan_barone@dscc.dla.mil
c. ADDRESS Defense Supply Center Columbus ATTN: DSCC-VAT Columbus, OH 43216-5000	**IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT:** Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 DSN 289-2340			

DD Form 1426, FEB 99 (EG) PREVIOUS EDITIONS ARE OBSOLETE WHS/DIOR, Feb 99

Source: https://assist.dla.mil -- Downloaded: 2026-10-19T04:01Z
Check the source to verify that this is the current version before use.