NOTICE: When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

CUSTODIAN
Navy - Wep
USAF

PROCUREMENT SPECIFICATION
NONE

MILITARY STANDARD


RING-RETAINING, EXTERNAL, BERYLLIUM COPPER

MS9012(ASG)

SHEET 1 OF 1

THIS STANDARD WAS DEVELOPED COOPERATIVELY WITH THE ENGINE AND PROPELLER UTILITY PARTS COMMITTEE OF THE SAE

MS9012(ASG)

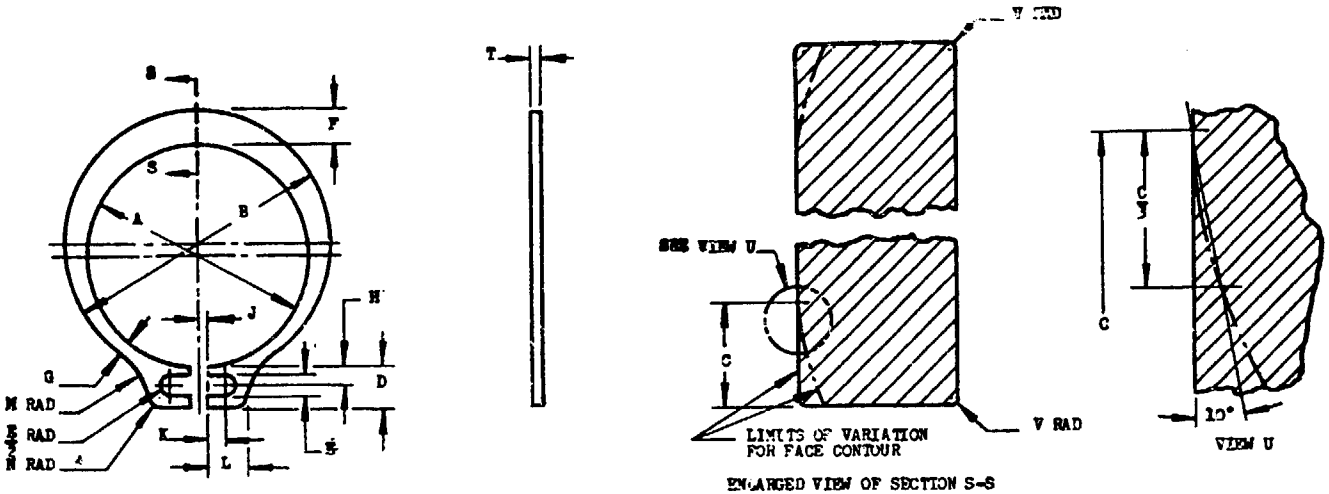

ENLARGED VIEW OF SECTION S-S

PART NO.		FREE DIAMETER A		FREE DIAMETER B	C	D	E +.010 -.002	F		G		H	J	K		'		M	N	V	THICKNESS T		APPROX. WEIGHT
		MAX.	MIN.	MAX.	MAX.	±.010		MAX.	MIN.	MAX.	MIN.		MAX.	MAX.	MIN.	MAX.	MIN.	±.016	±.016	MAX.	MAX.	MIN.	LBS/1000
MS9012-01		.114	.108	.142	.004	.046	.026	.0195	.0165	.0125	.0095	.023	.004	.016	.010	.042	.036	.040	.023	.003	.011	.009	.018
MS9012-02		.145	.139	.185	.005	.054	.026	.0275	.0245	.0175	.0145	.027	.004	.016	.010	.046	.040	.062	.027	.003	.011	.009	.026
MS9012-03		.170	.164	.210	.006	.050	.026	.027	.023	.018	.014	.023	.005	.027	.017	.059	.049	.060	.027	.005	.0163	.0137	.059
MS9012-04		.181	.175	.222	.006	.056	.026	.028	.024	.017	.013	.028	.005	.018	.008	.050	.040	.060	.028	.005	.0163	.0137	.063
MS9012-05		.198	.192	.242	.007	.056	.026	.030	.026	.019	.015	.028	.005	.018	.008	.050	.040	.060	.028	.005	.0163	.0137	.074
MS9012-06		.217	.211	.264	.007	.056	.026	.032	.028	.020	.016	.028	.005	.018	.008	.050	.040	.060	.028	.005	.0163	.0137	.086

(A) INACTIVE FOR DESIGN AFTER 13 JUNE 1960.
NO SUPERSEDING MS STANDARD
For definition and application of drawing status notes, see ANA Bulletin No. 337

MATERIAL: BERYLLIUM COPPER AMS 4532

HARDNESS: ROCKWELL 15N-79-82 (Precipitation Treated)

LUG SLOTS MUST NOT BREAK THRU INNER OR OUTER CONTOUR

BREAK SHARP EDGES .005 MAX.

DIMENSIONS IN INCHES. UNLESS OTHERWISE SPECIFIED: TOLERANCES; ANGULAR DIMENSIONS ± 2°

WITH ALLOWANCE FOR INITIAL SET, MINIMUM DIAMETRAL EXPANSION WITHOUT PERMANENT SET SHALL BE 18% OF FREE RING DIAMETER A.

MINIMUM DIAMETRAL EXPANSION WITHOUT FAILURE BY CRACKING SHALL BE 21% OF FREE DIAMETER A.

DO NOT USE UNASSIGNED PART NUMBERS.

FSC SUP CLASS 5340

APPROVED 1 Jul 54 REVISED (A) 13 Jun 60

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T13:08Z
Check the source to verify that this is the current version before use.