
FED. SUP CLASS
2590

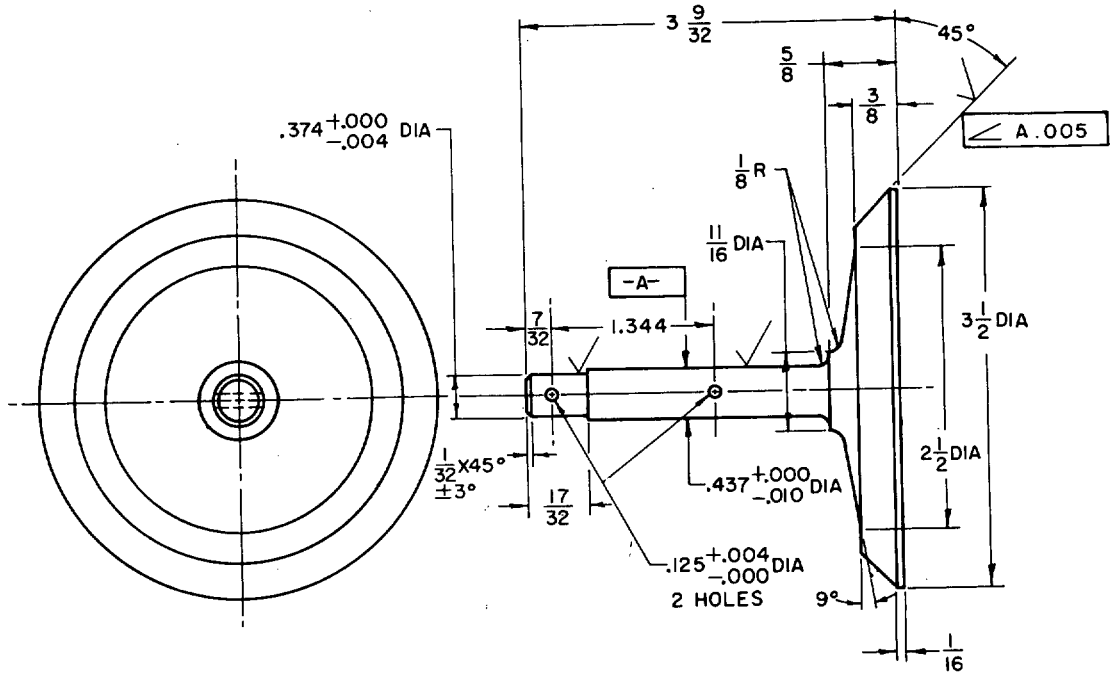

VALVE

(B) REQUIREMENTS:

1. MATERIAL:
   A. STEEL CASTING, QQ-S-681, CLASS 105-85.
      OPTIONAL MATERIAL: STEEL FORGING AISI 8625, AISI 8630, AISI 4130, AISI 5130, MIL-S-46172, GRADE D.
   B. ALUMINUM ALLOY, CASTING, SPEC. QQ-A-601, ALLOY 355 OR 356.
      OPTIONAL MATERIAL: ALUMINUM ALLOY, FORGING, SPEC. QQ-A-367, COMPOSITION 6061.

2. HEAT TREAT:
   A. STEEL: QUENCH AND TEMPER, BRINELL 243-271 (ROCKWELL "C" 23-28).
   B. ALUMINUM: SOLUTION TREAT AND ARTIFICIALLY AGE (T6) IN ACCORDANCE WITH MIL-H-6088.

3. FINISH:
   A. STEEL: CADMIUM PLATE IN ACCORDANCE WITH SPEC. QQ-P-416, TYPE II, CLASS 2.
   B. ALUMINUM: ANODIZE IN ACCORDANCE WITH MIL-A-8625.

4. UNLESS OTHERWISE SPECIFIED, ALL MACHINED SURFACES SHALL BE 125 ROOT MEAN SQUARE (rms) WHERE SHOWN WITH SURFACE ROUGHNESS SYMBOL ✓: MACHINED SURFACES 250 ✓ IN ACCORDANCE WITH MIL-STD-10.

5. UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES. TOLERANCES ARE: MACHINED SURFACES, FRACTIONS ± 1/64, DECIMALS ±.005, ANGLES ± 0° 30': UNMACHINED SURFACES, FRACTIONS ± 1/32, ANGLES ± 1°

6. MARKING SHALL CONSIST OF THE MS PART NUMBER AND THE MAUFACTURER'S IDENTIFICATION IN ACCORDANCE WITH MIL-STD-130.

(B) NOTES:

1. REFERENCED DOCUMENTS SHALL BE OF THE ISSUE IN EFFECT ON DATE OF INVITATION FOR BID.

(B) DENOTES CHANGES

MS PART NO.	MATERIAL
MS 51343-1	STEEL
MS 51343-2	ALUMINUM

P.A. ARMY-AT Other Cust	TITLE (B) VALVE, POPPET, HULL DRAIN: VEHICULAR, 3 INCH	MILITARY STANDARD MS 51343 (AT)
PROCUREMENT SPECIFICATION NONE	SUPERSEDES:	SHEET 1 OF 1

APPROVED 9 JANUARY 1961 REVISED (A) 18 OCTOBER 1966 (B) 25 NOV 83

Review activity:
DLA-CS

This military standard is approved for use by the US Army Tank-Automotive Command, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

DD FORM 1 SEP 87 672-1 (Limited coordination)

Source: https://assist.dla.mil -- Downloaded: 2026-04-23T18:00Z
Check the source to verify that this is the current version before use.