AA-O-00210a(GSA-FSS)
March 15, 1966
SUPERSEDING
AA-O-00210(GSA-FSS)
August 31, 1964

INTERIM FEDERAL SPECIFICATION

OFFICE FURNITURE, EXECUTIVE, COMBINATION METAL AND WOOD

CHAIRS, STRAIGHT, CHAIRS, ROTARY

This Interim Federal Specification was prepared by the Standardization Division, Federal Supply Service, General Services Administration, Washington, D. C. 20406, based upon currently available technical information. It is recommended that Federal agencies use it for procurement and forward recommendations for changes to the preparing activity at the address shown above.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification describes executive straight and rotary chairs fabricated of metal and wood as a part of a correlated group in contemporary design.

1.2 Classification

1.2.1 Types, Styles and Classes. The chairs shall be of the following types, styles, and classes as specified (see 6.2)

Type I. Bucket (Figures 1, 2, 3).

Style A - Straight, tubular legs, with glides.
Style B - Rotary, tilting, with casters.
Style C - Rotary, non-tilting, with glides.

Type II. High Back (Figures 4,5,6).

Style A - Straight, tubular legs, with glides.
Style B - Rotary, tilting, with casters.

Type III. Square, with arms (Figures 7, 8, 9, 10).

Style A - Straight, tubular legs, with glides.
Style B - Rotary, tilting, with casters.

Type IV. Posture, with arms (Figures 11, 12).

Rotary, adjustable tilting back, tilting seat, with casters.

Type V. Secretarial, without arms (Figures 13, 14, 15, 16).

Rotary, adjustable tilting back, fixed seat.

Class 1 - Leather.
Class 2 - Leather and fabric combination.
Class 3 - Artificial leather.
Class 4 - Artificial leather and fabric combination.
Class 5 - Fabric.
Class 6 - Customer's own material (COM).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Specifications and standards. The following specifications and standards of the issue in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein.

Federal Specifications:

V-T-295 - Thread, Nylon
FF-B-575 - Bolts, Hexagon and Square
FF-N-103 - Nails (Small) and Tacks: Cut
FF-S-00109 - Screws, Wood: Cross-recessed head
FF-S-111 - Screw, Wood
KK-L-291 - Leather, Cattlehide, Upholstery
QQ-A-591 - Aluminum Alloy Die Castings
QQ-C-320 - Chromium Plating (Electrodeposited)
QQ-N-290 - Nickel Plating (Electrodeposited)
TT-F-336 - Filler, Wood, Paste
TT-L-57 - Lacquer, Rubbing, Clear, (for Wood Furniture)
TT-S-720 - Stain: Wood, Non-grain-raising, Solvent-dye Type
CCC-A-00680 - Artificial Leather (Cloth Coated), Vinyl Resin, Expanded Layer, (Upholstery)
CCC-C-446 - Cloth, Muslin, Cotton
CCC-C-467 - Cloth, Burlap, Jute (or Kenaf)
CCC-T-191 - Textile Test Methods
PPP-B-601 - Boxes, Wood, Cleated-plywood
PPP-B-621 - Boxes, Wood, Nailed and Lock-corner
PPP-B-636 - Box, Fiberboard
PPP-T-45 - Tape, Gummed, Paper, Reinforced

Federal Standards:

Fed. Std. No. 123 - Marking for Domestic Shipment (Civilian Agencies)
Fed. Test Method Std. No. 175 - Adhesives: Methods of Testing

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Handbooks as outlined under General Information in the Index of Federal Specifications and Standards and at the prices indicated in the Index. The Index, which includes cumulative monthly supplements as issued, is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C., 20402.

(Single copies of this specification and other product specifications required by activities outside the Federal Government for bidding purposes are available without charge at the General Services Administration Regional Offices in Boston, New York, Washington, D.C., Atlanta, Chicago, Kansas City, Mo., Dallas, Denver, San Francisco, Los Angeles, and Seattle, Wash.

(Federal Government activities may obtain copies of Federal Specifications, Standards, and Handbooks and the Index of Federal Specifications and Standards from established distribution points in their agencies.)

Military Specifications:

MIL-R-5001 - Rubber; Latex Foam Sponge
MIL-L-10547 - Liners, Case, and Sheet, Overwrap, Water-Vaporproof or Waterproof, Flexible

Military Standards:

MIL-STD-20 - Welding, Terms and Definitions
MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129 - Marking for Shipment and Storage
MIL-STD-171 - System for Preparation, Painting, and Finishing Metal and Wood Surfaces.

(Copies of Military Specifications and Standards required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

2.2 Other publications. The following documents form a part of this specification to the extend specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

Commercial Standard:

CS35-61 - Hardwood Plywood
CS45-60 - Douglas Fir Plywood

(Copies of the Commercial Standards referenced above, which are Department of Commerce publications, may be obtained upon application, accompanied by money order, coupon, or cash, to the Superintendent of Documents, Government Printing Office, Washington, D. C. 20402. Prices may be obtained from the Superintendent of Documents).

American Society for Testing Materials

ASTM Designation: ASTM D 1055 - 62 - Standard Specifications and Methods of Test for Latex Foam Rubbers

ASTM D 751 - 60T - Tentative Methods of Testing Coated Fabrics

(Copies may be obtained upon application to American Society for Testing Materials, 1916 Race Street, Philadelphia 3, Pennsylvania).

Steel Products Manual, Carbon Steel Sheets

(Copies may be obtained from American Iron and Steel Institute, 350 Fifth Avenue, New York 1, New York).

3. REQUIREMENTS

3.1 Preproduction sample. Unless otherwise specified (see 6.2), before production is commenced, a sample of the finished item and each component part conforming to the requirements of this specification shall be offered for approval of the contracting officer or his authorized representative. Approval of the preproduction sample authorizes the commencement of production, but does not relieve the contractor of responsibility from compliance with all other applicable provisions of this specification.

3.2 Framing materials

3.2.1 Adhesives. The adhesives to be used and their permitted application shall be as shown in table I.

Table I - Adhesives

Application	Kind of Adhesives
All assembly joints, glue blocks, glued laminated stock or built-up stock.	Any adhesive that will develop an average block shear strength of not less than 2800 pounds per square inch when tested as specified in 4.3.1.1.
All hardwood plywood gluing	Any adhesive that will conform to the test requirements of the Type II bond or better, as described in the Commercial Standard CS-35-61 for Hardwood Plywood.
Adhesion of foam rubber pieces	Adhesive shall conform to MMM-A-130.

3.2.2 Filler. The filler shall be in accordance with the applicable requirements of TT-F-336 when tested as specified in 4.3.1.1.

3.2.3 Stain. The stain shall be in accordance with the applicable requirements of TT-S-720 when tested as specified in 4.3.1.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.2.4 Lacquer. The lacquer shall be in accordance with the applicable requirements of type I or type II of TT-L-57 when tested as specified in 4.3.1.1.

3.2.5 Dowels. Dowels shall be of ash, hickory, maple, birch, beech, or oak. All dowels shall be spirally and longitudinally grooved. Dowels shall be dried to a moisture content not exceeding 5 percent at the time of assembly. Where used, the dowels shall penetrate a minimum of three fourths of the penetrated member, except maximum penetration need not exceed 1 inch. Unless otherwise specified, dowels shall have a minimum diameter of 7/16 inch.

3.2.6 Wood.

3.2.6.1 Varieties of wood, Wood used in the construction of the unexposed components shall be fabricated from any of the following species of wood; Solid Birch, Maple, Oak, Ash, Beech, or Hackberry. All component parts of any one item shall be of the same species of wood. Armrests of Type III, Style A and B chairs, and Type IV Chair, shall be of genuine black walnut (Juglans nigra).

3.2.6.2 Characteristics. Wood shall be bright, well sanded and free from brashness, discolorations, worm holes, honeycomb, splits and shake, except that a few small burls, pin knots not exceeding two per square foot average, mineral streaks not exceeding 1/32 inch by 4 inches, or 1/16 inch by 2 inches, and not more than one per square foot average, will be permitted. The wood used in the fabrication of all unexposed wood parts shall be dried without brashness, casehardening or honeycombing. The following shall be permissible: Machine marks, wormholes, sapwood, sound tight pin knots (providing not more than two knots occur in any single piece and the occurrence is not on an edge or at a point that will interfere with the construction), and mineral streaks which will not affect serviceability or strength of the finished parts.

3.2.6.3 Plywood.

3.2.6.3.1 Hardwood plywood. All hardwood plywood shall be of veneer core construction conforming to the requirements of Commercial Standard CS-35-61 and as specified herein. Bondage shall be not less than type II. Grade 2 veneer faces are permissible for unexposed surfaces. Veneer core plies and veneers shall be in full length pieces and shall be applied in balanced construction form. The maximum thickness of veneer core plies shall be 1/8 inch for plywood under 3/4 inch thick and 3/16 inch thick for plywood over 3/4 inch thick.

3.2.6.3.2 Douglas Fir plywood. Douglas Fir plywood shall be of veneer core construction conforming to the requirements of Commercial Standard CS-45-60, interior type, grade A-D, INT.

3.2.6.4 Seasoning. Wood parts, including solid wood, plywood veneers and veneer cores shall be uniformly kiln dried to a moisture content of from 6 to 10 percent dependent upon the manufacturers' best commercial practice, and in addition shall be held in properly controlled, warm, dry storage for a sufficient period of time to insure a uniform distribution of moisture among the individual pieces. After gluing, all plywood veneer cores shall be permitted to cure out by one of the following methods to insure a uniform distribution of the glue joint moisture and the elimination of sunken joints, spring back and stresses:

(a) 7 days at 80°F. and 30% relative humidity.
(b) 4 days at 120°F. and 35% relative humidity.
(c) 24 hours at 160°F. and 44% relative humidity.
(d) 16 hours at 200°F. and 55% relative humidity.

3.2.7 Steel. The steel used in the fabrication of tubing used in frame and leg assemblies shall be SAE 1010 - 1020 commercial quality cold rolled strip steel.

All steel shall be bright, smooth, free from rust, scale, pits, scratches, laps and buckles affecting strength or appearance. The gage numbers specified are the manufacturer's standard gage for steel. The decimal equivalent shown for steel thicknesses are subject to the tolerances in table 14 of Steel Products Manual.

3.2.8 Hardware.

3.2.8.1 Screws. The screws shall be in accordance with FF-S-111 or FF-S-00109(COM-NBS) in the required size and shape.

3.2.8.2 Bolts. Bolts shall be in accordance with FF-B-575, Type II in the size specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.2.8.3 Tacks and staples. The tacks and staples shall be of the commercial upholstery type. All tacks shall be of blued steel and shall be in accordance with FF-N-103. Tacks for securing strip or sheet webbing shall be 12 ounce size. Tacks for securing burlap and cover material shall be 6 ounce size. Tacks for securing cambric and welting shall be 3 ounce size. Staples for securing the cover, burlap, cambric and welting materials shall be of the wire size not less than 0.030 by 0.020 inch with legs 3/8 inch long. Staples used for securing strip or sheet webbing to frame, shall be not less than 0.050 by 0.020 inch wire size with legs 1/2 inch (minimum) long. All staples shall be of steel, copper lacquered or zinc coated.

3.2.9 Chair bases.

3.2.9.1 All steel bases. The all steel base (figure 18) shall have tubular frame members of 16 gage electric welded, cold rolled FS 1018 steel tubing.

3.2.9.2 Die cast bases. The die cast aluminum base (figure 17) shall be of the following commercial designations and compositions as referenced in Federal Specification QQ-A-591, Aluminum Alloy Die Castings:

Commercial Designation (Alloy Number) - 218, 13, A13, 360 and the appropriate compositions called for in the specification.

The hub of all cast bases shall be furnished with seamless steel tubing not less than 0.062 inch thick or a commercial type, insertable hub having self-lubricating bearings. All base legs shall be bored to a depth of 1-1/2 inches to provide a drive fit for standard 7/16 inch diameter caster stems. Plastic hub liners of nylon, selcon, or zytel may be substituted for insertable metal hubs.

3.2.10 Glides.

3.2.10.1 Leg glides. Glides for the style A chairs shall be of the rubber shank expanding adapter type, rubber cushioned with the lower surface (in contact with the floor) of type 430 corrosion-resistant steel. Glide diameter shall approximate but not exceed diagonal measurement of tubular legs by more than 1/8 inch

3.2.10.2 Base glides. Glides for base of nontilting rotary style C chair shall be provided with a 7/16 inch diameter stem to permit insertion into the chair base. Glide shall be of the rubber cushioned type with lower surface, in contact with floor, of type 430 corrosion-resistant steel.

3.2.11 Casters. The casters shall conform to the requirements of type I, ball-bearing swivel, style a, stem and socket, material 1, hard-rubber composition wheel with soft rubber tread (nonmarking) of FF-C-82. All casters shall be hooded and shall have a chrome plated finish. All casters shall be spherical shaped and the minimum diameter, between hubs, shall be 2 inches for type I, II, III, and IV chairs and 1-5/8 inches for type V chairs.

3.2.12 Upholstery materials.

3.2.12.1 Leather. Leather shall conform to type II, finish C of KK-L-291, except that the leather is dyed and unembossed. Colors shall be as specified (see 6.2).

3.2.12.2 Artificial leather. The artificial leather shall conform to class 1 of CCC-A-00680. The finish shall be that of simulated top grain leather and the color shall be as specified (see 6.2).

3.2.12.3 Fabric. The fabric shall be 100 percent yarn dyed virgin nylon in homespun weave with not less than 13 threads per inch in the warp and not less than 12 threads per inch in the filling and shall weigh not less than 21 ounces per linear yard on a 54 inch width basis when tested as specified in 4.3.1.1. The breaking strength shall be a minimum of 150 pounds when tested as specified in 4.3.1.1. The reverse side shall be coated with a latex or acrylic compound to a minimum dry weight of 1-1/2 ounces. The fabric shall be treated chemically for spot resistance. The colors shall be as specified (see 6.2). The fabric shall show at least a fair fastness to light after an exposure for 60 hours when tested as specified in 4.3.1.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.2.12.4 Muslin. Muslin shall conform to type V, class 1 of CCC-C-446.

3.2.12.5 Burlap.

3.2.12.5.1 Insulation burlap. Insulation burlap shall conform to class 3 of CCC-C-467.

3.2.12.5.2 Sheet webbing burlap. Sheet webbing burlap shall weigh not less than 17 ounces per square yard when tested as specified in 4.3.1.1.

3.2.12.6 Cambric. Cambric shall weigh not less than 3.2 ounces per linear yard on a 30 inch width basis when tested as specified in 4.3.1.1. The color shall be black and one side of the fabric shall be glazed.

3.2.12.7 Non-woven fabric and wadding. The non-woven fabrics and wadding used shall consist of new neutral fabrics consisting of approximately 40 percent cotton fiber and 60 percent cotton linters with a latex binder. The waddings shall be either light or heavy duty as specified herein. The light duty wadding shall weigh approximately 7.2 ounces per square yard when tested as specified in 4.3.1.1 and have a compression set of approximately 18.3 percent. The heavy duty wadding shall weigh approximately 14.4 ounces per square yard when tested as specified in 4.3.1.1 and have a compression set of approximately 17.6 percent.

3.2.12.8 Foam rubber.

3.2.12.8.1 Slab stock. The slab stock foam rubber shall conform to Type II, Class Medium, Grade C, of MIL-R-5001, except that the compression resistance shall be measured by Method A in lieu of Method B as specified, and the low-temperature requirements shall be waived. (Class Medium of MIL-R-5001 is designated as RU 35 of ASTM-D-1055 - 62).

3.2.12.8.2 Pin-core. Pin-core foam rubber shall be cored from one or both sides with cores approximately 3/16 inch in diameter and shall conform to Type I, Grade C, Medium density of MIL-R-5001, or conform to RC 25 of ASTM Standard D 1055 - 62).

3.2.12.9 Rubber webbing. The rubber webbing shall be 2-1/4 inches plus or minus 1/8 inch wide having a breaking strength of not less than 300 pounds and an elongation of not less than 35 percent when tested as specified in 4.3.1.1

3.2.12.10 Sewing thread. Thread for machine sewing and stitching shall conform to the requirements of Type III, Size E, of V-T-295. Unless otherwise specified (see 6.2), the color of the thread shall approximate the color of the material.

3.2.12.11 Cord, welting. The welting cord shall be made from 8 plies of jute yarn, twisted to form a cord having a diameter of 1/8 to 3/16 inch, and shall have a minimum breaking strength of 215 pounds when tested as specified in 4.3.1.1. The weight per 205 linear feet shall be not less than 1 pound when tested as specified in 4.3.1.1. Alternatively, silver spring twine 60/6 ply of 100 percent rayon, approximately 3/32 inch in diameter may be used.

3.3 Construction

3.3.1 Design. The design of the chairs covered by this specification shall be as shown in figures 1 through 16.

3.3.2 Tolerances. Unless otherwise specified, the following tolerances are permissible

(a) Any height dimension	-	Plus or minus 1/4 inch.
(b) Width dimensions:		
Type I and II (overall)	-	Plus 1/2 inch minus 1/4 inch.
Type III (seat and back only)	-	Plus 1/4 inch minus 1/8 inch.
Type III (between front arm stumps)	-	Plus or minus 1/8 inch.
Type IV (seat and back)	-	Plus or minus 1/4 inch.
Type IV (between front arm stump)	-	Plus or minus 1/8 inch
Type V (seat and back)	-	Plus or minus 1/4 inch.
(c) Metal bases (rotary)	-	Plus 1 inch minus 1/8 inch.
(d) Angles less than 12 degrees	-	Plus or minus 1 degree.
(e) Angles over 12 degrees	-	Plus or minus 2 degrees.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.3 Definition of welding terms used herein.

3.3.3.1 Welding terms. All spot welding and electrical resistance welding shall be as defined in MIL-STD-20. Definitions of these terms in MIL-STD-20 are as follows:

Resistance welding: A group of welding processes wherein coalesence is produced by the heat obtained from resistance of the work to the flow of electric current in a circuit of which the work is a part, and by the application of pressure.

Spot welding: A resistance welding process wherein coalescence is produced by the heat obtained from resistance to the flow of electric current through the work parts held together under pressure by electrodes. The size and shape of the individually formed welds are limited primarily by the size and contour of the electrodes.

Fusion welding and brazing shall be defined as follows:

Fusion welding: Fusion welding consists of any welding process in which the weld is carried out solely by the melting of the metals to be joined, without any mechanical pressure. The joining is usually accomplished through the fusion of metal deposits from an external source.

Brazing: Brazing is the joining of metals with the aid of a filler metal of a different composition having a melting point above 800 degrees Fahrenheit. Brazing method shall be gasflux, using nickel bronze rod (nickel content 9.5%, tensile strength 70,000 - 75,000 p.s.i) acetylene, and oxygen (or propane) gases.

Brazing over fusion welding may be used to smooth welding joints.

3.3.4 Assembly. All mechanical and welded attachments shall produce secure, rigid joints and connections in proper alignment. Assembly shall provide rigid furniture that shall have sufficient strength to prohibit the loosening of any part, or result in any other defect which might affect serviceability or the safety of its occupants.

3.3.5 Chair mechanisms. Chairs, style B of Types I, II and III chairs shall be fitted with a chair control for tilting of the seat. The adjustment shall be made by means of malleable cast or pressed steel handles or hand wheels. An adjustment shall be provided for raising the seat over a range of not less than 3 inches. The mechanism shall be self-locking and shall permit revolving without changing height of the seat. Maximum tilting range 24 degrees.

Chair, Type IV. Chairs shall be fitted with a mechanism for tilting both the seat and back by use of tension units, raising the seat not less than 3 inches and raising the back by means of a malleable cast or pressed steel handle or handwheel. Both horizontal and vertical adjustment shall be provided for the back and it shall be easily adjustable.

Chair, Type V. - Chair shall be fitted with a chair control for tilting of the back. The adjustments for tilting the back rest, raising the seat not less than 3 inches, and raising the back rest shall be made by means of malleable cast or pressed steel handle or handwheel. Both horizontal and vertical adjustment shall be provided for the back rest and shall be easily adjustable. The mechanism shall be rigid without apparent looseness. The seat height adjustment shall be self-locking and shall permit revolving without changing the height of the seat.

Chair, Type I, style C.- The chair control mechanism for the Type I, style C rotary chair shall revolve but not tilt. The chair control shall be provided with "spider arms" to support the weight and stress imposed on the unit by the bucket chair seat. Control shall have a minimum height adjustment of three inches.

NOTE: All units shall be equipped with safety stop to insure the back from giving way on failure of the mechanism. Spindles of chair controls may be permanently secured to mechanism or may be unassembled.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.6 Welts. All welts shall be self-welts of leather (classes 1 and 2), artificial leather (classes 3 and 4), fabric (class 5), or customer's own material (class 6) as specified (see 1.2.1 and 6.2). The welts shall be uniformly drawn over the cord specified in 3.2.12.11 in suitable size for the particular application.

3.3.7 Type I, bucket chair. The type I bucket chair shall be either straight (style A), rotary, tilting with casters (style B), or rotary, nontilting with glides (style C) (figures 1, 2,and 3) as specified (see 1.2.1 and 6.2).

3.3.7.1 Dimensions. The dimensions in inches of the typeI chair shall be as follows:

Overall width	-	26-1/2
Width between arms	-	19-3/4 (above cushion)
Seat height	-	17-1/2
Back height	-	20-1/4
Seat depth	-	20

3.3.7.2 Construction.- Type I Chair. The seat shall consist of a platform of 1 inch thick veneer core fir plywood, minimum of 7 plies, joined to a preformed shell of 1/2 inch thick veneer core hardwood plywood having a minimum of 5 plies. The plywood shall be as specified in 3.2.6.3. The shell shall be shaped as in Figures 1 through 3. There shall be a seat brace block 1-1/16 inch thick by 1-1/2 inch wide by 8-1/2 inches long (minimum dimensions) attached with two 2 inch No. 9 flat head screws to the top of the platform on each side 7 inches from the front of the platform and flush with the sides. There shall be a seat brace block of the same cross section 16-3/4 inches long, curved to the shape of back, attached with three 2-inch No. 9 flat head screws to the seat platform, mitered and fitted to the inside backs. There shall be a minimum of three 1-1/2 inch No. 9 screws in the back and a minimum of two of the same on each side through the exterior of the shell and into the seat brace blocks. There shall be a top arm and front arm filler block, 1-1/16 inches wide by 3/4 inch thick, attached to the inside top and front of the shell on each side by two 1-1/2 inch screws for shaping and supporting the arm as shown in Figure 1. Pin-core rubber 2 inches thick shall be shaped and adhered to the inside of the sides and back and finished off with a 1/2 inch minimum thickness of slab stock foam rubber continuing over the top of the arms and back, fastened to the back forming a continuous line from the base of top edge of both arms and backs. The adhesive shall be as specified in 3.2.1. There shall be a tight seat foundation of 1-1/2 inch slab stock foam on top of 1-1/2 inch pin-core rubber attached to a 3/8 inch fir plywood seat pan, banded by 1/2 inch by 4-3/4 inch stock rubber around front edge. The pan shall be fitted with four evenly spaced "Tee" nuts to receive four round head slotted machine bolts 1/4 inch by 1-1/2 inch for attaching the tight seat to the seat platform. For additional bracing the back shall be secured to the seat brace blocks with four 1-1/2 inch by 1-1/2 inch by 1 inch by 1/8 inch steel "L" brackets. The bracket is bolted to the back by a 1-1/4 by 1/4 inch carriage bolt and screwed to the seat brace block with a 1 inch No. 9 flat head screw. Holes shall be bored in the seat platform (see Figures 1 through 3) to receive 1/4 inch "Tee" nuts for attaching the mounting plates of the legs or for attaching the base. A layer of heavy duty, non-woven fabric and wadding specified in 3.2.12.7 shall be applied to the outside face of the back and arms before application of the outer cover.

3.3.7.3 Legs, Type I style A chair.- The tubular legs of the Type I style A chair shall be 7/8 inch, 16 gage, (0.0598 inch) steel as specified in 3.2.7 and positioned as shown in Figures 1 and 2. The upper end of the legs shall be continuously fusion butt-welded to a steel mounting plate 2-3/4 inches square by 1/8 inch thick. The leg assembly shall be secured to the seat platform by four pan head machine bolts (1/4 inch by 1-1/4 inch). The bolts shall be received by four T-nuts inserted into the upper face of the platform.

3.3.7.4 Base, style B chairs. The base for the style B chairs shall be as shown in figure 17 and as specified in 3.2.9.1 and 3.3.5.

3.3.8 Type II, high back chair. The type II, high back chair shall be either straight (style A) or rotary, tilting with casters (style B)(figures 4,5, and 6) as specified (see 1.2.1 and 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.8.1 Dimensions. The dimensions in inches of the high back chair shall be as follows:

Overall width	28-1/2
Seat width	22-1/2
Back width (Top)	24-1/4
Front wing (Top)	25
Overall height	37
Arm height (from floor including glides)	24-3/4
Arm height (from platform, outside)	12-3/4
Arm height (from seat inside)	8

3.3.8.2 Construction - Type II chair.

3.3.8.2.1 Dimensions of framing members. The dimensions of the framing members shall be as shown in Table II.

TABLE II - Dimensions of framing members - Type II chair

Member	Finished Dimensions (in inches)
Front rail	1-3/4 by 2-1/2
Side rails (2)	1-1/16 by 2-1/2
Top back rail	1-1/16 by 2-1/2
Bottom back rail	1-1/16 by 2-1/2
Center back rail	1-1/16 by 2-1/2
Bottom back rail strip	1-1/16 by 1-1/4
Leg rails (2)	1-1/16 by 3
Back posts (2)	1-1/16 by 2-3/4
Arm stumps (2)	1-1/16 by 1-3/4 by 2
Top arm rails (2)	1-1/16 by 1-3/4
Bottom arm filler strips (2)	1-1/16 by 2
Back braces (2)	1-1/16 by 1-1/4
Side stretchers (2)	1-1/16 by 1-1/2
Wing blocks (2)	1-1/4 stock
Back post strip (2)	1-1/16 by 1-1/4

NOTE: The outside bottom edge of all perimeter framing members shall be rounded to a minimum of 3/4 inch radius.

3.3.8.2.2 Gluing of joints. All framing members shall be joined by dowels, specified in 3.2.5, and shall be thoroughly glued. The position of the members and the dowels shall be as shown in Figures 4,5 and 6. The number of dowels in each member shall be as specified herein. All joints shall be machined to make a smooth snug fit and shall have a thorough application of glue. The joints shall have complete contact along the joining surfaces and shall be held under pressure until the glue has set. The adhesives shall be as specified in 3.2.1.

3,3.8.2.3 Doweling. The number of dowels used and their location shall be as shown in Table III.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE III. Dowels-location and number- Type II Chair

Member	Joined to	Number of dowels	Location
Side rails	Front rail Back posts	2	Each end
Bottom back rail	Back posts	2	Each end
Center back rail	Back posts	2	Each end
Leg rails	Front rail Bottom back rail	2	Each end
Top back rail	Back posts	2	Each end
Back braces	Top back rail Center back rail	1	Each end
Side stretchers	Arm stump Back post strip	1	Each end
Top arm rails	Arm stump Back post strip	1	Each end
Arm stumps	Side rails	2	Inside bottom

3.3.8.2.4 Screws in frame. All screws shall be a minimum of No. 10 and all joints shall have a thorough application of glue before the screws are inserted. The number of screws used, their position and length, shall be as shown in Table IV. All screw lengths are minimum.

TABLE IV - Screws - location, length and number- Type II chair

Free-hole member	Screw insertion member	No. of screws	Length (in inches)
Back post strip (2) (Taper of strip requires 3 different screw lengths)	Back post	1 (Top)	1
		1 (Middle)	1-1/2
		1 (Bottom)	2
Wing-block (2)	Top arm rail	1	2-1/4
Seat brace block (2)	Front rail	1 ea.	1-3/4
(2)	Bottom back rail	1 ea.	1-3/4
Side rail (2)	Bottom arm filler strip	2 ea.	2
Bottom back rail	Bottom back rail strip	3	2
Back post (2)	Wing at top	2 ea.	2
Top arm rail	Wing at bottom	1 ea.	2-1/4

Note: The screws originate and pass through the "Free hole member" and are inserted into the "Screw insertion member".

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.8.2.5 Platform and foundation. The platform shall consist of interlaced rubber webbing strips specified in 3.2.12.9. There shall be five strips from the front rail to the bottom back rail and five strips from side rail to side rail, equally spaced. Each strip shall be tightly stretched, attached to the rails on each end, and stapled with six staples, specified in 3.2.8.3, on each end. There shall be a 1 inch thick slab stock foam rubber foundation cut to conform to the shape of chair as shown in Figure 4, on top of 1-1/2 inches of pin-core rubber for the seat, banded with 1/2 inch by 5-1/2 inch slab stock rubber around the edge.

3.3.8.2.6 Inside and outside back and arms. The inside of the back and arms shall be covered with sheet webbing, specified in 3.2.12.5.2, tacked or stapled, using tacks or staples specified in 3.2.8.3, to the framing members and all edges folded over and tacked or stapled again. The inside back and arms shall have a preformed 1-1/4 inch slab foam rubber foundation with a 1/2 inch thick foam rubber banding applied with adhesive specified in Table I. The 1/2 inch firm foam rubber banding shall be fastened to the top rail, wings, arm stump face, arms, and front edge of the seat with adhesive specified in Table I. The outside back and arms shall have 0.054 hardboard stapled securely to the framing members plus a layer of 1/2 inch thick heavy duty, non-woven cloth, specified in 3.2.12.7, prior to application of the upholstery material.

3.3.8.2.7 Legs, style A chair. The tubular legs of the style A chair shall be 7/8 inch square steel, specified in 3.2.7, and positioned as shown in Figures 4 and 5. The upper end of the leg shall be fusion butt-welded to a 2-3/4 inches square by 1/8 inch thick mounting plate. The leg assembly shall be secured to the leg rails by four pan head machine bolts (1/4 by 1-1/4 inches). The bolts shall be received by four T-nuts inserted into the upper surface of the leg rails of the seat platform. Each chair shall be furnished with glides specified in 3.2.10.1.

3.3.8.2.8 Base, style B chair. Base for the style B chair shall be as shown in Figure 18 and as specified in 3.2.9.1 and 3.3.5.

3.3.9 Type III, square chair. The type III, square chair shall be either straight (style A) or rotary, tilting with casters (style B) as specified (see 1.2.1 and 6.2).

3.3.9.1 Style A, straight chair (figures 7 and 8).

3.3.9.1.1 Dimensions. The dimensions in inches of the style A chair shall be as follows:

Overall width (outside arms)	25-3/4
Seat and back	20
Frame	22-1/4
Overall height (including glides)	34
Seat (from floor, including glides)	17-3/4
Arm (from floor, including glides)	25
Arm (from bottom of seat, front edge)	10-1/2
Overall depth (seat level)	24-1/2
Depth at arm height	22
Frame depth (outside dimension)	20
Seat depth (inside dimension)	18-1/2

3.3.9.1.2 Seat frame. The seat frame shall consist of a front rail and back rail 3 inches wide and two side rails 3-1/2 inches wide by 1-1/16 inches thick (minimum) a front edge block (wedge shape) 1-1/4 inches high by 3-1/4 inches by 3-1/4 inches deep and a back brace block (machined) of 2 inch by 2 inch stock by the width of the frame. The side rails shall be joined to the front and back rails by two 7/16 inch diameter dowels inserted into the ends of the side rails and the sides of the front and back rails with a thorough application of glue. The front edge block shall be glued and screwed to the front rail flush with the edge of the frame by one No. 9 screw penetrating rail to a depth of 3/4 inch. The back brace block shall be glued and screwed to the back rail by a minimum of three No. 9 screws penetrating rail to a depth of 3/4 inch. The bottom edge of the seat frame shall be rabbeted 3/4 inch wide by 3/16 inch deep around the perimeter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.9.1.3 Platform and foundation. The platform shall consist of interlaced rubber webbing strips specified in 3.2.12.9. There shall be four strips equally spaced from the front rail to the back rail and four equally spaced from side rail to side rail. Each strip shall be fastened on each end to the rails with staples specified in 3.2.8.3. There shall be a 2-1/2 inches thick slab stock foam rubber foundation or seat pad cut to conform to the shape of the chair. The slab stock foam shall be as specified in 3.2.12.8.1 and shall be secured to the seat frame with adhesive specified in 3.2.1.

3.3.9.1.4 Back. The back shall be of the 5-ply hardwood plywood specified in 3.2.6.3.1. There shall be a 3/4 inch wide by 3/16 inch deep rabbet on three sides. A wedge shaped, 15/16 inch by 3-1/4 inches by 3-1/4 inches edge block shall be glued and screwed flush to the inside top of the back. The back shall have a slab stock foam rubber pad (one piece or built-up stock) tapered from 2-1/2 inches thick at the seat to 1-3/4 inches thick at the top. The slab stock foam shall be as specified in 3.2.12.8.1 and shall be secured to the back with adhesive specified in 3.2.1. The back shall be attached to the seat frame with a thorough application of glue and by four 1-1/2 inch No. 9 screws into the back rail and two 1-1/4 inch screws into the back brace block. For reinforcement there shall be two steel angles (1 inch wide by 1/8 inch thick having legs 1-1/2 inch by 1-1/2 inch) attached to the seat brace block and into the plywood back by No. 10 x 1 inch sheet metal type screws as shown in Figure 7.

3.3.9.1.5 Tubular chair frame. Legs, armrest support and upper back rail of tubular frame shall be of 5/8 inch square, 16 gauge (0.0598 inch) seamless or continuously welded steel tubing fabricated of steel specified in 3.2.7. Tubing shall be rounded at corners to a radius ranging from 1/32 inch to 1/16 inch. The top ends of the legs and both ends of the armrest support shall be mitred and welded. The back rail of the chair frame shall extend between and shall be welded to the rear corner of the left and right leg and armrest assemblies. The armrest base plate shall be 1-3/4 inch wide by 13 inches long and shall be fabricated of 11 gage (0.1196 inch) steel specified in 3.2.7. This plate shall have three holes, properly spaced, not more than 1/32 inch greater in diameter than the screw used in attaching the armrest. The armrest base plates shall be securely fusion welded to the armrest shown in Figure 7. An armrest of walnut, specified in 3.2.6.1, and measuring 2-1/2 inches wide by 3/4 inch thick by 15 inches long shall be attached to the base plate. A spreader side rail shall extend between and shall be continuously fusion welded to the front and rear legs. The spreader shall be 2-1/2 inches by 1/2 inch 16 gage seamless or continuously welded steel tubing as shown in Figure 7.

There shall be two 1 inch by 1 inch by 11 gage steel angle-shape seat supports extending between and continuously fusion welded to the spreaders at the locations shown in Figure 7. The leg of the angles supporting the seat shall have two free holes in each for No. 10 x 1 inch sheet metal type screws with the holes being 2-1/2 inches from each end of the supports. A rear tie extending between and welded to the back posts, shall be 2 inches by 1/2 inch by 16 gage seamless or continuously welded steel tubing of the material specified in 3.2.7.

3.3.9.2 Style B, rotary chair (figures 9 and 10).

3.3.9.2.1 Dimensions. The dimensions in inches of the style B chair shall be as follows:

Overall width (outside armrest)	24-3/4
Seat and back	20
Frame	21-1/4
Arm (from bottom of seat)	10-13/16
Frame depth (outside dimension)	17-1/2
Seat depth (inside dimension)	18-1/2

3.3.9.2.2 Seat frame. The seat frame shall be of the construction specified in 3.3.9.1.2.

3.3.9.2.3 Platform and foundation. The platform and foundation shall be as specified in 3.3.9.1.3.

3.3.9.2.4 Back. The back shall be constructed as specified in 3.3.9.1.4.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.9.2.5 Tubular frame style B rotary chair. The tubular frame for the style B chair shall be of 5/8 inch square, 16 gauge, (0.0598 inch) seamless or continuously welded steel tubing fabricated of steel specified in 3.2.7. Tubing shall be rounded at corners to radii ranging from 1/32 inch to 1/16 inch. The top ends of the arm stumps and front ends of the tubular horizontal armrest supporting frame member shall be mitred and welded. The back rail of the chair frame shall be mitred and shall extend between and welded to the rear mitred corner of the left and right armrest supporting frame members. The lower ends of the arm stumps shall be mitered to receive mitered tubular sections spanning across the width of the metal frame. The tubular sections shall be continuously fusion welded to 11 gage mounting plates 2-1/4 inches wide by 4 inches long drilled to receive No. 12 screws. The mounting plate arm assembly shall be secured to the underside of the seat frame by a minimum of two 1-1/4 inch No. 12 sheet metal type screws on each plate. The armrest base plate shall be as specified in 3.3.9.1.5 except it shall be 11 inches long and the walnut armrest shall be 13 inches long.

3.3.10 Type IV, posture chair (figures 11 and 12)

3.3.10.1 Dimensions. The dimensions in inches of the type IV chair shall be as follows:

Overall width (outside of arms)	25-1/2
Seat	20-3/4
Frame (outside dimension)	22
Back (tapered) top dimension	21
Overall height	32-3/4
Seat (from floor)	17-1/2
Arm (from floor)	25
Arm (from bottom of frame)	11-1/2
Arm (from top of seat)	7-1/2
Overall depth	
Seat	20
Arm	15

3.3.10.2 Seat, frame and platform. The seat frame shall consist of two side rails 3-1/2 inches wide by 1-1/16 inches thick and a front and back rail 3-1/2 inches wide by 1-1/16 inches thick and a front and back edge block 1-1/4 inches by 3-1/4 inches by 3-1/4 inches. The seat frame members shall be joined by a thorough application of glue specified in 3.2.1 and two dowels specified in 3.2.5 in each joint. The edge blocks shall be thoroughly glued and screwed flush with the outer edges of the front and back rails by one No. 9 by 1 inch screw in each edge block. The platform shall consist of interlaced equally spaced rubber webbing strips specified in 3.2.12.9. There shall be four strips from the front rail to the back rail and four strips from side rail to side rail. The rubber webbing strips shall be fastened with six staples, specified in 3.2.8.3, on each end. The seat pad shall be of 2-1/2 inches thick slab foam rubber cut to shape and banded with 1/2 inch by 3-1/2 inch slab stock on all four sides.

3.3.10.3 Tubular chair frame. The arm assembly shall consist of front and rear arm stumps of 5/8 inch, square, tubular, 16 gage (0.0598 inch) seamless or continuously welded steel tubing fabricated of steel specified in 3.2.7. Tubing shall be rounded at corners to radii ranging from 1/32 inch to 1/16 inch. The upper ends of the arm stumps shall be mitered to receive the mitered ends of the horizontal armrest support. The lower ends of the arm stumps shall be mitred to receive the mitred tubular sections spanning under and across the side rails of the wood platform assembly. The tubular sections shall be continuously fusion welded to 11 gage (0.1196 inch) mounting plates 2-1/4 inches wide by 16-1/2 inches long. The steel mounting plates shall be secured to the under side of the seat frame by a minimum of six 1-1/4 inch by No. 12 machine screws on each plate. The armrest base plate shall be as specified in 3.3.9.1.5.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.3.10.4 Back. The back pan shall consist of two sections. The sections shall be of 3/8 inch 3-ply plywood specified in 3.2.6.3.1. The dimensions shall be 21 inches wide at the top, 18 inches wide at the bottom and 13 inches high. The back section shall have a rout on the inside surface perimeter (in between the two sections), 3/4 inch wide by 3/16 inch deep. The front section shall have a 1-1/2 inch thick slab stock foam rubber foundation banded with 1/4 inch by 1-7/8 inch slab stock all around back attached to the surface with adhesive specified in Table I. The sections shall be bolted together with two 3/16 inch carriage bolts which shall also fasten the back to the back supports.

3.3.10.5 Base Type IV chair. Base for the Type IV chair shall be as shown in Figure 18 and as specified in 3.2.9.2 and subsequent paragraphs.

3.3.11 Type V, secretarial chair (figures 13, 14, 15 and 16).

3.3.11.1 Dimensions. The dimensions in inches of the Type V chair shall be as follows:

Overall height	32
Seat height (from floor line)	17 adjustable to 20
Overall width	18
Seat width (rounded corners)	18 tapered from front to rear to 16
Back width (rounded corners)	16 tapered from top to bottom to 12
Seat depth	16

3.3.11.2 Construction, Type V chair. The seat shall have a pan of 1/2 inch 5-ply fir plywood as specified in 3.2.6.3.2. There shall be a 2 inch thick slab stock foam rubber pad banded with 1/2 inch by 2-1/2 inch slab stock all around seat as specified in 3.2.12.8.1 applied to the pan with adhesive as specified in 3.2.1. The pan shall have prepositioned T-nuts inserted in proper position to receive the machine screws (1/4 inch by 3/4 inch) for attaching the base. The back rest shall consist of two sections of 3/8 inch bent hardwood plywood as specified in 3.2.6.3.1. The rear section shall be routed 1/8 inch deep by 3/4 inch wide on the inside surface to receive the upholstery material. The front section of the back rest shall have 1 inch slab stock foam rubber pad as specified in 3.2.12.8.1 applied to the section with adhesive as specified in 3.2.1. The rubber shall be cut to shape allowing the circumference of the section to be covered by a minimum of 1/4 inch foam rubber Each section shall be upholstered separately and shall be held in position by two prepositioned carriage bolts (3/16 inch) inserted through the front section of the back rest and protruding through the back section into the back support brackets.

3.3.11.3 Base, Type V chair. The base and mechanism for the Type V chair shall be as specified in 3.2.9.2 and 3.3.6 and as shown in figure 17.

3.3.12 Application of upholstery. All chairs shall be covered with artificial leather, specified in 3.2.12.2, leather, specified in 3.2.12.1, or fabric, specified in 3.2.12.3, or combinations thereof, or customer's own material (COM) as specified (see 1.2.1 and 6.2). Covers shall be tailored carefully and so applied that they are neat and tight, free from wrinkles and bulges. Welts, specified in 3.3.6, shall lie straight along the edges for which they are specified. Covers for all units shall be tacked or stapled using tacks or staples specified in 3.2.8.3. Outside covers shall be applied using a metal tacking strip having tacks enclosed and not more than 1-3/8 inches apart or a flexible metal tacking strip. All chair seat bottoms shall be covered with cambric specified in 3.2.12.6 and applied so that the glazed side of the fabric is exposed. Cambric shall be attached by tacking or stapling using tacks or staples specified in 3.2.8.3. Plain seams without welts shall be used for the inside arms of the type I chairs and for the inside arms and top of the arm cover for the type II chairs. There shall be a continuous welt on the outside edge of the top, wings, arms and seat of the type II chairs. Types III and IV chairs shall have upper and lower welts on the seat and front and rear welts on all edges of the back. The seat top panel of the type V chair shall be sewn to the boxing with a plain seam and a welt shall be applied on the bottom edge of the seat and on the back edge of the back rest.

3.3.12.1 Sewing. Stitches, seams, stitching types shall conform to Fed. Std. No. 751. All seams shall be sewn with 7 to 11 stitches per inch for fabric and 5 to 9 stitches per inch for leather or artificial leather, using thread specified in 3.2.12.10. The stitch type shall be 301. Plain seams shall be type SSa-1 and welt seams shall be type SSk-1. Seam allowance shall be maintained and seams properly sewn so that no raw edges, run offs, broken or skipped stitches, twists, pleats, or puckers result. Top and bottom threads shall be adjusted to upholstering materials with proper tension so there will be no looped stitches or puckering of fabric and no cracking when cover is stretched to fit the furniture.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

3.4 Metal and wood finishes.

3.4.1 Zinc plating. Zinc plating shall be in accordance with MIL-STD-171(ORD), paragraph 5.1.1 (Organic finishes) and of the kind shown in Table I, Finish 1.9 (Zinc plating). The type shall be as shown in 1.9.2 and 1.9.2.1. The final finish shall be bright.

3.4.2 Chromium plating (Satin). Chromium plating shall be in accordance with QQ-C-320, Class 1, Type II. The copper plus nickel undercoat on the steel base metal shall conform to Class 1, Type III, of QQ-N-290."

3.4.3 Methods of wood finishing. The wooden arm rests shall be finish sanded smooth, corners and edges eased, and thoroughly cleaned and finished as specified herein.

3.4.3.1 Procedure for clear wood finish on open pore wood:

1. Sap stain to equalize wood color.
2. Apply selected colorant to wood to produce color specified. Stain and colorant shall conform to tests specified in 4.3.1.1.
3. Wash coat with adhesive sealer. Sealer shall withstand toughness and adhesion test specified in 4.3.1.1.

4. Scuff sand, using fineness of sandpaper grit needed to produce proper surface.
5. Fill to degree necessary to match sample.

6. Seal with adhesive type sealer. Sealer shall withstand toughness and adhesion test specified in 4.3.1.1.
7. Sand, using fineness of sandpaper grit needed to give proper surface.
8. Shade to tie in color variation, if necessary.

9. Top coat with lacquer (2 coats). The lacquer and finish shall be of a quality to meet the requirements specified in 4.3.1.1.
10. Rub, steel wool, wax or polish, as required, to a soft non-gloss patina.

NOTE: Operation number 8 may be performed where shown or after operation number 5.

3.5 Color and appearance of finish (wood armrests). The color and appearance of the finish shall conform to the standard finish reference panel as adopted by the Federal Supply Service, General Services Administration for color, texture, gloss and quality (see 6.3).

3.6 Identification marking. Each item shall be permanently and legibly marked in an inconspicuous place with the specification number, Federal Stock Number, contract number, date of manufacture and the manufacturer's name or trade-mark, so that the source of supply may be readily determined.

3.7 Workmanship. A high degree of craftmanship, with extra care in fabrication and quality control, shall be exercised in order to produce superior chairs suitable for use in executive offices. The methods of construction, assembly, upholstering, finishing, and the appearance of the chairs in general, shall be in strict accordance with the requirements of this specification. Chairs shall conform to the level of quality established herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

4. QUALITY ASSURANCE PROVISIONS

4.1 General quality assurance provisions

4.1.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the supplier is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified, the supplier may utilize his own facilities or any commercial laboratory acceptable to the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.1.2 Government verification. All quality assurance operations performed by the contractor shall be subject to Government verification at unscheduled intervals. Verification shall consist of surveillance of the operations to determine whether the practices, methods, and procedures of the written inspection plan are being properly applied, and Government product inspection, to measure quality of product offered for acceptance. Deviation from the prescribed or agreed-upon procedures, or instances of poor practices that might have an effect on the quality of the product will be immediately called to the attention of the contractor. Failure of the contractor to promptly correct the deficiencies discovered shall be cause for suspension of acceptance until the correction has been made or until conformance of product to prescribed criteria has been demonstrated. To avoid interference with operations, the contractor shall e signate a responsible official, or officials, to whom the Government inspector will report such instances.

4.2 Preproduction sample inspection. Examination and testing shall be made of the completely fabricated item for all provisions of this specification.

4.3 Sampling for inspection and acceptance. Sampling and inspection shall be performed in accordance with the provisions set forth in MIL-STD-105, except where otherwise indicated hereinafter.

4.3.1 Inspection of materials and components. In accordance with 4.1, the supplier is responsible for insuring that materials and components used were manufactured, tested, and inspected in accordance with the requirements of referenced subsidiary specifications and standards to the extent specified, or if none, in accordance with this specification.

4.3.1.1 Testing of components. In addition to the quality assurance testing provision of the subsidiary specifications, testing of the components shall be performed in accordance with Table V for the characteristics shown therein. The values specified in section 3 of this specification apply to the average determinations made on a sample unit for test purposes as specified in the applicable test method. The lot size shall be expressed in units applicable to the component being tested, i.e., tubes, cones, spools, yards, etc. When the sample size for components covered by the subsidiary specifications is not specified, the sample size for each characteristic shall be in accordance with inspection level S-2 of MIL-STD-105 except that for lot sizes of 501 (units of products) and over the sample size shall be 5. The lot shall be unacceptable if one or more sample units fail to meet any of the requirements specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

Table V - Instructions for testing components and materials

Component	Characteristic	Requirement Reference	Test Method	Sample Unit
Adhesive	Block shear test	3.2.1	1031 of Federal Test Method Std. No. 175 1/ 2/ 3/	½ pint
Fabric Upholstery	Yarns per inch (± 2) Weight per linear yard Identification of nylon Breaking strength Colorfastness to light	3.2.12.3	5050.1 of CCC-T-191 5041 of CCC-T-191 1530 of CCC-T-191 5100 of CCC-T-191 5660 of CCC-T-191	2 yards
Sheet Webbing Burlap	Weight per square yard	3.2.12.5.2	5041 of CCC-T-191	½ yard
Cambric	Weight per square yard	3.2.12.6	5041 of CCC-T-191	½ yard
Nonwoven fabric and wadding	Weight per square yard	3.2.12.7	5041 of CCC-T-191	½ yard
Rubber Webbing	Breaking strength, longitudinal Elongation	3.2.12.9	Method B, ASTM D 751 - 60T 4/	1 yard
Cord, Welting	Identification of jute Breaking strength Weight per 205 linear feet	3.2.12.11	1260 of CCC-T-191 4102 of CCC-T-191 4010 of CCC-T-191	7 yards
Finish system (Stain, sealer, filler, and lacquer) 5/	Spot test - alcohol Print resistance Cold check resistance Boiling water Ultra-Violet resistance Toughness and adhesion	3.2.4 and 3.4.3	4.3.3.3 and 4.3.3.3.1 of TT-L-57 4.3.3.4, 4.3.3.4.1, 4.3.3.4.2 and 4.3.3.4.3 of TT-L-57 4.3.3.5, 4.3.3.5.1, 4.3.3.5.3 of TT-L-57 4.3.3.6 of TT-L-57 4.3.3.7 of TT-L-57 4.3.1.1.1 herein	½ pint of each

1/ The following modifications apply when testing casein-type adhesive. The test blocks shall be placed under pressure between 10 and 20 minutes after spreading the adhesive, the adhering pressure shall be 175 ± 25 pounds per square inch, and the test blocks shall be held under pressure for at least four hours.

2/ The following modifications apply when testing animal adhesive. The moisture content of the wood shall be from 6 to 9 percent. The joints shall be conditioned at a relative humidity of 40 ± 4 percent.

3/ Whenever a specimen fails at a load of less than 2,800 pounds per square inch and the failure occurs 50 percent or more in the wood, the specimen shall be disregarded in computing the average. In case the shearing strength of one or more specimens is 2,800 pounds per square inch or higher, the variation among individual specimens is 10 percent or more (based on the strongest joint) the test shall be run again, provided the average is less than the required 2,800 pounds per square inch.

4/ Except the specimen and jaw widths shall be the same as the width of the webbing and specimen shall be placed in machine under one pound initial load.

5/ The test shall be made on completely finished wood panels of the same wood used in production. The finish shall be in accordance with procedures used in producing furniture.

4.3.1.1.1 Toughness and adhesion test. The toughness and adhesion test shall be made by using Bell Laboratories Adhesion Tester, U. S. Testing Company, Model Number 1001, in accordance with instructions for using, as provided for by the manufacturer of the tester (see 6.4). The panel shall be marred both parallel and perpendicular to the grain. The resulting indentation shall show no whitening which is evidence of film separation and shall not crack in a brittle manner in or along the indentation.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

4.3.2 Intermediate inspection.

4.3.2.1 Visual examination of the intermediate product. The lot size shall be expressed in units of fabricated chairs prior to application of the upholstery cover. The inspection level for purposes of determining the sample size shall be level II of MIL-STD-105. The unit of product for these examinations shall be one fabricated chair prior to application of the upholstery cover. The defects found during the examinations shall be classified in accordance with Table VI. The acceptable quality level (AQL) shall be 15.0 for major defects and 40.0 for total defects (major and minor combined) per hundred units.

TABLE VI - Intermediate product defects

Examine	Defect	Classification Major	Minor
Framing members	Species of wood in any wood component not as specified	X	
	Decay over 1/4 square inch in area in any component	X	
	Decay up to and including 1/4 square inch in area in more than one component		X
	Bark pocket over 1 inch long		X
	Bark or wane over 1 square inch in area		X
	Split, shake, or check over 2 inches in length	X	
	Split, shake, or check up to and including 2 inches in length which may affect serviceability		X
	Loosened grain, torn grain or chip-out which may affect serviceability		X
	Area over 4 square inches not smoothly surfaced		X
	Honeycomb	X	
	Decayed or loose knot over 1 inch average diameter	X	
	Decayed or loose knot up to and including 1 inch average diameter		X
	Sound tight knot on edge of piece of wood or at a construction point.	X	
	Sound tight knot over 3/4 inch average diameter		X
	More than two sound tight knots in one piece of wood.		X
	Sapwood or mineral streak which may affect serviceability or strength		X
	More than two wormholes in component that will be unexposed after upholstery attachment		X
	Undesirable wood defect filled in with plastic wood or other filling compound.		X
	Plywood not of construction specified.	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE VI - Intermediate product defects (continued)

Examine	Defect	Classification Major	Minor
Workmanship of joinery	Wood component missing	X	
	Loose or unsound joint.	X	
	Evidence that glue at joint or block has not been applied where required.		X
	Frame not constructed as specified	X	
	Evidence that joint is not type specified	X	
	Frame out of square, i. e., sprung.	X	
	Two or more screws missing.	X	
	Screw missing where required.		X
	More than one screw loose or not driven in all the way		X
	Screw point protrudes from the wood surface		X
	Corner block or glue block not accurately fitted into place.		X
	Wood member improperly positioned or not positioned as specified.	X	
	Wood member warped, cupped, or twisted out of specified shape.	X	
	Shape or contour of wood member not as specified.	X	
	Wood not full length piece where required		X
	Diameter of dowel less than specified by more than 1/6 inch	X	
	Component not dimensions specified (including tolerance)	X	
Construction and Workmanship of Platform	Webbing strips not number specified	X	
	Webbing strips not interwoven as specified		X
	Webbing strips not tensioned as specified		X
	Webbing strips not stapled to seat frame as specified.	X	
	Webbing strips not equally spaced.	X	
Foam Rubber Cushion			
Workmanship	Internal voids perceptible to sight or touch through uncut surfaces.	X	
	Presence of unrepaired surface voids 1/8 inch or greater in depth and 1/2 inch or larger in width on top or bottom.	X	
Cut edges to be banded	Unrepaired voids greater than one inch in width and 1/2 inch in depth on cut edges (to be banded)	X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE VI - Intermediate products defects (continued)

Examine	Defects	Classification Major	Minor
Foam Rubber Cushion (cont)			
Vertical surfaces (not banded)	Unrepaired exposed voids greater than one inch in width and exceeding 1/4 inch in depth	X	
Horizontal cut surfaces	Unrepaired voids greater than 3/4 inch in width and more than 1/8 inch in depth or greater than 1/2 inch in width and more than 1/4 inch in depth.	X	
Upholstery fabric	Color of material not as specified	X	
	Torn, cut, or contains hole	X	
	Misweave, i.e., multiple float or other fabric damage affecting serviceability.	X	
	Spotted, stained or dirty.		X
	Shade variations or faded, affecting appearance	X	
	Material has objectionable order		X
Construction and Workmanship of Upholstery	Material pieced where a continuous piece of material is required.	X	
	Seam open up to and including 2 inches in length		X
	Seam open over 2 inches in length	X	
	Seam uneven or not neatly accomplished affecting appearance.		X
	Seam in wrong location.		X
	Needle chews		X
	Skipped stitches or runoffs		X
	Raw edge noticeable at seam		X
	Welt missing where required	X	
	Color of thread does not match color of upholstery material.		X

4.3.3 End item inspection.

4.3.3.1 Visual examination of the end item. The lot size shall be expressed in units of completed chairs. The inspection level for purposes of determining the sample size shall be level I of MIL-STD-105. The unit product shall be one completed chair. The defects found during the examinations shall be classified in accordance with Table VII. The acceptable quality level (AQL) shall be 10.0 for major defects and 25.0 for total defects (major and minor combined) per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE VII - End item defects

Examine	Defect	Classification Major	Minor
Construction and Workmanship of all Chairs	General design or styling not as specified or not as on approved preproduction sample.	X	
	Contour of seat or back not in accordance with figure and not as specified.	X	
	Component missing	X	
	Cambric not applied with glazed side exposed		X
	Tucking of material at corner or fold not neatly accomplished affecting appearance		X
	Cover wrinkled or puckered at seam to an extent adversely affecting appearance		X
	Cambric not neatly attached.		X
	Furrow, lump or bulge affecting appearance		X
	Component in wrong location		X
	Component not size and shape specified	X	
	Component not assembled as specified	X	
	Component out of alignment or out of square affecting serviceability	X	
	Component loose or insecurely fastened where rigidity is required.	X	
	Poor fit of component part or to its mating part		X
	Welt loose along edges affecting serviceability		X
	Welt not straight		X
	Any tack or other protuberance that can be felt through the upholstery.		X
	Evidence of filler voids		X
	Height of cushion boxing not as specified		X
Construction and Workmanship of metal parts	Weld or braze missing where required	X	
	Weld or braze broken, not fused or burned through	X	
	Weld or braze incomplete where continuity is required or undercut.	X	
	Flush or spatter not removed	X	
	Weld or braze not ground smooth or not neatly accomplished	X	
	Contains hole where not required, does not have one where required		X

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

TABLE VII - End item defects (continued)

Examine	Defect	Classification Major	Minor
Construction and Workmanship of metal parts	More than one screw missing	X	
	Screw or bolts broken off		X
	Fin, burr or sharp edge	X	
	Finish not satin chrome	X	
	Finish not uniform		X
	Legs uneven (end item rocks more than 1/16 inch on flat surface).	X	
	Shape or angle of leg or tubular frame member not as specified.	X	
	Glide missing (Class A chairs)		X
	Glide not type or material specified. (Class A chairs)		X
	Glide wrong size (Class A chairs)		X
	Casters not as specified	X	

4.3.3.2 Overall examination. Each chair offered for shipment shall be inspected at a viewing distance of 6 feet. The chair shall be rejected if one or more of the following defects are found:

Wood finish not uniform

Scratch or bruise marks on wood.

Poor fit of upholstery as evidenced by wrinkles (other than comfort type in seat) at sides and corners.

Welts not straight.

Armrest position improper.

Metal finish not uniform.

Piece over 1/4 inch off level.

Metal frame not true.

Apparent imperfections of metal joinery.

If three or more chairs exhibit any of these defects, the visual examination under 4.3.3.1 shall be repeated.

4.3.4 Dimensional examination. The lot size shall be expressed in units of chairs. The inspection level shall be S-2 of MIL-STD-105. The unit of product shall be one chair. Any external overall dimensions that are not within the specified tolerance shall be classified as a defect. The acceptable quality level (AQL) shall be 4.0 defects per hundred units.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

5. PREPARATION FOR DELIVERY

5.1 Packaging. Furniture units shall be packaged in accordance with Level A, Level B, or Level C, as specified in the contract or order (see 6.2).

5.1.1 Level A. Furniture units shall be packaged as specified in the invitation for bids.

5.1.2 Level B. Furniture units shall be packaged as specified in the invitation for bids.

5.1.3 Level C. Furniture units shall be packaged in accordance with the manufacturer's commercial practice.

5.2 Packing. Furniture units, packaged Level A, B, or C, shall be packed for Level A, B, or C, as specified in the invitation for bids (see 6.2).

5.2.1 Levels A and B. Furniture units shall be packed as specified in the invitation for bids.

5.2.2 Level C. Furniture units shall be packed in containers of the type, size and kind commonly used for the purpose, in a manner that will insure acceptance by common carrier and safe delivery at destination. Shipping containers shall comply with the Uniform Freight Classification Rules or regulations of other carriers as applicable to the mode of transportation.

5.3 Marking.

5.3.1 Civil agencies. In addition to any special marking required by the contract or purchase order, marking of shipping containers shall be in accordance with Federal Standard No. 123.

5.3.2 Military agencies. In addition to any special marking required by the contract or purchase order, marking of shipping containers shall be in accordance with MIL-STD-129.

6. NOTES

6.1 Intended use. The combination metal and wood executive units covered by this specification are designed for use in executive offices of the Federal Government and are correlated with other furniture items within the group. The following Interim Federal Specifications cover the other items:

AA-0-00151 - Office Furniture: Cabinet, Telephone, Executive, Metal and Wood.
AA-0-00215 - Office Furniture: Executive, Combination Metal and Wood, Davenport, Chair, Easy.
AA-0-00219 - Office Furniture: Credenza, Executive, Metal and Wood.
AA-0-00220 - Office Furniture: Desks, Desk Attachments, Executive, Metal and Wood.
AA-0-00222 - Office Furniture: Bookcase, Executive, Metal and Wood.
AA-0-00225 - Office Furniture, Executive, Combination Metal and Wood, Settee, Sectional Units (Without Arms).
AA-0-00245 - Office Furniture: Tables, Executive, Metal and Wood.

6.2 Ordering data. Purchasers should select the preferred options permitted herein and include the following information in procurement documents:

(a) Title, number, and date of this specification.
(b) Type, style, and class required if applicable (see 1.2.1).
(c) When preproduction samples not required (see 3.1).
(d) Color of leather upholstery when applicable (see 3.2.12.1).
(e) Color of artificial leather upholstery when applicable (see 3.2.12.2).
(f) Color of fabric upholstery when applicable (see 3.2.12.3).
(g) Upholstery cover required (see 3.3.12).
(h) Selection of applicable level of packaging and packing required (see 5.1 and 5.2).
(i) Marking requirements (see 5.3).

6.3 Standard sample. Sample panels of the standard color for the walnut finish are obtainable, without charge, from the Business Service Center, Regional Office Building, Federal Supply Service, General Services Administration, Washington, D. C. 20407, or from the Business Service Center of the nearest GSA Regional Office.

6.4 Information with respect to Bell Laboratories Adhesion Tester, U. S. Testing Company, Model No. 1001, may be obtained from U. S. Testing Company, Inc. 1415 Park Avenue, Hoboken, New Jersey.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

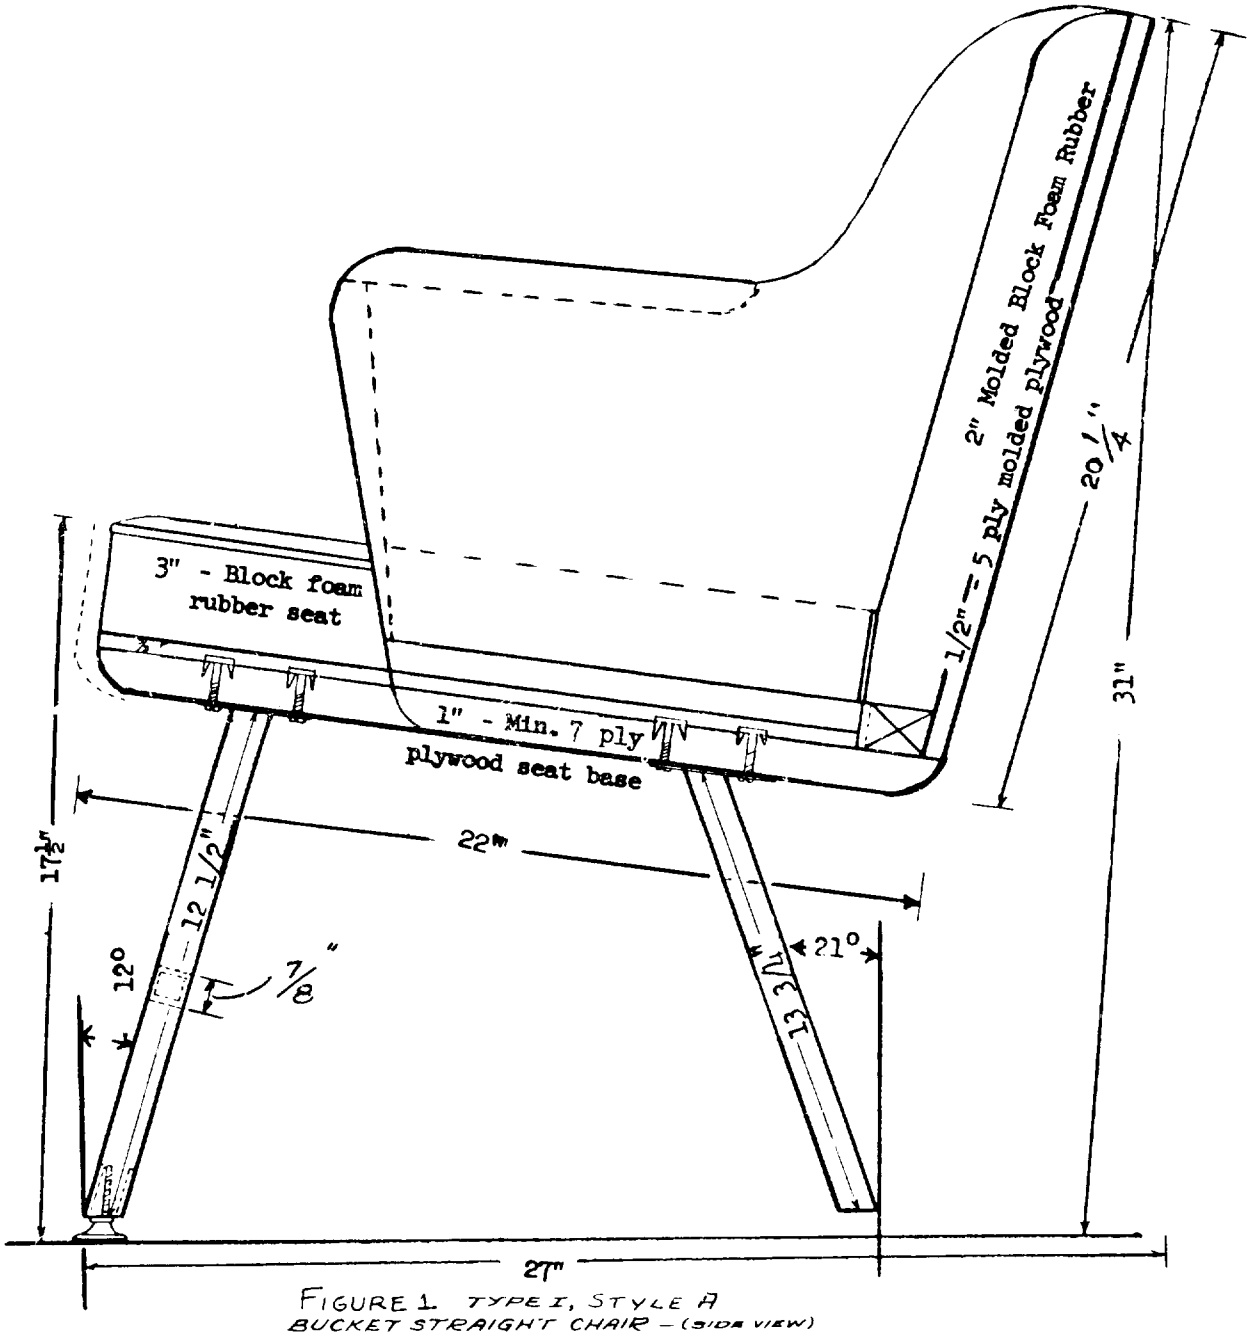


FIGURE 1. TYPE I, STYLE A
BUCKET STRAIGHT CHAIR – (SIDE VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

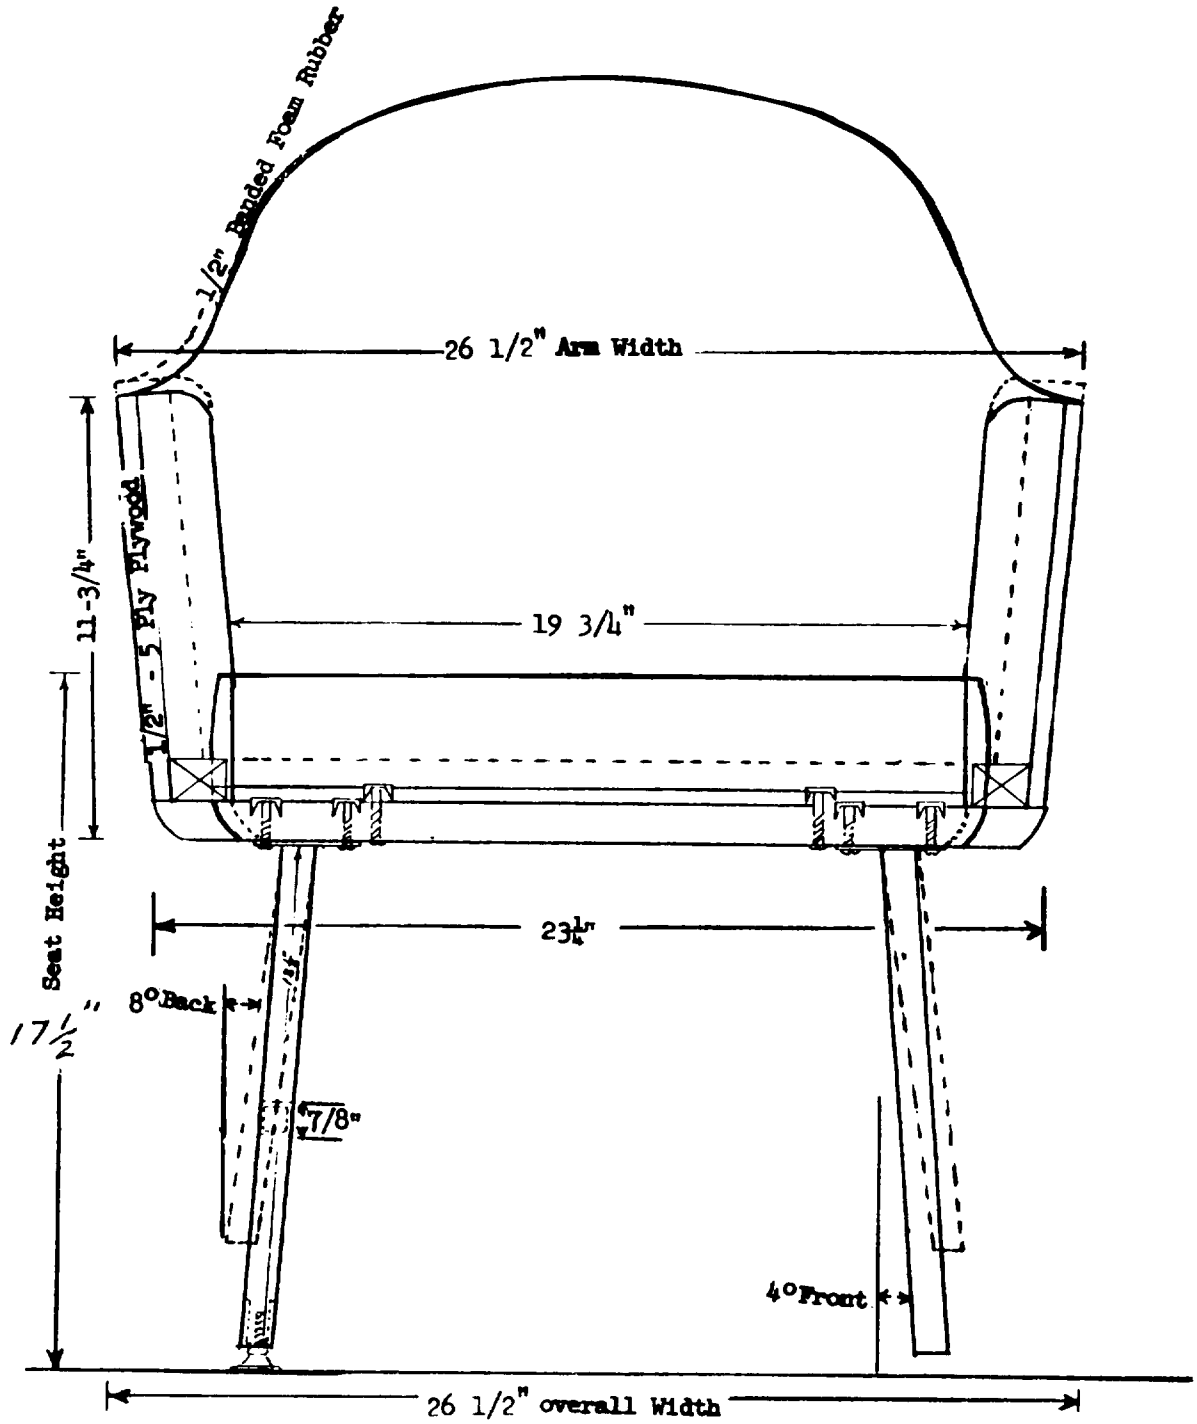


FIGURE 2 TYPE I, STYLE 1
BUCKET STRAIGHT CHAIR — (FRONT VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

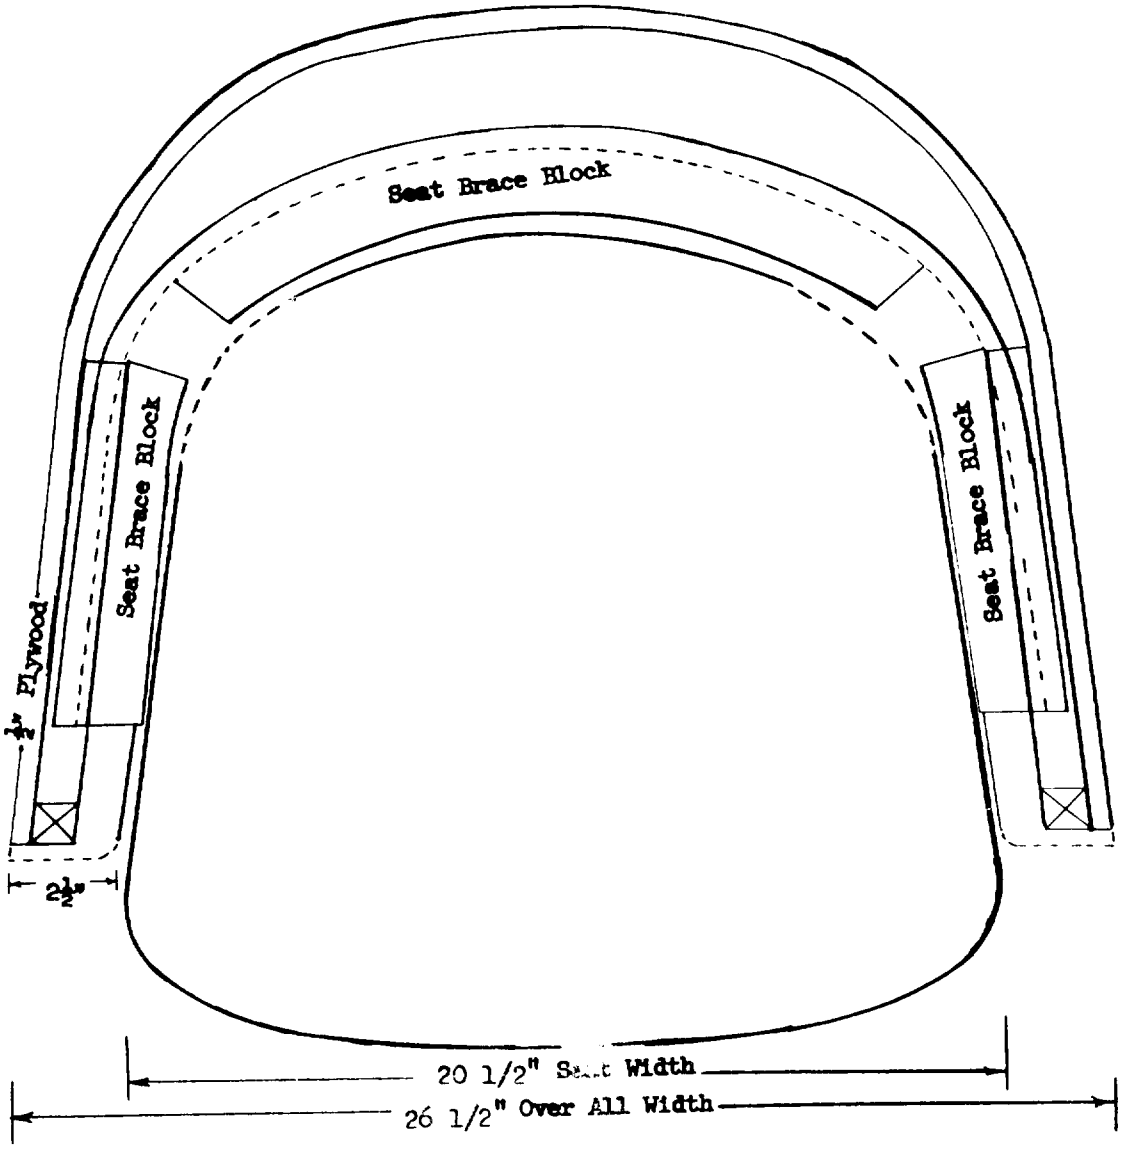


FIGURE 3 TYPE I, BUCKET CHAIR – (PLAN VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

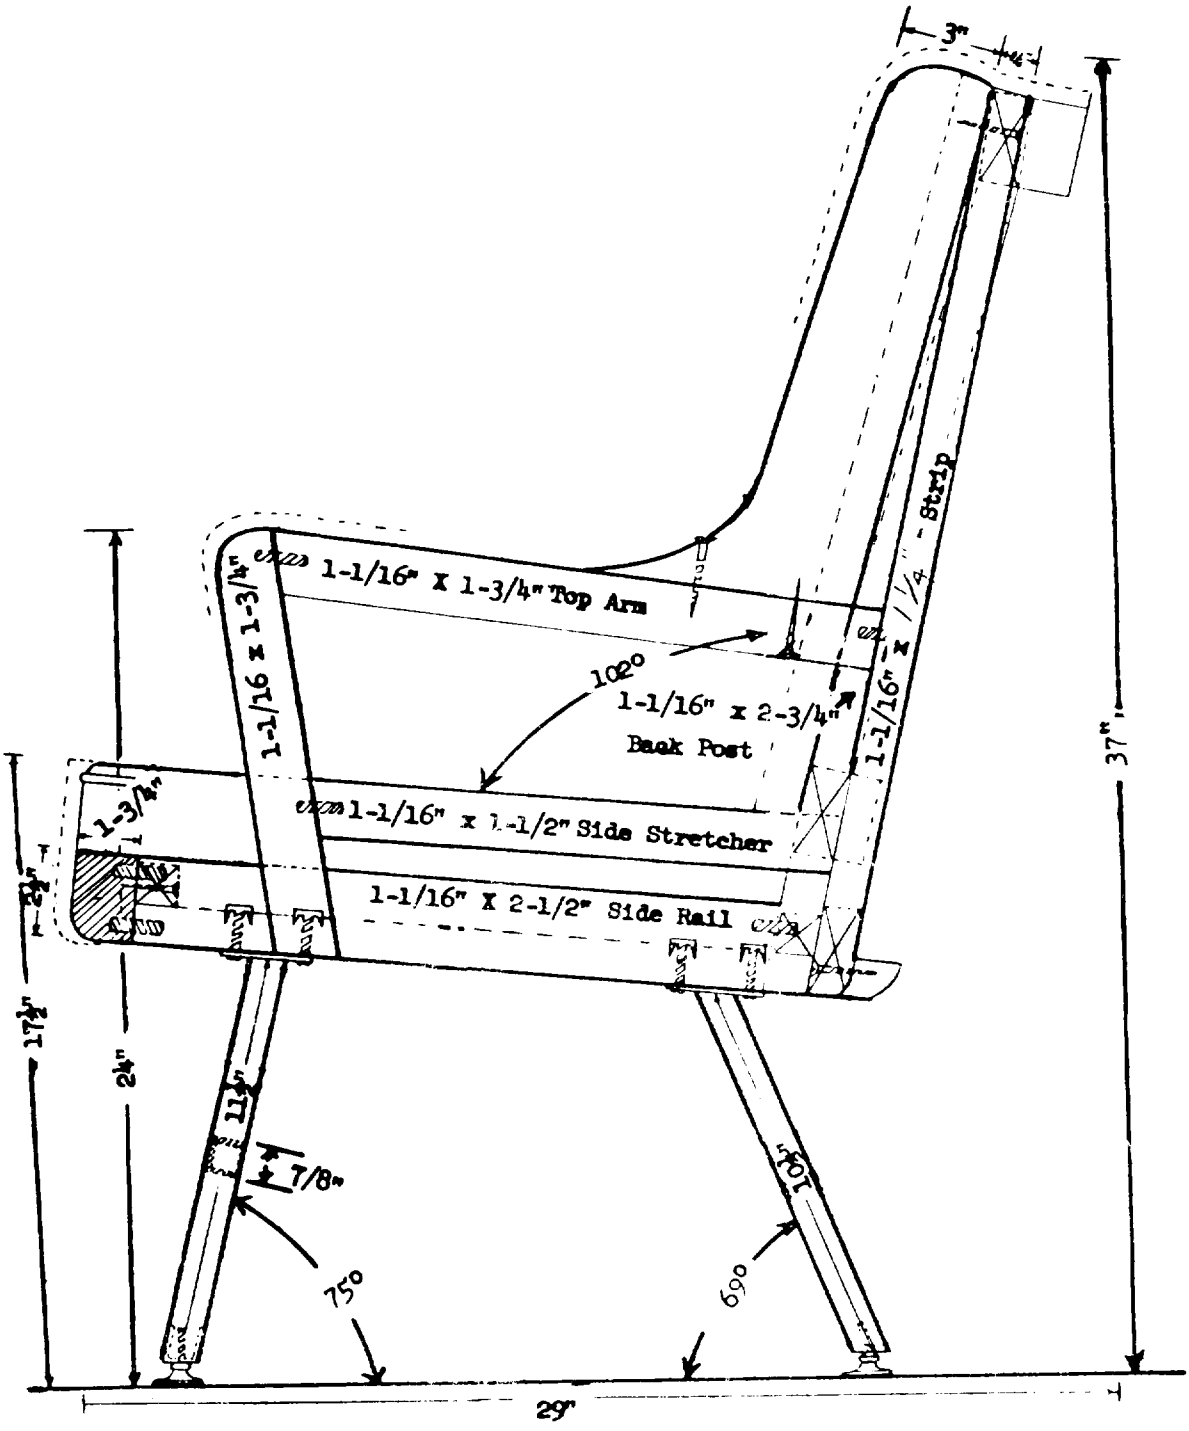


FIGURE 4. TYPE II, STYLE A
HIGH BACK STRAIGHT CHAIR - (SIDE VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

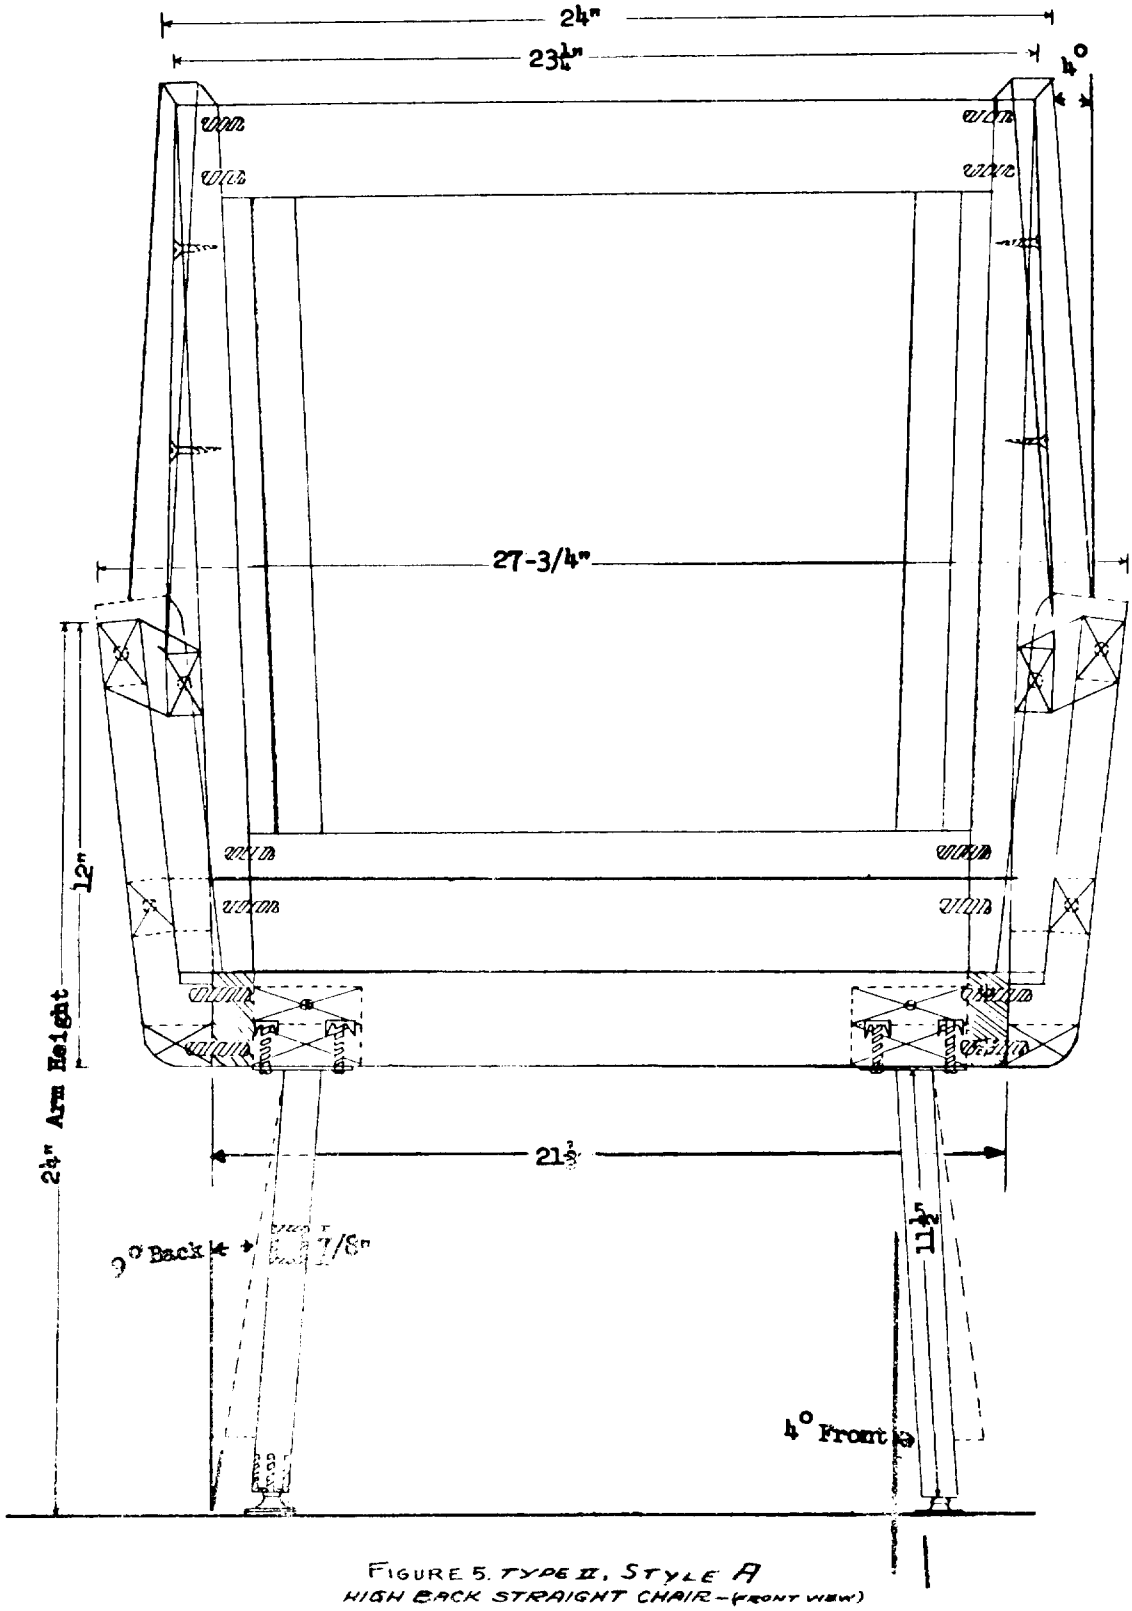


FIGURE 5. TYPE II, STYLE A
HIGH BACK STRAIGHT CHAIR - (FRONT VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

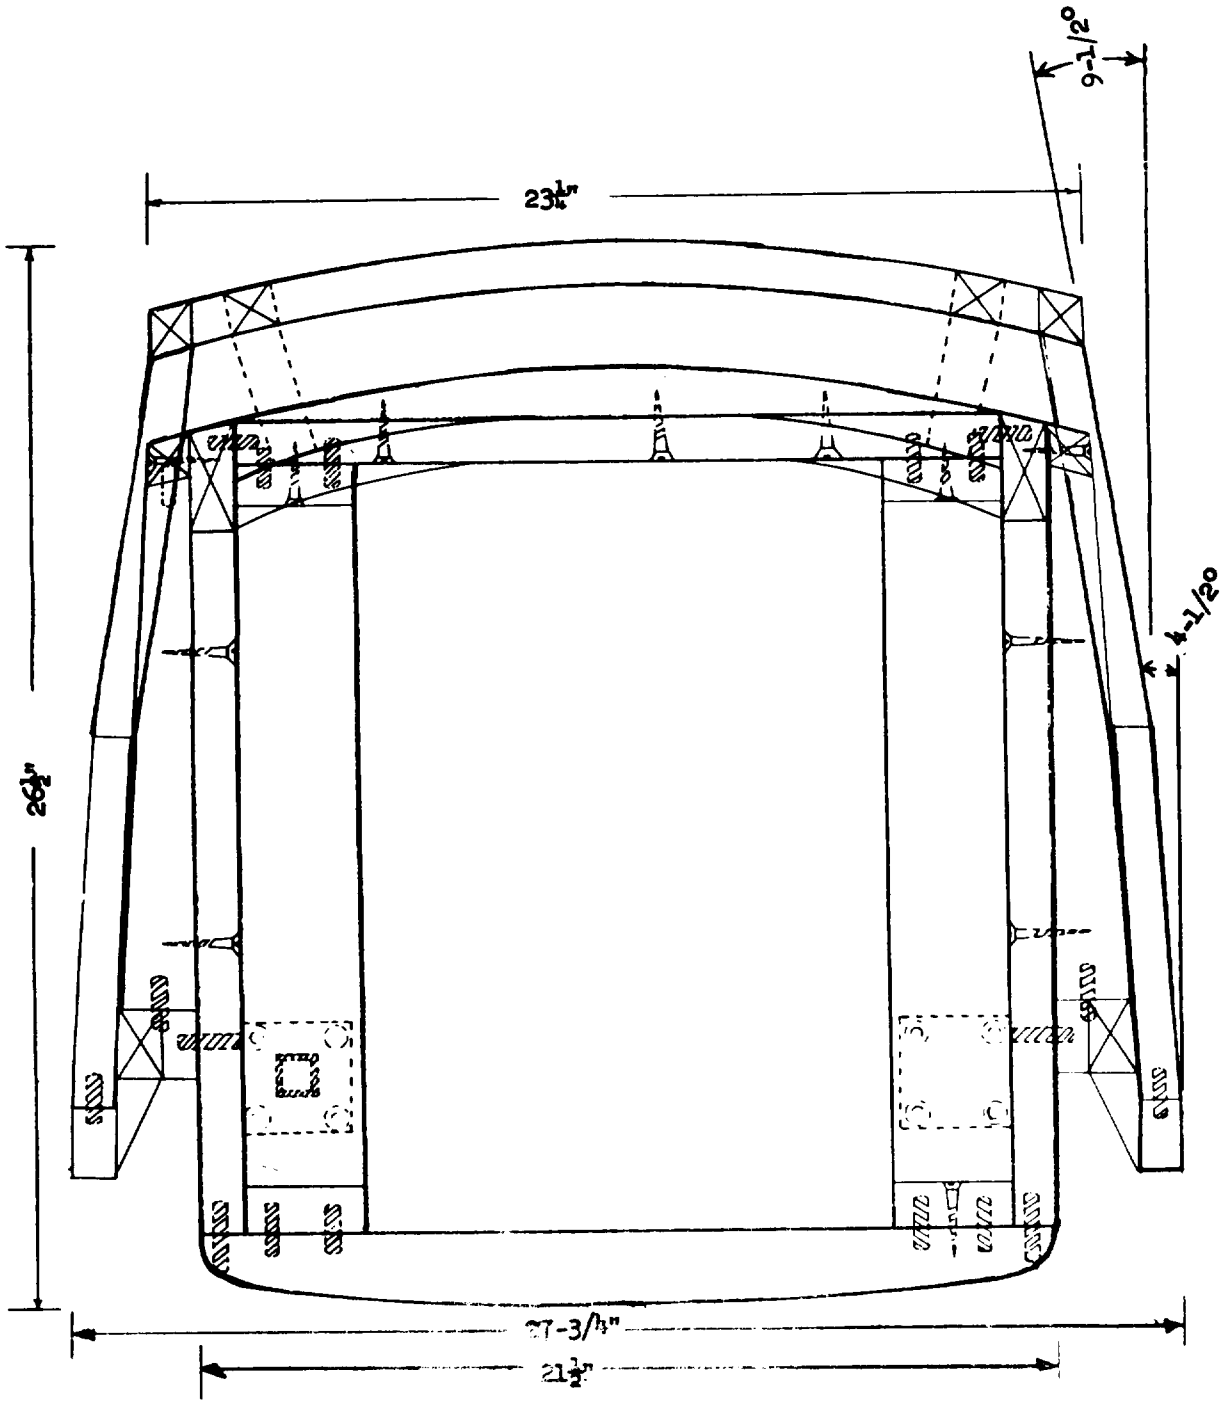


FIGURE 6. TYPE II, STYLE A
HIGH BACK STRAIGHT CHAIR - (PLAN VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

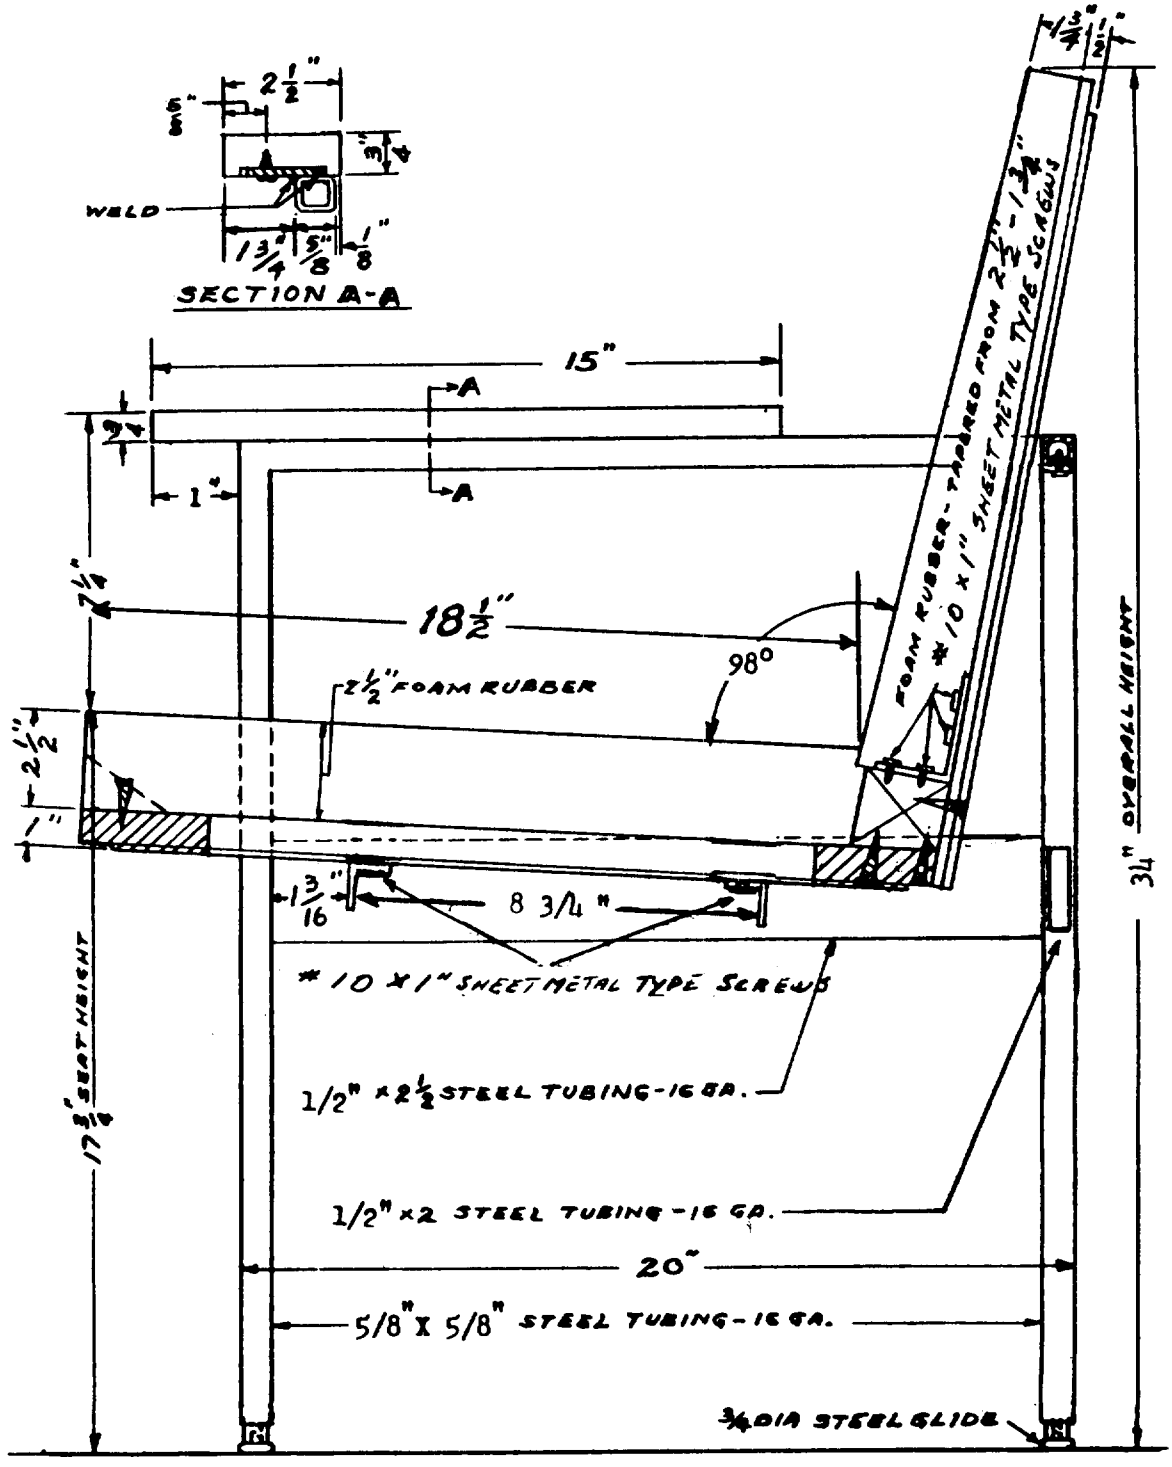


FIGURE 7. TYPE III, STYLE A
SQUARE STRAIGHT CHAIR (SIDE VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

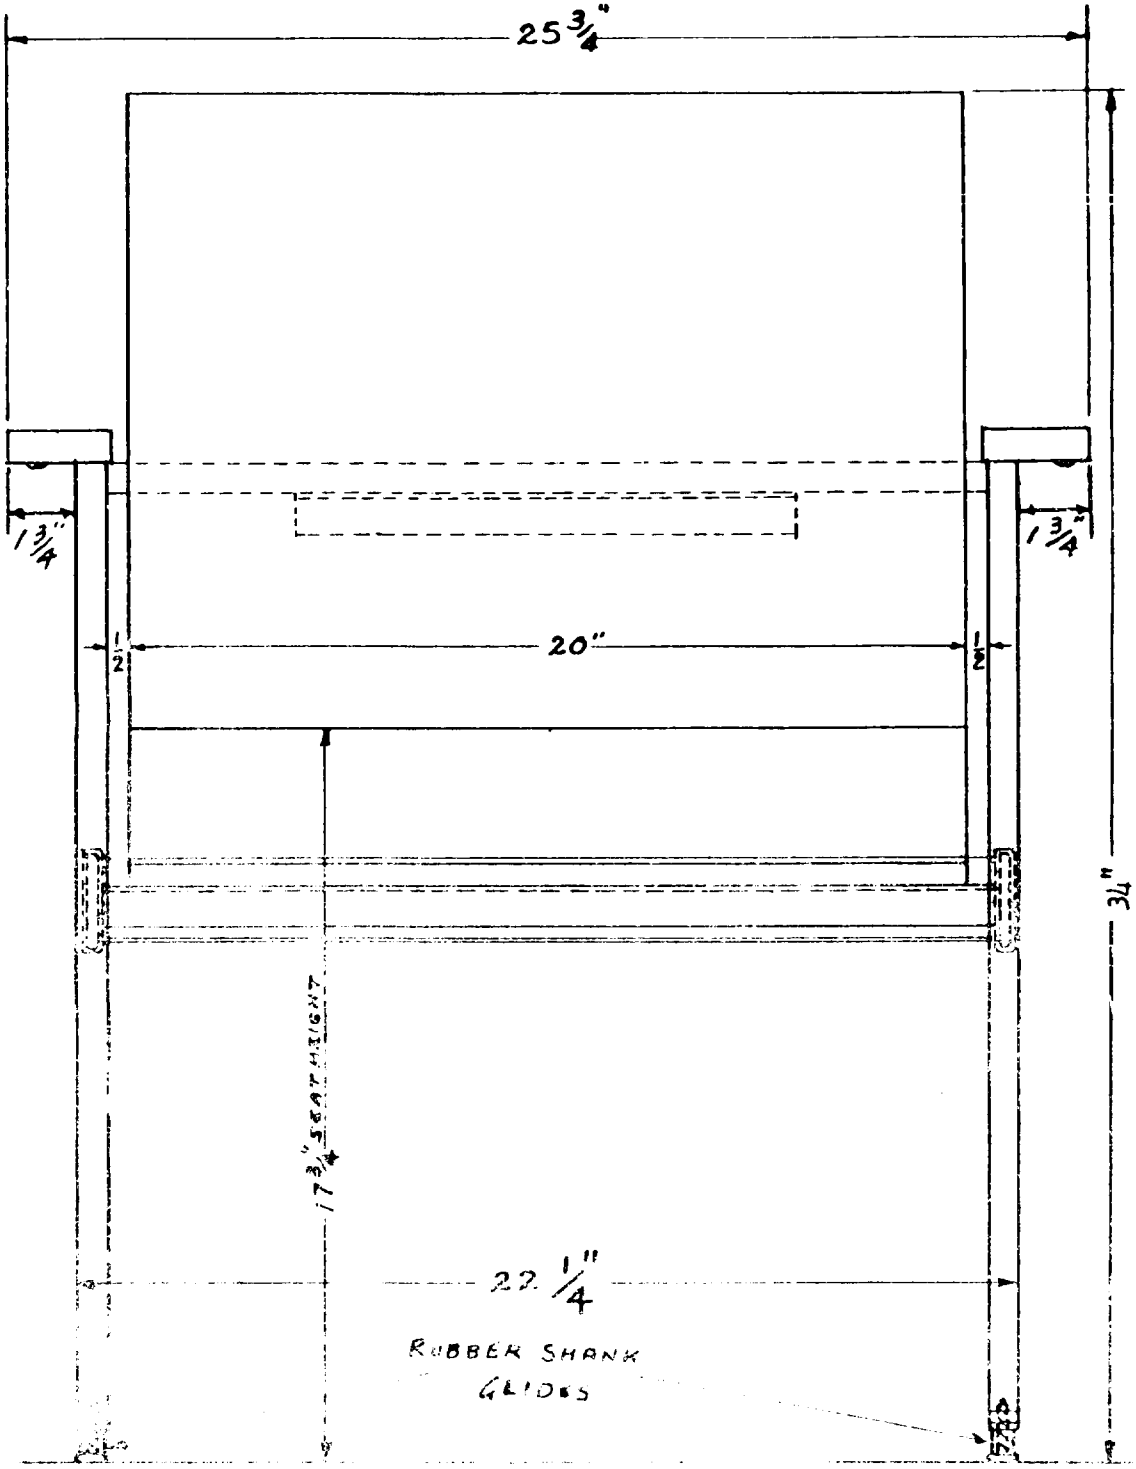


FIGURE 8. TYPE II, STYLE A
SQUARE STRAIGHT CHAIR -- (FRONT VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

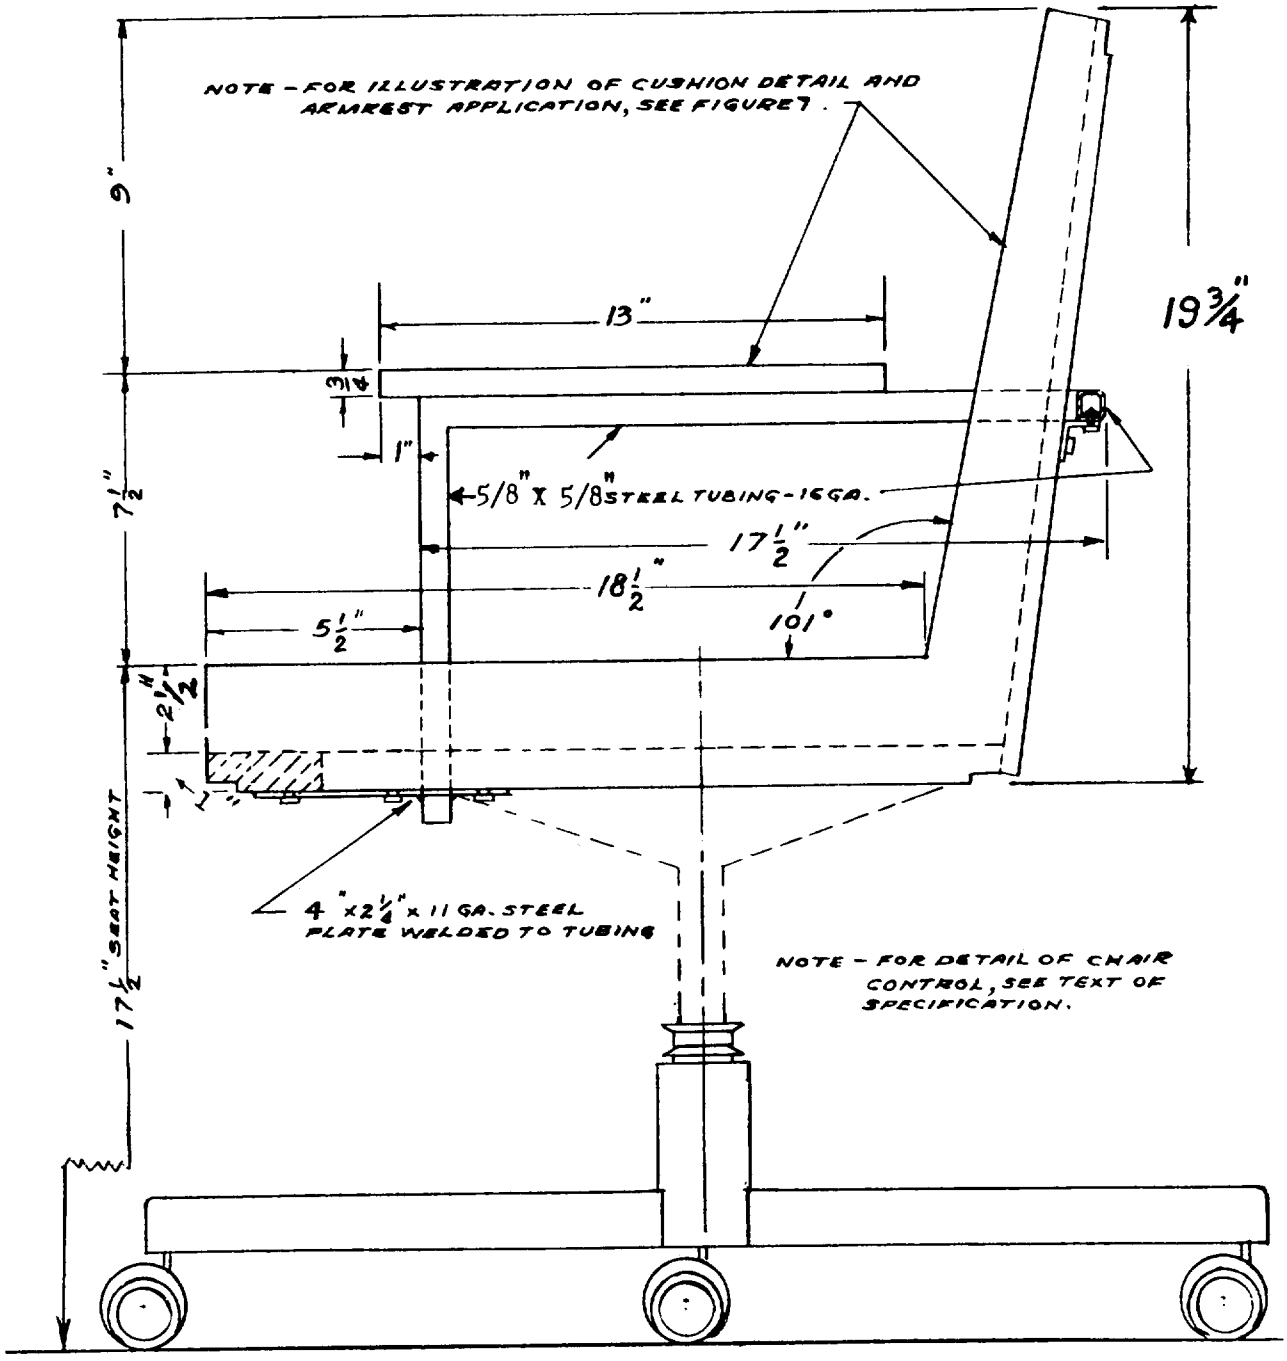


FIGURE 9. TYPE III, STYLE B SQUARE ROTARY CHAIR — (SIDE VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

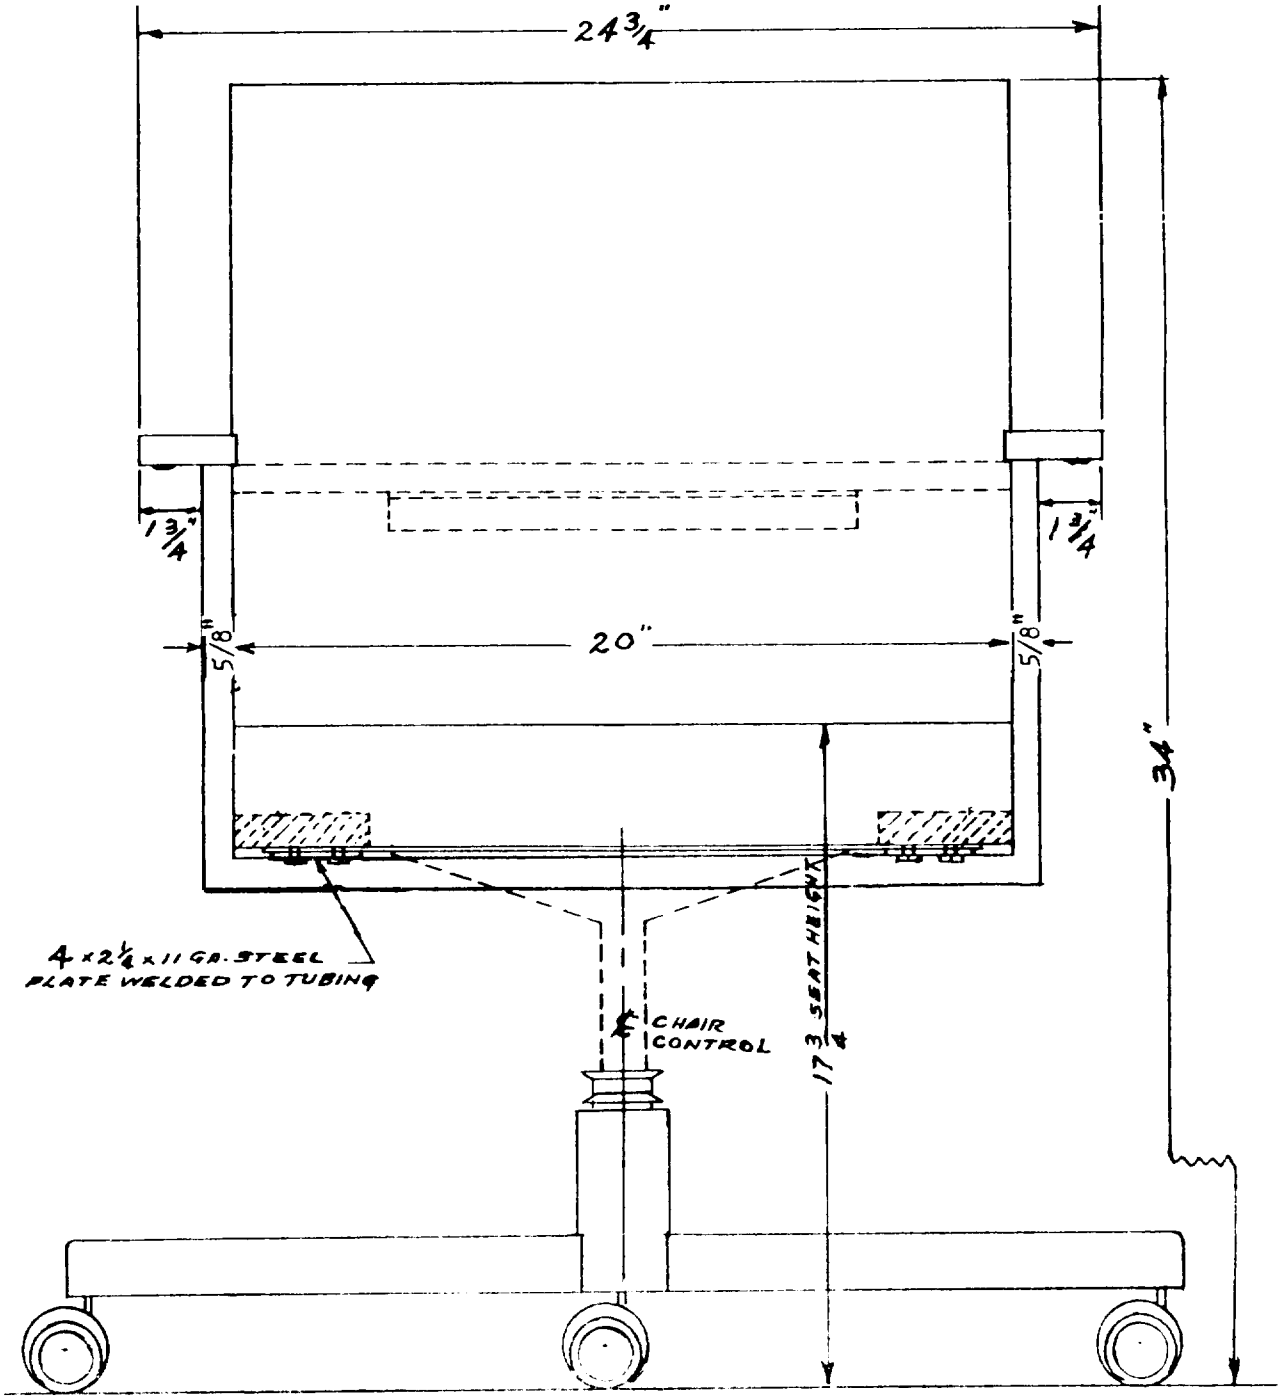


FIGURE 10. TYPE III, STYLE B
SQUARE ROTARY CHAIR — (FRONT VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

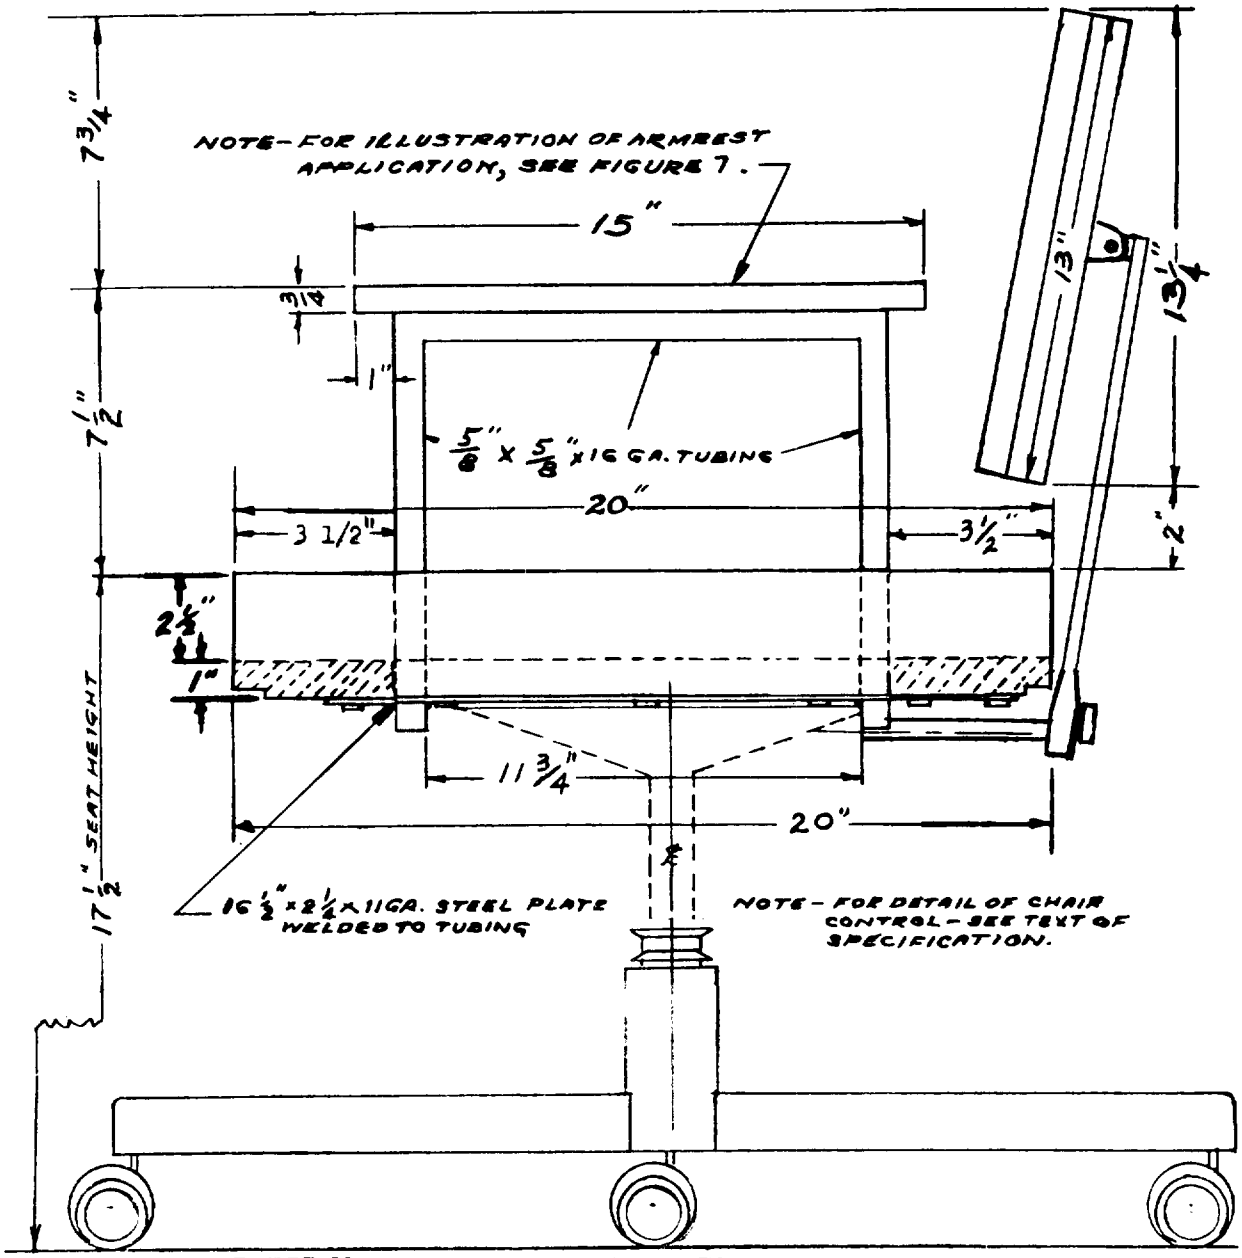


FIGURE 11 TYPE IV

EXECUTIVE POSTURE CHAIR — (SIDE VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

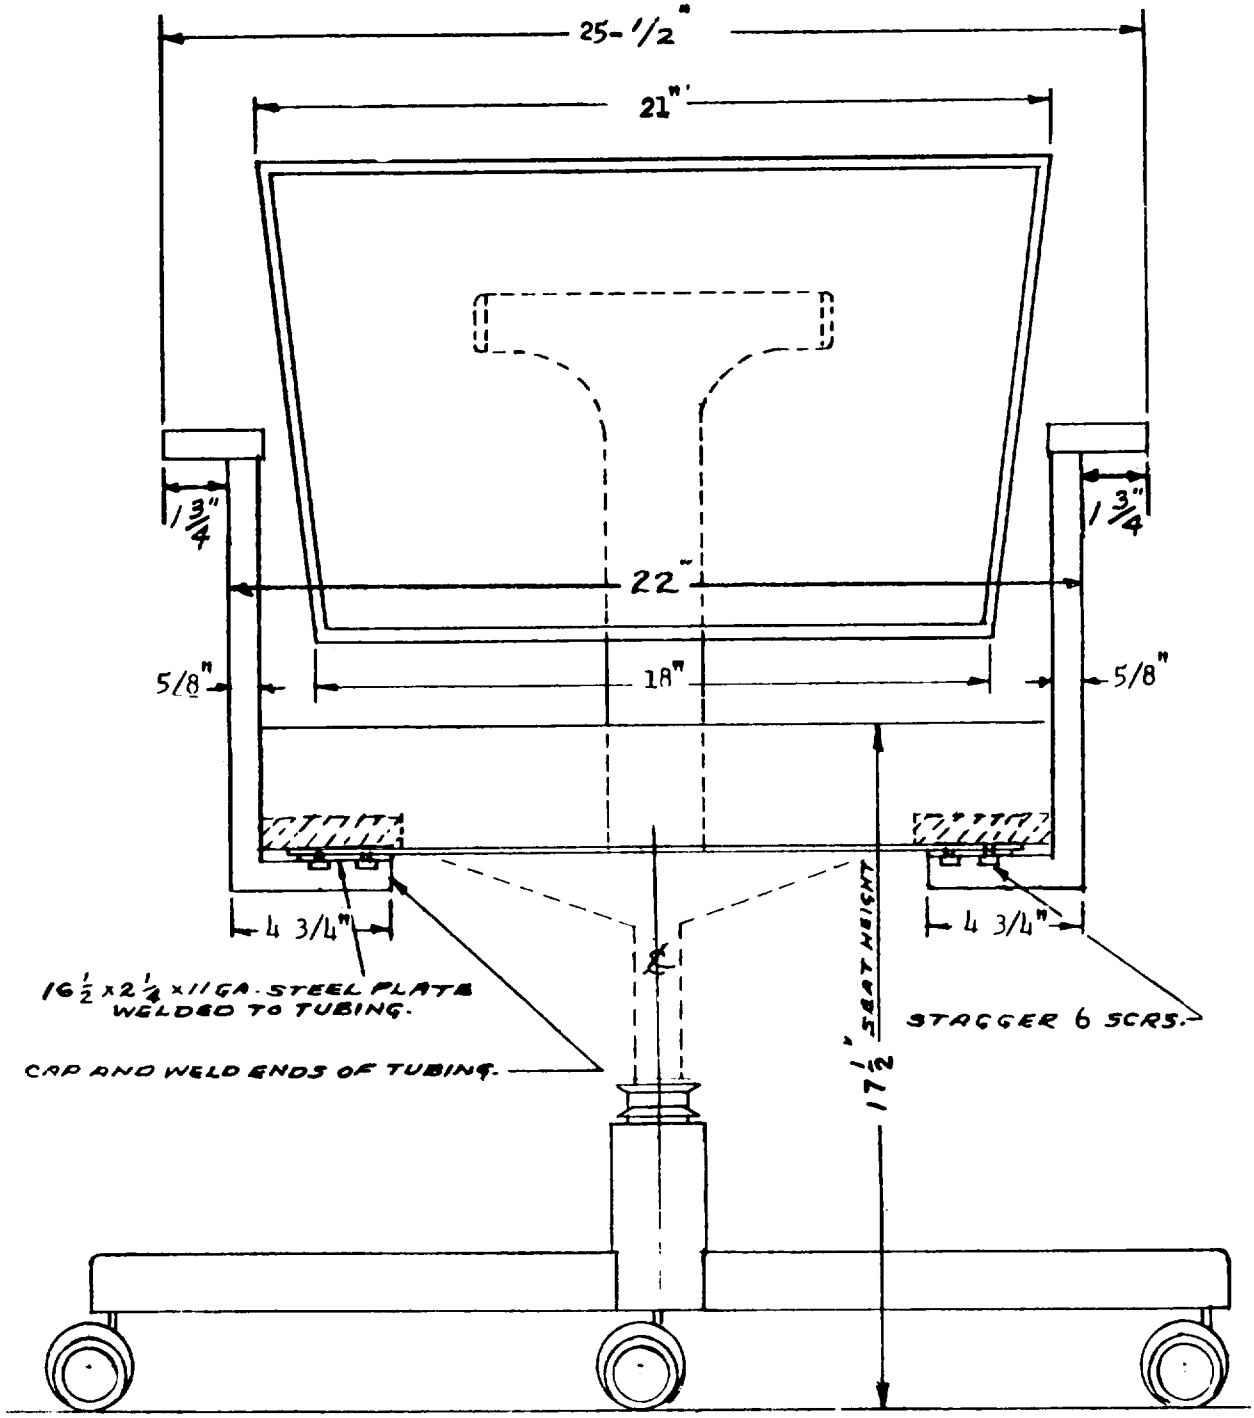


FIGURE 12 . TYPE IV.

EXECUTIVE POSTURE CHAIR — (FRONT VIEW)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

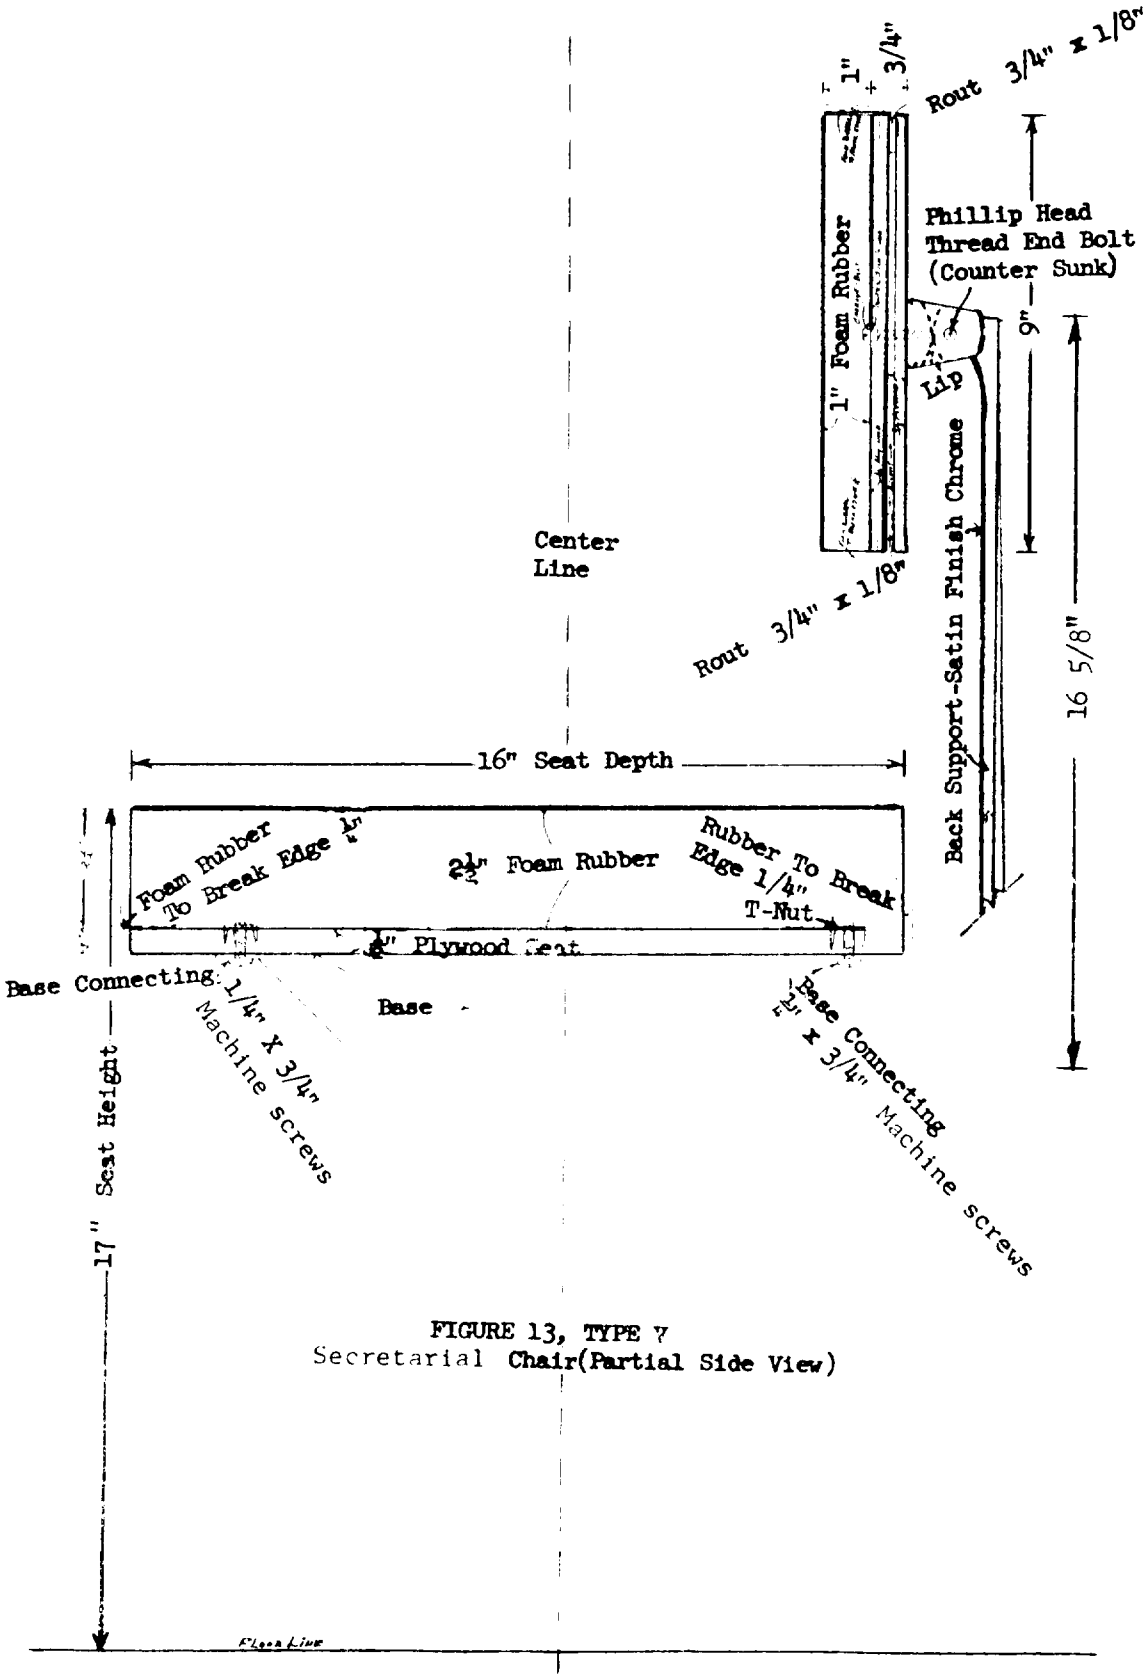


FIGURE 13, TYPE V
Secretarial Chair(Partial Side View)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

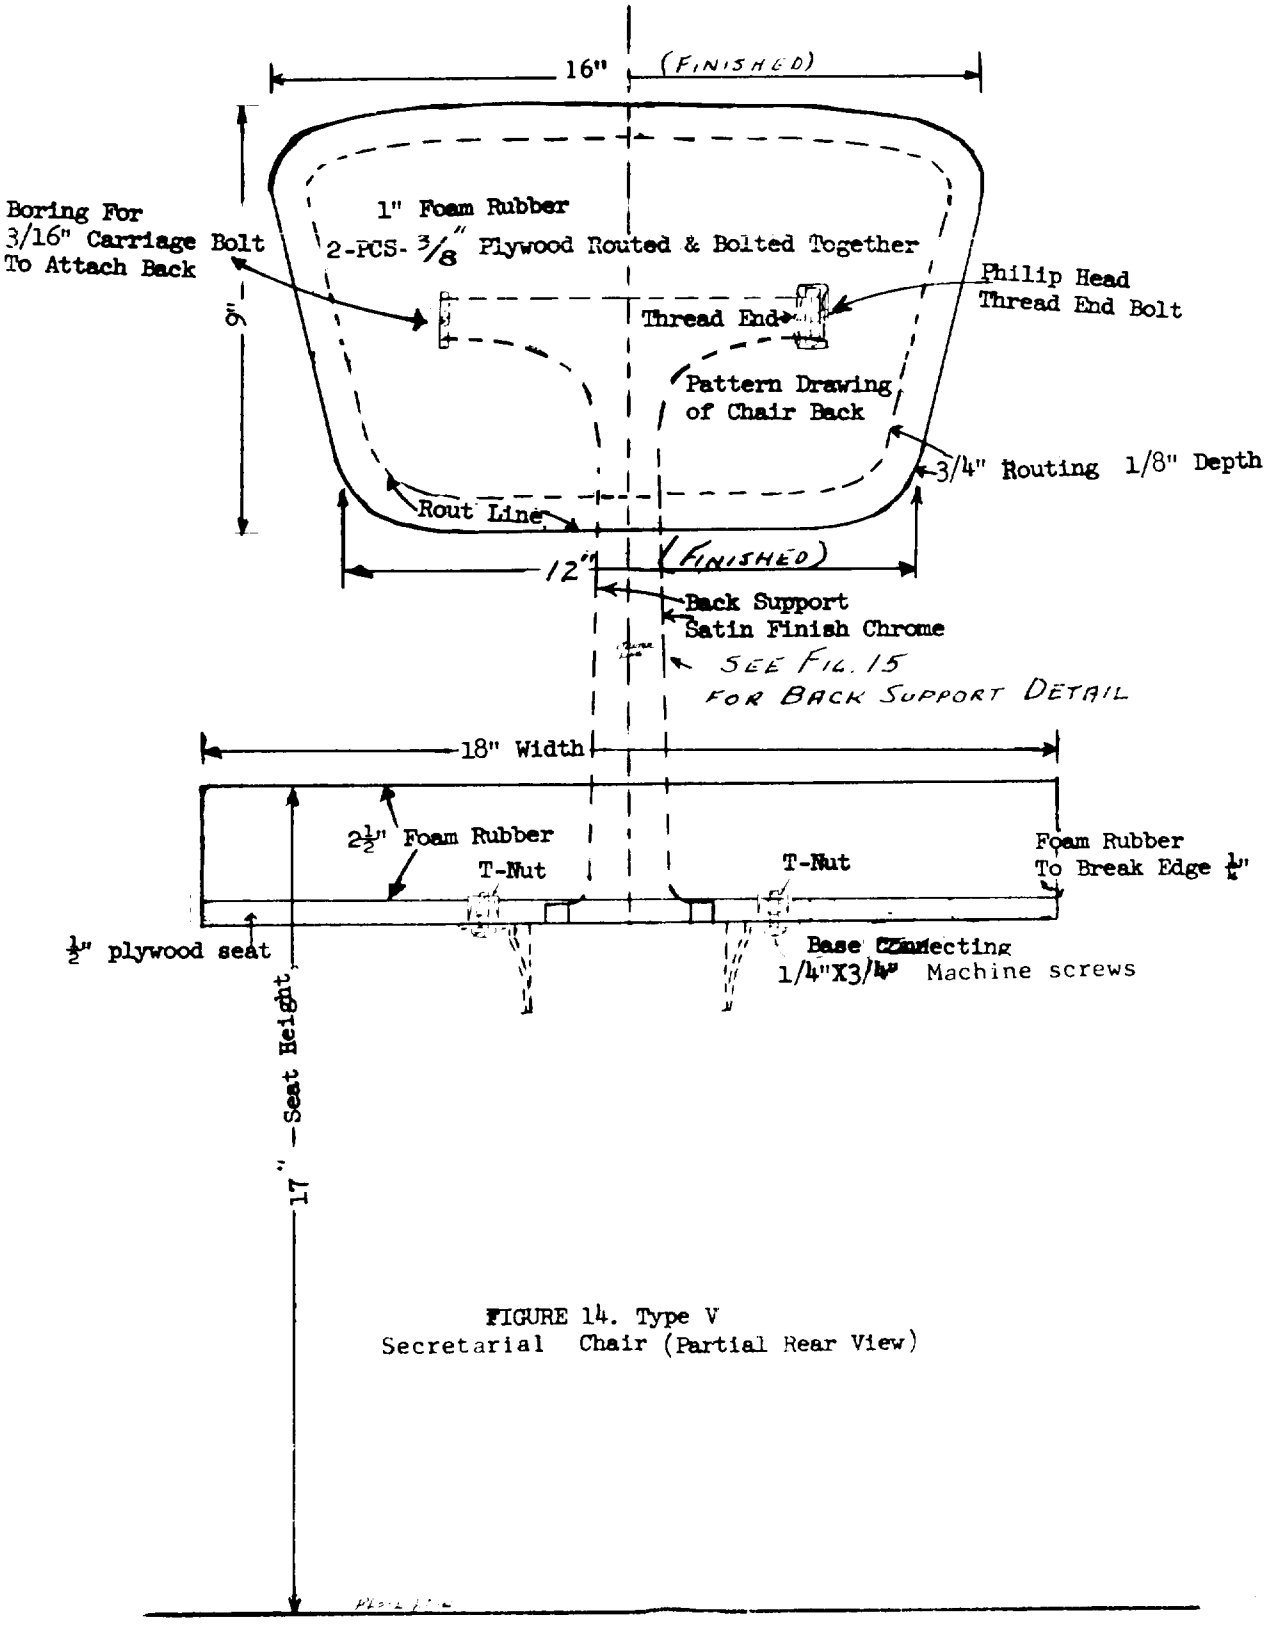


FIGURE 14. Type V
Secretarial Chair (Partial Rear View)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

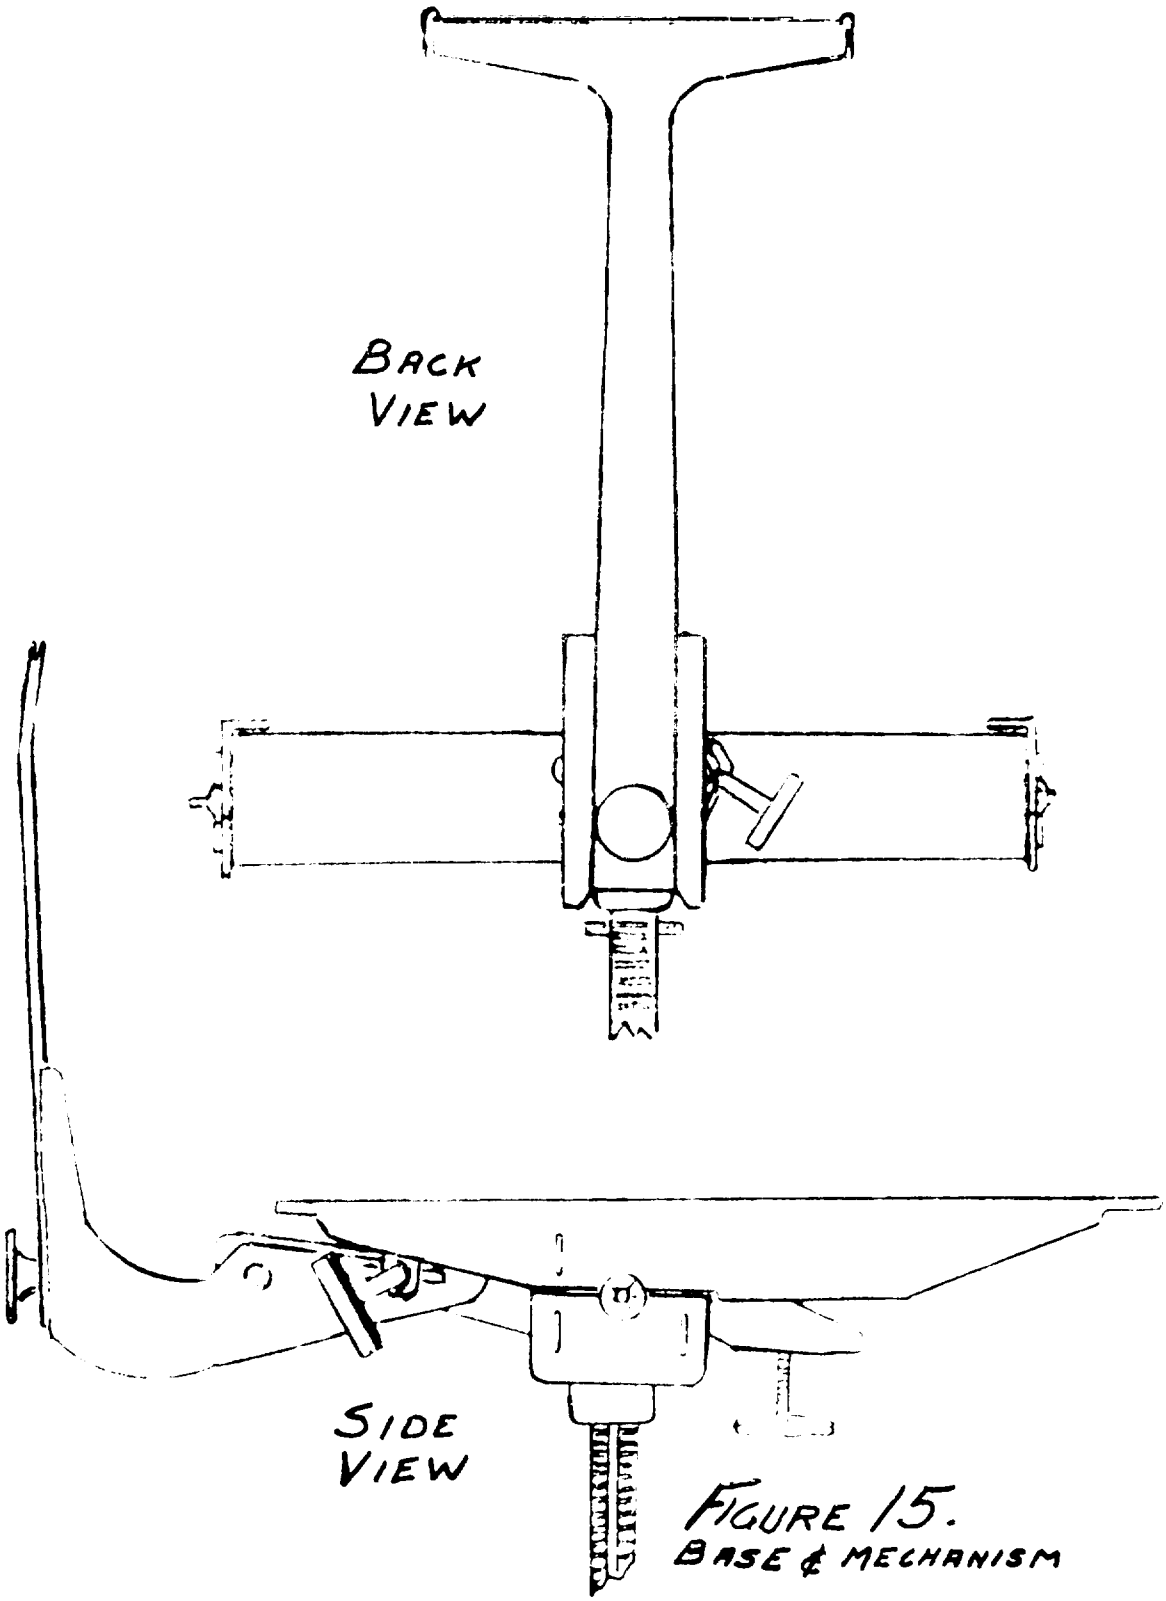


FIGURE 15.
BASE & MECHANISM

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

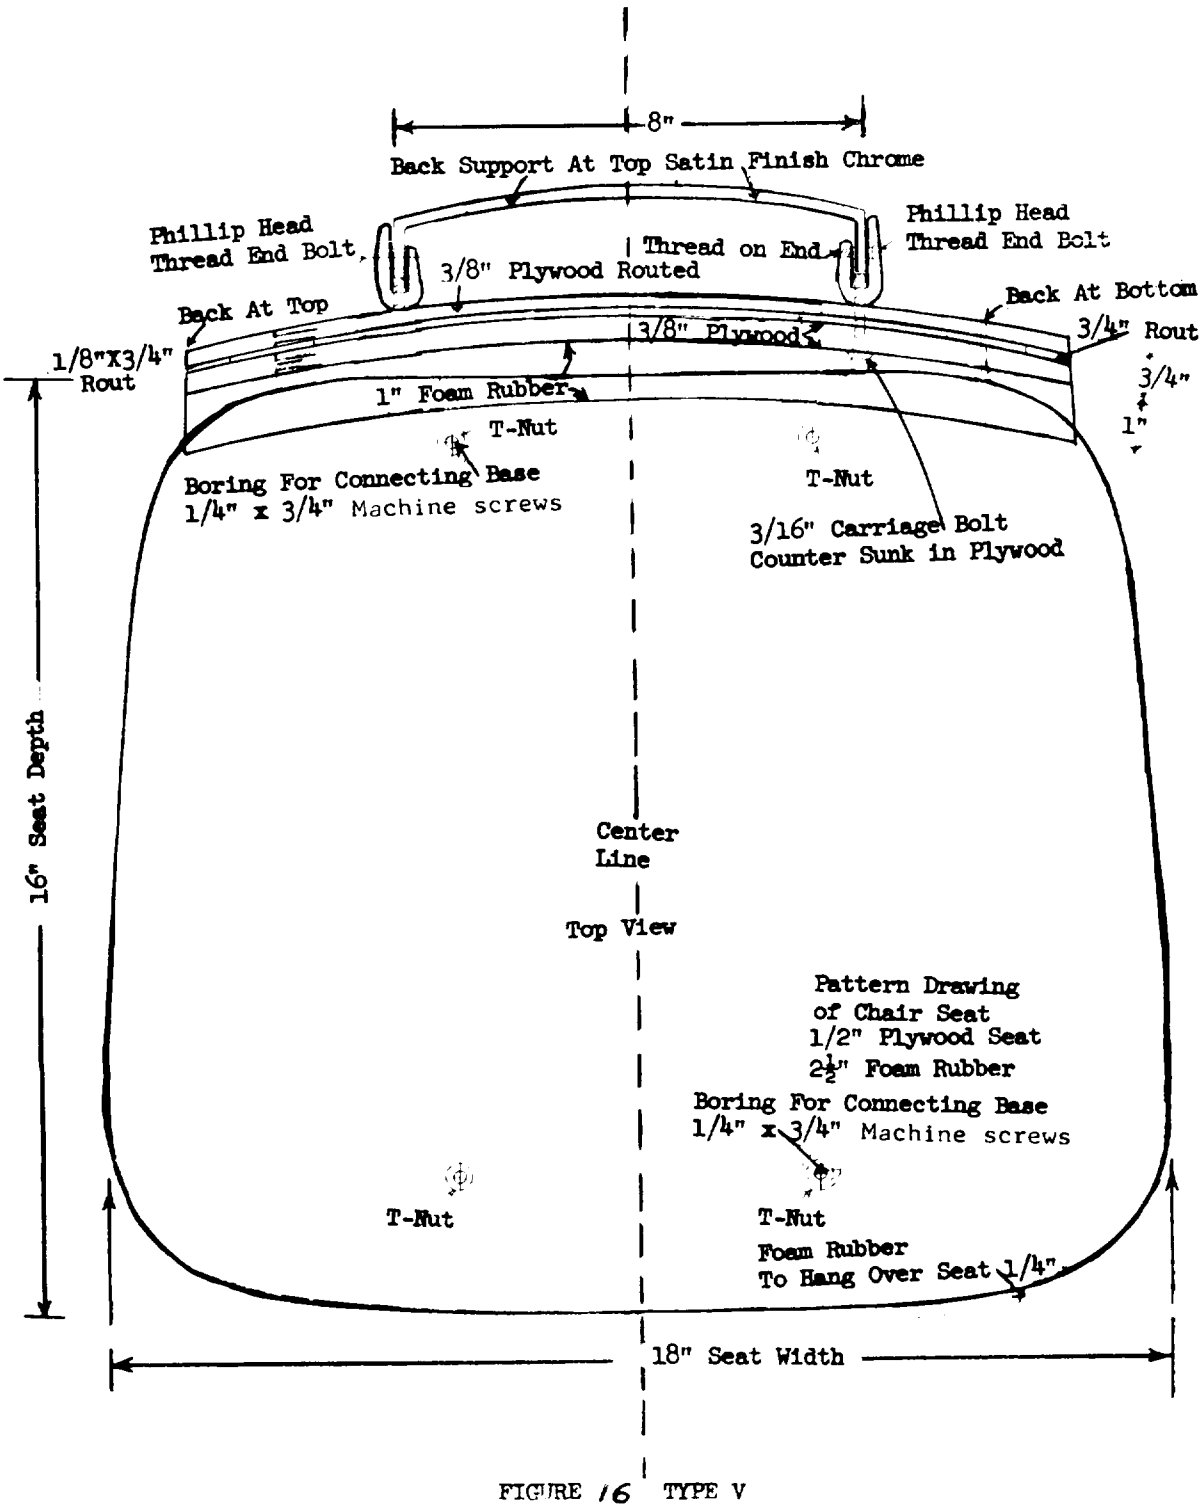


FIGURE 16 TYPE V
Secretarial Chair-(Plan view)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.


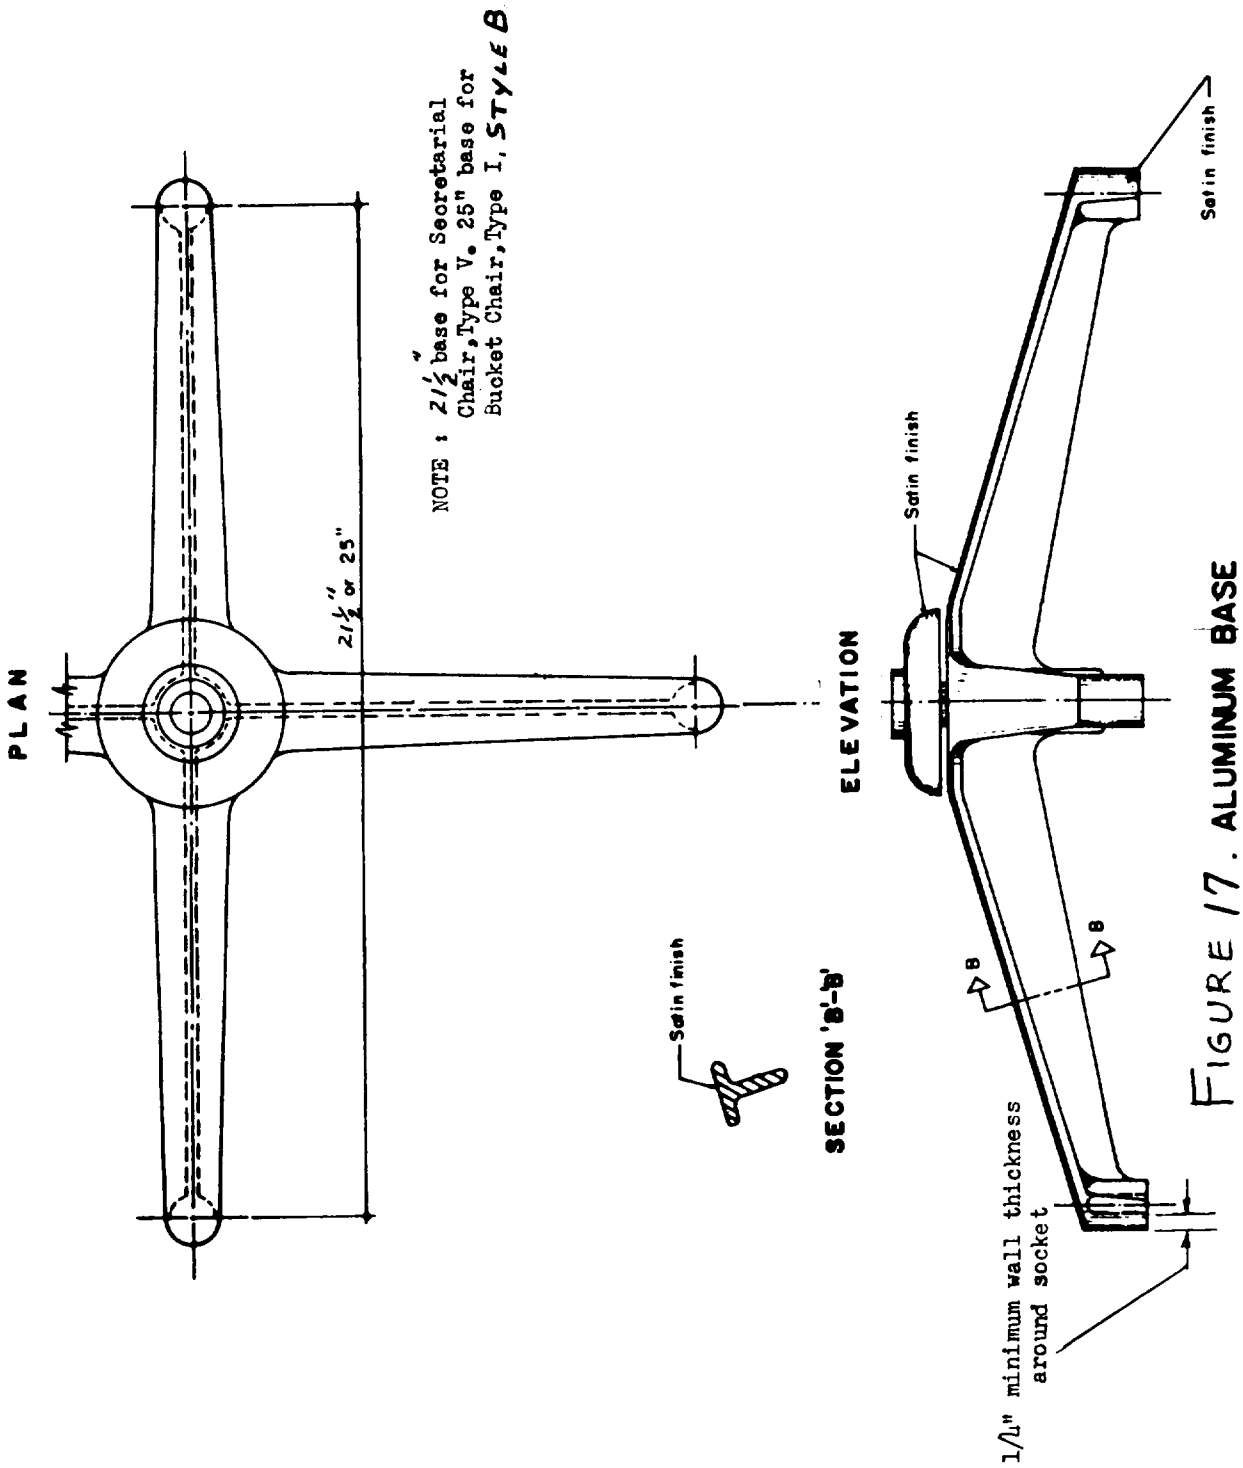


FIGURE 17. ALUMINUM BASE

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.

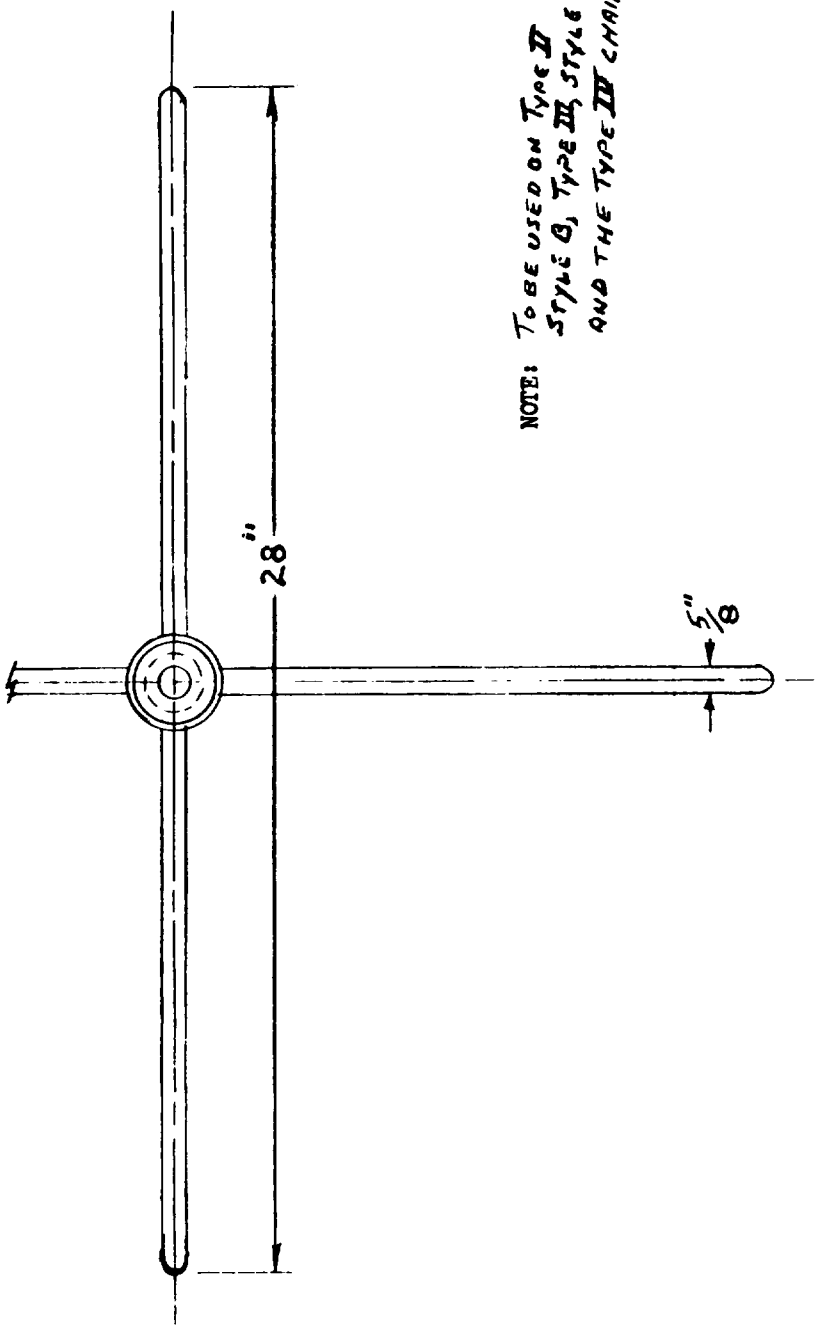

NOTE: To be used on Type II Style B, Type III, Style B, and the Type III chains.

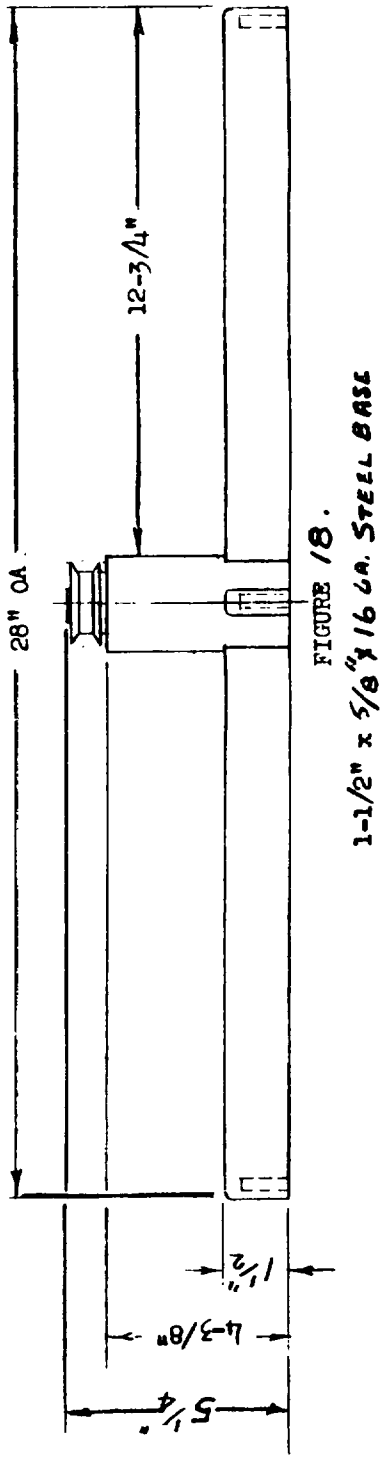


FIGURE 18. 1-1/2" x 5/8" x 16 GA. STEEL BASE

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:39Z
Check the source to verify that this is the current version before use.