METRIC
A-A-59133C
08 April 2020
SUPERSEDING
A-A-59133B
20 January 2010

COMMERCIAL ITEM DESCRIPTION

CLEANING COMPOUND, HIGH PRESSURE (STEAM) CLEANER

The General Services Administration has authorized the use of this commercial item description for all federal agencies.

1. SCOPE. This commercial item description (CID) covers alkaline steam cleaning compounds for use in steam cleaning machines for cleaning ferrous and nonferrous surfaces of equipment.

2. CLASSIFICATION. The cleaning compounds shall be classified by the following types. The type to be furnished shall be as specified (see 7.3(b)).

Type I - Compounds containing phosphates
Type II - Compounds containing no phosphates

3. SALIENT CHARACTERISTICS.

3.1 Performance requirements. The steam cleaning compound shall be equal to or superior in effectiveness to the comparison formula of Tables I and II. This shall be demonstrated by meeting the performance requirements of Table III when tested as specified therein.

3.2 Purity of Reagents. All reagents used for testing the salient characteristics of the compound shall be reagent grade chemicals meeting or exceeding the specifications of the Committee on Analytical Reagents of the American Chemical Society (ACS) when available. Other reagents may be used if it is first proved that they will not lessen the accuracy of the test.

3.3 Stock solutions.

3.3.1 Hard water stock solution. A 684 milligrams (mg) per liter (L) (40 grains per gallon) hard water solution is prepared by dissolving 0.8090 grams (g) of calcium acetate monohydrate ($Ca(C_2H_3O_2)_2 \cdot H_2O$) and 0.5546 g of magnesium sulfate heptahydrate ($M_gSO_4 \cdot 7H_2O$) per liter of freshly boiled distilled water.

Beneficial comments, recommendations, additions, deletions, clarifications, etc. and any data that may improve this document should be sent to DLA Aviation, VEB, 8000 Jefferson Davis Highway, Richmond, VA 23297-5616 or e-mailed to STDZNMGT@dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST database at https://assist.dla.mil

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

TABLE I. Composition of type I comparison compound.

Component	Weight percent (Wt.%)
Sodium metasilicate, pentahydrate ($Na_2SiO_3 \cdot 5H_2O$)	35.0
Sodium phosphate, monobasic monohydrate ($NaH_2PO_4 \cdot H_2O$)	10.5
Sodium tripolyphosphate ($Na_5P_3O_{10}$)	52.5
Nonionic surface-active agent, MIL-D-16791, type 1	2.0

TABLE II. Composition of type II comparison compound.

Component	Wt.%
Sodium metasilicate, anhydrous (Na_2SiO_3)	54.2
Citric acid, monohydrate ($C_6H_8O_7 \cdot H_2O$)	23.6
Citric acid, dihydrate ($C_6H_8O_7 \cdot 2H_2O$)	20.2
Nonionic surface-active agent, MIL-D-16791, type 1 with cloud point 54 ± 3 degrees Celsius (ºC)	2.0

TABLE III. Performance requirements.

Performance requirement	Limits	Test paragraph
Water softening or stability	Paragraph 3.4.1	3.4.2
Cleaning efficiency	Paragraph 3.5.1	3.5.5
Solubility	≤0.25 wt.% insoluble matter	3.6
pH value (0.50% solution, type I or 0.30% solution, type II)	$10.5 \leq pH \leq 11.4$	3.7.2
Corrosion	Paragraph 3.8.1	3.8.5
Surface tension (0.25% solution, type I or 0.15% solution, type II)	42 dynes/centimeter	3.9
Dust forming properties	Change in color	3.10
Penetration	≥30.0 mm	3.11
Segregation	<2% at all locations	3.12
Fineness	100% pass 3.35 mm sieve (U.S. No. 6 sieve) ≤3.0% pass 150 micrometer (µm) sieve (U.S. No. 100 sieve)	3.13
Rinsing	No white film	3.14
Phosphates (type II only)	None	3.15
Caking in storage	100% pass 3.35 mm sieve (U.S. No. 6 sieve)	3.16
Caking as received	None	3.17
Carbonates or bicarbonates	No effervescence	3.18
Fatty acid, soap, rosin, starch	None	3.19
Free sodium hydroxide	Paragraph 3.20.1	3.20.2
Biodegradability	≥ 90 wt.%	3.21

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.3.2 Cleaning compound stock solution. Weigh 10 g of the type I cleaning compound or 6 g of type II cleaning compound and transfer to a 2 L volumetric flask. Add 500 milliliters (mL) of hot distilled water and agitate to dissolve the cleaning compound. Cool to room temperature and dilute to volume with distilled water.

3.3.3 Comparison compound stock solution. Weigh 10 g of the Table I composition cleaning compound, or 6 g of Table II composition cleaning compound, and transfer to a 2 L volumetric flask. Add 500 mL of hot distilled water and agitate to dissolve the cleaning compound. Cool to room temperature and dilute to volume with distilled water.

3.3.4 Ammonium molybdate solution (Johnson's formula). Mix 55 g of ammonium molybdate ($(NH_4)_6Mo_7O_{24}\cdot 4H_2O$) and 50 g of ammonium nitrate (NH_4NO_3) with 10 mL of 15 normal (N) ammonium hydroxide (NH_4OH) and 20 mL of water. Stir and dilute to about 700 mL with water. Heat while stirring for 30 minutes until all salts have dissolved. Dilute to 1 L with water, let stand overnight and filter, but do not wash the residue.

3.4 Water softening or stability.

3.4.1 Performance requirements. When tested as specified in paragraph 3.4.2 at a temperature of 126.5 ºC to 129.5 ºC, a 0.25 wt.% solution of type I or a 0.15 wt.% solution of type II steam cleaning compound in water with a hardness of 342 mg/L (20 grains per gallon) shall give no evidence of precipitation or curd formation, nor shall there be an opalescence greater than that produced in a solution of the comparison compound of the same type as specified in Table I or Table II (as applicable) when the two compounds are tested simultaneously.

3.4.2 Test procedure. Add 20 mL of hard water stock solution (see 3.3.1) to a test tube (200 mm long X 25 mm outside diameter) containing 20 mL of the cleaning compound solution (see 3.3.2) and mix well. Immerse in the solution a test panel of UNS G10200 20-gage cold-rolled steel, 7.5 centimeters (cm) X 1.25 cm (3 inches X 1/2 inch) in size that has been polished with coarse emery cloth and cleaned with acetone. Place the test tube in a laboratory steam sterilizer at 126.5 ºC to 129.5 ºC (steam pressure of 145 to 165 kilopascals (21 to 24 pounds per square inch)) for 1 hour. Remove from the sterilizer. Cool to room temperature and examine for precipitation. Use an electrophotometer to measure opalescence in terms of optical density. Tests shall be run in quadruplicate. The same test shall be run in quadruplicate using the comparison compound solution (see 3.3.3) of the same type. The opalescence shall not be greater than that given by the statistical upper limit. The statistical upper limit at the 0.05 level may be obtained with the following formula:

$$\text{Statistical upper limit} = x + 0.72W$$

where x = Average of four determinations with the comparison compound.

W = Difference between the maximum and minimum values in the four determinations with the comparison compound.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.5 Cleaning efficiency.

3.5.1 Performance requirement. The cleaning compound shall be equal to or superior to the standard comparison steam cleaning compound of the same type in ability to remove a standard soil when tested as specified in 3.5.5.

3.5.2 Preparation of test panels. Test panels of UNS G10200 20-gage cold-rolled steel shall be prepared 6.5 X 6.5 cm (2-1/2 inches X 2-1/2 inches) in size. Each test panel shall have a hole 6 mm (1/4 inch) in diameter placed 3 mm (1/8 inch) from one corner. Sharp edges shall be smoothed with coarse emery cloth. The panels shall then be degreased in acetone. Both faces of each panel shall be polished with the same abrasive, stroking in one direction only. Clean in a hot alkaline solution until free from water break. Rinse in water, then dip in absolute ethyl alcohol and dry with paper toweling.

3.5.3 Preparation of soiled panels. The soiling material shall be 1065 grade mineral oil conforming to SAE-J1966, "Oil, Lubricating, Aircraft Piston Engine (Non dispersant Mineral Oil)". The cleaned panels, prepared as described in 3.5.2, shall be suspended on an "S" hook and dipped, one at a time, into a 400 mL beaker of the oil maintained at a temperature of 25 ºC ± 1 ºC. They shall be removed and allowed to drain at the same temperature for 30 minutes. The remaining drop of oil in the lower corner of each panel shall be removed with absorbent cotton.

3.5.4 Preparation of cleaning solutions. In a 2 L beaker, place 1,600 mL of 0.5 wt.% distilled water solution of the type I compound or 0.3 wt.% solution of the type II compound (see 3.3.2). Bring solution to a boil and keep at this temperature throughout the test. Maintain solution level throughout the test by addition of distilled water as required.

3.5.5 Test procedure. Immerse the soiled test panels, prepared as specified in 3.5.2, in the cleaning solution and in the comparison solution by means of a generic iron or copper hook, one end of which passes through the 6 mm (1/4 inch) hole and the other end over a glass rod placed across the top of the 2 L beaker. At the end of 2-1/2 minutes and 5 minute intervals, respectively, move the test panel forward and backward 3 times in each direction and then up and down 3 times in each direction; total agitation shall require not more than 6 seconds. At the end of 5 minutes immersion, remove the panel from the cleaning solution and give two six-second rinses in distilled water (no agitation) with a four second drain between rinses. The rinsing solutions shall consist of two 1 L beakers, each containing 800 mL of distilled water at 25 ºC ± 1 ºC. Dry the panel in a 50 ºC oven for 20 minutes, cool, and weigh. Thoroughly wash the panel with acetone, rinse in absolute ethyl alcohol, dry with paper toweling, and reweigh. The difference in weight is the amount of residual soil. Tests shall be run in quadruplicate. The residual soil of any test compound determination shall be not greater than that given by the statistical upper limit. The statistical upper limit at the 0.05 level may be obtained with the following formula:

$$\text{Statistical upper limit} = x + 0.72W$$

where x = Average of four determinations with the comparison compound.

W = Difference between the maximum and minimum values in the four determinations with the comparison compound.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.6 Solubility. Weigh 10 g of the compound and add to 100 mL of distilled water at 25 ºC ± 1 ºC in a 250 mL beaker. Stir until compound is thoroughly dissolved. Let stand 10 minutes. Filter through a tared Gooch crucible. Wash with distilled water until washing gives no alkaline reaction to phenophthalein. Dry at 105 ºC for 3 hours, cool and weigh. Gain in weight of crucible and contents is insoluble matter.

3.7 pH value.

3.7.1 Apparatus. The test shall be made with a pH meter having a sensitivity and readability of at least 0.05 pH. The meter shall be standardized against a pH 10 buffer solution immediately before making a test.

3.7.2 Test procedure. Prepare 100 mL of 0.5 wt.% distilled water solution of the type I compound or 0.3 wt.% solution of the type II compound (see 3.3.2). Determine the pH at a temperature of 25 ºC ± 1 ºC. No correction shall be made for sodium ion concentration.

3.8 Corrosion test.

3.8.1 Performance requirements. Boiling 0.25 wt.% and 1.2 wt.% solutions of the cleaning compound shall cause no loss in weight of aluminum or aluminum alloy test specimens in excess of that indicated in Table IV when tested as specified in 3.8.5. There shall be no visible staining, discoloration, etching, or pitting of the test specimens.

TABLE IV. Loss in weight permitted in corrosion test.

Type	Solution wt.%	UNS A91100	UNS A92024
I	0.25	1.2 mg	0.8 mg
I	1.2	0.8 mg	0.5 mg
II	0.15	1.2 mg	0.8 mg
II	1.2	0.8 mg	0.5 mg

3.8.2 Preparation of test panels. Test panels of UNS A91100 aluminum shall be cut 7.6 cm X 1.9 cm (3 inches X 3/4 inch) in size from approximately 0.9 mm (0.034 inch) thick sheet aluminum conforming to ASTM B209M, "Standard Specification for Aluminum and Aluminum-Alloy Sheet and Plate (Metric)", H14 or H24 temper. Test panels of UNS A92024-T3 aluminum shall be cut 7.6 cm X 1.9 cm (3 inches X 3/4 inch) in size from approximately 0.6 mm (0.025 inch) thick sheet aluminum conforming to SAE-AMS-QQ-A-250/4, "Aluminum Alloy 2024, Plate and Sheet". Sharp edges shall be smoothed with No. 150 alundum (Al_2O_3) polishing paper. Polish both faces with the same abrasive, stroking in one direction only. The UNS A91100 aluminum panels should be lightly polished with approximately 19 mg of metal removed in polishing to avoid smearing of the surface.

3.8.3 Cleaning of panels. Panels shall be cleaned with acetone using a swab of absorbent cotton. They shall then be wiped with paper toweling, dipped in absolute ethyl alcohol, and again wiped with paper toweling.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.8.4 Preparation of test solutions. Weigh 2.5 g of the type I cleaning compound or 1.5 g of the type II cleaning compound into a 1 L volumetric flask. Add 500 mL of hot distilled water and agitate to dissolve the cleaning compound. Cool to room temperature and dilute to volume with distilled water. Prepare another solution of the same type and in the same manner using 12.0 g of the compound.

3.8.5 Test procedure. Each cleaned test panel shall be weighed to 0.0001 g and immersed completely in 200 mL of the boiling solution of the compound in a 250 mL beaker. Keep the solution at a boil throughout the test, maintaining the solution level by additions of distilled water as required. After 60 minutes, remove the test panel from the boiling solution, rinse under flowing tap water (cold), rinse in distilled water (25 ºC ± 1 ºC), dip in absolute alcohol, wipe dry with paper toweling, and reweigh. The presence of corrosion products shall be noted. Tests shall be run in duplicate on each aluminum material in each solution.

3.9 Surface tension. Using a 0.25 wt.% distilled water solution of the type I compound or a 0.15 wt.% solution of the type II compound as prepared in paragraph 3.8.4, determine the surface tension in accordance with ASTM D1331, “Standard Test Methods for Surface and Interfacial Tension of Solutions of Paints, Solvents, Solutions of Surface-Active Agents, and Related Materials Active Agents, and Related Materials”.

3.10 Dust forming properties. The inside walls of a 250 mL glass-stoppered graduated cylinder shall be rendered completely free of any grease and moisture. A 25 g sample of the cleaner shall then be placed on the bottom of the clean graduated cylinder. The graduated cylinder shall then be stoppered, inverted, and immediately returned to its original position. After any suspended dust has been allowed to settle for 5 seconds, the stopper of the graduated cylinder shall be removed. A moistened piece of red litmus paper shall be suspended in the graduated cylinder without touching the walls so that the lower end of the litmus paper strip coincides with the 210 mL mark at the upper end of the graduated cylinder. After 60 seconds, the litmus paper shall be removed and examined for any color change. Excessive dusting is indicated by any change in the litmus paper from red to blue.

3.11 Penetration. Place 100 g of the compound in a flat bottom straight sided Pyrex glass crystallizing dish, 40 mm high by 80 mm in diameter. Place sufficient lead shot into a 250 mL low form beaker so that the combined weight of the beaker and shot equals 800 g. Place the weighted 250 mL beaker on top of the 100 g of compound. Place the assembly in a dessicator containing a saturated solution of potassium sulfate (K_2SO_4). Place the dessicator in an oven maintained at 43 ºC to 46 ºC for 24 hours. Remove the assembly from the oven and dessicator; remove weighted 250 mL beaker from compound and allow the crystallizing dish containing the compound to cool at room temperature for 2 hours. Determine penetration at three points on the surface, each at least 12 mm from the side of the crystallizing dish, using the penetrometer and grease-penetrometer cone prescribed in ASTM D217, "Standard Test Methods for Cone Penetration of Lubricating Grease", with a 5 second hold, 250 g total weight of the cone and attachments, and the temperature of the compound at 25 ºC ± 1 ºC. Run test in duplicate.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.12 Segregation. Samples taken from different portions of the container shall be analyzed for one constituent of the compound, such as silicates or total phosphates, using ASTM D800, "Standard Test Methods of Chemical Analysis of Industrial Metal Cleaning Compositions". The absolute difference between the wt.% at each portion and the average wt.% of the container shall be calculated.

3.13 Fineness. A 3.35 mm (U.S. No. 6) and a 150 µm (U.S. No. 100) sieve conforming to ASTM E11, "Standard Specification for Woven Wire Test Sieve Cloth and Test Sieves", shall be used in a sieve shaking apparatus. Transfer a 100 ± 0.1 g sample, without previously drying, to the 3.35 mm (U.S. No. 6) sieve. Allow the shaking apparatus to run 10 minutes. Examine the 3.35 mm (U.S. No. 6) screen for any retained cleaning compound and weigh the portion passing the 150 µm (U.S. No. 100) sieve. Calculate the percentage. If a sieving machine is not available, use the hand sieving procedure of ASTM D502, "Standard Test Method for Particle Size of Soaps and Other Detergents".

3.14 Rinsing. Test panels of UNS A92024-T3 aluminum shall be cut 6.5 cm X 6.5 cm (2-1/2 inches X 2-1/2 inches) in size from approximately 0.6 mm (0.025 inch) thick aluminum sheet. The test panels shall be polished and cleaned as specified in paragraph 3.8.2 and 3.8.3. Duplicate panels shall be tested. Prepare a 1.0 wt.% solution using 10 g of cleaning compound. Immerse a panel for 5 minutes in 400 mL of the boiling solution contained in a 600 mL beaker. Remove the panel, suspend at an angle of 45 degrees until dry, then suspend the panel in about 1 L of distilled water at 70 ºC ± 2 ºC for 3 minutes, withdrawing the panel slowly once each minute. Repeat the last step with a fresh sample of distilled water at 70 ºC. Remove the panel and let dry at an angle of 45 degrees as before. When dry, examine the panel for residue, then place a drop of absolute ethyl alcohol on the panel, allow to evaporate, and re-examine for white residue.

3.15 Phosphate (type II composition only). Place 1 g of the test compound into a 250 mL beaker and ignite over a gas flame. Titrate and dissolve the residue in 50 mL of water. Neutralize with HNO_3, add 10 mL of concentrated HNO_3 in excess, and filter into a second 250 mL beaker. Boil 30 minutes with beaker covered; remove cover and evaporate to dryness. Dissolve residue in 60 mL of water and add 15 mL of concentrated HNO_3 while stirring. Filter and add 6 g NH_4NO_3 to the filtrate. Filter again if there is any undissolved material. Heat the filtrate to near 80 ºC but no higher. Add 25 mL of the ammonium molybdate solution (see 3.3.4) to 10 mL of the filtrate and stir thoroughly. A yellow precipitate indicates the presence of phosphates.

3.16 Caking in storage. The compound shall retain free-flowing and granular characteristics when stored in an unheated warehouse for 12 months. This shall be tested in accordance with paragraph 3.13 on the bottom third of a 61 L (16 gallon) steel drum fitted with a steel cover with an airtight gasket attached filled with approximately 57 kg (125 pounds) of the compound for 12 months.

3.17 Caking as received. An as-received container of the steam cleaning compound shall be emptied and the contents examined for lumping or agglomerating of material. Visual evidence of either shall be cause for rejection of the compound.

3.18 Carbonates or bicarbonates. 6 N hydrochloric acid shall be added drop-wise to a 5 wt.% (5 g of compound per 100 mL of solution) distilled water solution of the compound and examined for effervescence.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

3.19 Fatty acid, soap, rosin, starch.

3.19.1 Fatty acid, soap, rosin. Place 10 g of the compound in a 100 mL tall form beaker. Add 30 mL of absolute ethyl alcohol. Place on a steam plate and stir for 5 minutes. Filter through dry double No. 41 Whatman paper or equilvalent. Evaporate filtrate to dryness. Dissolve residue in 20 mL distilled water. To half the solution, add 5 mL of 1.0 N acetic acid. To the other half, add 5 mL of 1.0 N calcium chloride solution. Formation of precipitates in both solutions indicates the presence of soap, rosin, or fatty acid.

3.19.2 Starch. Place one drop of an iodine solution on a freshly exposed surface of the sample. A violet color indicates the presence of starch.

3.20 Free sodium hydroxide.

3.20.1 Performance requirement. When tested as specified in paragraph 3.20.2, not more than 0.2 mL of 0.1 N hydrochloric acid shall be required to discharge any pink coloration.

3.20.2 Test procedure. Place 10 g of compound in a 100 mL tall form beaker. Add 30 mL petroleum ether (boiling range 35 ºC to 60 ºC) and stir 3 minutes with a glass rod. Decant off petroleum ether. Place on steam bath for 5 minutes to drive off hazardous gases, then dry in a vented oven for fifteen minutes at 105 ºC. Add 30 mL absolute ethyl alcohol and stir 2 minutes. Decant off alcohol through dry triple No. 41 Whatman filter paper or equivalent. Transfer 15 mL of the filtrate to a 125 mL flask and add several drops phenolphthalein indicator solution. If pink coloration results, titrate with 0.1 N hydrochloric acid.

3.21 Biodegradability.

3.21.1 Anionic synthetic detergents. When the detergent is an alkyl benzene sulfonate (ABS) or a linear alkylate sulfonate (LAS), the biodegradability shall be determined in accordance with the Soap and Detergent Association (SDA) Scientific and Technical Report No. 3, "Test Procedures and Standards - ABS and LAS".

3.21.2 Nonionic and other synthetic detergents. Until a standard test method for determining the biodegradability of a nonionic detergent is agreed upon by industry and is acceptable to the government, the supplier shall determine the biodegradability in accordance with one of the current methods of the American Cleaning Institute (ACI).

4. REGULATORY REQUIREMENTS.

4.1 Recovered materials. The offeror/contractor is encouraged to use recovered materials to the maximum extent practicable, in accordance with paragraph 23.403 of the Federal Acquisition Regulation (FAR).

4.2 Safety data sheet (SDS). Manufacturers shall prepare and submit a SDS in accordance with FED-STD-313, "Material Safety Data, Transportation Data and Disposal Data for Hazardous Materials Furnished to Government Activities", and meeting the requirements of 29 Code of Federal Regulations § 1910.1200, "Occupational Safety and Health Standards: Hazard Communication".

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

4.3 Marking, packaging, and labeling. The product shall be labeled, packed and marked in accordance with 49 CFR parts 100 to 185.

5. PRODUCT CONFORMANCE PROVISIONS.


5.1 Product conformance. The products provided shall meet the salient characteristics of this CID, conform to the producer's own drawings, specifications, standards, and quality assurance practices, and be the same product offered for sale in the commercial marketplace. Any certificate of analysis (COA) offered with the product to the commercial market shall be provided with each lot or batch of product. The lot or batch number and the date of inspection/analysis from the offer shall be on each COA. A full COA proving the salient characteristics of the product meets government requirements shall be provided upon request. The government reserves the right to require proof of such conformance.

5.2 Market acceptability. The product offered must have been previously sold either to the government or on the commercial market.

6. PACKAGING. Preservation, packing, and marking shall be as specified in the contract or order.

7. NOTES.

7.1 Part or identification number (PIN). The following PIN procedure is for government purposes and does not constitute a requirement for the contractor.

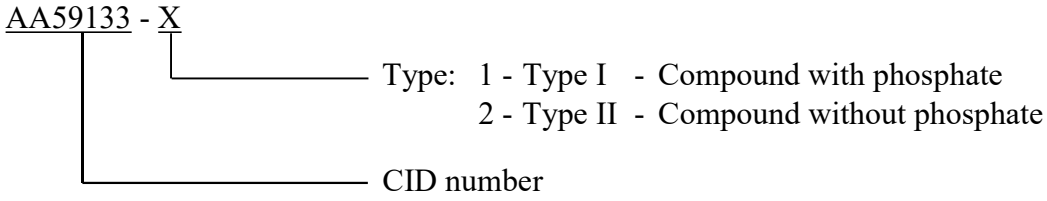

7.2 Sources of documents.

7.2.1 Electronic copies of ACS standards may be obtained from https://www.acs.org.

7.2.2 Electronic copies of ASTM documents may be obtained from https://www.astm.org/.

7.2.3 Electronic copies of CFR documents can be obtained from https://gov.ecfr.io/cgi-bin/ECFR.

7.2.4 Electronic copies of FAR documents may be obtained from https://www.acquisition.gov/browse/index/far.

7.2.5 Electronic copies of military specifications and standards can be obtained from https://quicksearch.dla.mil.

7.2.6 Electronic copies of SAE standards may be obtained from https://www.sae.org/.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

7.2.7 Electronic copies of SDA and ACI documents can be obtained from https://www.cleaninginstitute.org/

7.3 Ordering data. The contract or order should specify the following information:

a. CID document number, revision, and CID PIN.
b. Type (see 2).
c. Preservation, packing, labeling, and marking, if different (see 6.1).
d. Unit of issue and quantity required (see 6.2).

7.4 Subject term (key word) listing.

alkaline
ferrous
nonferrous
phosphates

7.5 National stock number (NSN). NSNs 6850-00-256-0157 and 6850-00-965-2329 correspond to this CID. These may not be the only NSNs associated with this document.

7.6 Shelf-life. This specification covers items where the assignment of a Federal shelf-life code is a consideration. Specific shelf-life requirements should be specified in the contract or purchase order, and should include, as a minimum, shelf-life code, shelf-life package markings in accordance with MIL-STD-129 or FED-STD-123, preparation of a materiel quality storage standard for type II (extendible) shelf-life items, and a minimum of 85 percent shelf-life remaining at time of receipt by the Government. These and other requirements, if necessary, are in DoDM 4140.27 Volumes 1 and 2. The shelf-life codes are in the Federal Logistics Information System Total Item Record. Additive information for shelf-life management may be obtained from DoDM 4140.27 Volumes 1 and 2, or the designated shelf-life Points of Contact (POC). The POC should be contacted in the following order: (1) the Inventory Control Points that manage the item and (2) the DoD Service and Agency administrators for the DoD Shelf-Life Program. Appropriate POCs for the DoD Shelf-Life Program can be contacted through the DoD Shelf-Life Management website: https://www.shelflife.dla.mil/.

7.7 Changes from previous issues. The margins of this specification are marked with vertical lines to indicate where changes from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the previous issue.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.

MILITARY INTERESTS:

Custodians:
Army – MR
Navy – SH
Air Force – 68
DLA – GS

Review Activities:
Army – AR
Navy – AS, MC, OS

CIVIL AGENCY
COORDINATING ACTIVITY:
GSA - FAS

Preparing Activity:
DLA – GS3

(Project 6850-2020-004)

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T10:04Z
Check the source to verify that this is the current version before use.