MIL-STD-1941(MR)
23 September 1983
Superseding
MIL-W-46086A(MR)
31 October 1978

MILITARY STANDARD

METAL-ARC WELDING OF HOMOGENEOUS ARMOR

NO DELIVERABLE DATA REQUIRED BY THIS DOCUMENT

/ FSC THJM /

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

DEPARTMENT OF DEFENSE
Washington, DC 20360

Metal-Arc Welding Of Homogeneous Armor

MIL-STD-1941(MR)

1. This Military Standard is approved for use by the Army Materials and Mechanics Research Center, Watertown, MA, Department of the Army, and is available for use by all Departments and Agencies of the Department of Defense.

2. Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Director, Army Materials and Mechanics Research Center, ATTN: DRXMR-SMS, Watertown, Massachusetts 02172, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

FOREWORD

This standard prescribes the classification of methods for the welding of homogeneous steel armor by metal-arc processes. Included in the document are joint-welding procedure details, weldors qualification requirements, and ballistic and inspection criteria for the evaluation of weldments employed in the fabrication of homogeneous rolled and cast armor.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

CONTENTS

Paragraph			Page
	1.	SCOPE	1
	1.1	Scope	1
	1.2	Classification	1
	2.	REFERENCED DOCUMENTS	2
	2.1	Issues of documents	2
	2.1.1	Other Government documents, drawings, and publications	2
	2.2	Other publications	3
	3.	DEFINITIONS	4
	3.1	Contractor and manufacturer	4
	3.2	Welding symbols	4
	3.3	Welding terms and definitions	4
	3.4	Routine positions	4
	3.5	Random positions	4
	4.	GENERAL REQUIREMENTS	5
	4.1	Weldments	5
	4.2	Armor	5
	4.3	Preparation of welding procedures and drawings	5
	4.4	Weldors qualification	5
	4.5	Number of radiographs	5
	4.6	Metric units	5
	5.	DETAILED REQUIREMENTS	6
	5.1	Recorded joint-welding procedure	6
	5.2	Types of electrodes used in conjunction with the various welding methods	6
	5.2.1	Method 1	6
	5.2.2	Method 2	6
	5.2.3	Method 3	6
	5.2.4	Method 4	6
	5.2.5	Method 5	6
	5.3	Shielding gas	6
	5.3.1	Composition	6
	5.3.2	Dew point	7
	5.3.3	Volume	7
	5.4	Heating of Weldments	7
	5.4.1	Preheating	7
	5.4.2	Postheating	7
	5.4.3	Interpass temperature	7
	5.5	Repair welding procedures	7
	5.6	Welded attachment procedures	7

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

CONTENTS - Continued.

5.7	Qualification for radiographic and joint welding procedures.	7
5.7.1	Test samples and workmanship specimens.	7
5.7.1.1	Fabrication of ballistic test samples and workmanship specimens	8
5.7.2	Sample production weldment.	8
5.8	Ballistic testing requirements.	8
5.8.1	Test samples.	8
5.8.1.1	Dimensions.	8
5.8.1.2	Number of test samples.	8
5.8.1.2.1	Joint types	8
5.8.1.2.2	Different armors.	8
5.8.1.3	Fabrication of test samples	8
5.8.1.3.1	For joint types 1, 2, 4, or 5	8
5.8.1.3.2	For joint types 3, 6, or 7.	9
5.8.2	Preparation of the ballistic test plate	9
5.8.3	Identification marking of test plates	9
5.8.3.1	Marking of retest plates.	9
5.8.4	Ballistic test requirements	10
5.8.4.1	Ballistic testing	10
5.8.4.2	Allowable cracking.	10
5.8.4.3	Magnetic particle or penetrant test	10
5.8.5	Test method	10
5.8.5.1	Test decision on additional impacts	10
5.8.5.2	Location of impact.	10
5.8.5.2.1	Direct impact	10
5.8.5.2.2	Point of impact	10
5.8.5.2.3	Unacceptable and acceptable impacts	11
5.8.5.3	Evaluation of test results.	11
5.8.5.3.1	Parallel cracks	11
5.8.5.3.2	Cracks outside the acceptable limits for impacts	11
5.8.5.3.3	Condition for a "no test" decision.	11
5.8.6	Visual examination of test plates	12
5.8.7	Radiographic inspection of the test plate	12
5.8.8	Repair of test plate.	12
5.8.9	Rejection of ballistic test plate	12
5.8.9.1	Retests	12
5.9	Workmanship	12
5.9.1	Test specimens.	12
5.9.1.1	Number.	12
5.9.1.2	Dimensions.	12
5.9.1.3	Preparation of specimens.	12
5.9.1.3.1	Full penetration weld specimens	13
5.9.1.3.1.1	Joint types 1, 2, 3, 4, 5, 6, and 7	13
5.9.1.3.1.2	Joint types 8 and 9	13
5.9.1.3.2	Partial penetration weld specimens.	13
5.9.1.4	Test method	13
5.9.1.5	Visual examination.	13
5.10	Radiographic procedure.	13
5.10.1	Radiographic drawings	13

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

CONTENTS - Continued.

5.10.2	Pilot vehicles.	14
5.10.3	Initial weldments	14
5.10.3.1	Film and position chart	14
5.10.3.2	Radiographic procedure.	15
5.11	Inspection of production weldments.	15
5.11.1	Visual.	15
5.11.1.1	Welding procedure	15
5.11.1.2	Welds	15
5.11.1.2.1	Markings of repairs to weldments.	15
5.11.1.3	Inspection of weldments subjected to straightening	15
5.11.2	Radiographic.	15
5.11.2.1	Spot checking	15
5.11.2.2	Daily exposure requirements	15
5.11.2.3	Selection of joints for radiography	16
5.11.2.4	Rejectable joints	16
5.11.2.5	Corresponding joints.	16
5.11.2.6	Checking of consecutive weldments	16
5.11.3	Quality control	17
APPENDIX A	FORMS, WORKMANSHIP SPECIMENS AND TEST PLATES FOR THE JOINT WELDING PROCEDURE	18
Paragraph 10.	SCOPE	18
10.1	Scope	18
20.	FORMS	18
20.1	Type.	18
20.2	Number.	18
20.3	Cover sheet	18
30.	DESCRIPTIONS OF FORMS	18
30.1	Figure 1.	18
30.2	Figure 2.	18
30.3	Figure 3.	18
30.4	Figure 4.	18
30.4.1	Joint A-A	19
30.4.2	Joint B-B	19
30.4.3	Joint C-C	19
30.4.4	Joint D-D	19
30.4.5	Joint H-H	19
30.5	Figure 5.	19
30.6	Figure 6.	19
30.6.1	Tables A and B.	19
30.6.2	Table C	20
30.7	Figure 7.	20
30.8	Figure 8.	20
30.9	Figure 9.	20
30.10	Figure 10	20
30.11	Figure 11 and 12.	20
30.11.1	Orientation	20
30.12	Ballistic test plate forms.	20

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Contents - Continued.

FIGURES

Figure	1	Cover sheet	21
	2	Table of contents for the welding procedure	22
	3	Perspective drawing of a complete hull.	23
	4	Summary of qualification tests for recorded joint welding procedure	24
	5	Summary of armor types & compositions	25
	6	Summary of electrodes with welding currents & voltages.	26
	7	Recorded joint welding procedure No. 1 Joint A-A	27
	8	Recorded joint welding procedure No. 2 Joint B-B	28
	9	Recorded joint welding procedure No. 3 Joint C-C	29
	10	Recorded joint welding procedure for Joints D-D, E-E, F-F and G-G.	30
	11	Recorded joint welding procedure No. 8a Joint H-H	31
	12	Recorded joint welding procedure No. 8b Joint H-H	32
	13	Armor welding data sheet No. 1.	33
	14	Armor welding data sheet No. 2.	34
	15	Armor welding data sheet No. 3.	35
	APPENDIX B	EVALUATION OF WELDOR CAPABILITY.	36
Paragraph	40.	SCOPE	36
	40.1	Scope	36
	50.	REQUIREMENTS.	36
	50.1	Weld type	36
	50.2	Position of weld.	36
	50.2.1	Groove welds.	36
	50.2.1.1	Flat position	36
	50.2.1.2	Horizontal position	36
	50.2.1.3	Vertical position	37
	50.2.1.4	Overhead position	37
	50.2.2	Fillet welds only	37
	50.2.3	Radiography of welds.	37
	50.2.4	Materials	37
	50.2.5	Electrodes.	38
	50.2.6	Workmanship	38
	60.	INSPECTION.	38
	60.1	Test specimens.	38
	60.1.1	Groove welds.	38
	60.1.2	Fillet welds.	38

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Contents - Continued.

	60.2	Inspection procedures	38
	60.2.1	Visual.	38
	60.2.2	Radiographic.	38
	70.	FACTORS IN THE JOINT-WELDING PROCEDURE.	38
	70.1	Factors to be included in the joint-welding procedure and changes requiring resubmittal of the procedure and requalification of weldors.	38
	80.	REQUIREMENTS FOR BALLISTIC TEST PLATES, BALLISTIC TESTS AND WORKMANSHIP SPECIMENS	43
	80.1	Thickness of ballistic test plates.	43
	80.2	Requirements for ballistic tests	44
	80.3	Size of workmanship specimens	44
	80.4	Weldor requalification requirements	44

TABLES

Table	I	Weldor evaluation with the "K" qualification plate	36
	II	Requirements for the joint-welding procedure.	39
	III	Thickness of ballistic test plates.	43
	IV	Requirements for ballistic tests.	44
	V	Workmanship specimen sizes.	44
Figure	16	Ballistic test plate.	45
	17	Some weld cracks (W.C.) which could occur from projectile impact, and measurement of total W.C. for acceptance purposes (see table IV)	46
	18	General form of workmanship specimens for joint types 1, 2 and 3.	47
	19	General form of workmanship specimen for joint types 4, 5, 6 and 7	48
	20	General form of workmanship specimen for joint types 8 and 9	49
	21	Groove weld test specimen for qualification of weldors or welding operators - for plate thickness of 0.5 in. (12.7 mm) or less.	50
	22	Groove weld test specimen for qualification of weldors or welding operators - for plate thickness of more than 0.5 in. (12.7 mm).	50
	23	Fillet weld test specimen for qualification of weldors or welding operators	51

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

1. SCOPE

1.1 Scope. This specification covers the requirements for the fabrication of weldments by metal-arc welding processes, which weldments are constructed of homogeneous rolled and cast armor and the steel attachments to this armor.

1.2 Classification. The welding methods shall be classified as follows:

Method 1 - Shielded metal-arc welding with austenitic electrodes.
Method 2 - Shielded metal-arc welding with ferritic electrodes.
Method 3 - Gas metal-arc welding with solid or cored ferritic electrodes.
Method 4 - Gas metal-arc welding with solid or cored austenitic electrodes.
Method 5 - Submerged-arc welding. Electrode type optional.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

2. REFERENCED DOCUMENTS

2.1 Issues of documents. The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this standard to the extent specified herein.

SPECIFICATIONS

MILITARY

DoD-D-1000	- Drawing, Engineering and Associated List.
MIL-I-6866	- Inspection, Penetrant, Method of.
MIL-I-6868	- Inspection Process, Magnetic Particle.
MIL-A-11356	- Armor, Steel, Cast, Homogeneous, Combat Vehicle Type (1/4 to 8 Inches, Inclusive).
MIL-A-12560	- Armor, Steel Plate, Wrought, Homogeneous, Combat Vehicle Type (1/4 to 6 Inches, Incl.)
MIL-E-13080	- Electrodes, Welding, Covered, Austenitic Steel (19-9 Modified) for Armor Applications.
MIL-E-22200/1	- Electrodes, Welding, Mineral Covered, Iron Powder, Low Hydrogen, Medium and High Tensile Steel, As-Welded or Stress-Relieved Weld Application.
MIL-E-22200/6	- Electrodes, Welding, Mineral Covered, Low Hydrogen, Medium and High Tensile Steel.
MIL-E-23765/2	- Electrodes and Rods - Welding, Solid, Low Alloy Steel.
MIL-A-46100	- Armor Plate, Steel, Wrought, High Hardness.
MIL-A-46177	- Armor, Steel Plate and Sheet, Wrought, Homogeneous (1/8 to Less Than 1/4 Inch Thick)

STANDARDS

MILITARY

DOD-STD-100	- Engineering Drawing Practices.
MIL-STD-21	- Welded Joint Designs, Armored Tank Type.
MIL-STD-453	- Inspection, Radiographic.
MIL-STD-1264	- Radiographic Inspection For Soundness Of Welds In Steel By Comparison To Graded ASTM E 390 Reference Radiogrphs

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

2.1.1 Other Government documents, drawings, and publications. The following other Government documents form a part of this standard to the extent specified herein.

ATAC-STD-114	- Reference Standards and Radiographic Procedures for Partial Penetration Steel Welds.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

(Copies of ATAC-STD-114 may be obtained from the US Army Tank-Automotive Command, ATTN: DRSTA-GSS, Warren, Michigan 48090.)

2.2 Other publications. The following documents form a part of this standard to the extent specified herein. Unless otherwise indicated, the issue in effect on date of invitation for bids or request for proposal shall apply.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM) STANDARDS

ASTM E 340 - Macroetching Metals and Alloys.
ASTM E 390 - Reference Radiographs for Steel Fusion Welds.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, Pennsylvania 19103.)

AMERICAN WELDING SOCIETY (AWS) STANDARDS

AWS A2.4 - Symbols for Welding and Nondestructive Testing.
AWS A3.0 - Welding Terms and Definitions.
AWS A5.17 - Carbon Steel Electrodes and Fluxes for Submerged-Arc Welding.

(Application for copies should be addressed to the American Welding Society, 550 Northwest LeJeunne Road, P.O. Box 351040, Miami, Florida 33126.)

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

3. DEFINITIONS

3.1 Contractor and manufacturer. The term "contractor" as used in this specification is defined as the organization having a direct contact with one Government activity. The term "manufacturer" is defined as the organization actually performing the operations covered by this specification. The contractor may or may not be the manufacturer.

3.2 Welding symbols. Symbols for welding shall be as specified in AWS A2.4.

3.3 Welding terms and definitions. Welding terms and definitions shall be as specified in AWS A3.0.

3.4 Routine positions. Routine positions are those established in areas where welding defects are most likely to occur and are to be radiographed on each weldment selected for examination.

3.5 Random positions. Random positions are those other than routine as defined in 3.4 that are selected at the discretion of the Government.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

4. GENERAL REQUIREMENTS

4.1 Weldments. The steel armor and steel for attachments to be used in the fabrication of weldments shall conform to the requirements of the applicable drawing, contract or order. Deviations in specified compositional requirements for materials shall not be permitted unless specifically approved by the procuring activity.

4.2 Armor. Unless otherwise specified in the procurement document, steel armor shall be welded in the fully heat-treated condition.

4.3 Preparation of welding procedures and drawings. Prior to the production fabrication of any weldment, the contractor or manufacturer shall prepare in accordance with DoD-STD-100 and DoD-D-1000 an isometric, perspective, or other suitable drawing of the structure showing the location of each joint and shall establish a recorded joint welding procedure(s) to cover all welding (including a general outline for the repair of base metal and repair of welded joints) to be performed under this standard.

4.4 Weldors or welding operator. The contractor shall be responsible for determining the qualification of the weldors or the welding operators to perform welding satisfactorily, as prescribed in the contractor's or the manufacturer's welding procedure. As a minimum for determining qualification, the weldors shall perform the tests given in Appendix B.

4.5 Number of radiographs. The number of radiographs of production weldments specified for routine spot-checking of a particular vehicle should not exceed the number that can be taken reasonably during an 8-hour day. The frequency of spot-checking and selection of the standard should be based on the importance of the particular joint in the vehicle and on the production schedule in the contractor's plant.

4.6 Metric units. When metric dimensions are required, units for inch may be converted to the metric equivalent by multiplying by the following conversion factor:

English	Multiply by	Equals	Metric SI units
inch	25.40	=	Millimeters (mm)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5. DETAILED REQUIREMENTS

5.1 Recorded joint-welding procedure. Before the production fabrication of any weldment; specified in MIL-A-11356, MIL-A-12560, MIL-A-46100, and MIL-A-46177, the contractor shall prepare, or have the manufacturer prepare, an isometric or perspective drawing showing the location of each joint and prepare a description of the joint-welding procedure that covers all welding, including the repair of base metal and welded joints. Each joint-welding procedure shall contain a reference to the location of the joint as shown in the isometric or perspective drawing, a detailed cross-sectional sketch of the joint, and shall include the factors listed in table II (page 39).

This information shall be prepared in duplicate on a form approved by the procuring activity. The cover sheet shall be signed by the manufacturer and the contractor and shall be submitted to the procuring activity for review and approval. Appendix A shows the form and content of an approved form.

5.2 Types of electrodes used in conjunction with the various welding methods.

5.2.1 Method 1. The electrodes used for filler metal shall conform to the requirements of MIL-E-13080, except that any austenitic-type electrode may be used if such use is recorded in the contractor's recorded joint-welding procedure.

5.2.2 Method 2. The electrodes used for filler metal shall conform to MIL-E-22200/1 or MIL-E-22200/6, except that any low hydrogen ferritic or iron-powder type of electrode having a yield point in excess of 80,000 psi (5.52×10^8 Pa) may be used if such use is recorded in the contractor's recorded joint-welding procedure. Maximum moisture content of the coating shall be 0.2 percent by weight.

5.2.3 Method 3. The electrodes used for filler metal shall conform to MIL-E-23765/2, except that other ferritic electrodes having a yield point in excess of 80,000 psi (5.52×10^8 Pa) may be used if such use is recorded in the contractor's recorded joint-welding procedure.

5.2.4 Method 4. The electrodes used for filler metal shall be austenitic, having a minimum ultimate tensile strength of 85,000 psi (5.86×10^8 Pa) and a minimum elongation in 2 in. (50.8 mm) (transverse section) of 7 percent. Such use shall be recorded in the contractor's joint-welding procedure.

5.2.5 Method 5. The electrodes used for filler metal and the fluxes shall conform to AWS A5.17. The electrode selection shall be recorded in the contractor's joint-welding procedure.

5.3 Shielding gas.

5.3.1 Composition. The composition of the shielding gas mixtures shall not be detrimental to the quality of the welded armor joint. The composition shall be recorded in the contractor's joint-welding procedure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.3.2 Dew point. The dew point of the shielding gas for armor welding shall not exceed -57°C (-70°F). The dew point shall be recorded in the contractor's joint-welding procedure.

5.3.3 Volume. The volume of the shielding gas shall be recorded in the contractor's joint-welding procedure.

5.4 Heating of Weldments.

5.4.1 Preheating. Welding shall not be performed when the ambient temperature of the weldment is below 60°F (15.6°C). When the contractor's recorded joint-welding procedure states that the entire weldment or any specified area including the joint is to be preheated, the preheating shall be performed in accordance with the conditions described in the recorded joint-welding procedure. Unless otherwise approved by the procuring activity, general or local preheating shall not be performed above 500°F (260°C). However, material specified in accordance with MIL-A-46100 shall not be preheated above 300°F (149°C).

5.4.2 Postheating. General or local postheating to a maximum of 500°F (260°C) will be permitted. Higher temperatures shall not be used unless authorized by the procuring activity. However, general or local postheating will be permitted only to a maximum of 300°F (149°C) for material specified in accordance with MIL-A-46100.

5.4.3 Interpass temperature. The maximum interpass temperature shall not exceed 500°F (260°C) regardless of the welding process used. However, for material specified in accordance with MIL-A-46100, the maximum interpass temperature shall not exceed 300°F (149°C).

5.5 Repair welding procedures. Repair welding procedures shall be prepared, signed, and submitted in accordance with 5.1. The procedure shall include Factors 5, 6, 7, 8, 9, 12 and 13 of table II (page 39) and the additional factors listed in footnote 1, table II.

5.6 Welded attachment procedures. A tabulation shall be prepared grouping attachments and parts which require the same size of fillet weld - for all attachments in the fighting compartments of military combat vehicles, and for attachments on other parts of such vehicles when failure of the attachment may affect the mechanical operation of the vehicles. For each group the tabulation shall show all factors of table II shown in Appendix B.

5.7 Qualification for radiographic and joint-welding procedures.

5.7.1 Test samples and workmanship specimens. The contractor shall fabricate test samples and specimens that meet the ballistic test and workmanship requirements in order to be qualified for production.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.7.1.1 Fabrication of ballistic test samples and workmanship specimens. Before production and approval of the recorded joint-welding procedure, the contractor or manufacturer shall fabricate ballistic test samples described in Section 5.8, and workmanship specimens described in Section 5.9 at each plant where production welding is to be performed using the recorded joint-welding procedure. Workmanship specimens shall be identified with the name of the contractor or the manufacturer and the date of manufacture.

5.7.2 Sample production weldment. When specified by the procuring activity and at the expense of the government, a sample production weldment may be required to be fabricated in accordance with the approved recorded joint-welding procedure for visual inspection, radiographic inspection and ballistic testing.

5.8 Ballistic testing requirements.

5.8.1 Test samples.

5.8.1.1 Dimensions. The test sample shall be constructed to the form and dimensions shown in figure 16 (page 45). The thickness of the ballistic test plate relative to the joint thickness of the plate shall be as shown in table III (page 43).

5.8.1.2 Number of test samples.

5.8.1.2.1 Joint types. When joint types 1, 2, 3, 4, 5, 6, or 7 of the designs specified in MIL-STD-21 or when partial penetration groove welds are included in the recorded joint-welding procedure, one ballistic test plate of the maximum "T" thickness and one test plate of the minimum "T" thickness involved in any one of these joint types shall be prepared. For joint types 8 or 9, ballistic test plates shall not be required.

5.8.1.2.2 Different armors. A separate ballistic test plate shall be prepared for each different category of armor. Different armor is defined as: Armor from different sources; armor of different chemical compositional ranges; or armor manufactured by different methods, such as rolling or casting. However, to reduce excessive ballistic testing, the contractor may, at the option of the procuring activity, submit a report showing the grouping of chemical compositions of the rolled or cast armor and identifying the chemical composition of the ballistic test plates for each group.

5.8.1.3 Fabrication of test samples.

5.8.1.3.1 For joint types 1, 2, 4, or 5. The test samples shall conform to the design for type 1, with the minimum included angle, minimum root opening, and maximum root face specified in the dimensional requirements for joint types 1, 2, 4, and 5 in the recorded joint-welding procedure. When welding with the gas metal-arc process, the size of the root opening may be changed to accommodate the requirements of the welding process.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.8.1.3.2 For joint types 3, 6, or 7. The test samples shall conform to the design for type 3, with the minimum included angle, minimum root opening, and maximum root face specified in the dimensional requirements for joint types 3, 6, and 7 in the recorded joint-welding procedure. When welding with the gas metal-arc process, the size of the root opening may be changed to accommodate the requirements of the welding process.

5.8.2 Preparation of the ballistic test plate. Each ballistic test plate shall be welded in accordance with the contractor's joint-welding procedure. Only one joint-welding procedure shall be used on a single test plate. A ballistic test plate shall be made for every welding position described in the procedure. The weld joints may be full penetration or partial penetration depending on the recorded joint-welding procedure. The ballistic test plate, shown in figure 16 (page 45), shall be prepared by welding sections ab and cd completely on both sides before welding crossbar ef. Each section and the crossbar shall be started at the same preheat or ambient temperature, $\pm$ 5°F ($\pm$ 3°C). Welding in the crossbar prior to completion of the legs shall not extend for more than 2 in. (51 mm) in either direction and shall be feathered to leave at least 8 in. (203 mm) of continuous, open groove before starting to weld the crossbar. For all welding, the interpass temperature of the plate shall not exceed the maximum allowable interpass temperature as stated in 5.4.3. The interpass temperature of the base metal shall be measured immediately before deposition of each bead at a point lying approximately at the intersection of a line 3 in. (76 mm) from, and parallel to, the center of each joint and a line perpendicular to and through the midpoint of the length of each joint.

5.8.3 Identification marking of test plates. Each ballistic test plate shall be marked clearly for easy identification on the front surface of the plate. Marking shall be in letters not less than 1 in. (25 mm) high and shall include the number of the plate, the manufacturer's name, the contractor's name, and a designation showing the front of the plate. The number of the plate and the contractor's name shall also be stamped into the metal or painted in the upper right corner. All marking shall be fully legible. Painted markings shall not be obliterated in normal handling. The front of the ballistic plate shall be determined as follows:

a. For double groove joints. The front of the ballistic test plate is considered to be the surface on which welding (excluding tacking) is begun on each leg and on the crossbar.

b. For single groove joints. The front of the ballistic test plate is considered to be the outside or ballistically exposed surface containing the wide side of the groove.

5.8.3.1 Marking of retest plates. When two ballistic test plates are submitted for retest, both shall be marked with the number of the original rejected plate as well as the new numbers with the suffix "R" indicating retest.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.8.4 Ballistic test requirements. A properly executed check list for armor data, as shown in the applicable military specification, shall be submitted with each ballistic test plate.

5.8.4.1 Ballistic testing. Unless otherwise specified, ballistic test plates shall be forwarded to Commander, US Army Aberdeen Proving Ground, ATTN: STEAP-MT-A, Aberdeen Prooving Ground, MD 21005.

5.8.4.2 Allowable cracking. The ballistic test plates shall meet the weld cracking requirements of table IV (page 44) after being subjected to ballistic shock in accordance with table IV.

5.8.4.3 Magnetic particle or dye penetrant test. In borderline cases, where crack length as measured by visual observation, is close to the maximum allowable, the area in the vicinity of the crack ends shall be inspected with magnetic particles in accordance with MIL-I-6868 or with liquid dye penetrant in accordance with MIL-I-6866, to assure an accurate determination of the crack length.

5.8.5 Test method. The ballistic test plates shall be supported solidly on each of the two sides normal to the line of fire and parallel to the longest welds, with these welds upright and subjected to ballistic shock in accordance with table IV (page 44). Plates of thicknesses not covered by table III (page 43) shall be tested as directed by the procuring activity.

5.8.5.1 Test decision on additional impacts. When a test plate is declared "no test", as defined in 5.8.5.3.3, after being shocked by the impact of the first projectile, but the condition of the plate will permit additional impacts, the plate shall be evaluated on the results of the first additional impact meeting the requirements for velocity and location in accordance with the following criteria:

a. When cracking exceeds that allowed by the specification, the qualification decision shall be "no test".

b. When cracking does not exceed that allowed by the specification, the qualification decision shall be "satisfactory".

5.8.5.2 Location of impact.

5.8.5.2.1 Direct impact. The direct impact of the 75-mm PP M1002 or the 57-mm PP M1001 shall contact a part of the weld to be considered as conforming to the requirements of the ballistic test. Contact of the weld by any part of the projectile that spreads after impact will not satisfy the test requirements.

5.8.5.2.2 Point of impact. The point of impact of the 37 mm HE projectile M54 shall be within 1-3/4 in. (44 mm) of the weld, as measured from the center of the point of impact to the center of the weld, to be considered as conforming to the requirements of the ballistic test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.8.5.2.3 Unacceptable and acceptable impacts. Impacts less than 6 in. (152 mm) from the top or bottom edge of the plate that cause excessive weld or plate cracking shall be considered as failing to meet the requirements of the test. If, however, the cracking is not excessive and the requirements of 5.8.5.2.1 and 5.8.5.2.2 are met, the impact shall be considered as acceptable.

5.8.5.3 Evaluation of test results. The plates shall meet the requirements for maximum weld cracking specified in table IV (page 44) subject to the interpretations in 5.8.5.3.1 and 5.8.5.3.3.

5.8.5.3.1 Parallel cracks. Cracks in the armor parallel to the weld and within 1/8 in. (3 mm) of the edge of the weld shall be considered as part of the total weld cracking area.

5.8.5.3.2 Cracks outside the acceptable limits for impacts. Any length of weld cracking revealed as a result of an impact which does not conform with 5.8.5.2.1 or 5.8.5.2.2, whichever is applicable, but which is otherwise acceptable per 5.8.5.2.3 shall be cause for rejection of the welding procedure.

5.8.5.3.3 Conditions for a "no test" decision. When test conditions are such that the level of performance of the welding procedure represented by the plate cannot be determined, a "no test" decision shall be rendered. The conditions for this decision are as follows:

a. The point of impact of the projectile is not located within the distance limits specified in 5.8.5.2.1 or 5.8.5.2.2 and cracking in excess of specified limits does not occur.

b. The striking velocity of the projectile is above the maximum allowed and excessive cracking occurs.

c. The striking velocity of the projectile is below the minimum allowed and excessive cracking does not occur.

d. The location of the center of impact of the projectile is less than 6 in. (152 mm) from the top or bottom edge of the plate and excessive cracking occurs.

e. Excessive cracking occurs from an impact subsequent to the first impact when more than one is required.

f. Cracks in the plate occur which are greater than 6 in. (152 mm) and do not pass through the center of impact.

g. Cracking of the plate occurs outside a circle of 6 in. (152 mm) radius, the center of which is the center of impact, and excessive weld cracking has not occurred. In this event the cracked plate shall be subjected to a ballistic limit test in accordance with the applicable material specification. If the plate passes the ballistic limit requirements, the weld procedure is acceptable; otherwise (ballistic limit failure) a "no test" decision shall be rendered.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.8.6 Visual examination of test plates. All welds in the ballistic test plate shall be examined visually before shipment to the designated proving ground. Welds shall be equal to, or better, than those of the workmanship specimen (see 5.9).

5.8.7 Radiographic inspection of the test plate. Prior to the ballistic shock test, the welded joints in each test plate shall be inspected radiographically by an authorized representative of the Government. Full penetration welds shall be inspected for conformance with Grade II of MIL-STD-1264, with the direction of radiation parallel to the weld interface, then normal to the weld face, and finally parallel to the opposite weld interface. Partial penetration welds shall be inspected for conformance to ATAC-STD-114. Radiographs shall be subject to review by the Government proving ground, and its decision as to acceptability shall be final. The Government proving ground may make additional radiographic inspections at its option. Should the test plate fail to pass the radiographic inspection, the ballistic shock test shall not be performed until after the defective weld area(s) has (have) been repaired by the fabricator.

5.8.8 Repair of test plate. Weld repair on a test plate shall not exceed a total length of 8 in. (203 mm). The same area shall not be repaired more than once. The reason(s) for, extent of, and location of repairs shall be reported on a separate sheet of paper and attached to the check list for armor data, as shown in the applicable military specification.

5.8.9 Rejection of ballistic test plate. Failure of any ballistic test plate to pass either the ballistic test or the radiographic inspection at the Government proving ground shall be cause for rejection of the recorded joint-welding procedure.

5.8.9.1 Retests. Retests may be made upon the request of the contractor. Two additional test plates shall be made using the recorded joint-welding procedure and marked in accordance with 5.8.3.1 and submitted to the proving ground for retest. Failure of either or both of these plates shall be cause for rejection of the welding procedure represented.

5.9 Workmanship.

5.9.1 Test specimens.

5.9.1.1 Number. One workmanship specimen shall be fabricated for each type of joint included in the recorded joint-welding procedure. Separate specimens will not be required for different compositions of armor or for different ambient or preheating temperatures, provided that all other factors in the procedures remain unchanged. Mild steel may be used for the specimen.

5.9.1.2 Dimensions. The size of the workmanship specimen shall be in accordance with table V (page 44).

5.9.1.3 Preparation of specimens. Each specimen shall be welded as shown in figures 18, 19, or 20 (Appendix B) using the recorded joint-welding procedure. Each layer of weld metal shall have a minimum of 1-1/2 in. (38 mm) of exposed surface.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.9.1.3.1 Full penetration weld specimens.

5.9.1.3.1.1 Joint types 1, 2, 3, 4, 5, 6, and 7. Joint types shall be in accordance with MIL-STD-21. Both plates used in making the specimen shall be prepared with the minimum included angle, the minimum root opening, and maximum root face, as detailed in the recorded joint-welding procedure for the particular joint type (see figures 18 and 19 of Appendix B).

5.9.1.3.1.2 Joint types 8 and 9. Joint types shall be in accordance with MIL-STD-21. Both plates used in making the specimen shall be of the maximum "T" thickness, with the maximum fillet size specified in design requirements for each joint type. The joints shall be prepared using the minimum angle between the plates and the maximum plate separation specified for the particular joint type in the recorded joint-welding procedure (see figure 20 of Appendix B).

5.9.1.3.2 Partial penetration weld specimens. Joint types and other details shall be as required by specification or drawings and as recorded in the contractor's joint-welding procedure.

5.9.1.4 Test method. The test specimen shall be cross-sectioned as shown in figures 18, 19, and 20 of Appendix B and macro-etched in accordance with ASTM E 340. Both parts of the specimen shall be made available to the Government for examination.

5.9.1.5 Visual examination. Workmanship specimens shall be examined visually and shall be free of the following defects:

a. Undercut.
b. Overlap.
c. Surface cavities.
d. Surface cracks in the weld metal or in the heat-affected zone of the base metal.

5.10 Radiographic procedure.

5.10.1 Radiographic drawings. A radiographic drawing and a welding assembly drawing shall be submitted to the cognizant procuring activity for review in establishment of radiographic standards and "Routine Position" (see 3.4). The radiographic drawing shall be prepared by the design agency containing the following:

a. An isometric or plan view (or both) of the weldment.

b. Identification, by letter or number, of the joint(s) to be radiographed as identified on the assembly drawing. These joints are limited to types 1 through 7 of MIL-STD-21.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

c. Identification of positions by letter or number.

d. Cross section of the joint(s) showing the identification and type of the joint(s), either by symbol or by number as assigned in MIL-STD-21, and the thickness of the mating pieces.

e. A table entitled "Routine Positions" (see 3.4) containing three columns entitled "Position, left side", "Position, right side", and "Film size".

f. A table entitled "Random positions" (see 3.5) containing two columns entitled "Positions" and "Film size".

g. Notes, reading as follows:

(1) " 'Random shots' to be selected by the Government in accordance with 5.11.2.7".

(2) "All radiographs to conform to Grade II of MIL-STD-1264 or meet Standard (insert number) of ATAC-STD-114."

(3) "Radiography to be performed in accordance with MIL-STD-453."

(4) "On consecutive exposures and weldments, when feasible, the direction of radiation shall be alternated from parallel to the weld interface, to normal to the weld face, and to parallel to the opposite weld interface. The cycle shall be repeated for all positions radiographed on the weldment".

(5) " 'Routine position, left side' will be radiographed alternately with 'Routine position, right side' on consecutive weldments taken from production for radiographic inspection within the limits established in 5.11.2.1 through 5.11.2.7".

5.10.2 Pilot vehicles. Radiographic examination shall be performed on all pilot vehicles on all joints identified on the radiographic drawing and shall comply with the designated standards.

5.10.3 Initial weldments. Each initial weldment in joints subject to direct ballistic attack shall be completely radiographed in accordance with the requirements of MIL-STD-453 and conform to Grade II of MIL-STD-1264.

5.10.3.1 Film and position chart. The films for the initial weldment shall be submitted to the procuring activity with the radiographic position chart (see 5.10.1) to which the following information has been added:

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

a. Location of film.
b. Direction of radiation.
c. Stage of assembly.
d. Equipment used.
e. Type of film.
f. Size and location of filter.
g. Focal-film distance.
h. Processing procedure for film.
i. Applicable radiographic standard(s).

5.10.3.2 Radiographic procedure. With the additions shown in 5.10.3.1, the chart becomes a radiographic procedure and, in conjunction with the radiograph of the initial weldment, becomes the basis for establishing the radiographic frequency to be used in production.

5.11 Inspection of production weldments.

5.11.1 Visual.

5.11.1.1 Welding procedures. All procedures used in the fabrication of weldments shall be subject to inspection for compliance with the recorded joint-welding procedure.

5.11.1.2 Welds. All welds shall be subject to visual inspection. Welds shall be equal to, or better than, the workmanship specimens.

5.11.1.2.1 Marking of repairs to weldments. All repairs to be made to weldments shall be indicated on the weldments by suitable markings, easily legible, and of such nature that the marking shall not be obliterated in handling. The system of marking shall be subject to approval by the Government.

5.11.1.3 Inspection of weldments subjected to straightening. All weldments subject to straightening shall have welded joints in the straightened area inspected by a penetrant or magnetic particle inspection method. Less than 100 percent inspection may be permitted when an adequate statistical quality control system has been established by the contractor or manufacturer and has been approved by an authorized Government inspector.

5.11.2 Radiographic.

5.11.2.1 Spot checking. Joints subject to direct ballistic attack shall be spot checked by radiography in accordance with 5.11.2.2 through 5.11.2.6 and with supplementary requirements to be determined by the designing agency after examination of the radiographs. The supplementary requirements concern the number of exposures, radiographic position, and radiographic standards. Information about such requirements shall be submitted in accordance with 5.10.3 and 5.10.3.1.

5.11.2.2 Daily exposure requirements. The number of radiographs required during a given day shall not be below the minimum specified as required by drawings or Supplementary Quality Assurance Provisions (SQAP) or Quality Assurance Requirements (QAR).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.11.2.3 Selection of joints for radiography. Usually, radiography shall be required on any specific joint, with a frequency to be determined by the drawings or SQAP or QAR in accordance to ATAC-STD-114 or MIL-STD-1264 according to the relative importance of the joint in the weldment. Thus, spot checking will not require radiographing of all joints in a single weldment.

5.11.2.4 Rejectable joints. When the radiographic spot check of a weldment indicates a rejectable defect in a particular joint, the remainder of the joint shall be radiographed. All defects then found in the joint shall be repaired and these repaired areas subsequently radiographed. The repaired areas shall conform to the radiographic standard established for the joint.

5.11.2.5 Corresponding joints. On the next weldment designated for spot checking, the joint found rejectable in 5.11.2.4 will require spot checking in addition to the other joints selected for radiography. Should a rejectable defect be found, the remainder of the joint shall be radiographed. All rejectable defects then found in the joint shall be repaired, and the repaired areas subsequently radiographed. The repaired areas shall conform to the radiographic standard established for the particular joint.

5.11.2.6 Checking of consecutive weldments. When the radiographs required by 5.11.2.5 indicate a rejectable defect, the corresponding joint on the next weldment shall be completely radiographed. If no rejectable defects are found, spot checking shall be resumed. If rejectable defects are found, the corresponding joint on the weldment immediately following (in production) shall be completely radiographed. Complete radiography of the corresponding joint shall be continued with each consecutive weldment produced until a joint with no rejectable defects is obtained. All defects in each rejectable joint shall be repaired. Radiographs of the repaired areas shall conform to the radiographic standard established for the particular joint.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

5.11.3 Quality control. It shall be the full responsibility of the contractor to maintain the quality control procedures and inspection standards necessary to assure that the part, the assembly, the sub-assembly or the end product meets the requirements of the drawings and the contract.

Custodian:
Army - MR

Review activities:
Army - AT, AR, ME, TE

User activity:
Army - AL

Preparing activity:
Army - MR
Project No. THJM A118

(WP #3220A/DISC-0003A FOR AMMRC USE ONLY)

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

APPENDIX A

FORMS, WORKMANSHIP SPECIMENS AND TEST PLATES FOR THE JOINT WELDING PROCEDURE

10. SCOPE

10.1 Scope. This appendix covers the preparation of forms and associated requirements for workmanship specimens and test plates for use in the joint-welding procedure.

20. FORMS

20.1 Type. The forms illustrated in this appendix may be used for submittal of the joint-welding procedure. Other forms may be used if all pertinent information is included and if the forms are approved by the procuring activity.

20.2 Number. The completed forms shall be submitted in duplicate to the procuring activity for review.

20.3 Cover sheet. The cover sheet shall include a description of the vehicle weldment, the book number, the Government specification number, and the date submitted. The cover sheet shall be signed by the contractor and the manufacturer, if other than the contractor.

30. DESCRIPTIONS OF FORMS

30.1 Figure 1. Cover sheet which shall be signed in accordance with 20.3.

30.2 Figure 2. Table of contents for the welding procedure.

30.3 Figure 3. Perspective drawing of a complete hull. An isometric drawing would be equally acceptable. For some types of structures, it may be preferable to show subassemblies, as well.

30.4 Figure 4. A summary of this type, although not required by the specification, provides in one place a complete picture of the different joints involved, the types of armor in each joint, and the exact status of procedure qualification. The summary illustrated serves the following purposes:

a. Indicates, for each joint in the structure, the joint type as defined in MIL-STD-21 and change notices to the latest revision thereto.

b. Indicates the welding method employed: Shielded metal-arc or gas metal-arc welding.

c. Provides an index to the recorded joint-welding procedure for each joint.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

d. Indicates the kind of armor in each joint.

e. Simplifies the problem of determining the minimum number of ballistic test plates and workmanship specimens required to qualify all welding in the structure.

f. Provides space for recording results of tests.

g. Indicates whether or not a given procedure has been qualified, whether it has been qualified in more than one welding position, and provides supporting evidence by recording the test plates which passed the required test.

30.4.1 Joint A-A. Requires two ballistic test plates, one of the maximum plate thickness and one of the minimum plate thickness involved in joints of types 3, 6 and 7 as defined by MIL-STD-21 and change notices to the latest revision thereto (see 5.8.1.2.1). Workmanship specimens are required for joint types 1 and 3 (see 5.9.1.3.1).

30.4.2 Joint B-B. This joint, involving two types of armor, requires separate ballistic test plates for each type.

30.4.3 Joint C-C. Although separate ballistic test plates are required to represent each kind of armor, one workmanship specimen made with either kind of armor is sufficient to represent both (see 5.9.1.1).

30.4.4 Joint D-D. One ballistic test plate is required for armor I; two are required for armor II. Armor I is used for only one joint of types 1, 2, 4 or 5 and one test plate represents both the maximum and the minimum thicknesses involved.

30.4.5 Joint H-H. A separate workmanship specimen is required for each welding position. This is because a change in welding position means a change in the recorded joint-welding procedure, which requires resubmittal of the procedure (see table II).

30.5 Figure 5. Space is provided in the last column for recording the draw temperature employed by the armor manufacturer in heat-treating the armor. It is desirable that this information be available for ready reference, since the specification requires the preheating shall not be done above 500°F (260°C).

30.6 Figure 6.

30.6.1 Tables A and B. The summary of electrodes for shielded metal-arc welding and gas metal-arc welding has been divided into table A for electrodes conforming to MIL-E-13080 and table B for electrodes that do not conform to this specification. Table A does not include the type of covering of ranges of chemical composition, because these factors are controlled by the designations for type and class.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

30.6.2 Table C. This table sets forth the ranges of currents and voltages to be used with each size of electrode. The tabulation simplifies the recorded joint procedure (see figure 7, for example) by making it possible to refer to each table rather than state the current and voltage range for each pass (see factor 8 of table II).

30.7 Figure 7. This form represents an attempt to devise the simplest possible form for recording a complete joint-welding procedure. Note that all of the factors listed in table I have been included.

30.8 Figure 8. This recorded joint welding procedure designates only electrodes B and C, whereas electrode F is also of the same type and class, and could, under the provisions of this specification, be employed without resubmittal of the procedure. This illustrates that a contractor may wish to subject a given procedure to limitations greater than those prescribed.

30.9 Figure 9. The sketch of the joint designates the kind of armor used in each part. This should be done whenever a joint involves more than one kind of armor. (This is also illustrated on figure 8.)

30.10 Figure 10. It is unnecessary to show in detail the recorded joint-welding procedures for these joints because they are prepared by completing forms similar to those on figures 7, 8, and 9). The contractor shall prepare a complete joint welding procedure for each joint. The joint designs are shown in order to provide a basis for illustrating this method of qualifying a group of welding procedures (see figure 4).

30.11 Figures 11 and 12. When a joint is welded in two or more positions, different procedures may be designated by literal suffixes such as 8a, 8b, 8c, etc., as here illustrated.

30.11.1 Orientation. When recorded joint welding procedures relate to the same joint, but differ with respect to the position of welding, it is desirable to orient the sketch under "Location and sequence of passes" in such a way as to convey the idea of welding position. Figures 11 and 12 cover the flat and horizontal positions, respectively. Similar treatment will readily identify the overhead position, and a different orientation can be selected as a conventional way to represent the vertical position.

30.12 Ballistic test plate forms. At the same time that the ballistic test plate is shipped to the proving ground, the forms listed below are to be forwarded to: US Army Aberdeen Proving Ground, ATTN: STEAP-MT-A, Aberdeen Proving Ground, MD 21005.

Figure 13. Sheet 1, ORD-SIP-CS-13 "Welded Armor Data".
Figure 14. Sheet 2, "Armor Plate Data".
Figure 15. Sheet 3, ORD-SIP-13 "Weld Radiographic Report".

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

RECORDED JOINT-WELDING PROCEDURE

For

MEDIUM TANK, MI (VEHICLE)

WELDED TANK (WELDMENT)

Book 10

DATE OF SUBMITTAL: 10 May 1977

MANUFACTURED BY

Mars Manufacturing Company

Detroit, Michigan

Contract No. _____

Signed for Manufacturer:

_____
(Signature)
(Name, Typed)

Title: _____

Date Signed: _____

Manufactured Under
Military Specification

_____

Signed for Contractor:

_____
(Signature)
(Name, Typed)

Title: _____

Date Signed: _____

FOR MILITARY USE ONLY

FIGURE 1. Cover sheet.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Recorded Joint Welding Procedures

for

A Welded Hull

Contents:

Cover . . . . . Figure 1

Contents . . . . . Figure 2

Perspective drawing showing locations of welded joints . . . Figure 3

Summary of welding procedure qualification tests . . . . . Figure 4

Summary of armor types and compositions . . . . . Figure 5

Summary of electrodes and welding currents & voltages . . . . Figure 6

Recorded joint welding procedures . . . . . Figures 7-12

Armor welding data sheet forms . . . . . Figures 13-15

Miscellaneous Information:

FIGURE 2. Table of contents for the welding procedure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Notes: 1. Joint details are shown in recorded joint welding procedures, reference to which is given in table on sheet 4.

2. The joint designs shown in the recorded joint welding procedures are for illustration purposes only, and it is not necessarily indicated that applications of these joints in similar locations will be approved for any specific vehicle.

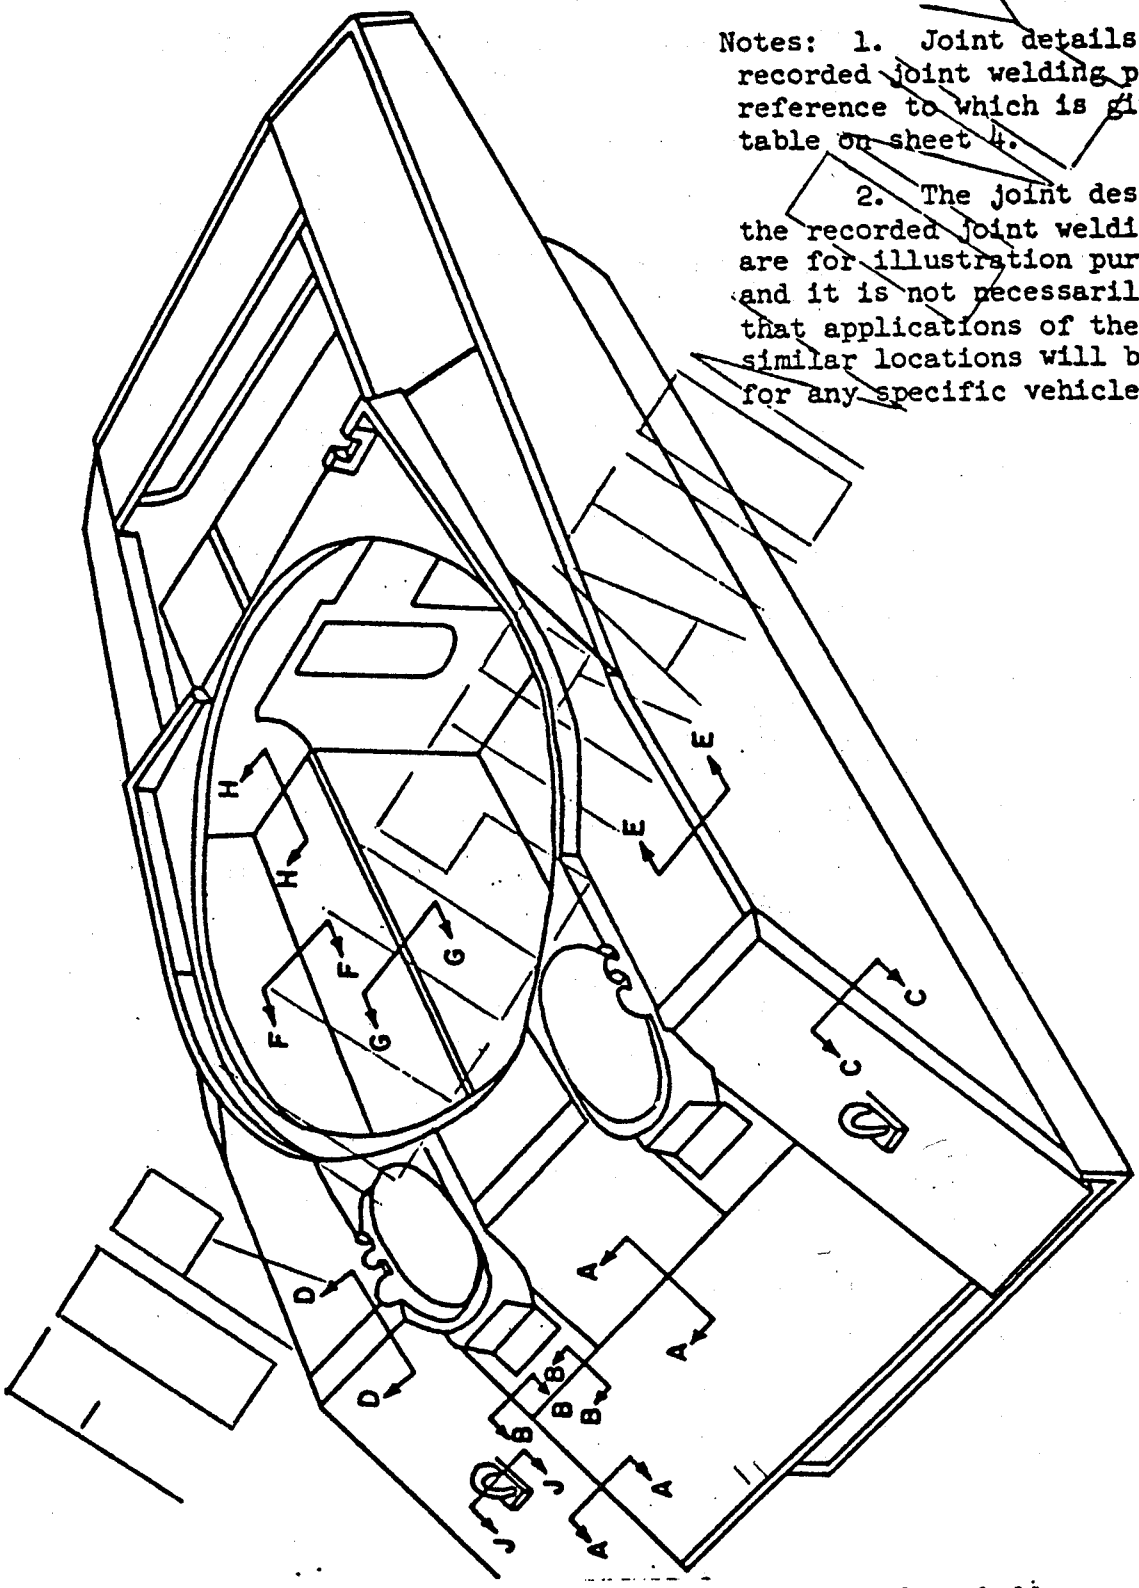


FIGURE 3. Perspective drawing of a complete hull.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Joint No.	Joint Type*	Recorded Joint Welding Procedure No.	** Armor Reference Designation	Status of Procedure Qualification					
				Ballistic Tests			Workmanship Specimens		
				Flat	Vertical	Horizontal	Flat	Vertical	Horizontal
A-A	3	1	1	Passed (Plates #17 and 18)	Not Tested	Not Tested	Not Required	Not Required	Not Required
B-B	3	2	1 and III	Passed (Plates #17 and 18) / Passed (Plate #19)	ditto	ditto	ditto	ditto	ditto
C-C	6	3	1 and II	Passed (Plates #17 and 18) / Passed (Plate #22)	ditto	ditto	Passed (Specimen #51)	Not Tested	Not Tested
D-D	1	4	1 and II	Passed (Plate #16) / Passed (Plates #20 & 21)	ditto	ditto	Not Required / Not Required	Not Required / Not Required	Not Required / Not Required
E-E	6	5	II	Passed (Plate #22)	ditto	ditto	Passed (Specimen #51)	Not Tested	Not Tested
F-F	4	6	II	Passed (Plates #20 & 21)	ditto	ditto	Passed (Specimen #52	ditto	ditto
G-G	4	7	II	Passed (Plates #20 & 21)	ditto	ditto	Passed (Specimen #52)	ditto	ditto
H-H	9	8	II	Not Required)	Not Required	Not Required	Passed (Specimen #53)	Passed (Specimen #54)	Passed (Specimen #55)
J-J	9	9	1 and II	ditto	ditto	ditto	ditto	ditto	ditto

*Joint type is that defined in MIL-STD-21
**See "Summary of Armor Types and Compositions" (Figure 5)

FIGURE 4. Summary of qualification tests for recorded joint welding procedure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Armor Reference Designation	Type	Specification No.	Manufacturer	Chemical Composition Range (%)											Draw Temperature*
				C	Mn	Si	S	P	Cr	Ni	Mo	V	Cu	Zr	
I	Rolled Homogeneous	MIL-S-12560	"X"	.26 .30	.95 1.15	.60 .90	.035 Max.	.035 Max.	.60 .70		.20 .25			.07 .11	800
II	Rolled Homogeneous	MIL-S-12560	"Y"	.23 .30	.85 1.00	.20 .30	.04 Max	.03 Max	.75 .90	.90 1.10	.30 .35		.07 .16		600
III	Cast Homogeneous	MIL-S-11356	"Z"	.21 .31	1.30 1.80	.25 .75	.05 Max.	.05 Max.	.20 .70		.25 .45				1100

* Draw temperature employed by the armor manufacturer in heat-treating the armor.

FIGURE 5. Summary of armor types and compositions.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Table A. Electrodes Conforming With Specification No. XXX

Electrode Reference Designation	Manufacturer	Brand Name	Type	Class
A	"X"	Bestweld	V	WD-EL-307-10
B	"X"	Superweld	VI	WD-ET-308-10
C	"Y"	Bestalloy	VI	WD-ET-308-10
D	"Y"	Superloy	VI	WD-ET-308-10
E	"Z"	Bestarc	V	WD-ET-307-10
F	"Z"	Superarc	VI	WD-ET-308-10

Table B. Electrodes Not Conforming With Specification No. XXX

Electrode Reference Designation	Manufacturer	Brand Name	Type of Covering		Chemical Composition Range (%)								
					C	Mn	Si	S	P	Cr	Ni	Mo	V	Others
G	"Q"	Excelweld	Lime	Core Wire	.15 Max.	3.50 4.50	.25 .60	.03 Max.	.04 Max.	19.5 21.5	9.0 10.5			
				Deposited Weld Metal	.17 Max.	5.00 4.50	.80 Max.			18.0 20.5		.50 1.00		
H	"R"	Wonderweld	Titania	Core Wire	.15 Max.	1.50 2.00	.25 .60	.03 Max.	.04 Max.	19.5 21.5	9.0 10.5			
				Deposited Weld Metal	.17 Max.	1.25 2.00	.80 Max.			18.0 20.5		1.80 2.25		

Table C. Ranges of Current* and Voltage To Be Used With Each Size of Electrode

Diameter of Electrode	Current Range (Amperes)			Voltage Range		
	Flat Position	Vertical Position	Horizontal Position	Flat Position	Vertical Position	Horizontal Position
5/32	85-115	75-100	80-105	21-28	20-26	20-26
3/16	150-185	135-165	145-175	23-29	22-27	22-27
1/4	200-245	--	190-230	24-30	23-28	23-28
5/16	310-340	--	--	25-32	24-30	24-30


* Current values. Welding current may be measured with a tong-type tester. Current variations for all types and sizes of electrodes shall be limited to approximately ± 15 percent.

FIGURE 6. Summary of electrodes with welding currents and voltages.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Recorded Joint Welding Procedure No. 1

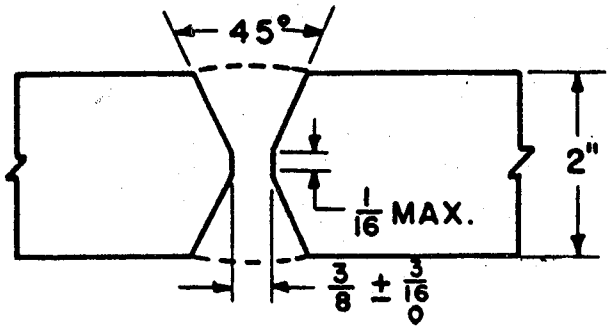
Joint A-A



Joint Welding Procedure: General Information

Armor (reference designation)	I
Electrode (reference designation)	B, C, or F
Power Source (AC-DC) and Polarity if DC	DC, Reverse
Welding Current & Arc Voltage Range	As Specified in Table C, Figure 6
Use of Spatter Compound on Scarfed Edges	None
Backing	Copper
Preheating	None
Position of Welding	Flat

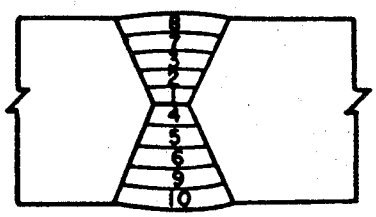
Joint Welding Procedure: Details of

Pass	Electrode	Type of Pass	Location & Sequence of Passes
1	3/16	Stringer	
2,3	1/4	Weave	
4	3/16	Stringer	
5,6	1/4	Weave	
7 to 10	5/16	Full Weave	

Note: Root of weld shall be ground to sound metal before depositing pass No. 4

FIGURE 7. Recorded joint welding procedure No. 1 Joint A-A.

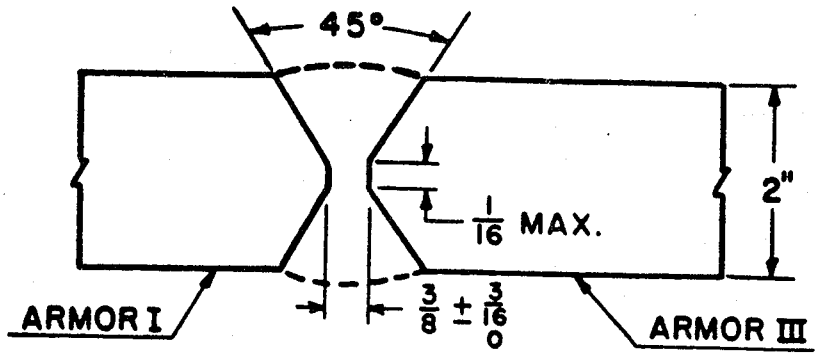Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.




Recorded Joint Welding Procedure No. 2

Joint B-B

Joint Welding Procedure: General Information

Armor (reference designation)	I and III
Electrode (reference designation)	B or C
Power Source (AC or DC) and Polarity if DC	DC, Reverse
Welding Current & Arc Voltage Range	As Specified in Table C, Figure 6
Use of Spatter Compound on Scarfed Edges	None
Backing	Copper
Preheating	None
Position of Welding	Flat

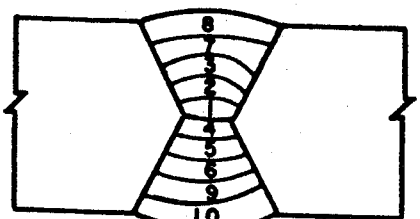
Joint Welding Procedure: Details of

Pass No.	Electrode Size	Type of Pass	Location & Sequence of Passes
1	3/16	Stringer	
2,3	1/4	Weave	
4	3/16	Stringer	
5,6	1/4	Weave	
7 to 10	5/16	Full Weave	

Note: Root of Weld shall be ground to sound metal before depositing pass No. 4

FIGURE 8. Recorded joint welding procedure No. 2 Joint B-B.

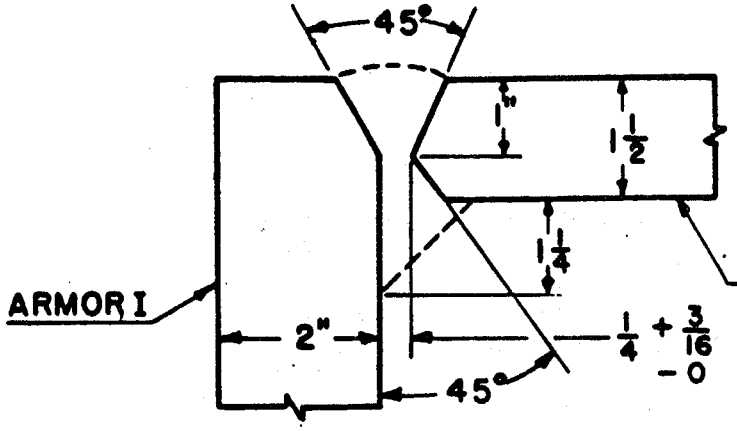Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.




Recorded Joint Welding Procedure No. 3

Joint C-C

Joint Welding Procedure: General Information

Armor (reference designation)	I and II
Electrode (reference designation)	B.C. or F
Power Source (AC or DC) and Polarity if DC	D. C. Reverse
Welding Current & Arc Voltage Range	As Specified in Table C, Figure 6
Use of Spatter Compound on Scarfed Edges	None
Backing	Copper
Preheating	None
Position of Welding	Flat

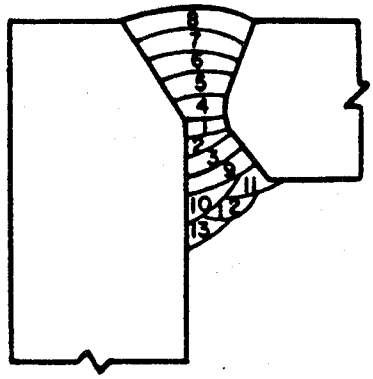Joint Welding Procedure: Details of

Pass No.	Electrode Size	Type of Pass	Location & Sequence of Passes
1	3/16	Stringer	
2,3	1/4	Weave	
4	3/16	Stringer	
5,6	1/4	Weave	
7 to 9	5/16	Full Weave	
10 to 13	5/16	Weave	

Note: Root of Weld shall be ground to sound metal before depositing pass No. 4

FIGURE 9. Recorded joint welding procedure No. 3 Joint C-C.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.


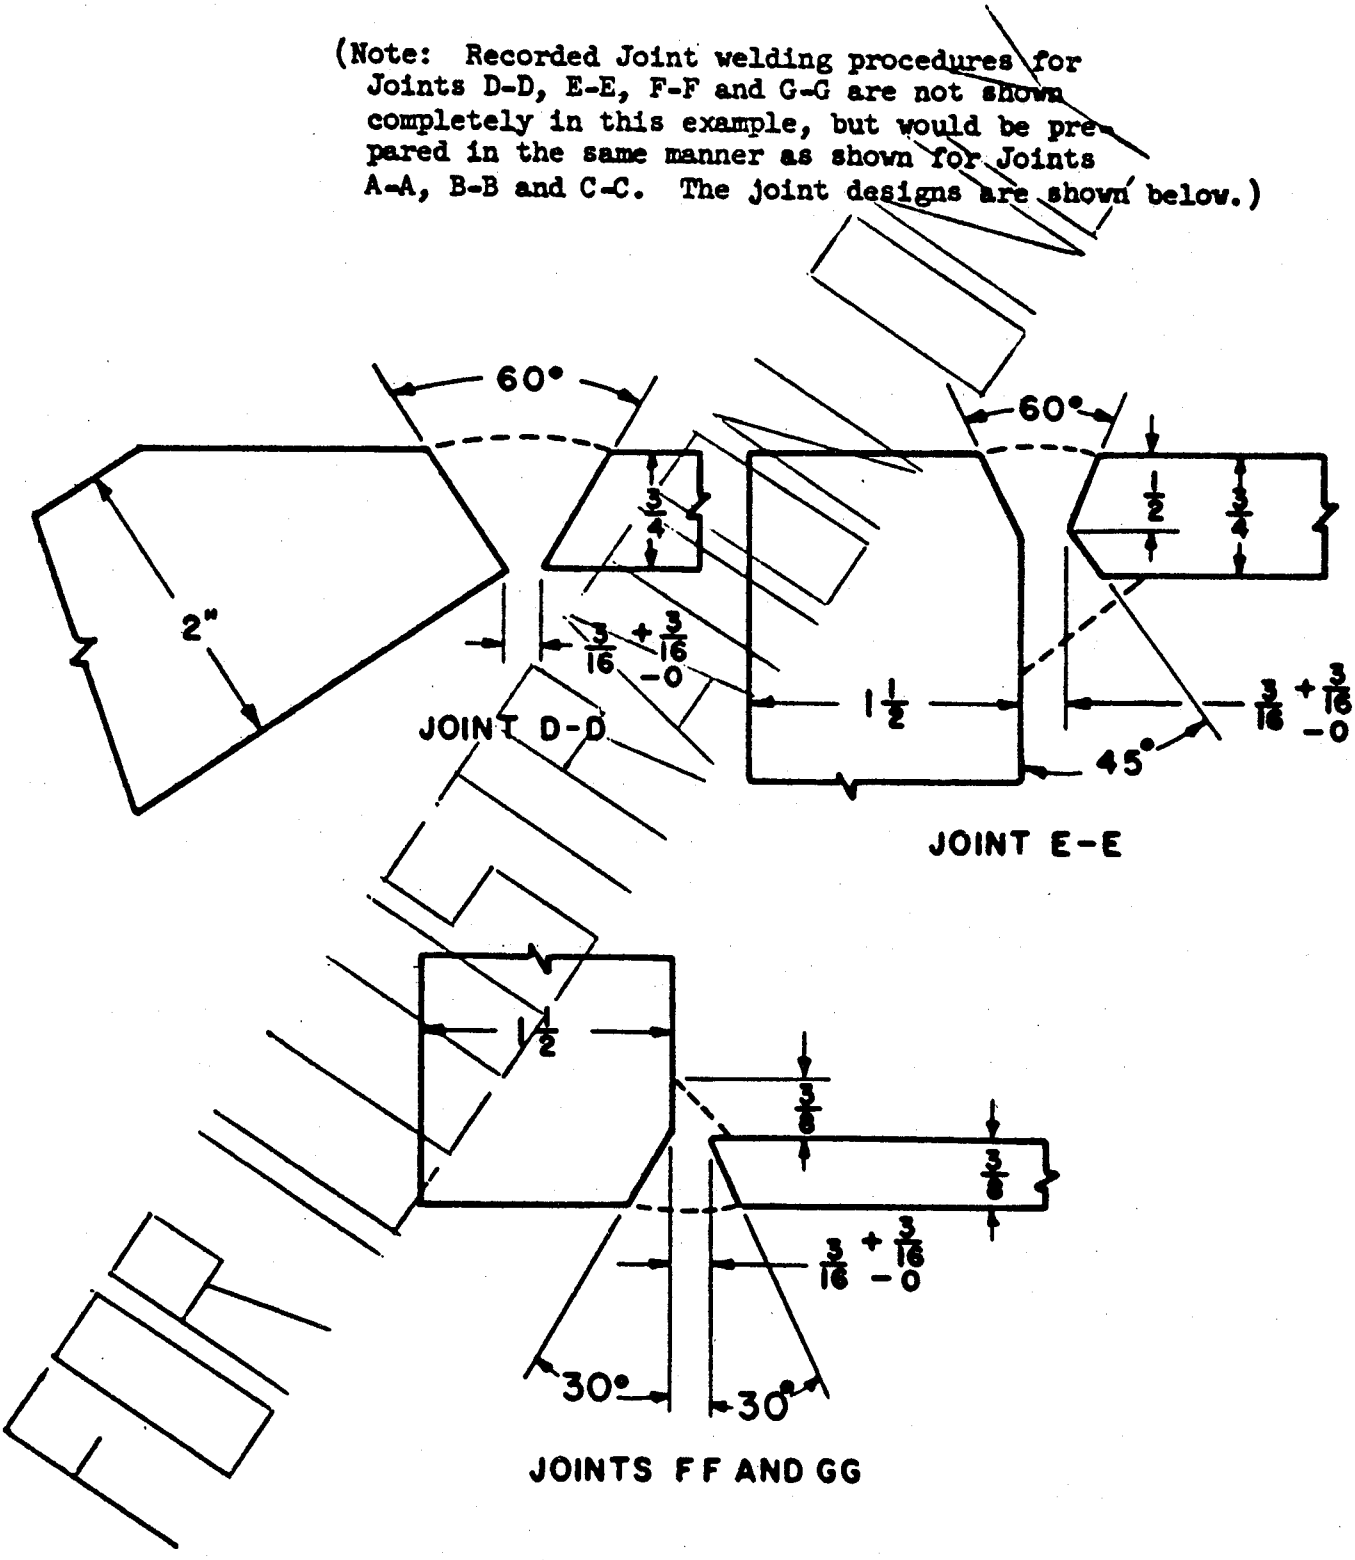


FIGURE 10. Recorded joint welding procedure for joints D-D, E-E, F-F and G-G.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

Recorded Joint Welding Procedure No. 8 a

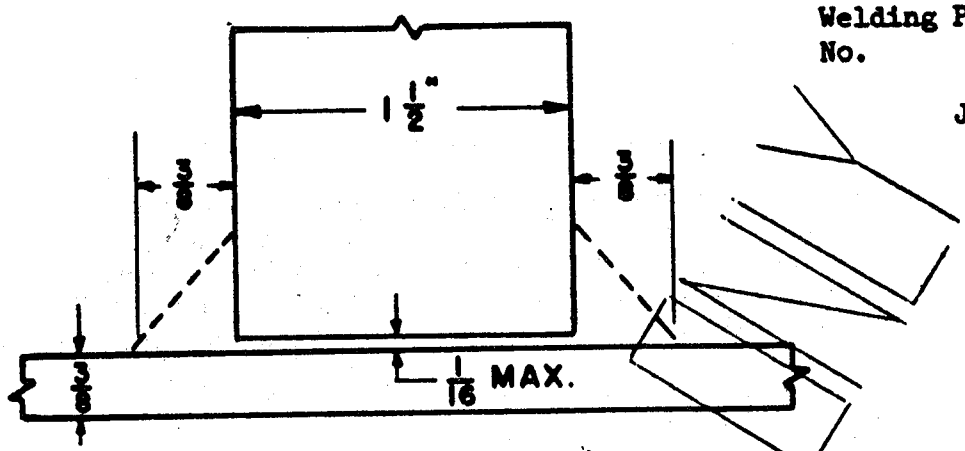Joint H-H



Joint Welding Procedure: General Information

Armor (reference designation)	II
Electrode (reference designation)	A or E
Power Source (AC or DC) and Polarity if DC	DC, Reverse
Welding Current & Arc Voltage Range	As Specified in Table C, Figure 6
Use of Spatter Compound on Scarfed Edges	None
Backing	----
Preheating	None
Position of Welding	Flat

Joint Welding Procedure: Details of


Pass No.	Electrode Size	Type of Pass	Location & Sequence of Passes
1	1/4	Weave	

FIGURE 11. Recorded joint welding procedure No. 8a Joint H-H.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

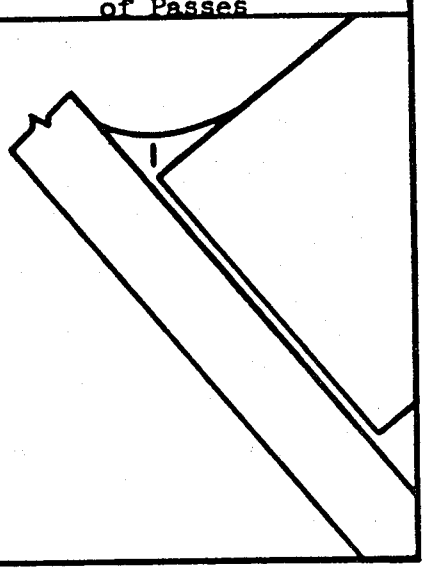Recorded Joint Welding Procedure No. 8 B

Joint H-H

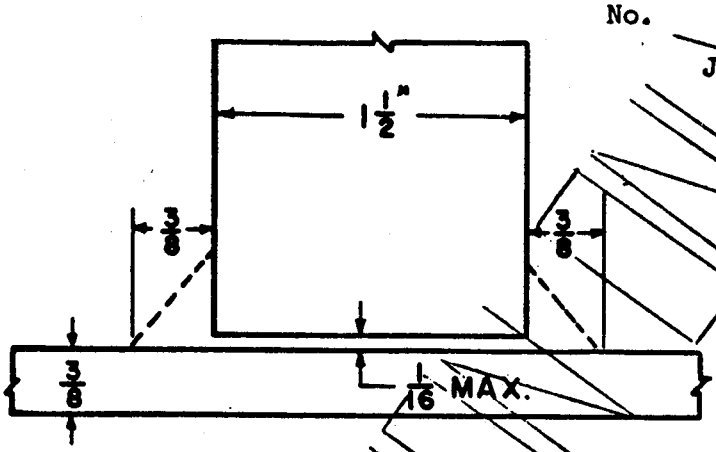
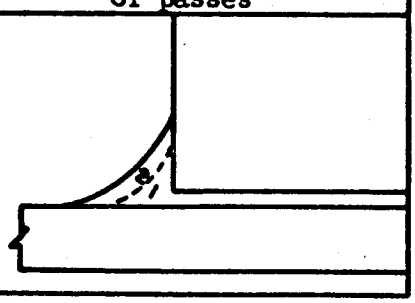


Figure 6

Joint Welding Procedures: General Information

Armor (reference designation)	II
Electrode (reference designation)	A or E
Power Source (AC or DC) and Polarity if DC	DC, Reverse
Welding Current & Arc Voltage Range	As Specified in Table C.
Use of Spatter Compound on Scarfed Edges	None
Backing	----
Preheating	None
Position of Welding	Horizontal

Joint Welding Procedure: Details of

Pass No.	Electrode Size	Type of Pass	Location & Sequence of passes
1	3/16	Stringer	
2	3/16	Weave	

(Note: Recorded Joint Welding Procedures are not shown for Joint H-H in the vertical position and Joint J-J in the flat, horizontal and vertical positions: but would be prepared in the same manner as illustrated for Joint H-H in the flat and horizontal positions.)

FIGURE 12. Recorded joint welding procedure No. 8b Joint H-H.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

THIS FORM MAY BE REPRODUCED FOR USAGE

ARMOR WELDING DATA SHEET #1	REPORT No.
	SHEET No. of

WELDED ARMOR DATA

Plate No.	SUBMITTED BY
DATE	
TYPE	ADDRESS
THICKNESS	
SPECIFICATION	CONTRACT NO.
ORDNANCE MATERIAL CONCERNED	
WELDED BY	
OBJECT	

On a dimension sketch of the groove and Weldment, Indicate:(1) the included angle: (2) the root opening; (3) the root face; (4) the bead sequence; (5) additional sketch of spacer strip on back-up, if any; (6) width of marking, if any on edges of cast plate; (7) average height of weld reinforcement

Weld reinforcement (has) (has not) been removed.

WELDING DATA

PLATE PREPARATION - Flame cutting - Flame softening - Grinding - Machining

POSITION OF WELDING: Flat - Horizontal - Vertical - Overhead

WELDING: Automatic - Hand - POLARITY: - Str - Rev - AC -DC

PREHEAT POSTHEAT

PEENING BUTTERING

PASS	ELEC SIZE	TYPE PASS	AMPS	VOLTS	CRACKING	CHIP OR GRIND	SPEED IN/IN.	INTERPASS.TEMP.(F) A-B	C-D	E-F-G
1										
2										
3										
4										
5										
6										
7										
8										
9										
10										
11										
12										
13										
14										
15										
16										

B - BEADING PASS W- WEAVING PASS

Figure 13. Armor Welding Data Sheet No. 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

THIS FORM MAY BE REPRODUCED FOR USAGE

ARMOR WELDING DATA SHEET # 2	REPORT No. SHEET No. of

ARMOR PLATE DATA

TEST PLATE No.

	PLATE "A"	PLATE "B"
MANUFACTURER		
TYPE		
THICKNESS		
HEAT		
LOT		
PROCESS	O.H. ELEC ACID BASIC	O.H. ELEC ACID BASIC

CHEMICAL COMPOSITION

	C	Mn	Si	P	S	Cr	Ni	Mo	Zr	V	FACE	BACK
PLATE "A"												
PLATE "B"												

HEAT TREATMENT DATA

HEAT TREATED BY

TABLE 1 ELECTRODE OR FILLER METAL DATA

SIZE	Manufacturer	Trade Name	Type	Class

TABLE 2

MANUFACTURER TRADE NAME AND SIZE	CHEMICAL ANALYSIS								
		C	Mn	Si	S	P	Cr	Ni	Mo	COATING
	CORE WIRE									
	WELD METAL									
	CORE WIRE									
	WELD METAL									
	CORE WIRE									
	WELD METAL									
	CORE WIRE									
	WELD METAL									

TABLE 3 (AUTOMATIC WELDING)

MANUFACTURER	TRADE NAME	SIZE	FLUX

RADIOGRAPHED BY

RADIOGRAPH SERIAL No.

REMARKS: The procedure used in fabricating the crossbar weld (is) (is not) the same as the procedure used in fabricating the leg welds.

FABRICATOR REPRESENTATIVE	RESIDENCE INSPECTOR OF ORDNANCE

Figure 14. Armor Welding Data Sheet No. 2.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

THIS FORM MAY BE REPRODUCED FOR USAGE

ARMOR WELDING DATA SHEET # 3	(1) REPORT No. SHEET No. of

(2) X-RAY SERIAL NO.

WELD RADIOGRAPHIC REPORT

(3) PLATE SUBMITTED BY			(4) Plate No.	(5) SPEC
(6) RADIOGRAPH BY				(7) DATE
(8) PLATE THICKNESS	(9) KV	(10) MA		(11) TIME
(12) FOCAL DIST.	(13) TYPE OF FILM			(14) SCREEN OR FILTERS

SHOCK TEST PLATE

Showing Locations of Radiographs and Results of Tests

(15) CRACK INCOMPELTE FUSION INCOMPLETE PENETRATION
POROSITY AND SLAG INCLUSIONS UNCERCUTTING

(16) RESULTS

(17) NEGATIVES READ BY

Figure 15. Armor Welding Data Sheet No. 3.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

APPENDIX B

EVALUATION OF WELDOR CAPABILITY

40. SCOPE

40.1 Scope. This appendix covers the minimum requirements for evaluation by the contractor or manufacturer of the capability of weldors to perform under the requirements of this specification.

50. REQUIREMENTS

50.1 Weld type. Each weldor shall demonstrate his capability to weld groove or fillet welds or both by fabricating the specimens shown in figures 20, 21 and 22, as applicable.

50.2 Position of weld. Each weldor shall demonstrate his capability in the position in which he will weld in production by welding the test specimens in the positions prescribed in 50.2.1.1 through 50.2.1.4. Weldors found acceptable in one or more positions will be considered acceptable in other positions under the conditions specified in table I.

TABLE I. Weldor evaluation with the "K" qualification plate1/

"K" plate position	Qualified in groove welds in the following positions				Qualified for fillet welds in the following positions2/			
	Flat	Horiz	Vert	OH	Flat	Horiz	Vert	OH
Flat	Yes	No	No	No	Yes	Yes	No	No
Horizontal	Yes	Yes	No	No	Yes	Yes	No	No
Vertical	Yes	Yes	Yes	No	Yes	Yes	Yes	No
Overhead	Yes	Yes	No	Yes	Yes	Yes	No	Yes

1/ See figure 21.

2/ For fillet welds only, "K" joint qualification is not required (see 50.2.2).

50.2.1 Groove welds.

50.2.1.1 Flat position. The plates shall be placed in an approximately horizontal plane, and the weld metal deposited from the upper side.

50.2.1.2 Horizontal position. The plates shall be placed in an approximately vertical plane with the welding groove in an approximately horizontal position.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

50.2.1.3 Vertical position. The plates shall be placed in an approximately vertical plane with the welding groove in an approximately vertical position, approximately 90° to the horizontal plane.

50.2.1.4 Overhead position. The plates shall be placed in an approximately horizontal plane, and the weld metal deposited from the underside.

50.2.2 Fillet welds only. The weldor for fillet welds only shall fabricate a specimen in accordance with figure 23. The arrangement of the test plates for the various positions refers only to the making of the fillet weld. The closing weld (cross hatched in figure 23) between fillet welds may be made in any position as follows:

a. The welding of plates so placed that each fillet weld is deposited with its axis approximately horizontal and its throat approximately vertical will determine the capability of weldors for flat fillet welds.

b. The welding of plates so placed that each weld is deposited on the upper side of the horizontal surface and against the vertical surface will determine the capability of weldors for flat and horizontal fillet welds.

c. The welding of plates so placed that each weld is made vertically will determine the capability of weldors for flat, horizontal and vertical fillet welds.

d. The welding of plates so placed that each weld is deposited on the under side of the horizontal surface and against the vertical surface will determine the capability of weldors for flat, horizontal, and overhead fillet welds.

50.2.3 Radiography of welds. The completed weld shall be radiographed and shall comply with the following standards:

For full penetration welds: Grade II of MIL-STD-1264 with the direction of radiation parallel to the weld interface, then normal to the weld face, and finally parallel to the opposite weld interface.

For partial penetration welds: ATAC-STD-114.

In either case defects within 1 in. (25.4 mm) of either end of the weld shall not be regarded as cause for rejection. Radiographic negatives shall be suitably identified and returned for Government inspection, when requested.

50.2.4 Materials. Specimens may be made of either mild steel or armor.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

50.2.5 Electrodes. The electrodes for groove or fillet welds shall conform to the type of electrode for method 1, 2, 3 or 4 of this specification (see 1.2) as applicable. The diameter of electrode used for any layer of a groove weld shall be the maximum diameter that will be used for that width in the recorded joint-welding procedure.

50.2.6 Workmanship. Welds shall be equal to, or better than, the workmanship specimens prepared for the recorded joint-welding procedures.

60. INSPECTION

60.1 Test specimens.

60.1.1 Groove welds. Groove welds shall be fabricated to the form and dimensions shown in figure 21 or 22, as applicable, using the same welding current values for the electrodes that would be used in the recorded joint-welding procedures. When the thickness of the plates in the structure does not exceed 1/2 in. (12.7 mm), the specimen shall be as shown in figure 21 and the two plates shall be 3/8 by 4 by 12 in. (9.5 by 102 by 305 mm) with the butt weld made on the 12 in. (305 mm) dimension. When the thickness of the plates to be welded exceeds 1/2 in. (12.7 mm) the specimen shall be as shown in figure 22 and the two plates shall be 1 by 4 by 12 in. (25.4 by 102 by 305 mm). All dimensions shall be considered minimum. Weldors capable of welding the 1 in. (25.4 mm) plates do not have to weld the 3/8 in. (9.5 mm) plates.

60.1.2 Fillet welds. The specimen shall be of the form and dimensions shown in figure 23.

60.2 Inspection procedures.

60.2.1 Visual. Visual examination of the weld shall be made for compliance with the workmanship requirement (see 50.2.6).

60.2.2 Radiographic. Welds shall be radiographed in accordance with MIL-STD-453.

70. FACTORS IN THE JOINT-WELDING PROCEDURE

70.1 Factors to be included in the joint-welding procedure and changes requiring resubmittal of the procedure and requalification of weldors. Factors to be included in the joint-welding procedure and changes requiring resubmittal of the procedure and requalification of weldors shall be as specified in table II.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

TABLE II. Requirements for the joint-welding procedure[1/]

Factors to be included in joint-welding procedure	When factor is changed, joint-welding procedure to be revised and procedure requalified, as indicated	When factor is changed, weldor to be requalified, as indicated
1. Composition of armor.	Yes - When a change in composition outside the steel producer's declared chemical range is made, unless a specific waiver is granted by the procuring activity.	No.
2. Thickness of armor for each joint type.	Yes - When the maximum or minimum thickness for the joint type represented by the procedure qualification plates tested for representation of the joint type is exceeded (see table III).	Yes (see 60.1.1).
3. Dimensions of root opening, root face and included angle for each joint type. Each dimension shall have a specified tolerance.[2/]	Yes - When established limits are increased or decreased, i.e., basic dimensions plus tolerances.	No.
4. Backing or spacer strip, if used.	Yes - When backing or spacer strip is added or removed, or when basic type of material of backing or spacer strip is changed.	Yes - When backing or spacer strip is removed.
5. Position in which welding will be performed.	Yes.	Yes (see 50.2.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

TABLE II. Requirements for the joint-welding procedure (cont'd)

Factors to be included in joint-welding procedure	When factor is changed, joint-welding procedure to be revised and procedure requalified, as indicated	When factor is changed, weldor to be requalified, as indicated
6. Electrode type and class if not qualified under MIL-E-13080, MIL-E-22200/1, MIL-E-22200/6, or MIL-E-23765/2. Electrodes should be designated as SMAW or GMAW, as appropriate.	Yes - when the brand used for procedure qualification has been recorded but does not meet the requirements of MIL-E-13080, MIL-E-22200/1, MIL-E-22200/6, or MIL-E-23765/2; substitution of any other brand will require requalification of procedure. However, when the brand used for procedure qualification has met the requirements of MIL-E-13080, MIL-E-22200/1, MIL-E-22200/6, or MIL-E-23765/2 for a specific type and class, and provided that all other factors remain the same, any other brand that has met the requirements of the foregoing specifications for the same type and class and may be substituted without qualification of procedure.	No.
7. Electrode sizes[3]/ for all passes.	Yes - when (for groove welds) the actual width of groove, at which any given size of electrode is used, is decreased; or (for fillet welds) when the diameter used at any given distance from the root of the weld is increased.	Yes - when (for groove welds) the actual width of groove, at which any given size of electrode is used, is decreased; or (for fillet welds) when the diameter used at any given distance from the root of the weld is increased.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

TABLE II. Requirements for the joint-welding procedure (cont'd)

Factors to be included in joint-welding procedure	When factor is changed, joint-welding procedure to be revised and procedure requalified, as indicated	When factor is changed, weldor to be requalified, as indicated
8. Welding current[4/] and arc-voltage range for all passes (see 8.4).	Yes - When outside the limits established in the recorded joint-welding procedure (either above or below).	Yes - When outside the limits established in the recorded joint-welding procedure (either above or below)
9. Preheat and interpass temperature range (see 4.1.1).	Yes - When the range is changed.	No.
10. Location, type and approximate number of passes.	Yes - In case of change from beading to weaving, or vice versa.	No.
11. Method of preparing root of joint before welding second side.	Yes.	No.
12. Source of power, AC or DC, and polarity if DC is used.	Yes.	No.
13. Spatter compound.	Yes - When spatter compound is used on any area where weld metal is to be deposited.	No.
14. Temperature of plate at time welding is started and method of attaining temperature.	Yes - When ambient or preheat temperature is more than 20°F (11.2°C) below that of the test plate. No - When method of attaining temperature is changed.	No.
15. Shielding medium type.	Yes - when changing to another medium.	Yes.
16. Composition, volume, and dew point of the shielding gas.	Yes.	No.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

TABLE II. Requirements for the joint-welding procedure (cont'd)

Factors to be included in joint-welding procedure	When factor is changed, joint-welding procedure to be revised and procedure requalified, as indicated	When factor is changed, weldor to be requalified, as indicated
17. Method of joint edge preparation.	No - When method changes from thermal to mechanical (machining or grinding).	No.

1/ Additional factors for repair welding:

a. Method to be used (grinding or other) for removal of the defect.
b. Contour of cavity prior to welding, such as minimum root dimension and included angle.
c. Use of backing or spacer strip, in case of complete removal of the weld.
d. Inspection method to determine complete removal of defect (dye penetrant, magnetic particle, visual, radiographic, etc.).

2/ Root opening. It should be noted that MIL-STD-21 provides for minimum root openings ranging from 3/16 to 1/2 in. (4.8 to 12.7 mm). In all cases, these root openings are known as "design openings". In other words, they are the root openings which would exist after completion of the weld if the root face had not melted away. This type of root-opening dimension is used because it can be shown on assembly drawings and still permit the addition of plate dimensions plus root-opening dimensions to give the correct over-all dimension for the structure. The "design opening" is not ordinarily the root opening which is actually visible before welding, since this opening must include an increase for the amount of contraction across the joint during welding. Thus, this root opening, sometimes known as the "set-up opening", equals the "design opening" plus the shrinkage allowance.

3/ Option on electrode size. The contractor shall specify in his recorded joint-welding procedure the diameter of the electrode to be used for deposition of the root pass in each width of root opening from the minimum to the maximum. A contractor may specify that a 1/8 in. (3.2 mm) electrode shall be used for the minimum root opening of 3/16 in. (4.8 mm) and that a 3/16 in. (4.8 mm) electrode shall be used for a root opening of 1/4 to 1/2 in. (6.4 to 12.7 mm). In the operation of the procedure, the contractor may use a smaller diameter of electrode than that specified for the particular root opening, but he may not use an electrode larger than that specified without requalifying his procedure. The contractor may not use a 3/16 in. electrode for the 3/16 in. minimum root opening when a 1/8 in. (3.2 mm) electrode has been specified in his recorded joint-welding procedure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

4/ Current values. Welding current may be measured with a tong-type tester. Current variations for all types and sizes of electrodes shall be limited to approximately ± 15 percent.

80. REQUIREMENTS FOR BALLISTIC TEST PLATES, BALLISTIC TESTS AND WORKMANSHIP SPECIMENS

80.1 Thickness of ballistic test plates. Thickness of ballistic test plates shall be as specified in table III.

TABLE III. Thickness of ballistic test plates

Maximum or minimum "T" thickness of plate in joint: in. (mm)	Thickness of ballistic test plate: in. (mm) 1/,2/,4/
1/8 to 3/4 (3.2 to 19.0)	1/2 (12.7)3/
3/4 to 1-1/8 (19.1 to 28.6)	1 (25.4)
Greater than 1-1/8 (28.6)	1-1/2 (38.1)

1/ For cast and rolled armor, thickness tolerances shall not exceed plus or minus 0.030 in. (0.76 mm).

2/ Before welding, cast or rolled plates 18 by 40 in. (46 by 102 cm), or smaller, shall have a maximum out-of-flatness tolerance of 1/16 in. (1.6 mm) in any direction. Plates 36 by 36 in. (91.4 by 91.4 cm) shall have a maximum out-of-flatness tolerance of 1/8 in. (3.2 mm) in any direction.

3/ For cast armor 1 in. (25.4 mm) plate shall be used.

4/ Ballistic test plate thickness may equal the armor thickness for production use provided it is no less than 1/2 in. (12.7 mm) nor more than 2 in. (50.8 mm). Striking velocities shall be adjusted in accordance with Footnotes 1(a) and 1(b) of table IV. A 1/2-in. (12.7 mm) thick plate shall be submitted for production plates thinner than the 1/2 in. (12.7 mm) nominal size, and a 1-1/2 in. (38.1 mm) shall be submitted for production plates thicker than the 2-in. (50.8 mm) nominal size.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

80.2 Requirements for ballistic tests. Requirements for ballistic tests shall be as specified in table IV.

TABLE IV. Requirements for ballistic tests

Thickness of plate, in. (mm)	Type of homogeneous armor	Projectile	Striking velocity f/s ± 25 f/s (m/s ± 7.6 m/s)1/	Maximum allowable weld cracking, in. (mm)2/
1-1/2 (38.1)	Rolled	75 mm PP M1002	1200 (365.8)	15 (381)
1-1/2 (38.1)	Cast	75 mm PP M1002	1050 (320)	10 (254)
1 (25.4)	Rolled	57 mm PP M1001	1050 (320)	9 (228.6)
1 (25.4)	Cast	57 mm PP M1001	975 (297)	6 (152.4)
1/2 (12.7)	Rolled	37 mm HE M54	2525 (770)	15 (381)

1/ If the actual plate thickness is more than the nominal thickness, the test striking velocity shall be increased. If the actual plate thickness is less than the nominal thickness, the test striking velocity shall be decreased.

a. For cast armor only the correction factor shall be 6 f/s (1.83 m/s) of velocity for each 0.01 in. (0.25 mm) deviation in plate thickness.

b. For rolled armor only the correction factor shall be 7 f/s (2.13 m/s) velocity for each 0.01 in. (0.25 mm) deviation in plate thickness.

2/ Typical crack situations are illustrated in Figure 17.

80.3 Size of workmanship specimen. Workmanship specimen sizes shall be as specified in table V.

TABLE V. Workmanship specimen sizes

Plate thickness, in. (mm)	Minimum plate size, in. (mm)
1/8 to 1-1/4 (3.2 to 31.8) incl	4 by 12 (102 by 305)
greater than 1-1/4 (31.8)	4 by 16 (102 by 406)

80.4 Weldor requalification requirements.

a. If the weldor has not welded for the period of 1 month (20 working days or 30 calendar days) or longer, the weldor must requalify in the position the welding is to be performed in.

b. If the weldor has three consecutive rejected welds or weld repairs, the weldor must requalify.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.



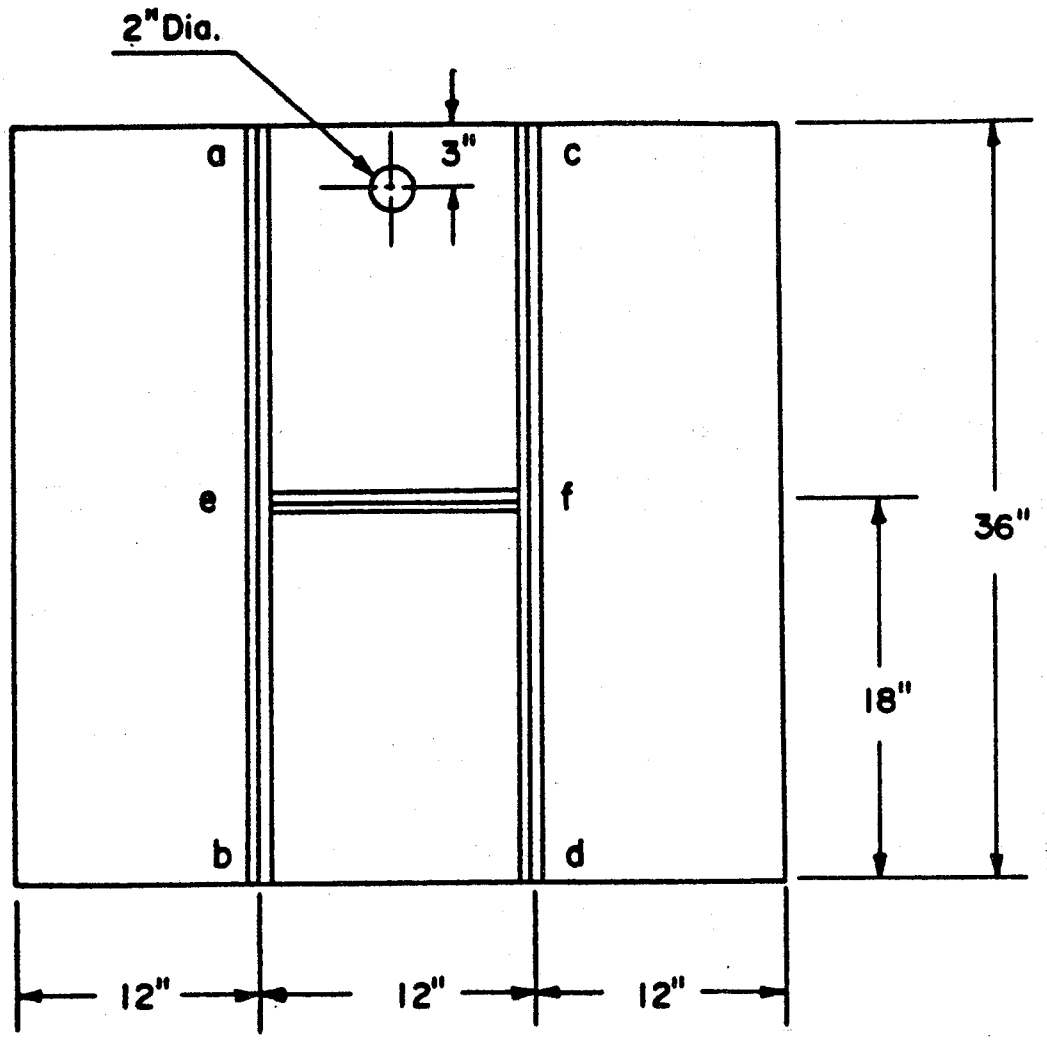


FIGURE 16. Ballistic test plate.

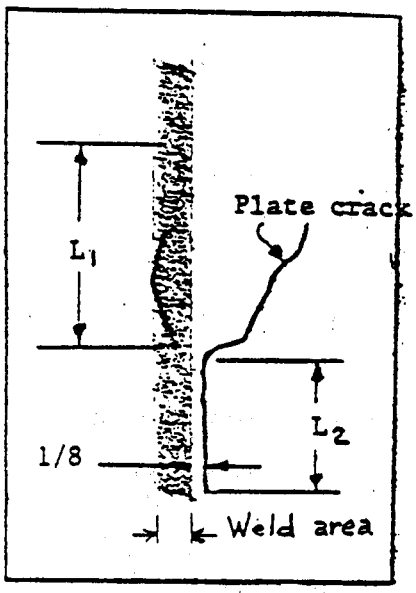
Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.




TOTAL W.C. = $L_1 + L_2$

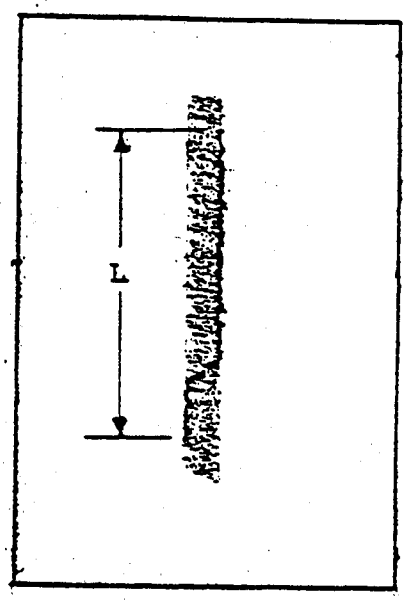


TOTAL W.C. = L

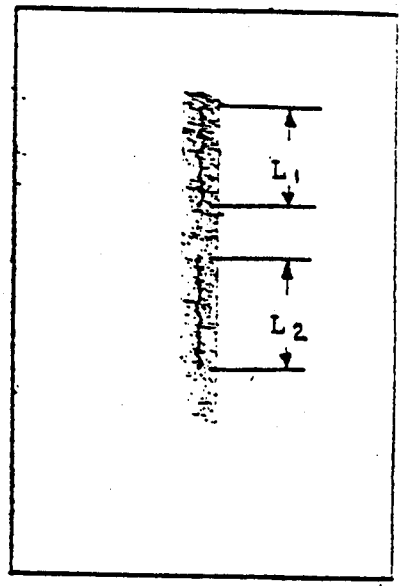


TOTAL W.C. = $L_1 + L_2$

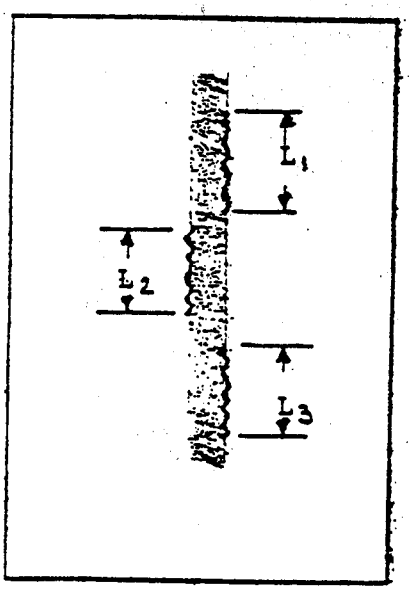

TOTAL W.C. = $L_1 + L_2 + L_3$

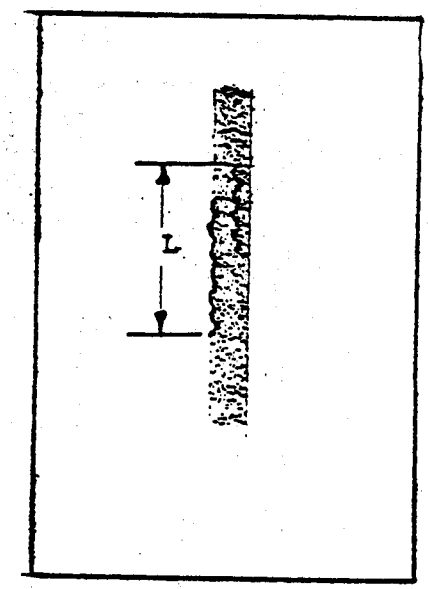

TOTAL W.C. = L

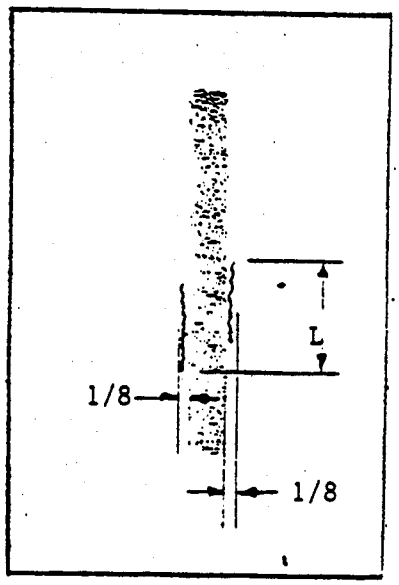

TOTAL W.C. =L

Figure 17. Some weld cracks (W.C.) which could occur from projectile impact, and measurement of total W.C. for acceptance purposes (See Table IV).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

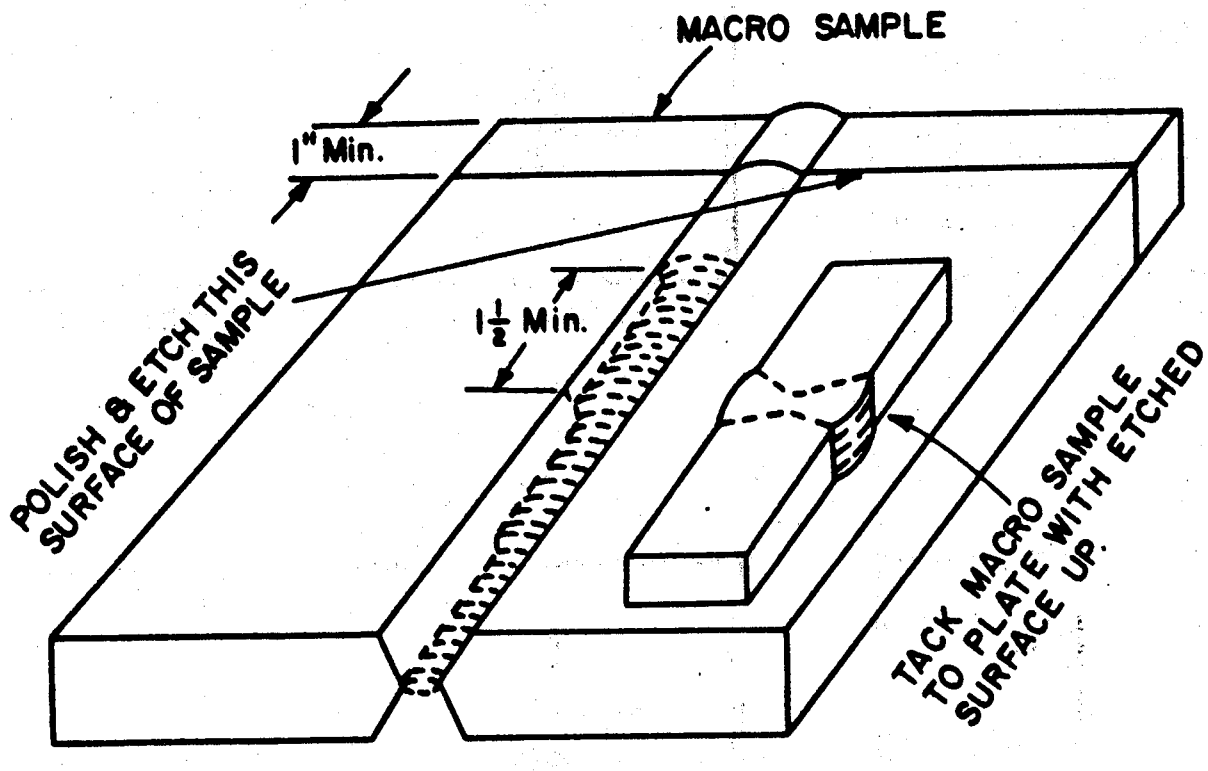


FIGURE 18. General form of workmanship specimen for joint types 1, 2 and 3.

Note: Joint type No. 3 is illustrated. However, groove details of actual specimens shall conform to details of contractor's recorded joint welding procedure for each type of joint involved.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

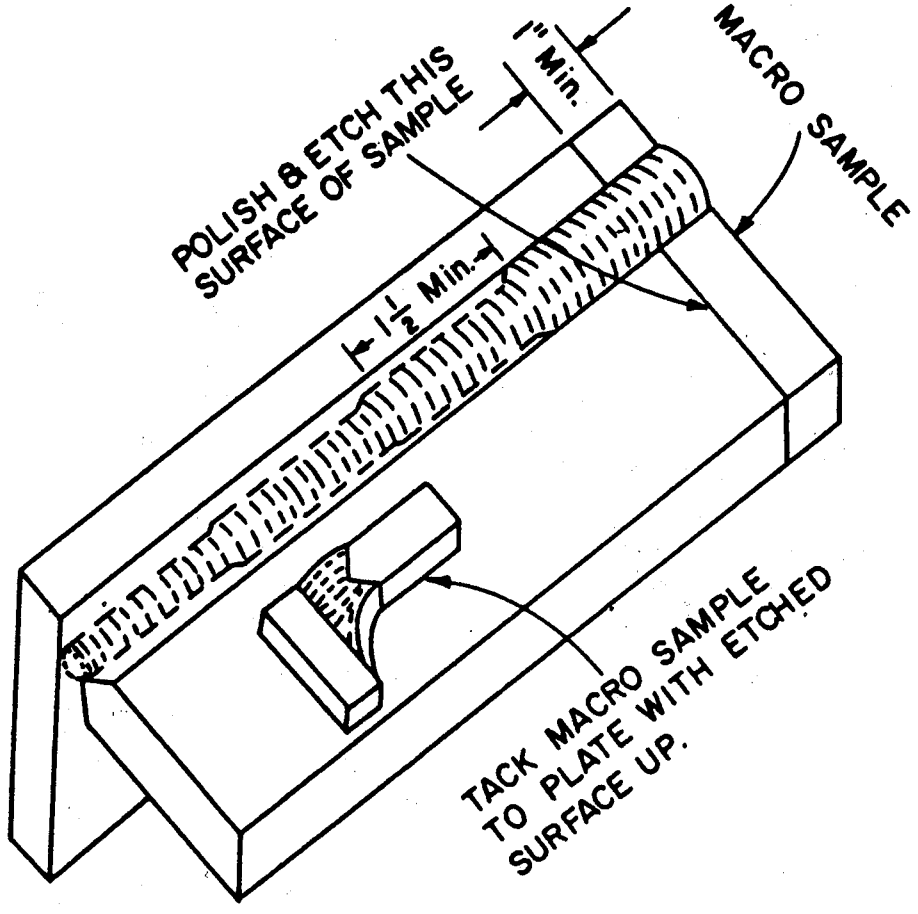


FIGURE 19. General form of workmanship specimen for joint types 4, 5, 6 and 7.

Note: Joint type No. 5 is illustrated. However, groove details of actual specimens shall conform to details of contractor's recorded joint welding procedure for each type of joint involved.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

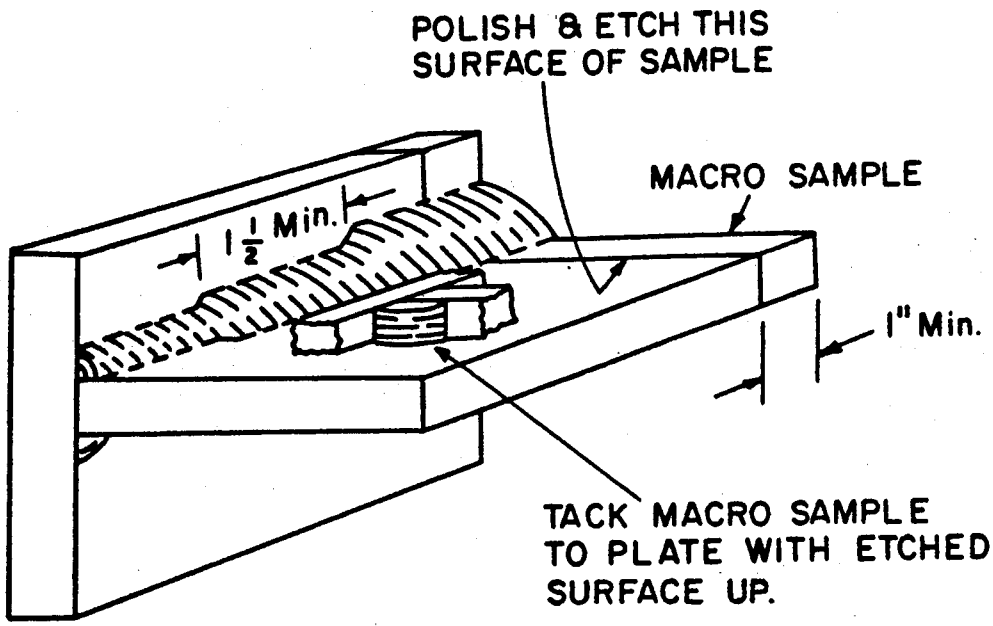


FIGURE 20. General form of workmanship specimen for joint types 8 and 9.

Note: Type 9 is illustrated. However, groove details of actual specimens shall conform to details of contractor's recorded joint welding procedure for each type of joint involved.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

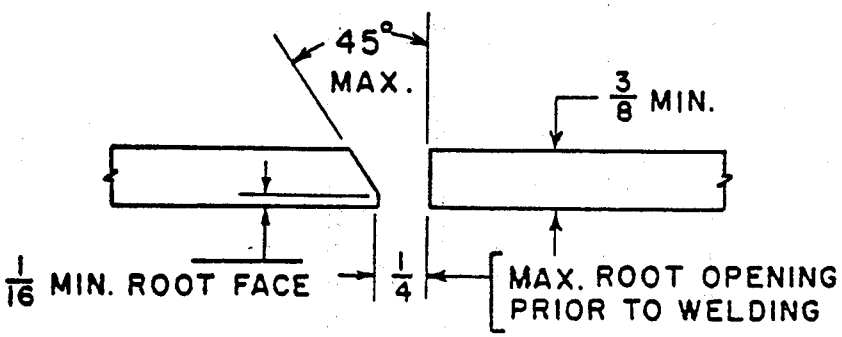


FIGURE 21. Groove weld test specimen for qualification of weldors or welding operators - for plate thickness of 0.5 in. (12.7 mm) or less.

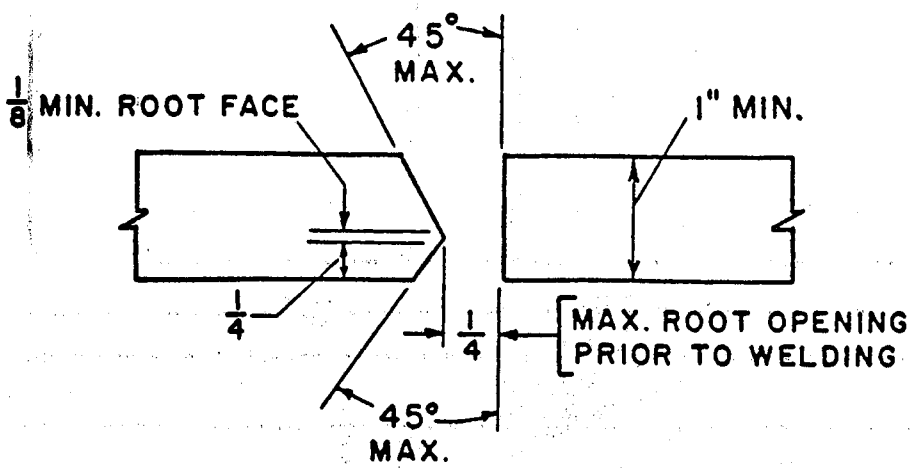


FIGURE 22. Groove weld test specimen for qualification of weldors or welding operators - for plate thickness of more than 0.5 in. (12.7 mm).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.

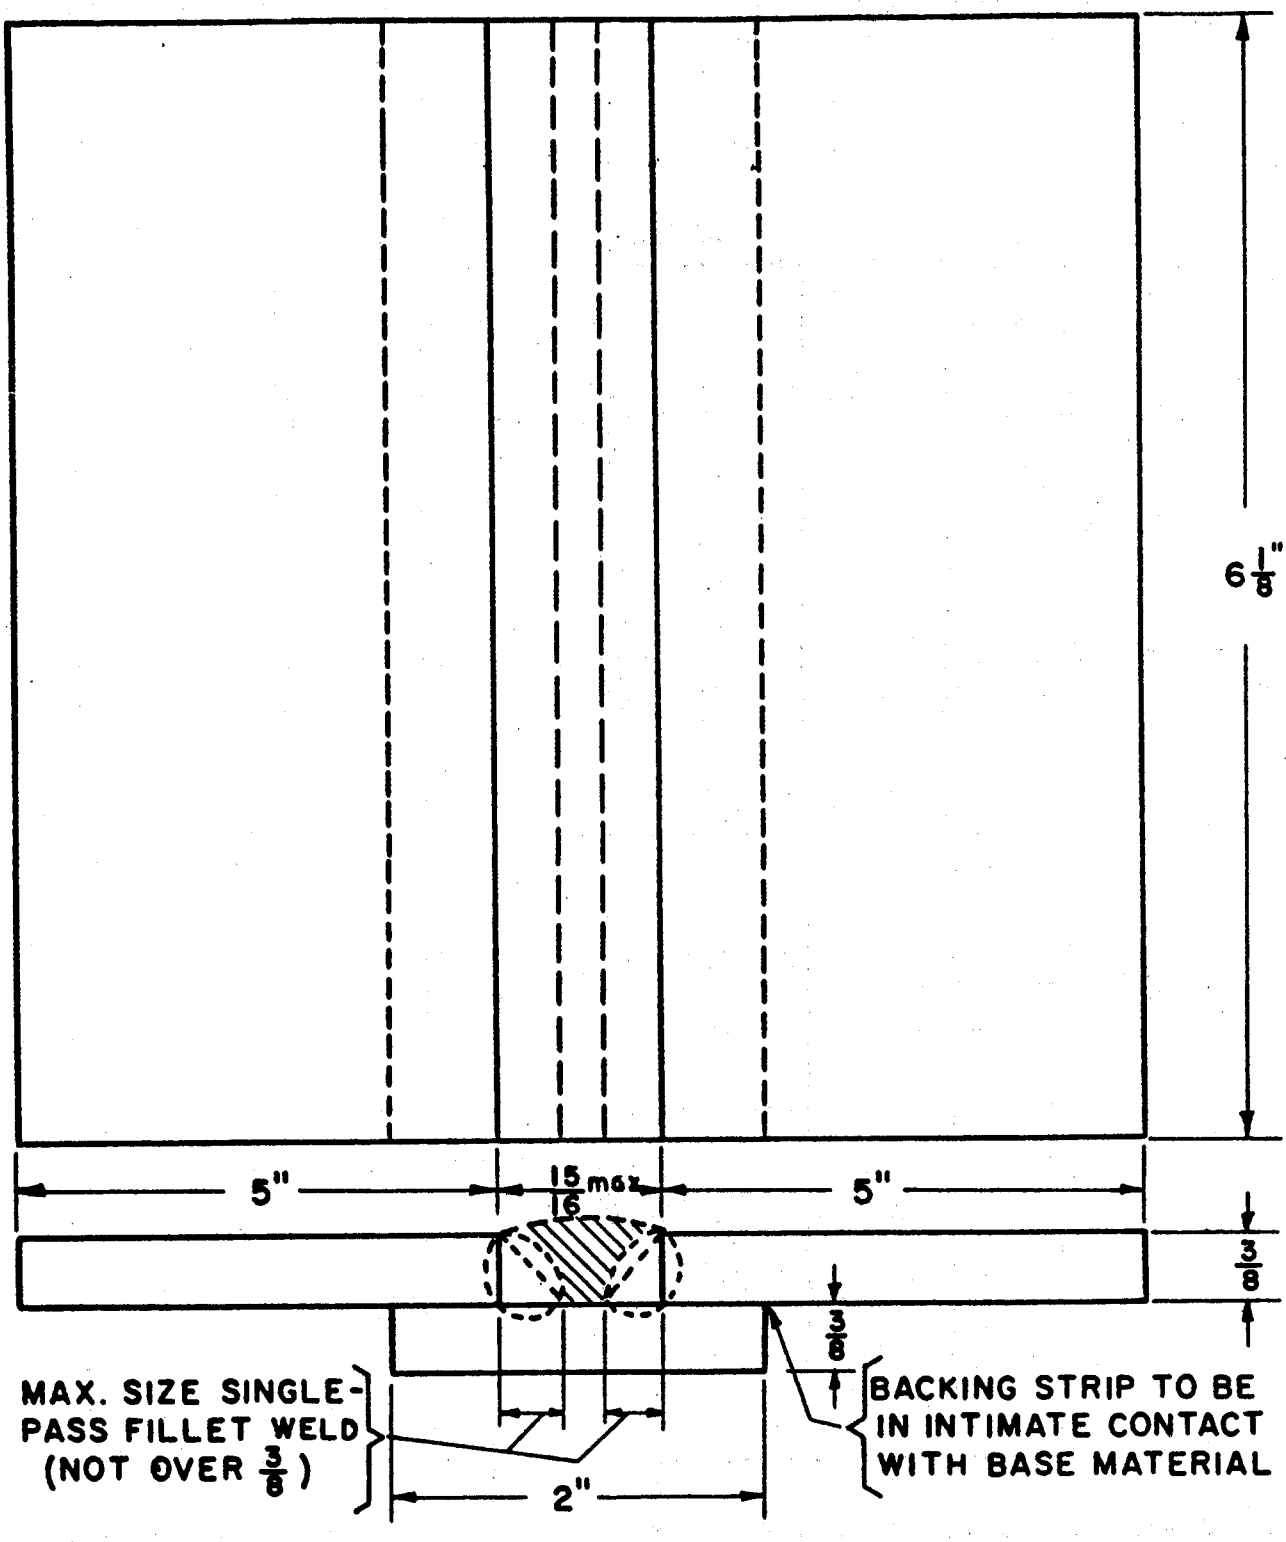


FIGURE 23. Fillet weld test specimen for qualification of weldors or welding operators.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T07:55Z
Check the source to verify that this is the current version before use.