INCH-POUND

MIL-B-82800(OS)
5 February 1990
SUPERSEDING
WS 21188
8 November 1983
(See 6.6)

MILITARY SPECIFICATION

BROADGOODS, GRAPHITE CLOTH, PHENOLIC-PREIMPREGNATED

This specification is approved for use by the Naval Sea Systems Command, Department of the Navy and is available for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 **Scope.** This specification defines one type of graphite cloth broadgoods preimpregnated with phenolic resin, referred to herein as the cloth (see 6.1).

2. APPLICABLE DOCUMENTS

2.1 **Government documents.**

2.1.1 **Specifications, standards and handbooks.** The following specifications, standards and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation (see 6.2).

STANDARDS

MILITARY

MIL-STD-129 Marking for Shipment and Storage

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commanding Officer, Naval Ordnance Station, Standardization Branch (3730), Indian Head, MD 20640-5000, by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 1340

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

MILITARY

MIL-R-9299 Resin, Phenolic, Laminating

MIL-R-82814 Reinforcement, Graphite

(Unless otherwise indicated, copies of federal and military specifications, standards and handbooks are available from: Military Specifications and Standards, Bldg. 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.1.2 **Other Government documents, drawings, and publications.** The following other Government documents, drawings, and publications form a part of this document to the extent specified herein. Unless otherwise specified, the issues are those cited in the solicitation.

CODE OF FEDERAL REGULATIONS (CFR)

49 CFR 100-199 Transportation

(Application for copies of CFRs should be addressed to the Superintendent of Documents, U. S. Government Printing Office, Washington, D.C. 20402-0001.)

2.2 **Non-Government publications.** The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation (see 6.2).

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM C 177 Steady-State Heat Flux Measurements and Thermal Transmission Properties by Means of the Guarded Hot-Plate Apparatus (DoD adopted)

ASTM C 613 Resin Content of Carbon and Graphite Prepregs by Solvent Extraction (DoD adopted)

ASTM D 695 Compressive Properties of Rigid Plastics (DoD adopted)

ASTM D 740 Methyl Ethyl Ketone (DoD adopted)

ASTM D 790 Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials (DoD adopted)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

ASTM E 228 Linear Thermal Expansion of Solid Materials with a Vitreous Silica Dilatometer (DoD adopted)

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103-1187.)

AMERICAN TRUCKING ASSOCIATION, INC.

National Motor Freight Classification

(Application for copies should be addressed to the American Trucking Association, Inc., Attn: Traffic Dept., 2200 Mill Road, Alexandria, VA 22314-4677.)

NATIONAL RAILROAD FREIGHT COMMITTEE

Uniform Freight Classification (UFC) 6000

(Application for copies should be addressed to the National Railroad Freight Committee, 222 South Riverside Plaza, Suite 1120, Chicago, IL 60606-5945.)

(Non-Government standards and other publications are normally available from the organizations that prepare or distribute the documents. These documents also may be available in or through libraries or other informational services.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), a sample shall be subjected to first article inspection (see 6.3) in accordance with 4.3.

3.2 Material. The cloth shall be woven graphite cloth broadgoods impregnated with a carbon-filled phenolic resin.

3.2.1 Reinforcement. The reinforcement shall be a graphite fabric conforming to MIL-R-82814.

3.2.2 Resin Filler. The resin filler shall be carbon black with a minimum carbon assay of 90 percent.

3.2.3 Resin. The resin system shall conform to MIL-R-9299, Grade A.

3.3 Uncured and cured material physical and mechanical properties.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

3.3.1 **Uncured material physical properties.** The physical properties of the uncured cloth shall conform to the requirements specified in table I.

TABLE I. Uncured material physical properties.

Property	Percent by Weight	
	Minimum	Maximum
Cloth content	47.0	57.0
Resin solids, dry weight	32.0	37.0
Filler content	5.0	16.0
Resin flow	8.0	18.0
Volatile content	2.5	4.0

3.3.2 **Cured material physical and mechanical properties.** The physical and mechanical properties of the cured cloth shall conform to the requirements specified in table II.

3.4 **Age of material.** The cloth shall be shipped within 3 months after the manufacturing date and shall be tested and certified within 60 days before shipment. The contractor shall certify that the material has been stored at a maximum temperature of 50°F between date of manufacture of the cloth and date of shipment. Temperature excursions above 50°F are permissible provided the cumulative time above 50°F does not exceed 30 days.

3.5 **Shelf life.** The material specified herein shall have a shelf life of 9 months after date of manufacture when stored at 50°F maximum in sealed watertight plastic bags. The cumulative time out of storage of the cloth roll shall not exceed 30 days.

3.5.1 **Shelf life extension.** The shelf life extension of the cloth roll may be extended for one additional 6-month period provided the average value of three specimens from the beginning of the cloth roll conforms to the following when tested as specified in 4.6.2.1 and 4.6.2.3.

	Minimum	Maximum
Volatile Content, percent by weight	2.5	9.0
Resin Flow, percent by weight	8.0	18.0

3.6 **Workmanship.** The material shall have no holes, tears, or nonuniform weave and shall be free from dirt, grease, oil, and other contaminants which could render more than 10 percent (including selvage) of the material unsuitable for the intended use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

TABLE II. Cured material physical and mechanical properties.

Property		Limits	
		Minimum	Maximum
Density, gram/cubic centimeter (g/cc)		1.40	1.47
Residual volatiles, percent		0.0	2.50
Resin content, percent		30.0	37.0
Compressive strength, edgewise, pounds per square inch (psi)	Warp direction	14,000	40,000
	Fill direction	12,000	24,000
Interlaminar double shear strength, psi		1,800	4,500
Thermal conductivity, Btu/ft-hr degrees Fahrenheit (°F) at 250°F, fill direction			
With ply		0.10	3.0
Across ply		0.10	1.5
Coefficient of thermal expansion at 75 to 400°F, microinches/inch - °F			
Across ply		2.0	15.0
With ply		0.5	8.0
Flexural strength, psi	Warp direction	23,000	35,000
	Fill direction	18,000	26,000

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements (examinations and tests) specified herein. Except as otherwise specified in the contract or purchase order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to ensure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items shall meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of ensuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling inspection, as part of manufacturing operations, is

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

an acceptable practice to ascertain conformance to requirements, however, this does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to accept defective material.

4.2 **Classification of inspections.** The inspection requirements specified herein are classified as follows:

a. First article inspection (see 4.3).

b. Quality conformance inspection (see 4.4).

4.3 **First article inspection.** First article inspection (see 3.1) shall consist of the tests specified in table III. Failure to meet the requirements specified herein shall be cause for rejection of the first article sample.

TABLE III. First article inspection.

Tests	Requirement	Test Method
Cured Material		
Thermal conductivity test	3.3.2	4.6.3.1.6
Coefficient of thermal expansion test	3.3.2	4.6.3.1.7
Flexural strength test	3.3.2	4.6.3.1.8
Compressive strength test (fill)	3.3.2	4.6.3.1.4

4.4 **Quality conformance inspection.** Quality conformance inspection shall consist of the examination and tests specified in table IV.

4.4.1 **Sampling for inspection.**

4.4.1.1 **Lot.** A lot shall consist of not more than 1000 pounds of cloth which has been impregnated in one continuous run using one batch of resin and filler, mixed in one vessel at one time and submitted for inspection at one time.

4.4.1.2 **Sampling for uncured material properties.** Each roll in the lot shall be tested for uncured material properties at the beginning and at the end of the roll. Three specimens from each location shall be tested.

4.4.1.3 **Sampling for cured material properties.** Sampling for cured material properties shall conform to the requirements in table V. The test specimens shall be removed from the beginning of the sample roll, and three specimens shall be tested.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

TABLE IV. Quality conformance inspection.

Examination and tests	Requirement	Test Method
Uncured Material		
Visual examination	3.2, 3.6 and section 5	4.6.1
Volatile content test	3.3.1	4.6.2.1
Filler content test	3.3.1	4.6.2.2
Resin solids, dry weight test	3.3.1	4.6.2.2
Cloth content test	3.3.1	4.6.2.2
Resin flow test	3.3.1	4.6.2.3
Cured material		
Density test	3.3.2	4.6.3.1.1
Resin content test	3.3.2	4.6.3.1.3
Compressive strength (warp) test	3.3.2	4.6.3.1.4
Interlaminar shear test	3.3.2	4.6.3.1.5
Residual volatiles test	3.3.2	4.6.3.1.2

TABLE V. Roll sampling for cured material properties.

Number of rolls in the lot	Number of sample rolls to be selected for inspection
1 to 3	All
4 to 40	3

4.4.1.4 **Noncompliance of samples.** Failure of one or more of the samples to meet all of the specified requirements shall be cause for rejection of the lot.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

4.5 **Test results.** The average results of three tests at each location for each property shall conform to the specified property requirements in section 3. Individual specimen test results shall be recorded.

4.6 **Methods of inspection.** The following inspection methods shall be used. Unless otherwise specified in the method, all weights, volumes, temperatures, and times shall be measured to the nearest specified unit or decimal.

NOTE: Reagent grade chemicals shall be used for chemical reactions in the conduct of all tests defined herein. Solvents and indicators may be commercial nonreagent grade materials.

4.6.1 **Visual examination.** Each container shall be visually examined for conformance to section 5. Conformance to 3.2 and 3.6 shall also be determined by visual examination.

4.6.2 **Uncured material tests.**

4.6.2.1 **Volatile content test.**

a. Cut a 16 ± 2-square-inch specimen with a minimum width of 1.5 inches, and weigh to nearest 0.001 gram (g) (W1).

b. Place specimen in recirculating oven preheated to and stabilized at 325 ± 10°F for 10 ± 1 minutes. Specimens should be placed such that they will get adequate air circulation.

c. Remove specimen, place in desiccator, and cool to room temperature.

d. Remove specimen from desiccator, and weigh to nearest 0.001 gram (W2).

e. Calculate percent volatiles for each specimen as follows:

$$\text{Percent volatiles} = \frac{W1 - W2}{W1} \times 100$$

Where: W1 = original weight of specimen, g

W2 = final weight of specimen after devolatilization, g

f. Record average volatile content to nearest 0.1 percent.

4.6.2.2 **Resin solids, filler content, and cloth content test.**

a. Place a 1.5 ± 0.1-g specimen weighed to the nearest 0.001 g (specimen weight) in 250-milliliter (ml) beaker.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

b. Calculate devolatilized specimen weight (W) as follows:

$$W = \text{specimen weight} - \frac{(\text{percent volatiles})\ (\text{specimen weight})}{100}$$

Where: Percent volatiles is the value determined from the volatile content (see 4.6.2.1).

c. Add 50 ml of N,N dimethyl formamide (DMF), and bring to boil. Gently stir boiling DMF and preimpregnated cloth for minimum of 5 minutes. Remove beaker from heat source, and cool for a minimum of 5 minutes while stirring gently.

d. Decant and transfer liquid solution to second 250-ml beaker.

e. Rinse remaining fabric with DMF several times to ensure complete extraction of resin and filler from fabric, and add rinses to second 250-ml beaker.

f. Final rinse fabric with acetone to remove all traces of DMF.

g. Add all rinses to second 250-ml beaker.

h. Dry a filter and a filtering crucible at 350 ± 10°F for a minimum of 30 minutes. Weigh crucible and filter to nearest 0.001 g (W2).

i. Dry fabric in oven for 15 ± 1 minutes at 325 ± 10°F, cool in desiccator to room temperature, and reweigh to nearest 0.001 g (W1).

j. Using aspirator or vacuum pump, filter contents of second 250-ml beaker through filter and filtering crucible into vacuum flask.

k. Rinse the crucible and the filter several times with acetone to remove all resin.

l. Dry crucible and contents at 350 ± 10°F for 20 ± 1 minutes, cool in desiccator to room temperature, and reweigh to nearest 0.001 g (W3).

m. Calculate resin solids content, filler content, and cloth content as follows:

$$\text{Resin solids content (percent)} = \frac{W - (W1 + W4)}{W}\ (100)$$

$$\text{Filler content (percent)} = \frac{W4}{W} \times 100$$

$$\text{Cloth content (percent)} = \frac{W1}{W} \times 100$$

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

Where: W = calculated devolatilized weight of preimpregnated specimen, g

W1 = weight of fabric after resin and filler removal, g

W2 = crucible and filter weight, g

W3 = filler + crucible and filter weight, g

W4 = W3 - W2 = filler content, g

n. Record resin solids, filler content, and cloth content to nearest 0.1 percent.

4.6.2.2.1 **Alternate method for resin solids, filler content, and cloth content test.** Dry resin solid, carbon filler content and cloth content requirements of 3.3.1 may be performed in accordance with the Soxhlet extraction method specified in ASTM C 613.

4.6.2.3 **Resin flow test.**

a. Using a 4-inch by 4-inch ± 1/8-inch template, cut four squares across width of fabric. All squares shall be bias cut to eliminate fiber loss in testing. Stack squares uniformly on each other to make specimen.

b. Weigh specimen of four plies to nearest 0.01 g, and record as W1.

c. Place specimen between release film. Preheat press to 325 ± 10°F, position specimen in middle of press plate, and apply press load of 1000 ± 60 psi. Press-load specimen for minimum of 10 minutes at 325 ± 10°F.

d. Remove specimen from press, and cool to ambient temperature.

e. Using knife, scrape off resin flash to original size of specimen. Do not remove any reinforcement from original dimensions.

f. Reweigh specimen to nearest 0.01 g, and record as W2.

g. Calculate percent resin flow as follows:

$$\text{Percent flow} = \frac{(W1 - W2)}{W1} 100$$

Where: W1 = original weight of specimen, g

W2 = final weight of specimen, g

h. Record resin flow to nearest 0.1 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

4.6.3 **Cured material tests.**

4.6.3.1 **Preparation of test panels.** A test panel of sufficient size to provide the specimens for the required tests shall be prepared as follows:

a. Cut sample material as required to fabricate panel as specified in individual test procedures, and cure plies into a panel between separator film on smooth caul plates as follows:

(1) Orient plies such that the warp fibers of each ply are aligned in the same direction.

(2) Place stack of plies into press preset at 325 ± 10°F.

(3) Increase pressure slowly to 1000 ± 10 psi allowing resin to stage (see 6.4.4) to minimum flash at ply edges.

(4) Hold pressure and temperature for 120 ± 15 minutes, or 1 hour per inch of thickness, whichever is greater.

NOTE: The outer 1/2 inch of the test panel shall not be used for preparation of the specimens.

4.6.3.1.1 **Density test.**

a. Cut sufficient plies to produce test panel 0.125 ± 0.025 inch thick by 4 inches (minimum) by 5 inches (minimum), mark warp direction, and prepare panel as specified in 4.6.3.1.

b. Cut specimen 1 inch by 1 inch (approx) by panel thickness at random from test panel. Wipe specimen clean using methyl ethyl ketone (MEK) conforming to ASTM D 740, and allow to dry in air a minimum of 20 minutes before testing.

c. Weigh and record weight of specimen in air to nearest 0.1 mg (W1).

d. Weigh specimen in water at 73 ± 3°F and record weight to nearest 0.1 mg using wire and sinker if required (W2).

e. Calculate density as follows:

$$\text{Density (g/cc)} = \frac{0.9975\ W1}{(W1 + W3 - W2)}$$

Where W1 = weight of specimen in air, g

W2 = weight of specimen, wire, and sinker suspended in water, g

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

W3 = weight of wire and sinker suspended in water to the same depth as in W2 determination to nearest 0.1 mg, g.

0.9975 = conversion factor to convert specific gravity to g/cc.

f. Record density to nearest 0.01 g/cc.

4.6.3.1.2 **Residual volatile content test.**

a. Cut sufficient plies to produce test panel 0.250 ± 0.050 inch thick by 4.000 ± 0.125 by 4.000 ± 0.125 inches. Prepare panel as specified in 4.6.3.1 with the following exception

Apply contact pressure for 30 ± 5 seconds and dump pressure for 2 cycles before slowly applying maximum pressure. (The material shall not be staged.)

b. Cut specimen 1.000 ± 0.050 inch by 1.000 ± 0.050 inch by panel thickness from center 2-inch by 2-inch section of test panel. Top and bottom molded surfaces shall not be machined. Wipe specimen clean using MEK, and allow to air dry 20 minutes minimum before testing.

c. Place specimen in desiccator and desiccate for 18 hours minimum.

d. Weigh specimen to nearest 0.001 g and record as W1.

e. Place specimen in air-circulating oven preheated to and stabilized at 325 ± 10°F for 30 ± 6 minutes; condition specimen at 325 ± 10°F for 4 to 4.5 hours.

f. Remove specimen from oven and cool in desiccator for 30 minutes or until specimen reaches room temperature.

g. Reweigh specimen to nearest 0.001 g. Record as W2.

h. Calculate percent residual volatiles as follows:

$$\text{Percent volatiles} = \frac{(W1 - W2)}{W1} 100$$

Where: W1 = original weight of specimen, g

W2 = devolatilized weight of specimen, g

i. Record residual volatiles to nearest 0.01 percent.

4.6.3.1.3 **Resin content test.** Resin content shall be determined, using the test panel prepared in 4.6.3.1, as follows:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

a. Cut specimen 0.60 ± 0.10 inch by 1.50 ± 0.05 inch by panel thickness at random from test panel.

b. Wipe specimen clean using MEK, and allow to dry in air 20 minutes minimum before testing.

c. Record specimen weight to nearest 0.001 g (W).

d. Place test specimen in Vycor test tube and tightly attach tube to test apparatus (see figure 1).

e. Start vacuum pump and evacuate system to within 3 inches of mercury of absolute vacuum (minimum). Check for air leaks by clamping off hose to vacuum pump and noting manometer. The leak rate must be less than 0.2 inch of mercury per minute. Recheck joints until this level is achieved.

f. With vacuum on and pressure stabilized, place Fisher burner under the specimen. Adjust flame area to completely cover sample.

NOTE: A tube furnace maintained at 1500 ± 25°F may be used in place of the Fisher burners.

g. Continue pyrolysis for 30 ± 6 minutes or until manometer or gauge reading is same reading as it was before pyrolysis, whichever is longer.

NOTE: If residue collects in Vycor test tube, place Fisher burners under those areas until burnout is complete.

h. When pyrolysis is complete, turn off burners and cool under vacuum until specimen is at room temperature (touch Vycor test tube just under test specimen).

i. When specimen is cool, turn off vacuum and carefully let air into system. When pressure equilibrium is reached, remove specimen from test tube and weigh to nearest 0.001 g (W1).

$$\text{Resin content, percent} = \frac{(W1 - W2)}{W1} \times 100\ (K)$$

Where: W1 = weight of sample before pyrolysis, g

W2 = weight of sample after pyrolysis, g

K = constant ratio of percent resin (Soxhlet extraction of DMF wash) to percent weight loss by pyrolysis (K for U.S. Polymeric = 2.110; K for Fiberite = 2.125).

k. Record resin content to nearest 0.1 percent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

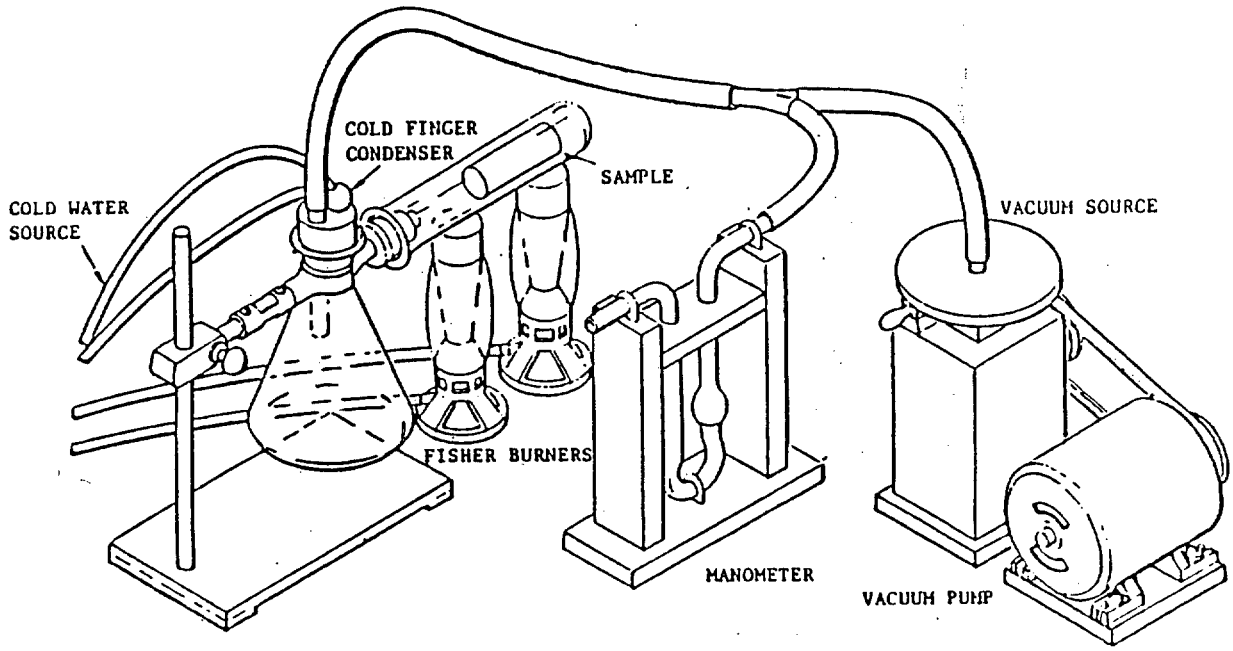


FIGURE 1. Resin content apparatus setup.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

4.6.3.1.4 **Compressive strength test.** The compressive strength shall be determined, using the test panel prepared in 4.6.3.1, as follows:

a. Machine specimen to dimensions shown on figure 2.

b. Measure width and thickness of specimen to nearest 0.001 inch in gauge section area. Calculate and record cross-section area.

c. Center specimen in support jig (see figure 4 of ASTM D 695) so ends project evenly beyond both ends of jig. Tighten finger tight only.

d. Place specimen and support jig in testing machine and align so specimen ends are parallel with surface of compression tool. Adjust crosshead of testing machine until it just contacts top of specimen.

e. The testing machine crosshead speed shall be 0.05 ± 0.01 inch per minute. Start machine.

f. Record maximum load carried by specimen during test.

g. Calculate compressive strength by dividing maximum load by original cross-sectional area.

h. Record compressive strength to nearest 10 psi.

4.6.3.1.5 **Interlaminar shear test.**

a. Cut sufficient plies to produce cured layup panel 1.50 ± 0.25 inch thick across the plies by minimum dimensions of 1.5 by 1.5 inch.

b. Spray mold with release agent, and layup plies into mold.

c. Cure as specified in 4.6.3.1.

d. After cure, remove mold from press, remove test panel from mold, and allow panel to cool to room temperature.

e. Cut specimen of sufficient size to produce 0.375 inch diameter by 1.125 inch minimum length finished specimen, with length being perpendicular to plies of test panel.

f. Center specimen to get length of cylindrical specimen perpendicular to plies, and machine specimens to diameter of 0.375 ± 0.001 inch.

g. Measure diameter of test specimen to 0.0001 inch and calculate cross-sectional area (A).

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

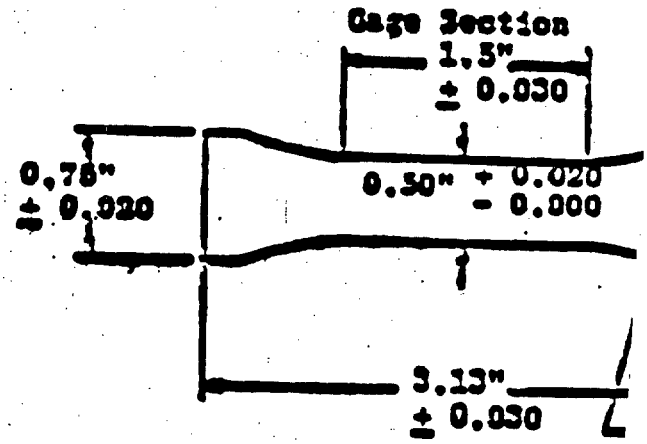


FIGURE 2. Compressive strength test specimen.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

h. Place specimen in a tensile loading shear jig conforming to figure 3.

i. Place shear fixture in testing machine, align, and pin ends of fixture.

j. Set machine at indicated crosshead speed of 0.015 to 0.025 inch per minute, and test.

k. Record maximum load carried by specimen during test as L.

l. Calculations:

$$\text{Interlaminar shear (psi)} = \frac{L}{2A}$$

Where: L = maximum load carried by the specimen during testing, in pounds

A = original cross-sectional area of specimen, in square inches

m. Record interlaminar shear to nearest 10 psi.

4.6.3.1.6 **Thermal conductivity test.** Thermal conductivity shall conform with ASTM C 177 and as follows:

a. Prepare test panel of required size and cure as specified in 4.6.3.1.

b. Data shall be recorded for temperature of 250 ± 10°F.

c. Maximum test panel dimension shall be 9.00 inches. Wrinkles are not permitted in the "with ply" direction.

d. Record thermal conductivity to nearest 0.01 Btu/ft-hr-degrees F.

4.6.3.1.7 **Coefficient of thermal expansion test.** The coefficient of thermal expansion (see 6.4.1) shall be determined in accordance with ASTM E 228 and as follows:


a. Prepare test panel of required size and cure as specified in 4.6.3.1.

b. Data shall be recorded for temperature range from 75 to 400°F.

c. Maximum test panel specimen length shall be 4.0 inches.

d. Record coefficient of thermal expansion to nearest microinch/inch - degrees F.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

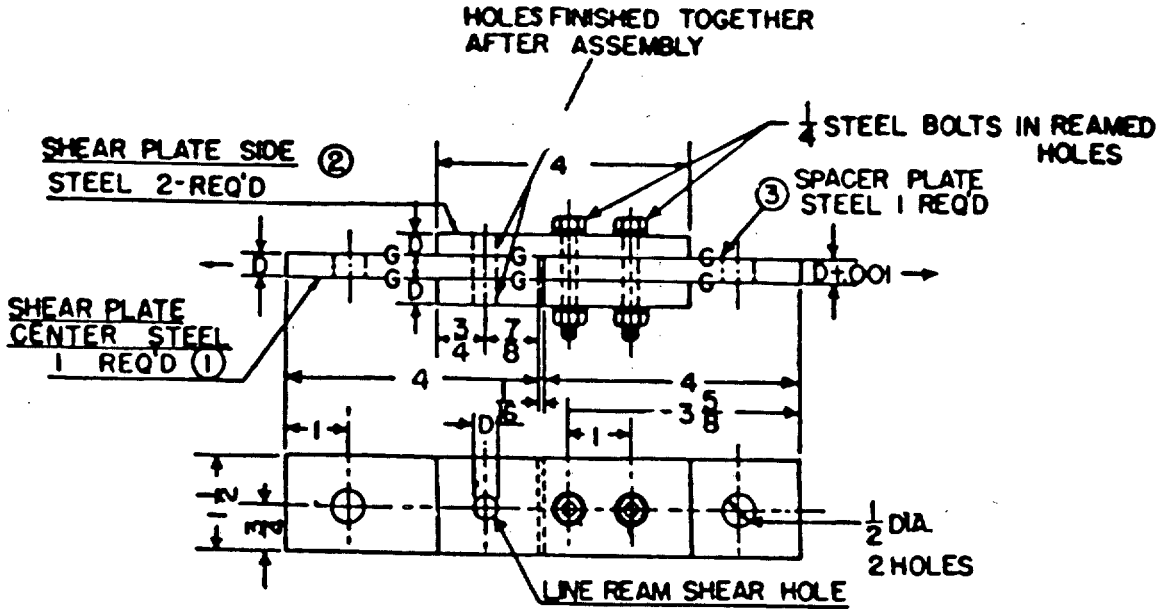

NOTES

1. D is nominal diameter of test cylinder.
2. Finish: machine after heat treatment.
3. Grind surfaces denoted G.
4. Spacer plate (3) to be 0.001 inch thicker than (1).
5. Edges of shear hole must be sharp.
6. All dimensions in inches; tol ± 1/64; specimen diamete — 0.001; diameter sh 0.000, — 0.001.
7. Alinement of shear holes m.
8. Material: steel, heat-treated 35–40.

FIGURE 3. Shear jig, tensile loading.

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

4.6.3.1.8 **Flexural strength test.** Flexural strength shall be determined in accordance with ASTM D 790, Method 1, and as follows:

a. Prepare test panel of required size and cure as specified in 4.6.3.1.

b. Maximum test specimen thickness shall be 0.25 inch.

c. Record flexural strength to nearest 10 psi.

4.7 **Inspection of packaging.** The cloth containers and container markings shall be visually examined for compliance with section 5.

5. PACKAGING

5.1 **Packaging.** Unless otherwise specified in the contract or order (see 6.2), packaging shall be level C as specified herein.

5.1.1 **Level C.** The cloth shall be packaged to afford adequate protection against loss, contamination, deterioration and damage during shipment from the supply source to the first receiving activity and during storage under the shelf life period and conditions specified in 3.5. Containers in the same shipment shall be of the same size. The packaging shall conform to UFC 6000, National Motor Freight Classification, 49 CFR 171-178, or to other carrier rules and regulations as applicable to the mode of transportation.

5.2 **Marking.**

5.2.1 **Standard marking.** In addition to any special marking required by the contract or order (see 6.2), interior and exterior containers shall be marked in accordance with MIL-STD-129.

5.2.2 **Special marking.** In addition to the marking requirements of 5.2.1, each container marking shall include the following information:

a. Title, number and date of this specification.

b. Manufacturer's name and address.

c. Material trade name and identification.

d. Number of rolls.

e. Lot number and date of quality conformance inspection (see 4.4).

f. Shelf life and inspection/test date for extension (see 3.5). In addition, the marking shall include the following:

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

"SHELF LIFE EXTENSION

THE SHELF LIFE OF AN INDIVIDUAL LOT MAY BE EXTENDED FOR AN ADDITIONAL 12-MONTH PERIOD PROVIDED THE CLOTH, UPON RETEST, CONFORMS TO THE RESIN FLOW AND VOLATILES CONTENT REQUIREMENT SPECIFIED IN MIL-G-82800."

g. Mark each roll on inside of spool with contractor name, roll number, lot number, and material name with ink stamp, stencil, or adhesive label.

h. Mark opposite sides of each shipping container with the following:

"TEMPERATURE SENSITIVE MATERIAL.
DO NOT EXPOSE TO TEMPERATURE HIGHER THAN 100°F."

5.3 **Shipment temperature.** The temperature of the material during shipment shall not exceed 100°F as measured by a temperature-indicating tape placed on the inside of the spool of at least one cloth roll in each container in each shipment.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 **Intended use.** The cloth specified herein is intended for use in the manufacture of the Standard Missile Mk 104 Dual Thrust Rocket Motor nozzles.

6.2 **Acquisition requirements.** Acquisition documents must specify the following:

a. Title, number and date of this specification.

b. Issue of DODISS to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.1.1, 2.1.2 and 2.2).

c. Whether first article inspection is required (see 3.1 and 6.3).

d. Packaging required, if other than as specified in 5.1.

e. Special marking, if other than as specified in 5.2.2.

6.3 **First article.** When first article inspection is required, the contracting officer should provide specific guidance to offerors on the material to be inspected. The material should be a first article sample and should consist of a quantity of the release compound sufficient to perform all of the inspections specified in 4.3. The first article sample should be packaged and marked as specified in section 5. The contracting officer should include specific instructions in acquisition documents regarding arrangements for

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

examinations, approval of first article test results and disposition of first articles. Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract.

6.4 Definitions.

6.4.1 Coefficient of thermal expansion. The secant slope between 75 and 400°F of the linear expansion.

6.4.2 Sample roll. A cloth roll of impregnated cloth selected from the lot in accordance with the sampling plan (4.4.1).

6.4.3 Specimen. A portion of the sample cloth roll selected for inspection and test.

6.4.4 Stage. A method of stabilizing and retaining the phenolic polymer in a solid state on the carbon cloth by temperature cycling.

6.5 Subject term (key word) listing.

Nozzles, rocket
Rocket Motor, Dual Thrust, Mk 104
Standard Missile

6.6 Supersedure information. MIL-B-82800 incorporates the following engineering change proposal (ECP) and specification change notice (SCN):

ECP	SCN
SSS1029 (8/24/84)	SCN 1 (8/24/84)

Preparing Activity:
NAVY-OS
(Project 1340-N821)

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

INSTRUCTIONS

1. The preparing activity must complete blocks 1, 2, 3, and 8. In block 1, both the document number and revision letter should be given.
2. The submitter of this form must complete blocks 4, 5, 6, and 7.
3. The preparing activity must provide a reply within 30 days from receipt of the form.

NOTE: This form may not be used to request copies of documents, nor to request waivers, or clarification of requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

I RECOMMEND A CHANGE:	1. DOCUMENT NUMBER	2. DOCUMENT DATE (YYMMDD)
	MIL-B-82800	5 February 1990

3. DOCUMENT TITLE

BROADGOODS, GRAPHITE CLOTH, PHENOLIC-PREIMPREGNATED

4. NATURE OF CHANGE *(Identify paragraph number and include proposed rewrite, if possible. Attach extra sheets as needed.)*

5. REASON FOR RECOMMENDATION

6. SUBMITTER

a. NAME (Last, First, Middle Initial)	b. ORGANIZATION	
c. ADDRESS (Include Zip Code)	d. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON (If applicable)	7. DATE SUBMITTED (YYMMDD)

8. PREPARING ACTIVITY NAVAL ORDNANCE STATION (CODE 3730) INDIAN HEAD, MD 20640-5000

a. NAME	b. TELEPHONE (Include Area Code) (1) Commercial (2) AUTOVON
c. ADDRESS (Include Zip Code)	IF YOU DO NOT RECEIVE A REPLY WITHIN 45 DAYS, CONTACT: Defense Quality and Standardization Office 5203 Leesburg Pike, Suite 1403, Falls Church, VA 22041-3466 Telephone (703) 756-2340 AUTOVON 289-2340

Source: https://assist.dla.mil -- Downloaded: 2026-10-23T07:26Z
Check the source to verify that the content is the current version before use.