GGG-P-831F
April 10, 1995
SUPERSEDING
GGG-P-831E
January 27, 1966

FEDERAL SPECIFICATION

PUNCHES; CENTER, DRIVE PIN, ALIGNING, AND PRICK

This specification is approved by the Commissioner, Federal Supply Service, General Services Administration, for the use of all Federal agencies.

1. SCOPE AND CLASSIFICATION

1.1 Scope. This specification covers punches commonly used by mechanics and metal workers.

1.1.1 Federal specification coverage. Federal specifications do not cover all varieties of the commodity indicated by the title of the specification, or which are commercially available, but are intended to cover only those generally used by the Federal Government.

1.2 Classification.

1.2.1 Types, classes, and styles. Punches shall be of the following types, classes, and styles as specified (see 6.1):

Type II - Center
- Class A - Solid
- Class B - Automatic, adjustable
  - Style 1 - With plastic knob
  - Style 2 - Without plastic knob

Type VIII - Drive pin
- Class A - Standard point length
  - Style 1 - 4 inch overall length
  - Style 2 - Variable overall length
- Class B - Extra long point length
- Class C - Solid (starting)

Type IX - Aligning

Type X - Prick

Beneficial comments, recommendations, additions, deletions, clarifications, etc., and any data which may improve this document should be sent to: General Services Administration, Tools and Appliances Commodity Center (6FETE-CO), Washington, DC 20406.

FSC 5120

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents. The following documents, of the issues in effect on date of invitation for bids or request for proposal, form a part of this specification to the extent specified herein:

Federal Standard:

FED-STD-H28 - Screw-Threads Standards for Federal Services

(Activities outside the Federal Government may obtain copies of Federal Specifications, Standards, and Commercial Item Descriptions as outlined under General Information in the Index of Federal Specifications, Standards and Commercial Item Descriptions. The Index is for sale on a subscription basis by the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402.)

(Single copies of this specification, and other Federal Specifications and Commercial Item Descriptions required by activities outside the Federal Government for bidding purposes are available without charge from General Services Administration, Federal Supply Service Bureau, Specification Section, Suite 8100, 470 L'Enfant Plaza, SW, Washington, DC 20407.)

(Federal Government activities may obtain copies of Federal standardization documents and the Index of Federal Specifications, Standards, and Commercial Item Descriptions from established distribution points in their agencies.)

2.2 Other publications. The following documents form a part of this specification to the extent specified herein. Unless a specific issue is identified, the issue in effect on date of invitation for bids or request for proposal shall apply.

American National Standards Institute (ANSI):

ANSI B 46.1 - Surface Texture; Surface Roughness; Waiveness and Lay; and Surface Finish Roughness Height (in Microinches)

ANSI B 209.2 - Metal Punches and Drift Pins, Safety Requirements

(Private sector and civil agencies may purchase copies of this voluntary standard from the American National Standards Institute, 11 West 42nd Street, New York, NY 10036.)

ANSI/ASQC Z1.4 - Sampling Procedures and Tables for Inspection by Attributes

(Private sector and civil agencies may purchase copies of this voluntary standard from the American Society for Quality Control, P.O. Box 3005, 611 E. Wisconsin Ave., Milwaukee, WI 43201-4606.)

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:42Z
Check the source to verify that this is the currentversion before use.

American Society for Testing and Materials (ASTM):

ASTM E 10	-	Test Method for Brinell Hardness of Metallic Materials
ASTM E 18	-	Methods of Test for Rockwell Hardness and Rockwell Superficial Hardness of Metallic Materials

(Private sector and civil agencies may purchase copies of this voluntary standard from the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(DoD activities may obtain copies of those adopted voluntary standards listed in the DoD Index of Specifications and Standards free of charge from the Standardization Document Order Desk, Building 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

3. REQUIREMENTS

3.1 Illustrations. Illustrations herein are descriptive and not restrictive and are not intended to preclude the purchase of punches otherwise conforming to this specification.

3.2 Material. The punches shall be manufactured in accordance with ANSI B 209.2.

3.2.1 Hardness. The struck end of all punches shall not exceed Rockwell "C" Hardness (HRC) of 45 when tested as specified in 4.3.5.

3.3 Screw threads. Screw threads for type II, class B punches shall be in accordance with FED-STD-H28.

3.4 Interchangeable parts (type II, class B). All parts having the same manufacturer's part number shall be constructed to definite standards, tolerances, and clearances in order that such parts may be interchangeable, replaced, or adjusted without requiring modification.

3.5 Finish. Punches shall be free from oxide scale, rust, fins, sharp edges or corners (except cutting arithmetic average (AA) using a 0.030 inch cutoff for types II and X punches when tested as edges), pits, burrs, cracks, and other detrimental defects. Except for knurled surfaces, machined surfaces shall have a maximum surface finish of 63 microinches specified in 4.3.6. Manufacturer's commercial finish is acceptable on the other types of punches.

3.6 Identification marking. Punches shall be marked with the manufacturer's name or identifying symbol, and the state or country of manufacture, unless otherwise specified. All marking shall be engraved, etched, molded, or indented (stamped) directly on the item's surface in such a manner that it remains clearly legible throughout the life of the item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.

3.7 Sets. When sets of punches are specified (see 6.1), all punches contained in the set shall conform to the requirements of their respective type, class, and style covered by this specification.

3.7.1 Containers for sets. Punches, when ordered in encased sets, shall be furnished in durable wooden or plastic boxes, fabric wraps, plastic wraps, or rolls as specified (see 6.1). The containers shall have a separate compartment for each tool. Each tool compartment shall be legibly and permanently marked with the tool size or a listing shall be permanently affixed to the inside of the container. In addition, each tool compartment shall provide a safe, compact, and secure method of storing the tool, shall provide for convenient tool selection, and shall prevent damage to the tool during handling, shipment, and storage. With the container secured in a closed position, tools shall not be displaced from their individual compartments by any orientation of the container.

3.7.1.1 Plastic boxes. The boxes and covers shall be constructed of a double layer, impact resistant material. The box shall have at least one shutter hook, snap-type latch, or similar hardware to secure the box in a closed position. Boxes shall be fitted with at least two hinges or a continuous hinge.

3.7.1.2 Wooden boxes. The boxes and covers shall be constructed of hardwood such as maple, ash, hickory, or birch. The box shall have at least one shutter hook, snap-type latch, or similar hardware to secure the box in a closed position. Boxes shall be fitted with at least two hinges or a continuous hinge. Unless otherwise specified (see 6.1), the box shall have a natural finish.

3.7.1.3 Fabric wraps or rolls. Fabric wraps or rolls shall be of durable material such as canvas or duck and shall be provided with durable ties.

3.7.1.4 Plastic wraps or rolls. Plastic wraps or rolls shall be of plastic or plastic-coated cloth. The wraps or rolls shall be provided with snap fasteners or durable ties.

3.8 Type II, center. Type II center punches shall be used for making distinct impressions on steel, brass, aluminum, and wood. Type II punches shall be capable of withstanding the tests specified in 4.3.1, 4.3.2, and 4.3.3, as applicable.

3.8.1 Class A, solid. Class A punches shall have the point smoothly machined or ground to the included angle specified in table I, and the tapered portion smoothly machined or ground concentric with the axis of the punch showing a runout of not more than 0.020 inch total indicator reading. The struck end of the punch shall be uniformly chamfered, or rounded, and smoothly finished. The chamfering or rounding shall be in accordance with ANSI B 209.2. The face of the struck end shall be at right angles to the longitudinal axis of the punch within 2°. Class A punches shall possess an HRC of 50 to 63 within a minimum of 1/2 inch from the point end (see 4.3.5).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.

3.8.1.1 Body shape. The body of the punches shall be either circular, square, hexagonal, or octagonal in cross section. The punch may have a machined or upset head that will minimize mushrooming (see optional head design, figure 1).


3.8.1.1.1 Circular body. Circular body punches shall be knurled and shall be provided with either a square or round struck head.

3.8.1.1.2 Square body. Square body punches shall have the corners rounded. The square body punches shall be provided with either a round or square struck head.

3.8.1.2 Class A punches. Class A punches shall conform to table I and be similar to figure 1.

TABLE I. Type II, class A, solid center punch

Size number	Included angle of point ± 5°	Diameter at top of point (minimum) A	Body size cross section ± 1/32	Overall length (minimum)
	Degrees	Inch	Inch	Inches
0	90	1/16	3/16	3-1/8
2	90	5/64	1/4	3-1/4
4	90	1/8	5/16	3-3/4
5	90	5/32	3/8	4
7	90	7/32	1/2	4
10	90	3/8	5/8	6



Optional Head Design




Figure 1. Type II, class A, solid center punch.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the currentversion before use.

3.8.2 Class B, automatic, adjustable. Class B punches shall consist of a high-grade tool-steel punch point, a brass, steel, or aluminum-alloy body and screwcap, and an internal mechanism which automatically strikes a blow of a required force by a movement of the body of the punch in the direction of the point. The working parts shall be hardened to minimize wear, distortion or fracture, and shall be accessible for replacement. Brass bodies and brass screwcaps shall be plated to resist corrosion. The point end of class B punches shall have an HRC of from 50 to 63 with the exception of the threaded portion. The bodies and screwcaps, when made of aluminum alloy, shall have a Brinell hardness of from 117 to 125 (see 4.3.5).

3.8.2.1 Punch point. The punch point shall have a center point smoothly machined or ground concentric with the punch-point body and, when assembled, shall show a runout of not more than a 0.020 inch total indicator reading. The punch point shall be removable for resharpening and shall be easily replaced. The point shall have an included angle of 80° ± 5°.

3.8.2.2 Body. The outer diameter of the body shall be knurled. The inner portion of the body shall be designed for proper housing of the automatic mechanism and punch point.

3.8.2.3 Screwcap. The outer diameter of the screwcap shall be knurled. The screwcap shall be adjustable on the body, working in conjunction with a spring which shall regulate the force of the stroke.

3.8.2.4 Style 1, with plastic knob. Style 1 center punches shall be provided with a plastic knob securely attached to the adjusting screwcap in such a manner that it will not become loose or detached under service conditions. The plastic knob shall be round and fluted, or otherwise designed to promote hand comfort. Plastic knobs with a cellulose-nitrate base shall not be used. Plastic knobs shall withstand the tests specified in 4.3.2. The style 1 center punch shall conform to table II and shall be similar to figure 2.

TABLE II. Type II, class B, style 1, automatic, adjustable center punch with plastic knob

Size number	Diameter of body + 1/16 - 0	Overall length extended* (maximum)	Overall length closed* (minimum)
	Inch	Inches	Inches
1	1/2	4-1/2	4-1/4

* Extended and closed dimensions are obtained by tightening and loosening the screwcap to adjust the force of the stroke.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the current version before use.

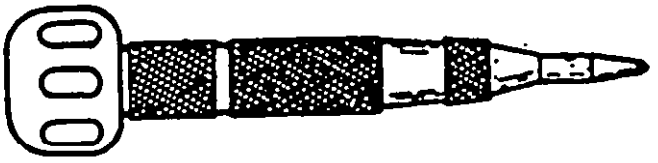


Figure 2. Type II, class B, style 1, automatic adjustable center punch with plastic knob.

3.8.2.5 Style 2, without plastic knob. The style 2 center punch shall be furnished without a plastic knob, shall conform to table III, and be similar to figure 3.

TABLE III. Type II, class B, style 2, automatic, adjustable center punch without plastic knob

Size number	Diameter of body + 1/16 - 0	Overall length closed (minimum)	Pressure required to actuate mechanism*	
			Minimum	Maximum
	Inch	Inches	Pounds	Pounds
1	3/8	3-1/8	5	15
2	1/2	4-1/8	10	25
3	5/8	5	40	55

* With the screwcap in a closed position, the required load to actuate the mechanism shall fall within the specified range (when tested on a platform scale).



Figure 3. Type II, class B, style 2, automatic, adjustable center punch without plastic knob.

3.9 Type VIII, drive pin. Type VIII punches shall be used in driving pins or bolts from holes having a force or drive fit. The struck-end face of the punch shall be uniformly chamfered and smoothly machined or ground at right angles to the longitudinal axis of the punch within 2°. The chamfering shall be in accordance with ANSI B 209.2. The entire length of the point of the punches shall be smoothly machined or ground concentric with the axis of the body showing a runout of not more than a 0.020 inch total

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the current version before use.

indicator reading. Type VIII punches shall be capable of withstanding the test specified in 4.3.3. Type VIII, classes A, B, and C punches shall have an HRC of 50 to 63 throughout their point length (see 4.3.5).

3.9.1 Body shape. The body of the punches shall be either circular, hexagonal, octagonal, or square in the cross section. The punch may have an upset head that will minimize mushrooming (see optional head design figures 4 and 5).


3.9.1.1 Circular body. Circular body punches shall be knurled in such a manner as to facilitate a firm grip under normal service conditions.

3.9.2 Class A, standard-point length.

3.9.2.1 Style 1, 4 inch overall length. Class A, style 1 punches shall be furnished in normal sets, special sets, or individual punches as specified (see 6.1). Normal sets shall consist of one each of sizes 1 through 8. Special sets shall consist of any combination of sizes required. Class A, style 1 punches shall conform to table IV and be similar to figures 4A or 4B.


TABLE IV. Type VIII, class A, style 1 drive pin punch, standard point length, 4 inch overall length

Size number	Diameter of point + 0.000 - 0.015 A	Point length (minimum) B	Body size cross section ± 1/32 C	Overall length ± 1/8 D
	Inch	Inch	Inch	Inches
1	1/16	1/2	1/4	4
2	3/32	11/16	1/4	4
3	1/8	3/4	5/16	4
4	5/32	13/16	5/16	4
5	3/16	15/16	5/16	4
6	7/32	1	5/16	4
7	1/4	1	3/8	4
8	5/16	1	3/8	4
9	3/8	1	1/2	4



Optional Head Design

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the current version before use.

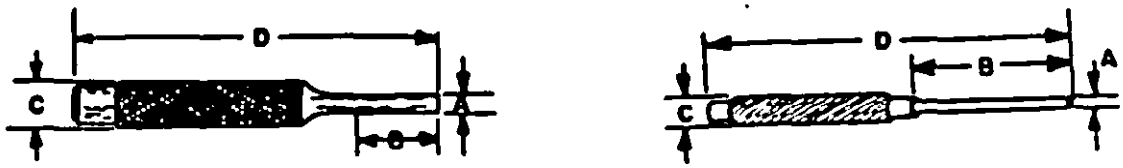

A B

Figure 4. Type VIII, class A, styles 1 and 2 and class B drive pin punches.

3.9.2.2 Style 2, varied-overall length. Class A, style 2 punches shall conform to table V and be similar to figures 4A or 4B.

TABLE V. Type VIII, class A, style 2, drive pin punch, standard point length, varied-overall length

Size number	Diameter of point + 0.000 - 0.015 A	Point length (minimum) B	Body size cross section ± 1/32 C	Overall length (minimum) D
	Inch	Inches	Inch	Inches
1	1/16	1/2	1/4	3
2	3/32	11/16	1/4	4
3	1/8	3/4	5/16	4-1/2
4	5/32	13/16	5/16	5
5	3/16	1	5/16	5
10	3/16	1-1/2	5/16	6
6	7/32	1	3/8	5
7	1/4	1	3/8	5-1/2
8	5/16	1	7/16	6
9	3/8	1	1/2	6

3.9.3 Class B, extra long point length. Class B punch shall conform to table VI and be similar to figures 4A or 4B.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.

TABLE VI. Type VIII, class B, drive pin punch, extra long point length

Size number	Diameter of point + 0.000 - 0.015 A	Point length (minimum) B	Body size cross section ± 1/32 C	Overall length (minimum) D
	Inch	Inches	Inch	Inches
0	1/16	1-1/2	1/4	6
1	1/8	3-1/2	3/8	8
1a	5/32	3-1/2	3/8	8
2	3/16	3-1/2	1/2	8
3	1/4	3-1/2	1/2	8
4	5/16	3-1/2	1/2	8
5	3/8	3-1/2	9/16	8
6	1/2	3-1/2	5/8	8

3.9.4 Class C, solid (starting). Class C punches shall conform to table VII and be similar to figure 5.

TABLE VII. Type VIII, class C, drive pin punch, solid (starting)

Size number	Diameter of point + 0.000 - 0.015 A	Taper length B		Body size cross section ± 1/32 C	Overall length (minimum) D
		Minimum	Maximum		
	Inch	Inches	Inches	Inch	Inches
1	1/16	1-1/2	2-1/2	5/16	4
1a	3/32	1-1/2	2-1/2	5/16	4
2	1/8	1-1/2	2-3/4	5/16	4-1/2
3	3/16	1-3/4	3	3/8	5
4	1/4	2	3-1/2	1/2	5-1/2
5	5/16	2	3-1/2	1/2	5-3/4
6	3/8	2	4	5/8	6
8	1/2	2-1/2	5	5/8	6-1/2

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.



Optional Head Design

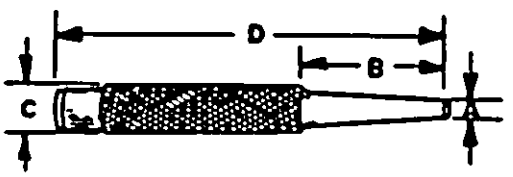


Figure 5. Type VIII, class C, drive pin punch, solid (starting).

3.10 Type IX, aligning. Type IX punches shall be used for lining up holes in plates, frames, and housings by either hammering or prying. The struck-end face of the punch shall be uniformly chamfered and smoothly finished at right angles to the longitudinal axis of the body. Chamfering of the punches shall be in accordance with ANSI B 209.2. The taper length shall be smoothly finished and concentric with the axis of the body showing a runout of not more than a 0.060 inch total indicator reading. The punches shall be capable of withstanding the bending moment test specified in 4.3.4. The punches shall have an HRC of 50 to 63 throughout a minimum of 25 percent of the taper length from the point of the taper (see 4. 3.5).

3.10.1 Body shape. The body of the punches shall be either circular, hexagonal, octagonal, or square in cross section. The punch may have an upset head that will minimize mushrooming (see optional head design, figure 6).


3.10.1.1 Circular body. Circular body punches shall be knurled in such a manner as to facilitate a firm grip under normal service conditions.

Source: https://assist.dla.mil -- Downloaded: 202640-26T12:42Z
Check the source to verify that this is the currentversion before use.

3.10.1.2 Type IX punches. Type IX punches shall conform to table VIII and be similar to figure 6.

TABLE VIII. Type IX, aligning punch

Size number	Diameter of point + 0.000 - 0.015 A	Taper length B		Body size cross section ± 1/32 C	Overall length (minimum) D	Bending moment
		Minimum	Maximum			
	Inch	Inches	Inches	Inch	Inches	Inch-pounds
1	3/32	3-1/2	5	1/4	8	30
2	1/8	3-1/2	5	5/16	8	50
3	5/32	4	6-1/2	3/8	8	70
4	5/32	6	8-1/2	1/2	12	70
5	3/16	4	6-1/2	3/8	8	100
6	3/16	6	8-1/2	9/16	12	100
7	7/32	4	6-1/2	7/16	8	130
8	1/4	4	6-1/2	7/16	8-1/2	300
9	1/4	7	8-1/2	5/8	12	300
10	5/16	4	6-1/2	1/2	8-1/2	500
11	5/16	7	8-1/2	5/8	12	500
12	3/8	4	6-1/2	9/16	9	800
13	3/8	7	8-1/2	3/4	12	800
14	1/2	10	12	3/4	18	1,000



Optional Head Design

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the current version before use.


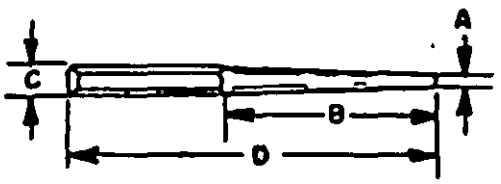


Figure 6. Type IX, aligning punch.

3.11 Type X, prick. Type X punch points shall have a 50° ± 5° included angle. The tapered portion shall be machined or ground concentric with the axis of the punch showing a runout of not more than 0.020 inch total indicator reading. The struck end of the punch shall be uniformly chamfered, rounded, or upset to minimize mushrooming, and shall be smoothly finished. The face of the struck end shall be at right angles to the longitudinal axis of the punch within 2°. The point end shall have an HRC of 50 to 63 within a minimum of 1/2 inch from the point end. Punches shall conform to table IX and be similar to figure 7. Type X punches shall be able to withstand the test specified in 4.3.3.

TABLE IX. Type X, prick punch

Size number	Body size cross section ± 1/32	Overall length (minimum)
	Inch	Inches
1	1/4	4
1a	5/16	4
2	3/8	4
3	1/2	5



Optional Head Design

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.



Figure 7. Type X, prick punch.

3.11.1 Body shape. The body of the punches shall be either circular, hexagonal, octagonal, or square in cross section. The punch may have an upset head that will minimize mushrooming (see optional head design, figure 7).

3.11.1.1 Circular body. Circular body punches shall be knurled in such a manner as to facilitate a firm grip under normal service conditions.

3.12 Metric products. Products manufactured to metric dimensions will be considered on an equal basis with those manufactured using inch-pound units, provided they fall within the tolerances specified and all other requirements of this document are met. If a product is manufactured to metric dimensions and those dimensions exceed the tolerances specified in the inch-pound units, a request should be made to the specification preparing activity for changes to this document.

3.13 Workmanship. Punches shall be free of manufacturing and material defects such as seams in excess of commercially acceptable levels, laps, pipes, and cold shuts which may adversely impact the item's serviceability, durability, safety or appearance.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure that supplies and services conform to prescribed requirements.

4.1.1 Component and material inspection. In accordance with 4.1 above, sampling for inspection shall be in accordance with ANSI/ASQC Z1.4. The lot size shall consist of all punches of the same size offered for acceptance at one time.

4.2 Examination.

Source: https://assist.dla.mil -- Downloaded: 202610-26T12:42Z
Check the source to verify that this is the currentversion before use.

4.2.1 Visual, dimensional and marking requirements. Each sample unit shall be examined for design, workmanship, dimensional and identification marking. The Inspection Level shall be Level I with an Acceptable Quality Level (AQL) of 2.5, expressed in terms of defects per hundred units.

4.2.2 Examination of containers and sets. Each sample unit shall be examined for any nonconformance with assembly of sets, including the boxes or rolls (see 3.7 through 3.7.1.4). The Inspection Level shall be S-2 with an AQL of 6.5, expressed in terms of defects per hundred units.

4.3 Testing. Each sample unit shall be tested in accordance with 4.3.1 through 4.3.5. The sample unit shall be one punch. The Inspection Level shall be S-4 with an AQL of 4.0, expressed in terms of defects per hundred units.

4.3.1 Functional test for type II, center punch, class B, automatic, adjustable, styles 1 and 2. Each sample punch shall be cycled 100 times to determine whether the automatic device functions properly and whether the adjustment regulates pressure properly.

4.3.2 Plastic knob test, type II, center, class B, automatic, adjustable style 1, plastic knob. The punches shall be subjected to the tests specified in 4.3.3.1 and 4.3.3.2.

4.3.2.1 Heat-distortion test. The knob of the punch shall be completely immersed in boiling water at 212°F for a period of two minutes. At the end of this period, the punch shall be removed from the water and the knob shall show no significant signs of distortion or blistering.

4.3.2.2 Impact test at room temperature. Each sample punch shall be held knob downward and dropped on a concrete floor from a height of 10 feet. After impact there shall be no breakage, loosening, buckling, spalling, or cracking of the knob.

4.3.3 Impact test for type II, classes A and B, type VIII, classes A, B, and C, and type X punches. The impact test for the type II, classes A and B, type VIII, classes A, B, and C, and type X punches shall be performed in accordance with ANSI B 209.2.

4.3.4 Bending moment test for type IX, aligning punch. The bending moment test for the type IX, aligning punches shall be performed in accordance with ANSI B 209.2.

4.3.5 Hardness test. The sample punches shall be tested in accordance with ASTM E 10 for Brinell and ASTM E 18 for Rockwell to determine compliance with the hardness requirement of the respective types.

4.3.6 Surface roughness. Surface roughness specified in 3.5 shall be tested in accordance with ANSI B 46.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z .
Check the source to verify that this is the current version before use.

4.4 Inspection of preparation for delivery requirements. An inspection shall be made to determine that the preservation, packaging, packing, and marking comply with the requirements in section 5 of this specification. Defects shall be scored in accordance with table XII. The lot size shall be the number of shipping containers in the end item inspection lot. The sample unit shall be one container. The Inspection Level shall be S-2 with an AQL of 4.0, expressed in terms of defects per hundred units.

TABLE XII. Classification of preparation for delivery defects

Examine	Defect
Marking (exterior and interior)	Omitted; incorrect; illegible; improper size, location, sequence, or method of application
Materials	Any component missing, damaged, or not as specified
Workmanship	Inadequate application of components such as incomplete closure of container flaps, loose strapping, inadequate stapling Distortion of container
Contents	Number per container is more or less than required Net weight exceeds requirements.

5. PREPARATION FOR DELIVERY.

5.1 Preservation, packaging, packing, and marking. Preservation, packaging, packing, and marking shall be as specified in the contract or purchase order.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful but is not mandatory.)

6.1 Acquisition requirements. Acquisition documents must specify the following:

a. Title, number, and date of this specification.
b. Type, class, and style, if applicable, of punches required (see 1.2).
c. Size number of punches required (see applicable tables).
d. Whether punches in sets are required (see 3.7)
e. Whether sets should be furnished in wooden boxes, plastic boxes, fabric wraps, rolls, or plastic containers (see 3.7.1).

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.

f. If special finish is required for wooden boxes (see 3.7.1.2).
g. Whether normal set, special set as required, or individual punches of type VIII, class A, style 1 are required (see 3.9.2.1).

6.2 Supersession data. Type IV (Coopers') punch formally included in GGG-P-831E has been deleted without replacement.

DOD coordination has been waived.

PREPARING ACTIVITY:

GSA - FSS

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T12:42Z
Check the source to verify that this is the current version before use.