NOT MEASUREMENT SENSITIVE

P-P-560C
September 24, 2018
SUPERSEDING
P-P-560B
June 2, 1981

FEDERAL SPECIFICATION

POLISH, PLASTIC

The General Services Administration has authorized the use of this federal specification, by all federal agencies.

1. SCOPE

1.1 Scope. This specification covers three types of polish that are capable of removing accumulated service soils and of producing a smooth, lustrous finish on plastic acrylic materials.

1.2 Classification.

1.2.1 Types. Polishes furnished under this specification are of the following types, as specified (see 6.2):

Type I - Liquid
Type II - Paste
Type III - Aerosol

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3 and 4 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements of documents cited in sections 3 and 4 of this specification, whether or not they are listed.

Comments, suggestions, or questions on this document should be addressed to: Commander, Naval Air Warfare Center Aircraft Division, (Code 4.1.2.2), Route 547, Joint Base MDL, NJ 08733-5100 or emailed to michael.sikora@navy.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at https://assist.dla.mil.

AMSC N/A FSC 7930

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications and standards form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

FEDERAL SPECIFICATION

TT-N-95	Naphtha, Aliphatic

FEDERAL STANDARD

FED-STD-313	Material Safety Data, Transportation Data, and Disposal Data for Hazardous Materials Furnished to Government Activities

COMMERCIAL ITEM DESCRIPTION

A-A-50129	Cloth, Flannel, Lightweight

DEPARTMENT OF DEFENSE SPECIFICATIONS

MIL-PRF-8184	Plastic Sheet, Acrylic, Modified
MIL-G-21164	Grease, Molybdenum Disulfide, for Low and High Temperatures, NATO Code Number G-353
MIL-PRF-25690	Plastic Sheets and Formed Parts, Modified Acrylic Base, Monolithic-Crack Propagation Resistant
MIL-PRF-81733	Sealing and coating compound, corrosion inhibitive
MIL-PRF-83282	Hydraulic Fluid, Fire Resistant, Synthetic Hydrocarbon Base, Aircraft, Metric, NATO Code Number H-537

DEPARTMENT OF DEFENSE STANDARDS

MIL-STD-129	Military Marking for Shipment and Storage
MIL-STD-1916	DOD Preferred Methods for Acceptance of Products

(Copies of these documents are available online at http://quicksearch.dla.mil.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

ASTM INTERNATIONAL

ASTM D56	Standard Test Method for Flash Point by Tag Closed Cup Tester

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

ASTM D1003	Standard Test Method for Haze and Luminous Transmittance of Transparent Plastics
ASTM D2240	Standard Test Method for Rubber Property—Durometer Hardness
ASTM E168	Standard Practices for General Techniques of Infrared Quantitative Analysis
ASTM F484	Standard Test Method for Stress Crazing of Acrylic Plastics in Contact with Liquid or Semi-liquid Compounds,
ASTM F502	Standard Test Method for Effects of Cleaning and Chemical Maintenance Materials on Painted Aircraft Surfaces
ASTM F735	Standard Test Method for Abrasion Resistance of Transparent Plastics and Coatings Using the Oscillating Sand Method
ASTM F1110	Standard Test Method for Sandwich Corrosion Test

(Copies of these documents are available online at https://www.astm.org/.)

SAE INTERNATIONAL

SAE AMS-P-83310	Plastic Sheet, Polycarbonate, Transparent
SAE AMS-S-8802	Sealing Compound, Temperature Resistant, Integral Fuel Tanks and Fuel Cell Cavities, High Adhesion

(Copies of these documents are available online at http://www.sae.org.)

2.3 Order of precedence. Unless otherwise noted herein or in the contract, in the event of a conflict between the text of this document and the references cited herein (except for related specification sheets), the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Qualification. The polishes furnished under this specification shall be products that are authorized by the qualifying activity for listing on the applicable qualified products list before contract award (see 4.2 and 6.3).

3.2 Materials. The composition of the polish shall be optional with the manufacturer, but shall be restricted by requirements specified herein. The polish shall contain no ingredient or impurities that may cause the formation of hydrogen sulfide.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

3.2.1 Toxicity. The cleaners supplied under this specification shall have no adverse effect on the health of personnel when all precautions are followed for its usage in accordance with the applicable Safety Data Sheet (SDS) (see 6.7).

3.3 Cleaning and anti-static characteristics. The polish shall dry sufficiently to permit easy removal 10 minutes after being applied and shall continue to be removable for at least 24 hours. The compound, with no more than two applications, shall efficiently remove from plastic surfaces all residue, masking glue, lubricating oil, lubricating grease, and soil. After polishing, the cleaned surfaces shall be free from any trace of oily film, residue or marring and produce a parallel luminous transmittance reading that shall be not less than 89.0 percent. Surfaces shall show static charge dissipates and the highest recorded reading shall be less than 10kv when tested as specified in 4.5.1.

3.4 Polishing efficiency. After being polished as specified in 4.5.2, the acrylic panels shall be free from residue, discoloration, scratching or marring. The panels shall produce a parallel luminous transmittance that shall be not less than 89.0 percent and the Δ haze shall be not greater than 5 percent.

3.5 Stress crazing. The polish shall not craze, stain or discolor Type B (MIL-PRF-8184) and Type C (MIL-PRF-25690) or acrylic SAE AMS-P-83310 polycarbonate, when tested in accordance with 4.5.3.

3.6 Flash point (Type I and Type II only). The polish flash point shall be not less than 27 °C (81°F), when tested as specified in 4.5.4.

3.7 Sandwich corrosion. After 24 hours, the polish sandwich corrosion rating shall be not greater than one, nor have an effect greater than that obtained for reagent water, when tested in accordance with 4.5.5. When viewed under 10X magnification, the test specimen shall exhibit no white aluminum corrosion product.

3.8 Sealant compatibility. When tested as specified in 4.5.6, the polish specimen's hardness measurement shall be not less than 25 Shore hardness A units, after immersion in each polish at room temperature.

3.9 Accelerated storage stability (Type I and Type II only). After being tested as specified in 4.5.7, the polish shall not separate, crystallize nor show any other change in physical properties.

3.10 Room temperature storage stability. The polish, after being stored as specified in 4.5.8, shall not separate, crystallize, nor show any other change in physical properties. After completing the room temperature storage period, polish shall then conform to the requirements of 3.3, 3.4, 3.5 and 3.7. In addition, Type III containers shall show no signs of corrosion, leakage or distortion.

3.11 Consistency (Type I only). The polish shall flow to a point within 5 to 15 centimeters (cm) from the origin within 5 minutes, when tested accordance with 4.5.9.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

3.12 Effects on painted surfaces. The polish, after being tested as specified in 4.5.10, shall show no streaking, discoloration, blistering nor softening in excess of one pencil hardness.

3.13 Fourier Transform Infrared Spectroscopy (FTIR) test. After being tested as specified in 4.5.11, the peaks in the fingerprint region of the IR spectra shall match the standard and other regions shall not exhibit any contamination peaks. Contaminants are cause for rejection.

3.14 Workmanship (Type I and Type II only). The polish when examined visually shall be a smooth homogenous mixture, free of lumps, when tested in accordance with 4.5.12.

3.15 Solids test (Type I and Type II only). The average of three samples shall be 10 percent ±2 percent, when tested in accordance with 4.5.13.

3.16 Identification of material. In addition to any marking required by the contract or order (see 6.2), each unit, intermediate, and exterior container shall be marked in accordance with MIL-STD-129. The marking shall also include the following (see 4.5.16):

Keep from freezing
Date of manufacture
Lot #

CAUTION

Remove rings or other hard objects from the hands before cleaning or polishing plastic surfaces.

Do not use hard, dirty, or gritty cloths.

Do not apply water, solvent, or polish to acrylic type plastic unless the plastic is cool and is protected from the heating effects of sunlight.

Do not use, store or dispose of near sources of heat, flames, sparks or other hot surfaces.

Application instructions:

Wipe the plastic with a cloth or wipe saturated with water or aliphatic naphtha conforming to TT-N-95, Type II. Use a bare hand to remove any dirt, sand, or mud that may cause scratches. Apply the polish evenly, let dry, then wipe clean with an authorized cloth or wipe. (Light scratches can be removed by vigorous rubbing, but care should be taken not to rub too long in one place.)

Cans containing Type I and Type III polish shall be marked with the following:

Shake well before using.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

4. VERIFICATION

4.1 Classification of inspections. The inspection requirements specified herein are classified as follows:

a. Qualification inspection (see 4.2).
b. Conformance inspection (see 4.3).

4.2 Qualification inspection. The qualification inspection (see 6.3) shall consist of all tests and examinations of this specification. Failure of any examination or test shall be cause for rejection.

4.2.1 Qualification sample. This sample shall consist of eight 16-ounce (0.473 mL) containers of polish or twelve 13-ounce aerosol cans for Type III. Additional samples may be required if a service evaluation is required by the qualifying activity (see 6.3). Samples shall be plainly identified by securely attached durable tags with the following information:

Sample for qualification inspection
Polish, Plastic
Type
Name of Manufacturer
Product code number
Date of manufacture
Batch or lot number

Submitted by (name) (date) for qualification inspection in accordance with the requirements of specification P-P-560C under authorization of (reference qualifying activity's authorizing letter). (See 6.3.)

4.3 Conformance inspection. Conformance inspection shall consist of the tests listed in table I. Conformance inspection samples shall be as specified in 4.3.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

TABLE I. Conformance inspections.

TEST	REQUIREMENT	TEST REFERENCE	TYPES
Cleaning and anti-static characteristics	3.3	4.5.1	I, II, III
Stress crazing	3.5	4.5.3	I, II, III
Accelerated storage stability	3.9	4.5.7	I, II
FTIR test	3.13	4.5.11	I, II
Workmanship	3.14	4.5.12	I, II
Solids test	3.15	4.5.13	I, II

4.3.1 Sampling for conformance tests. The sample unit shall be 16 ounces (0.473 mL) for Type I polish, 1 pound (0.45 kg) for Type II polish and 13-ounce cans for Type III aerosol. These samples shall be selected at random from each lot (see 4.3.2) in accordance with MIL-STD-1916. The lot shall be unacceptable if any sample fails to meet any of the test requirements specified in 4.3.

4.3.2 Size of a lot. A lot shall consist of all the polish manufactured at the same time, from the same batch of material, and submitted for inspection at the same time. The lot size shall be expressed in pints for Type I polish, in pounds for Type II polish and 13-ounce cans for Type III polish.

4.4 Test conditions. Unless otherwise specified in the test method or paragraph, all tests shall be conducted at the inspection conditions specified herein. The inspection conditions shall be a room temperature of 22 ±2 ºC (72 ±4 ºF) and a relative humidity of 50 ±20 percent.

4.5 Test methods.

4.5.1 Cleaning and anti-static characteristics test.

4.5.1.1 Materials.

a. MIL-PRF-25690 acrylic coupons shall be conditioned by suspending in an oven maintained at 70-80 °C (158-176 °F) for four hours. MIL-PRF-8184 acrylic coupons shall be conditioned for two hours at 120° ±1°C (248 ± °F). Immediately following the initial conditioning, the test coupons shall be conditioned for 48 hours at a standard condition of 22 ±2 ºC (72 ±4 ºF) and a relative humidity of 50 ±5 percent.

b. Four pieces of 4 by 4 by ¼ inch acrylic plastic conforming to finish A,

c. MIL-PRF-8184 and four identical pieces of acrylic plastic conforming to MIL-PRF-25690. Masking paper removed.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

d. Flannel cloth A-A-50129.

e. A cleaning tool made to accommodate a 4 by 4-inch piece of flannel cloth. The tool shall weigh 3 lbs. Refer to figure 1 and figure 2.

f. A test panel template, defined to be a long piece of acrylic with a 4 by 4-inch hole in the middle used to house a test panel, providing a tight, even fit.

g. MIL-PRF-83282 hydraulic fluid and Carbon Black soil mixture, prepared 24 hours beforehand.

h. ETS Model 212 or equivalent static meter. Refer to figure 3.

4.5.1.2 Cleaning apparatus. The apparatus to be used is the Gardner Washability machine or equivalent as approved by the qualifying activity. The brush holder of the machine shall be replaced by a holder made to accommodate a 4 by 4-inch (10.2 by 10.2 cm) piece of flannel cloth. The weight of the holder shall be adjusted to 3 lbs. (1.36 kg). A template shall be prepared from ¼ inch (0.64 cm) thick acrylic plastic, the same size as the bottom of the tray of the machine measuring 7 by 18 inches (17.8 by 45.7 cm). A rectangle shall be cut from the center of this template large enough to permit a tight fit for a plastic test panel, measuring 4 by 4 by ¼ inch (10.2 by 10.2 by 6.4 cm).

4.5.1.3 Anti-static characteristics apparatus. Place the test panel on a grounded metallic plate. Secure the static meter one inch above the surface of the test panel. Once secured, zero the measurement on the static meter. The static meter shall be zeroed with the test panel prior to performing the cleaning efficiency test.

4.5.1.4 Cleaning efficiency procedure. Prepare two 4 by 4 by 0.25-inch pieces of acrylic coupons conforming to MIL-PRF-25690 and two similar panels conforming to MIL-PRF-8184. Prepare the soil mixture by blending 50 grams of carbon black and 500 grams of MIL-PRF-83282 hydraulic fluid first by hand, then with a high-speed blender. Allow the mixture to blend for 15 minutes, and then allow it to sit for 24 hours prior to use. Use a flannel cloth to lightly soil one face of a test panel. Place the soiled test panel into the template. For Type I and Type II, apply an even coating of the test compound onto the test panel using circular motions with a clean piece of flannel cloth. Allow compound to dry for 10 minutes. For Type III, liberally apply to soiled panels and allow to dwell for 5 minutes. Prior to cleaning, blot excess cleaner with flannel wipe. Secure a clean piece of flannel cloth onto the cleaning tool, ensuring that it is lightly stretched on the tool. Pass the cleaning tool fully over the soiled test panel from side to side, without applying downward pressure for a total 10 cycles. Examine the test panel and if residue remains after the initial cleaning, repeat the cleaning process. Make sure the template is completely cleaned off prior to testing each panel.

4.5.1.5 Anti-static characteristics testing. Within two minutes of cleaning the test panel, measure the anti-static characteristics. Place the cleaned test panel onto a grounded metallic plate. Secure the static meter one inch above the surface of the test panel to begin measuring.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

Record a measurement every ten seconds for 100 seconds, then every fifty seconds for 200 seconds. Ensure that static measurements are dissipating during duration of test and transmittance conforms to requirements specified in 3.3.

4.5.1.6 Removability (Type I and Type II). Apply the polish to a clean panel and allow it to dry for 24 hours. After 24 hours, clean the panel with a flannel cloth. Note the amount of time needed to completely remove the polish in accordance with 3.3. Also note if it cannot be removed by hand.

4.5.2 Polishing efficiency procedure. Prepare two 4 by 4 by 0.25-inch pieces of acrylic coupons conforming to MIL-PRF-25690 and two similar panels conforming to MIL-PRF-8184. Remove masking paper, rinse both sides with distilled water, and dry each panel by blowing it lightly with nitrogen or filtered air. Be careful to only handle the edges of each specimen. Measure and record the initial haze and luminous transmittance values of each acrylic panel, in accordance with ASTM D1003, prior to abrading. Abrade one side of each at 100 strokes, using the Oscillating Sand Technique per ASTM F735 (50 cycles = 100 strokes). The abrasive shall be Alundum ZF-12. Wash panel with distilled water, then dry with nitrogen or filtered air and ensure the abrasion is uniform over the entire surface. Measure haze and luminous transmittance on each coupon after the abrasion cycle, where the resulting haze shall be 35% ± 10% of the initial value. For Type I and Type II, apply a coating of polish to the abraded side of the coupon using a circular motion and piece of flannel cloth equivalent to A-A-50129. For Type III, liberally apply to the abraded panels. Allow it to dry for ten minutes before polishing it using a new piece of flannel cloth over a weighted device exerting a pressure of 6 lbs. Refer to figure 4. The device consists of an inverted 8 ounce glass jar containing metal shots. Polish specimen until there is no evidence of sample residue left on panel. Re-measure haze and luminous transmittance on each coupon. The results shall conform to requirements specified in 3.4.

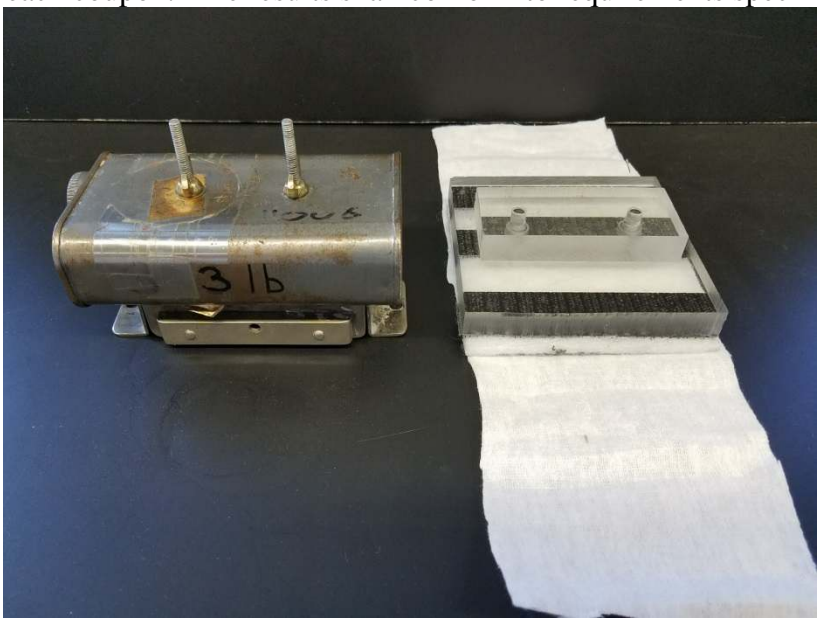


FIGURE 1. 3lb. cleaning tool disassembled.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

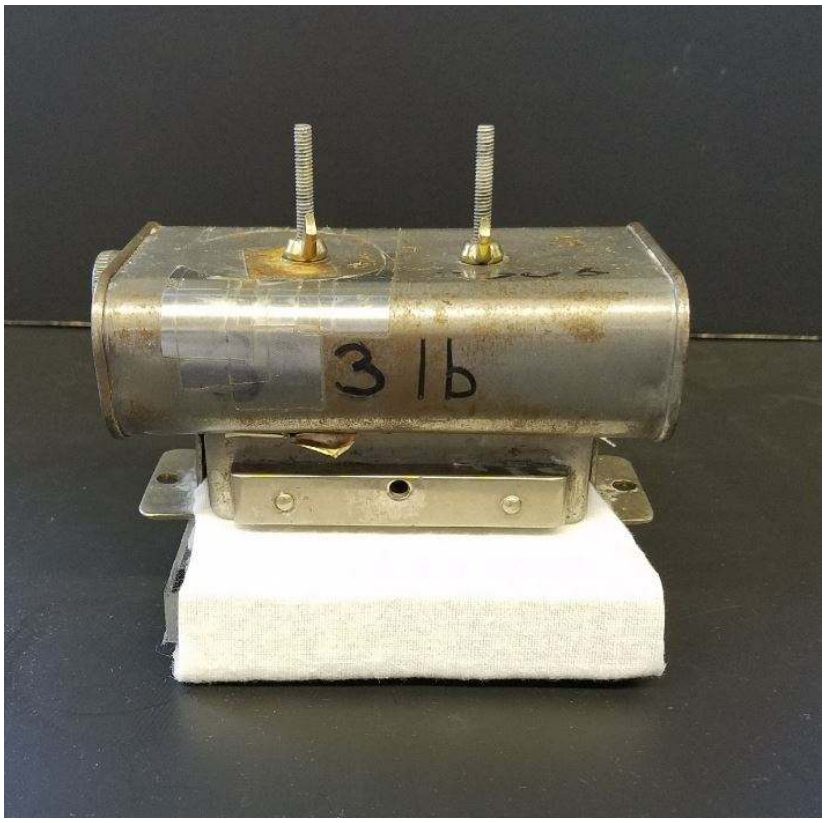


FIGURE 2. 3lb. cleaning tool assembled.



FIGURE 3. ETS Model 212 static meter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.



FIGURE 4. 6 lb. polishing tool.

4.5.3 Stress crazing test. Stress crazing effects of the polish shall be determined by ASTM F484. Ten minutes after the calculated load is applied, the specimens shall be examined for craze (cracks or fissures); crazed specimens shall be replaced. The polish shall be applied, using a piece of flannel in accordance with A-A-50129 or equivalent as approved by the qualifying activity, to the top (tension side) of the specimens at time intervals of 30 minutes, 1 hour, 2 hours, 4 hours, and 8 hours after the initial 10-minute period. An increase of stress on the specimen through an exertion of pressure when applying the polish shall be avoided. After 24 hours, the specimens shall be examined for evidence of chemical attack and for craze while under stress. To prevent heating of the specimens, the light source shall be utilized only when examining the specimen for craze. All craze appearing at the edge of the specimen shall be disregarded unless they grow and extend 1/8 inch (0.32 cm) from either edge of the specimen. Tape the edge of the coupons to avoid edge impingement. Specimens shall conform to requirements specified in 3.5.

4.5.4 Flash point test. The flash point of the cleaning and polishing compound shall be determined in accordance with ASTM D56, and the results shall conform to the requirements specified in 3.6.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

4.5.5 Sandwich corrosion test. The polish shall be tested as received. Testing shall be conducted for 24 hours at standard room temperature of 22 ±2 ºC (72 ±4 ºF) in accordance with ASTM F1110, and results shall conform to requirements specified in 3.7.

4.5.6 Sealant compatibility test.

4.5.6.1 Preparation of test specimens. Sealants qualified to SAE AMS-S-8802, Class B-2 and MIL-PRF-81733 Type II, Class 2 shall be mixed as specified by their respective manufacturers and processed to form sheets 0.125 inch (3.18 mm) thick. The sealant shall be cured for 14 days at 22 ±2 ºC (72 ±4 ºF) at 50 ±5 percent relative humidity. These conditions shall be considered standard conditions. The sealing compound may be given an accelerated cure for 48 hours, minimum at standard conditions followed by 24 hours, minimum at 60 ºC (140 ºF). The cured sealants are the sheet stock from which the specimens for each sealant shall be cut.

4.5.6.2 Test procedure. The instantaneous Type A Durometer hardness of each sealant specimen shall be measured as specified in ASTM D2240 before exposing it to the polish. The reading shall be taken using two 0.125 inch (3.2 mm) thick specimens, stacked to make a total thickness of 0.25 inch (6.4 mm). Two specimens of each sealant shall be immersed in cleaner at standard conditions and at 60 ºC (140 ºF) for 24 hours. After exposure, specimens shall be removed, wiped dry, and tested within 30 minutes for Type A Durometer hardness. Record hardness before and after exposure and document other material changes (color, softening, dissolution, tackiness). Specimens shall conform to requirements specified in 3.8.

4.5.7 Accelerated storage stability test procedure.

4.5.7.1 Cold cycle. Take a 16-ounce bottle and transfer contents to an appropriate Nalgene bottle and place in a cold box at a temperature of 0° ±2 °C (32 °F ±4 °F) for one hour. After one hour, remove from the cold box and allow sample to warm to ambient room temperature. Note any physical changes in sample.

4.5.7.2 Hot cycle. Take the same sample bottle conditioned in 4.5.7.1 and place in an oven at 60° ±2 °C (140 °F ±4 ºF) for three hours. After three hours, remove bottle and allow it to cool to ambient room temperature. The Type I polish shall be shaken by hand for one minute. The Type II polish shall be stirred for one minute. The sample shall be visually examined as specified in 3.9.

4.5.8 Room temperature storage stability test procedure. Two 13-ounce cans of Type III polish or two 16-ounce containers of the Type I or Type II polish shall be placed in a clear container and stored in the dark for 6 months at 22° ±2 °C (72° ±4 ºF). The containers of Type I polish shall then be removed from storage and be shaken thoroughly by hand for one minute. The Type II polish shall be stirred for one minute. After sitting 4 hours, the sample shall then be examined for separation, crystallization or other significant change in physical properties. After examination, the polish that has been stored shall then be subjected to the tests specified in 4.5.1, 4.5.2, 4.5.3 and 4.5.5 and conform to requirements specified in 3.10.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

4.5.9 Consistency (Type I) test procedure. Consistency shall be determined by ASTM F1080. Mix 250 mL of sample in a blender for one minute or until vortex forms. Ensure consistometer is level before adding sample to the reservoir. Add 100 mL of mixed sample to the reservoir and level with a spatula. Open consistometer gate and start timer. Record the distance sample has flowed after 5 minutes. Results shall conform to the requirements in 3.11.

4.5.10 Effects on painted surfaces test. Effects on painted surfaces shall be determined in accordance with ASTM F502 and conform to requirements in 3.12.

4.5.11 Fourier Transform Infrared Spectroscopy (FTIR) test. Dispense a small sample onto the ATR Crystal of the FTIR instrument. Operate the instrument/software to perform IR scan and obtain IR spectrum. Compare scan spectrum to the known retain standard spectrum. The obtained FTIR spectrum shall match the standard spectrum with no missing or extraneous peaks. Any other peaks or contaminants identified (or missing) are cause for batch lot failure or re-test. Storage stability spectrum shall match the initial spectrum with no missing or extraneous peaks. Spectrum shall conform to requirements specified in 3.13.

4.5.12 Workmanship inspection. Polish shall be inspected upon initial receipt and conform to requirements specified in 3.14.

4.5.13 Solids test. Shake the sample for a minimum of one minute. Place 5 grams of polish into each of three weighing dishes and record weight to within ±0.0001 gram. Place the dishes in a forced draft oven for 4 hours at 121° ±5 °C (250° ±10 °F). Cool the dishes to room temperature in a desiccator and reweigh to determine the percent of non-volatiles.
Results shall conform to requirements specified in 3.11.

4.5.14 Identification of material inspection. Visually examine the test container for conformance to 3.16.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the military service's system commands. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

6. NOTES

INFORMATION FOR GUIDANCE ONLY. (This section contains information of a general or explanatory nature that is helpful, but is not mandatory.)

6.1 Intended use. The polish is intended for use in the cleaning and polishing of plastic materials in the removal of light scratches, and in the application of an anti-static film that will prevent the electrostatic attraction of dust, lint, ash, etc., to the acrylic plastic.

6.2 Acquisition requirements. Acquisition documents should specify the following:

a. Title, number, and date of this specification
b. Type required (see 1.2)
c. Quantity
d. Size of container
e. Additional markings, if required
f. Packaging requirements (see 5.1)

6.3 Qualification. With respect to products requiring qualification, awards will be made only for products which are, at the time set for opening of bids, been tested and approved for inclusion in the applicable Qualified Products List (P-P-560), whether or not such products have actually been so listed by that date. The attention of the contractors is called to these requirements, and manufacturers are urged to arrange to have the products that they propose to offer to the Federal Government tested for qualification in order that they may be eligible to be awarded contracts or orders for the products covered by this specification. Information pertaining to qualification of products may be obtained from the Commander, Naval Air Warfare Center Aircraft Division, Code 4.3.4.6, Building 2188, Patuxent River, MD 20670-1908. An online listing of products qualified to this specification may be found in the Qualified Products Database (QPD) at https://assist.dla.mil.

6.3.1 Qualification report. The sample must be accompanied by a report from the manufacturer or an acceptable commercial laboratory. The report in duplicate must show the product inspection results for all the requirements of this specification and will refer specifically to the applicable requirements in the specification. The qualification inspection performed by the qualifying laboratory will consist of a review for approval of the manufacturer's report to determine compliance with all of the requirements of Section 3 of this specification. Unless otherwise specified, the qualification inspection will not be complete until conformance to the storage stability requirement (3.10) has been established.

6.3.2 Toxicological data. The manufacturer must provide a certification that the polish contains no substance known to be toxic to the user under normal conditions of use (3.3). The contractor must furnish the toxicological data (3.2.1) necessary to evaluate the safety of the polish for its intended use. A statement must include the chemical name and the percent of each ingredient. These reports must be signed by an authorized representative and must be accompanied by evidence of the agent's authority to bind his principal. Commander, Naval Air

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.

Warfare Center Aircraft Division, Code 4.3.4.6, Building 2188, Patuxent River, MD 20670-1908.

6.3.3 Retention of qualification. In order to retain qualification of a product approved for listing on the Qualified Products List (QPL), the manufacturer must verify by certification to the qualifying activity that the manufacturer's product complies with the requirements of this specification. The time of periodic verification by certification is in two-year intervals from the date of original qualification. The Government reserves the right to re-examine the qualified product whenever deemed necessary to determine that the product continues to meet any or all of the specification requirements.

6.3.3.1 Material composition and performance. Material furnished under contract must be identical with polish samples that have been submitted by the manufacturer and have been inspected and approved for inclusion in the Qualified Products List. In the event that material furnished under contract is found to deviate from the composition of the approved product or that the product fails to perform satisfactorily in service, approval of such material will be subject to immediate withdrawal from the Qualified Products List.

6.4 Subject term (key word) listing.

Anti-static film
Cleaning
Crazing
Fourier Transform Infrared Spectroscopy (FTIR)

6.5 Changes from previous issue. Marginal notations are not used in this revision to identify changes with respect to the previous issued due to the extent of the changes.

CONCLUDING MATERIAL

Custodians:
Army - GL
Navy - AS

Preparing activity:
Navy - AS
(Project 7930-2018-001)

Review activities:
Army - EA, MD

CIVIL AGENCY:
GSA - FAS
HHS - FDA

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at https://assist.dla.mil.

Source: https://assist.dla.mil -- Downloaded: 2026-10-26T11:17Z
Check the source to verify that this is the current version before use.