MIL-P-43700C
1 May 1987
SUPERSEDING
MIL-P-43700B
20 March 1980

MILITARY SPECIFICATION

PONCHO, WET WEATHER

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This document covers two types and two classes of extra lightweight ponchos, with hoods.

1.2 Classification. The ponchos shall be of the following types and classes as specified (see 6.2).

Type I	-	Standard size (92 inches by 66 inches)
Class 1	-	Olive green 207
Class 3	-	Woodland camouflage
Type II	-	Small size (82 inches by 60 inches)
Class 3	-	Woodland camouflage

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Documents. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: U.S. Army Natick Research, Development, and Engineering Center, Natick, MA 01760-5014 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8405

DISTRIBUTION STATEMENT A. Approved for public release; distribution is unlimited

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

FEDERAL

V-T-285 - Thread, Polyester.
PPP-B-636 - Boxes, Shipping, Fiberboard.
PPP-T-45 - Tape, Gummed, Paper, Reinforced and Plain, For Sealing and Securing.

MILITARY

MIL-B-371 - Braid, Textile, Tubular.
MIL-F-10884 - Fasteners, Snap.
MIL-G-16491 - Grommet, Metallic.
MIL-L-35078 - Loads, Unit: Preparation of Semiperishable Subsistence Items; Clothing, Personal Equipment and Equipage; General Specification for
MIL-C-43473 - Cloth, Coated, Nylon, Polyurethane Coated.

STANDARDS

FEDERAL

FED-STD-191 - Textile Test Methods.
FED-STD-751 - Stitches, Seams and Stitching.

MILITARY

MIL-STD-105 - Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129 - Marking for Shipment and Storage.
MIL-STD-147 - Palletized Unit Loads.
MIL-STD-731 - Quality of Wood Members for Containers and Pallets

(Copies of documents required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting activity.)

2.2 Other publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted shall be those listed in the issues of the DODISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS shall be the issues of the nongovernment documents which are current on the date of the solicitation.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 3951 - Standard Practice for Commercial Packaging

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Technical society and technical association documents are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

2.3 Order of precedence. In the event of a conflict between the text of this document and the references cited herein, the text of this document shall take precedence. Nothing in this document, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Guide samples. Samples, when furnished, are solely for guidance and information to the contractor (see 6.3). Variations from this document may appear in the sample in which case this document shall govern.

3.2 Materials.

3.2.1 Coated cloth. The coated cloth utilized in the fabrication of the class 1 poncho shall be 1.6 ounce rip-stop nylon, Olive Green 207, polyurethane coated one side, conforming to type I of MIL-C-43473. The coated cloth utilized in the fabrication of the class 3 poncho shall be 1.6 ounce rip-stop nylon, woodland camouflage pattern, polyurethane coated one side, conforming to type III of MIL-C-43473.

3.2.2 Thread. The thread for seaming the ponchos shall be polyester thread type I, class 1, sub-class A, sizes A and AA conforming to V-T-285.

3.2.2.1 Color and colorfastness. All thread shall be dyed Olive Drab S-1, C.A. 66022, and no colorfastness requirements shall apply.

3.2.2.2 Thread lubricant. Water and isopropyl alcohol only may be used for lubrication of the thread during sewing of the coated cloth (see 4.3.1.1).

3.2.3 Grommets. The grommets shall conform to type II, class 3, sizes 0 and 3 of MIL-G-16491.

3.2.4 Snap fasteners. The snap fasteners shall consist of a socket and stud eyelet combination conforming to MIL-F-10884 as follows:

a. The socket shall be construction A, B, C, or D, style 2, finish 2.
b. The stud eyelet combination shall be size 1 or 2, style 2, finish 2.

3.2.5 Drawcords. The drawcords shall be braid, textile, dyed Olive Green 107, conforming to type IV, class 3 of MIL-B-371 except that the requirement for colorfastness to laundering shall not apply. The ends of the drawcord shall be either tipped or resin coated.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.2.6 Clamp, cord. The cord shall consist of a lock body and lock wheel. The lock body shall conform to Fastex No. 238-390703-00-5612, color GN604, or equal, and the lock wheel shall conform to Fastex No. 238-082051-00-0101, or equal, (see 4.3.1.1 and 6.6).

3.2.7 Reinforcement materials.

3.2.7.1 Snap fastener and grommet reinforcements. The cloth for reinforcing the grommets and snap fasteners shall be lightly coated cotton cloth weighing a minimum of 7.5 ounces per square yard and having a minimum breaking strength of 75 pounds in both warp and filling. The light coating on both sides shall be accomplished within a polymerized or copolymerized vinyl chloride resin plasticized exclusively with either phosphate or phthalate esters (see 4.3.1.1).

3.2.8 Seam sealant. The seam sealant used to seal the seams and allowable needle holes shall be a dull unpigmented solvent solution of polyurethane. The unpigmented sealant may be tinted providing there is no visual change in the exterior appearance of the garment and no infrared reflectance change of the finished seam when tested as specified in MIL-C-43473. If plasticization of the sealant is necessary, only phosphate or phthalate ester plasticizer may be used (see 4.3.1.1). The sealant shall meet the hydrolytic stability requirement when tested as specified in 4.3.1.

3.2.8.1 Color and appearance. The seam sealant used on the class 1 poncho, when dry, shall produce a color gloss and appearance matching the basic coated cloth specified in 3.2.1. The seam sealant used on the class 3 ponchos, when dry, shall not change the color gloss and appearance of the camouflage print on the basic camouflage coated cloth specified in 3.2.1, when tested as specified in 4.3.1.

* 3.2.9 Seam dusting powder. All sealant areas shall be dusted. The dusting powder shall be whiting, talc or other finely divided mineral material which does not support mildew growth (see 4.3.1.1).

3.3 Design. The poncho shall have sides and ends that are hemmed and shall be equipped with snap fasteners for closing, as well as grommets for attaching tent pin lines. The poncho shall have a hood with a drawcord for face opening adjustment. In addition, a drawcord shall be included for type I, class 3 poncho for waist adjustment.

3.4 Patterns. Standard patterns which provide an allowance of 1/2 inch for all seams except waist drawcord tabs and side edges of hood facing pieces which provide an allowance of 1/4 inch, and separate side and end facings which provide an allowance of 3/8 inch will be furnished by the Government. The Government patterns shall not be altered in any way and are to be used only as a guide for cutting the contractor's working patterns. The working patterns shall be identical to the Government patterns.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.4.1 List of pattern parts.

3.4.1.1 Method 1. The component parts of the poncho, constructed in accordance with method 1, shall be cut from materials as specified in accordance with the pattern parts indicated:

List of pattern parts

Materials	Nomenclature	Cut Parts
Cloth, coated, nylon, olive green polyurethane coated; or	Body of poncho	2
	Hood	1
Cloth, coated, nylon, woodland camouflage pattern polyurethane coated, as applicable	Hood facing piece	2

3.4.1.2 Method 2. The component parts of the poncho, constructed in accordance with method 2, shall be cut from materials as specified in accordance with the pattern parts indicated:

List of pattern parts

Materials	Nomenclature	Cut Parts
Cloth, coated, nylon, olive green polyurethane coated; or	Neck reinforcement piece	1
	Hood	1
Cloth, coated, nylon, woodland camouflage pattern polyurethane coated, as applicable	Hood facing piece	2
	Body of poncho	1

3.5 Construction. The construction shall conform in all respects to the requirements specified in tables I, or II and herein. Figures 1, 2, and 3 are furnished solely for guidance and information. Should variation from the document appear in the figures, the document shall govern.

3.5.1 Care during fabrication. Care shall be taken during fabrication operations, especially during seaming, stitching, and sealing, to insure that the coated cloth area adjacent to the seams is not damaged (see 6.4).

3.5.2 Stitches, seams, and stitches. All stitches, seams and stitching shall conform to FED-STD-751. The type of seam, stitching, and stitches per inch shall be as specified in table I or II as applicable. Seam allowances shall be maintained with seams sewn so that no raw edges, run-offs, twists, pleats, puckers, or open seams occur. The needle shall be the smallest possible size which can be used with specified thread in order to minimize the size of the hole made in the coated cloth by the needle.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.5.2.1 Type 301 stitching. Ends of all stitching shall be backstitched or overstitched 1/2 inch minimum except when caught in other stitching or turned under in a hem. Thread tension shall be maintained so that there will be no loose stitching resulting in puckering of the materials sewn. The lock shall be embedded in the materials sewn.

3.5.2.1.1 Repairs of type 301 stitching. Repairs of type 301 stitching shall be as follows:

a. When thread breaks or bobbin run-outs occur during sewing, the stitching shall be repaired by restarting the stitching a minimum of 1 inch back of the end of the stitching. 1/

b. Thread breaks or two or more consecutive skipped or run-off stitches noted during inspection of the item (in-process or end item) shall be repaired by overstitching. The stitching shall start a minimum of 1 inch in back of the defective area and continue a minimum of 1 inch beyond the defective area onto the existing stitching. Loose or excessively tight stitching shall be repaired by removing the defective stitching, without damaging the materials, and restitching in the required manner. 1/

1/ When making the above repairs, the ends of the stitching are not required to be backstitched.

3.5.2.2 Type 401 stitching. Thread tension shall be maintained so that there will be no loose stitching. Both ends of all seams or stitching produced with 401 stitch type, when not turned under in a hem or held down by other stitching, shall have a 1/2 to 3/4 inch chain extending beyond each end. The looper (underthread) shall be on the inside of the poncho. All repairs shall be in accordance with 3.5.2.1.1a and 3.5.2.1.1b. Repairs may be made using 301 stitch type.

3.5.3 Sealing of seams and stitching.

3.5.3.1 Sealed areas. All stitching, except the peripheral hems and the facing piece seams around the face opening of the hood, shall be sealed with the sealant specified in 3.2.8 to meet the seam hydrostatic requirement in 3.5.4.1. The waist drawcord tabs, when applicable, shall be sealed on the outside with a minimum of three coats of sealant. The straight joining seams on the front and back, or the straight side joining seam of the poncho shall be sealed with a minimum of three coats of sealant on either the inside or outside of the poncho. The center seam of the hood and the seam joining the hood to the neck of the poncho shall be sealed with a minimum of three coats of sealant on either the inside or outside of the poncho, and with a minimum of one coat of sealant on the side opposite to that sealed with the three coats. Additional coats may be applied to any seam on either side as required to meet the seam hydrostatic requirement.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.5.3.2. Application. The sealant shall be applied in such a manner as not to cause twists, pleats or puckers on the seam or on the cloth adjacent to the seam. The first coat of sealant on the inside and outside shall be brushed on and worked in such a manner as to completely wet and cover the stitching and needle holes and shall be worked in under any turned edges of the seams. The succeeding coats of sealant may be brushed or squeegeed on. The cement line shall extend not less than 1/4 or more than 1 inch on each side of the seam or stitching. The coats of sealant shall be allowed to dry before the ponchos are folded or before sealed surfaces are allowed to contact any other parts of the poncho or other sealed surfaces.

3.5.3.3. Dusting. When the coats of sealant are dry, the sealed seams shall be dusted thoroughly with the seam dusting powder specified in 3.2.9. Care shall be exercised that only sealed seam areas are dusted and that dust is not distributed over other areas of the poncho.

3.5.4 Sealed seam area performance requirements.

3.5.4.1 Hydrostatic resistance. The sealed seams and the immediate adjacent area shall pass the hydrostatic test as specified in 4.3.4. Before testing, the test area shall be flexed as specified in 4.4.1 and shall show no peeling, whitening, or lifting of the sealant.

3.5.4.2 Resistance to low temperature flexing. Unless otherwise specified (see 6.2), the seam sealant shall be tested for resistance to low temperature flexing as specified in 4.3.4. After testing, the seam sealant show no cracking, flaking, or separation from the coated fabric.

3.5.4.3 Blocking. The sealed seam shall block no more than Scale Rating No. 3 when tested as specified in 4.3.4.

3.6 Marking.

3.6.1 Type I. Each type I, (class 1 and 3) poncho shall have a combined contractor and instruction marking. The location shall be as specified in figure 1 except that, for the class 3 poncho, the exact location shall be adjusted so that none of the marking is any part of the black portion of the camouflage print. The marking shall be clearly and legibly printed directly on the uncoated side (inside) of the poncho with black, 1/4 inch high letters and shall contain the following data:

Nomenclature
Stock Number
Name of contractor
Date and number of contract
Multipurpose ponchos
Rain garment and ground sheet
Blanket or sleeping bag cover (snap the two long edges together)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Tent (snap two ponchos together as side walls)
Floor (third poncho will snap inside tent as a floor)
Two open tents will go end to end with common center pole

The marking shall retain good legibility and shall show fair fastness to crocking, both wet and dry, when tested as specified in 4.3.4.

3.6.2 Type II. The type II, (class 3) poncho shall be marked in accordance with the marking for the class 3 poncho in 3.6.1 except that the data shall be as follows:

Nomenclature
Stock Number

The marking shall retain good legibility and shall show fair fastness to crocking, both wet and dry, when tested as specified in 4.3.4.

* 3.6.3 Care instruction marking (type I and II ponchos). Each poncho shall have care instructions marking located approximately 1 inch above the marking specified in 3.6.1 and 3.6.2. The marking shall be clearly and legibly printed directly on the uncoated side (inside) of the poncho with black, 1/4 inch high letters and shall contain the following information:

CAUTION: DO NOT MACHINE LAUNDER. DO NOT DRY CLEAN. HAND WASH IN WARM WATER AND MILD SOAP OR DETERGENT USING A SOFT BRISTLE BRUSH. RINSE THOROUGHLY AND AIR DRY.

The marking shall retain good legibility and shall show "fair" fastness to crocking, both wet and dry, when tested as specified in 4.3.4.

3.7 Repairs on finished poncho.

3.7.1 Repairable areas generated during manufacture of the poncho shall be generally defined as follows:

3.7.1.1 Scuffs. Any break in the coated surface (nylon yarns intact) other than a pickoff of the coating or a pinhole. Scuffs not exceeding four in number may be repaired. The size of any repair shall not exceed 2 inches in length and 1 inch in width.

3.7.1.2 Pinhole. Pinholes in coating not exceeding eight in number may be repaired and the sizes of the repair shall not exceed 3/4 inch in length and width.

3.7.1.3 Needle holes. Needle hole repairs shall not exceed 2 inches in length and 1 inch in width.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.7.1.4. Pick-offs. Pick-offs in the coating not exceeding four in number may be repaired and the overall size of such repairs shall not exceed 1/2 inch in diameter.

3.7.2. Repair compound. The repair compound shall be as specified in 3.2.8.

3.7.3 Repair procedure. Each repairable area shall be coated with a minimum of two coats of the repair compound. The first coat of compound shall be brushed in and worked in such a manner as to completely wet and cover the scuff, pinhole, needle hole, or pick-off. The second coat shall be brushed smoothly and evenly over the first coating. The repaired areas, after the compound is dry, shall be lightly dusted with the mica specified in 3.2.9.

3.7.4 Requirements for repaired areas. The repaired areas shall show no stiffening or other defects that would affect the serviceability or the outside appearance of the poncho. The repaired area shall conform to the blocking requirements of the sealed seams specified in 3.5.4.3. The repair compound shall be well adhered to the coated fabric and when subjected to a flexing or scrubbing action between the hands, will show no lifting of the edge, and no cracking, flaking or removal of the repair compound.

3.8 Manufacturing operations requirements. The poncho shall be made in accordance with all operations listed in table I or II although not necessarily in the same sequential order, utilizing working patterns which have been cut by the supplier to conform with standard patterns.

No part of the poncho shall be cut less than 1/2 inch from the beginning of the coating of an untrimmed edge of the coated cloth. The type I poncho shall conform to the finished measurements shown in figure 1. The type II poncho shall conform to the finished measurements shown on figure 2. Stitches, seams and stitching shall conform to the requirements of 3.5.2 and sealing of seams and stitching shall be in conformance with 3.5.3.

3.8.1 Method 1. The center seamed poncho shall be made in accordance with the operations listed in table I.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE I. MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
1.	Cut poncho. a. The coated side of the material shall be on the outside of the poncho. b. The coated cloth shall be carefully laid in uniform widths and lengths and care shall be taken in spreading the material. The plies shall not be stretched or pulled and one side of the lay shall be even. c. All component parts of the poncho shall be cut out of the material in such a manner as to assure that they harmonize with each other in shade, except the waistcord grommet tabs, hood facing, side and end facings. d. Side and end facings shall be cut with sufficient seam allowance to fit a standard folder and shall finish 1-1/2 ± 1/4 inches wide. The facings may be cut on a stripping machine. e. All snap fastener and grommet reinforcement pieces shall be cut of one continuous piece the full length or width of the poncho. The reinforcement pieces shall be of sufficient width to be caught in the double stitching of the facings. f. Cut hood drawcord 46 ± 1 inch long. * g. Cut waist drawcord 93 ± 1 inches long (applicable only for type I, class 3 poncho).						

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2020-10-21T22:05Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

TABLE I. (cont'd)

NO.	MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
1.	Cut poncho. (cont'd) h. The use of drill holes is prohibited except for marking the position of the center hem grommets.						
2.	Replacement of damaged parts. a. Care shall be exercised during the spreading, cutting, and manufacturing operations to assure that material defects and damages, as specified in 4.3.2, are excluded and replaced with nondefective and properly matched material. b. There shall be no replacement of parts or removal or replacement of stitching after assembly of the finished poncho.						
3.	Join front halves of poncho. Join front halves of poncho from bottom to neck with two rows of stitching, 3/16 inch apart. The rows of stitching shall be 1/16 to 1/8 inch from turned edges.	401	LSc-2	9-11	AA	A or AA	
4.	Attach hood to poncho. Seam hood to neck of poncho in a continuous seam from edge to edge with the hood overlapping the body on the outside. The seam shall be two rows of stitching 3/16 inch apart. The rows of stitching shall be 1/16 to 1/8 inch from the turned edges.	401	LSc-2	9-11	AA	A or AA	

NO.	TABLE I. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
5.	Join center back seam and hood.						
	Join center back seam and hood in one continuous operation with two rows of stitching 3/16 inch apart. The rows of stitching shall be 1/16 to 1/8 inch from turned edges. Hood-poncho joining seams may be staggered by not more than 1/2 inch. Bottom edge of poncho and front of the hood shall finish even.	401	LSc-2	9-11	AA	A or AA	
6.	Hem sides and ends of poncho.						
	a. All snap fasteners and grommets on the sides and ends of the poncho shall be reinforced and the reinforced pieces may be stitched in the hem in one operation. The reinforcement pieces shall be inside the hem between the body and facing and caught in each row of stitching.						
	b. The sides and ends of the poncho shall be faced with a strip of self material, the raw edges turned in and double stitched with stitching 1/16 to 1/8 inch from turned edges. The facing shall finish 1-1/2 ± 1/4 inches wide.	301	LSm-2	9-11	AA	AA	
	or	or					
		401	LSm-2	9-11	AA	A or AA	
	c. The sides and ends of the poncho may have grown-on hem as indicated by pattern. The ends shall be turned to the inside with the raw edge turned in and the hem stitched, 1/16 to 1/8 inch from each turned edge. Hem shall finish 1-1/2 ± 1/4 inches wide.	301	LSd-1	9-11	AA	AA	
		or					
		401	OSf-1	9-11	AA	A or AA	
	d. Close open ends of hems and facing in line with hem stitching.	301	SSa-1	9-11	AA	AA	

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

TABLE I. (cont'd)

NO.	MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
7.	Grommets. Eight grommets, size No. 3, reinforced, shall be inserted in the four hems and centered in the hems located as follows: (a) One in each corner; (b) One in each hem equidistant from the corners (1 inch tolerance permitted), (see operation 1.e).						
8.	Snap fasteners. The snap fasteners shall be inserted in both long hems as shown on figure 1 or figure 2 as applicable. There shall be no prepunched holes for inserting the snap fasteners. When the poncho is folded in half, either way, the snap fasteners shall correspond without gaping along the side seams when fasteners are snapped together.						
9.	Join hood facing pieces. a. The hood facing shall consist of left and right facing pieces of the basic fabric. b. Seam ends of left and right pieces at the back and at the front.	301	SSa-1	9-11	AA	AA	
10.	Position and attach hood grommets. Mark position and attach two No. 0 grommets through reinforcement pieces and front of hood as indicated by marks on pattern.						

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE I. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
11.	Seam facing to front of hood.						
	a. Seam facing to front edge of hood to form tunnel for face drawcord. Thread drawcord through grommets with drawcord crossing between grommets inside the facing.	301	SSa-1	9-11	AA	AA	
	b. Thread both ends of drawcord through the first hole of the slide keeper, then through the second hole and knot the ends.						
	c. Position drawcord around periphery of hood.						
	d. Turn down the facing over drawcord, turning the edge and single stitch 1/8 inch from edge, forming the face tunnel; the face drawcord tunnel shall finish 3/4 to 7/8 inch wide.	301	LSd-1	9-11	AA	AA	
	or						
	e. The back edge of hood facing may be hemmed prior to the seaming operation.	301	EFa-1	9-11	AA	AA	
	f. The joining seam at the top of facing shall be positioned on, or adjacent to the hood joining seam. The joining seam at the bottom of facing shall be centered between the face drawcord grommets at the front. A 1/2 inch off center tolerance is allowed for both positions.						

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

TABLE I. (cont'd)

NO.	MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
*12.	Make waist drawcord tabs (applicable only to type I, class 3 poncho).						
	a. Cut two pieces of the reinforcement material 1-1/8 inches wide by 5 inches long, fold in half, and attach a size No. 0 grommet to each tab, 1/2 to 5/8 inch front the folded edge, centered on the 1-1/8 inch width.						
	b. Spread open ends of tabs, position on the inside front (uncoated side of the poncho) as indicated by marks on the pattern and stitch each end with a 7/8 ± 1/8 inch box of stitching 1/8 to 1/4 inch from the edge.	301		9-11	AA	AA	
13.	Sealing of seams.						
	All seams and stitching shall be sealed as specified in 3.5.3.						
14.	Cleaning.						
	All ends of threads shall be trimmed and loose threads removed from poncho; all spots and stains shall be removed.						

NATICK Form 903

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.8.2 Method 2. The one-piece or side seamed poncho with manufacturing operations specified in table II, can be made in any of the three following ways:

a. One piece if coated cloth of sufficient width is available.

b. Two panels if the side panel does not exceed 20 inches in width.

c. Three panels when one side panel would exceed 20 inches. Then two side panels of equal width shall be used.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE II. MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
1.	Cut poncho. a. The coated side of the material shall be on the outside of the poncho. b. The coated cloth shall be carefully laid in uniform widths and lengths and care shall be taken in spreading the material. The plies shall not be stretched or pulled and one side of the lay shall be even. c. All component parts of the poncho shall be cut out of the material in such a manner as to assure that they harmonize with each other in shade, except the waistcord grommet tabs, hood facing, side and end facings, and neck reinforcement piece. d. Side and end facings shall be cut with sufficient seam allowance to fit a standard folder and shall finish 1-1/4 to 1-3/4 inches wide. The facings may be cut on a stripping machine. e. All snap fastener and grommet reinforcement pieces shall be cut in one continuous piece the full length or width of the poncho. The reinforcement pieces shall be of sufficient width to be caught in the double stitching of the facings. f. Cut hood drawcord 46 $\pm$ 1 inches long. * g. Cut waist drawcord 93 $\pm$ 1 inches long (applicable only for type I, class 3 poncho).						

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE II. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
1.	Cut poncho. (cont'd) h. The neck binding may be strip cut and shall be cut on the bias, 3/4 inch to 7/8 inch wide. i. The use of drill holes is prohibited except for marking the position of the center hem grommets.						
2.	Replacement of damaged parts. a. Care shall be exercised during the spreading, cutting and manufacturing operations to assure that material defects and damages, as specified in 4.3.2, are excluded and replaced with nondefective and properly matched material. b. There shall be no replacement of parts or removal or replacement of stitching after assembly of the finished poncho.						
3.	Join side pieces to poncho. Seam the long side to body poncho with two rows of stitching, 3/16 inch apart. The rows of stitching shall be 1/16 to 1/8 inch from turned edges.	401	LSc-2	9-11	AA	A	
4.	Hem sides and ends of poncho. a. All snap fasteners and grommets on the sides and ends of the poncho shall be reinforced and the reinforced pieces may be stitched in the hem in one operation. The reinforcement pieces shall be inside the hem between the body and facing and caught in each row of stitching.						

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

TABLE II. (cont'd)

NO.	MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
4.	Hem sides and ends of poncho. (cont'd)						
	b. The sides and ends of the poncho shall be faced with a strip of self material, the raw edges turned in and double stitched with stitching 1/16 to 1/8 inch from turned edges. The facing shall finish 1-1/2 ± 1/4 inches wide.	301	LSm-2	9-11	AA	AA	
		or					
		401	LSm-2	9-11	AA	A	
	or						
	c. The sides and ends of the poncho may have grown-on hem as indicated by pattern. The ends shall be turned to the inside with the raw edge turned in and the hem stitched, 1/16 to 1/8 inch from each turned edge. Hem shall finish 1-1/2 ± 1/4 inches wide.	301	LSd-1	9-11	AA	AA	
		or					
		401	OSf-1	9-11	AA	A	
	d. Close open ends of hems and facing in line with hem stitching.	301	SSa-1	9-11	AA	AA	
5.	Grommets.						
	Eight grommets, size No. 3, reinforced, shall be inserted in the four hems and centered in the hems located as follows: (a) One in each corner; (b) One in each hem equidistant from the corners (1 inch tolerance permitted), (see operation 1.e).						
6.	Snap fasteners.						
	The snap fasteners shall be inserted in both long hems as shown on figure 1 or figure 2 as applicable. There shall be no prepunched holes for inserting the snap fasteners. When the poncho is folded in half, either way, the snap fasteners shall correspond without gaping along the side seams when fasteners are snapped together.						

TABLE II. (cont'd)

NO.	MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
7.	Attach neck reinforcement piece.						
	Position the neck reinforcement piece on poncho with the upper edges even with the neck opening. Seam the lower edge of reinforcement piece through poncho with the stitching 1/16 to 1/8 inch from turned edge.	301	SSa-1	9-11	AA	AA	
8.	Make hood.						
	The backseam shall be joined with two rows of stitching 3/16 inch apart. The rows of stitching shall be 1/16 to 1/8 inch from turned edges.	401	LSc-2	9-11	AA	A	
9.	Join hood facing pieces.						
	a. The hood facing shall consist of left and right facing pieces of the basic fabric.						
	b. Seam ends of left and right pieces at the back and at the front.	301	SSa-1	9-11	AA	AA	
10.	Position and attach hood grommets.						
	Mark position and attach two No. 0 grommets through reinforcement pieces and front of hood as indicated by marks on pattern.						
11.	Seam facing to front of hood.						
	a. Seam facing to front edge of hood to form tunnel for face drawcord. Thread drawcord through grommets with drawcord crossing between grommets inside the facing.	301	SSa-1	9-11	AA	AA	

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE II. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
11.	Seam facing to front of hood. (cont'd)						
	b. Thread both ends of drawcord through the first hole of the slide keeper, then through the second hole and knot the ends.						
	c. Position drawcord around periphery of hood.						
	d. Turn down the facing over drawcord, turning the edge and single stitch 1/8 inch from edge, forming the face drawcord tunnel; the face drawcord tunnel shall finish 3/4 to 7/8 inch wide.	301	LSd-1	9-11	AA	AA	
	or						
	e. The back edge of hood facing may be hemmed prior to the seaming operation.	301	EFa-1	9-11	AA	A or AA	
	f. The joining seam at the top of facing shall be positioned on, or adjacent to, the hood joining seam. The joining seam at the bottom of facing shall be centered between the face drawcord grommets at the front. A 1/2 inch off center tolerance is allowed for both positions.						
12.	Join hood to neck of poncho.						
	a. Seam hood to neck of poncho through neck reinforcement piece and binding strip 1/4 to 3/8 inch seam allowance.	301	SSa-1	9-11	AA	AA	
	b. Turn hood over first stitching and then fold binding strip around and under the edges of the neck, reinforcement and hood and raise stitch 1/16 to 3/32 inch from folded edge through all plies of the material as shown on figure 3.	301	(Figure 3a shows finished seams)	9-11	AA	AA	

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE II. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
12.	Join hood to neck of poncho. (cont'd)						
	or						
	c. Seam hood to neck of poncho through neck reinforcement piece and binding strip with a folder.	301	BSb-1	9-11	AA	AA	
	d. Turn hood under bound edges of first seam and top stitch through hood 1/16 to 3/32 inch from the edge of bound seams.	301	(Figure 3b shows finished seams)	9-11	AA	AA	
13.	Make waist drawcord tabs (applicable only to type I, class 3 poncho).						
	a. Cut two pieces of the reinforcement material 1-1/8 inches wide by 5 inches long, fold in half, and attach a size No. 0 grommet to each tab, 1/2 to 5/8 inch front the folded edge, centered on the 1-1/8 inch width.						
	b. Spread open ends of tabs, position on the inside front (uncoated side of the poncho) as indicated by marks on the pattern and stitch each end with a 7/8 ± 1/8 inch box of stitching 1/8 to 1/4 inch from the edge.	301		9-11	AA	AA	
14.	Sealing of seams.						
	All seams and stitching shall be sealed as specified in 3.5.3.						

NATICK Form 903
1 Dec 76 EDITION OF 1 OCT 76 WILL BE USED UNTIL EXHAUSTED.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

NO.	TABLE II. (cont'd) MANUFACTURING OPERATIONS REQUIREMENTS	STITCH TYPE	SEAM AND STITCHING TYPE	STITCHES PER INCH	THREAD		
					NEEDLE	BOBBIN/ LOOPER	COVER
15.	Cleaning. All ends of threads shall be trimmed and loose threads removed from poncho; all spots and stains shall be removed.						

NATICK Form 903

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

3.9 Dimensions. The dimensions of the finished type I poncho and the location of the snap fasteners and grommets shall be as indicated in figure 1. The dimensions of the finished type II poncho and location of snap fasteners and grommets shall be as indicated in figure 2. The hood shall be 18 ± 1/2 inches in height and 15-1/2 ± 1/2 inches in width. Measurements shall be taken as indicated in 4.3.3. Tolerance for measurement of distance between side peripheral hem snap fasteners and grommets shall be 1/4 inch.

3.10 Workmanship. The poncho shall conform to the quality and grade of product established by this document. The occurrence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in this document where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

* 4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this document shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirement in the document shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2. Responsibility for dimensional requirements. Unless otherwise specified in the contract or purchase order, the contractor is responsible for assuring that all specified dimensions have been met. When dimensions cannot be examined on the end item, inspection shall be made at any point, or at all points in the manufacturing process necessary to assure compliance with all dimensional requirements.

4.2 Certificate of compliance. When certificates of compliance are submitted, the Government reserves the right to inspect such items to determine the validity of the certification.

4.3 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated hereinafter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

4.3.1 Component and material inspection. In accordance with 4.1, components and materials shall be inspected in accordance with all the requirements of referenced documents unless otherwise excluded, amended, modified, or qualified in this document or applicable purchase document. The seam sealant specified in 3.2.8 shall be tested for hydrostatic stability in accordance with 4.4.4 and for color, gloss and appearance in accordance with 4.4.5. The sample for testing shall be a one pint composite. The inspection level shall be S-1 and shall be used only to determine the number of containers to be sampled in arriving at the composite. Three specimens shall be tested for each characteristic and there shall be no failure of any specimen to meet the requirement as specified.

4.3.1.1 Component and material certification. A certificate of compliance will be accepted as evidence that the components and materials listed below conform to the requirements specified.

Component	Requirement paragraph
Thread lubricant (material)	3.2.2.2
Cord clamp	3.2.6
Reinforcement material (fastener and grommet)	3.2.7.1
Seam sealant (material only)	3.2.8
Seam dusting material	3.2.9

4.3.2 End item visual examination. The end item shall be examined for the defects listed in table II. The lot size shall be expressed in units of ponchos. The sample unit shall be one poncho. The inspection level shall be II and the acceptable quality level (AQL), expressed in terms of defects per hundred units, shall be 2.5 for major defects, 15.0 for major and minor A defects combined, and 65.0 for total (major, minor A, and minor B) defects combined.

Table III End item visual defects

Examine	Defect	Classification Major	Minor A	Minor B
Cleanness:				
	Any spot or stain of a permanent nature on any portion of garment which would be visible when poncho is worn.	X		
	Any spot or stain of a permanent nature not visible when poncho is worn.		X	
	Removable spot or stain on outside of poncho.			X
	Thread ends not trimmed.			X

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Cleanness: (cont'd)				
	Excessive seam dusting powder distributed over exterior or interior seams of poncho.		X	
	Dusting powder on any area other than seams (except that which may have come from seams as garment is folded).		X	
	Fabric or thread scraps not removed from garment.			X
Component and assembly:				
	Any defective component, (unless otherwise specified).	X		
	Any component part omitted, (unless otherwise specified).	X		
	Any required operation omitted or improperly performed.	X		
Drawcord:				
	Any end not tipped or resin coated.			X
	Any drawcord omitted or caught in tunnel stitching.	X		
	Any end not knotted.			X
Grommets:				
	Grommet within 1/16 inch of edge.	X		
	Omitted, broken, bent, or not securely clinched:			
	- one grommet.		X	
	- two grommets.	X		
	One or more too tightly clinched, cutting coated cloth.	X		
	One or more having sharp or rough edge.	X		
	Not clinched through reinforcement when applicable:			
	- one or two grommets.		X	
	- three or more grommets.	X		
	Any not completely on hem.	X		

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Marking:				
	Marking missing, incorrect, or illegible.		X	
	Not located as specified.			X
Coated cloth defects and damages:				
	Any blister.	X		
	Lump exceeding 1/4 inch in diameter or three or more lumps of any size within a square foot area.		X	
	Hard permanent crease or wrinkle.	X		
	Uneven coating resulting in sharply contrasting shade area of heavy warpwise lines.		X	
	Foreign matter.		X	
	Any uncoated area.	X		
Workmanship damages:				
	Needle chew.	X		
	Any mend, cut, or hole in other than hem area.	X		
	Any mend, cut, or hole in hem area:			
	- less than 3/16 inch in length or diameter.		X	
	- 3/16 inch or more in length or diameter.	X		
	Any tear or burn.	X		
	Any scuff, pinhole, pick-off, or needle hole uncoated.	X		
	Repair compound on fabric crack, lifts or flakes when flexed or scrubbed.		X	
	Any repaired area not dusted.		X	
	More than four scuffs repaired.		X	
	Any scuff repair exceeding 2 inches in length and 1 inch in width.		X	
	More than eight pinholes repaired.		X	
	Any pinhole repair exceeding 3/4 inch in length or width.		X	
	Any needlehole repair exceeding 2 inches in length and 1 inch in width.		X	

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Workmanship damages: (cont'd)				
	Any pick-off repair area exceeding 1/2 inch in diameter.		X	
	NOTE: Coated cloth defects and workmanship damages to the coating of the basic cloth, shall be determined by visual examination using through lighting on the finished poncho. The through lighting equipment shall conform to the following requirements: A table with a clear glass top, lighted with a minimum of two parallel 25-watt fluorescent bulbs spaced 5 to 6 inches apart (distance between bulbs). The top of the glass shall be 9 to 10 inches above the top of the bulbs. The inside of the light housing shall be painted flat white. The table, sides and ends, shall be 6 to 8 inches from the bulbs. The table shall be used in a darkened area. The darkened area shall be defined as follows: The surface to be examined shall be illuminated with not more than 25 foot candles of artificial or natural or combination of artificial and natural light with the test lights out (see 6.6). The poncho shall be examined with the outside of the poncho towards the table light.			
Sealing of seams and stitching:				
	Any seam or stitching required to be sealed, not properly sealed, i.e., sealant not under the turned edge of seam or does not completely cover the stitching or any needle hole, or evidence of air bubbles.	X		

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Sealing of seams and stitching: (cont'd)				
	Cement line extends less than 1/4 inch.		X	
	Cement line exceeds more than 1 inch on either side of seam or stitching.			X
	Sealant not dusted (to be scored only when the condition exists on the major portion of the seam).		X	
	Sealant not dull and transparent. 1/		X	
	Sealant changes color or appearance of seam area. 1/		X	
	Sealant cracks or flakes when creased. 2/	X		
	Sealant tacky. 2/	X		
	Seam badly twisted, pleated, or puckered when the condition is caused by improperly performed sealing operation. 2/			X
	Sealant blocked to the extent that unfolding of the poncho results in breaking of sealant or pick-off of coating from the fabric. 2/	X		
Seams and stitching:				
Accuracy of seaming:				
	Seam badly twisted, pleated or puckered.		X	
NOTE:	A characteristic of nylon is to show a certain amount of puckering at seams of stitching. This puckering is not to be classified as a defect.			
	Part of poncho caught in any unrelated operation or stitching.		X	
	End of stitching not caught in other seams or stitching, not securely backstitched.		X	
	Wrong shade of thread in contrast with color and shade of poncho.			X
	Rows of stitching in LSc-2 seams not 3/16 inch apart.			X

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Accuracy of seaming: (cont'd)				
	Stitching more than 1/8 inch from edge.			X
	Stitching less than 1/16 inch from edge resulting in no damages to the material.			X
	Stitching less than 1/16 inch from edge resulting in damage to the material.	X		
Open seams:				
	Open seam at peripheral hem or at hood facing piece:			
	- more than 1/4 inch but not more than 1 inch.		X	
	- more than 1 inch.	X		
	Any other open seam:			
	- more than 1/8 inch but not more than 1/2 inch.		X	
	- more than 1/2 inch.	X		
	NOTE: One or more broken or two or more continuous skipped or run-off stitches constitute an open seam. On double stitched seams, a seam is considered open when one or both sides of the seam is open.			
Raw edge (when edge is required to be turned under and stitched):				
	- on peripheral hem of poncho or facing of hood:			
	- more than 1/2 inch but not more than 1 inch.		X	
	- more than 1 inch.	X		
	NOTE: Raw edge not securely caught in stitching shall be classified as an open seam.			
Run-off:				
	Joining seam - when resulting in an open seam, use open seam classification.			

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Run-off: (cont'd)				
	No defect when not resulting in an open seam.			
Seam and stitch type:				
	Looper thread located on outside of poncho when 401 stitch type is used.			X
Stitch tension:				
	Loose tension in any area of peripheral hem or facing of poncho:			
	- more than 1 inch but not more than 2 inches.		X	
	- more than 2 inches.	X		
	Tight tension (stitches break when normal strain is applied to the seam or stitching).	X		
Stitches per inch (to be scored only when the condition exists on the major portion of the seam):				
	Less than minimum specified:			
	- 1 stitch.			X
	- 2 or more stitches.		X	
	More than maximum specified:			
	- 2 stitches.			X
	- 3 stitches.		X	
	- 4 stitches.	X		
Snap fastener:				
	Stud or socket omitted, defective, improperly clinched or having rough or sharp edge.	X		
	Stud and socket reversed, i.e., placed on side opposite to side indicated on figure.	X		

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Table III End item visual defects (cont'd)

Examine	Defect	Classification Major	Minor A	Minor B
Hood:				
	Drawcord not crossed between grommets.		X	
	Drawcord slide keeper omitted.		X	
	Drawcord not properly assembled through slide keeper.			X
	Drawcord end not knotted.			X
Waist drawcord tab:	(applicable only to type I, class 3 poncho)			
	The center of the waist drawcord tab less than 12-1/2 inches or more than 13-1/2 inches below the neck seam.		X	
	Drawcord not knotted each side of each garment.			X

1/ Although sealant passed component testing for color, gloss and appearance, the method of application in sealing operation may cause changes in color, gloss, and appearance of seam area if not properly applied.

2/ Poncho drawn for examination for these defects shall have been production folded for packing for a minimum of 1 hour.

4.3.3 End item dimensional examination. The end item shall be examined for the defects listed below. The lot size shall be expressed in units of ponchos. The sample unit shall be one poncho. The inspection level shall be S-3 and the AQL, expressed in terms of defects per hundred units, shall be 4.0.

Examine	Defect
Poncho body	Length more or less than specified as applicable.
	Width more or less than specified, as applicable.
	Width of hem less than 1-1/4 inches or more than 1-3/4 inches.

NOTE: Length measurement taken from end to end along center of poncho. Width measurement is taken from edge to edge. Height of hood measurement is taken with the hood folded in half, along face opening from top folded edge to seam joining hood to neck of poncho. Half width of hood measurement is taken with hood folded in half from front folded edge at point in line with lower edge of face openings.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

Examine	Defect
Hood	Height less than 17-1/2 inches or more than 18-1/2 inches. Width less than 15 inches or more than 16 inches.
Hem snap fasteners	Measurement of location of any snap fastener from another snap fastener or center grommet varies from nominal measurement specified in figure 1 or figure 2, as applicable, by more than 1/4 inch.
Hem grommets	Center hem grommet not equidistant from corner grommets by more than 1 inch.
Hood drawcord	Hood drawcord less than 45 inches or more than 47 inches.
Waist drawcord	Waist drawcord less than 92 inches or more than 94 inches (applicable only to type I, class 3 poncho).

4.3.4 End item testing. The methods of testing specified in FED-STD-191, wherever applicable and as listed below shall be followed. All tests are applicable to the individual sample unit. The lot size shall be expressed in units of one poncho. The sample unit shall be one completely fabricated poncho. The inspection level shall be S-2 and the AQL, expressed in terms of defects per hundred units, for each characteristic shall be 6.5.

Characteristic	Requirement reference	Test Method	Number of determinations per sample unit
Sealed seam area, hydrostatic resistance	3.5.4.1	4.4.1	7
Sealed seam sealant: Resistance to low temperature flexing	3.5.4.2	4.4.2	1
Resistance to blocking	3.5.4.3	4.4.3 1	
Colorfastness and legibility of labels	3.6	5651	1

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

4.3.5 Packaging examination. The fully packaged end item shall be examined for the defects listed below. The lot size shall be expressed in units of shipping containers. The sample unit shall be one shipping container fully packaged. The inspection level shall be S-2 and the AQL, expressed in terms of defects per hundred units, shall be 2.5.

Examine	Defect
Marking (exterior and interior)	Omitted; incorrect; illegible, of improper size, location, sequence, or method of application.
Materials	Any component missing, damaged or not as specified.
Workmanship	Inadequate application of components such as: incomplete closure of container flaps, loose strapping, improper taping, or inadequate stapling. Bulged or distorted container.
Contents	Number of intermediate containers per shipping container is more or less than required. Number of ponchos per intermediate container is more or less than required. 1/

1/ For this defect, one intermediate container from each shipping container in the sample shall be examined.

4.3.6 Palletization examination. The fully packaged and palletized end items shall be examined for the defects listed below. The lot size shall be expressed in units of palletized unit loads. The sample unit shall be one palletized unit load, fully packaged. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5.

Examine	Defect
Finished dimension	Length, width or height exceeds specified maximum requirement.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted; incorrect; illegible; of improper size, location, sequence or method of application.

4.4 Methods of inspection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

4.4.1 Determination of hydrostatic resistance of sealed seam area. The hydrostatic resistance of sealed seam areas of the poncho shall be determined in accordance with Method 5516 of FED-STD-191 except for the following: The seam area of the fabricated poncho, sample unit, shall be tested without cutting or otherwise damaging the poncho. The seam shall be flexed 10 times in the following manner. The poncho seam shall be grasped using the thumb and fingers of each hand in such a manner that the thumbs are parallel to each other and approximately 1/2 inch beyond (outside) the edges of the sealant. With the seam held firmly in the above manner the thumbs shall be brought together so the cloth and the sealant are in contact. The sealed area shall be flexed vigorously 10 times with the cloth and sealant in contact with itself throughout the test. The flexing action shall be such that when fully flexed in either direction there shall be a minimum of 2 inches between each thumb nail when the flexed area is fully extended with the test area in contact with itself at all times. The test area shall be visually examined for the characteristic indicated in 3.5.4.1 prior to conduct of the hydrostatic test. The water level shall be adjusted to yield a hydrostatic head of 50 centimeters and after this adjustment the valve shall be opened and the water level maintained at 50 centimeters for 10 minutes.

4.4.1.1 Report.

4.4.1.1.1 Poncho fabricated with center or side seams. Tests shall be run on the finished poncho at seven different locations as follows: One on the front joining seam, one on the back joining seam; two on the center hood seam; and three on the seam joining the hood to the neck of the poncho. The seven determinations shall be reported separately as "pass" or "fail". No more than one area of the seven test areas on each poncho shall show leakage in less than 10 minutes at the required hydrostatic head. A failure of the poncho is defined as a hydrostatic failure in two or more of the seven determinations.

4.4.1.1.2 Poncho fabricated with no center or side seam. Tests shall be run on the finished poncho at five different locations as follows: Two on the center hood seam and three on the seam joining the hood and reinforcement piece to the neck of the poncho. The five determinations shall be reported separately as "pass" or "fail". No more than one area of the five test areas on each poncho shall show leakage in less than 10 minutes at the required hydrostatic head. A failure of the poncho is defined as a hydrostatic failure in two or more of the five determinations.

4.4.2 Determination of low temperature flexibility of sealed seam sealant. Method 5874 of FED-STD-191 shall be followed except that the test for hydrostatic resistance shall not be performed. The poncho (test specimen) shall be exposed for 35 $\pm$ 5 minutes at a temperature of 0 $\pm$ 5°F and tested immediately thereafter without removal from the low temperature test chamber. The hood joining seam of the poncho shall be folded back on itself 180 degrees so that the two outer sealed seam surfaces are superimposed. The roller weight shall be passed along the fold and across the seam. Any cracking, flaking or separation of sealant shall be classified as a failure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

4.4.3 Determination of resistance to blocking. Method 5872 of FED-STD-191 shall be followed except that the sample unit shall be one completely fabricated poncho and that the test specimen shall be prepared by folding the hood seam of the poncho so that only the two outer sealed seam surfaces are superimposed and are in the center of the glass plates.

4.4.4 Sealant hydrolytic stability. Three coats of sealant specified in 3.2.8 shall be applied in a 2 inch stripe across an 8 by 8-inch piece of coated cloth specified in 3.2.1. The sealant shall be applied to the coated side of the cloth and shall be allowed to dry at standard conditions for 24 hours prior to testing. The specimen with the sealant shall be laid flat, coated side up, on a supporting plate and the assembly placed in a desiccator containing water in the lower portion. The water level shall be approximately 1 inch below the specimen. The lid of the desiccator shall be put in place and the desiccator placed in a circulating air oven having a temperature of 125 $\pm$ 2°F for a period of seven days. At the end of the aging period, the specimen shall be removed from the desiccator, the specimen folded in such a manner that the stripe of sealant is in complete contact across the specimen and the sample placed under a load of 4 pounds evenly distributed over the sample for 5 minutes. The load shall be removed and the sample opened up and laid flat. There shall be no more than a number 3 blocking (the sample can be separated without the sealant being removed from the coated cloth).

4.4.5 Color, gloss and appearance of sealant. Three specimens prepared as specified in 4.4.4 shall be examined for color, gloss and appearance in accordance with Method 9010 of FED-STD-191.

5. PACKAGING

5.1 Preservation. Preservation shall be level A or Commercial as specified (see 6.2).

5.1.1 Level A. Each poncho laid flat shall have the length folded in half twice, with the hood inside the fold, to a folded dimension of approximately 23 inches. The width shall be folded in twice from each end toward the center in increments of approximately 13 inches resulting in a completely folded poncho measuring 23 inches by 14 inches. Eight folded ponchos shall be unit packed flat, with each one reversed in an intermediate fiberboard box conforming to style RSC, type CF, (variety SW) or SF, class domestic, grade 200 of PPP-B-636. The outside dimensions of each box shall be 23-1/4 inches in length, 14-3/4 inches in width, and 5 inches in depth. Box closure will be secured with 1-1/2 inch minimum width gummed paper tape conforming to type III, grade b of PPP-T-45.

5.1.2 Commercial. Ponchos shall be preserved in accordance with ASTM D 3951.

5.2 Packing. Packing shall be level A, B, or Commercial as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

* 5.2.1 Level A packing. Twenty-four ponchos of one type and class only, preserved as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, grade V2s of PPP-B-636. Level A intermediate packs shall be packed flat, three in depth, within the shipping container. Inside dimensions of each shipping container shall approximate 23-1/2 inches in length, 15 inches in width, and 15 inches in depth. Approximate dimensions are furnished as a guide only. Each shipping container shall be closed in accordance with method III, waterproofed in accordance with method V, and reinforced as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.3.5. Towards the end of the contract or when there are less than the same amount per container of the same size, mixed sizes may be packed within the same container. Shipping containers shall be arranged in unit loads in accordance with MIL-L-35078 for the type and class of load specified (6.2). Strapping shall be limited to non-metallic strapping, except for type II, class F loads.

* 5.2.2 Level B packing. Twenty-four ponchos of one type and class only, preserved as specified in 5.1, shall be packed in a snug-fitting fiberboard shipping container conforming to style RSC, type CF (variety SW) or SF, class domestic, grade 275 of PPP-B-636. Level A intermediate packs shall be packed flat, three in depth, within the shipping container. Inside dimensions of each shipping container shall approximate 23-1/2 inches in length, 15 inches in width, and 15 inches in depth. Approximate dimensions are furnished as a guide only. Each shipping container shall be closed in accordance with method II as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.3.5. Towards the end of the contract or when there are less than the required amount per container of the same size, mixed sizes may be packed within the same container.

* 5.2.2.1 Weather-resistant containers. When specified (see 6.2), the shipping container shall be a grade V3c, V3s, or V4s fiberboard box fabricated in accordance with PPP-B-636 and closed in accordance with method III as specified in the appendix of PPP-B-636, except that the inspection shall be in accordance with 4.3.5.

* 5.2.3 Commercial packing. Ponchos preserved as specified in 5.1 shall be packed in accordance with ASTM D 3951.

5.3 Palletization. When specified (see 6.2), ponchos packed as specified in 5.2.2 and 5.2.3, shall be palletized on a 4-way entry pallet in accordance with load type Ia of MIL-STD-147. Pallet types shall be type I (4-way entry), type IV or type V in accordance with MIL-STD-147. Pallets shall be fabricated from wood groups I, II, III, or IV of MIL-STD-731. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means K and L or film bonding means O or P. Pallet pattern shall be number 32 in accordance with appendix of MIL-STD-147. Interlocking of loads shall be effected by reversing the pattern of each course.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

5.4 Marking. In addition to any special marking required by the contract, intermediate packs, shipping containers, and palletized unit loads shall be marked in accordance with MIL-STD-129 or ASTM D 3951 as applicable.

5.4.1 Labels, mixed sizes. Each shipping container packed with mixed sizes shall have securely attached to the end and side directly under the printing or stenciling a white paper label 5 by 4 inches, with the words "MIXED NSN's" plainly stamped or printed thereon and under these words shall be legibly stamped or printed the correct quantity and NSN's contained therein.

6. NOTES

* 6.1 Intended use. The ponchos are intended to be used as rain garments, ground sheets, blankets, sleeping bag covers, or shelter halfs.

6.2 Ordering data. Acquisition documents should specify the following:

a. Title, number, and date of this document.
b. Type and class of poncho required (see 1.2).
c. When resistance to low temperature flexing is not required (see 3.5.4.2).
d. Selection of applicable levels of preservation and packing (see 5.1 and 5.2).
e. Type and class of unit load required (see 5.2.1).
f. When weather-resistant grade fiberboard shipping containers are required for level B packing (see 5.2.2.1).
g. When palletization is required (see 5.3).

6.3 Sample. For access to samples, address the procuring activity issuing the invitation for bids (see 3.1).

6.4 Fabrication operations. Experience has shown that sewing machine speeds up to 3200 stitches per minute will result in a more efficient sewing operation and higher quality stitching and seaming on this type of fabric (see 3.5.1).

6.5 Illumination of test surface. An instrument found suitable for determining the illumination of the test surface (see 4.3.2) is Weston Illumination Meter, Model 756, made by Daystrom, Incorporated, Weston Instrument Division, Newark, NJ 07114.

6.6 Clamp, cord. A source of supply for clamp, cord, lock body and lock wheel specified in 3.2.6 is available from Fastex, Division Illinois Tool, Incorporated, 195 Algonquin Road, Des Plaines, IL 60016.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

6.7 Subject term (key word) listing.

Camouflage
Clothing, protective
Poncho
Wet Weather

6.8 Changes from previous issue. The margins of this document are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

Custodians:

Army - GL
Navy - NU
Air Force - 99

Review activities:

Army - MD
Navy - MC
DLA - CT

User activities:


Navy - YD
Air Force - 45


Preparing activity:

Army - GL

Project No. 8405-0002

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

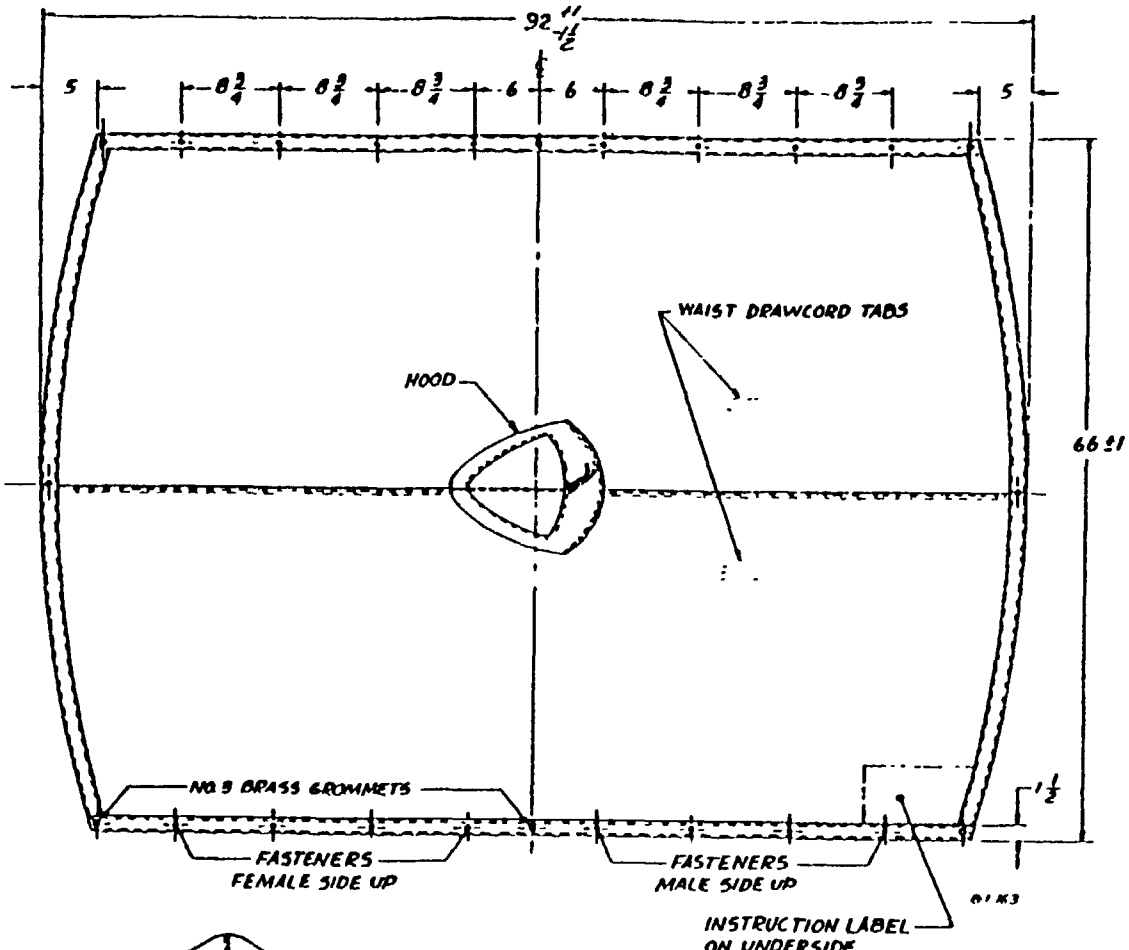

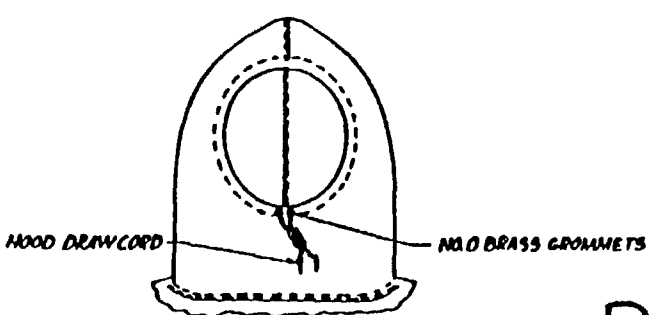

HOOD DETAILS

FIG. 1 Type I


PONCHO, WET WEATHER


MIL-P-43700C

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.


PONCHO, WET WEATHER

FIG 2 Type II

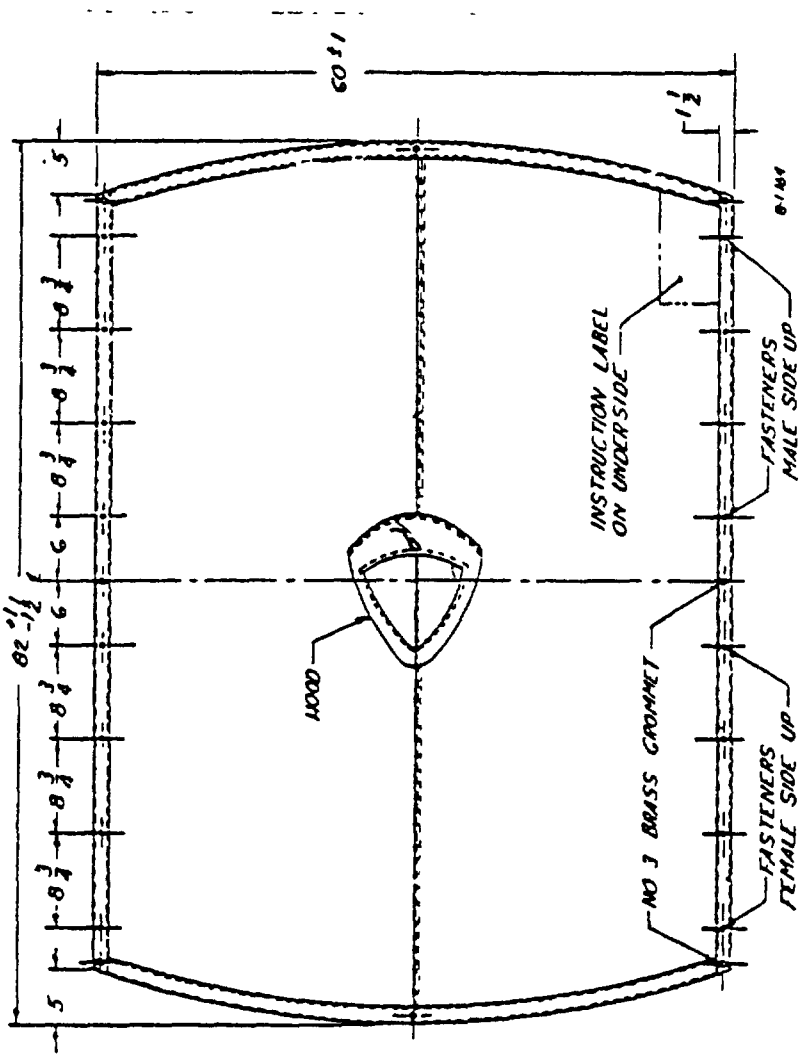

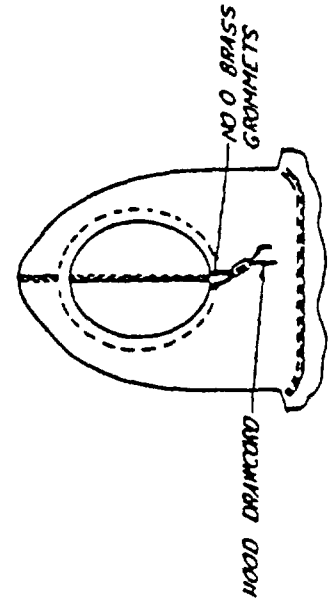

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

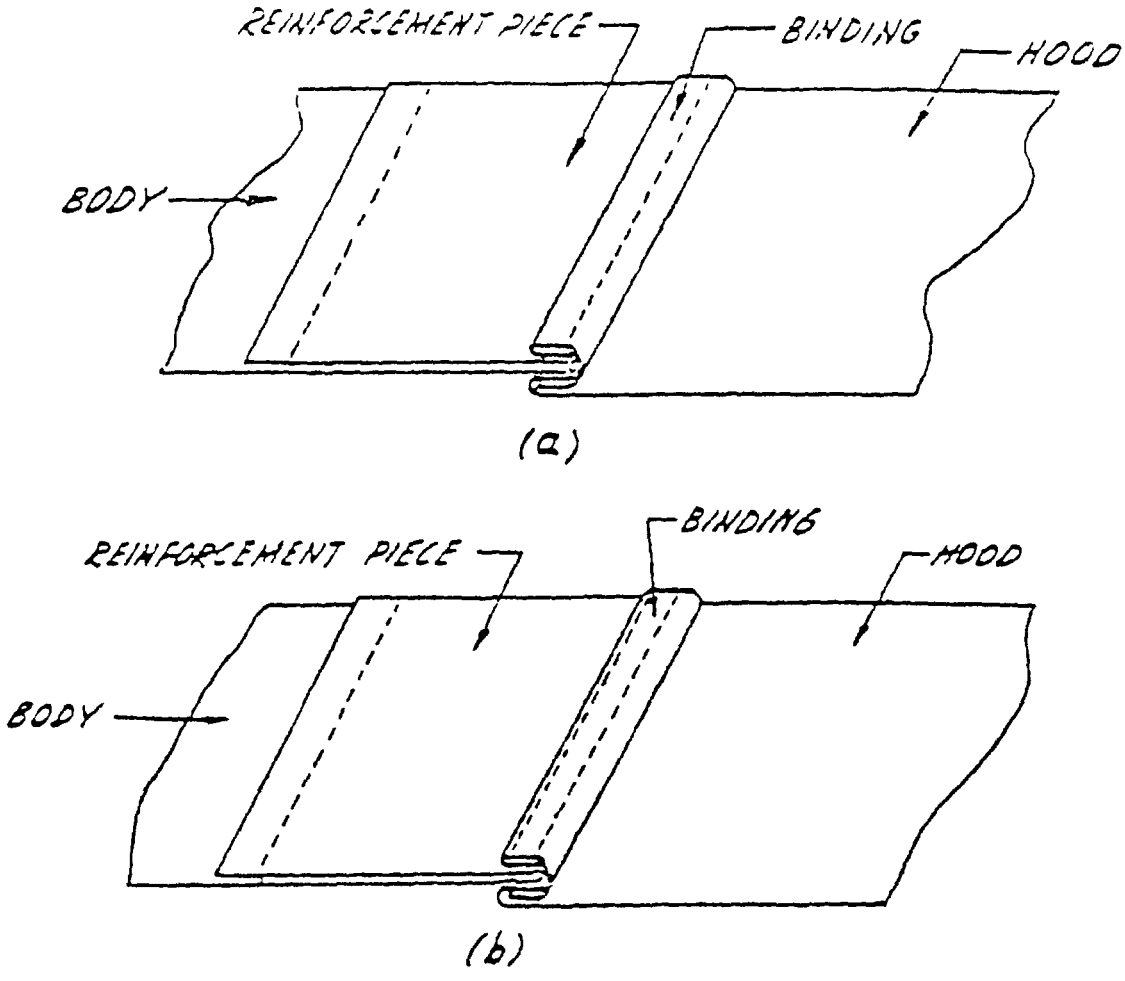

HOOD-NECK JOINING SEAM (OPERATION 12 OF TABLE II)

FIG. 3 - PONCHOS, WET WEATHER

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

U.S. ARMY NATICK RESEARCH, DEVELOPMENT
and ENGINEERING CENTER
ATTN: STRNC-ES
Natick, MA 01760-5014

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO 12062 WASHINGTON D C
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
U.S Army Natick Research, Development
and Engineering Center
ATTN: STRNC-ES
Natick, MA 01760-5014

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2 DOCUMENT TITLE
MIL-P-43700C	Poncho, WEt Weather

3a. NAME OF SUBMITTING ORGANIZATION	4 TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ USER
	☐ MANUFACTURER
	☐ OTHER *(Specify)* _____

5. PROBLEM AREAS

a. Paragraph Number and Wording

b. Recommended Wording

c. Reason/Rationale for Recommendation

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8 DATE OF SUBMISSION *(YYMMDD)*

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T22:03Z
Check the source to verify that this is the current version before use.