MIL-C-1283F
9 May 1985
SUPERSEDING
MIL-C-1283E
12 June 1974

MILITARY SPECIFICATION

CAN, GASOLINE, MILITARY, 5-GALLON

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers a 5-gallon gasoline can for military use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified (see 6.2), the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation, form a part of this specification to the extent specified herein.

SPECIFICATIONS

FEDERAL

QQ-S-781	- Strapping, Steel, and Seals.
NN-P-71	- Pallets, Material Handling, Wood, Stringer Construction, 2-Way, and 4-Way (Partial).
PPP-F-320	- Fiberboard; Corrugated and Solid, Sheet Stock (Container Grade), and Cut Shapes.
PPP-S-760	- Strapping, Nonmetallic (and Connectors).

MILITARY

MIL-C-4556	- Coating Kit, Epoxy, for Interior of Steel Fuel Tanks.

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: USA Belvoir Research and Development Center, ATTN: STRBE-DS, Fort Belvoir, VA 22060-5606 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

STANDARDS

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes.
MIL-STD-129	- Marking for Shipment and Storage.
MIL-STD-147	- Palletized Unit Loads.

2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

DEPARTMENT OF TRANSPORTATION

Regulation of Transportation of Explosives and Other Dangerous Articles by Freight.

Specification 5L, Steel Barrels or Drums.

(Application for copies should be addressed to the Superintendent of Documents, Government Printing Office, Washington, DC 20402.)

DRAWINGS

ME

TA13219E2670	- Can, Gasoline, Military, 5-Gallon Capacity; Assembly and Details of Head.

(Copies of specifications, standards, and drawings required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. The issues of the documents which are indicated as DoD adopted shall be the issue listed in the current DoDISS and the supplement thereto, if applicable.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM D 3951 - Standard Practice for Commercial Packaging.

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

(Industry association specifications and standards are generally available for reference from libraries. They are also distributed among technical groups and using Federal agencies.)

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, the text of this specification shall take precedence.

3. REQUIREMENTS

3.1 Description. The gasoline can shall consist of three sections: the head, the body and the bottom. The can shall be in accordance with TA13219E2670 and as specified herein.

3.1.1 Drawings. The drawings forming a part of this specification are end product drawings. No deviation from the prescribed dimensions or tolerances is permissible without prior approval of the contracting officer. Any data (e.g., shop drawings, layouts, flow sheets, processing procedures, etc.) prepared by the contractor or obtained from a vendor to support fabrication and manufacture of the production item shall be made available, upon request, for inspection by the contracting officer or his designated representative.

3.2 First article. When specified, a sample shall be subjected to first article inspection and test.

3.3 Material. Material shall be as specified herein and on the applicable drawings. Materials not specified shall be selected by the contractor and shall be subject to all provisions of this specification.

3.4 Design and construction.

3.4.1 Head section. The head section shall consist of a head and handle assembly, filling plug assembly, closure flange, and vent tube.

3.4.1.1 Head and handle assembly. The head and handle assembly shall conform to the applicable drawings. When tested as specified in 4.5.2.6, the handles shall withstand vertical pull of 500 pounds.

3.4.1.2 Closure flange and filling plug assembly. The closure flange and the filling plug assembly shall conform to the applicable drawings.

3.4.1.3 Vent tube. The vent tube shall be secured by a clip, spot welded to the inside surfaces of the head. The bend of the tube shall be such that the spot welds on the clip create a positive pressure between the tube and the underside closure flange. No soldering shall be used in attaching the vent tubes. Detailed construction shall be in accordance with the drawings.

3.4.2 Body and bottom sections. The body and bottom sections shall be in accordance with the drawings and after forming the body and bottom shall have no dent more than 1/8-inch deep.

3.4.3 Seams. All seams shall be formed as shown on the drawings. Lap seams shall be seam welded and shall be free of any burn penetrations. Seaming compound as specified on the drawings shall be used in forming the double bottom

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

seam. The seaming compound shall be applied so that no excess compound will remain on the inside or outside of the can. The can shall show no evidence of leakage when tested as specified in 4.5.2.2, 4.5.2.3 (part I) and 4.5.2.4. The can shall show no indication of rupturing when tested as specified in 4.5.2.3 (part II).

3.5 Finish.

3.5.1 Surface preparation. Prior to double seaming of the can bottom, all loose metal splinters on the outside of the can, and loose weld scale and flash shall be removed by wire brush or abrasive wheel. Prior to application of coatings, all interior and exterior surfaces shall be thoroughly cleaned and prepared for coating as specified on the drawings.

3.5.2 Interior coating. After the surface preparation specified in 3.5.1 and prior to attaching the bottom section to the body section and the head section to the body section, interior surfaces of the can shall be coated with a coating conforming to MIL-C-4556. The coating shall cover all interior surfaces of the can, including the exterior surfaces of the vent tube. Care shall be exercised that the countersink of the can bottom and the corresponding area of the can body are thoroughly coated. The vent tube interior need not be coated. The dry film thickness shall be 0.6 mil $\pm$0.2 mil except that up to 1.2 mil thickness will be permitted in limited areas such as lap seams, vent tube, and embossings which are difficult to coat uniformly. The coating shall be baked prior to double seaming. The baking shall be in accordance with the coating manufacturer's instructions.

3.5.2.1 Appearance. The coating shall be smooth, uniform, and shall be free of sags, runs, blisters, globs, mottling, or other indications of improper application.

3.5.2.2 Impact resistance. When tested as specified in 4.5.2.5, the coating shall not crack, chip, or peel.

3.5.2.3 Thoroughness-of-cure. When tested as specified in 4.5.2.7, the coating shall not soften or whiten.

3.5.2.4 Boiling water resistance. When tested as specified in 4.5.2.8, the coating shall not blister, soften, lift, crack, whiten, lose gloss or adhesion, or permit rusting.

3.5.3 Exterior coating. After attaching the bottom, body, and head sections and inserting the filler plug assembly with a dummy gasket, one coat of enamel as specified on the drawings shall be applied. The enamel shall have a dry thickness of not less than 1.0 mil at all external surfaces of the gasoline can. The enamel shall be smooth and uniform, and free of runs, wrinkles, drops, or areas of no coat coverage. After the enamel coating, the dummy gasket shall be removed and replaced with a gasket as specified on the drawings.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

3.6 Marking for identification. All cans shall be marked in accordance with the drawings and DOT specification 5L, Steel Barrels or Drums, of DOT Regulations of Transportation of Explosives and Other Dangerous Articles by Freight.

3.7 Workmanship. All parts, components, and assemblies of the cans, including molded parts, stampings, machined surfaces and welded parts, shall be clean and free of all extraneous material.

3.7.1 Steel fabrication. The finished cans shall be free from kinks and sharp bends. Specified bends shall be free from cracks and fractures. All burrs and sharp edges shall be removed. The forming of material shall be done by methods that will not cause injury to the metal. Shearing or sawing shall be done neatly and accurately. Corners shall be square. All bends shall be made with metal dies or fixtures to insure uniformity of size and shape.

3.7.2 Welding. The surfaces of parts to be welded shall be free from all foreign matter. Welds shall transmit stress without permanent deformation or failure when the parts connected by the welds are subjected to test and service loading. Welds shall conform to the requirements specified on the drawings.

4. QUALITY ASSURANCE PROVISIONS

4.1 Responsibility for inspection. Unless otherwise specified in the contract or purchase order, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for the performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Component and material inspection. The contractor is responsible for insuring that components and materials are manufactured, examined, and tested in accordance with referenced specifications and standards.

4.2 Classification of inspections. Inspections shall be classified as follows:

a. First article inspection (see 4.3).
b. Quality conformance inspection (see 4.4).
c. Inspection of packaging (see 4.6).

4.3 First article inspection.

4.3.1 Examination. The first article gasoline can shall be examined as specified in 4.5.1. Presence of one or more defects shall be cause for rejection.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

4.3.2 Tests. The first article gasoline can shall be tested as specified in 4.5.2.1 through 4.5.2.8. Samples of coated material shall be tested as specified in 4.5.2.1. Failure of any test shall be cause for rejection.

4.4 Quality conformance inspection.

4.4.1 Sampling. Sampling for examination and tests shall be in accordance with MIL-STD-105, except where otherwise indicated.

4.4.1.1 Lot. For the purpose of inspection, a lot shall consist of all the gasoline cans offered for acceptance at one time, but shall not exceed 1500 cans.

4.4.2 Examination.

4.4.2.1 Samples. Samples selected in accordance with 4.4.1 shall be examined as specified in 4.5.1. Acceptable Quality Level (AQL) shall be 2.5 percent defective for major defects and 10.0 percent defective for minor defects.

4.4.3 Tests.

4.4.3.1 Individual. Each gasoline can shall be tested as specified in 4.5.2.2. Failure of the test shall be cause for rejection.

4.4.3.2 Samples. Sample selected in accordance with 4.4.1 shall be tested as specified in table I.

TABLE I. Completed can.

Test	Requirement Paragraph	Test Paragraph	Inspection Level	AQL Acceptance No.
Hydrostatic	3.4.3	4.5.2.3	1/	1/
Drop	3.4.3	4.5.2.4	1/	1/
Impact resistance	3.5.2.2	4.5.2.5	S-2	4.0
Handle weld	3.4.1.1	4.5.2.6	S-2	4.0

1/ Unless otherwise specified (see 6.2) within an hour after the start of each run on each line, two sample cans shall be taken at random and subjected to the tests specified in 4.5.2.3 and 4.5.2.4. Should there be an interruption in production exceeding 60 minutes, the hydrostatic and drop tests shall be repeated when the line again starts production. Should any can fail these tests, two additional cans for each test that failed shall be taken from the completed lot and subjected to the same test that failed. If either of the retested cans leak, the completed lot shall be rejected.

4.5 Inspection procedure.

4.5.1 Examination. The gasoline cans shall be examined for the following defects:

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

Major

101. Construction not as specified.
102. Crack, fracture, or any sharp edge or burr.
103. Welding not of the type specified.
104. Spot welding not spaced as specified.
105. One or more spot welds missing or broken.
106. Burnt holes, cracked, fractured, not fused.
107. Slag inclusion, undercut.
108. Bottom chine not rolled upon outer side of body wall.
109. Bottom chine open.
110. Not seam-welded at juncture of head and body.
111. Pronounced wrinkling of head, body and bottom sections.
112. Embossing missing.
113. Head section assembly handles less than three tubes.
114. Handles not secure.
115. Filling plug missing.
116. Holes or laminations in filling plug.
117. Type or design of filling plug not as specified.
118. Filling plug gasket seat not smooth and flat.
119. Filling plug not plated after threading.
120. Improper fit of filling plug.
121. Filling plug thread malformed or broken.
122. Less than five full threads on filling plug.
123. Gasket missing.
124. Gasket size or type not as specified.
125. Closure loose when plug is tightened.
126. Closure gasket seat at outer edge is rough.
127. Closure not zinc plated.
128. Closure not installed properly.
129. Closure vent hole not as specified.
130. Threads of closure malformed.
131. Closure bent.
132. Closure gasket seat at vent burred or puffed out.
133. Vent tube missing or loose.
134. Open seams of interior finish.
135. Interior not coated as specified.
136. Can not completely drained and dried before plug is secured.
137. Material not as specified.
138. Workmanship not as specified.

MINOR

201. Exterior finish not type or color specified.
202. Runs, sags, wrinkles, drops, area of no film, separation of color or finish not smooth on exterior.
203. Dents more than 1/8-inch-deep.
204. Welding not smooth; scale not removed.
205. Excess weld.
206. Vertically welded seam not on end.
207. Seam compound visible.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

208. Head extends beyond offset on body or is not flush to body.
209. Depth and size of embossing not as specified.
210. Embossing not correct or located as specified.
211. Handles bent.
212. Bottom seam on handle open.
213. Handle not positioned correctly (at closure end).
214. Bottom seam on handle having either edge lower than the other.
215. Filling plug not installed tightly.
216. Plug swivel wire missing.
217. Plug swivel wire not secured to plug.
218. Plug swivel hasp missing.
219. Plug swivel connector link not secured to can by cotter pin and washer.
220. Filling plug lugs extend over front of can.
221. Paint finish adhering to top or bottom surface of gasket.
222. Gasket deformed or torn.
223. Paint on gasket seat surface of head.
224. Gasket seat at vent opening not on same plane as rest of gasket seat.
225. Any white residue, dirt, loose rust, seam compound or foreign matter on interior finish.
226. Incomplete, illegible, wrong location or missing identification markings.

4.5.2 Tests.

4.5.2.1 Samples of material. Coated material shall be tested as indicated in table II. Three determinations will be made on each sample. The average of the three determinations shall constitute the sample unit requirement.

TABLE II. Coated material.

Characteristics	Req. para.	Test para.	Sample unit	Sample size	Acc. no.
Thoroughness-of cure	3.5.2.3	4.5.2.7	Area approximately 3 square inches on each bottom, body and head space of can.	3 1/	0
Boil test	3.5.2.4	4.5.2.8	Two panels approximately 4 inches by 6 inches (one cut from bottom and one cut from body of can).	3 2/	0

1/ Sampling for this characteristic shall be performed on a daily production basis, representative of production from each shift.
2/ Sampling for this characteristic shall be performed upon receipt of each shipment of interior coating material.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

4.5.2.2 Leakage. Subject the clean, dry gasoline cans to an internal air pressure of 10 pounds per square inch (psi). Place the pressurized gasoline can under water, or cover it with a bubble-forming detergent. Nonconformance to 3.4.3 shall constitute failure of this test.

4.5.2.3 Hydrostatic pressure. Conduct the test as follows:

Part I: Subject clean, dry gasoline cans to a hydrostatic pressure of 30 psi. Sustain this pressure for 5 minutes. Any evidence of leakage shall constitute failure of this test.

Part II: Subject the same gasoline cans that passed part I to a hydrostatic pressure of 60 psi and release. Examine the cans for structural failure. Any evidence of rupture or cracking shall constitute failure of this test.

4.5.2.4 Drop. Fill the gasoline cans with water to about 98 percent of actual capacity, or to the lower thread on the closure flange. Vertically drop the filled cans a distance of 6 feet so that it strikes diagonally on its chine upon concrete or a steel plate. Again suspend and vertically drop the same cans from the same distance onto the same surface so that the closure will strike first. Evidence of leakage shall constitute failure of this test.

4.5.2.5 Impact. Strike the gasoline cans with a 2-pound, 1-inch diameter cylindrical, round nose, steel rod dropped from a height of 10 inches. A guide tube shall be used in alining the drop weight and measuring the dropping distance. The diameter of the rounded impacting end of the steel rod shall be 1/2-inch (see 6.4). Test spots shall consist only of flat, nonindented, nonwelded portions of the can. Each spot to be tested shall be held uppermost, with the can firmly supported beneath and braced by hand, knee, or other convenient method. For impacting the bottom, the can shall be supported upside down on its carrying handles. The impact shall be delivered to the outside of the can. The can shall be impacted at 10 points uniformly distributed over the can. Examine the interior of the can with the aid drum-light. Nonconformance to 3.5.2.2 shall constitute failure of this test.

4.5.2.6 Handle spot weld. An even vertical pull of 500 pounds shall be applied and released to each handle bar at the following positions:

a. Front of each outside bar.
b. Rear of each outside bar.
c. Rear of middle bar.

The fixture shown in figure 1 may be used to obtain an even handle pull. The test may be conducted prior to welding of the head to the body. Evidence of welds to pull away from the can head, or handle to pull away from can head shall constitute failure of the test.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

4.5.2.7 Thoroughness-of-cure. A test area of approximately 3 square inches shall be wetted with acetone for 5 minutes; the acetone shall be kept from evaporating from the test surface by covering it with a watchglass, use of acetone-soaked cotton wadding, or other suitable device. Immediately after the 5-minute exposure and while still wet, examine the test surface coating for softening or whitening. Nonconformance to 3.5.2.3 shall constitute failure of the test.

4.5.2.8 Boil test. Two panels, 4 inches by 6 inches, shall be used for this test. Panels of sheet steel identical to the material used in 3.4.2 shall be prepared and coated on both sides as specified in 3.5.1 and 3.5.2. One panel shall be completely immersed in boiling distilled water for 2 hours. After cooling to room temperature, the panel shall be examined immediately for differences in appearance from the control panel that was not boiled. Nonconformance to 3.5.2.4 shall constitute failure of this test.

4.6 Inspection of packaging.

4.6.1 Quality conformance inspection of pack.

4.6.1.1 Unit of product. For the purpose of inspection, a completed pack prepared for shipment shall be considered a unit of product.

4.6.1.2 Sampling. Sampling for examination shall be in accordance with MIL-STD-105.

4.6.1.3 Examination. Samples selected in accordance with 4.6.1.2 shall be examined for the following defects. Acceptable quality level (AQL) shall be 2.5 percent defective.

139.	Materials not specified for level A. Each incorrect material shall constitute one defect.
140.	Number of cans per bundle not as specified for level A.
141.	Cans not palletized as specified for level A.
142.	Palletized load not provided with a cap as specified for level A.
143.	Packing not in accordance with the referenced document as specified for industrial.
144.	Marking illegible, incorrect, missing, or incomplete for level A or industrial.

5. PACKAGING.

5.1 Preservation (see 6.5). Each can shall be completely drained and dried, and the cap replaced.

5.2 Packing. Packing shall be level A or industrial as specified (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

5.2.1 Level A. Seven cans shall be strapped in a bundle as shown on figure 2, then palletized in accordance with 5.2.1.1.

5.2.1.1 Palletization. Six bundles, (42 cans), packed as specified in 5.2.1 shall be positioned three bundles to a course and two courses high on a pallet conforming to NN-P-71, type IV. The method of palletization shall be in accordance with MIL-STD-147, load type VIII, without the horizontal separator. A fiberboard cap fabricated from material conforming to PPP-F-320, V2s shall be provided. Securing shall be by bonding means D, K, and L of MIL-STD-147, using strapping conforming to QQ-S-781, class 1, type I or IV, finish B, size 1/2 inch X .020 inch.

5.2.2 Industrial. Cans, completely drained and dried as specified in 5.1, shall be packaged in accordance with ASTM D 3951.

5.3 Marking.

5.3.1 Military. Marking for military levels of protection shall be in accordance with MIL-STD-129.

5.3.2 Industrial. Marking for industrial packaging shall be in accordance with ASTM D 3951. In addition, weight and cube data shall be marked on the shipping container.

6. NOTES

6.1 Intended use. The gasoline can is intended for use in transporting liquid fuels by commercial common carriers, military motor vehicles, aircraft, and vessel transportation, and for storage of and dispensing of liquid fuels.

6.2 Ordering data. Procurement documents should specify the following:

a. Title, number, and date of this specification.
b. Date of issue of DoDISS applicable and exceptions thereto (see 2.1.1).
c. The time frame required for submission of first article gasoline cans, and number of models required (see 3.2).
d. When sample tests are not required (table I).
e. Degree of packing required (see 5.2).

6.3 First article. Any changes or deviations of production gasoline cans from the approved first article gasoline cans during production will be subject to the approval of the contracting officer. Approval of the first article gasoline cans will not relieve the contractor of his obligation to furnish gasoline cans conforming to this specification.

6.4 A variable impact tester, 28-inch-pound range, manufactured by Gardner Laboratory, Inc., Bethesda, Maryland, has been found satisfactory (see 4.5.2.5).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

6.5 Packaging. Degrees of preservation have not been included, as the preservation specified is the minimum acceptable for any degree of protection. For purposes of preservation/packing level marking, the preservation shall be designated as level A.

Custodians:
Army - ME
Navy - YD
Air Force - 99

Review Activities:
Army - GL, EA, SM
Air Force - 84

User activities:
Navy - MC, CG

Preparing activity:
Army - ME

Project 7240-0225

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

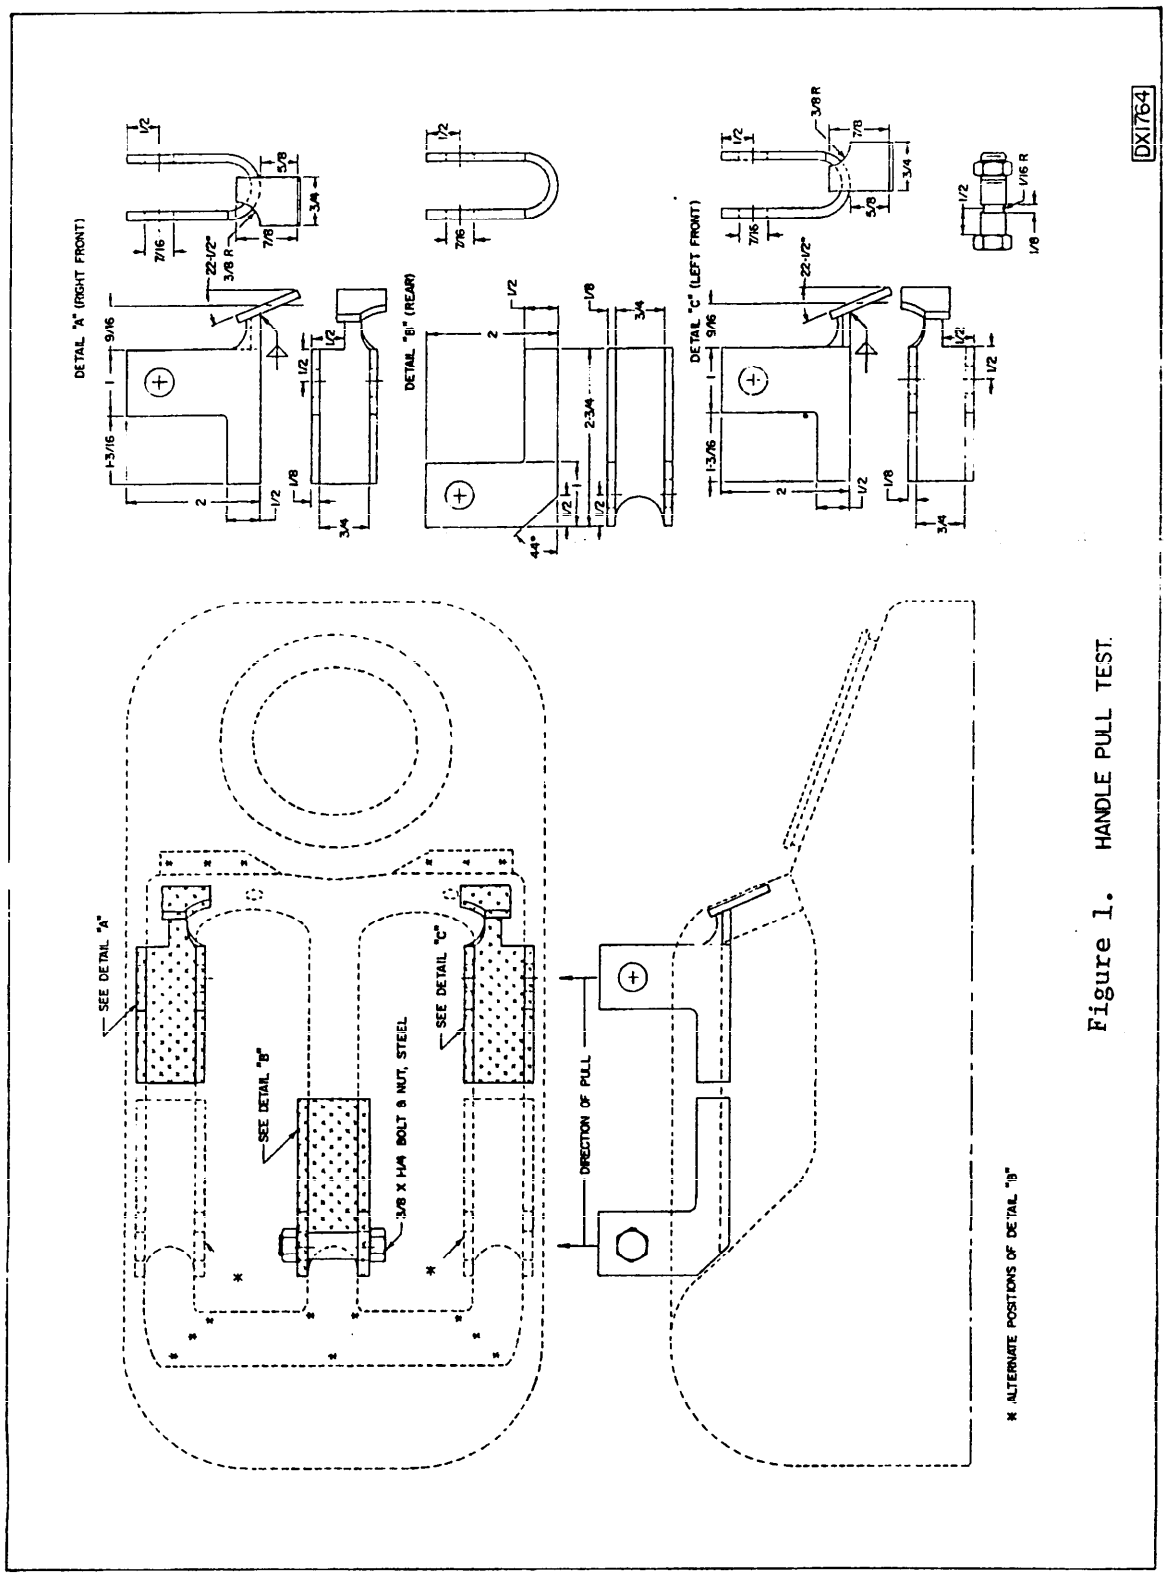


Figure 1. HANDLE PULL TEST.

Source: https://assist.dla.mil -- Downloaded: 202610-16T13:04Z
Check the source to verify that this is the current version before use.

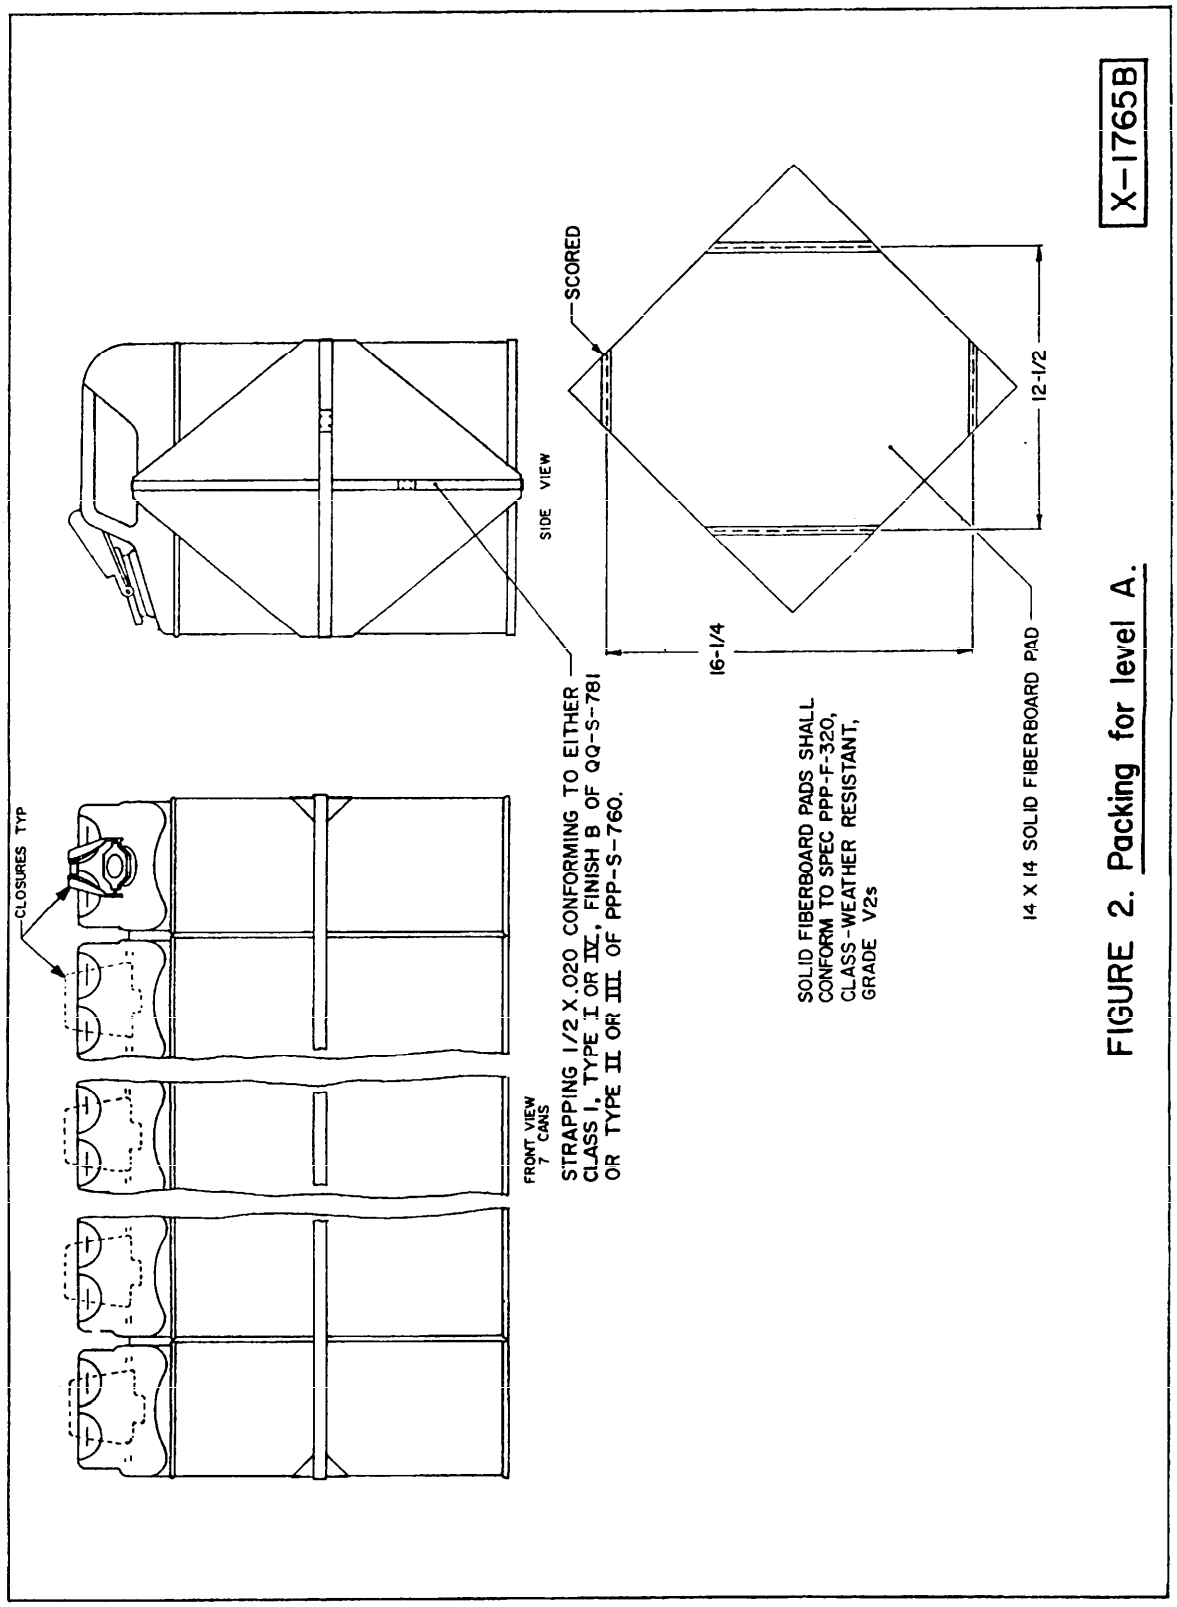


FIGURE 2. Packing for level A.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE ARMY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12062 WASHINGTON D. C.
POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE ARMY

Commander
US Army Belvoir R&D Center
ATTN: STRBE-DS
Ft. Belvoir, VA 22060-5606

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T13:04Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-C-1283G	Can, Gasoline, Military, 5-Gallon

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR ☐ USER ☐ MANUFACTURER ☐ OTHER *(Specify)*: _____
b. ADDRESS *(Street, City, State, ZIP Code)*	

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 202610-16T13:04Z
Check the source to verify that this is the currentversion before use.