MILITARY SPECIFICATION SHEET

THERMOSETTING POLYMER (EPOXY) MATRIX, 350°F(177°C) CURE, INTERMEDIATE MODULUS CARBON FIBER REINFORCED PREPREG TAPE, (WIDTHS UP TO 60 INCHES)

This specification is approved for use within the Naval Air Systems Command, Department of the Navy, and is available for use by all Departments and Agencies of the Department of Defense.

The complete requirements for acquiring this material shall consist of this document and the latest issue of MIL-T-29586(AS).

1. SCOPE

1.1 Scope. This specification in conjunction with MIL-T-29586(AS) establishes the requirements for a 350°F(177°C) cured epoxy prepreg reinforced with intermediate modulus unidirectional carbon fiber tow.

1.2 Classification (nominal Areal Weight): As specified in the contract or purchase order, the prepreg tape material shall be supplied in the Classes specified in Table I.

Table I. Classes of Prepreg Material

Class	Nominal Ply Thickness	Fiber Areal Weight
37	0.0037 inch (.0095 cm)	2.6 oz/yd^2 (95 g/m^2)
56	0.0056 inch (.0142 cm)	4.2 oz/yd^2 (145 g/m^2)
74	0.0074 inch (.0188 cm)	5.5 oz/yd^2 (190 g/m^2)

2. APPLICABLE DOCUMENTS

2.1 Government Documents.

2.1.1 Specifications and standards. The following specification forms a part of this document to the extent specified herein. Unless otherwise specified, the issue of this document shall be the one listed in the issue of the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

DISTRIBUTION STATEMENT A: Approved for public release; distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

SPECIFICATIONS

MILITARY

MIL-T-29586(AS) Thermosetting Polymer Matrix, Unidirectional Carbon Fiber Reinforced Prepreg Tape (Widths Up To 60 Inches), General Specification For

(Unless otherwise indicated, copies of federal and military specifications and standards are available from the Standardization Documents Order Desk, Bldg. 4D, 700 Robbins Avenue, Philadelphia, PA 19111-5094.)

2.2 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of the documents which are DOD adopted are those listed in the issue of the DODISS cited in the solicitation. Unless otherwise specified, the issues of documents not listed in the DODISS are the issues of the documents cited in the solicitation.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

ASTM D4473 Measuring The Cure Behavior Of Thermosetting Resins Using Dynamic Mechanical Procedures

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103-1187).

SOCIETY OF AUTOMOTIVE ENGINEERS (SAE)

AMS 3892/10 Tow, Carbon, For Structural Composites, 550(3790) Tensile Strength, 38,000,000 (221) Tensile Modulus

(Application for copies should be addressed to the Society Of Automotive Engineers, 400 Commonwealth Drive, Warrendale, PA 15096-0001).

SUPPLIERS OF ADVANCED COMPOSITE MATERIALS ASSOCIATION (SACMA)

SRM 16 Tow Tensile Testing Of Carbon Fibers

(Application for copies should be addressed to the Suppliers Of Advanced Composite Materials Association, 1600 Wilson Blvd., Suite 1008, Arlington, VA 22209).

2.2 Order of precedence. In the event of a conflict between the text of this document and the reference cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS:

3.1 Matrix resin. The impregnating resin shall be an epoxy, 350°F(177°C) cure, having a continuous service temperature range of -65°F(-54°C) to 250°F(121°C).

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

3.2 Carbon fiber. The carbon fiber reinforcement shall meet the requirements specified in AMS 3892/10 except the tensile properties shall be as specified in Table II when tested in accordance with SRM 16.

TABLE II. Carbon fiber properties

Tensile Modulus Msi (GPa)	Tensile Stress Ksi (MPa)	Tensile Strain %
38 - 44 (262 - 290)	590 min (4,071 min)	1.40 min

3.3 Prepreg physical properties. Prepreg physical properties shall meet the requirements specified in Table III when tested in accordance with MIL-T-29586(AS).

TABLE III. Prepreg Physical Properties

Physical Property	Limits	REQUIREMENTS Nominal Areal Weight		
		95	145	190
Volatile 1/ Content, % by wt. (Max)	Ind. Value Ind. Roll Avg.	2.0 1.5	2.0 1.5	2.0 1.5
Resin Content, % by wt.	Ind. Value Ind. Roll Avg.	31-39 32-38	31-39 32-38	31-39 32-38
Fiber Areal wt., oz/yd^2 (g/m^2)	Ind. Value Ind. Roll Avg.	2.55-2.96 (88-102) 2.61-2.90 (90-100)	4.06-4.35 (140-150) 4.09-4.32 (141-149)	5.37-5.66 (185-195) 5.39-5.63 (186-194)
Gelation 2/ Time,	Maximum Minimum	12 6	12 6	12 6
Flow 3/ Percent	Maximum Minimum	23 13	23 13	23 13
Tack	—	complete adherence	complete adherence	complete adherence

1/ - Volatile weight loss shall be determined after 20 ± 2 minutes exposure to 350 ± 5°F(177 ± 3°C).
2/ - Gel time shall be determined at 350 ± 2°F(177 ± 1°C).
3/ - Platen press temperature and pressure shall be 350 ± 5°F(177 ± 1°C) and 50 ± 3 Psig(345 ± 25 Kpa).

3.4 Prepreg chemical properties. The chemical properties of the prepreg material shall be as specified in MIL-T-29586(AS) when tested as specified in 4.3.1.

3.5 Cured laminated physical properties: The physical properties of the cured laminates shall meet the requirements specified in Table IV when tested in accordance with MIL-T-29586(AS) except where noted otherwise.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

TABLE IV. Cured Laminate Physical Properties

Physical Property	Limits	Requirements Nominal Areal Weights		
		95	145	190
Cured Ply Thickness, inch(cm)	Maximum	0.0040(0.0102)	0.0061(0.0155)	0.0080(0.0203)
	Minimum	0.0034(0.0086)	0.0051(0.0130)	0.0068(0.0173)
	Nominal	0.0037(0.0095)	0.0056(0.0142)	0.0074(0.0188)
Density, lb/ft^3 (g/cm^3)	Maximum	97.5(1.56)	97.5(1.56)	97.5(1.56)
	Minimum	93.7(1.50)	93.7(1.50)	93.7(1.50)
Dry Glass Transition Temp 1/	Minimum	356°F(180°C)	356°F(180°C)	356°F(180°C)
Wet Glass Transition Temperature	----	Not Required	Not Required	Not Required

1/ - The test method in 4.3.2 shall be used for Tg determination in lieu of the method specified in MIL-T-29586(AS).

3.6 Cured laminate mechanical properties: The cured laminate mechanical requirements shall be as specified in Table V when tested in accordance with MIL-T-29586(AS).

TABLE V. Mechanical Properties of Cured Test Laminates

Mechanical Property	TEST TEMPERATURE 1/ 2/	TEST CONDITION 2/	REQUIREMENT	
			MINIMUM ROLL AVERAGE	INDIVIDUAL SPECIMEN REQUIREMENT
0° Ultimate Tensile Strength, Ksi(MPa)	MIN	DRY	300(2070)	280 (1932) Min
	RT	DRY	320(2208)	300 (2070) Min
	HOT	WET	300(2070)	280 (1932) Min
0° Tensile Modulus Msi(GPa)	MIN	DRY	21.0(145)	20.0 - 25.0(138-173)
	RT	DRY	22.0(152)	21.0 - 25.0(145-173)
	HOT	WET	21.0(145)	20.0 - 25.0(138-173)
0° Tensile Strain %	MIN	DRY	1.30	1.25 Min.
	RT	DRY	1.30	1.25 Min.
	HOT	WET	1.30	1.25 Min.
90° Ultimate Tensile Strength Ksi(MPa)	MIN	DRY	4.00(27.6)	3.50 (24.1) Min
	RT	DRY	5.00(34.5)	4.20 (29.0) Min
	HOT	WET	2.50(17.2)	2.15 (14.8) Min
90° Tensile Modulus Msi(GPa)	MIN	DRY	1.30(8.97)	1.10(7.59)Min
	RT	DRY	1.20(8.28)	1.00(6.90)Min
	HOT	WET	1.00(6.90)	0.85(5.86)Min
90 ° Tensile Strain %	MIN	DRY	0.30	0.25 Min
	RT	DRY	0.40	0.35 Min
	HOT	WET	0.30	0.25 Min

1/ - MIN = -65 ± 5°F (-54 ± 3°C), RT = 75 ± 5°F (24 ± 3°C), HOT = 180 ± 5°F (82 ± 3°C), MAX = 250 ± 5°F (121 ± 3°C)

2/ - Specimen conditioning shall be performed in accordance with MIL-T-29586(AS)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

TABLE V. Mechanical Properties of Cured Test Laminates

Mechanical Property	TEST TEMPERATURE 1/ 2/	SPECIFICATION REQUIREMENT		
		TEST CONDITION 2/	MINIMUM ROLL AVERAGE	INDIVIDUAL SPECIMEN REQUIREMENT
Poisson's Ratio	RT	DRY	0.30-0.34	0.26-0.38
0° Ultimate Compression Strength Ksi(MPa)	MIN	DRY	200(1380)	180(1242) Min
	RT	DRY	200(1380)	180(1242) Min
	HOT	WET	150(1035)	135(931) Min
	MAX	DRY	170(1173)	150(1035) Min
0° Compression Modulus Msi(GPa)	MIN	DRY	20.0(138)	19.0(131) Min
	RT	DRY	20.0(138)	19.0(131) Min
	HOT	WET	19.0(131)	18.0(124) Min
0° Thin Short Beam Shear Ksi(MPa)	MIN	DRY	14.0(97)	12.0(83) Min
	RT	DRY	14.0(97)	12.0(83) Min
	RT	FLUIDS	13.0(90)	11.0(76) Min
	HOT	WET	9.0(62)	8.0(55) Min
	HOT	FLUIDS	9.0(62)	8.0(55) Min
0° Thick Short Beam Shear Ksi(MPa)	RT	DRY	12.0(83)	11.0(76) Min
	HOT	WET	9.0(62)	8.0(55) Min
	MAX	DRY	9.0(62)	8.0(55) Min
Compression After Impact Ksi(MPa)	RT	DRY	19.0(131)	18.0(124) Min
Open Hole Compression Ksi(MPa)	RT	DRY	45(310)	40(276) Min
	HOT	WET	38(262)	35(241) Min
	MAX	DRY	40(276)	35(241) Min
Open Hole Tension Ksi(MPa)	MIN	DRY	50(345)	40(276) Min
	RT	DRY	60(414)	50(345) Min
45° Inplane Shear Stress Ksi(MPa)	MIN	DRY	11.0(76)	9.0(62) Min
	RT	DRY	9.0(62)	7.0(48) Min
	HOT	WET	7.0(48)	6.0(41) Min
	MAX	DRY	7.0(48)	6.0(41) Min
45° Inplane Shear Modulus Msi(GPa)	MIN	DRY	0.80(5.52)	0.68(4.69) Min
	RT	DRY	0.70(4.83)	0.60(4.14) Min
	MAX	DRY	0.60(4.14)	0.51(3.52) Min
	HOT	WET	0.50(3.45)	0.43(2.97) Min

1/ - MIN = -65 ± 5°F (-54 ± 3°C), RT = 75 ± 5°F (24 ± 3°C), HOT = 180 ± 5°F (82 ± 3°C), MAX = 250 ± 5°F (121 ± 3°C)
2/ - Specimen conditioning shall be performed in accordance with MIL-T-29586(AS)

3.7 Cure cycle: The material shall be cured as specified in Figure 1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

3.8 Refrigerated storage life conditioning. Refrigerated storage life conditioning shall be a minimum of 1 year exposure to a temperature of 10°F or below, or 90 days to a temperature above 10°F and below 40°F. The material shall be conditioned in its original packaging system. As specified in MIL-T-29586(AS), the material shall meet the handling life and mechanical life requirements in 3.8.1 and 3.8.2 after conditioning. For the 1 year (10°F and below) storage period, the material shall be capable of meeting the handling and mechanical life requirements when time/temperature excursions from this condition are within those specified in Figure 2.

3.8.1 Handling life conditioning. Handling life conditioning shall be a minimum of 500 hours exposure to a temperature of 80 ± 5°F (27 ± 2°C) and a relative humidity of 55 ± 5%. After conditioning, the material shall meet the requirements specified in MIL-T-29586(AS).

3.8.2 Mechanical life (open mold life) conditioning. Mechanical (open mold) life conditioning shall be a minimum of 1000 hours exposure to a temperature of 80 ± 5°F (27 ± 2°C) and a relative humidity of 55 ± 5%. After conditioning, the material shall meet the requirements specified in MIL-T-29586(AS).

4. QUALITY ASSURANCE PROVISIONS.

4.1. Responsibility for inspection. (See MIL-T-29586(AS))

4.2 Classification of inspections. (See MIL-T-29586(AS))

4.3. Test methods.

4.3.1 Prepreg chemical property tests.

4.3.1.1 Infrared test method. The procedure for IR analysis shall be as follows:

> Select a 2-inch by 2-inch minimum prepreg sample. Extract the resin from the prepreg with a suitable solvent and use the decanted fluid to coat a suitable salt crystal (KBr or NaCl) plate. It is permissible to allow the decanted fluid to evaporate under a chemical hood until the viscosity of the dissolved resin becomes thick enough to achieve a coat consistency for salt crystal coating. Do not heat the solution to cause thickening. Apply sufficient resin and allow all solvent to evaporate so that only 10 to 30 percent transmittance is achieved at the highest absorbing peak (usually at a wavelength of 1520 cm^{-1}). The peak height shall remain on the scale. Complete the IR trace using a Perkin-Elmer Model 283, Beckman IR-12 or equivalent analyzer. The analyzer shall be calibrated in accordance with the manufacturer's instructions prior to performing IR analysis.

4.3.1.1.1 Data to be reported. A software package shall be used to generate a correlation coefficient between the baseline IR trace supplied in the original qualification data and the trace generated during quality conformance testing. Unless otherwise specified by the purchaser, the minimum correlation coefficient shall be as specified by the supplier and included in the required qualification data.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

4.3.1.2 HPLC test method. The procedure for HPLC analysis shall be as follows:

a. Procedure for Detector Wavelength Calibration.

(1) Turn on the detector and allow at least 15 minutes for warm-up.

(2) Flush the detector cell with 2 ml of water.

(3) For a single beam detector, adjust the wavelength selector from 220 to 240 nm in the smallest increment indicated and record the detector response.

(4) For a single and double beam detector - flush the detector cell with 2 ml of the aniline standard, adjust the wavelength selector from 220 to 240 nm in the smallest increment indicated, and record the detector response.

(5) For a double beam detector, note the wavelength of the signal maximum directly; for a single beam detector, the water background must be subtracted from the aniline standard to obtain the wavelength of the signal maximum.

(6) Repeat steps (2) through (5) two more times.

b. The wavelength at the signal maximum must be 230 $\pm$ 1 nm. Adjust the wavelength indicator to meet this requirement.

c. Measure the flow rate of each pump separately and also the combination of the two pumps with controller setting at 50% A and 50% B. One procedure for measuring the flow rate is described as follows:

(1) Prime the two pumps with degassed 63/37, CH_3CN/H_2O

(2) Set flow rate at 2 ml/min and measure the time required to fill a 10 ml volumetric flask. Repeat three times, and report the mean time and standard deviation.

(3) The acceptable mean time shall be 300 $\pm$ 15 sec.

d. Test Procedure

(1) Solvents used for sample preparation and mobile phase in HPLC must meet the following purity requirement:

Acetonitrile (CH_3CN) - Baker Analyzed Reagent, HPLC Grade, 9017, or equivalent with maximum UV cutoff at 190 nm.

H_2O - Milli-Q system or equivalent.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

(2) The column shall be calibrated using the following set of parameters.

Sample:	Diethyl pimelate (DEP) 6 percent by volume in acetonitrile
Mobile Phase:	63 Percent CH_3CN/37 percent H_2O
Flow Rate:	1.5 ml/minute
Detection:	UV 220 nm
Injection Volume:	10 microliters 1/
Attenuation:	Peak height of DEP to be between 50 and 100% of full scale.
Chart Speed:	5 cm/minute (2 inches/minute)

1/ If other than 10 microliters injected volume is used, sample concentration should be proportionally adjusted.

(3) Procedure for Column Calibration

A sample of 6 percent DEP is prepared in acetonitrile. Mobile phase (63 percent of CH_3CN 37 percent H_2O) is prepared, filtered, and deareated. Using the above instrument parameters, a 10 microliter aliquot of sample is injected into the column and a chromatogram as illustrated in Figure 3 is obtained.

(4) Determine the column plate count using the 5 sigma method as follows (see Figure 3):

$N(DEP) = \text{column plate count} = 25\ (T/TW)^2$

e. Prepreg Testing

(1) Extract a sample of prepreg with 63:37, CH_3CN:H_2O solvent. Sample concentration should be 3 mg of prepreg/1 ml of solvent. Resin dissolution is ensured by shaking for 10 minutes. The solution is filtered through a 0.5 micron Millipore FH filter or equivalent.

(2) Instrument Parameters

Column:	micro=Bondapak C_{18} Waters 1/ or equivalent.
Mobile Phase:	Premixed 63% CH_3CN/37% H_2O
Flow Rate:	1.5 ml/min.
Injection Volume:	10 microliters 2/
Detection:	UV 220 nm
Attenuation:	0.2 AUFS
Chart Speed:	1 cm/min.

1/ Minimum column plate count requirement N(DEP) 3,500 using 5 sigma method.

2/ If other than 10 microliters injected volume is used, the sample concentration should be proportionally adjusted.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

f. An alternate test method is Gradient B mobile Phase HPLC. Procedures are the same except for the following:

(1) Use 3% DEP for control in d(2) and d(3).

(2) Sample extraction in e(1) should be extract a sample of prepreg with 90:10, CH_3CN: H_2O solvent.

(3) The solution mobile phase in e(2) is as follows:

Mobile Phase Gradient Program

Time(minutes)	Concentration (Balance is H_2O)
0	60% CH_3CN
14	100% CH_3CN 3/
18	100% CH_3CN
20	60% CH_3CN 3/
24	60% CH_3CN

3/ Gradient to be linear

(4) Detection rate in e(2) shall be UV 230 nm.

4.3.1.2.1 Data to be reported. The peak area ratio shall be determine for each type of epoxy, hardener, and catalyst used in the resin system. All ratios shall be reported using the largest hardener peak area as the ratio denominator.

4.3.1.3 RDS test method. A complex viscosity versus time plot shall be generated utilizing the procedure in ASTM D4473. Additional test conditions shall be as follows:

Test Temperature (constant) - 350 ± 2°F
Sample Plates - 50 mm diameter, parallel
Gap Setting - 0.5 mm
Test Time - 15 minutes minimum
Frequency - 10 radians per second
Strain - 50 percent

4.3.1.3.1 Data to be reported. The initial viscosity, minimum viscosity, time to reach minimum viscosity, and time to reach the gel point shall be determined from the generated RDS plot. The gel time shall be determined at the point where the complex viscosity reached 1000 poise.

4.3.2 Glass transition temperature. The glass transition temperature shall be determined using the penetration or flexural method as specified herein. The test shall be performed on three separate specimens. Individual and average values shall be reported.

4.3.2.1 Specimen preparation.

4.3.2.1.1 Penetration method. Specimens for the penetration method shall be taken from the middle area of the thick SBS panel. They shall be approximately 0.25 inch (0.64 cm) in width by 0.25 inch (0.64 cm) in length by the laminate thickness.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

4.3.2.1.2 Flexural method. Specimens for the flexural method shall be taken from the middle area of the thick SBS panel. They shall be approximately 0.05 inch (0.13 cm) in width by 0.25 inch (0.64 cm) in length and one ply thick (middle ply).

4.3.2.2 Test procedure. Using a Perkin-Elmer or Dupont TMA or equivalent with a heating rate of 20°C/min and a probe load of 10 grams, perform the test as specified herein.

4.3.2.2.1 Penetration method. Place the specimen on the quartz platform. The probe shall rest on the side of the specimen (not the peel ply sides) such that it is parallel to the plies. Perform the test until the desired step change is obtained.

4.3.2.2.2 Flexural method. Place the specimen on the edges of the flex platform. The knife edge of the probe shall be parallel to the knife edges of the flex platform and perpendicular to the plies. Perform the test until the desired step change is obtained.

4.3.2.3 Calculation of the transition temperature for TMA methods. The glass transition temperature shall be determined by drawing two tangents to the slopes of the thermogram; one tangent to the baseline and the other tangent to the steepest slope of the curve. The glass transition temperature shall be determined at the interception point of these two tangents (see Figures 4A and 4B for examples).

5. PACKAGING (see MIL-T-29586(AS))

6. NOTES

6.1 Intended use. This material is intended for use in the fabrication of airframe, aerospace, or related primary or secondary load bearing structures where high strength/weight and stiffness is required and the service or design conditions are within -65°F(-54°C) to 250°F(121°C).

6.2 Subject term (keyword) listing.

Carbon/Epoxy
Composite
Graphite/Epoxy
Laminate
Polymer Matrix Composite
Prepreg

Preparing Activity:
Navy - AS
(DOD Project No. CMPS-N067-01)

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

1 - Vacuum leak check the bag as specified in the general specification

2 - Apply 23 inches Hg vacuum (minimum) to bag before applying pressure to the laminate

3 - Vent bag to atmosphere when pressure reaches 20 psig

4 - Pressure shall reach 85 +15/-0 psig before laminate temperature reaches 230F (110C)

5 - Temperature shall be determined based on lagging thermocouple

6 - Heat from room temperature to 355 +/-10F (180 +/-5C) with a heat-up rate of 1-5F/minute (.5-3C/minute). Hold at 355 +/- 10F (180 +/- 5C) for two hours minimum. Cool down using a rate of 1-5F/minute (.5-3C/minute).

7 - Heat up and cool down rates for any thermocouple must be in the specified range when measured in any 15 minute interval.

8 - A minimum heat-up rate of 0.3F/minute (0.2C/minute) is acceptable between 70F (21C) and 100F (38C), and between 335F (168C) and 345F (174C)

9 - Maintaining a constant temperature between 150F (66C) and 220F (104C) is acceptable if the laminate is kept within the limits shown below.

10 - During laminate cool down, release pressure when the laminate temperature is 150F (66C) or less.

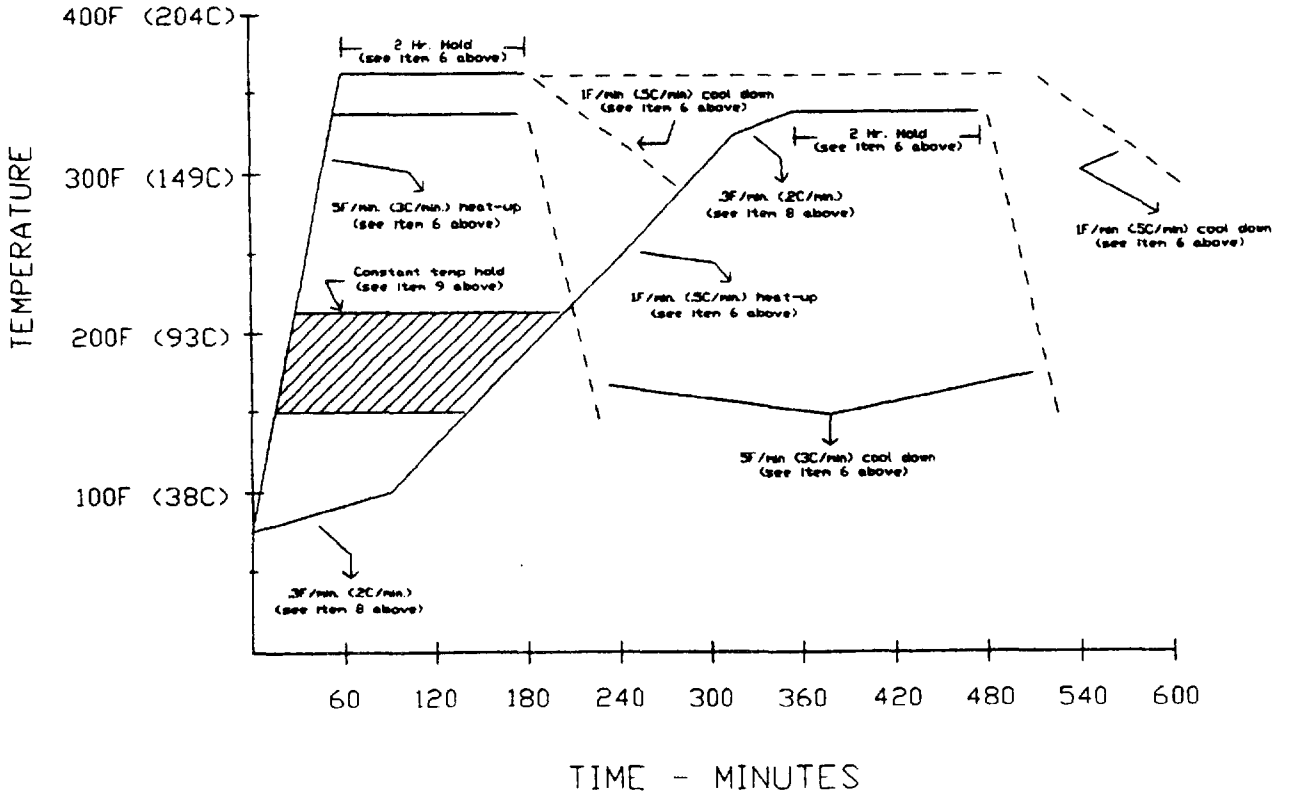


FIGURE 1. Laminate Cure Cycle

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.


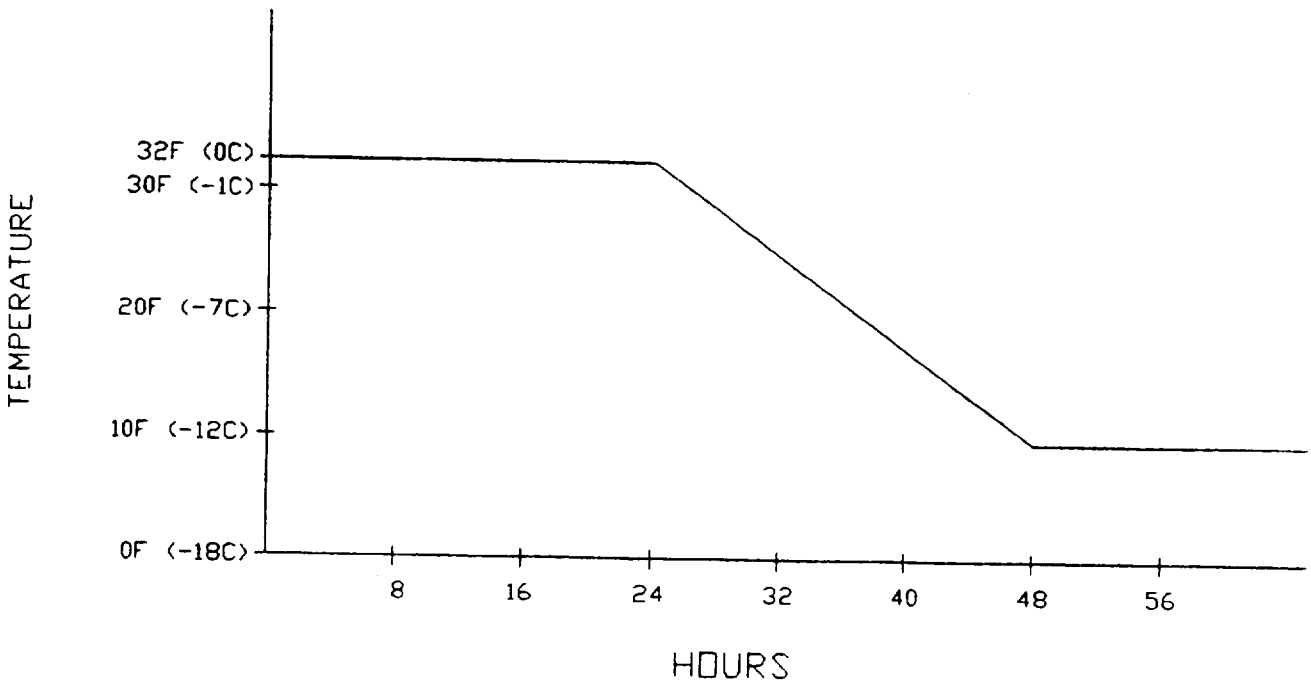


FIGURE 2. Acceptable Time Excursions From the 10°F and Below

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

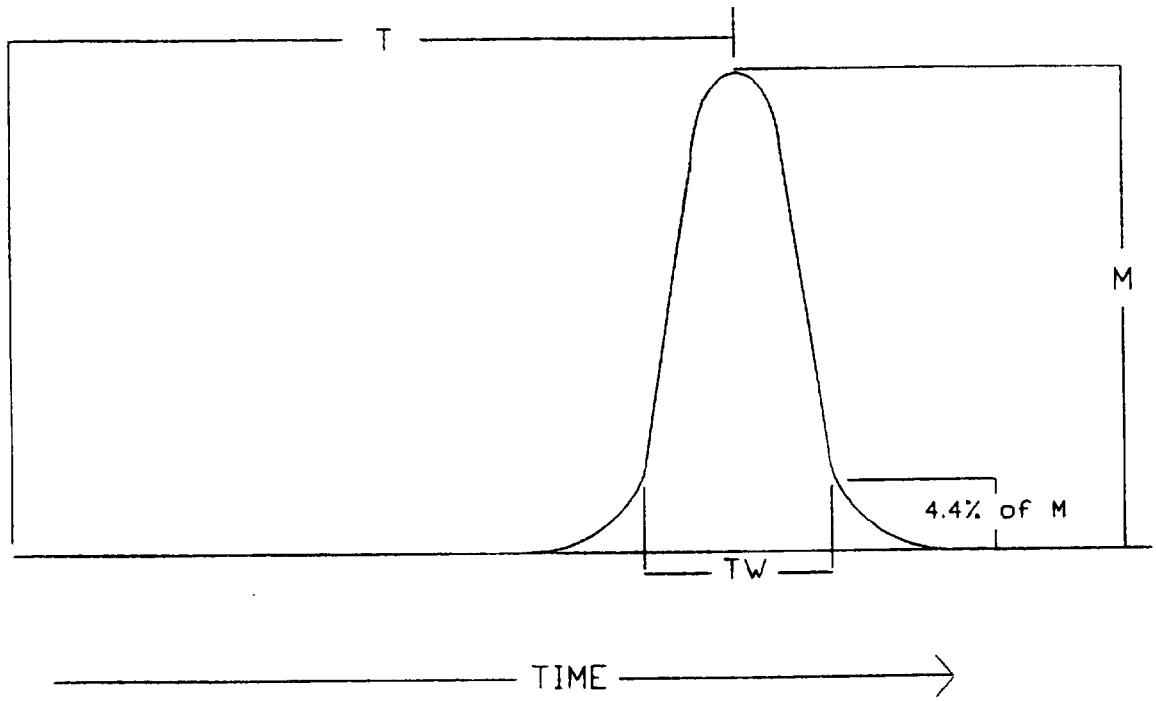


T - Time from initial sample injection to maximum peak height.

TW - Time between 4.4% of the maximum peak height.

M - Maximum peak height.


FIGURE 3. Chromatogram For Column Calibration.

Source: https://assist.dla.mil -- Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.

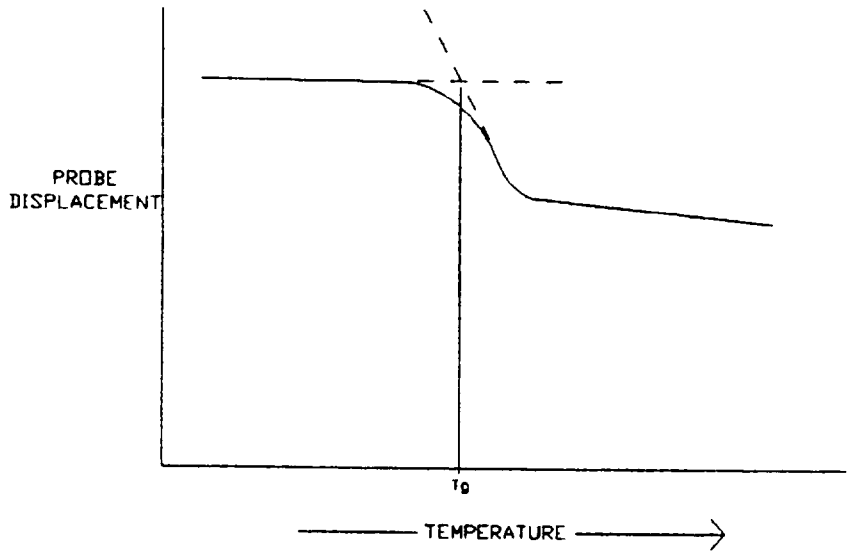

Tg - Glass Transition Temperature

FIGURE 4A. Determination Of Tg For The Flexural Method

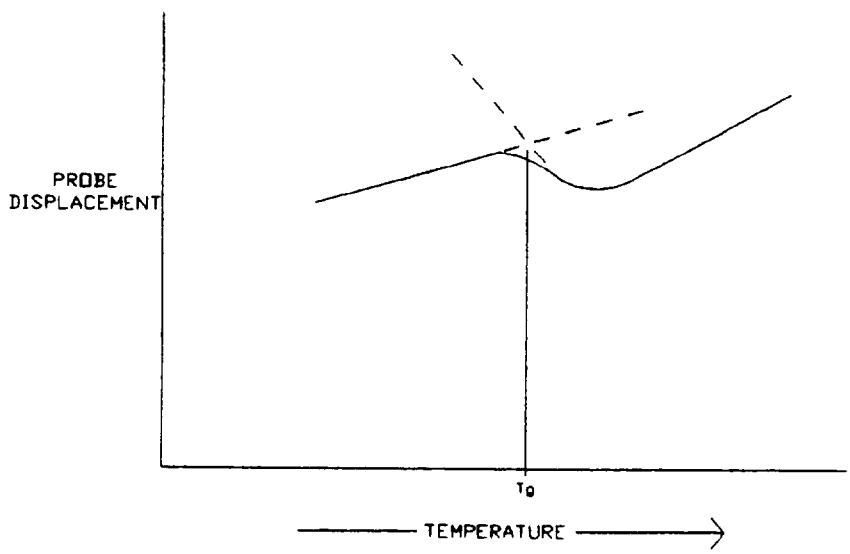

Tg - Glass Transition Temperature

FIGURE 4B. Determination Of Tg For The Penetration Method.

Source: https://assist.dla.mil - Downloaded: 2026-10-21T00:19Z
Check the source to verify that this is the current version before use.