MIL-O-836F
8 September 1986
SUPERSEDING
MIL-O-836E
5 October 1973

MILITARY SPECIFICATION

OVERSHOES, MEN'S, RUBBER, 5 BUCKLE TYPE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for two types of black, medium weight, rubber, five buckle overshoes.

1.2 Classification. The overshoe shall be of the following types and sizes (see 6.2).

Type I - for wear over combat boot
Type II - for wear over dress shoe

Schedule of sizes 5, 6, 7, 8, 9, 10, 11, 12, 13, 14, and 15

Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Officer in Charge, Navy Clothing and Textile Research Facility, 21 Strathmore Road, Natick, MA 01760-2490 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

AMSC N/A FSC 8430

DISTRIBUTION STATEMENT A. Approved for public release, distribution is unlimited.

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the current version before use.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

* 2.1.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of these documents shall be those listed in the Department of Defense Index of Specifications and Standards (DODISS) and supplement thereto, cited in the solicitation.

SPECIFICATIONS

FEDERAL

NN-P-71	- Pallet, Material Handling, Wood, Post Construction, 4 Way Entry
CCC-C-419	- Cloth, Duck, Cotton, Unbleached, Plied-Yarns, Army and Numbered
CCC-C-429	- Cloth, Osnaburg, Cotton
CCC-C-432	- Cloth, Sheeting, Cotton, (Unbleached, and Dyed)

MILITARY

MIL-F-495	- Finish, Chemical, Black for Copper Alloys
MIL-P-15011	- Pallet, Material Handling, Wood, Post Construction, 4 Way Entry
MIL-B-17757	- Boxes, Fiberboard, Corrugated (Modular Sizes)

STANDARDS

FEDERAL

FED-STD-191	- Textile Test Methods
FED-STD-601	- Rubber, Sampling and Testing

MILITARY

MIL-STD-105	- Sampling Procedures and Tables for Inspection by Attributes
MIL-STD-129	- Marking for Shipment and Storage
MIL-STD-147	- Palletized Unit Loads
MIL-STD-284	- Visual Inspection Guide for Rubber Footwear

(Copies of specifications, standards, drawings, and publications required by contractors in connection with specific procurement functions should be obtained from the procuring activity or as directed by the contracting officer.)

* 2.1.2 Other Government documents, drawings, and publications. The following other Government documents, drawings, and publications form a part of this specification to the extent specified herein.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

LAWS AND REGULATIONS

U.S. POSTAL SERVICE MANUAL

(Copies of the manual may be obtained from the Superintendent of Documents, U.S. Government Printing Office, Washington, DC 20402).

2.2 Other publications. The following document(s) form a part of this specification to the extent specified herein. Unless otherwise specified, the issues of documents which are indicated as DoD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. Unless otherwise specified, the issues of documents not listed in the DoDISS shall be the issue of the nongovernment document which is current on the date of the solicitation.

American Society for Testing and Materials

D 1630-61 - Rubber Property - Abrasion Resistance
D 412-80 - Rubber Properties in Tension

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103).

NATIONAL MOTOR FREIGHT TRAFFIC ASSOCIATION, INC., AGENT

National Motor Freight Classification

(Applications for copies should be addressed to the American Trucking Association, ATTN: Traffic Department, 1616 P Street, N.W., Washington, DC 20036).

UNIFORM CLASSIFICATION COMMITTEE, AGENT

Uniform Freight Classification

(Application for copies should be addressed to the Uniform Classification Committee, Room 1106, 222 South Riverside Plaza, Chicago, IL 60606).

2.3 Order of precedence. In the event of a conflict between the text of this specification and the references cited herein, (except for associated detail specifications, specification sheets or MS standards), the text of this specification shall take precedence. Nothing in this specification, however, shall supersede applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 Guide sample. Samples, when furnished, are solely for guidance and information to the contractor (see 6.4). Variations from this specification may appear in the sample in which case this specification shall govern.

* 3.2 First article. When specified, the contractor shall furnish sample unit(s) for first article inspection and approval (see 4.3 and 6.3).

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

3.3 Material.

3.3.1 Fabrics. All fabrics to be coated shall contain not more than 0.003 percent copper and not more than 0.0013 percent manganese. In case of a dispute, the uncoated fabrics shall be tested as specified in 4.4.1. The requirement for seam efficiency shall not apply to cloth conforming to CCC-C-432.

3.3.1.1 Lining fabric.

3.3.1.1.1 Fabric for lining. The lining fabric shall be a cotton jersey (flat) knit having not less than 18 wales and 24 courses per inch, and a minimum weight of 6.5 ounces per square yard. The fabric shall be dyed brown or black and shall have good fastness to water and crocking when tested as specified in 4.4.1.

3.3.1.1.2 Fabric for pocket lining. The pocket lining shall be a cotton jersey (flat) knit fabric having not less than 24 wales and 32 courses per inch, and a minimum weight of 5.0 ounces per square yard. The fabric shall be dyed brown or black and shall have good fastness to water and crocking when tested as specified in 4.4.1.

3.3.1.2 Facing fabric. The fabric for front stay facing shall be a knitted or a woven fabric, dyed black or brown. The knitted fabric shall be a jersey (flat) knit fabric having not less than 24 wales and 30 courses per inch and a minimum weight of 3.5 ounces per square yard, and shall show good fastness to water and crocking when tested as specified in 4.4.1. The woven fabric shall conform to type III, class 2 of CCC-C-432.

3.3.1.3 Fabric for friction front stay. The front stay fabric shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 except that the minimum filling yarns per inch shall be 25.

* 3.3.1.4 Fabric for top pocket reinforcement (optional). The top pocket reinforcement fabric shall be cotton osnaburg cloth conforming to type II, class 3 of CCC-C-429 with a minimum filling yarn of 25 per inch, or cotton sheeting conforming to type VII, class 1 of CCC-C-432 except that the minimum weight per square yard shall be 4.8 ounces and the minimum yarns per inch shall be 47 in the warp and 46 in the filling.

* 3.3.1.5 Fabric for pocket stay. The pocket stay fabric shall be cotton sheeting conforming to type VII, class 1 with a minimum weight of 4.8 ounces per square yard and a minimum yarns per inch of 47 (W) and 46 (F), or type III, class 2 of CCC-C-432, as applicable. As an alternate, the fabric for the pocket stay shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 with a minimum filling yarn of 25 per inch.

* 3.3.1.6 Fabric for insole. The insole fabric shall be cotton sheeting conforming to type VII, class 1 of CCC-C-432 with exceptions noted in 3.3.1.4. As an alternate, the fabric for the insole may be cotton osnaburg conforming to type II, class 3 of CCC-C-429 except that the minimum filling yarns per inch shall be 25.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

3.3.1.7 Fabric for binder sole. The binder sole fabric shall be cotton osnaburg conforming to type II, class 5 of CCC-C-429 or cotton sheeting conforming to type III, class 1 of CCC-C-432 except that the minimum filling yarns per inch shall be 44 and the minimum weight per square yard shall be 3.75 ounces.

3.3.1.8 Fabric for cloth stay, cloth back strip, buckle strap, and buckle stay. The fabric for the cloth stay, cloth back strip, buckle strap, and buckle stay shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 or cotton sheeting conforming to type VII, class 1 of CCC-C-432 with exceptions as noted in 3.3.1.4.

3.3.1.8.1 Fabric for buckle straps (optional). The buckle strap fabric shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 or cotton sheeting conforming to type VII, class 1 of CCC-C-432 with the exceptions noted in 3.3.1.4 or No. 6 medium texture cotton duck conforming to type I of CCC-C-419.

3.3.1.9 Fabric for stiffening counter. The stiffening counter fabric shall be cotton sheeting conforming to type I, class 1 of CCC-C-432.

3.3.1.10 Fabric for cloth heel piece. The cloth heel piece fabric shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 or cotton sheeting conforming to type VII, class 1 of CCC-C-432 with exceptions noted in 3.3.1.4.

* 3.3.1.11 Fabric for inner vamp. The inner vamp fabric shall be cotton sheeting conforming to type VII, class 1 of CCC-C-432 or as an alternate, the fabric for the inner vamp shall be cotton osnaburg conforming to type II, class 3 of CCC-C-429 with the exceptions noted in 3.3.1.4.

3.3.1.12 Cord for buckle straps. The cord used in the construction of buckle straps shall be a twine with a breaking strength of not less than 12 pounds when tested as specified in 4.4.1.

3.3.2 Rubber compounds. The rubber compounds shall be natural rubber, synthetic rubber or a mixture of both.

3.3.2.1 Upper compounds.

3.3.2.1.1 Tensile strength. The tensile strength shall be not less than 1450 pounds per square inch (psi) when tested as specified in 4.4.1. After aging, the tensile strength shall not be less than 75 percent of the original findings.

3.3.2.1.2 Elongation. The ultimate elongation shall be not less than 350 percent when tested as specified in 4.4.1. After aging, the elongation shall not be less than 75 percent of the original findings.

3.3.2.2 Sole and heel compounds. The outsole and heel compound shall be nonmarking when tested as specified in 4.4.1.

3.3.2.2.1 Abrasive index. The sole and heel abrasive index shall be not less than 45. After aging, the abrasive index shall be not less than 75 percent of the original index when tested as specified in 4.4.1.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

3.3.2.2.2 Hardness. The sole and heel hardness shall be 55 (+ 5). After aging, hardness shall be not more than 65 when tested as specified in 4.4.1.

3.3.2.3 Accelerated aging. The test specimen shall be aged in accordance with the procedures of FED-STD-601, test method 7221 for 16 hours at 212°F (+ 2°F).

3.3.3 Cements. The cements and adhesive shall be suitable compounds that prepare or activate the components for vulcanization.

3.4 Components.

3.4.1 Lining. The lining fabric specified in 3.3.1.1.1 shall be coated on one side with lining compound.

3.4.2 Pocket lining. The pocket lining fabric specified in 3.3.1.1.2 shall be coated on one side with lining compound.

3.4.3 Front stay facing (optional). The front stay facing fabric specified in 3.3.1.2 shall be coated or friction coated on one side with lining compound.

3.4.4 Friction front stay. The front stay fabric specified in 3.3.1.3 shall be frictioned on both sides and bias cut.

3.4.5 Top pocket reinforcement (optional). The reinforcement for top of pocket shall be made of two plies of the fabric specified in 3.3.1.4 and shall be frictioned on both sides.

3.4.6 Pocket stay. The pocket stay shall be either cloth or gum type. The cloth pocket stay shall be placed either between the pocket lining and the gum pocket or on the face of the gum pocket. When inserted between the lining and gum pocket, the cloth pocket stay shall be made of type VII, class 1 fabric specified in 3.3.1.5 and frictioned on both sides. When applied to the face of the pocket, the cloth pocket stay shall be made of type III, class 2 fabric specified in 3.3.1.5, dyed black or brown and coated on one side with upper compound. The gum pocket stay shall be made of upper compound or equivalent and shall be not less than 0.020 inch thick. The pocket stay shall reinforce the full width of the pocket at the bottom and shall be correctly centered.

3.4.7 Insole. The insole shall be made of the fabric specified in 3.3.1.6 and shall be calender coated on one side with stiffening compound to an overall thickness of not less than 0.030 inch.

3.4.8 Filler and binder sole. The filler sole shall be made of stiffening compound and the binder sole shall be made of the fabric specified in 3.3.1.7. The fabric shall be frictioned on both sides, or frictioned on one side and coated on the other side with stiffening compound, or frictioned on both sides and coated on one side with stiffening compound to a total thickness of not less than 0.025 inch. The total thickness of the inside bottom parts, including the inner-sole, filler and binder sole combined, shall be not less than 0.125 inch. The filler sole may be deleted providing the binder sole is coated with stiffening compound to a minimum thickness of 0.080 inch.

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

3.4.9 Cloth stay or (optional) cloth back strip. Cloth stay or cloth back strip shall be made of either of the fabrics specified in 3.3.1.8 and shall be frictioned on both sides and calender coated on one side with lining compound to an overall thickness of not less than 0.025 inch. At the option of the contractor, a plain strip made of lining compound and not less than 0.020 inch thick may be substituted for the calender coat.

3.4.10 Stiffening counter. The stiffening counter shall be made of the fabric specified in 3.3.1.9 and shall be frictioned on one side and coated on the other side with stiffening compound to an overall thickness of not less than 0.040 inch, or if stiffening compound only, not less than 0.045 inch. At the option of the contractor, the stiffening counter may be a gum type made of outsole compound not less than 0.050 inch thick.

3.4.11 Cloth heel piece (optional). The cloth heel piece shall be made of either of the fabrics specified in 3.3.1.10 and shall be frictioned on both sides.

3.4.12 Gum upper or gum quarter and vamp. The gum upper or gum quarter and vamp shall be made of upper compound, and shall be plain or engraved and not less than 0.030 inch thick.

3.4.13 Gum pocket. The gum pocket, when used, shall be made of upper compound, and shall be plain or engraved and not less than 0.025 inch thick. If lining is coated to an overall thickness of 0.040 inch, no gum pocket will be required.

3.4.14 Gum back strip (optional). The gum back strip shall be made of upper or outsole compound, shall be plain or engraved and shall be not less than 0.030 inch thick. If a combined heel piece and back strip are used, the gum strip back stays may be omitted.

3.4.15 Gum heel piece. The gum heel piece shall be made of upper compound, shall be plain or engraved, and shall be not less than 0.025 inch thick.

3.4.16 Gum front stay. The gum front stay shall be made of upper compound or equivalent, shall be plain or engraved and shall be not less than 0.030 inch thick.

3.4.17 Inner vamp. The inner vamp shall be either gum or friction type. The gum inner vamp shall be made of upper compound not less than 0.020 inch thick. The friction type shall be made from the fabric specified in 3.3.1.11 and shall be frictioned on both sides. The gum heel piece shall overlap the inner vamp and gum vamp when separate gum vamps are used on the inside and outside shanks of the overshoe.

3.4.18 Composite gum toe cap and toe reinforcement. The toe cap and toe reinforcement shall be made of upper compound, plain or fine knurled, and not less than 0.030 inch thick. The top of the gum toe reinforcement shall rise to a height of approximately 2-3/4 inches above the edge of the lasted overshoe, when measured up over the center of the toe.

3.4.19 Foxing.

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the currentversion before use.

* 3.4.19.1 Calendered soles. The foxing for the type I and type II calendered outsole and heel overshoe shall be made of outsole compound or equivalent, plain or fine knurled, and not less than 0.030 inch thick. The foxing shall extend completely around the bottom edge of the overshoe, shall overlap the toe cap and shall rise to a height of approximately 3/4 inch above the edge of the lasted overshoe. The foxing shall be applied before the outsole and extend under it.

3.4.19.2 Molded Soles. The foxing for the type II molded outsole overshoe shall consist of either a combination of one gum and one friction foxing or two gum foxings.

3.4.19.2.1 Combination. The combination foxing shall consist of the fabric specified in 3.3.1.3, frictioned on both sides and coated on one side with a gum compound to a total thickness of not less than 0.025 inch thick. The friction foxing shall extend completely around the bottom of the shoe and shall rise to a height of not less than 3/4 inch from the bottom of the sole. The gum foxing shall be made of gummed compound not less than 0.040 inch thick and shall extend completely around the edge of the sole or shall extend from breast of heel to breast of heel and shall rise not less than 7/8 inch from the edge of sole.

3.4.19.2.2 Gum (two). When two gum foxings are used, the first gum foxing shall be of gum compound not less than 0.025 inch thick applied under the outsole and shall rise to a height of not less than 7/8 inch above the bottom edge of the outsole and shall extend from breast of heel to breast of heel around the toe. The second gum foxing shall be of gum compound not less than 0.040 inch thick applied outside the outsole and shall rise to a height of not less than 5/8 inch above the bottom edge of the outsole and shall extend completely around the bottom of overshoe.

3.4.20 Outsole and heel.

* 3.4.20.1 Type I - Calendered. The outsole and heel shall be made of sole and heel compounds (see 3.3.2.2) which shall be calendered into a design suitable for shipboard use. The outsole shall be corrugated and cleated (chevron type) of the contractor's own design which shall be approved by the contracting officer (see 6.2). The outsole thickness shall be 0.215 inch at the ball and 0.315 inch thick at the back part of the heel and shall be oversize, bumper-edge type, with extension heel and shall be placed over the foxing and secured thereto.

* 3.4.20.2 Type II - Molded. The type II molded outsole shall be made of sole and heel compounds (see 3.3.2.2) which shall be molded into a design conforming in general appearance and dimensions to figure 1. The design shall be approved by the contracting officer (see 6.2). The minimum thickness of the outsole shall be 0.250 inch.

3.4.20.2.1 Sole welt. The type II molded outsole shall have a sole welt made of outsole compound a minimum of 0.080 inch thick and 3/8 inch wide, and shall extend completely around the upper edge of the outsole. The sole welt may be either molded into the outsole or applied separately.

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the currentversion before use.

* 3.4.20.3 Type II Calendered. The type II calendered outsole and heel shall be made of sole and heel compounds (see 3.3.2.2) which shall be calendered into a design suitable for shipboard use. The design shall be corrugated and cleated (chevron type) of the contractor's own design, and shall be approved by the contracting officer (see 6.2). The outsole thickness shall be not less than 0.215 inch thickness at the ball and not less than 0.315 inch thick at the back part of the heel.

3.4.21 Gum top bind. The gum top bind shall be made of outsole compound or equivalent, a minimum of than 0.030 inch thick and 5/16 inch wide. The bind may be plain or engraved.

3.4.22 Buckles. The buckles shall be of ladder and clasp type and the size commercially known as No. 3. Ladders and clasps shall be made from cold-rolled sheet, or strip carbon steel. Ladders shall be 0.022 inch to 0.025 inch thick, clasps shall be 0.029 to 0.034 inch thick for body and tongue. Ladders shall be approximately 1-5/8 inches long by 5/8 inch wide and shall have five tongue slots and one buckle strap slot. The tongue slots shall be approximately 3/8 by 1/8 inch and buckle strap slot 1/2 by 1/8 inch. The clasp, including tongue and body, shall be approximately 1-1/2 inches in length when open and 1 inch when closed. The tongue shall be approximately 11/64 inch and the body approximately 23/32 inch wide at their narrowest points. The body shall have one strap buckle slot approximately 17/32 by 1/8 inch. Ladders and clasps shall be attached to the front edges of the quarters by a buckle strap, set between the gum quarter and cloth buckle stay cover at die points. The outside quarters shall carry five clasps and the inside quarters five ladders.

* 3.4.22.1 Finish. The ladders and clasps shall be given a surface finish consisting of electroplated zinc followed by phosphating and drying, then coated with a black enamel. The coating shall level out to a dry, uniform film without objectionable orange peel, wrinkles, drips, streaks, no film or area of thin film, and shall show no corrosion when tested as specified in 4.4.1. As an alternate, the surface finish may be a black chemical finish in accordance with MIL-F-495 and lacquered or epoxy resin coated, or a black enamel finish with a minimum of two coats.

3.4.23 Buckle straps. Buckle straps shall be made of either of the fabrics specified in 3.3.1.8 or 3.3.1.8.1 and shall be frictioned on both sides. Buckle straps shall be folded and shall include two reinforcement cords specified in 3.3.1.12, placed inside the strap, one cord at each edge. The folded strap shall be not less than 3/8 inch in width. Alternately, the buckle strap without cord may be placed on a combination gum buckle stay and strap cover. Buckle straps that deviate in any respect from the requirements specified above, shall require the approval of the contracting officer.

3.4.24 Buckle stay covers.

3.4.24.1 Cloth The cloth buckle stay covers shall be made of either of the fabrics specified in 3.3.1.8 and shall be frictioned on both sides. The cloth buckle stay cover shall be either one piece, full length, or separate pieces that firmly secure each buckle strap to the quarter. As an alternate, the buckle stay cover may be of one piece, full length, made of upper compound not less than 0.030 inch thick.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

3.4.24.2 Gum. The gum buckle stay covers shall be made of upper compound, plain or engraved and not less than 0.020 inch thick. The gum buckle stay cover shall overlap the cloth buckle stay cover and shall be firmly secured to the cloth buckle stay cover and gum quarters. The gum buckle stay cover shall be either one piece full length or separate pieces. When cloth buckle stay cover is coated, no gum buckle stay cover is required.

3.4.25 Pocket opening. The pocket opening shall start at a point 4 (+ 1/2) inches above the top edge of the outsole (measured up over the center of the toe) and extend in a straight line to the top of the overshoe, for size 10, with other sizes graded up or down consistent with grading of lasts.

3.5 Design. The overshoes specified herein shall be five-buckle with a semi-blucher throat opening. The insole shall be regular fabric coated type. The outsole shall be either cleated or nonslip in design.

3.5.1 Figures. Figures 1 and 2 are furnished for information purposes only. To the extent of any inconsistencies between the specification and the figures, the specification shall govern.

3.5.2 Molds. The molds used to produce the applicable style overshoes shall be furnished by the government.

3.6 Patterns. Before commencing production, the contractor shall submit patterns for approval by the contracting officer (see 6.2).

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the currentversion before use.

3.7 Construction. The overshoes shall be constructed in accordance with approved patterns and lasts utilizing recognized commercial methods. All overlapped parts shall be substantially rolled or pressed before vulcanization.

3.7.1 Replacement of defective components. During the cutting and manufacturing process, components having material defects or damages that are classified as defects in 4.4.2.1 shall be removed from production and replaced with non-defective and properly matched components.

3.7.2 Lasts. The lasts shall be provided by the Contractor and approved by the Contracting Officer. The lasts shall conform to the requirements shown in table I and figure 2. The surface of the last shall be smooth, clean and free from any protrusions. All measurements and tolerances are expressed in inches.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

TABLE I. Last dimensions in inches

Type I

SIZE	5	6	7	8	9	TOLERANCE: (±)
A. Waist (Girth)	11-9/16	11-13/16	12-1/16	12-5/16	12-9/16	1/4
B. Ball	11-3/8	11-5/8	11-7/8	12-1/8	12-3/8	1/4
C. Ankle	11	11-1/4	11-1/2	11-3/4	12	1/4
D. Choke	16-5/8	17	17-3/8	17-6/8	18-1/8	1/4
E. Leg (14 inches up)	13-3/4	14	14-1/4	14-1/2	14-3/4	1/4
F. Ball width	4-4/12	4-5/12	4-6/12	4-7/12	4-8/12	1/8
G. Toe spring	1-11/64	1-12/64	1-13/64	1-14/64	1-15/64	1/8
H. Toe depth (1-1/2 inches back)	1-31/32	2	2-1/32	2-2/32	2-3/32	1/8
I. Length of bottom (L.O.B)	10-10/12	11-2/12	11-6/12	11-10/12	12-2/12	1/8

TABLE I. Last dimensions in inches

Type I (cont'd)

Size	10	11	12	13	14	15	Tolerance (±)
A.	12-13/16	13-1/16	13-5/16	13-9/16	13-13/16	14-1/16	1/4
B.	12-5/8	12-7/8	13-1/8	13-3/8	13-5/8	13-7/8	1/4
C.	12-1/4	12-1/2	12-3/4	13	13-1/4	13-1/2	1/4
D.	18-1/2	18-7/8	19-2/8	19-5/8	20	20-3/8	1/4
E.	15	15-1/4	15-1/2	15-3/4	16	16-1/4	1/4
F.	4-9/12	4-10/12	4-11/12	5	5-1/12	5-2/12	1/8
G.	1-1/4	1-17/64	1-18/64	1-19/64	1-20/64	1-21/64	1/8
H.	2-1/8	2-5/32	2-6/32	2-7/32	2-8/32	2-9/32	1/8
I.	12-6/12	12-10/12	13-2/12	13-6/12	13-10/12	14-2/12	1/8

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

TABLE I. LAST DIMENSIONS IN INCHES

Size	Type II 5	6	7	8	9	Tolerance: (±)
A. Waist (Girth)	11	11-1/4	11-1/2	11-3/4	12	1/4
B. Ball	10-7/8	11-1/8	11-3/8	11-5/8	11-7/8	1/4
C. Ankle	10-1/2	10-3/4	11	11-1/4	11-1/2	1/4
D. Choke	15-7/8	16-1/4	16-5/8	17	17-3/8	1/4
E. Leg (14 inches up)	13-1/4	13-1/2	13-3/4	14	14-1/4	1/4
F. Ball width	4-1/12	4-2/12	4-3/12	4-1/12	4-5/12	1/8
G. Toe spring	1-3/64	1-4/64	1-5/64	1-6/64	1-7/64	1/8
H. Toe depth (1-1/2 inches back)	1-27/32	1-28/32	1-29/32	1-28/32	1-31/32	1/8
I. Length of bottom (L.O.B.)	10-10/12	11-2/12	11-6/12	11-10/12	12-2/12	1/8

TABLE I. Last dimensions in inches

Type II (Cont'd)

SIZE	10	11	12	13	14	15	Tolerance (±)
A.	12-1/4	12-1/2	12-3/4	13	13-1/4	13-1/2	1/4
B.	12-1/8	12-3/8	12-5/8	12-7/8	13-1/8	13-3/8	1/4
C.	11-3/4	12	12-1/4	12-1/2	12-3/4	13	1/4
D.	17-3/4	18-1/8	18-1/2	18-7/8	19-1/4	19-5/8	1/4
E.	14-1/2	14-3/4	15	15-1/4	15-1/2	15-3/4	1/4
F.	4-1/2	4-7/12	4-8/12	4-9/12	4-10/12	4-11/12	1/8
G.	1-1/8	1-9/64	1-10/64	1-11/64	1-12/64	1-13/64	1/8
H.	2	2-1/32	2-2/32	2-3/32	2-4/32	2-5/32	1/8
I.	12-6/12	12-10/12	13-2/12	13-6/12	13-10/12	14-2/12	1/8

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

3.7.3 Vulcanization. The overshoes shall be vulcanized under pressure and there shall be neither blisters nor air pockets in the seams and all parts shall be cured into a single unit.

3.7.4 Leakage. After vulcanization, the overshoes shall show no leakage when tested as specified in 4.4.3.1.

3.7.5 Finish. The overshoes shall have a natural heater finish.

3.7.6 Color. The color of the overshoes shall be black.

3.7.7 Height. The overshoes shall be 13-1/2 (+ 3/8) inches high for size 10 with contractor's grading between sizes. The height of the overshoes shall be measured inside at the back.

3.8 Identification.

3.8.1 Size marking. The size of each overshoe shall be incised or branded on the outsole in the shank near the breast of the heel, using figures not less than 1/2 inch high. Alternatively, on type II overshoes, the size may be pin stamped at the top edge of the back strip. The size and the letters U.S. shall be stamped with indelible ink in a contrasting color using figures and letters not less than 1/2 inch high on the pocket or leg lining, approximately 1 inch below the top of the overshoe.

3.8.2 Contractual data. The name of the contractor, contract number, and date shall be legibly stamped or printed with indelible ink in a contrasting color on the leg lining or pocket lining near the top of the overshoe. Letters and figures shall be not less than 1/4 inch high.

3.8.3 Labeling. The manufacturer's labels may be used when desired. The labels shall be not more than 1-1/2 inches in diameter, and not more than one label shall be used in each overshoe.

3.9 Workmanship. The overshoes shall be clean, well finished and thoroughly waterproof, and shall conform to the quality and grade of product established by this specification. The occurence of defects shall not exceed the applicable acceptable quality levels.

4. QUALITY ASSURANCE PROVISIONS

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the currentversion before use.

4.1 Responsibility for inspection. Unless otherwise specified in the contract, the contractor is responsible for the performance of all inspection requirements as specified herein. Except as otherwise specified in the contract or order, the contractor may use his own or any other facilities suitable for performance of the inspection requirements specified herein, unless disapproved by the Government. The Government reserves the right to perform any of the inspections set forth in the specification where such inspections are deemed necessary to assure supplies and services conform to prescribed requirements.

4.1.1 Responsibility for compliance. All items must meet all requirements of sections 3 and 5. The inspection set forth in this specification shall become a part of the contractor's overall inspection system or quality program. The absence of any inspection requirements in the specification shall not relieve the contractor of the responsibility of assuring that all products or supplies submitted to the Government for acceptance comply with all requirements of the contract. Sampling in quality conformance does not authorize submission of known defective material, either indicated or actual, nor does it commit the Government to acceptance of defective material.

4.1.2 Certificate of compliance. Where certificates of compliance are submitted, the Government reserves the right to check test such items to determine the validity of the certification.

4.2 Classification of inspection. The inspection requirements specified herein are classified as follows:

1. First article inspection (see 4.3).
2. Quality conformance inspection (see 4.4).

4.3 First article inspection. The first article submitted in accordance with 3.2 shall be inspected as specified in 4.4.2 for compliance with design, construction, workmanship and dimensional requirements.

4.4 Quality conformance inspection. Sampling for inspection shall be performed in accordance with MIL-STD-105, except where otherwise indicated.

4.4.1 Component and material inspection. In accordance with 4.1 above, components and materials shall be tested in accordance with all the requirements of referenced specifications, drawings, and standards unless otherwise excluded, amended, modified, or qualified in this specification or applicable procurement documents. In addition, a certificate of compliance shall be furnished for the composition of rubber compound of 3.3.2, and the buckle's material identification and finish of 3.4.22 and 3.4.22.1. Testing shall be performed on components and materials listed in table II for the characteristics shown. The determinations made on a sample unit for test purposes as specified in the applicable test methods. All test reports shall contain the individual values utilized in expressing the final result. The inspection level for all test characteristics of each compnent, except for the rubber compounds, shall be S-1. For all components, the acceptable quality level (AQL) for all test characteristics that are applicable to the sample unit requirements shall be 4.0 defects per hunded units. An AQL is not

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the currenversion before use.

applicable to lot average requirements. For each type of rubber compound, the sample unit shall be a composite of the rubber prepared in the form indicated below. A lot of a rubber compound shall consist of the amount of rubber compound that is produced or compounded in one day. The composite test sample of rubber shall be vulcanized in the same manner employed in the manufacture of the overshoe and the test unit (sample unit) shall consist of the number of pieces formed to the dimensions as follows:

(a) Upper compound - two pieces 6 inch by 6 inch by 0.10 inch.
(b) Outsole and heel compound - two pieces 6 inch by 6 inch by 0.250 inch.

There shall be no failure to meet the lot average requirements as specified.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

TABLE II. Material tests

Component and lot size expressed in terms of	Characteristic	Requirement para	Test method	Requirements applicable to: Sample unit	Requirements applicable to: Lot average	No. determinations per sample unit	Results reported as: Pass or fail	Results reported as: Numerically to nearest	Sample unit
Knitted cotton fabrics lining, pocket lining and front stay facing) (1 yd full width each)	Wales/inch		5070 1/	X	--	5	--	1.0 wale	1 yard full width
	Courses/inch		5070 1/	X	--	5	--	1.0 course	
	Weight	3.3.1.1.1, 3.3.1.1.2, and 3.3.1.2	5041 1/	X	--	5	--	0.1 oz/sq yd	
	Colorfastness to water		5630 1/	X	--	1	X	-------	
	Colorfastness to dry crocking		5651 1/	X	--	3	X	-------	
	Colorfastness to wet crocking		5651 1/	X	--	3	X	------	
	Copper content	3.3.1	2053 1/ 2/	X	--	2	--	.001%	
	Manganese content	3.3.1	2053 1/ 2/	X	--	2	--	.0001%	
Woven fabrics (1 yd full width)	Copper content	3.3.1	2053 1/ 2/	X	--	2	--	.001%	1/4 yd full width
	Manganese content	3.3.1	2053 1/ 2/	X	--	2	--	.0001%	
Reinforcement cord (gross yards)	Breaking strength	3.3.1.12	6016 1/	X	--	10	--	0.5 lb	8 yds
Rubber compound (batch)	Chemical composition	3.3.2	2/	--	--	--	--	--	--

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

TABLE II. Material tests (Cont'd)

Component and lot size expressed in terms of	Characteristic	Requirement para	Test method	Requirements applicable to: Sample unit	Requirements applicable to: Lot average	No. determinations per sample unit	Results reported as: Pass or fail	Results reported as: Numerically to nearest	Sample unit
Upper compound (batch)	Tensile strength initial	3.3.2.1.1	D412-8 4/	--	X	3	--	10 psi	
	Elongation initial	3.3.2.1.2	D412-8 4/	--	X	3	--	5 percent	(see 4.4.1)
	Tensile strength after accelerated aging	3.3.2.1.1	D412-8 4/5/	--	X	3	--	10 psi	
	Elongation after accelerated aging	3.3.2.2	D412-8 4/5/	--	X	3	--	5 percent	
Sole and heel compounds (batch)	Nonmarking	3.3.2.2	4.4.4.3	X	--	1	X	--	
	Abrasive index, initial	3.3.2.2.1	D1630-61 4/	--	X	3	--	Index unit	
	Abrasive index, after accelerated aging	3.3.2.2.1	D1630-61 4/5/	--	X	3	--	Index unit	(see 4.4.1)
	Hardness, initial	3.3.2.2.2	3021 3/5/	--	X	5	--	Whole scale reading	
	Hardness after accelerated aging	3.3.2.2.2	7221 3/ 3021 3/	--	X	5	--	Whole scale reading	
Buckles (1 gross)	Material identification	3.4.22	2/	--	--	--	--	--	--
	Finish	3.4.22.1	2/	--	X	--	--	--	--
	Corrosion	3.4.22.1	4.5.1	X	--	--	X	--	5 buckles

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

TABLE II. Material tests (Cont'd)

Note: Samples of fabrics to be submitted for testing shall not processed with rubber compound. Sample of rubber compounds to be submitted for testing shall be vulcanized in the same manner as finished overshoes.

1/ FED-STD-191.

2/ A Certificate of Compliance shall be submitted and will be acceptable for stated requirement.

3/ FED-STD-601.

4/ Refer to ASTM Standard

5/ Paragraph 3.3.23 defines the aging procedure.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

4.4.1.1 In-process inspection. Inspection shall be made at any point during any phase of manufacture to assure compliance with all operations and processes which cannot be determined in the completely fabricated overshoe. The Government reserves the right to exclude from consideration for acceptance any lot for which in-process inspection has indicated non-conformance.

4.4.2 Examination of the end item.

4.4.2.1 Visual examination. The visual inspection of the finished overshoe shall be conducted in accordance with the defects listed in tables I and II of MIL-STD-284 and with defects listed in table III. The sample unit shall be one overshoe and the lot size shall be expressed in terms of one overshoe. The selection shall be made in pairs. The inspection level and AQL shall be as indicated in 4.4.2.2.

TABLE III. Classification of defects

Defect	Classification Major	Minor
Contractual data or "U.S." markings omitted, incorrect, illegible or misplaced		X
Size marking omitted, incorrect, illegible or misplaced	X	
Color of lining materials not as specified		X
Air pocket or channel in any seam	X	
Poor or uneven lasting affecting serviceability	X	
Poor or uneven lasting affecting appearance		X
Any ladder or clasp (buckle) omitted, misplaced, damaged, or malformed interfering with proper functioning	X	
Dimension of any component other than specified		X
Height of overshoe less than specified		X
Height of lettering and figures of size marking and contractual data less than specified		X
Diameter of contractor's label larger than specified (if applicable)		X

4.4.2.2 Acceptable quality levels and inspection levels. The inspection levels and acceptable quality levels (AQL's) expressed in defects per hundred units shall be as follows:

	Inspection level	AQL
For defects listed in 4.4.2.1 and Table III		
Major Defects	II	2.5
Total Defects (major and minor combined)	II	10.0

4.4.3 Testing of the end item.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

4.4.3.1 Leakage testing. The overshoes shall be tested for leakage in accordance with the requirements in 3.7.4. The test method shall be as specified in 4.4.4.2. The sample unit shall be one overshoe and the lot size shall be expressed in units of one overshoe. Requirements are applicable to the individual unit. The inspection level shall be S-3 and the AQL shall be 2.5 defects per hundred units.

4.4.4 Test methods. Wherever applicable, tests shall be conducted in accordance with FED-STD-191, FED-STD-601, and the ASTM Handbook and as specified in table III.

4.4.4.1 Corrosion resistance test. The specimen of complete buckle (ladder and clasp) shall be tested for corrosion resistance specified in 3.4.22.1 by submerging in a boiling, 10 percent (by weight) aqueous solution of sodium chloride for a period of 15 minutes. The specimen upon being removed from this solution shall be immediately immersed in a 10 percent (by weight) aqueous solution of sodium chloride at room temperature. The specimen shall be removed from this solution and without having the adhering liquid wiped off, allowed to dry for 24 hours at room temperature. The specimen shall then be rinsed in lukewarm water and allowed to dry. On inspection, the specimen shall show no sign of corrosive action having occurred.

4.4.4.2 Leakage test. Overshoes shall be tested for leakage requirements specified in 3.7.4 by inserting a hose or pipe connected to a source of compressed air of 1 pound per square inch pressure well down into the overshoe. The top of the overshoe shall be closed in a manner to prevent the escape of air and the overshoe shall then be immersed to within 3 inches of the top in a tank of water. Evidence of leakage, will be indicated by bubbles of air that form and rise to the surface of the water.

4.4.4.3 Nonmarking. A corner of the stock shall be drawn with moderate pressure across a sheet of bond paper. If the mark made can be easily erased by rubbing with the fingers, the compound being tested shall be considered a nonmarking compound.

4.4.5 Examination of packaging requirements. An examination shall be made to determine that the packaging, packing and marking comply with the section 5 requirements. The sample unit shall be one shipping container fully prepared for delivery with the exception that it need not be closed. Defects of closure listed below shall be examined on shipping containers fully prepared for delivery. The lot size shall be the number of shipping containers in the end item inspection lot. The inspection level shall be S-2 and the AQL shall be 2.5 defects per 100 units in accordance with MIL-STD-105.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

Examine	Defect
Marking (exterior)	Omitted; incorrect; illegible; of improper size, location, sequence or method of application.
Materials	Any component missing, damaged, or not as specified.
Workmanship	Inadequate application of components, such as incomplete closure of container flaps, loose strapping, inadequate stapling or improper taping.
	Bulged or distorted container.
Contents	Number of items per container is more or less than required.
	Not packaged as specified.

4.4.6 Palletization examination. An examination shall be made to determine that the palletization complies with the section 5 requirements. Defects shall be scored in accordance with the list below. The sample unit shall be one palletized unit load fully packaged. The lot size shall be the number of palletized unit loads in the end item inspection lot. The inspection level shall be S-1 and the AQL, expressed in terms of defects per hundred units, shall be 6.5 in accordance with MIL-STD-105.

Examine	Defect
Finished dimensions	Length, width, or height exceeds specified maximum requirements.
Palletization	Pallet pattern not as specified. Interlocking of loads not as specified. Load not bonded with required straps as specified.
Weight	Exceeds maximum load limits.
Marking	Omitted, incorrect,illegible,of improper size, location, sequence, or method of application.

5. PACKAGING

5.1 Preservation Packaging. Packaging shall be level A or C as specified (see 6.2).

5.1.1 Level A. Each pair of overshoes shall be tied together at the top with cotton twine inserted through the buckles.

5.1.2 Level C. Overshoes shall be packaged to afford adequate protection against damage during shipment from the contractor to the first receiving activity. The package and the quantity per package shall be the same as that normally used by the contractor for retail distribution.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

5.2 Packing. Packing shall be level A, B, or C as specified (see 6.2).

5.2.1 Level A. Ten pair of overshoes of one type and size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled, closed, and reinforced conforming to class weather-resistant, grade V2s, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class weather-resistant, variety DW, grade V15c of MIL-B-17757. Level A packages shall be arranged as specified in 5.2.1.1. Each container shall have the contents completely covered on the top and bottom, and between each layer of overshoes, with a sheet of commercial grade kraft paper. Toward the end of the contract or when there are less than the required amount per container of the same size, mixed sizes of one type only may be packed within the same shipping container.

5.2.1.1 Packing arrangement. The overshoes shall be placed in a shipping container in the following manner:

a. Place a bottom layer of 3 pairs of overshoes in the container, with the upper portion of the overshoes folded over and the heels and soles facing up, with the back of the heels touching one side panel.

b. Place a middle layer of 4 pairs of overshoes on their sides, with the heels of the overshoes touching the opposite side panel.

c. Complete the pack by placing a top layer of 3 pairs of overshoes in the container in the same manner as the bottom layer.

5.2.2 Level B. Ten pairs of overshoes of one type and size only, packaged as specified in 5.1, shall be packed in a fiberboard shipping container assembled and closed conforming to type CF, class domestic, variety DW, grade 275, size 3A of MIL-B-17757. The fiberboard for the box liner shall conform to type CF, class domestic, variety DW, grade 275 of MIL-B-17757. Level A packages shall be arranged as specified in 5.2.1.1. Each container shall have the contents completely covered on the top and bottom, and between each layer of overshoes, with a sheet of commercial grade kraft paper. Toward the end of the contract or when there are less than the required amount per container of the same size, mixed sizes of one type only may be packed within the same shipping container.

5.2.3 Level C. Overshoes, packaged as specified in 5.1, shall be packed in a manner to insure carrier acceptance and safe delivery at destination at the lowest transportation rate for such supplies. The quantity per shipping container shall be the same as that normally used by the contractor for retail distribution. Containers shall be in accordance with Uniform Freight Classification Rules or National Motor Freight Classification Rules, as applicable.

5.3 Palletization. When specified (see 6.2) item packed as specified shall be palletized on a 4-way entry pallet in accordance with load type 1A of MIL-STD-147. Each prepared load shall be bonded with primary and secondary straps in accordance with bonding means C, K, and L or O or P. Pallet pattern shall be in accordance with the appendix of MIL-STD-147.

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

The pallet shall be 4-way, Type IV, V or VIII, Class 1, Style A, Size 2, wood group I, II, III or IV, Grade A of NN-P-71, or 4-way, Style 1, Size A, Type I, Class 1 of wood group I, II, III, or IV, Grade A of MIL-P-15011. Interlocking of loads shall be effected by reversing the pattern of each course. If the container is of a size which does not conform to any of the patterns specified in MIL-STD-147, the pallet pattern used shall be approved by the contracting officer.

5.4 Marking. In addition to any special marking required by the contract or order, shipping containers shall be marked in accordance with MIL-STD-129.

5.4.1 Labels, mixed sizes. Each shipping container packed with mixed sizes of one type only, shall have securely attached to the end and side, directly under the printing or stenciling, a white paper label 5 by 4 inches, with the words "MIXED SIZES" plainly printed or stamped thereon and under these words shall be legibly printed or stamped the correct quantity and sizes contained therein.

6. NOTES

* 6.1 Intended use. The overshoes are intended to be worn by military personnel for the following uses:

Type I - Over combat boot for land use.
Type II - Over dress shoes/safety footwear for shipboard use

* 6.2 Ordering data. Procurement documents should specify the following:

(a) Title, number and date of this specification.
(b) Types and sizes required (see 1.2).
(c) Requirements for submission of outsole and heel for approval of design (see 3.4.20).
(d) Approval of patterns (see 3.6).
(e) Selection of applicable levels of packaging and packing required (see 5.1 and 5.2).
(f) When palletization is required (see 5.3).
(g) When a first article inspection is required, the item will be tested.

6.3 First Article. When a first article inspection is required, the item will be tested and should be a first article sample. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examination, quantity, and testing, and approval of the first article.

* 6.4 Samples. For access to samples, address the procuring office issuing the invitation for bids.

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

6.5 Changes from previous issue. The margins of this specification are marked with an asterisk to indicate where changes (additions, modifications, corrections, deletions) from the previous issue were made. This was done as a convenience only and the Government assumes no liability whatsoever for any inaccuracies in these notations. Bidders and contractors are cautioned to evaluate the requirements of this document based on the entire content irrespective of the marginal notations and relationship to the last previous issue.

6.6 Subject term (key word) listings:

Buckle, five
Footwear
Protection, feet
Rubber

Custodian:
Navy - NU
Army - GL
Air Force 99

Review Activity:
DLA - CT
Army - MD

User activities:
Navy - CG, MC

Preparing Activity:
Navy - NU
Project No. 8430-0336

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

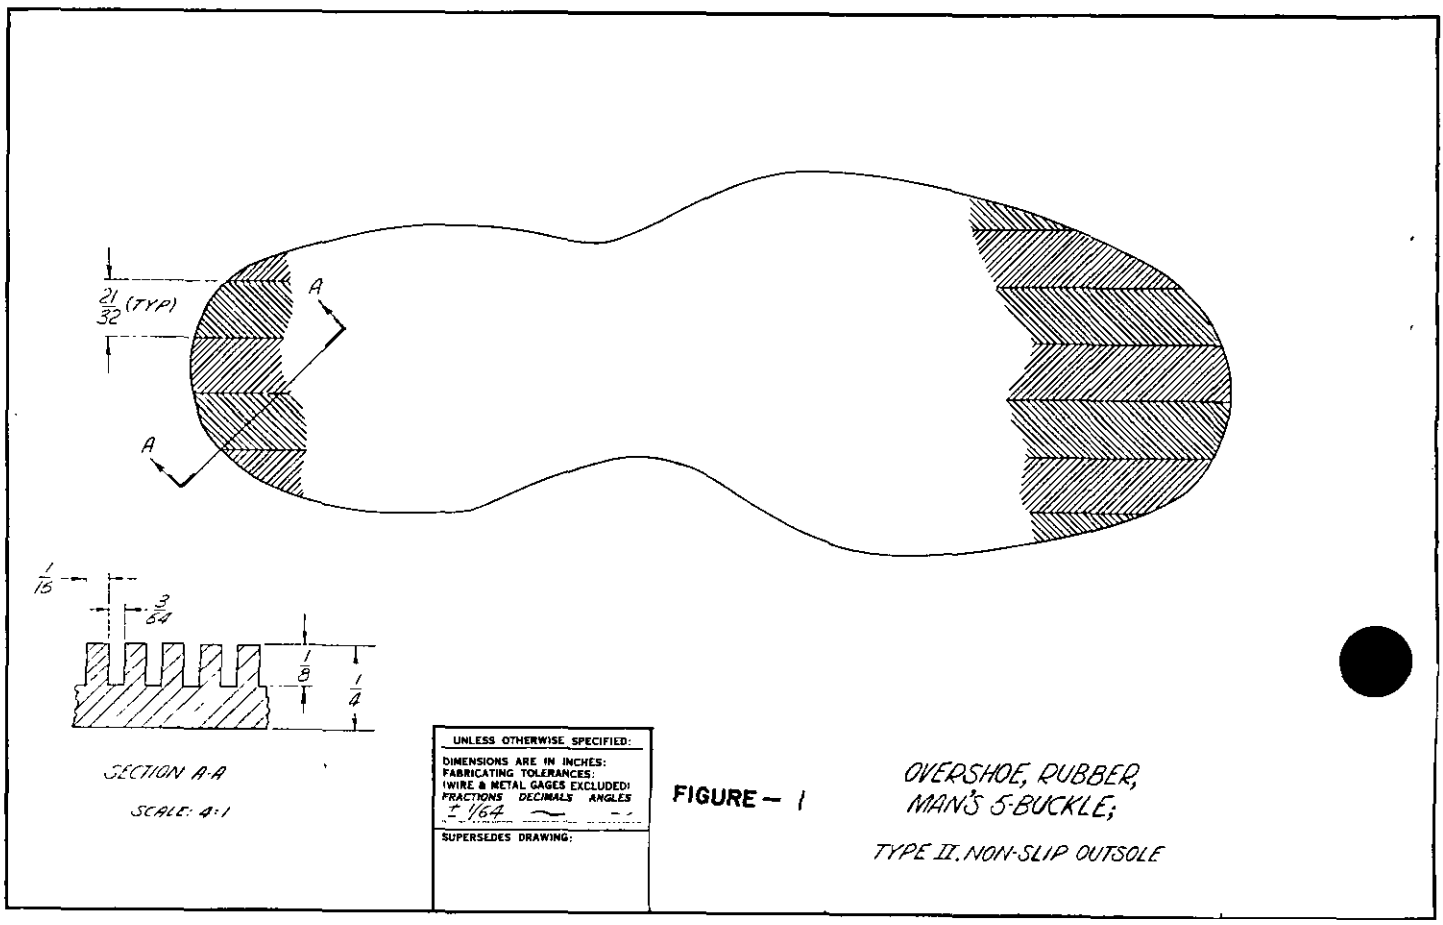


FIGURE – 1

OVERSHOE, RUBBER, MAN'S 5-BUCKLE;

TYPE II. NON-SLIP OUTSOLE

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.

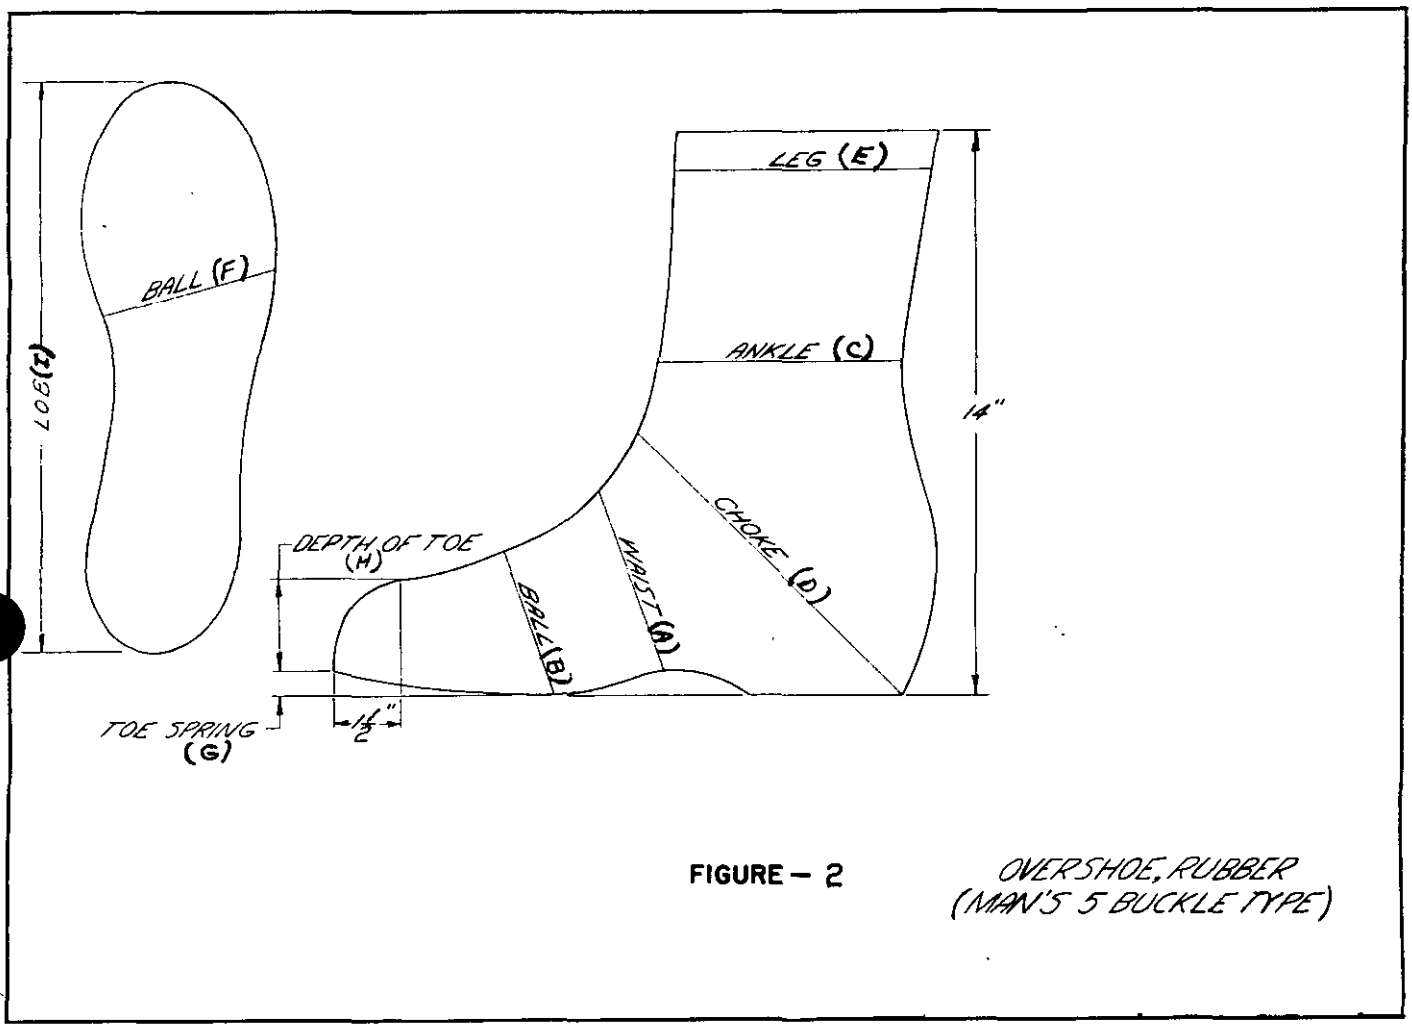


FIGURE – 2 OVERSHOE, RUBBER (MAN'S 5 BUCKLE TYPE)

Source: https://assist.dla.mil -- Downloaded: 202640-16T11:33Z
Check the source to verify that this is the current version before use.

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge *(DO NOT STAPLE)*, and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.

NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document*(s)* or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE $300

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Officer in Charge
Navy Clothing and Textile Research Facility
21 Strathmore Road (Code 50)
Natick, MA 01760-2490

Source: https://assist.dla.mil -- Downloaded: 202610-16T11:33Z
Check the source to verify that this is the current version before use.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions – Reverse Side)

1. DOCUMENT NUMBER	2. DOCUMENT TITLE
MIL-O-926F	OVERSHOE, MEN'S, RUBBER, 5 BUCKLE TYPE

3a. NAME OF SUBMITTING ORGANIZATION	4. TYPE OF ORGANIZATION *(Mark one)*
	☐ VENDOR
	☐ USER
b. ADDRESS *(Street, City, State, ZIP Code)*	☐ MANUFACTURER
	☐ OTHER *(Specify)*: _____

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER *(Last, First, MI)* – Optional	b. WORK TELEPHONE NUMBER *(Include Area Code)* – Optional
c. MAILING ADDRESS *(Street, City, State, ZIP Code)* – Optional	8. DATE OF SUBMISSION *(YYMMDD)*

DD FORM 82 MAR 1426 PREVIOUS EDITION IS OBSOLETE.

Source: https://assist.dla.mil -- Downloaded: 2026-10-16T11:33Z
Check the source to verify that this is the current version before use.